

### (CODE) (PAGES) (NASA CT. OR TMX OR AD NUMBER) (CATEGORY)

### FABRICATION OF ONE SILICON-GERMANIUM THERMOELECTRIC TEST UNIT

RC	A
DIRECT E	

		GPO PRICE	\$ _	
FINAL	REPOR	CFSTI PRICE	S) <b>\$</b> _	
		Hard copy (	HC)_	2.00
		Microfiche (	MF) _	.50

ff 653 July 65

This work was performed for the Jet Propulsion Laboratory, California Institute of Technology, sponsored by the National Aeronautics and Space Administration under Contract NAS7-100.

### PREPARED FOR:

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION
JET PROPULSION LABORATORY
CALIFORNIA INSTITUTE OF TECHNOLOGY
4800 OAK GROVE DRIVE
PASADENA, CALIFORNIA - 91103

Order No.951136





### FABRICATION OF ONE

### SILICON-GERMANIUM THERMOELECTRIC TEST UNIT

FINAL REPORT

AUGUST 31, 1965

ORDER NO. 951136

The objective is the fabrication of a thermoelectric test unit which can be used to evaluate the performance of silicon-germanium thermocouples and modules.

This work was performed for the Jet Propulsion Laboratory, California Institute of Technology, sponsored by the National Aeronautics and Space Administration under Contract NAS7-100.

PREPARED BY

APPROVED BY

R. C. Fortin

G. M. Rose, Manager Thermoelectric Device Development

RADIO CORPORATION OF AMERICA
SPECIAL ELECTRONICS COMPONENTS DIVISION
DIRECT ENERGY CONVERSION DEPARTMENT
THERMOELECTRIC PRODUCTS ENGINEERING
HARRISON, NEW JERSEY

### TABLE OF CONTENTS

		Page
I.	Summary	1
II.	Introduction	2
III.	Test Unit Description	12
IV.	Operation and Performance	26
٧.	Conclusions	41

### FINAL REPORT

### FABRICATION OF ONE SI-GE THERMOELECTRIC TEST UNIT

### I. SUMMARY

RCA has fabricated one thermoelectric test unit to aid the Jet Propulsion Laboratory in assessing the applicability of silicon-germanium thermoelectric power conversion to their space power needs.

The unit was designed to feature versatility in adaptation to a sufficient variety of test conditions within the device process and materials limitations to illustrate the application of silicon-germanium thermoelectric couples and modules to practical power conversion devices.

The normal variations associated with engineering fabrication of a one-of-a-kind device will result in a unit which may exhibit the usual degree of variability to be expected from a laboratory product.

It consists of four, six-couple modules intended for high temperature radiative coupling to a heat source. These modules are arranged in two pairs on opposite sides of each of two planar, graphite ribbon heaters operating at power inputs up to 300 watts at EH = 20 volts and IH = 15 amperes, approximately. The graphite heater has long life when operated in vacuum at pressures of 1 x 10-5 Torr or less. A variety of cold junction temperatures may be secured through thermal coupling adjustments between module radiators and a fluid cooled heat exchanger. Process and materials requirements permit operation over a range of hot junction temperatures to  $900^{\circ}\text{C}$  and cold junction temperatures to  $371^{\circ}\text{C}$ .

Provision is included for monitoring temperatures of cold and hot junctions, radiator, heat exchanger outlet, frame and base mount through use of chromelalumel thermocouples. An inconel sheathed couple design is used at the hot junction to extend its life and accuracy while operating in the immediate vicinity of the high temperature and metallurgically active constituents of the silicon-molybdenum alloy hot shoe.

The completed unit was subjected to a life test through six thermal cycles spanning 330 hours of operation. The conditions selected permitted operation at maximum hot junction temperature, maximum  $\Delta$  T capability and near maximum heater input. The performance observed reached the levels expected with average power output of 1.05 watts per couple. The test duration of 330 hours brought the unit through approximately 75% of the expected initial characteristic adjustment toward ultimate stability under the conditions used.

### II. INTRODUCTION

Under Contract No. NAS7-100, Order No. 951136 RCA was to fabricate a silicon-germanium thermoelectric test unit for the Jet Propulsion Laboratory. The unit was intended as an aid in determining the applicability of silicon-germanium power modules to the requirements of space power systems. To best achieve this purpose a design was selected which would enable operation over a range of conditions encompassing those most likely to occur in practical power conversion applications. Provision for determining major performance characteristics resulting from selected operating conditions was included. The results obtained could then be extended to aid in predicting performance of silicon-germanium thermoelectric devices when included as a power source in an overall space system.

### A. General Features

The SiGe thermoelectric test unit was designed for laboratory determination of the thermoelectric characteristics of silicon-germanium alloys in practical thermocouple and modular configurations. Provisions were made for maximum test plan variety through test point access to each power thermocouple and temperature measurement thermocouple, and through a wide range of heater inputs and methods of securing a wide variety of cold junction temperatures. The unit size was selected to fit into the usually available sizes of laboratory vacuum test chambers. General design features may be seen from reference to Figures 1 and 2.

### Major physical characteristics are:

Weight - 3000 gms (6.6 lbs) - approx.

Height -13-3/4 inches - approx.

Width - 7 inches - approx.

Depth - 8 inches - approx.

Total

### Test Points for which access will be provided are:

Individual couple	32
Heater input	4
Module temp. measurement couples	24
Frame & Exchanger temp. couples	6
	-

66

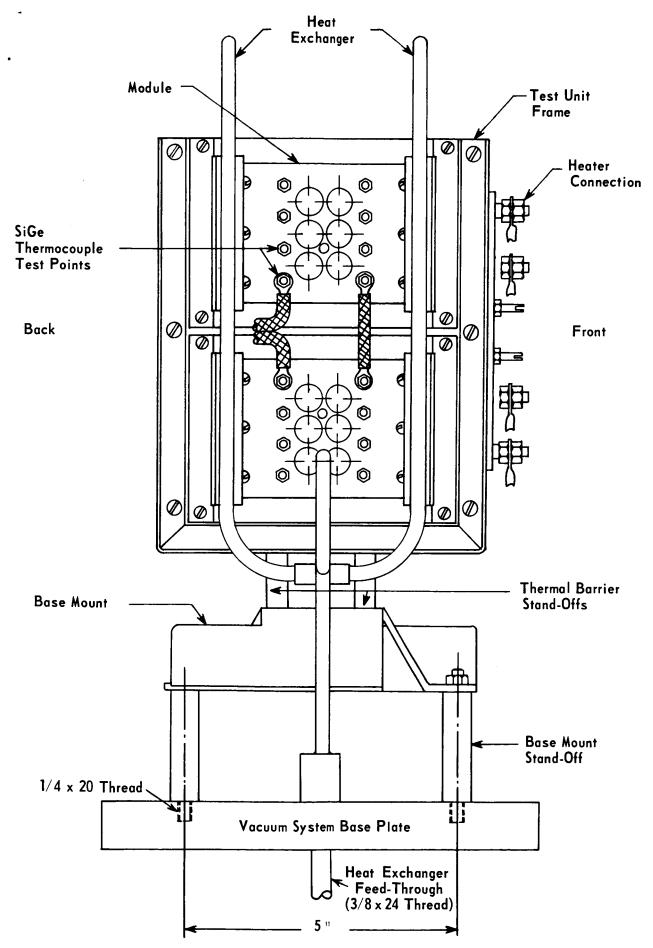


FIGURE 1 - TEST UNIT ASSEMBLY - LEFT SIDE VIEW

RCA-DEC. 8-31-65

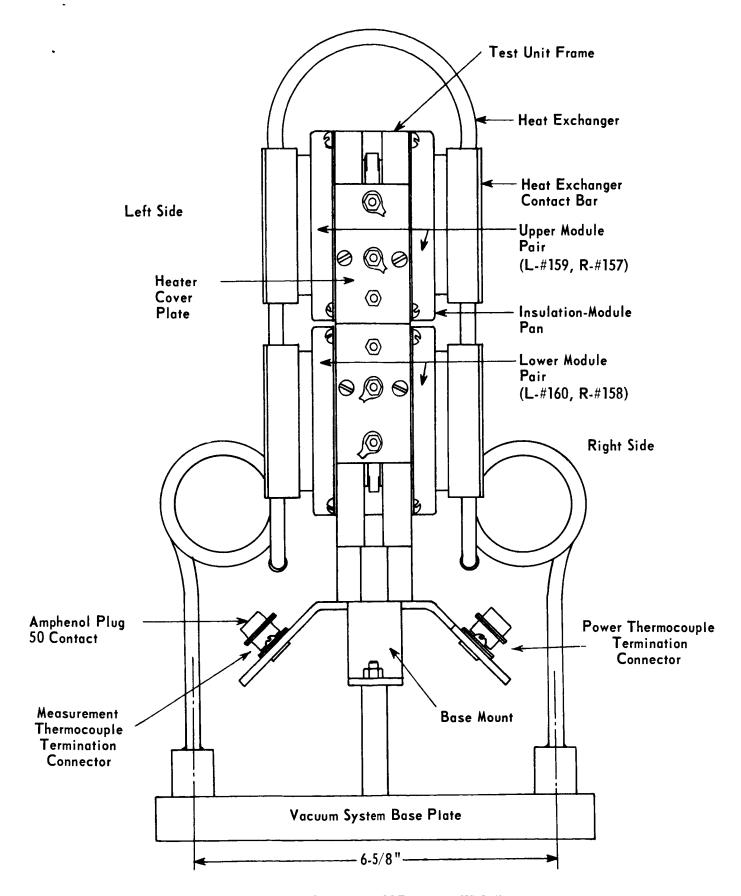


FIGURE 2 - TEST UNIT ASSEMBLY - FRONT VIEW

The base mount was designed to support the unit structure through 2 inch copper standoff spacers to be fastened directly to the vacuum chamber base plate or base-plate adaptor. Figure 3 indicates the position and size of the mounting holes required to give proper registry between the heat exchanger and the test unit base mount. If the unit is to be mounted directly upon the test chamber base plate, allowance should be made for the vacuum seal dimensions associated with the heat exchanger feed-throughs so that proper assembly registry may be maintained. The heat exchanger feed-throughs are  $2\frac{1}{2}$  inches long at the 3/8" outside diameter and are threaded at 24threads per inch for 2 inches. All wiring with the exception of the heater leads and power module output leads are terminated in two (2), Amphenol, 50 contact, quick disconnect, miniature, diallyl phthalate body (glass filled per MIL-M-19833, type GD1-30) connectors located on wings provided at the base mount. Facing the front of the test unit (front defined as that face containing the heater connections) all power module terminations appear at the connector on the right side and all measurement thermocouple terminations appear at the connector on the left side. Also on the left side are the heater terminations. The heat exchanger outlet is on the right and to this side is located the outlet temperature thermocouple.

Figure 4 identifies the power couple and module test points in terms of the right-hand connector pin numbers. Figure 5 is a schematic representation of the power couple, module and test point locations for the complete test unit just as they appear on the test unit. Couple test points are given the connector pin numbers at which they terminate. Couple interconnecting straps are shown in dashed outline very much as they would appear could the inside of the radiator plate be observed. Each element of each power thermocouple is identified by an "N" or "P". Both couple numbers and module numbers are scribed on the radiator plate of each module. Figure 6 shows the power module interconnection arrangement used in wiring the test unit. This wiring is terminated at two ceramic stand-off insulators located on the right-hand base mount apron.

Figure 7 identifies all measurement thermocouples with indicated polarity in terms of the left hand connector pin numbers.

In total there are twenty-six terminations associated directly with the thermoelectric power couples and modules, thirty terminations for the measurement thermocouples and two terminals for the heater. For complete instrumentation a minimum of fifty-eight (58) separate wires must be carried through the vacuum chamber base plate. In addition, water inlet and outlet feed-throughs must be provided. The module test frame is isolated thermally from the base mount by four (4) one inch ceramic stand-off insulators. This reduces heat losses from the units under test and permits the base mount and connectors to operate at near room temperatures. The test frame is designed to accommodate two heater and module pair assemblies in fixed registry, one above the other. Provision is made for


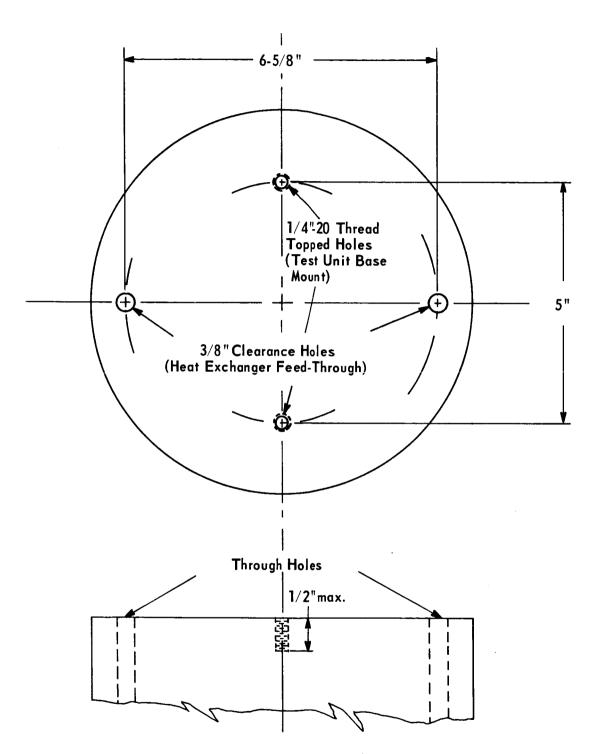


FIGURE 3 VACUUM BASE PLATE MOUNTING HOLE LOCATIONS

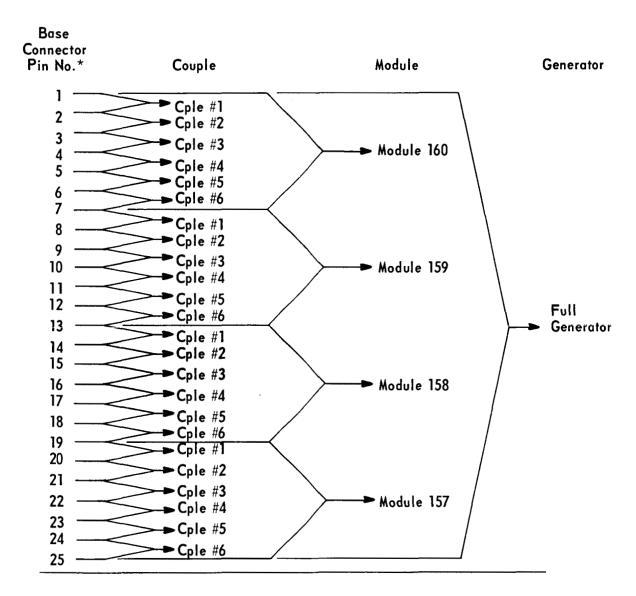

<sup>\*</sup> Note: When facing heater leads the connector containing the Power Thermocouple terminations appears on the right hand apron of the base mount. The generator power take-off terminations are located on this same apron.

FIGURE 4 POWER THERMOCOUPLE MEASUREMENT CONNECTIONS JPL-MODEL-T.D.-65-201


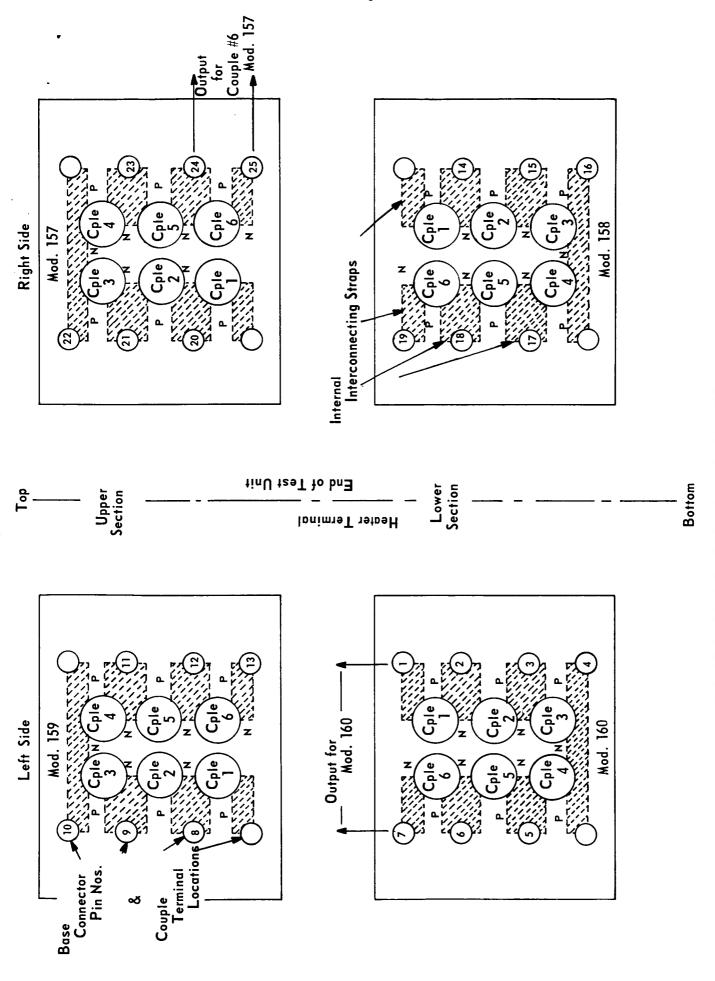


FIGURE 5 MODULE INTERNAL INTERCONNECTION DIAGRAM.

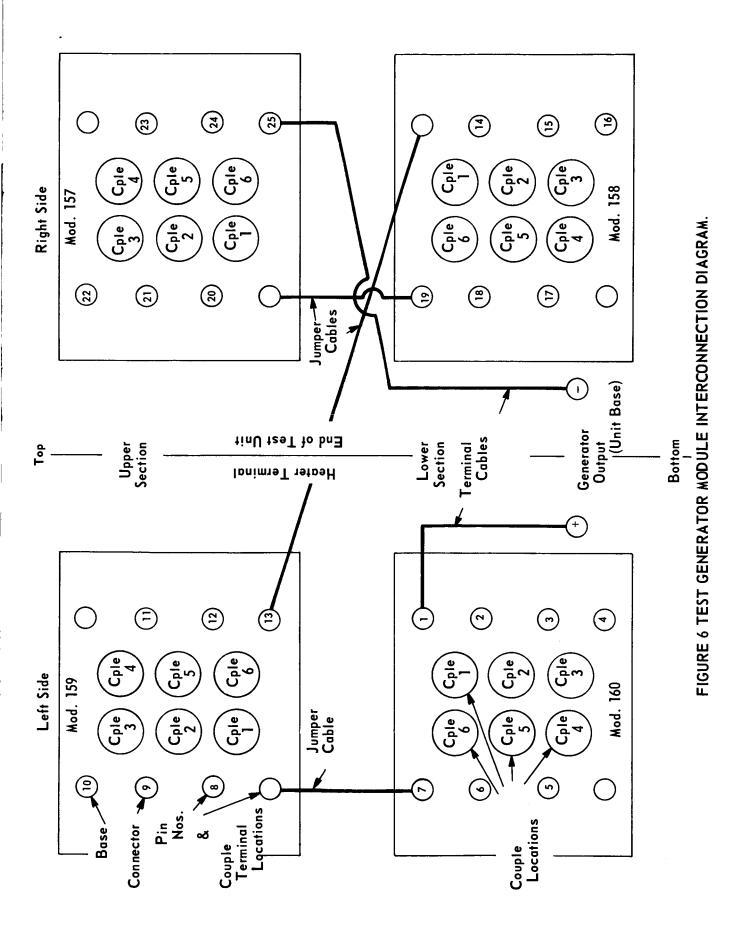

Base Connector

No.	Polarity	Position
1 — 2 —	—— P -	→ Hot Shoe - Module 159 (Couple #2)
3	—— Р ·	Hot Shoe - Module 160 (Couple #5)
5 — 6 —	P .	→ Hot Shoe - Module 157 (Couple #5)
7 — 8 —	——— P ·	Hot Shoe - Module 158 (Couple #2)
9 — 10 —	——— Р ·	Cold Shoe - Module 159 (Couple #2)
11 — 12 —	——— Р ——— N	Cold Shoe - Module 160 (Couple #2)
13 — 14 —	P N	Cold Shoe - Module 157 (Couple #2)
15 — 16 —	P N	Cold Shoe - Module 158 (Couple #2)
17 —	N	Open
18 - 19 -	P N	Radiator - Module 159
20 — 21 —	P N	Radiator - Module 160
22 - 23 -	—— P	Radiator - Module 157
24 <i>-</i> 25 <i>-</i>	——— Р ——— N	Radiator - Module 158
26 – 27 –	P N	Test Unit Mid-Frame
28 – 29 –	——— P	Base Mount (at Measurement TC Connector)
30 - 31 -	——— Р ——— N	Heat Exchanger Outlet

<sup>\*</sup> Note: When facing the heater leads the connector containing the Measurement Thermocouple terminations appears on the left hand apron of the base mount. The heater input terminations are located on this same apron.

FIGURE 7 MEASUREMENT THERMOCOUPLE CONNECTIONS JPL-MODEL-T.D.-65-201

removal, replacement or adjustment of modules or heaters without disturbance to any other portion of the test unit assembly.

The heat exchanger is a separate assembly which may be fastened directly to the module radiator wings or removed entirely, depending upon the cold junction temperatures desired.

Both the heat exchanger and test frame and base mount assembly were designed for proper registry when mounted upon the same base plane.

### III. TEST UNIT DESCRIPTION

### A. Test Unit Frame

The module test frame is made of aluminum angle and bar stock. Channels are milled in the heater support bars which are also fitted with stops for positive and precise location of each heater. Connections to each heater are made outside the heater cover plates which may be removed separately for individual heater replacement or adjustment.

The insulated module pan assemblies are fastened to the frame on opposite sides of each heater and consist of an aluminum pan to which the module radiator is fastened in such a manner as to form the bottom of the pan. The couples then appear surrounded by the walls of the pan and separated from them by Dyna Quartz insulation to the level of the hot shoe.

### B. Base Mount

The base mount is made of aluminum formed to support the Amphenol connector bodies and to fasten to the vacuum chamber base stand-offs. The mounting holes are set on 5-inch centers. Copper stand-offs are provided of proper height to maintain registry with the heat exchanger when both assemblies are direct mounted to the same vacuum system base plate. Thermal isolation between the module test frame and the base mount is maintained through the use of four, 1-inch ceramic stand-offs. This reduces conduction heat losses from the modules under test.

### C. Heat Exchanger

The heat exchanger is made of Monel tubing terminated in copper feed-through fittings located on 6-5/8 inch centers. Copper contact bars are brazed to the tubing in the proper positions for fastening to the module radiator wings. Adjustment of the radiator temperature is achieved through changes in conduction coupling between the radiator wings and the heat exchanger contact bars. This can be accomplished through the interposition of thermal resistance between radiator wings and heat exchanger in the form of shims or washers of varied material, number, conducting area, and thickness while maintaining a constant fluid flow and temperature. This method provides the condition of greatest cold junction temperature uniformity amongst the test modules regardless of their location between inlet and outlet terminations of the heat exchanger. The test unit as designed will give temperature adjustment capability, by this method, from the 371°C maximum permitted by the module structure, down to approximately 150°C with 20°C water at approximately ten gallons per hour. Reference to Figures 1 and 2 will clarify details of the heat exchanger design.

### D. Heater

The heater is designed to provide a uniform, planar heat source having extended life up to temperatures of 1500°K while operating in pressures of 10-5 Torr or less. The heating element is made of ½ inch woven graphite ribbon. For the six-couple module, source temperature uniformity is secured through use of a heater design utilizing two graphite ribbon legs mounted in one plane and connected, electrically, in series. Within the generator and module rating limitations, the full range of thermal test conditions will require individual heater inputs of from 200 to 300 watts approximately. Typical current-voltage requirements for each heater will range from approximately 12.5 amperes and 16 volts to 15 amperes and 20 volts. With the two heaters connected in series, this range would appear as 12.5 amperes and 32 volts to 15 amperes and 40 volts, approximately. Major features of the heater structure can be seen in Figure 8. In the event of heater replacement, the heater-to-module frame orientation instruction must be followed.

### E. Silicon-Germanium Thermoelectric Module

The average couple weight for this test unit design is 8.3 grams. This includes a completely bonded assembly of an N-type and a P-type silicongermanium alloy thermoelement, a silicon alloy hot shoe and two tungsten cold shoes. Constructional and dimensional details are presented in Figure 9.

Each module, without thermal shunt insulation, but otherwise completely assembled, including six couples, thermal stress compensation, electrical interconnecting straps and test terminals, electrical insulators, and a radiator base plate weighs approximately 226 grams.

Reference to Figure 10 will disclose the major structural and dimensional features of the test module design.

The recommended maximum operating values for hot and cold junction temperatures are 900°C and 371°C respectively. These values arise from considerations of structure, thermal stress compensation, and electrical heater design rather than from silicon-germanium limitations. Utilizing water at approximately 20°C the practical minimum cold junction temperature will run about 150°C. Thus the maximum practically obtainable couple temperature differential is 750°C for this test unit. However, a maximum temperature differential for this thermocouple design is set at 900°C.

The principal thermoelectric properties of the silicon-germanium alloy used in this test unit design are shown in Figures 11 and 12 (Seebeck Coefficient), Figures 13 and 14 (Electrical Resistivity), and Figures 15 and 16 (Thermal Resistivity). Physical properties appear from the following

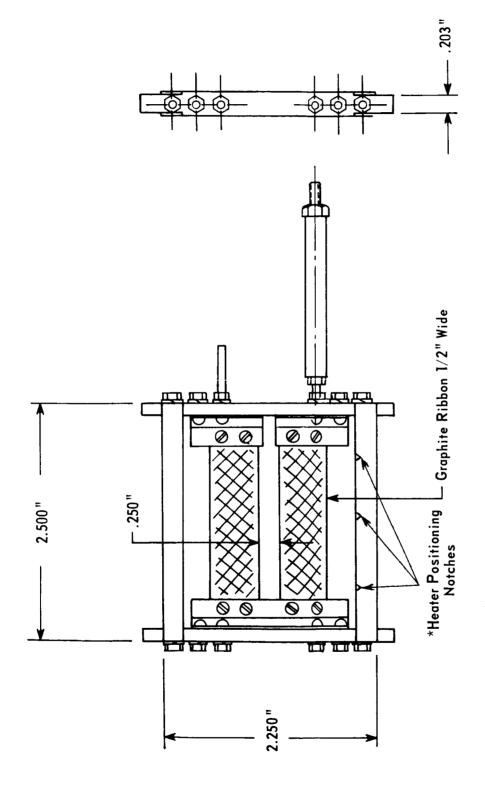


FIGURE 8 - GRAPHITE RIBBON HEATER

\* Notched Frame Member always placed nearest frame center bar when inserted into test module frame.

RCA-DEC.-8-31-65

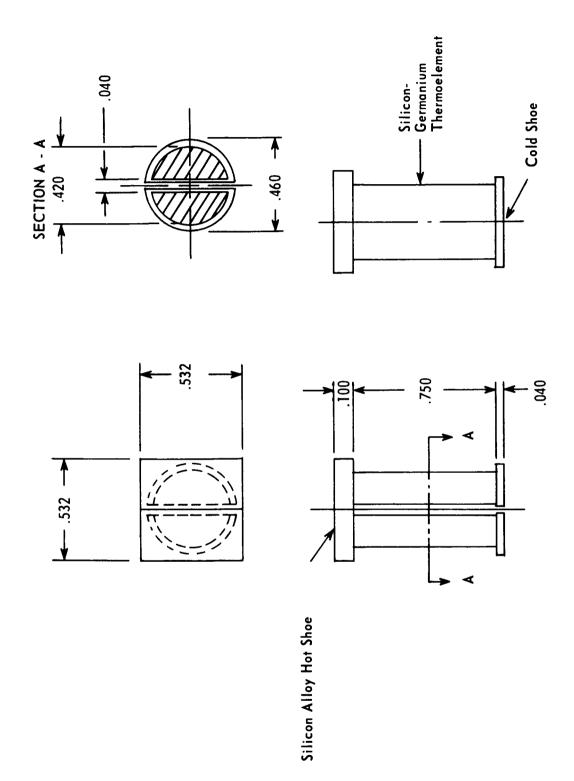
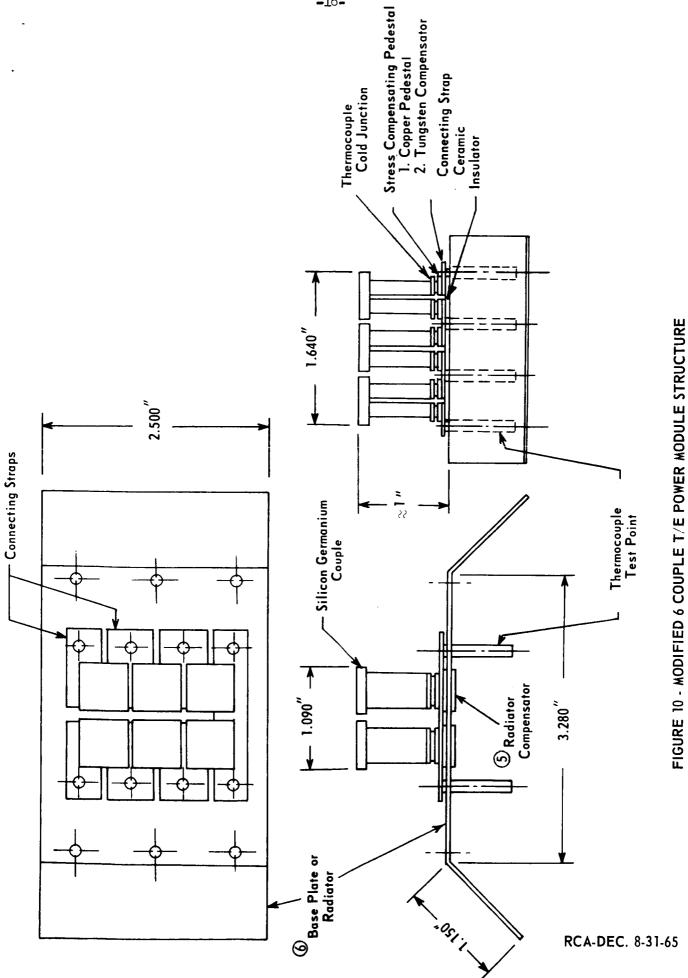
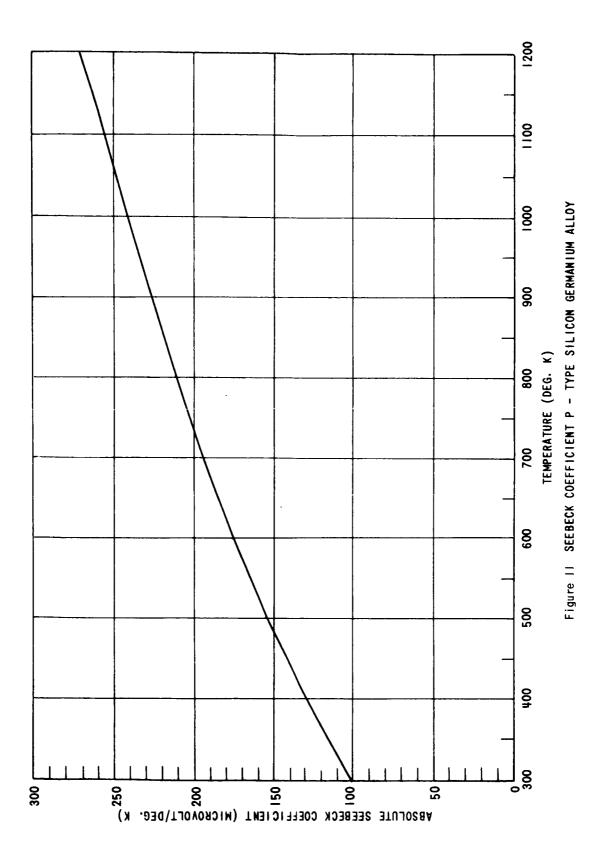
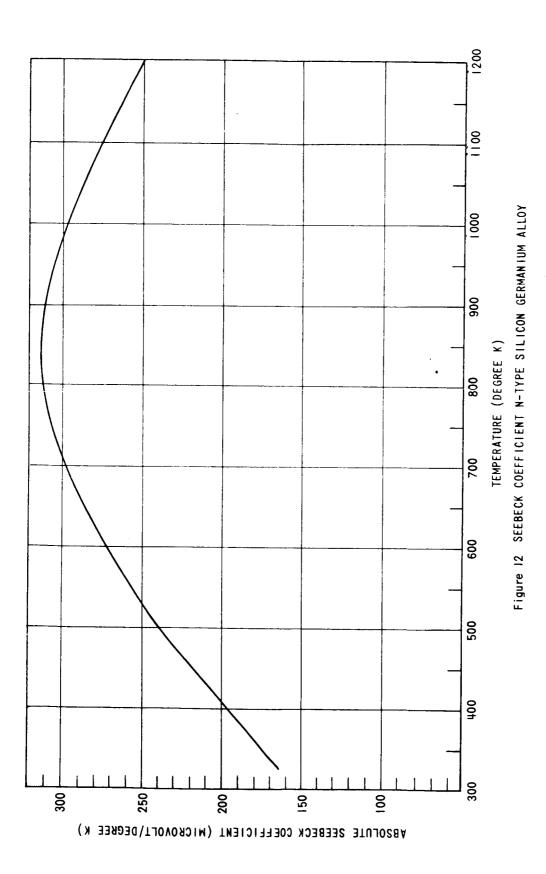
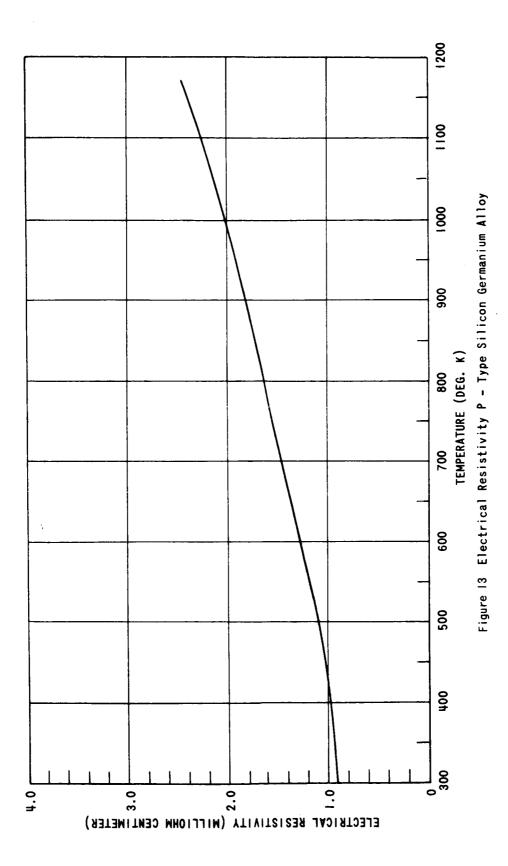


FIGURE 9 - SILICON GERMANIUM THERMOCOUPLE











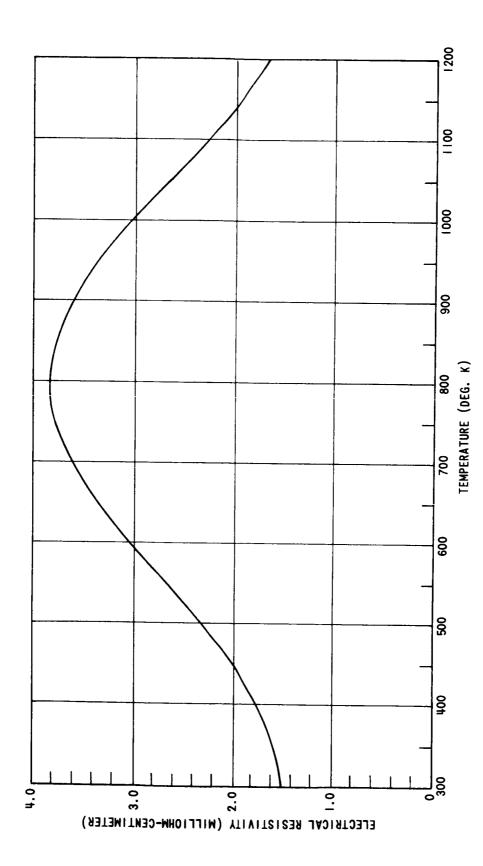


Figure 14 Electrical Resistivity N-Type Silicon Germanium Alloy

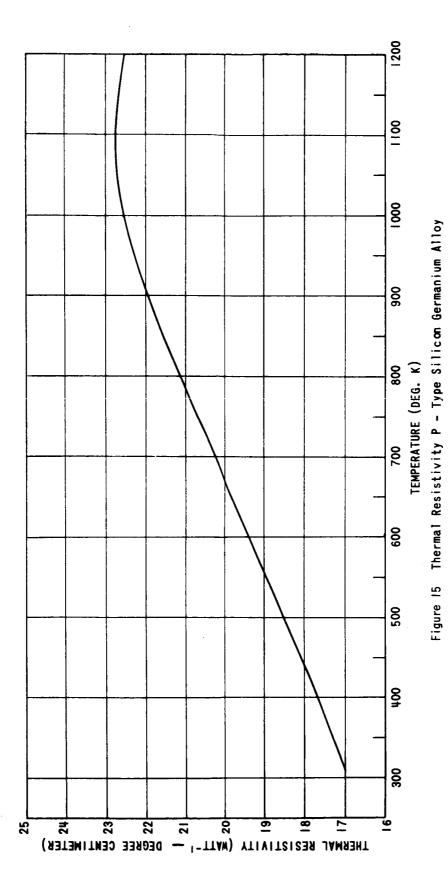

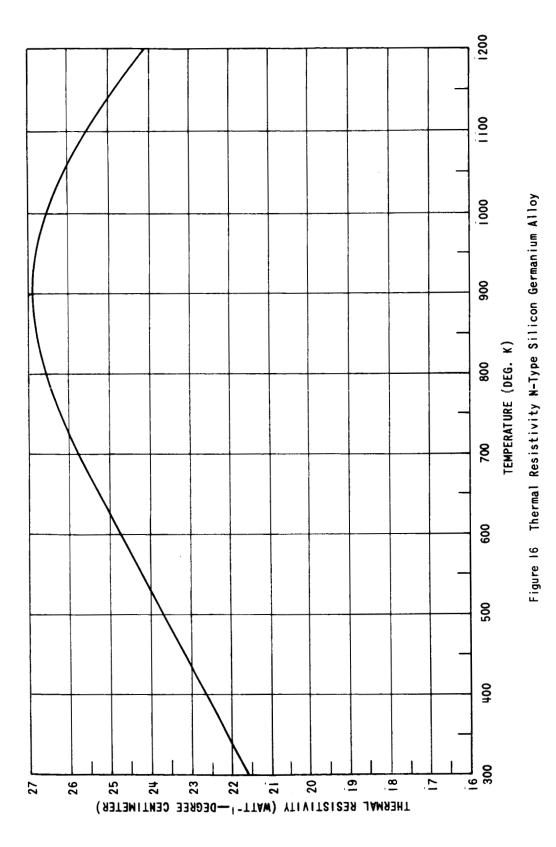

tabulation and dimensional values will be found in Figures 9 and 10 as referenced earlier.

Melting point Hot tensile strength (500°C) Compressive strength (30°C) Density Coefficient of thermal expansion in excess of 1200°C in excess of 4000 psi in excess of 146,000 psi 3.1 gms/cc 5.0 x 10-6 per °C


The N-type alloy is phosphorus doped. The P-type alloy is boron doped. A silicon-molybdenum alloy material with thermal expansion characteristics near those of the thermoelement alloys is used for the hot junction shoe material. This same alloy exhibits relatively high values of electrical and thermal conductivity.

The thermocouples, thermal stress compensating pedestal, electrical connectors, ceramic insulators and tungsten compensators are braze-bonded to a copper base plate serving also as the cold junction radiator. Eight test points, extending through the base plate, are provided for each module. Screw terminals at each test point make possible individual couple readings of power output, Seebeck voltage, and internal resistance. In the completely assembled test unit all test points will be wired and terminated in the base mount connectors. See Figures 4, 5, 6, 7, above.

Each module is supplied with one hot junction, one cold junction and one radiator temperature thermocouple. Chromel-alumel type couples are used. The cold junction thermocouple is permanently affixed to each module on the electrical connecting strap immediately adjacent to couple No. 2. The radiator temperature thermocouple is fastened under one of the radiator-to-module pan mounting screws. Both thermocouples use 28 gauge wire.

The hot junction thermocouple mounting has been designed to facilitate replacement without disturbing any other portion of the test unit. Performance of most of the commonly used thermocouple materials has been erratic in the immediate presence of or in direct contact with silicon alloys at normal hot junction temperatures, primarily because of metallurgical and chemical deterioration of the measurement couple. Although test results are limited it appears that a commercially available Inconel 600 sheathed and electrically insulated construction may prove satisfactory for this service. The Inconel sheath acts as a barrier between the silicon alloy material and the measurement couple providing an increased useful performance life to the latter. Figure 17 gives specification details of the thermocouple used for this test unit as supplied by the Claud S. Gordon Company of Richmond, Illinois.

Supplied by: Claud S. Gordon Co. Richmond, Illinois

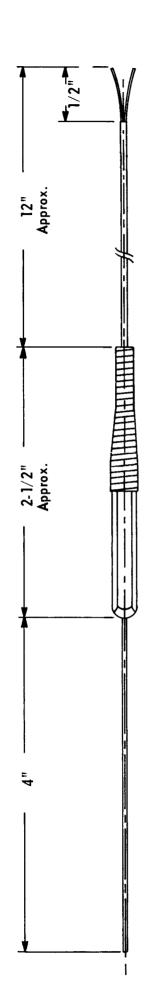

# SHEATHED THERMOCOUPLE

- 1. Sheath 0.020" dia., Inconel-600
  - 2. Ungrounded Junction
- 3. MgO Insulation 4. Chromel-Alumel (0.00)
- 4. Chromel-Alumel (0.002"dia. Approx.) Standard "K" Calibration
  - 5. Operates at 1000° C (1832° F) in 1 x 10<sup>-5</sup> Torr vacuum

## TRANSITION FITTING

- 1. Chrome plated Brass with Chrome plated steel guard.
- 2. Savereisen potting
- 3. Felted Asbestos between Chromel-Alumel leads and glass braid covered connecting wires
- 4. Do not use epoxy or plastic in fitting or for abrasion shield
- 5. Operates up to  $530^{\rm o}$  C (1000° F) in  $1 \times 10^{-5}$  Torr vacuum.

## CONNECTING WIRES

- 1. Silicone coated glass braid insulated 0.012" dia-Approx.- Chromel-Alumel wires.
- 2. Weld or Braze to Thermocouple wires at Transition
  - 3. Strip insulation from end 1/2" of wires.
- 4. Do not use epoxy or plastic in insulation or at abrasion shield.
- 5. Operates up to 350° C (660° F) in 1 x 10<sup>-5</sup> Torr vacuum.

FIGURE 17 SHEATHED MEASUREMENT THERMOCOUPLE SPECIFICATION

The tip of the 0.020" diameter sheath is inserted into a hole drilled in the "P" doped half of the silicon-moly alloy hot shoe. Prior to insertion the hole is filled with a slurry of powdered boron nitride as a means of isolating the Inconel sheath from the silicon alloy in addition to providing a more intimate contact with the junction region to be measured. The transition fitting mounted upon a ceramic stand-off to the module pan gives rigid support to the thermocouple. All hot junction thermocouple supports are mounted in a similar fashion to that side of each module pan assembly opposite the heater leads. The measurement couple junctions are located in the hot shoe of No. 5 couple for modules 157 and 160 and No. 2 couple for modules 158 and 159. In addition to the hot junction thermocouple in each module, a sighting hole to the intersection of four power couple hot shoes is provided for temperature measurement using the optical pyrometer method. The Micro Optical Pyrometer, Model 95, manufactured by the Pyrometer Instrument Company, Inc., of Bergenfield, N. J. has given excellent results in laboratory measurements at RCA. No stability or measurement accuracy problems occur at the cold junction and radiator temperatures.

The bonds between all couple and module structure interfaces are strong, extremely stable up to rated operating temperatures, exhibit very low contact resistance, and have a high thermal conductivity. When the thermocouples are bonded to the base plate, they become self-supporting cantilever-type structures, free to expand during operation without creating destructive thermal stress conditions.

The physical characteristics of the module are listed as follows:

### Element Material

N-type
P-type
Hot Shoe Material
Overall heat accepting surface
dimensions
Emissivity of heat accepting
surface
Total base plate dimensions
Base plate material
Emissivity of base plate
Module height
Module weight

Phosphorus doped, SiGe Alloy Boron doped, SiGe Alloy Silicon-Molybdenum Alloy 1-5/8" x 1-1/8"

Approx. - 0.8

 $5\frac{1}{2} \times 2\frac{1}{2}$  Copper, Ni Plated Approx. - 0.5 Approx. - 1 inch Approx. - 226 gms.

Reference to Figure 10 will clarify module constructional and dimensional details.

### IV. OPERATION AND PERFORMANCE

### A. Operation

### 1. Test Set-Up

Requirements for setting up the unit for testing include mounting and preparation of the test chamber, instrumentation, securing the desired test conditions, and initiating the test run.

Mounting of the test unit requires four holes in the test chamber base plate of size and location as shown in Figure 3. Care should be exercised in order to maintain heat exchanger and module frame registry. Since the heat exchanger connections pass through the chamber base, vacuum tight seals must be provided. The heat exchanger feed-throughs are finished with 2 inches of  $3/8 \times 24$  thread for vacuum seal clamping and water connections. All water connections should remain outside the vacuum chamber. The water outlet side of the exchanger is thermocoupled for outlet temperature readings.

Provision should be made for a minimum of 58 electrical feed-throughs. Fifteen chromel-alumel pairs are needed for measurement thermocouples. Twenty-four, 24 gauge, copper wires provide for couple, module and generator voltage and resistance readings. Four, high current (20 amperes) feed-throughs are needed, two for the heater input and two for generator output. If it is desired to operate the two test unit heaters under differing conditions, a fifth high current feed through will be needed. Two connector plugs with 6 to 8 inch "pig tail" leads are included for wiring to existing vacuum chamber feed-throughs.

When water cooling is desired a source providing a constant flow of from 8 to 12 gallons per hour at a known temperature between 20 and 30°C should be assured.

Under typical operating conditions a temperature rise of approximately 6°C will be observed between the inlet and outlet of the heat exchanger.

All temperature measurement thermocouples are "K" calibration, Chromel-Alumel and may be read by any one of several commercially available potentiometer type instruments including recorders. Temperatures to be read will range from 50°C to 900°C under the variety of operating conditions acceptable to the test unit.

Individual power thermocouple, module and generator output voltages will range from 0 to 500 millivolts for each couple, 0 to 2.5 volts for each module, and up to 10 volts for the full generator. The maximum values

indicated are for no-load voltage readings at  $\Delta$  T levels of approximately 750°C resulting from the operation of this test unit. Any voltage measuring instrument having a 1000 ohm per volt sensitivity or better is adequate.

The values of resistance encountered range from 50 milliohms for the individual thermocouple to a maximum of 1 ohm for the total generator. Securing reliable and correct internal resistance values requires some care. A method for reading hot and cold resistance, which was found most satisfactory and was used for this test, is based upon reading an AC voltage developed through the introduction into the generator of a calibrated AC current. A current of one ampere is used which is low enough so that its I<sup>2</sup>R heating effect may be neglected. However, this AC current is introduced only during the period resistance readings are taken. An AC voltmeter having characteristics similar to the Ballantine Model 320 should be perfectly adequate.

Generator output current may be read using any normal laboratory instrument capable of reading up to 7.5 amperes.

The test unit heaters are connected in series. However, improved intermodule hot junction temperature uniformity is possible with each heater operating from completely separate, adjustable supplies. Maximum power requirements reach approximately 600 watts at 40 volts and 15 amperes. Sixty cycle AC is used and for greatest performance stability some method of regulation is necessary.

Securing the desired thermal test conditions is largely a matter of deciding upon a hot shoe temperature and adjusting the cold shoe temperature to achieve the  $\Delta$ T required to produce the electrical output needed. Since these two temperatures are not independent of each other a process of successive approximation must be used to approach the conditions desired.

With the unit completely instrumented and the heater supply connected, close the vacuum system and start pumping down. Bring the chamber pressure to the 1 x 10<sup>-14</sup> Torr level. At this point vacuum chamber base plate cooling and test unit heat exchanger cooling should be turned on. Set the heat exchanger cooling water flow to approximately ten gallons per hour. Start applying power to the test unit heater, very slowly, making sure the chamber pressure does not exceed 2.0 x  $10^{-14}$  Torr. When the hot shoe temperature reaches 300 to  $10^{-14}$  Torr. From this point until the desired hot shoe temperature is reached both chamber pressure and cold shoe temperature should also be monitored with each increase in heater power. Heater input should not be increased beyond the point at which either the hot shoe temperature reaches its maximum


rated level of 900°C or the cold shoe temperature reaches its maximum rating of 371°C. During the warm-up and outgassing period it is important to permit the unit temperatures to stabilize after each heater power increase, particularly as either hot shoe or cold shoe temperature limits are approached. Once thermal equilibrium is reached, cold and hot shoe temperature readings will provide a basis upon which to determine the kind and amount of radiator-to-heat exchanger adjustment necessary to approach more closely the conditions desired.

The unit, as delivered, includes maximum thermal coupling between module radiators and the heat exchanger. With a heater power input of 600 watts,  $T_{\rm H}$  and  $T_{\rm C}$  should reach average levels of approximately 900°C and 170°C, respectively. With cooling water flow at 10 gallons per hour and an inlet temperature of 25°C, the water temperature at the outlet will be approximately 31°C. Generator adjustments as delivered will result in conditions providing the maximum  $\Delta$  T of which the unit is capable. Figure 18 presents the range of test conditions obtainable with maximum radiator-to-heat exchanger coupling.

If  $T_C$  is not at the value desired after reaching thermal equilibrium on the first approximation cycle, it will be necessary to adjust the radiator-to-heat exchanger coupling. If  $T_C$  is higher than desired and maximum coupling has not been used this coupling must be increased. If too low, the coupling must be reduced.

To make an adjustment the unit must be brought back to room temperature and the vacuum chamber opened up to provide access to the unit. Once the unit is accessible the heat exchanger coupling adjustment can be made. Thermal coupling adjustment is achieved through changes in the conduction path between module radiator wings and the heat-exchanger contact bars at the points of fastening. Maximum coupling is secured through placing a full length copper shim between the two surfaces. Thermal coupling may be reduced successively through replacing the copper shim with stainless steel and then with Hastelloy. Contact shims of these three materials are supplied. Since three bolts are used at each radiator wing for fastening to the heat exchanger, further decoupling steps can be taken through using three washers followed by two, then one and finally no contact at all. At this point minimum coupling is achieved with no water flow in the heat exchanger and heat rejection must depend upon radiation alone.

After adjustment the unit is brought back to temperature and a check made upon the new conditions. This adjustment cycle may be repeated until the desired conditions have been approximated. Usually no more than two cycles are required to reach the test conditions desired and often the first approximation is adequate.

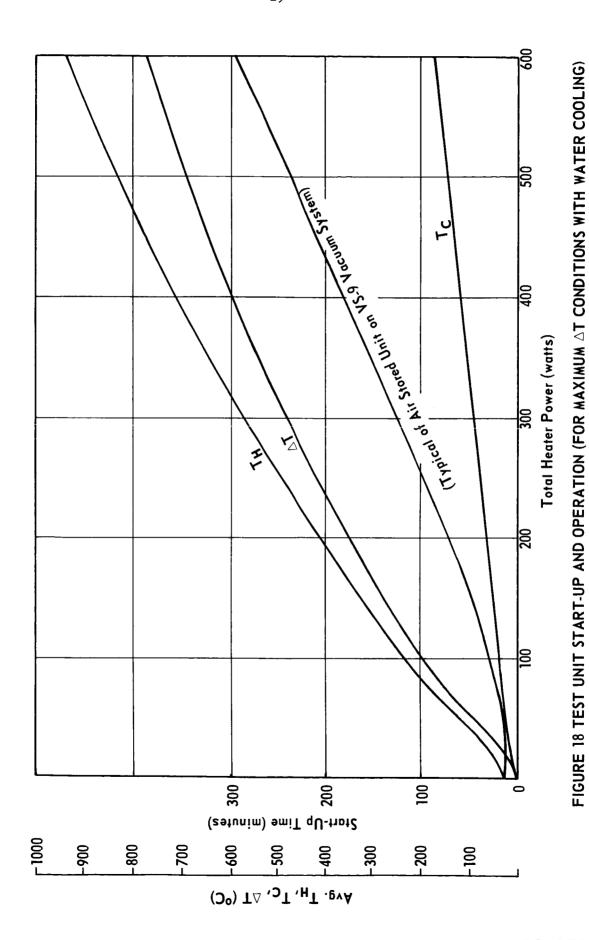

RCA-DEC.-8-31-65

### 2. Test Run

The unit should be protected from events which could result in operation at hot or cold shoe temperatures exceeding the suggested maximums of 900°C and 371°C respectively. Heater life may be impaired if the test chamber pressure is permitted to remain for any length of time above 1 x 10°4 Torr. A pressure sensitive control such as appears in the Veeco RC3A power supply may be utilized to provide the protection needed.


### B. Performance

Before delivery the test unit was to be operated through four thermal cycles during a period of approximately one hundred (100) hours. Actually, the unit was subjected to six complete thermal cycles over a period of three hundred thirty hours. Two hundred twenty five hours of operation at full temperature were encompassed within this period. One try-out cycle of forty-two hours preceded the test run giving the unit a total of three hundred seventy two hours of test time. Figure 19 diagrams the total test period. Plates I, II, III, IV, and V present the actual test data developed during the operating period.

The conditions chosen were intended to determine test unit performance at maximum obtainable  $\Delta$  T, maximum  $T_H$ , hot shoe thermocouple performance at maximum reading temperatures, normal maximum heater input and heat exchanger performance with water flowing. Test conditions were maintained as nearly constant as practicable throughout the period to provide a valid basis for noting performance changes with time. The test conditions for the first cycle differ from those of the remaining cycles only because it proved to be the first approximation for determination of maximum thermal coupling to the heat exchanger. Therefore, its results are not included in the presentations of Figures 20, 21 and 22.

The test conditions desired were  $T_H \approx 900^{\circ}\text{C}$ ,  $T_C \approx 150^{\circ}\text{C}$ , and  $\Delta$  T = 750°C. Actual average values obtained throughout the test period are shown in the following tabulation.

Unit	$\underline{\mathrm{T}_{\mathrm{H}}(^{\mathrm{o}\mathrm{C}})}$	T <sub>C</sub> (°C)	$\nabla_{L(oC)}$
Full Generator Module 157 158 159 160	904	169	735
	913	166	747
	897	183	714
	916	167	749
	888	159	729

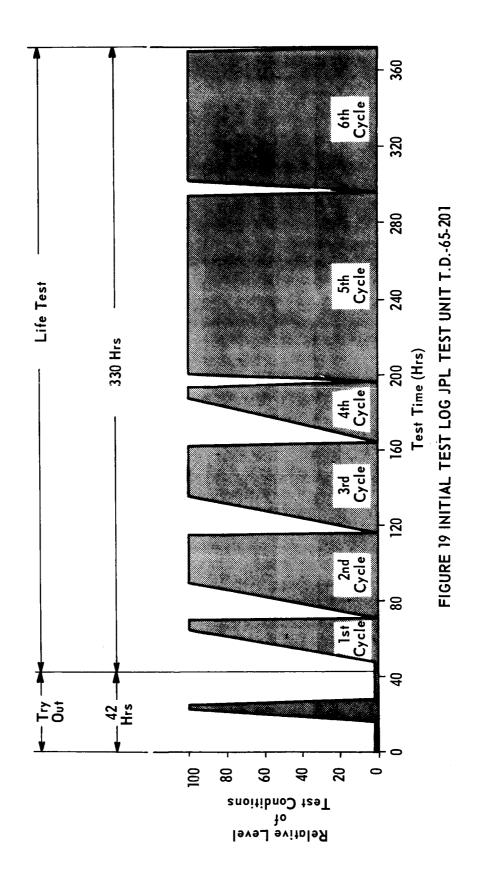

JPL TEST GENERATOR

TOTAL TEST UNIT

INITIAL LIFE TEST

arofo	lst lst	lst	2nd	2nd	3rd	3rd	3rd	lth	1th	5th	5th	5th	犵뀨	6th	6th	6th
Hrs.	, 23	29		89	88	112	122	135	154	158	225	253	255	261	328	330
(00)	903			006	899	895	1	905	1	706	905	910	1	915	606*	
(00)	285	ı	161	191	170	178	ı	191	ı	168	167	172	1	182	991	1
Avg. AT(OC)	. 618	•	734	739	729	717	ι	744	1	736	738	738	1	733	743	ı
Output																
olts) -	3.7	ı	3.97	3.95	1,00	3.95	1	14.00	•	7	3.95	3.9	1	3.95	4.05	
		ı	7.95	7.90	8.25	8,30	,	8,30	1	8,1,2	8.40	8.40	•	8,30	8.10	ı
nohms) 298		300		286	9	655	320	645	325	299	680	099	330	682	680	340
· (smuc	. 690	1	575	2%	630	618	ı	620	•	620	620	620	,	620	620	ı
(*)	5.3	1	6.35	6.20	6.40	9,40	ı	6.40	ı	0 <sup>†</sup> l <sup>•</sup> 0	6.35	0tl.	1	6.30	6.20	ı
PL (watts)	. 19,6	ı	25.2	24.5	25.4	25•3	ı	25.6		25.6	25.1	25.0	:	24•9	25.1	
Input																
(volts)	36.5	ı	39.0	39.2	39.0	39.0	ı	0.04	ŧ	0.01	39.8	39.8	•	39.7	0.01	
•	14.0	1	14.55	14.5	15.1	15.0	1	15.0	ı	15.0	15.0	15.0	ı	15.0	15.0	ı
• (s:	515	1	268	269	588	585	ı	009	•	009	265	265	ı	595	009	
Vacuum (mm Hg)	. 5x10-5	<del>ار</del> ا	2.5×10-5	2.5x10-5	5 <b>x10-</b> 5	1.5×10-5	•	3.6x10-5	•	3.7×10-5	1.3×10-5	8×10-6	ı	8×10-6	3x10-5	ı

\*Thermocouple Values

JPL TEST GENERATOR

MODULE NO. 157

INITIAL LIFE TEST

										-1	33 <b>-</b>													
6th	330		,	t	ŧ	1	ı	85.4	•	1				1	ı	•	•		15.3	14.2	14.0	13.7	13.9	14.3
6th	328	:	*952	161	191	1.08	2.17	172	6.30	02.9		•	182/365	٠,	<u> </u>	<u> </u>	· ·		29.5	27.9	28.9	28.2	28 28 29 29	20.02
6th	261		920	175	745	1.05	2.15	175	6.30	6.62		,	172/369	169/346	194/379	195/376	155/346	171/355	30.8	28.0	29.1	28.7	28 <b>.</b> 6	29.1
5th	255		1	ı	1	•	1	83.5	1	ı			1			1		•	14.6	13.9	13.7	13.5	13.6	O• ††
Sth	253		915	167	748	1,05	2.16	170	o <del>1</del> .9	6.13			169/361	155/341	191/376	194/373	161/340	166/349	29.7	27.4	28.8	27.9	28 1	۲ <b>۵</b> ۰
5th	225		915	163	752	1.03	2,16	174	6.35	45.9			168/368	162/345	190/381	193/379	160/346	156/356	30.5	28.0	29.2	28°4	28 <b>.</b> 6	29.1
5th	158		905	163	742	1.07	2.18	169	0t/•9	6.85			172/365						29.6	28.2	28.7	28.0	27.8	7.02
lth	154		1	ı	1	1	1	82.0	1	ı			ı	1	•	•	1	1	14.7	13.5	13.8	13.2	13.8	13.
lth	135		910	154	756	1.06	2.15	164	0 <sup>†</sup> (9	6.81			171/365						29.0	26.6	27.9	27 •0	27.1	5(.3
3rd	111		ı	t	1		1	80.0	ŧ	1			1	1			•		14.1	13.2	13.4	13.1	13.2	13.4
3rd	112		006	178	722	1.03	2,11	991	6.40	09•9							158/330		29.0	27.0	28.1	27.3	27.5	21.0
3rd	88		900	170	730	1.03	2,10	164	0 <sup>†</sup> 10	09*9			170/356	158/329	186/365	184/359	157/335	171/349	28.8	26.5	27.6	26.8	26.9	77.1
2nd	89		910	163	747	0.985	1.99	11,9	6.20	6.11			150/325	142/304	200/369	194/359	150/313	153/317	26.0	24.0	25.0	24.5	24.3	24.6
2nd	7.		905	162	770	1,02	2.04	114	6.35	6.48			152/356	. 018/841	202/372 3	197/363	155/319	155/320	21,29	23.4	24.2	23.8	23.9	24.0
lst	25		ı	ı	ı	,	•	74.8	1	1			•	•	1	•	•	,	73,3	12.6	12.4	12.3	12.5	12.6
lst	23		910	797	9179	0.87	1.70	159	5.0	4.61			158/309	134/274	193/338	191/334	142/285	166/312	28.3	26.1	26.9	56.4 1	56.4 26.4	27.0
lst	0		•	ı	,	ı	•	74.0		•			•	•	1	ı	•	•	13,3	12.6	12.4	12.3	12.5	12.6
Cycle	Accum. Hrs.	Total Module	Avg. TH(OC)	Avg. TC(°C)	Avg. AT(°C)	Er (volts)	Enc (volts)	R (mohms)	I (amps)	Pr (watts)	Couples	7	# J	5	EL/2 3	TOOT,	(mvolts) 5	9	<i>"#</i>	1 2	В.	t (smdom)	w	9

\*Thermocouple Reading

JPL TEST GENERATOR

MODULE NO. 158

INITIAL LIFE TEST

1	_							2			34 <b>-</b>							2	~	6	æ	∞ <i>-</i> -
6th	330		1	ı	1	•	1	87.	•	1		1	•	•	•	1	1	17.	77	13.	13.	13.8
6th	328		*888	178	710	0.0	2.08	179	6.2	5.58		121/338	146/332	165/353	1817/366	163/346	162/356	33.2	29.2	28.9	29.1	28°0
6th	261		910	203	707	0.89	2,02	179	6.3	5.61		330	319	. 04E/651	326	332	344	33.6	28.7	28.9	28.7	28.6
5th	255		1	1	ı	1	•	86.0	1	ı		•		,	•	1	•	17.0	14.0	13.6	13.6	۲. پرو
5th	253		900	185	715	0.88	1.98	174	6.40	5.63				160/344				32.7	28,1	28.3	28.1	28 <b>°</b> 0
5th	225		900	179	721	0.88	700₹	178	6.35	5.58		337	318	160/350 1	363	337	353	33•3	29.0	28.8	28.8	28 <b>.</b> 4
5th	158		905	180	725	0.92	<b>5.</b> 06	173	04.9	5.89				165/347				32.5	28.0	27.9	27.8	27.6 28.8
lth	154		•	•	•	ı	1	84.2	•	ı		,		•	•		•	17,1	13.7	13.6	13.2	13.6
hth	135		900	172	728	0.91	2.05	169	0 <sup>†</sup> 10	5.83		120/334	134/314	165/345	178/358	152/331	165/351	32.0	27.3	27.3	27.2	27.1
3rd	114		1	ı	ı	•	ı	82.8	1	ı		ï	1		•		1	16.3	13.5	13.2	13.2	13.1
3rd	11.2		890	197	663	006.0	2,00	171	0 <sup>†</sup> 10	5.76		129/336	133/313	160/339	169/346	148/325	162/346	32.1	27.9	27.8	27.7	27.6
3rd	88		880	186	η69	006.0	1.98	167	04.9	5.76				/335		/321		31.4	27.4	27.1	27.0	27.0
2nd	89		903	172	731	0.905	1.93	153	6.20	2,60		104/295	141/310					28.8	25,1	24.8	24.8	24.7
2nd	717		868	173	725	0.925	1.94	11,17	6.35	5.87		108/296	145/312				13/1/300	27 • h	24.2	23.7	23.8	23.7
lst	25		ı	ı	•	1	•	77 •0	•	ı		ı	•		•	•	•	15.6	12.8	12.3	12.3	12 5.5 7.0
lst	23		905	284	621	0.89	1.78	166	5,30	4.72		133/305	26/259	173/314	176/317	130/272	158/306	32.2	27.1	26.4	26.h	26.7
lst	0		ı	ı	1	1	,	76.5	•	ı		•	1	•	ı		ı	15.5	12.5	12,2	12,1	12.2
Cycle	Accum. Hrs.	Total Module	Avg. TH(OC)	Avg. T <sub>C</sub> (OC)	AVE. AT (OC)	El (volts)	Eoc (volts	R (mohms)	I (amps)	Pr (watts)	Couples	# <sub>1</sub>	2	EL/E 3	7 700 7	(mvolts)5	9	#1	5 2	R 3	μ (mohms)	w

\*Thermocouple Reading

JPL TEST GENERATOR

MODULE NO. 159	
IFE TEST	1
LIFE	
INITIAL	

6th	330	1		ı	1	ı	82.5	•	•		1		ı	1 1	13.05.05 13.05.05 13.05.05	1
6th	328	*	164	757	1.10	2.18	172	6.20	6.82		30/361	77/385	96/389	169/343 179/375	288.0 288.0 286.0 286.0	) •
6th	261	030	180	750	1.07	2,16	173	6.30	6.75					166/330 16180/365 1	2828 2838 2838 2838 2838 2838 2838 2838	•
5th	255	1		1	ı	1	81.8	1	1		1	i ř	iři		13.70	İ
5th	253	030	169	191	1.04	2.12	168	0109	99•9		54/350	20/370 26/370	93/381	165/330 175/364	288 289 279 279 279 279 279	1
ξth	225	) J	165	71,0	1.05	2.16	173	6.35	29.9		355	2,6	388	165/336 16176/371 17	28.5 28.6 28.9 26.9 26.1	}
5th	158	O.Lo	)16 166	7177	1.08	2.18	167	04.9	6.92		351		387	169/334 1 171/370 1	2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2	) •
1th	151		1 1	ı	ı	•	80.1	ı	1		, ,	I 1		11	13.9	
μth	135	5	160	750	1.07	2.14	163	ot.9	6.85		69/349	07/280	95/382	166/329	27.8 27.1 27.3 28.8 24.7	i •
3rd	111		1 1		•	1	79.2	•	1			I ;		11	23.05.4 23.05.4 23.05.4 24.05.4	}
3rd	112	5	9 <u>4</u> 0	734	1,05	2.12	164	01.9	6.13		77/355	02/200	86/372	165/325 184/366	27.7.5 27.7.5 28.9 28.9 7.8.5 7.8.5	
3rd	88	S	920	753	1.04	2,10	162	04.9	29•9		348		368	164/319 178/358	22 22 22 22 22 22 22 22 22 22 22 22 22	ī
2nd	89	7.	715 159	756	1.06	2,065	150	6.20	6.58		332	27.0		307	2222 2222 2222 2222 2222 2222 2222 2222 2222	
2nd	प्रा	Č	915	752	1,06	2.05	143	6.35	6.73		161/326	100/324 1	205/380 2	157/307 1	23.23.29 23.23.29 23.23.29 23.23.29	<del>1</del>
lst	25		1 1	t		1	73.3	•	ı		ı	T (*	1 1	11	12.00 12.00 12.00 11.00 11.00 10.00	1
lst	23	ì	309	616	0.89	1.76	162	5,30	4.61		.50/300	27/27	69/321	126/257 153/303	27.8 27.0 26.9 28.1 24.3	•
lst	0		1 1	•	•	1	72.5		ı				1 1	1 1	12.0 12.0 12.0 10.0 10.0 10.0	1
Cycle	Accum. Hrs.	Total Module	Avg. TH(C)	AVP. AT(OC)	Er (volts)	Enc (volts)	R (mohms)	I (amps)	P <sub>L</sub> (watts)	Couples	# H	2.0	EL/Eoc	(mvolts)5 6	#1 2 8 3 (motums) 4 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5	Ò

\*Thermocouple Reading

JPL TEST GENERATOR

MODULE NO. 160	
INITIAL LIFE TEST	

Cycle 1st	Accum. Hrs. 0	Total Module	Avg. T <sub>H</sub> (OC)	Avg. T <sub>C</sub> (°C)	Avg. A T(°C)	EL (volts) -		(mohms) 73.0	L (watts)	Couples	#1 - 1	- 2	$E_{L/E_{oc}}$ 3 - 1	(mvolts)5 - 1	#1 12.7 2 12.0 R 3 12.6 mohms) 4 12.0
lst	23		872	281	591	0.97	1.84	159	, y 1		156/306	128/271	189/340 91/33h	139/275 165/314	27 26.5 27 27 26.1 25.0
lst	25		ı	•	ı	ı	1	73.5	ŧ 1		1	•	1 1	1 1	12.9 12.4 12.0 12.1 12.0
2nd	717		698	1148	721	0.98	1.97	140	6.23			154/318 1	194/366 1 191/356 1		23.5 23.5 23.5 23.5 25.5 25.5 25.5 25.5
2nd	89		898	11,48	720	0.95	1.96	147 200	5.90		290	319	194/ <i>3</i> 70 1 191/358 1	320	24.7 24.3 25.4 24.2 23.1
3rd	88		895	156	739	0.98	2,03	159	6.27					156/321	26.5 26.5 26.3 25.3
3rd	112		880	162	718	0.98	2,02	161	6.27		51/331	50/324	.80/361 82/355	158/321 158/334	26.8 26.8 26.8 25.3
3rd	114		•	•	ı	•	1	79•3	1 1		1	•	1 1		13.6 13.0 13.0 13.0
1th	135		900	158	742	0.95	2,01	160	6.08		149/327	150/324	184/367	150/316 146/324	27.5 28.9 27.0 25.0
ltth	154		ı	•	•	1	1 6	80•2	1		ı	1	1 1	1 1	2. 5. 5. 5. 5. 5. 5. 5. 5. 5. 5. 5. 5. 5.
Sth	158		895	163	732	0.97	2.05	165	6.20		336	331	377	154/321	28 27 28 27 27 27 26 27 26
5th	225		900	162	738	0.93	2.03	171	, y , 8		335	331	373	149/324	28.9 28.1 29.3 28.2 26.9
5th	253		895	165	730	0.93	1.99	166	%					150/320	28.4 27.8 29.0 27.8 26.1
5th	255		ı	1	ı	1	,	81.9	ı <b>ı</b>		ı		.,,	11	13.4 13.4 13.9 13.4 13.4
6th	261		900	172	728	96.0	2.05	171	6.05		334	335	372	155/324 146/326	28.7 28.2 28.2 26.3
6th	328		*876	160	716	0.98	2.04	170	90.9		144/333	150/335	188/374	156/328	22 22 22 22 22 22 22 22 22 22 22 22 22
6th	330		1	•	•	ı	1 6	83.3			1	•	ı	1	14.2 13.7 14.0 13.7

\*Thermocouple Reading

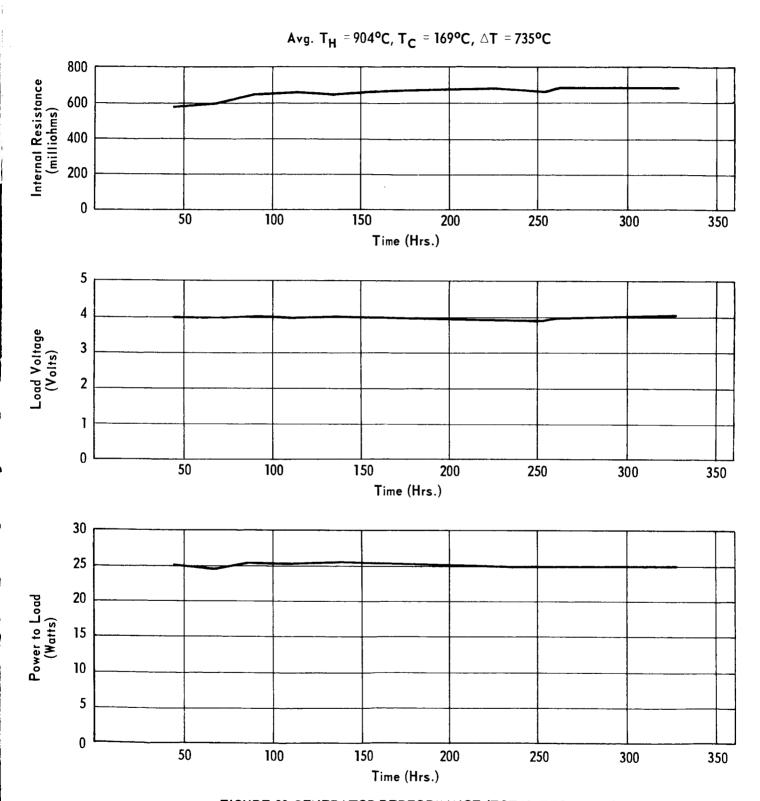
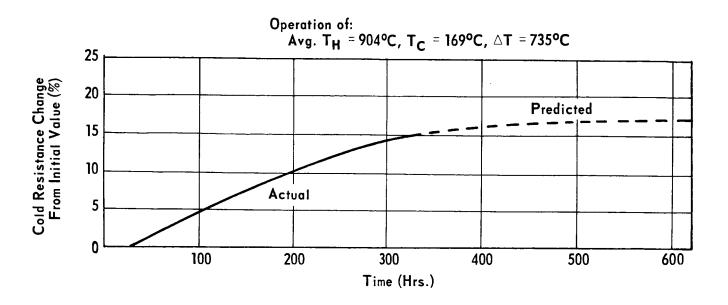


FIGURE 20 GENERATOR PERFORMANCE (TOTAL TEST UNIT)



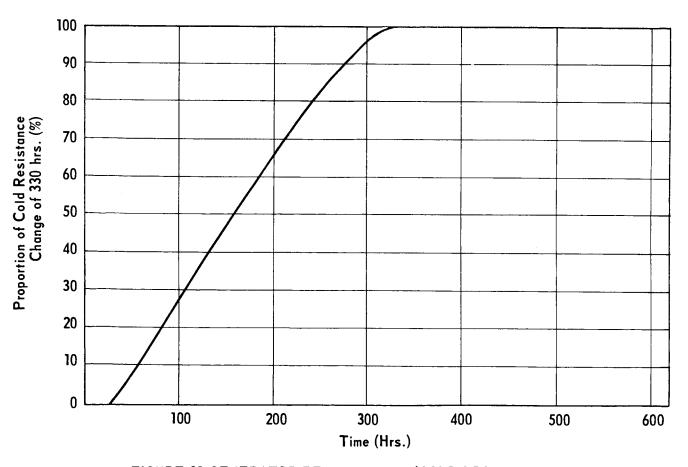

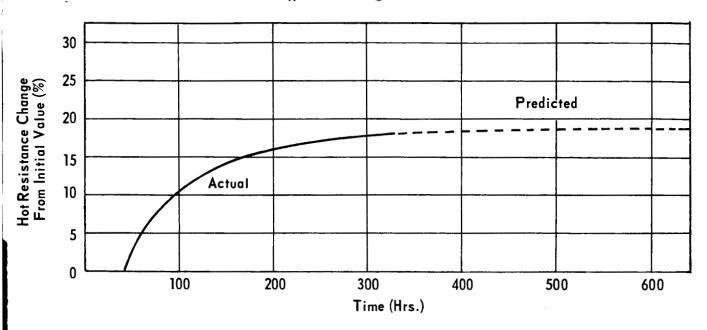


FIGURE 21 GENERATOR PERFORMANCE (COLD RESISTANCE VS. TIME)





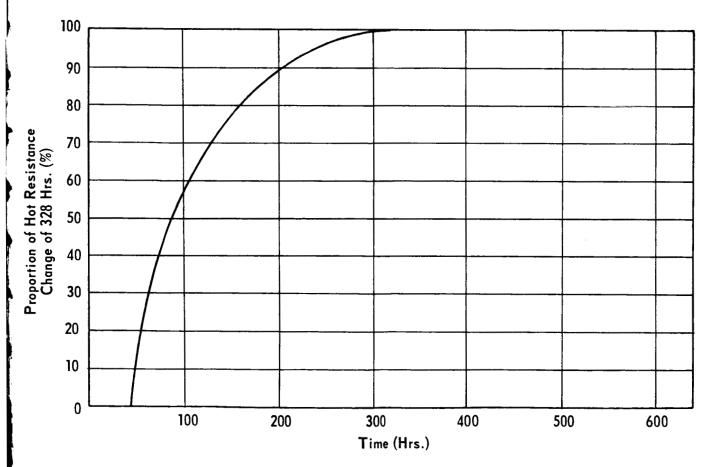


FIGURE 22 GENERATOR PERFORMANCE (HOT RESISTANCE VS. TIME)

Hot shoe temperature readings were taken using the optical pyrometer with the exception of those at the 328 hour point. The optical method was used for reasons of consistency because of difficulty with the special sheathed thermocouples used for the first time in this unit. Sheathed thermocouples as delivered initially by the Claud.S. Gordon Company used an epoxy potting compound in the transition fitting between the couple sheath and the lead wires. Although this compound was rated for operation up to 200°C, experience with the initial couples resulted in five failures out of ten units at temperatures under 100°C. The failure mechanism appeared to be a separation of the thermocouple wire resulting from the high thermal expansion characteristic of the epoxy material. Reference to Figure 17 will help clarify this discussion of the thermocouple problem. It was felt this initial thermocouple would perform within its ratings, as tests revealed the method used for mounting the transition fitting would prevent its operating at temperatures greater than 50% of the maximum permissible cold shoe temperature of 371°C or a maximum of 186°C.

New thermocouples were secured from the Claud S. Gordon Co. using a low expansion Sauereisen compound for the transition fitting. The manufacturer's temperature rating for this design is 532°C. No difficulty is expected from this higher temperature construction. It was subjected to a series of cycles up to its rating without any evidence of damage resulting.

No evidence of sheath or thermocouple deterioration appeared through the first 240 hours of operation at 900°C in contact with the silicon-molybdenum alloy hot shoe. Much longer periods of operation will be required to ascertain the adequacy of the sheathed construction when used in the presence of silicon alloys.

The test unit, as delivered, provides for ease of hot shoe thermocouple replacement without disturbance to any other portion of the test unit should failure occur within a given test period.

Agreement between optical pyrometer and thermocouple temperature readings on the average was very good. Comparisons made during the 5th and 6th cycles between the two reading methods show average optical readings to be 910°C and average thermocouple readings to be 901°C. This provides an average difference of essentially 1%. The maximum differences in individual readings were in the order of 3.5 to 5%. On the average the thermocouple reading was lower than the optical reading.

Figure 20 shows that the generator developed voltage and power-to-load remained essentially constant at 4.0 volts and 25 watts, respectively, throughout the test. Generator hot resistance increased by some 18% over the initial value. Figures 21 and 22 provide curves of cold and hot resistance change and rates of change for the test period. Under the test conditions chosen the total resistance change should stabilize at approximately 20% at an operating time of from 1000 to 1500 hours. As can be seen, approximately 75% of the expected change has already occurred at the 330 hour point.

### V. CONCLUSIONS

RCA has fabricated a silicon-germanium thermoelectric test unit for the Jet Propulsion Laboratory. It is adaptable to a range of test conditions encompassing those encountered in practical space power system environments. As a result it will provide useful data for assessing the application of silicon-germanium thermoelectric devices to space power needs.

Initial life testing to 330 hours at maximum  $\triangle$  T conditions indicates a performance in agreement with that of calculation and experience for couples of the design used. Provisions have been made for test condition and performance monitoring applicable to mechanized readout.