

N66-19038	
(ACCESSION NUMBER)	(THRU)
93	1
(PAGES)	(CODE)
CR 66068	17
(NASA CR OR TMX OR AD NUMBER)	(CATEGORY)

ELECTROPHORETIC DEPOSITION
OF GRADATED OXIDATION RESISTANT COATINGS
ON TANTALUM-10 TUNGSTEN ALLOY

By P. F. Campbell, K. A. Gebler,
and M. H. Ortner

GPO PRICE \$

CFSTI PRICE(S) \$

June 1965

Hard copy (HC) \$3.00

Microfiche (MF) .75

ff 653 July 65

Distribution of this report is provided in the interest of
information exchange. Responsibility for the contents
resides in the author or organization that prepared it.

Prepared under Contract No. NAS 1-3533 by
VITRO LABORATORIES
West Orange, New Jersey

Langley Research Center

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION

SUMMARY AND CONCLUSIONS

19038

Experimental equipment was successfully tested for the preparation of two-component electrophoretic coatings which are continuously gradated in composition over a thickness of 4-8 mils. A variety of intermetallic compounds and refractory oxides were screened as pellets and as coatings for potential use as gradated coatings for the protection of Ta-10W from oxidation at temperatures above 3000°F. Gradated coatings consisting of MoSi₂-CaO-stabilized zirconia and WSi₂-2%TiO₂/CaO-stabilized zirconia were chosen for application to test specimens. Tensile specimens, leading edge specimens, and coupons were coated with each of the chosen systems, and these were sent to NASA for evaluation.

Several problems remain unresolved with these and with similar coating systems and require further study. The most important of these are:

1. Identification of possible reactions which occur among the components of the coating systems upon exposure to high temperature air oxidation.
2. Choice of optimum combinations of intermetallic compounds and refractory oxides for gradated coatings.
3. Methods of obtaining maximum sintered density in the outer, refractory oxide portion of the coatings.
4. Investigation of the effects of coating thickness and composition gradient upon oxidation resistance.

Authn

FOREWORD

This is the Final Report under NASA Contract NAS 1-3533, and covers the work performed during the period 1 January 1964 - 31 May 1965 on the application of electrophoretically deposited, gradated intermetallic compound-refractory oxide coatings to tantalum-10 tungsten alloy foil gage specimens.

This program was accomplished under the technical direction of Mr. Bland A. Stein and Mr. Eldon E. Mathauser of the National Aeronautics and Space Administration, Langley Research Center, Structural Materials Branch.

This report has been assigned Vitro Laboratories' internal number VL-2352-7-O.

TABLE OF CONTENTS

	<u>Page No.</u>
INTRODUCTION	1
ELECTROPHORETIC DEPOSITION EQUIPMENT FOR GRADATED COATINGS	2
SCREENING OF INTERMETALLIC-REFRACTORY OXIDE COMBINATIONS	8
Physical Property and Analytical Data for the Substrate and Coating Materials	8
Sintering of Pure Oxides, Intermetallic Compounds, and Composite Systems	9
Sintering of Oxide-Intermetallic Powder Mixtures	10
Studies of Bonding Between Oxides and Intermetallic Compounds	11
Oxidation Screening Tests of Intermetallic Compounds . . .	12
COATING STUDIES	13
Intermetallic Compounds	13
Diffusion Barrier Studies	15
Refractory Oxide Studies	16
SINTERING STUDIES OF TWO SELECTED GRADATED COATING SYSTEMS	18
MoSi ₂ -Refractory Oxide Systems	18
WSi ₂ -Refractory Oxide Systems	19
PREPARATION OF FINAL SAMPLES FOR NASA EVALUATION	20

TABLE OF CONTENTS

	<u>Page No.</u>
BIBLIOGRAPHY	22
APPENDIX A - TABLES	
APPENDIX B - ILLUSTRATIONS	

LIST OF TABLES (APPENDIX A)

Number	Title	Page
1	Sedimentation Trials of Coating Materials	24
2	Selected Physical Properties of Refractory Materials. . .	24
3	Source and Form of Coating Materials	25
4	Typical Analyses of Zirconia Compounds	26
5	Spectrographic Analysis of MoSi_2 After Dilute HCl Leach	27
6	X-Ray Diffraction Analysis of Vitro-Synthesized TaAl_3 . .	28
7	Spectrographic Analysis of Zirconium Diboride Powder. .	29
8	Spectrographic Analysis of Tungsten Disilicide Powder (Source A)	30
9	Sintering Trials of Oxides and Intermetallic Compounds .	32
10	Density of 50-50 Blends of Oxide-Intermetallic Compounds After Sintering in Argon at 1700°C for 30 Minutes	33
11	Sintering Trials of Oxides, Intermetallic Compounds, and Composite Systems	34
12	Oxidation Trials of Sintered Intermetallic Compounds. . .	35
13	Effect of Metallic Binders on Ductility of Ta-10W Substrate and Adherence of Coatings	36
14	Sintering Experiments - Intermetallic Compounds on Ta-10W	37
15	Knoop Hardness Measurements for Intermetallic Coatings on Ta-10W Substrate	38

LIST OF TABLES (APPENDIX A)

<u>Number</u>	<u>Title</u>	<u>Page</u>
16	Evaluation of Diffusion Barriers for Tantalum	39
17	Results of Sintering Fluxed ZrO_2 at 1700°C	40
18	Sintering Trials of MoSi_2 -Oxide Coatings on Ta-10W . . .	41
19	Sintering Results on Gradated Coatings	42
20	Results of Oxidation Tests on Ta-10W Specimens Having Gradated Oxide-Intermetallic Coatings	43

LIST OF ILLUSTRATIONS (APPENDIX B)

Number	Title	Page
1	Pumping System for Electrophoretic Deposition of Gradated Coatings	44
2	Effluent Composition and Volumetric Flow Rate vs. Pumping Speed for 5 Minute Run Through 1/4 in. Diameter Tubing	45
3	Coating Rate of Various 1 ^W /o Dispersions	46
4	Coating Rate of Various 1 ^W /o Dispersions	47
5	Photomicrograph of Sintered CaZrO ₃ and SrZrO ₃	48
6	Photomicrograph of Sintered 8%Y ₂ O ₃ -Stabilized Zirconia	49
7	Photomicrographs of 50SrZrO ₃ -50TaSi ₂ and 50SrZrO ₃ -50(90ZrB ₂ -10MoSi ₂)	50
8	Photomicrograph of 50CaZrO ₃ -50TaSi ₂ Composite	51
9	Photomicrographs of Sintered Intermetallic Compounds	52
10	Photomicrographs of Sintered 8%Y ₂ O ₃ -Stabilized ZrO ₂	53
11	Photomicrographs of Sintered CaO-Stabilized ZrO ₂ Composites	54
12	Photomicrographs of 8%Y ₂ O ₃ -Stabilized ZrO ₂ Composites	55
13	SrZrO ₃ -MoSi ₂ Three-Layer Composite	56
14	SrZrO ₃ -TaAl ₃ Three-Layer Composite	57
15	Interface Between Pure Oxide and 50/50 Oxide- Intermetallics in Three-Layer Composites of CaZrO ₃ - MoSi ₂ and SrZrO ₃ -(90ZrB ₂ -10MoSi ₂).	58

LIST OF ILLUSTRATIONS

Number	Title	Page
16	Reaction of Intermetallic Compounds with Ta-10W at 1750°-1800°C in Argon	59
17	WSi ₂ and 90ZrB ₂ -10MoSi ₂ Coatings on Ta-10W Alloy. . .	60
18	Effect of Heat-Treatment on Microhardness of Ta-10W Substrate	61
19	Ta-10W Specimen, Coated with WSi ₂ , Sintered at 1400°C, and Siliconized at 1350°C	62
20	WSi ₂ -Coated Ta-10W Specimen After Static Oxidation at 3000°F	63
21	Mo Coating on Chemically Cleaned Ta-10W	64
22	Liquidus Curves of Systems CoO-ZrO ₂ , NiO-ZrO ₂ , and ZnO-ZrO ₂	65
23	Liquidus Curves of Binary ZrO ₂ -Oxide Systems	66
24	Cross Sections of Al ₂ O ₃ Modified CaO-Stabilized ZrO ₂ Specimens	67
25	Cross Sections of TiO ₂ Modified CaO-Stabilized ZrO ₂ Specimens	68
26	Cross Sections of Co ₂ O ₃ Modified CaO-Stabilized ZrO ₂ Specimens	69
27	MoSi ₂ -ZrO ₂ Gradated Coating Over Sintered MoSi ₂	70
28	MoSi ₂ -ZrO ₂ Gradated Coating Over Sintered MoSi ₂	71
29	MoSi ₂ -ZrO ₂ Gradated Coating After Oxidation at 1600°-1650°C for 20 Minutes	72

LIST OF ILLUSTRATIONS

<u>Number</u>	<u>Title</u>	<u>Page</u>
30	Al ₂ O ₃ (MgO)-WSi ₂ Graded Coating After Static Oxidation Test at 2912°F	73
31	(ZrO ₂ -2%TiO ₂)-WSi ₂ on Ta-10W After Static Air Oxidation Test at 3000°F	74
32	Specimens Coated for NASA Evaluation	75

INTRODUCTION

The objective of this program was the development of equipment and techniques for producing a thin oxidation resistant coating for tantalum-10 tungsten alloy foil gage material for application at temperatures to 3500°F. The coating was to be applied by electrophoretic codeposition of inter-metallic compound and refractory oxide materials to produce a deposit which was continuously gradated in composition from nearly pure inter-metallic compound adjacent to the substrate to nearly pure refractory oxide at the coating surface.

A secondary objective of this program was the identification of two intermetallic compound-refractory oxide compositions to provide the required 3500°F capability.

Preliminary screening tests involving sintering and oxidation tests were carried out on several intermetallic-oxide combinations. The two coating systems which were selected, on the basis of these studies, for application to the Ta-10W specimens supplied by NASA were MoSi_2 -(3.5% CaO stabilized- ZrO_2) and WSi_2 -(ZrO_2 -2% TiO_2).

Test specimens of the WSi_2 - ZrO_2 / TiO_2 system survived an average of 3 hours exposure to static air oxidation at 3000°F. When satisfactory coating and sintering procedures were established for each coating system, 22 coupons, 12 sheet tensile specimens, and 10 leading edge specimens were coated with each composition and delivered to NASA for evaluation.

ELECTROPHORETIC DEPOSITION EQUIPMENT FOR GRADATED COATINGS

When a D. C. potential is applied across two electrodes which dip into a dispersion of colloidal or near-colloidal size particles (i. e. 0.2-40 micron) suspended in a non-aqueous medium, the particles are observed to migrate to one of the electrodes where their charge is neutralized and they are deposited. This phenomenon, termed electrophoresis, was first observed in 1809 by Reuss^{1*}. Some of the major commercial applications of this process include the deposition of thermionic and insulating materials on electron tube filaments, formation of rubber gloves by electrophoretic deposition of latex onto a mandrel and, more recently, the fabrication of aluminum-clad steel and the painting of steel furniture, partitioning and other components²⁻⁸.

The theory of electrophoresis, which has been discussed by many authors⁹⁻¹⁴ is a controversial subject which will be reviewed here only briefly. The most widely accepted theory, due to Stern¹⁵, gives the mobility of the suspended particle (U) as a function of the applied field (E), zeta potential of the adsorbed double layer (z), and dielectric constant (D) and viscosity (η) of the fluid medium as follows:

$$U = \frac{zED}{4\pi\eta}$$

It will be noted that the mobility is independent of the particle size, shape, and composition so long as the zeta potential and suspending medium are constant. The zeta potential can be made to remain constant through the use of activating agents which are adsorbed uniformly upon the surface of all of the particles in the suspension. This technique is extremely important since mixtures of two or more materials, when dispersed, will deposit upon a substrate in exactly the same ratio that exists in the coating bath. Thus alloys, cermets, and mixed refractory coatings may be prepared by the electrophoretic process to yield deposits wherein the coating composition is indistinguishable from the same material prepared in bulk by conventional powder metallurgical or ceramic techniques.

* Superscripts refer to literature sources listed in the Bibliography

In the electrophoretic process the coating materials are prepared in the form of a fine powder of about 10 micron average particle size. If more than one component is desired in the coating, the individual powders are either prealloyed or are weighed in the required proportion and blended. For the most common coating materials the powders are commercially available in -325 mesh size. If a finer particle size is desired, the powders are jet-milled or ball-milled in alundum, steel, or silicon carbide-lined jars. The powder mixture is then leached to remove impurities, and added to a mixture of isopropanol and nitromethane. The powders generally acquire a static surface charge during ball-milling, and a charge may also be induced on the particle surfaces by the addition of certain proprietary protein-like additives. The resulting dispersion is therefore stabilized by electrostatic repulsion of the charged particles. The dispersion concentration is generally maintained between 1 and 10 wt %, depending upon the coating rate desired.

The coating equipment consists of a stainless steel tank with an overflow at the top and an opening at the bottom. The dispersion is agitated by a recirculating pump whose exhaust is connected to the bottom of the coating tank. The tank serves as an inert electrode and the article to be coated is the second electrode. The electrodes are connected to a D.C. regulated power supply and an external timer which cuts off the power after a set interval. Coating is accomplished at 20-200 V.D.C. and about 5-20 ma. for 0.25-5 minutes depending upon the coating thickness which is desired. After coating, the article is dried in air or under an infra-red lamp and, if the point of electrode contact must also be coated, this area is manually "patched" by applying some of the powdered material of the dispersion with a rounded tool. The coating at this point is about 40% dense and has considerable green strength, however, it is not yet bonded to the substrate or fully densified. To increase the strength of the green coating, the article may then be hydrostatically pressed at 10,000-100,000 psi. This step is required only when the coating must be shipped in the green state or when difficult-to-sinter chemistries are involved. Following hydrostatic pressing the coating is sintered or hot-pressed to increase its density and to bond it to the substrate. It is here that the most variability is encountered in the process. The sintering time, temperature, and atmosphere must be adjusted to the properties of the coating-substrate system. Following sintering, the coating is evaluated by microscopic inspection of the surface and of sections through the specimen, and physical and chemical measurements such as density, porosity, mechanical properties, chemical uniformity, and oxidation or abrasion resistance are also easily obtainable.

Critical variables in the deposition step, which control the uniformity, adherence, and reliability of the coating are:

1. Surface cleanliness and finish of the substrate.
2. Particle size and size distribution of the dispersed powder.
3. Maintenance of the zein and electrolyte concentrations at the proper levels.
4. Purity of the powder.
5. Electrode geometry and deposition voltage.

In the present program, the normal electrophoretic deposition equipment described above was modified so as to permit the deposition of a 2-component intermetallic compound-refractory oxide coating in which the composition of the coating was continuously gradated from a high concentration of the intermetallic adjacent to the substrate to a high concentration of refractory oxide at the outer surface. The gradation in composition was investigated for two reasons; to provide a mechanism for bonding the stable refractory oxide to the substrate, and to overcome the mismatch of coefficients of thermal expansion between the Ta-10W substrate and the oxide outer surface. Heretofore, such gradation in a coating has only been approached by plasma spraying a series of layers of varying composition¹⁶. A laminar structure of this type, however, would be mechanically weaker than a homogeneously gradated coating.

The simplest method of preparing a gradated oxide-intermetallic compound coating by electrophoretic deposition is to fill a coating tank containing an overflow with a dispersion of the intermetallic compound, and to pump a second dispersion of a refractory oxide into the tank during the application of the coating voltage to the sample. There are two major problems with this system:

1. A large volume of the oxide dispersion is required, and the mixed dispersions must be discarded after each experiment.

2. Assuming perfect mixing of the two dispersions, the concentration of the intermetallic compound in the tank decreases exponentially with time. Control of the concentration gradient in the coating is therefore difficult.

To minimize the volume of dispersion which is required and to obtain positive control of the concentration of the two components during the coating cycle, a special pumping system and a continuous flow coating vessel were designed. The system, shown in Figure 1, consists of two Sigmamotor Type T-8 tubing pumps driven by a 1/2 hp, 1800 rpm motor which is coupled to the pumps through a Vickers variable speed reducer and two variable speed drives connected in opposition. The maximum pumping speed of the tubing pumps is set by the output rpm of the Vickers control. The function of the two variable speed drives is to vary the speed of one pump from 5%-100% of the maximum while the other pump operates between 100% and 5% of the maximum. The equipment was designed and purchased under Vitro's in-house research program.

In the system described above the coating voltage is held constant and the coating time is adjusted by means of the variable speed drives. To insure that a uniform gradation is obtained in the system it is necessary that the coating rate of the two dispersions be approximately equal. The coating rate, in turn, is governed primarily by the concentration of the two dispersions, and is also affected by the particle size distribution of the powders and their surface adsorbing properties.

A calibration curve for the variation in composition of the pump effluents as a function of the setting of the control on the Graham variable speed drive was determined by pumping the fluid used in a standard electrophoretic bath with no solids present. The curve is shown in Figure 2. The composition vs. pump drive setting curve was nearly linear over the range of the control, and the slope of the curve was found to be invariant at input pumping speeds ranging from 210-840 rpm. The average total volumetric flowrate at 210 input rpm was 15 ± 3 ml/min; the variation of 3 ml/min occurring as the setting on the Graham drive was moved above or below the center position. This variation was probably due to small differences between the pumping rates of the Sigmamotor tubing pumps. As the input rpm to the tubing pumps was increased from 210-840 rpm, the total flowrate increased from 15 to 75 ml/min.

Studies were also carried out to determine the effect of solids concentration upon the coating rate of the various intermetallic compounds and oxides. Before the dispersions were prepared, a sieve analysis was run on 1 gram of a typical oxide (CaZrO_3) and intermetallic compound (MoSi_2) to check the approximate particle size distributions. The analyses were performed with a standard 325 mesh sieve and with two extremely fine-mesh photoetched screens obtained from the Buckbee-Mears Company. The results indicated that both powders have approximately the same distribution.

Screen Analysis of 1 Gram of MoSi_2 and CaZrO_3 Powder

	<u>MoSi_2</u>	<u>CaZrO_3</u>
% -325 mesh	0	0
% on 8-12 micron screen	25	35
% on 3-7 micron screen	50	49
% through 3-7 micron screen	<u>6</u>	<u>0</u>
% recovery	81	84

To prepare uniformly gradated coatings from two dispersions of different compounds at the same concentration it is necessary that the coating rates of the individual dispersions be equal or nearly equal. Accordingly, the coating rates of dispersions containing 1 wt.% of 90ZrB_2 - 10MoSi_2 , MoSi_2 , WSi_2 , 8% Y_2O_3 -stabilized ZrO_2 , 3.5% CaO -stabilized ZrO_2 , SrZrO_3 , and CaZrO_3 were investigated. The dispersions were prepared as follows:

-325 mesh solids	8.5 grams
60% isopropanol-40% nitromethane	850 ml
Zein binder solution	6 ml
Electrolyte solution	0.5 ml

Steel panels were coated from these dispersions at 200 and 300 volts for periods of 1/4, 1/2, 1, 2, 3, and 4 minutes, and the coating thickness and weight increase was recorded as a function of time. The results, shown in Figures 3 and 4 indicated that the coating rates of the MoSi_2 and calcia-stabilized zirconia were lower than those of the other materials. The curves for yttria-stabilized zirconia and 90ZrB_2 - 10MoSi_2 indicate that these dispersions can be made to coat at the same rate at some potential intermediate between 200 and 300 VDC.

Since the principal factor which affects the coating rate is the particle size distribution of the dispersion, a sedimentation experiment was performed on several of the coating materials by the procedure reported by Skinner and Riley¹⁷. A weighed quantity of nominal -325 mesh powder was slurried in

distilled water and poured carefully into the top of a 34 inch high column of deionized water. The slurry was allowed to sediment for 22 minutes, then the material which had settled to the bottom was removed and recycled for a second 22-minute period through an identical column. The coarse and fine fractions were then recovered, dried, and weighed. According to Stokes' Law, the 22-minute sedimentation time will remove all particles larger than 15 microns in diameter, assuming an average particle density of 6 g/cc. The pertinent equation for the time of fall (t), of spherical powder of radius r and density d_1 , through a column of liquid of density d_2 , height h, and viscosity n, under the gravitational acceleration g is:

$$t = 9hn/2gr^2 (d_1 - d_2)$$

The results of the sedimentation trials are summarized in Table 1 together with data obtained on several of the same materials after milling at 150 rpm under isopropanol in a steel mill containing several steel spheres for six or forty-eight hours. The milled materials were evaporated to dryness, leached with 250 ml of 50% HCl to remove metallic contaminants, and then washed and dried before use.

The wide variation in the particle size distribution of the nominal -325 mesh powders is evident from the data of Table 1 and, as reported in a later section, had a serious effect upon the sinterability of the coatings. Based upon these results, the remaining oxides and intermetallics were milled to a finer average particle size.

SCREENING OF INTERMETALLIC-REFRACTORY OXIDE COMBINATIONS

A number of intermetallic-refractory oxide combinations were investigated for the purpose of selecting two systems which appeared promising as oxidation-resistant coatings for the Ta-10W specimens.

Physical Property and Analytical Data for the Substrate and Coating Materials. - The physical property data of interest in this program for the Ta-10W substrate and the coating materials to be studied are listed in Table 2.

The sources and forms of the commercially available coating materials are listed in Table 3. The $TaAl_3$ was not available and was synthesized from the elements.

Analytical data for the various intermetallic compounds and refractory oxides used in this program are included in Tables 4 through 8.

Two sources of WSi_2 were used in this program. Source 'A' material was used in the early experimental work and the source 'B' material was purchased during the latter part of the program and was used for the preparation of the final samples for NASA. A spectrographic analysis of the source 'A' WSi_2 is given in Table 8. Analysis of source 'B' material was as follows:

% Tungsten	76.0 %
% Silicon	23.4 %
% Carbon	0.12%
% Iron (Fe)	0.15%
% Oxygen	0.20%

Sintering Studies of Pure Oxides, Intermetallic Compounds and Composite Systems. - To determine the approximate temperature range required to sinter the gradated coatings to be prepared in the program, sintering trials were conducted on pure oxide and intermetallic compounds in the form of pressed discs. Before preparing the discs, all materials were ballmilled to 100% -325 mesh size in a chrome-manganese steel mill, and the resulting powders were leached in dilute hydrochloric acid, washed, and dried to remove metallic contaminants. The powders were then pressed in a steel die at 20,000 psi to 0.5 in. diameter discs, and these samples were sintered under various conditions. Following sintering, the apparent density was determined by weighing in air and in water. The sintering and density data are given in Table 9. The samples were then sectioned, mounted, polished, and photographed. At 1400°C in argon all of the intermetallic compounds except Ta_2Be_{17} could be sintered to apparent densities higher than 80% of theoretical in one hour. In the oxide systems only $SrZrO_3$ reached a reasonable density under these conditions. Calcium zirconate could be sintered to high apparent density at 1700°C for 45 minutes in argon, and an apparent density of 89% was attained with yttria-stabilized zirconia when this material was vacuum sintered at 1900°C. The calcia-stabilized zirconia was more refractory, and yielded an apparent density of only 74% after 45 minutes in argon at 1700°C.

Photomicrographs of cross sections through sintered specimens of $SrZrO_3$, $CaZrO_3$, and 8% Y_2O_3 -stabilized zirconia are shown in Figures 5 and 6.

Sintering of Oxide-Intermetallic Powder Mixtures. - To determine the behavior of the oxide-intermetallic systems when in contact, powder blends containing 50wt% of a refractory oxide and an intermetallic compound were prepared. The mixed powders were pressed in a steel die to 0.5 in. diameter discs which were sintered in argon at 1700°C for 30 minutes. The immersion density of the samples was determined and compared to the theoretical value calculated on the assumption that no new phases were formed from the two components. The results are listed in Table 10. The sinterability of the mixtures paralleled that of the pure compounds. The calcia-stabilized zirconia yielded the lowest densities when combined with the various intermetallic compounds, and the tantalum beryllide gave the lowest density of all the intermetallics when combined with the various oxides. The best results, under these sintering conditions were obtained with combinations of CaZrO_3 or SrZrO_3 and the various silicide compounds. Photomicrographs of composites of SrZrO_3 with TaSi_2 and 90ZrB_2 - 10MoSi_2 , and of CaZrO_3 plus TaSi_2 are shown in Figures 7 and 8. The structures appear to be coarse dispersions of the intermetallic compound in a sintered matrix of oxide with no evidence of interaction between the two phases.

Additional work was carried out on the sintering of calcia-stabilized and yttria-stabilized zirconia, alone and in combination with various intermetallic compounds. These systems required further study since, as shown in Table 10 the zirconias were the most difficult of the oxides to sinter to high density at temperatures below 1900°C. In addition previous work on the pure intermetallic compounds showed that synthetic $\text{Ta}_2\text{Be}_{17}$ could not be sintered to a dense body in 30 minutes at 1400°C. However, when the time at 1400°C was extended to 2 hours and a commercial powder was used, a density of 93% of theory was obtained.

The results of the additional sintering experiments on a variety of materials are summarized in Table 11. The last column of the table refers to the figure number of a photomicrograph of the sample which will be found in subsequent pages of this report.

Based on the data obtained, yttria-stabilized zirconia, calcium zirconate, and strontium zirconate in combination with any of the intermetallic compounds appeared to be the most practicable systems for further study as candidate coating systems.

Studies of Bonding Between Oxides and Intermetallic Compounds. - To study the bonding which occurs between oxide and intermetallic phases, and to explore the possibility of interfacial reactions or eutectic formation, a series of experiments were performed in which 3-layer composites were pressed and sintered together and then examined microscopically. The composites consisted of a sandwich of a 50:50 mixture of oxide and intermetallic between a layer of pure oxide and a layer of pure intermetallic. To prepare the composites, the three types of powders were poured in sequence into a 3/4 in. diameter steel die and unidirectionally pressed at 21,600 psi. The compact was placed in a rubber sheath which was evacuated to remove entrapped gases and was then isostatically pressed at 50,000 psi. The 3-layer discs were finally sintered at 1700°C for 30 minutes under reduced pressure. The compounds selected for study were those which yielded the highest sintered density in earlier work on 50:50 powder mixtures; i.e., SrZrO₃-MoSi₂, SrZrO₃-ZrB₂/MoSi₂, SrZrO₃-TaAl₃, CaZrO₃-MoSi₂, and CaZrO₃-TaSi₂. Typical microstructures of these composites are shown in Figures 13 through 15. Several common features can be seen in the metallographs. The bonding between the 50:50 mixtures and the oxide layer is better than that between the mixture and the intermetallic compounds in both the SrZrO₃-MoSi₂ and SrZrO₃-TaAl₃ systems. This is probably due to the fact that the oxide forms the matrix in the central composite layer and it therefore tends to sinter together with the outer oxide layer of the sandwich. The oxide also occupies more than 50% of the volume of the composite layer since the mixture was prepared on a weight basis and the density of the oxide is lower than that of the intermetallic compound. The photomicrographs of the mixed compositions (Figures 13-15) indicate that the average particle size of the intermetallic compounds is larger than that of the oxides, resulting in a coarse dispersion. The microstructural appearance of the 3-layer composite samples was quite encouraging and indicated that a dense structure could be achieved in a continuously gradated coating.

Oxidation Screening Tests of Intermetallic Compounds. - In previous work it was found that each of the intermetallic compounds under study could be sintered to relatively high density in 1 to 2-1/2 hours at 1400°C in argon. Since none of the compounds was eliminated from further consideration as a coating material on the basis of sinterability, a second screening test was carried out by determining the weight gain or loss of sintered discs of the individual compounds which were subjected to oxidation by heating with an oxyacetylene torch at 1700°-2500°C for various periods of time. Brightness temperatures were determined during the test by sighting on the heated face of the specimen with an optical pyrometer. The measured temperatures were not corrected for emittance. The results of the oxidation trials are summarized in Table 12.

Based upon the results of the oxidation trials, MoSi₂ and 90ZrB₂-10MoSi₂ appeared promising for application at temperatures in the neighborhood of 3500°F (1950°C).

COATING STUDIES

Intermetallic Compounds. - The objective of these studies was to determine the optimum conditions for obtaining adherence of the intermetallic compounds and oxides to the Ta-10W alloy substrate, and to investigate factors affecting the ductility of the substrate. The pure intermetallic compounds were studied first since they form the bonding layer of the graded coating to the substrate. The sintering experiments were carried out in a Globar-heated tube furnace at temperatures to 1400°C and in an induction heated furnace at higher temperatures. All sintering was carried out in a flowing argon atmosphere.

At 1400°C for 1 hour, TaAl_3 , TaSi_2 , and $\text{Ta}_2\text{Be}_{17}$ coatings on Ta-10W sintered well but were not adherent to the substrate. Under the same conditions, MoSi_2 and 90ZrB₂-10MoSi₂ also sintered to high density and exhibited slight adherence. When the temperature was increased to 1700°-1800°C, the TaAl_3 coating reacted with the Ta-10W to form a liquid phase. The $\text{Ta}_2\text{Be}_{17}$ and TaSi_2 coatings did not bond to the substrate in this temperature range. After 3 hours at 1800°C, the MoSi_2 bonded to the substrate, but only moderate adherence was obtained with the 90ZrB₂-10MoSi₂. In a separate experiment an uncoated Ta-10W panel was exposed at 1700°-1800°C to the argon atmosphere for one hour. After heating, the sample remained bright, indicating that surface oxidation does not occur during sintering of the coatings and is not causing loss of adherence.

In experiments to determine the effect of metallic binders upon adherence, ten weight percent of -325 chromium, nickel, and tantalum powders were added to dispersions of 90ZrB₂-10MoSi₂ and MoSi_2 , coatings were pressed at 20 tsi and sintered for one hour in argon at 1700°-1750°C. The results, summarized in Table 13 indicate that both chromium and nickel binders caused severe embrittlement of the substrate and that nickel was ineffective in improving adherence of the coatings to the substrate. The tantalum binder had no effect upon either the ductility of the substrate or the adherence of the coating.

In a subsequent experiment to check the effect of the organic binder used in electrophoretic deposition upon the adherence of the coating, a series of coating materials without binder were placed upon the Ta-10W panels, and these samples were heated to 1750°-1800°C in argon for one hour. The results are shown in Figure 16. Tantalum silicide and tungsten silicide plus 10% ZrB₂-10MoSi₂ reacted with the substrate to form a molten phase. The remaining materials; pure ZrB₂-10MoSi₂, ZrB₂-MoSi₂ plus

10%MoSi₂ or tantalum, MoSi₂, and -10 micron tantalum each sintered, but none adhered to the substrate.

In an effort to improve the sinterability and adherence of the inter-metallic compounds, the ZrB₂-10MoSi₂, WSi₂, TaSi₂, and MoSi₂ were screened through -325 mesh and the fines used for coating a set of Ta-10W panels. The panels were then isostatically pressed at 25 tsi and sintered in argon for one to two hours at 1700°-1800°C. The results are summarized in Table 14, and photomicrographs of two of the coatings are shown in Figure 17.

To check the effects of heat-treatment on the ductility of the substrate, an uncoated panel was heated at 1700°-1750°C in argon for one hour and hardness measurements were made of this specimen and of an uncoated, unheated panel. Sections through these samples are shown in Figure 18. After heat-treatment, the substrate microhardness increased from 340 kg/mm² to 470 kg/mm², however, the sample retained its bright appearance and remained ductile. Other hardness measurements of the coated samples are listed in Table 15. Substrates coated with ZrB₂-10MoSi₂ were invariably embrittled after heat-treatment, and diffusion of some component of the coating into the substrate is apparent in Figure 17. The silicide coatings, in general, had little effect upon the substrate ductility as evidenced by the microhardness measurements of Table 15.

Tungsten disilicide was also investigated as a base coating on Ta-10W for possible use in bonding to a graded WSi₂-refractory oxide coating. This material was prepared for use in electrophoretic dispersions by milling in isopropanol for 48 hours in a steel mill. After milling, the finely-ground powder was leached with a 50% HCl solution, then washed and dried.

Coatings of this material were applied electrophoretically to sand-blasted and chemically cleaned Ta-10W substrates. The coatings were densified to 30 tsi, and heat treated in argon at 1400°C for one hour. The resultant coatings appeared quite dense and adherent to the substrates.

An alternate heat-treating procedure, designed to eliminate any free tungsten in the tungsten silicide powder, and to improve the density of the coating, consisted of embedding the coated specimens in silicon metal powder and heating at 1350°C for two hours in an argon atmosphere. Figure 19 shows a cross section of a specimen prepared in this manner. Good bonding to the substrate is evident and the heat treatment did not appreciably affect the ductility of the substrate.

A static oxidation test at 3000°F was made on a coated panel of this type. The coating resisted penetration by oxygen for 30 minutes at this temperature even though it was only one mil thick. Figure 20 shows the specimen after the oxidation test.

Since the test results with this material were very promising, it was therefore anticipated that a WSi_2 coating, prepared in the manner described, would serve as an excellent base for WSi_2 -oxide graded coatings on Ta-10W alloy substrates.

Diffusion Barrier Studies

Since the use of a thin layer of MoSi_2 or Mo metal coated to the Ta-10W panels beneath the graded coating appeared promising in improving adherence, further studies of different materials as diffusion barriers were undertaken.

The molybdenum barrier layer was prepared by depositing molybdenum metal on chemically cleaned Ta-10W, pressing isostatically at 20 tsi, and sintering in argon for 2 hours at 1500°C. The molybdenum coating, as shown in Figure 21, was dense and well-bonded and there was no evidence of contamination of the substrate. The hardness of the Mo-coated substrate was 322 KHN (50g load) as compared to 235 KHN for an uncoated, annealed, 20 mil panel.

As complete elimination of embrittlement of the Ta-10W was not achieved with molybdenum, a second material, tungsten, was studied for possible use as a diffusion barrier. Recently, a paper was published¹⁸ indicating that tungsten and rhenium are the best of the available refractory metals (m. p. above 1700°C) for minimizing diffusion of tantalum. In this study, diffusion couples were prepared of tantalum combined with W, Re, Os, Ru, Ir, Hf, V, Cr, and Pt. The couples were annealed for 4 hours at 1700°C or for 3 hours at 1800°C in argon and then examined microscopically to determine the extent of interdiffusion. Of the materials studied, Ta-W and Ta-Re showed minimum diffusion zones under the specified annealing conditions. Iridium and osmium, which also evidenced low diffusion, were rejected because of the formation of very hard brittle phases at the diffusion interface. The experimental results are summarized in Table 16.

Based upon this evidence, tungsten coatings were electrophoretically deposited upon Ta-10W substrates which were previously sandblasted and chemically cleaned. The coated specimens were then densified at 20 tsi and sintered at 1400°C for two hours in an argon atmosphere. A coating of ZrB₂-10MoSi₂ was then applied to determine if embrittlement of the substrate could be avoided by the use of a diffusion barrier. After densifying the composite coating at 40 tsi, the specimens were sintered at 1650°C for two hours in argon. This procedure was identical to that used previously for the molybdenum diffusion barriers.

The adherence of these coatings for specimens fired to 1650°C was poor. The coatings were split and pulled away from the substrate. It is likely that the high shrinkage of the tungsten layer was responsible for the poor adherence. Because of this difficulty, no further work was done with the ZrB₂-10MoSi₂ intermetallic.

Refractory Oxide Studies

In a parallel NASA program conducted by Vitro¹⁹, studies were made to improve the density of the refractory oxide phase of the graded coating system by the addition of a fluxing component. The purpose of this material was to provide a liquid phase at temperatures lower than the melting point of the primary refractory oxide. The liquid phase then acts as a sintering aid by promoting material transport, leading to increased densification rates and higher ultimate densities.

Various investigators have studied the effect of metal and oxide additions to zirconia. Ruh, et al²⁰ note the effect of liquid phase titanium in promoting the sintering of zirconia. In other work, Ruh and Garrett²¹ demonstrated the increased sintering of zirconia by additions of chromium

in quantities above the solubility limit, i. e. over 1%. This is another example of the beneficial effect of liquid phase formation during sintering.

Additions other than metals may prove more useful for present purposes; for example any one of a number of oxides which combine with zirconia to form eutectics which melt at temperatures below the melting point of zirconia itself. A number of potentially applicable liquidus curves²² for zirconia and other oxides are shown in Figures 22 and 23.

One experiment was performed in which a pellet composed of 90 ^{w/o} ZrO₂(CaO) and 10 ^{w/o} TiO₂ was treated at 1700°C for two hours in an argon atmosphere. This pellet was fused and hard and an extensive, even excessive, amount of liquid phase was present during sintering to aid the densification.

Considerable effort was also devoted to the preparation, sintering and study of CaO-stabilized ZrO₂ samples to which various potential fluxing materials were added.

Ten gram batches of each composition were weighed, isopropyl alcohol was added, and the sample was mixed thoroughly in a mortar while the alcohol evaporated. The mixed material was then dry-pressed into 1/2" diameter x 1/8" thick pellets. These pellet specimens were sintered in argon at 1700°C for two hours.

The results of these experiments are listed in Table 17 and applicable photographs of several specimens are shown in Figures 24, 25, and 26. The materials which appeared to have the greatest effect in promoting the densification of CaO-stabilized ZrO₂ at 1700°C were TiO₂ and Al₂O₃.

SINTERING STUDIES OF TWO SELECTED GRADATED COATING SYSTEMS

Based upon the work reported in the previous sections, the following two systems were chosen for application to the Ta-10W substrate specimens:

MoSi₂-MoSi₂/CaO-stabilized zirconia grade
WSi₂-WSi₂/2%TiO₂-CaO-stabilized zirconia grade

Sintering and oxidation tests performed with these systems are reported in the following paragraphs.

MoSi₂-Refractory Oxide Systems. - In all experiments, the Ta-10W substrate was prepared by grit-blasting, then chemical cleaning in an etching bath containing 15 ml lactic acid plus 5 ml of nitric acid, plus 5 ml of hydrochloric acid, and washing in distilled water. Table 18 summarizes the significant experiments which were performed. The data indicated that adherent coatings on Ta-10W could be produced from MoSi₂ which had a particle size of approximately 5 microns or less, and that a thin layer of MoSi₂ which is sintered on the Ta-10W substrate will bond to the subsequent gradated coating. Improved adherence was also obtained by depositing from a 5% instead of a 1% dispersion.

A photomicrograph of a MoSi₂-ZrO₂(CaO-stabilized) coating over a sintered MoSi₂ layer is shown in Figure 27. This photograph shows the MoSi₂ to Ta-10W bond which has developed after sintering at 1400°C. The gradated layer appears very porous in this photograph because the oxide was soft after sintering at this temperature and could not be polished without causing pull-outs and voids.

Another portion of this same specimen was refired to 1700°C for one hour. The results are shown in Figure 28. Visual inspection of this sample showed that hardness and density were higher than in the 1400°C specimen shown in Figure 27.

To prepare coated Ta-10W specimens for oxidation tests, a base coat of MoSi₂ (leached with HCl and ball-milled) was deposited at 100 volts for 1-1/2 minutes, after which it was isostatically pressed at 30 tsi and sintered in argon at 1400°C for one hour. A gradated coating of MoSi₂-ZrO₂ was then applied to the MoSi₂-coated Ta-10W substrate.

The gradated coatings were isostatically densified at 30 tsi and sintered at 1400° and 1600°C for two hours in an argon atmosphere. Measurement of the coatings indicated that the thickness of the sintered MoSi₂ base coat was one mil and that of the MoSi₂-ZrO₂ grade was three to four mils.

The coatings sintered at 1400°C were only presintered. Those sintered at 1600°C were improved in density and adherence, and had a hard glass-like surface. Some porosity, however, was still evident in the gradated layer.

Oxidation tests at 3000°F were conducted on the MoSi₂-ZrO₂ specimens. Failure occurred almost immediately on specimens which were prepared by sintering at 1400°C. The specimens prepared by sintering at 1600°C survived 15-20 minutes before oxidation effects could be noticed. A photograph of an oxidized specimen is shown in Figure 29.

The poor results on these specimens indicated that improvement in the sintering of the specimens is necessary to obtain better oxidation resistance. The major defect, as shown in the photomicrograph, was the high porosity of these coatings.

WSi₂-Refractory Oxide Systems. - Small panel specimens having gradated coatings on Ta-10W were prepared by electrophoretic deposition and isostatic densification at 20 tsi. The primary objective of this work was to determine the effect of increased sintering temperature on the structure of the coating, and to promote the development of non-porous surfaces for improved oxidation resistance. The gradated coating systems studied and the results of sintering experiments are shown in Table 19.

These experiments indicate that the increase in sintering temperature was beneficial in increasing the densities of the WSi₂-CaZrO₃ and WSi₂-Al₂O₃(MgO) gradated coatings. On the other hand, the density of the WSi₂-ZrO₂(CaO) gradated coating was still below 90% of theoretical, and the 1700°C temperature used was apparently still too low by several hundred degrees for complete sintering of the very refractory ZrO₂ component.

Coating, sintering, and oxidation testing were performed for specimens of four different gradated coating systems:

1. CaZrO₃-WSi₂
2. Al₂O₃(4 MgO)-WSi₂

3. (3.5%CaO-stabilized ZrO_2 -2% TiO_2)- WSi_2
4. (3.5%CaO-stabilized ZrO_2 -5% Al_2O_3)- WSi_2

All specimens were prepared by depositing WSi_2 onto a sandblasted and etched Ta-10W panel, densifying, sintering in argon at 1400°C , and siliconizing at 1350° - 1375°C to yield a 1.5-2.0 mil-thick WSi_2 layer. Next, the desired gradated coatings were deposited onto the WSi_2 , densified, sintered at 1600°C , and siliconized at 1375°C . For comparison purposes, a few specimens were prepared without siliconizing the gradated portion of the coating.

The specimens were oxidation tested in static air as shown in Table 20, which summarizes test conditions and results.

A study of the results of these oxidation tests indicated that the best protection was obtained with the $\text{Al}_2\text{O}_3(\text{MgO})$ - WSi_2 and 3.5%CaO-stabilized ZrO_2 -2% TiO_2)- WSi_2 coatings. Judging from post-test appearance, both types were either solid or very viscous liquids at the test temperature. In both coatings, gas bubbles were apparent under the surface. The cause of these bubbles was not determined. Cross sections of these two coatings are shown in Figures 30 and 31.

PREPARATION OF FINAL SAMPLES FOR NASA EVALUATION

In the final phase of this program, the two gradated coating systems discussed in the previous section were each applied to 12 tensile, 10 leading edge, and 22 coupon-type specimens. Drawings of the three types of specimens are shown in Figure 32. The sample preparation procedure for both coatings was as follows:

MoSi₂-CaO-Stabilized Zirconia Gradated Coating on Ta-10W. -The procedure used in preparing these samples was as follows:

1. Grit-blast, hand-radius edges and acid etch in 15-5-5 mixture of lactic acid, nitric acid, and hydrofluoric acid for 10 minutes.
2. Coat with MoSi_2 at 100 VDC for 1-1/2.
3. Press at 30 tsi and fire in argon for 1 hour at 1400°C .

4. Coat with silicon, heat 2 hours in argon at 1350°C.
5. Apply MoSi₂/CaO-stabilized zirconia gradated coating at 150 VDS for 2-1/2 minutes.
6. Press at 20 tsi and sinter for 1 hour in argon at 1600°C.

WSi₂-(3.5%CaO-Stabilized ZrO₂-2%TiO₂) Coatings on Ta-10W. -

1. Grit-blast lightly with Grade A-10 Al₂O₃ and etch in mixture of 2HF:2HNO₃:1H₂SO₄.
2. Electrophoretically coat 4 mils of WSi₂.
3. Sinter 2 hours in argon at 1600°C.
4. Embed in silicon powder and heat 2 hours in argon (or at pressure of 0.01 torr) at 1350°C.
5. Apply 5 mils of gradated coating at 100 VDC for about 2-5 minutes.
6. Press at 10 tsi and sinter for 1 hour at 1600°C in argon.
7. Embed in silicon powder and heat treat at about 0.01 torr for 16 hours at 1300°C.

BIBLIOGRAPHY

1. Encyclopedia Britannica, Vol. 6, p. 226.
2. E. J. Roehl, Metal Finishing, 42, 313-316 (May, 1944).
3. J. C. Dunbar and T. J. Mitchell, J. Sci. Food Agriculture, 4, 190-96 (1953).
4. S. A. Troelstra, Phillips Technical Review, 12 No. 10, 293-303 (April, 1951).
5. G. F. Kinney and J. V. Festa, Sylvania Technologist, 10 #2, 48-52 (April, 1957).
6. A. H. Stewart, Electroplating, 2, 513-518 (August, 1949).
7. M. Bier, Ed., "Electrophoresis, Theory, Methods, and Applications," Academic Press, N. Y. (1959).
8. Anon, Metallurgia, 67, #402, 189-190 (April, 1963).
9. E. J. W. Verwey, Rev. Trav. Chim., 60, 625 (1941).
10. H. C. Hamaker, Trans. Farad. Soc., 36, 180 (1940).
11. H. C. Hamaker and E. J. W. Verwey, Trans. Farad. Soc., 36, 186 (1940).
12. H. C. Hamaker, *ibid*, 36, 279 (1940).
13. C. G. A. Hill et al, *ibid*, 43, 407 (1947).
14. H. Koelmans and J. Th. G. Overbeek, Disc. Farad. Soc., 18, 52, (1954).
15. O. Stern, Z. Electrochem., 30, 508 (1942).
16. ITRI Summary Report B237-34 under Contract NAS7-113, "Protective Coatings for Refractory Metals in Rocket Engines," (24 March 1965).

BIBLIOGRAPHY

17. K. G. Skinner and M. J. Riley, Bull. Amer. Ceram. Soc., 36 #10, (1957).
18. E. M. Passmore, et al, "Diffusion Barriers for Columbium and Tantalum," Trans. ASM, 57, 760-765 (1964).
19. Contract NAS9-3413, NASA/Manned Spacecraft Center, Vitro Laboratories Monthly Progress Reports 7 through 10 (8 February - 7 June 1965).
20. R. Ruh, et al, "Effect of Metal Additions on the Microstructure of Zirconia," J. Amer. Ceram. Soc. 47, 632 (1964).
21. R. Ruh, et al, "Reactions of Zirconia and Chromium," ibid, 47, 627 (1964).
22. E. Ryshkewitch, "Oxide Ceramics," Academic Press, N. Y. (1960).

TABLE 1
SEDIMENTATION TRIALS OF COATING MATERIALS

<u>Material</u>	<u>Preparation</u>	<u>%Coarse (>15μ)</u>	<u>%Fine (<15μ)</u>
WSi ₂ (Source A)	As-received -325 mesh	57.3	42.7
3.5CaO-96.5ZrO ₂	As-received -325 mesh(lot#1)	86.0	14.0
3.5CaO-96.5ZrO ₂	As-received -325 mesh(lot#2)	13.4	86.6
3.5CaO-96.5ZrO ₂	Lot #2, milled 6 hours	3.0	97.0
MoSi ₂	As-received -325	48.7	51.3
MoSi ₂	Milled 48 hours	6.3	93.7
SrZrO ₃	As-received -325 mesh	28.8	71.2
8Y ₂ O ₃ -92ZrO ₂	As-received -325 mesh	32	68

TABLE 2
SELECTED PHYSICAL PROPERTIES OF REFRACTORY MATERIALS

	<u>M. P. (°F)</u>	<u>Density (g/cc)</u>	<u>Knoop Microhardness 100g load (kg/mm²)</u>	<u>Thermal Expansion Per °F x 10⁶</u>
Al ₂ O ₃	3720	3.96	2260	4.7 (to 1500°F)
ZrO ₂ (cubic)	4760	5.6-6.26	900	4.7 (to 3800°F)
Ta-10W	5495	16.9	230(annealed)	3.9 (1600-2200°F)
Ta ₂ Be ₁₇	3610	5.05	1120*	8.72(to 2750°F)
TaSi ₂	4350	9.1	1200	4.67(to 2600°F)
90ZrB ₂ -10MoSi ₂	4280	6.12(calc.)	1500	3.9
MoSi ₂	3690	6.24	1260	4.5 (to 2600°F)
CaZrO ₃	4170	4.78	--	6.4 (to 2400°F)
TaAl ₃	4950	6.92	--	6.5
SrZrO ₃	4900	5.48	--	--
3.5%CaO Stabilized ZrO ₂	4700	5.65(calc.)	--	--
8%Y ₂ O ₃ Stabilized ZrO ₂	4800	5.67(calc.)	--	--
WSi ₂	3955	9.8	--	4.4 (to 1958°F)

*Vickers Hardness 2.5 kg load

APPENDIX A

TABLES

TABLE 3

SOURCE AND FORM OF COATING MATERIALS

<u>Material</u>	<u>Source and Form</u>
3.5% Calcia-stabilized, hafnia-free zirconia	Zirconium Corp. of America, Grade CH nominal 5 micron powder
8% Yttria-stabilized zirconia	Zirconium Corp. of America, nominal 5 micron powder
Calcium zirconate	Zirconium Corp. of America, nominal 5 micron powder
Zirconium diboride	A. D. Mackay, -200 mesh powder 99% pure
Molybdenum disilicide	Shieldalloy, 3 micron powder
Alumina (alpha)	Linde Type A, 0.3 micron powder 99.98% pure
Tantalum silicide (TaSi_2)	A. D. Mackay, -150+325 mesh powder, 99+% pure
Tantalum beryllide ($\text{Ta}_2\text{Be}_{17}$)	Brush Beryllium, -200 mesh powder
Strontium zirconate (SrZrO_3)	Zirconium Corp. of America, -325 mesh powder. (Typical analysis 0.1% Al_2O_3 , 0.1% SiO_2 , 0.9% CaO , 1.7% BaO , balance SrZrO_3)
Tungsten disilicide	Source A - Shieldalloy -325 mesh powder Source B - Cerac, Inc. -325 mesh powder

TABLE 4

TYPICAL ANALYSES OF ZIRCONIA COMPOUNDS

3.5%Calcia-Stabilized Zirconia		8%Y ₂ O ₃ -Stabilized Zirconia		Calcium Zirconate	
Al	200 ppm	ZrO ₂	91.8%*	CaZrO ₃	99 %
B	1	Y ₂ O ₃	8%**	SiO ₂	0.5%
Cd	0.5	SiO ₂	0.2%	L.O.I.	1 %
Cl	10	Al ₂ O ₃	0.1%		
Cr	50				
Co	1				
Cu	25				
Fe	500	*ZrO ₂ impurities shown in Column 1			
Hf	100				
Pb	5				
Mg	200	**Y ₂ O ₃ is commercial grade, containing about 10% rare earths, compatible with ZrO ₂			
Mn	10				
Ni	10				
Si	1500				
Ti	150				
(SO ₄)	500				

TABLE 5

SPECTROGRAPHIC ANALYSES OF MoSi_2 AFTER DILUTE HCl LEACH

Impurity	%	Impurity	%
Al	0.05	Ni	0.001
B	0.005	Sn	0.001
Ba	0.005	Ti	0.003
Ca	0.2	V	0.01
Co	0.005		
Cr	0.02		
Cu	0.007		
Fe	0.1		
Mg	0.005		
Mn	0.005		

Ag, Be, Bi, Ga, In, Pd, Sr, Zr - Not detected, 0.001%

As, Au, Cd, Hf, Ir, Li, Na, Os, Ru, Sb, Ta, W - Not detected, 0.05%

Ge, Cb, Pb, Rh, Pt - Not detected, 0.005%

TABLE 6

X-RAY DIFFRACTION ANALYSIS OF VITRO-SYNTHESIZED TaAl₃

<u>ASTM Standard Data* For TaAl₃</u>	<u>Vitro Sample</u>
<u>"d" Spacing (Angstroms)</u>	<u>"d" Spacing (Angstroms)</u>
4.26	4.28
3.50	3.50
2.71	2.72
2.28	2.29
2.13	2.13
1.92	1.91
1.75	1.75
1.68	1.685
1.56	1.561
1.47	1.470
1.43	1.427
1.36	1.358
1.29	1.293
1.26	1.262
1.21	1.213
1.17	1.168
1.14	1.145

*ASTM Card 2-1128

TABLE 7

SPECTROGRAPHIC ANALYSIS OF ZIRCONIUM DIBORIDE POWDER

<u>Impurity</u>	<u>%</u>	
Ca	0.005	Not Detected, 0.005% - Ag, Al, Ba, Be, Bi, Cu, Ga, In, Mg, Ni, Pd, Sn, Sr, V, Cb, Pb, Pt, Rh, Ge
Co	0.02	
Cr	0.01	
Fe	0.07	
Hf	1	Not Detected, 0.05% - As, Au, Cd, Ir, Li, Na, Os, Ru, Sb, Ta, Tl, W, Zn
Mn	0.001	
Mo	0.02	
Si	0.003	
Ti	0.05	

TABLE 8
SPECTROGRAPHIC ANALYSIS OF TUNGSTEN
DISILICIDE POWDER (SOURCE A)

SILVER -----	ND<0.001%
ALUMINUM-----	0.07%
ARSENIC-----	ND<0.05%
GOLD-----	ND<0.05%
BORON-----	0.01%
BARIUM-----	ND<0.001%
BERYLLIUM-----	ND<0.001%
BISMUTH-----	ND<0.001%
CALCIUM-----	0.03%
CADIUM-----	ND<0.05%
COBALT-----	0.001%
CHROMIUM-----	0.007%
COPPER-----	0.005%
IRON-----	0.1%
GALLIUM-----	ND<0.001%
GERMANIUM-----	ND<0.005%
HAFNIUM-----	ND<0.05%
INDIUM-----	ND<0.001%
IRIDIUM-----	ND<0.05%
LITHIUM-----	ND<0.05%
MAGNESIUM-----	0.007%
MANGANESE-----	0.005%
MOLYBDENUM-----	0.05%
SODIUM-----	ND<0.05%
COLUMBIUM-----	ND<0.05%
NICKEL-----	0.005%
OSMIUM-----	ND<0.05%
LEAD-----	ND<0.003%
PALLADIUM-----	ND<0.001%
PLATINUM-----	ND<0.005%
RUTHENIUM-----	ND<0.05
RHODIUM-----	ND<0.005%
ANTIMONY-----	ND<0.05%
SILICON-----	High
TIN-----	ND<0.001%
STRONTIUM-----	ND<0.001%
TANTALUM-----	ND<0.05%
TELLURIUM-----	ND<0.1%

THALLIUM-----	ND<0.01%
TITANIUM-----	0.02%
VANADIUM-----	0.001%
TUNGSTEN-----	High
ZINC-----	ND<0.03%
ZIRCONIUM-----	0.005%

* * *

(ND< - Not Detected Less Than)

TABLE 9
SINTERING TRIALS OF OXIDES AND INTERMETALLIC COMPOUNDS

<u>Compound</u>	<u>Sintering Conditions*</u>	<u>Apparent Density</u>	
		<u>g/cc</u>	<u>% Theoretical</u>
3.5CaO-96.5ZrO ₂	a	1.24	22
	b	3.99	71
	c	4.18	74
8Y ₂ O ₃ -92ZrO ₂	a	4.29	76
	b	4.44	78
	d	5.05	89
CaZrO ₃	a	3.48	73
	b	3.89	81
	c	4.12	86
SrZrO ₃	a	4.44	81
	b	4.45	81
	c	4.90	89
Al ₂ O ₃	c	3.50	88
TaAl ₃	a	6.18	89
Ta ₂ Be ₁₇	a	(Powdery, did not sinter)	
TaSi ₂	a	8.30	91
90ZrB ₂ -10MoSi ₂	a	5.82	95

*Conditions: a) 60 min., 1400°C in Argon
b) Same as (a); then 15 min., 1700°C in Argon
c) 45 min., 1700°C in Argon
d) 45 min., 1900°C, 10⁻⁶ Torr

TABLE 10

APPARENT DENSITY OF 50-50 BLENDS OF OXIDE-INTERMETALLIC COMPOUNDS AFTER SINTERING IN ARGON AT 1700°C FOR 30 MINUTES

Oxide	Intermetallic				
	TaAl ₃	Ta ₂ Be ₁₇	TaSi ₂	90ZrB ₂ - 10MoSi ₂	MoSi ₂
3.5CaO-96.5ZrO ₂	calc. density - 6.28	5.35	7.37	5.88	5.94
	obs. density - 4.6	1.7	4.34	2.8	2.67
	% Theory - 73%	30%	59%	48%	45%
8Y ₂ O ₃ -92ZrO ₂	6.29	5.36	7.38	5.89	5.95
	4.73	-	5.69	3.2	3.78
	75%	-	77%	54%	63%
CaZrO ₃	5.85	4.92	6.94	5.45	5.51
	4.56	3.25	4.93	4.58	-
	78%	66%	71%	84%	-
SrZrO ₃	6.20	5.26	7.29	5.80	5.86
	5.15	2.49	5.84	4.35	4.60
	67%	47%	80%	75%	78%
Al ₂ O ₃	5.44	4.50	6.53	5.04	5.10
	1.79	-	3.80	2.87	3.16
	33%	-	58%	57%	62%

TABLE 11

SINTERING TRIALS OF PURE OXIDES, INTERMETALLIC COMPOUNDS,
AND COMPOSITE SYSTEMS
(All samples isostatically pressed at 30 tsi before sintering)

Material	Sintering Conditions	Apparent Density (g/cc)	Apparent Density (%Theory)	Figure Number Reference
90ZrB ₂ -10MoSi ₂	60 min. -1400°C-Argon	5.82	95	9
Ta ₂ Be ₁₇	2-1/2 hrs. 1400°C-Argon	4.7	93	9
TaAl ₃	60 min. -1400°C-Argon	6.18	89	9
TaSi ₂	60 min. -1400°C-Argon	8.30	91	9
8Y ₂ O ₃ -92ZrO ₂	5 hrs. -1725°C-Argon	4.80	85	10
8Y ₂ O ₃ -92ZrO ₂	10 hrs. -1725°C-Argon	4.93	87	10
3.5CaO-96.5ZrO ₂	5 hrs. -1725°C-Argon	4.66	83.5	-
3.5CaO-96.5ZrO ₂	10 hrs. -1725°C-Argon	5.05	89	-
50(3.5CaO-96.5ZrO ₂)-50MoSi ₂	3-1/2 hrs. -1725°C-Argon	5.9	99	11
50(3.5CaO-96.5ZrO ₂)-50TaSi ₂	3-1/2 hrs. -1725°C-Argon	6.1	83	11
50(3.5CaO-96.5ZrO ₂)- 50(90ZrB ₂ -10MoSi ₂)	3-1/2 hrs. -1725°C-Argon	5.5	94	-
50(8Y ₂ O ₃ -92ZrO ₂)-50MoSi ₂	3-1/2 hrs. -1725°C-Argon	5.64	95	12
50(8Y ₂ O ₃ -92ZrO ₂)-50TaSi ₂	3-1/2 hrs. -1725°C-Argon	7.37	99	12
50(8Y ₂ O ₃ -92ZrO ₂)- 50(90ZrB ₂ -10MoSi ₂)	3-1/2 hrs. -1725°C-Argon	5.88	99	12

TABLE 12

OXIDATION TRIALS OF SINTERED INTERMETALLIC COMPOUNDS

<u>Compound</u>	<u>Temperature (°C)</u>	<u>Time (min)</u>	<u>%Wt. Change</u>	<u>Notes</u>
TaAl ₃	1700-1750	30	+ 2.4	-
	1750-1800	10	+ 6.3	-
	1850	1/6	-	Melted and reacted with Al ₂ O ₃ setter
	1900	1/4	-	Melted and reacted with ZrO ₂ setter
Ta ₂ Be ₁₇	1750-1785	15	+ 6.1	Localized melting at 1785°C
	1800	1	+ 6.8	Melting
	2000	3/4	+ 4.2	Melting and vapor- ization
TaSi ₂	1700-1750	30	- 15	-
	1800	10	- 16.1	Surface spalling dur- ing cooling
	1850	3	-6.1, -4.0	Surface melting
MoSi ₂	1700-1750	30	- 3.2	-
	1950	6	- 9.9	Surface melting
	2000	3	- 4.0	Surface melting
90ZrB ₂ -10MoSi ₂	1700	30	- 2.0	Protective oxide surface layer formed
	2000	2	- 4.7	-
	2000	5	- 3.3	-
	2500	1/2	-17.2	Beginning of melting
WSi ₂	1700	1/2	-	Surface glaze, no change in dimensions

TABLE 13
EFFECT OF METALLIC BINDERS ON DUCTILITY OF
Ta-10W SUBSTRATE AND ADHERENCE OF COATINGS

Intermetallic Compound	Cr	Ni	Ta
ZrB ₂ -10 MoSi ₂	Sintered well, good adherence reacted severely with substrate rendering it highly embrittled	Embrittled substrate, did not enhance bonding	sintered well, No adherence to the substrate-substrate ductile.
MoSi ₂	Melted and reacted with substrate causing severe embrittlement	Sintered well, did not promote better bonding to the substrate. Substrate embrittled.	Coating sintered, no adherence to the substrate. Substrate ductile.

TABLE 14

SINTERING EXPERIMENTS-INTERMETALLIC COMPOUNDS ON Ta-10W

<u>Intermetallic Coating</u>	<u>Sintering Time and Temp. (°C)</u>	<u>Results</u>
ZrB ₂ -10MoSi ₂	1700-1750, 2 hrs	Coating pressed 25 tsi, good sintering characteristics deep diffusion into substrate, good adherence.
ZrB ₂ -10MoSi ₂	1700-1750, 1 hr	Coating not pressed, sintered well, poor bonding to substrate, narrow diffusion zone.
ZrB ₂ -10MoSi ₂	temp held steady @ 1800°C - 1 hr	Coating pressed 25 tsi, good sintered coating, good adherence, deep diffusion.
WSi ₂	1750-1775 - 1 hr	Coating unpressed, coating material reacted with substrate.
WSi ₂	1700-1750 - 1 hr	Coating pressed 25 tsi; coating sintered, slight oxidation, good adherence to substrate.
TaSi ₂	1700-1750 - 2 hrs	Coating pressed 25 tsi, sintered well, slight diffusion, good adherence.
MoSi ₂	1650-1700, 1 hr	Coating material melted, very slight reaction and bonding to substrate.
ZrB ₂ -10MoSi ₂ +10%Cr	1700-1750°C, 1 hr	Pressed coating 25 tsi, reacted with substrate, substrate very brittle, coating spalled on cooling.

TABLE 15

KNOOP HARDNESS MEASUREMENTS FOR INTERMETALLIC COATINGS
ON Ta-10W SUBSTRATE

<u>Coating Composition</u>	<u>Sintering Conditions</u>	<u>Knoop Hardness Numbers Using a 50 Gram Load</u>		
		<u>Coating</u>	<u>Interface</u>	<u>Substrate</u>
ZrB ₂ -10MoSi ₂	1700°-1750°C, 2 hrs	3630	791-695	468-445
TaSi ₂	1700°-1750°C, 2hrs	549	4941-1235	385-367
Ta-10W	as received	-	-	361-322
Ta-10W	1700°-1750°C, 1 hr	-	-	473-468
WSi ₂	1700°-1750°C, 1 hr	1971	581	361-322
MoSi ₂	1650°-1700°C, 1 hr	-	-	445
ZrB ₂ -10MoSi ₂ +10%Cr	1700°-1750°C, 1 hr	-	-	520-473

TABLE 16

EVALUATION OF DIFFUSION BARRIERS FOR TANTALUM¹⁸
(Diffusion-annealed 4 hrs. at 1700°C or 3 hrs. at 1800°C in Argon)

Couple	Total Diffusion zone thickness(u)	Porosity	Predominant Diffusion Direction	Diffusion Zone Hardness (KHN)	
				Increment	Maximum
Ta-W(1800°)	20	Some	Into W	450	770
Ta-Re	<50	None	Into Re	200	470
Ta-Re(1800°)	15	Little	Into Re	265	300
Ta-Os	30	None	Equal	600	890
Ta-Ru	45	None	Into Ta	920	1050
Ta-Ir	40	None	Into Ta	990	1350
Ta-Ir(1800°)	40	Some	Into Ta	1175	1480
Ta-Hf	630	None	Into Ta	410	470
Ta-V*	125	Some	Into Ta	415	600
Ta-Cr*	360	Some	Into Ta	200	820
Ta-Pt*	40-100	None	Unknown	880-1030	1250

* 1 Hour annealing at 1700°C

TABLE 17
RESULTS OF SINTERING FLUXED ZrO_2 AT 1700°C

Composition			Appearance
ZrO_2 99%	TiO_2 1%		White, porous
98	2		Light Brown, surface impervious, glassy
95	5		Dark Brown, impervious, glassy
90	10		Dark Brown, impervious, glassy
ZrO_2 99%	Co_2O_3 1%		Pale Green, porous
98	2		Pale Green, porous
95	5		Dark Gray, impervious
90	10		Dark Gray, impervious
ZrO_2 99%	Cr 1%		Gray, porous
98	2		Gray, porous
95	5		Gray, porous
90	10		Gray, porous
ZrO_2 99%	Al_2O_3 1%		White, porous
98	2		White, porous
95	5		White, impervious
90	10		White, impervious
ZrO_2 100%			White, porous

TABLE 18
SINTERING TRIALS OF MoSi₂-OXIDE COATINGS ON Ta-10W

	Intermetallic Coating	Oxide Coating	Pressing Pressure (tsi)	Sintering Conditioning	Results
1	MoSi ₂ , particles less than 15 microns	----	20 tsi	1400°C 1hr.	Non-Adherent Soft coating
2	MoSi ₂ , particles less than 5 microns	----	"	"	Adherent soft coating
3	MoSi ₂ , particles less than 15 microns	----	30 tsi	1500°C 2hrs.	Non-Adherent soft coating
4	MoSi ₂ , particles less than 5 microns	----	"	"	Adherent hard coating
5	MoSi ₂ , particles less than 15 microns	SrZrO ₃ , particles less than 15 microns	"	"	Non-Adherent soft coating
6	MoSi ₂ particles less than 15 microns on sintered Mo barrier coating	SrZrO ₃ , particles less than 15 microns	"	"	Non-Adherent soft coating
7	MoSi ₂ , particles less than 15 microns 5% solids in dispersion	----	"	1400°C 1 hr.	Adherent with fair to good density
8	MoSi ₂ , particles less than 15 microns 1% solids in dispersion	----	"	"	Non-Adherent with high density
9	MoSi ₂ , particles less than 5 microns 1% solids in dispersion, on sin- tered MoSi ₂ bond layer	ZrO ₂ (CaO stabilized)" milled 6 hrs.	"	"	Adherent with fair density and hardness
10	MoSi ₂ , particles less than 5 microns, 1% solids in disper- sion, no MoSi ₂ bond layer	ZrO ₂ (CaO stabilized) " milled 6 hrs.	"	"	Non-Adherent
11	No. 9 refired	----	-	1700°C 1 hr.	Adherent, with good density and high hardness

TABLE 19
SINTERING RESULTS ON GRADATED COATINGS

Gradated Coating System	Deposition Data	Sintering Temp	Sintering Time	Results
WSi ₂ -ZrO ₂ (CaO)		1600°C	1 hr.	Coating semi-hard, porous.
WSi ₂ -CaZrO ₃		1600°C	1 hr.	Coating hard, dense, reduced and cracked off substrate.
WSi ₂ -ZrO ₂ (CaO)	Grade - 55 sec - 100 volts ZrO ₂ (CaO) - 45 sec - 150 volts ZrO ₂ (CaO) - 45 sec - 200 volts	1700°C	1 hr.	Coating harder than that fired at 1600°C but still porous and cracked off substrate.
WSi ₂ -CaZrO ₃	Grade - 55 sec - 100 volts CaZrO ₃ - 45 sec - 150 volts CaZrO ₃ - 45 sec - 200 volts	1700°C	1 hr.	Coating hard and dense but cracked off substrate.
WSi ₂ -Al ₂ O ₃ (MgO)	Grade - 50 sec - 100 volts Al ₂ O ₃ - 45 sec - 150 volts Al ₂ O ₃ - 45 sec - 200 volts	1700°C	2 hrs.	Coating hard and quite dense, adherent. Shrinkage cracks at one end of panel.

TABLE 20

RESULTS OF OXIDATION TESTS ON Ta-10W SPECIMENS
HAVING GRADATED OXIDE-INTERMETALLIC COATINGS

Gradated Coating	Specimen No.	Siliconizing Treatment	Oxidation Test Temperature	Results
CaZrO ₃ -WSi ₂	1	Yes	2912°F	Removed after short time exposure. Surface bubbly and glassy, yellow. Specimen otherwise intact.
	2	Yes	2912°F	Removed after short time exposure. Coating on leading edge deteriorated on entrance to hot zone.
	3	Yes	2912°F	Removed after 10 minutes exposure. Yellow glassy reacted surface, uneven. Movement and flow of material noted during exposure.
Al ₂ O ₃ (MgO)-WSi ₂	1	Yes	2912°F	Removed after 30 minutes exposure. Surface dark, glassy and wrinkled. Failure site at bottom center where in contact with ZrO ₂ setter pellet. No edge failure.
	2	Yes	2912°F	Removed after 30 minutes exposure. Surface dry. Failure at end and patch areas.
	3	Yes	3000°F	Removed after 5 minutes exposure. Failure at one corner.

Comments: This coating system was selected for further study because the surface appears to have a high density and high viscosity and the resistance to oxidation (30 minutes) was second best of the four systems studied.

(3.5%CaO-Stabilized ZrO ₂ -2%TiO ₂)-WSi ₂	1	No	2950°F	Removed after 10 minutes exposure. Coating dark, glassy. Failure at corners on both ends.
	2	Yes	3000°F	Removed after 45 minutes exposure. Tight, glassy, adherent coat of yellow cast. Small bubbles on surface. Failure on underside where in contact with ZrO ₂ setter pellet.
	3	No	3000°F	Removed after 30 minutes exposure. Failure on one edge and at patch spot.
	4	No	3000°F	Removed after 10 minutes exposure. Failure at ends where in contact with Al ₂ O ₃ setter plate. Remainder of surface did not fail and coating had good adherence.

Comments: This coating system was selected for further study because of the high density and viscosity of the surface and because it had the best oxidation resistance of the four systems studied.

(3.5%CaO-Stabilized ZrO ₂ -5%Al ₂ O ₃)-WSi ₂	1	No	2912°F	Removed after short time exposure. Extreme failure.
	2	Yes	3000°F	Removed after short time exposure. Failure on bottom surface from center to edge.

APPENDIX B

ILLUSTRATIONS

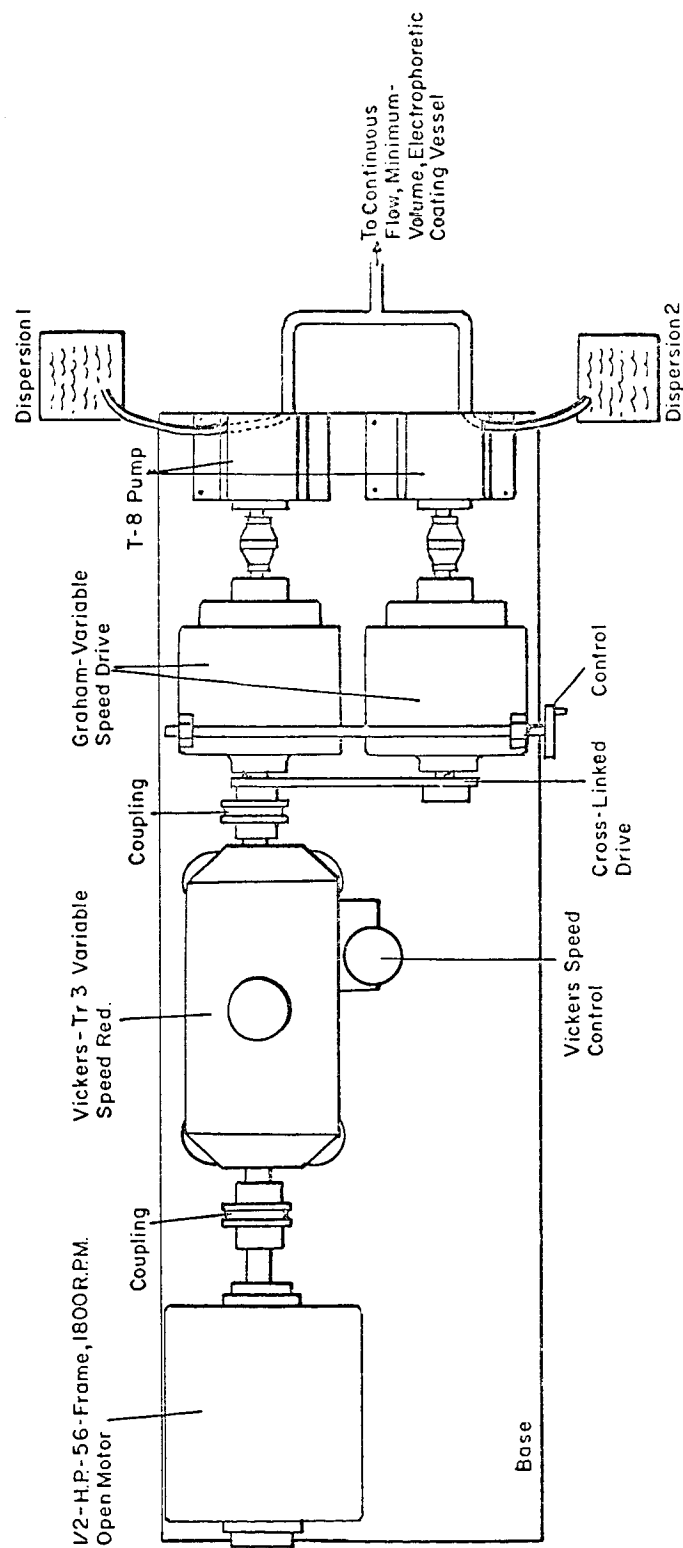


FIGURE 1
PUMPING SYSTEM FOR ELECTROPHORETIC DEPOSITION
OF GRADATED COATINGS

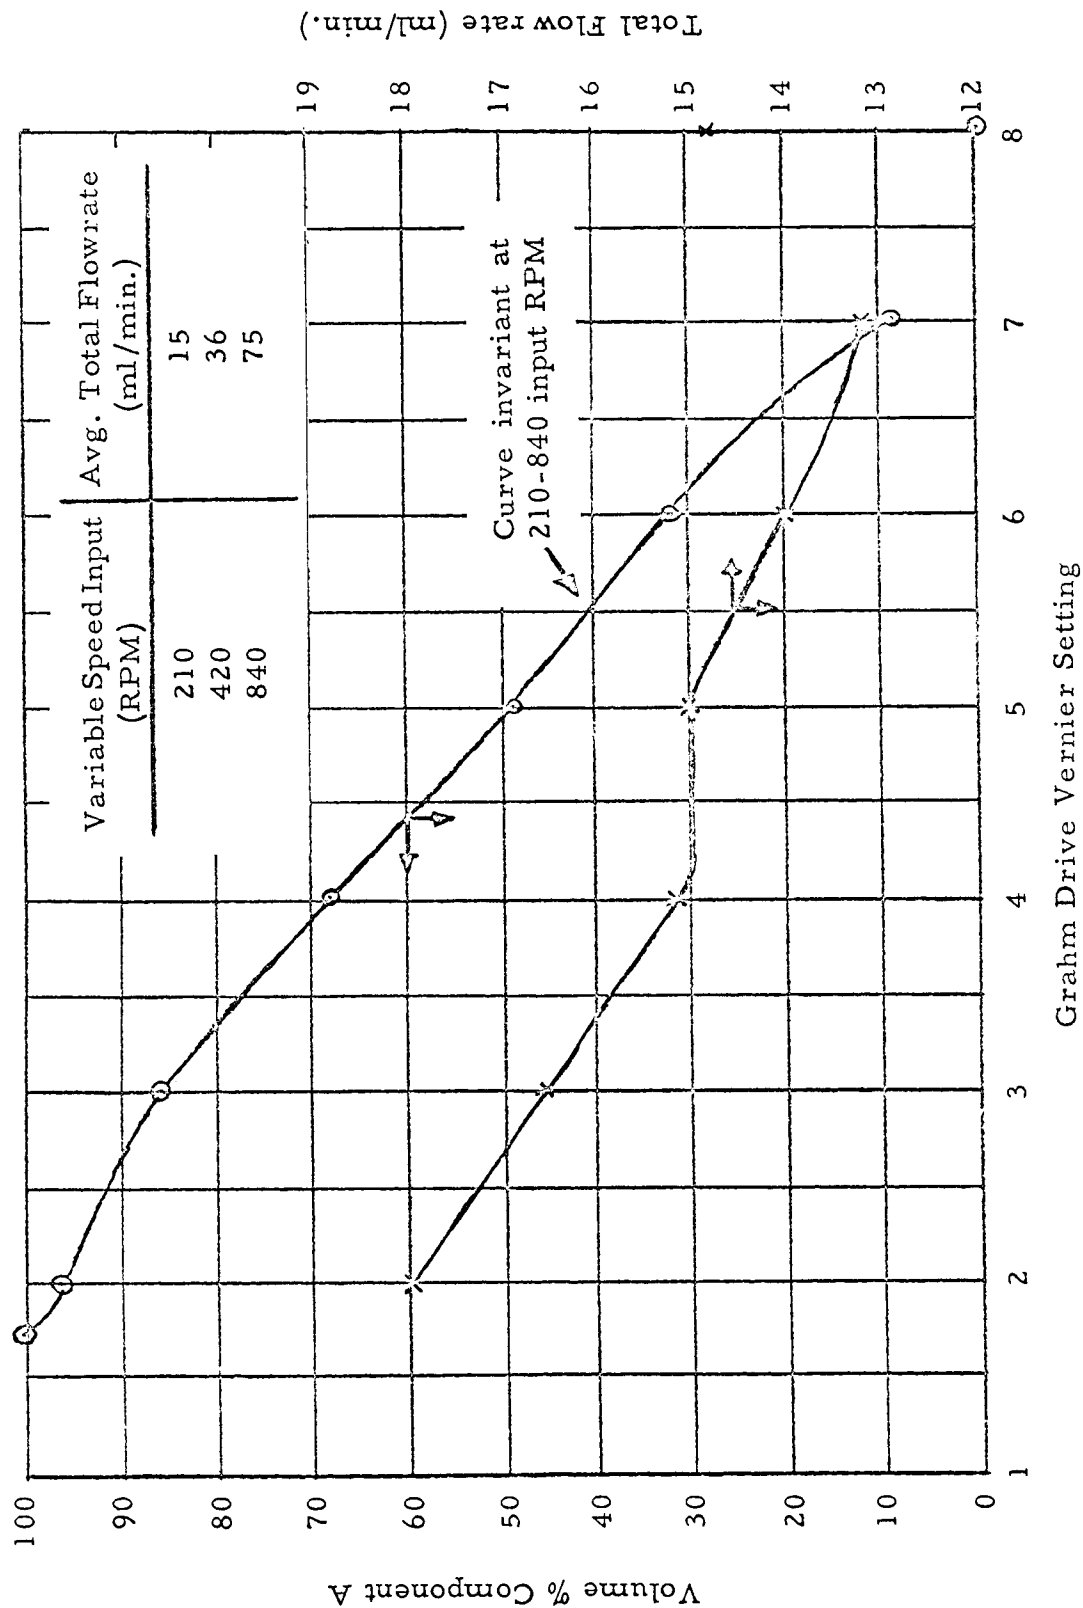


FIGURE 2
EFFLUENT COMPOSITION AND VOLUMETRIC FLOW RATE
VS. PUMPING SPEED FOR 5 MINUTE RUN
THROUGH 1/4 INCH DIAMETER TUBING
(Variable Speed Input = 210 RPM)

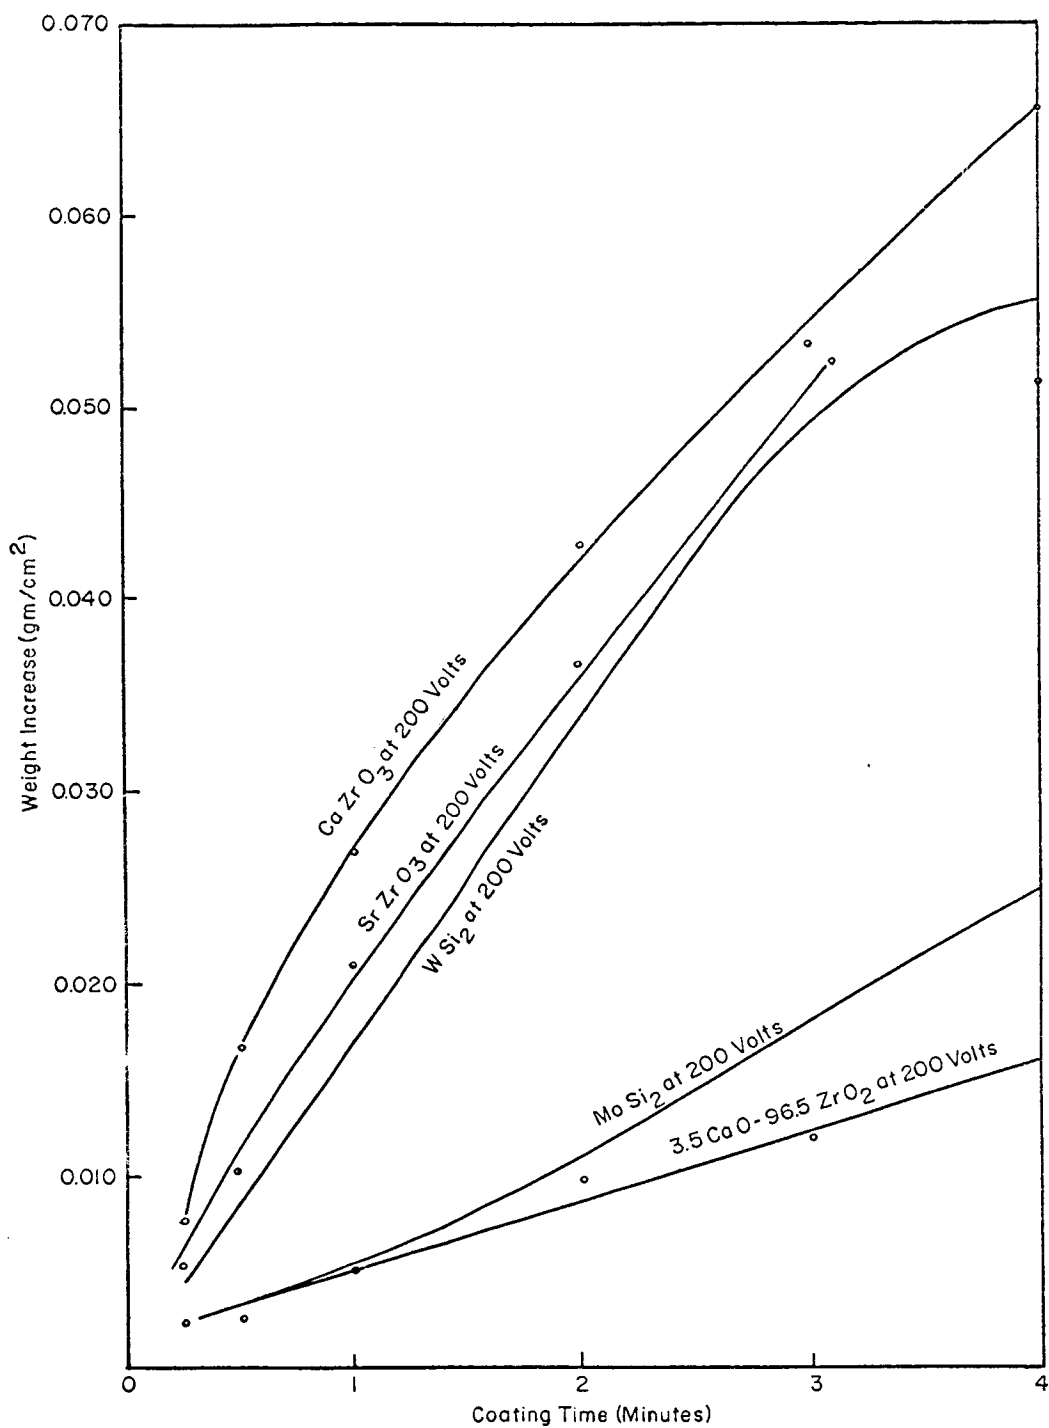


FIGURE 3
COATING RATE OF VARIOUS 1 w/o DISPERSIONS

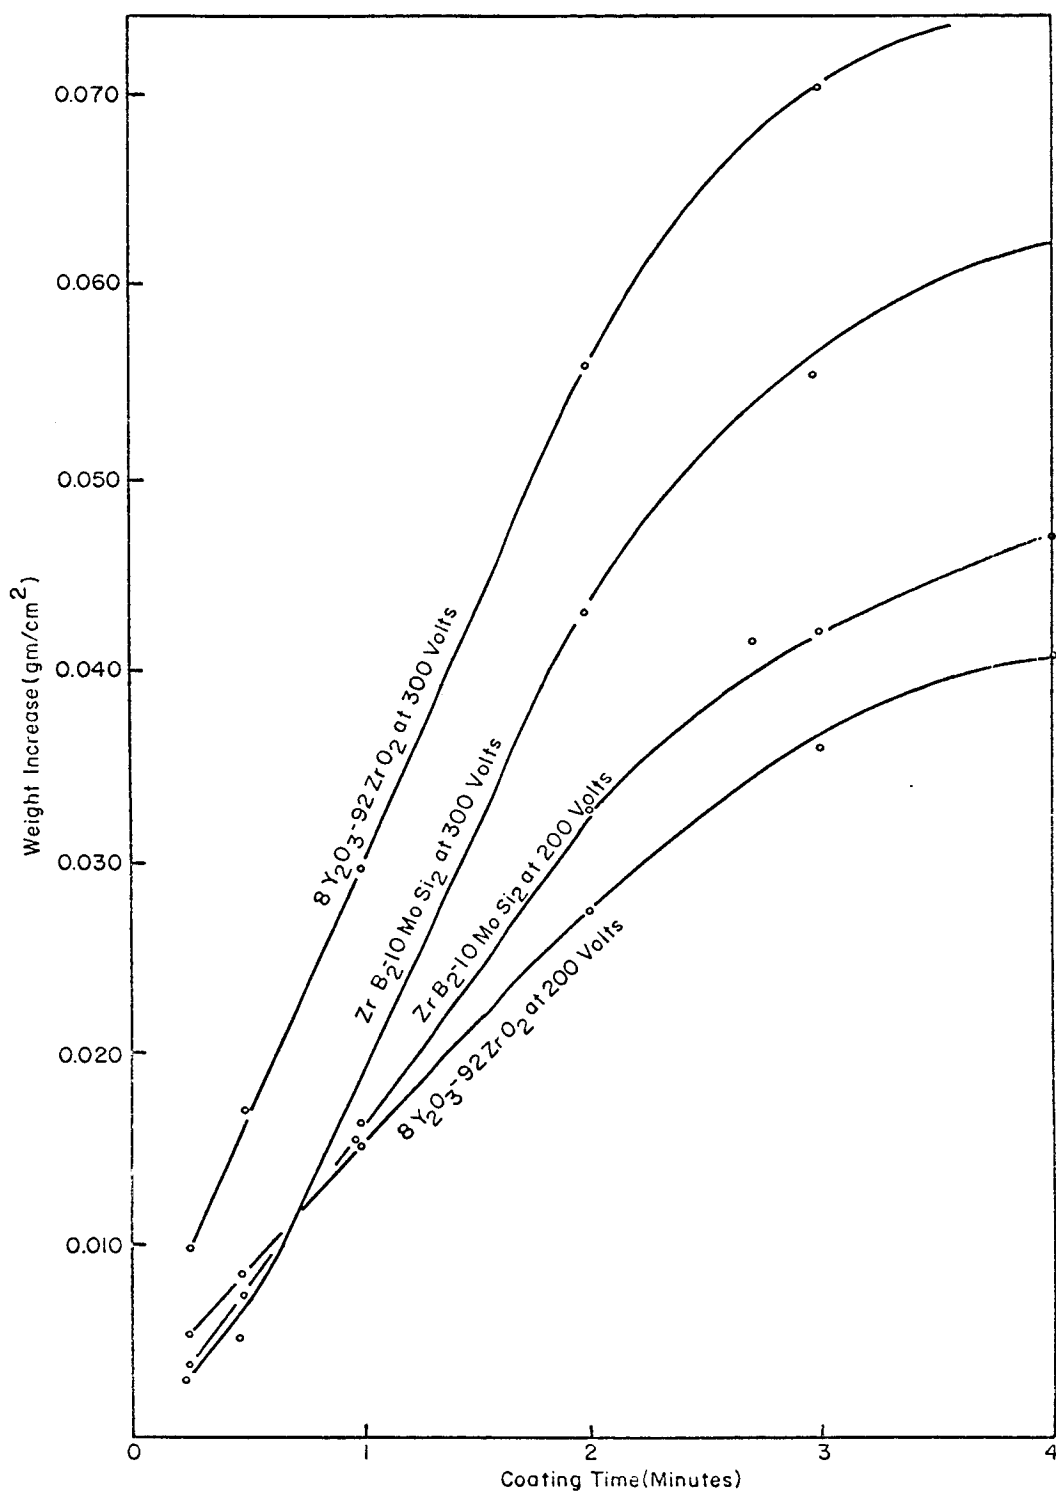


FIGURE 4
COATING RATE OF VARIOUS 1 w/o DISPERSIONS



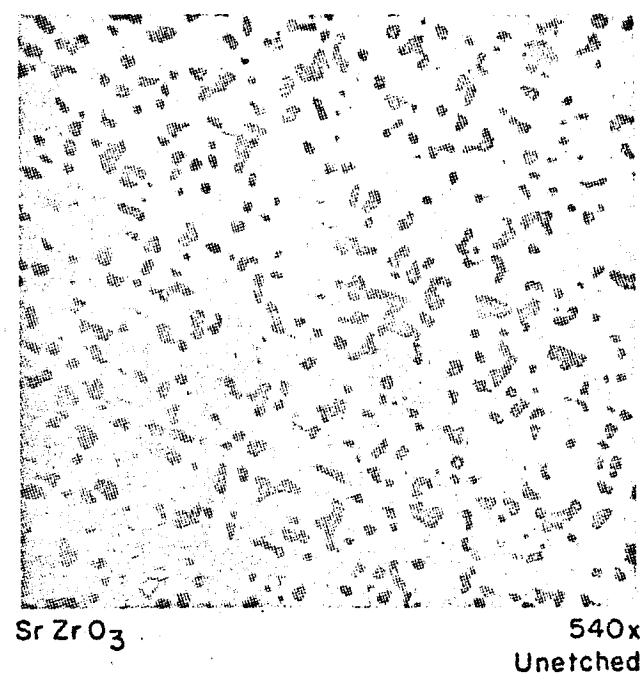



FIGURE 5
PHOTOMICROGRAPH OF SINTERED CaZrO₃ AND SrZrO₃
(Sintering Conditions - 45 min., 1700°C in Argon)

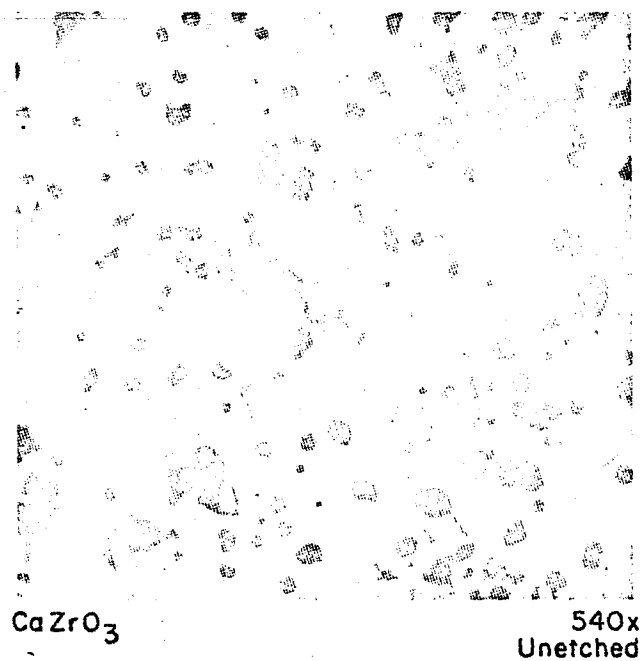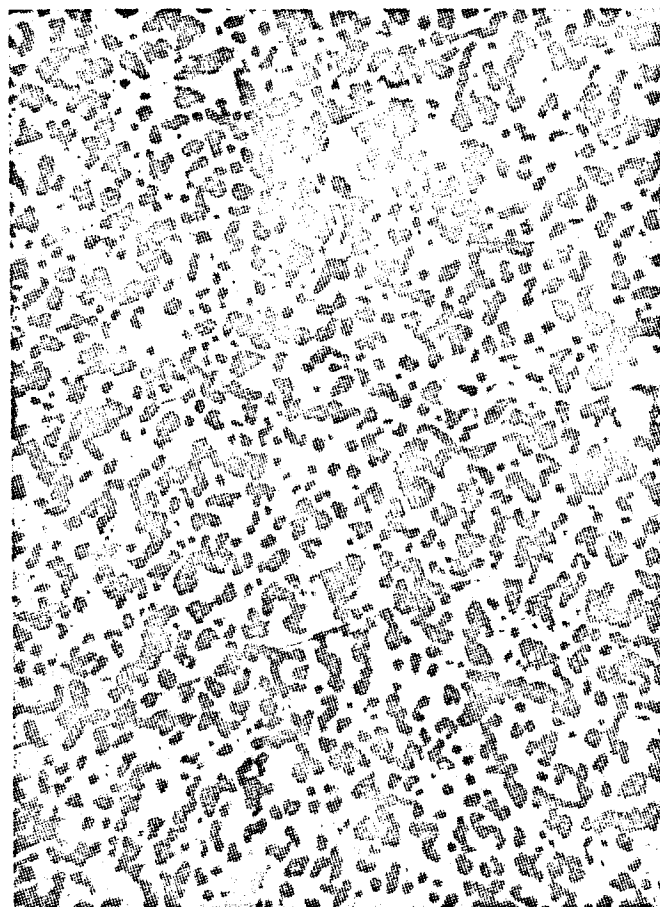

540x
Unetched

FIGURE 6
PHOTOMICROGRAPH OF SINTERED
8% YTTRIA-STABILIZED ZIRCONIA

(Sintering Conditions - 1900°C,
45 min., 10^{-6} torr)

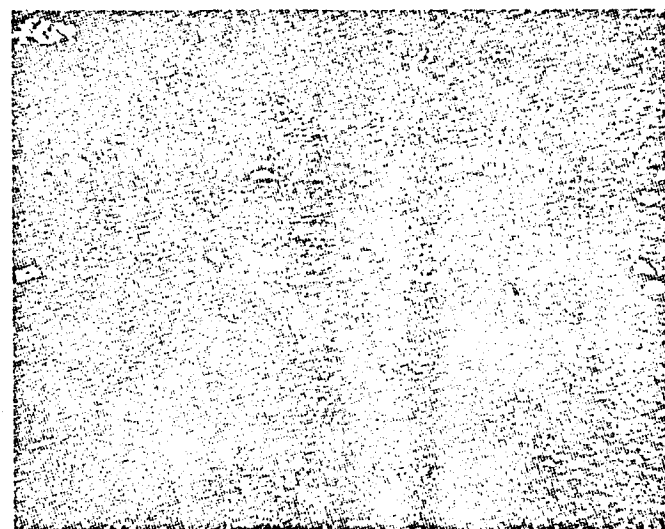

$\text{SrZrO}_3\text{-TaSi}_2$
Density=80% Theory

80x
Unetched



$50\text{SrZrO}_3\text{-}50(90\text{ZrB}_2\text{-}10\text{MoSi}_2)$
Density=75% Theory

350x
Unetched

← $90\text{ZrB}_2\text{-}10\text{MoSi}_2$
Void
 SrZrO_3

FIGURE 7

PHOTOMICROGRAPHS OF $50\text{SrZrO}_3\text{-}50\text{TaSi}_2$
AND $50\text{SrZrO}_3\text{-}50(90\text{ZrB}_2\text{-}10\text{MoSi}_2)$

(Sintered at 1700°C for 30 Minutes in Argon)



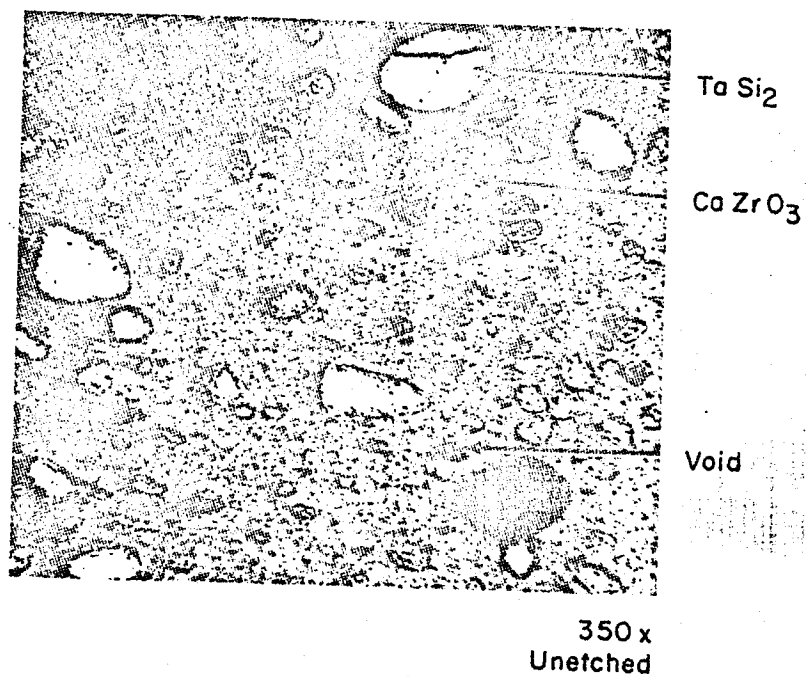



FIGURE 8
PHOTOMICROGRAPH OF 50CaZrO₃-50TaSi₂
COMPOSITE
(Sintered at 1700°C for 30 min. in Argon)

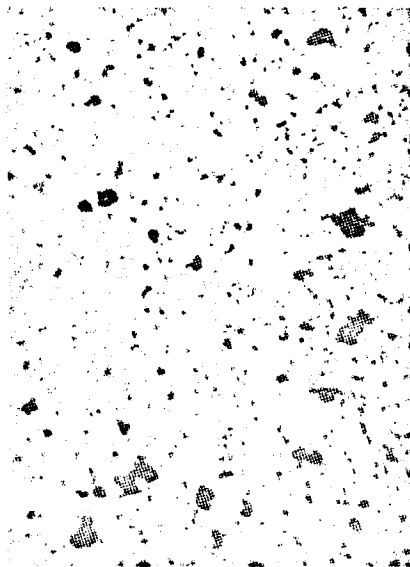


TaAl₃ 1hr, 1400°C, Argon

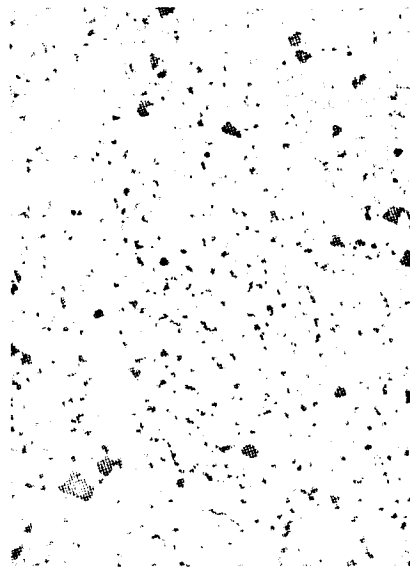

Ta₂Be₁₇ 2.5hrs, 1400°C, Argon

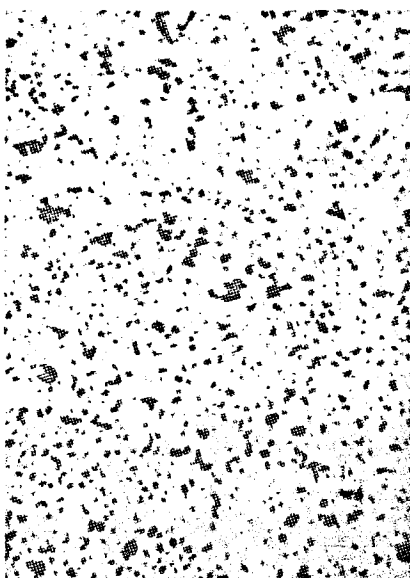


TaSi₂ 1hr, 1400°C, Argon

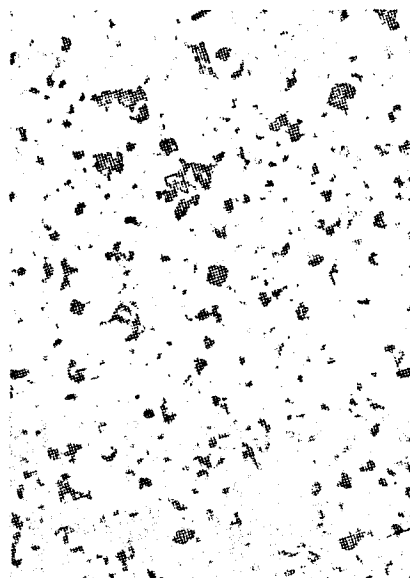


90ZrB₂-10MoSi₂-1hr, 1400°C, Argon

FIGURE 9
PHOTOMICROGRAPHS OF SINTERED INTERMETALLIC COMPOUNDS
(400X Magnification, Unetched)

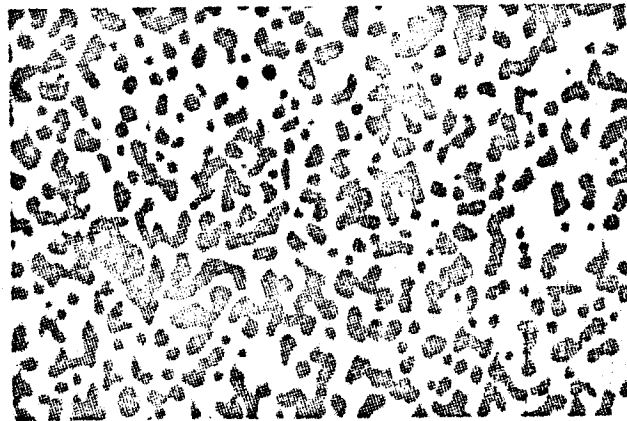

5 hrs -1725°C-Argon


400x , Unetched

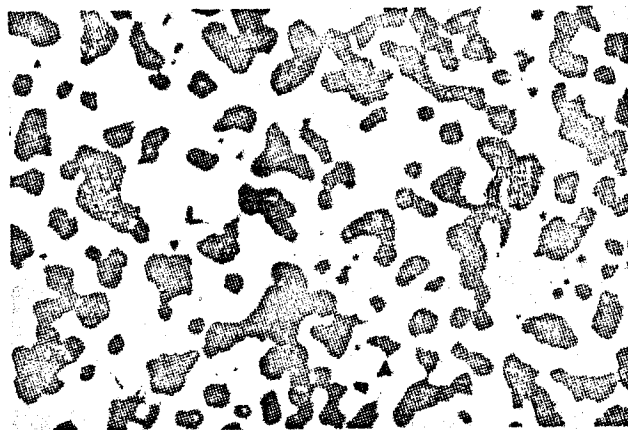

10 hrs -1725°C-Argon


800x , Unetched

FIGURE 10
PHOTOMICROGRAPHS OF SINTERED 8% Y_2O_3 -STABILIZED ZrO_2

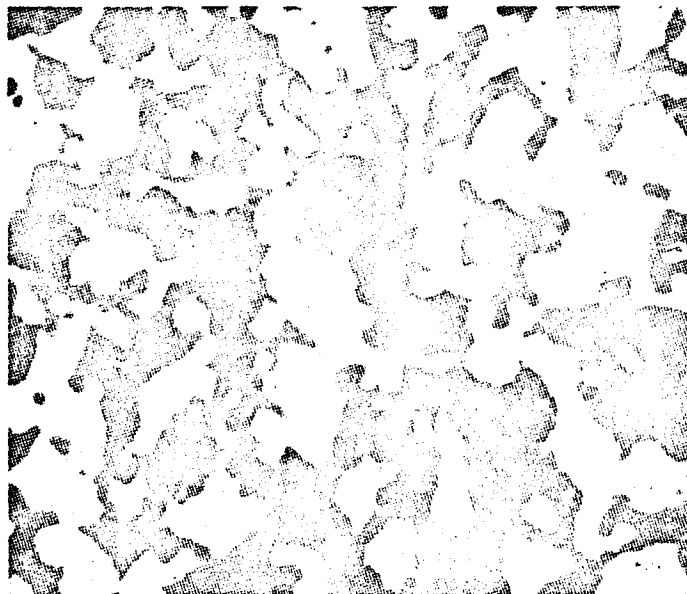

50(3.5 CaO-96 ZrO₂)-50 MoSi₂

400x
Unetched

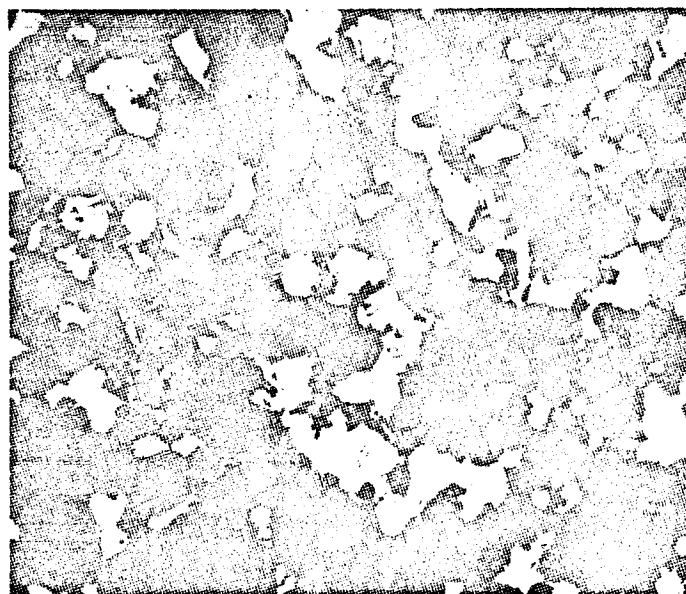


50(3.5 CaO-96.5 ZrO₂)-50 TaSi₂

400x
Unetched


FIGURE 11

PHOTOMICROGRAPHS OF SINTERED
CaO-STABILIZED ZrO₂ COMPOSITES
(Sintered 3.5 hrs. at 1725°C in Argon)

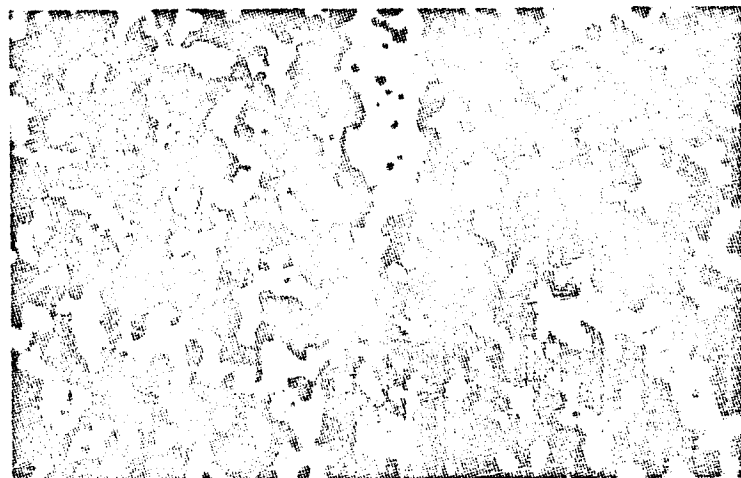

50($8\text{Y}_2\text{O}_3$ -92 ZrO_2)-50 MoSi_2

400x

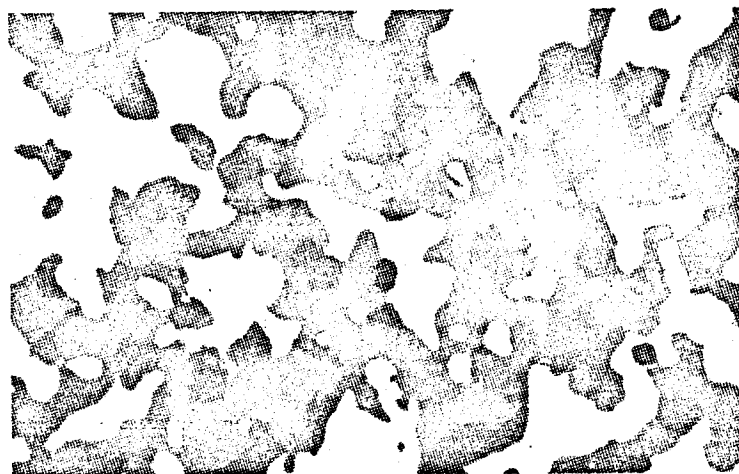

50($8\text{Y}_2\text{O}_3$ -92 ZrO_2)-50(90 ZrB_2 -10 MoSi_2)

400x

FIGURE 12

PHOTOMICROGRAPHS AT 400X MAGNIFICATION
OF 8% Y_2O_3 STABILIZED ZrO_2 COMPOSITES

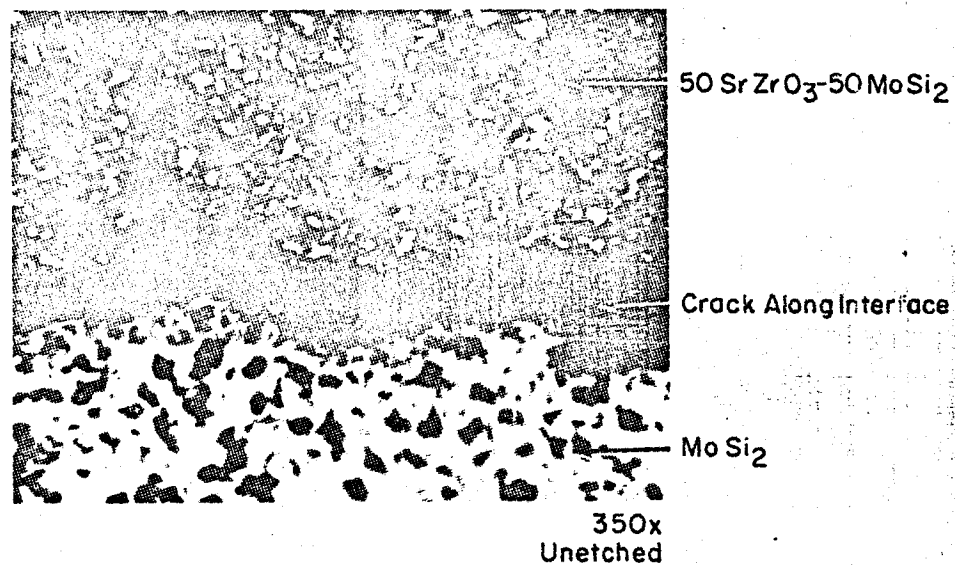
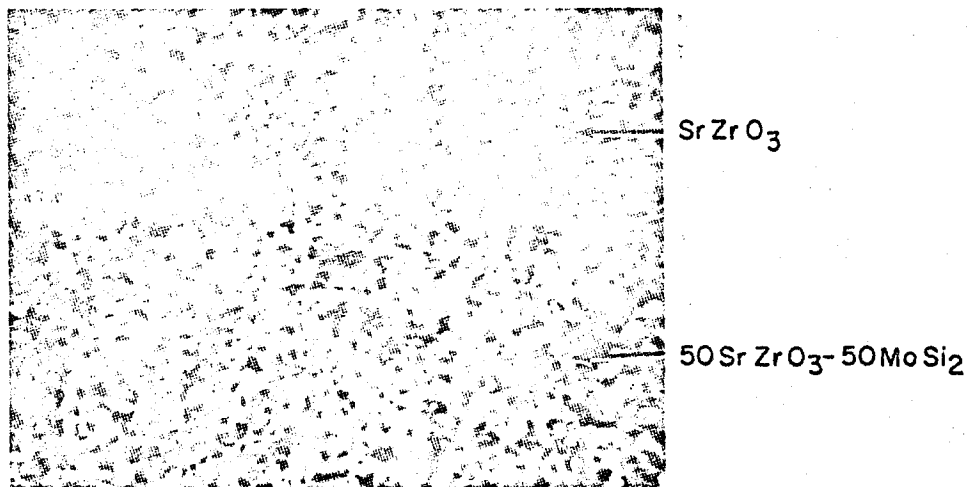


FIGURE 13
 SrZrO_3 - MoSi_2 THREE-LAYER COMPOSITE


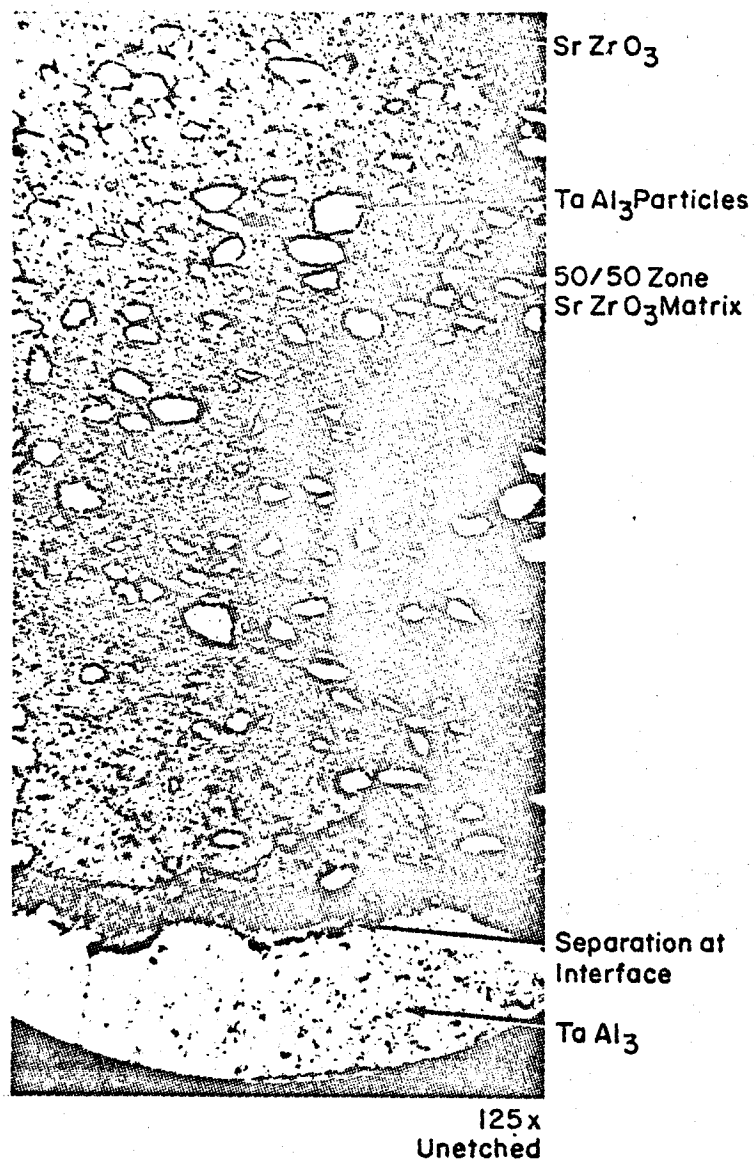



FIGURE 14
 $\text{SrZrO}_3\text{-TaAl}_3$ THREE LAYER COMPOSITE (OVERALL VIEW)

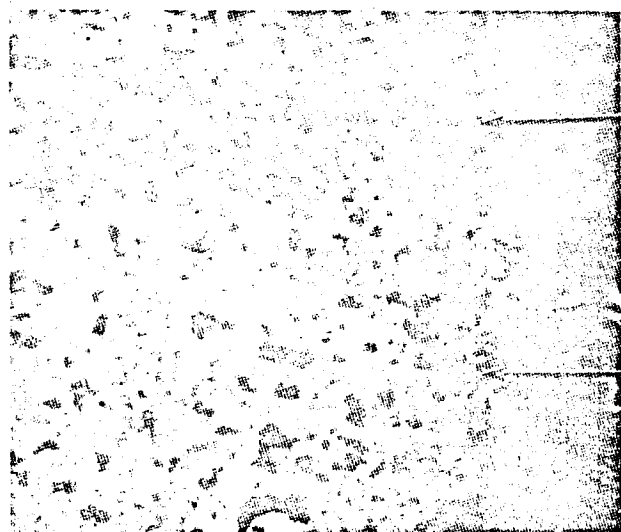

Porous CaZrO_3 Layer

50 CaZrO_3 -50 MoSi_2

350x Unetched

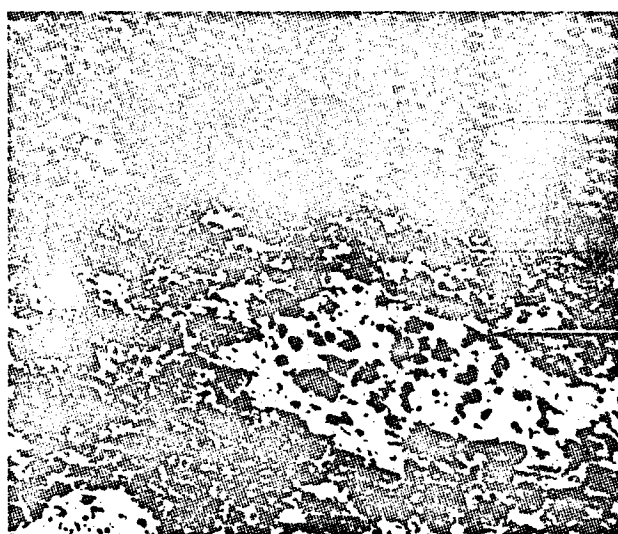

SrZrO_3 Layer

50 SrZrO_3 -
50(90 ZrB_2 -10 MoSi_2) Layer

350x Unetched

FIGURE 15

INTERFACE BETWEEN PURE OXIDE AND
50/50 OXIDE-INTERMETALLIC IN THREE LAYER
COMPOSITES OF
 CaZrO_3 - MoSi_2 and SrZrO_3 -(90 ZrB_2 -10 MoSi_2)


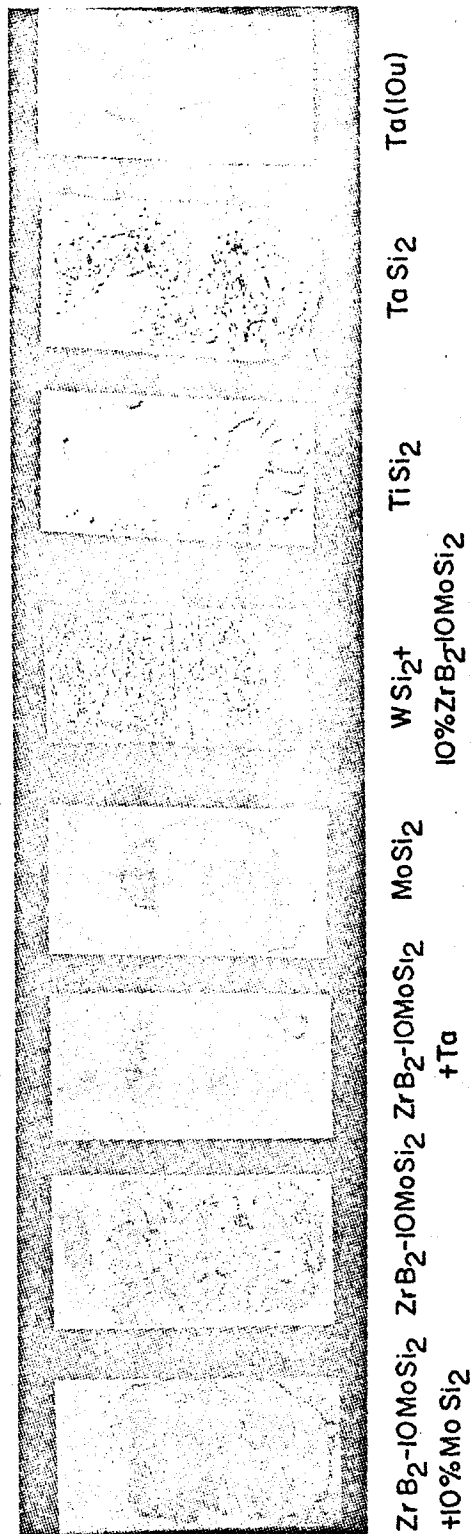



FIGURE 16
 REACTION OF INTERMETALLIC COMPOUNDS WITH
 Ta-10W AT 1750°C - 1800°C IN ARGON

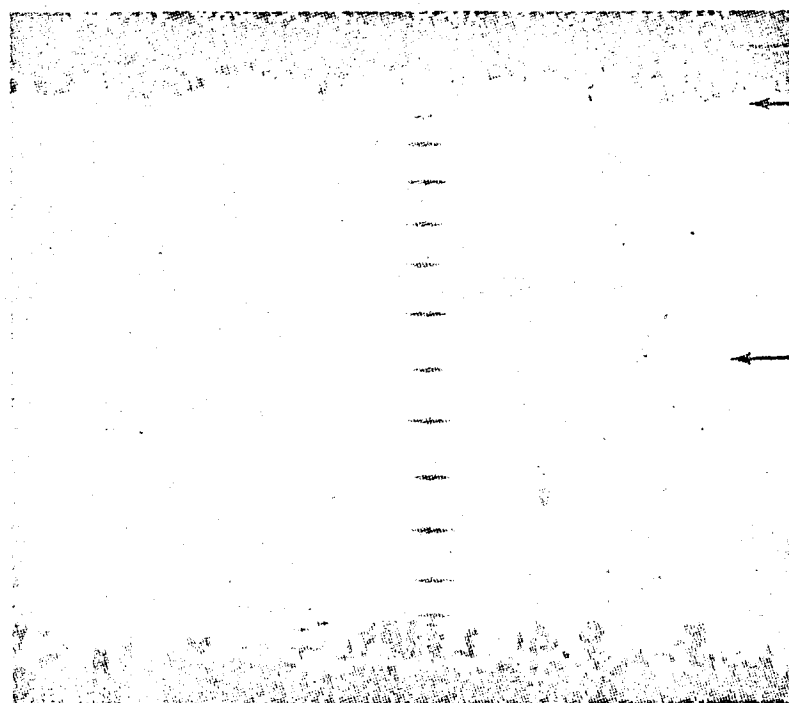

WSi₂ Coating Hardness 1970 kg/mm²
 Diffusion Zone Hardness 580 kg/mm²

← Ta-10W Substrate Hardness
 340 kg/mm²

Pressed 25 tsi
 1700°-1750°C, 1 hr, Argon

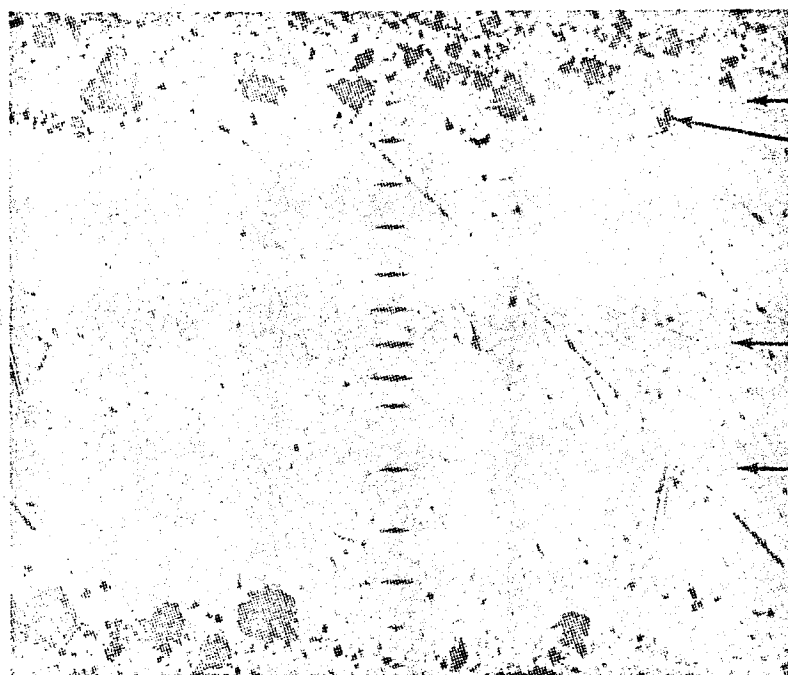

90 ZrB₂-10 Mo Si₂
 Void

← Ta-10W Substrate Hardness
 460 kg/mm²

← Substrate Showing Grain Boundary
 Diffusion Of Coating

Pressed 25 tsi
 1700°-1750°C, 2 hrs, Argon


FIGURE 17

WSi₂ AND 90ZrB₂ - 10 MoSi₂ COATINGS ON Ta-10W ALLOY
 (Magnification 150X, Unetched)



Microhardness
340 kg/mm²

Ta-10 W As Received

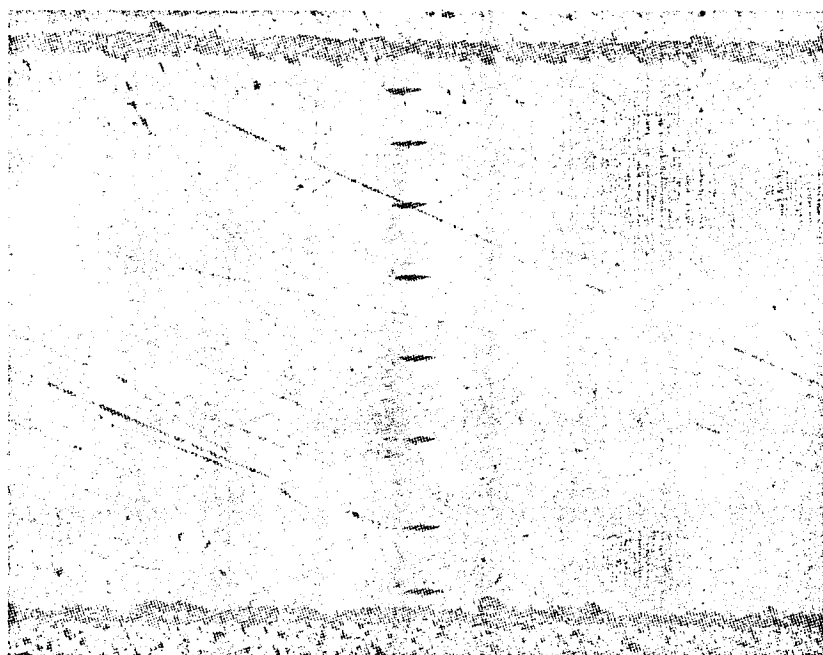


Microhardness
470 kg/mm²


After Heating
1700°-1750°C, 1hr, Argon

FIGURE 18

EFFECT OF HEAT-TREATMENT ON
MICROHARDNESS OF Ta-10W SUBSTRATE
(Magnification 150X, Unetched)

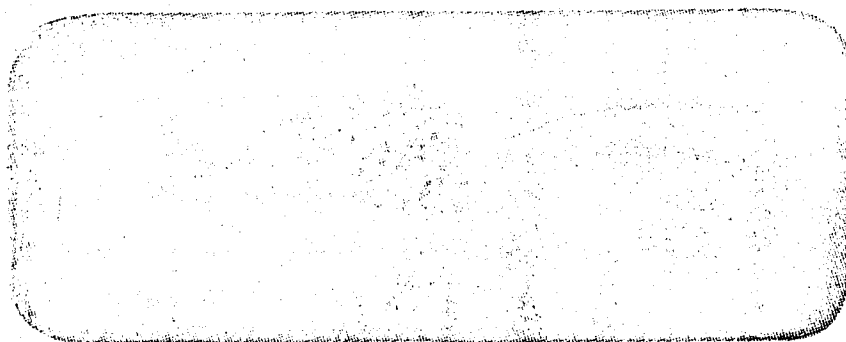

9 x

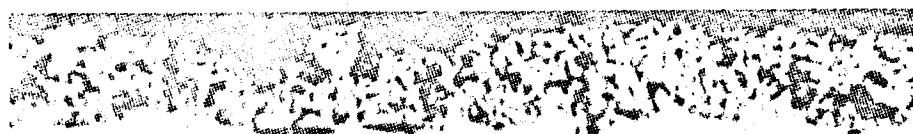

WSi₂ Coating


Bond Layer

Substrate


400x

FIGURE 19

Ta-10W SPECIMEN, COATED WITH WSi₂,
SINTERED AT 1400°C, AND SILICONIZED AT 1350°C

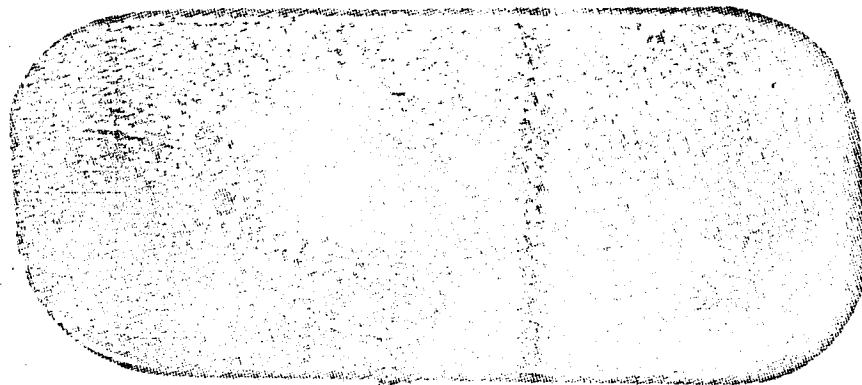

9x

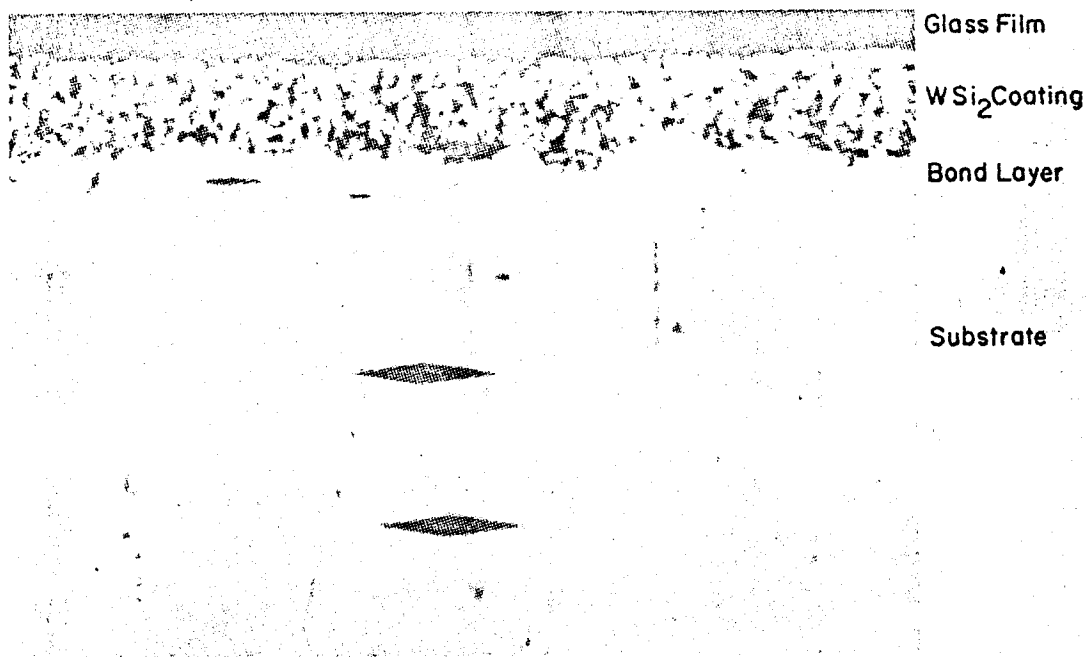

Glass Film

WSi₂ Coating

Bond Layer

Substrate

400x

FIGURE 20

WSi₂-COATED Ta-10W SPECIMEN AFTER
STATIC OXIDATION FOR 30 MINUTES AT 3000°F

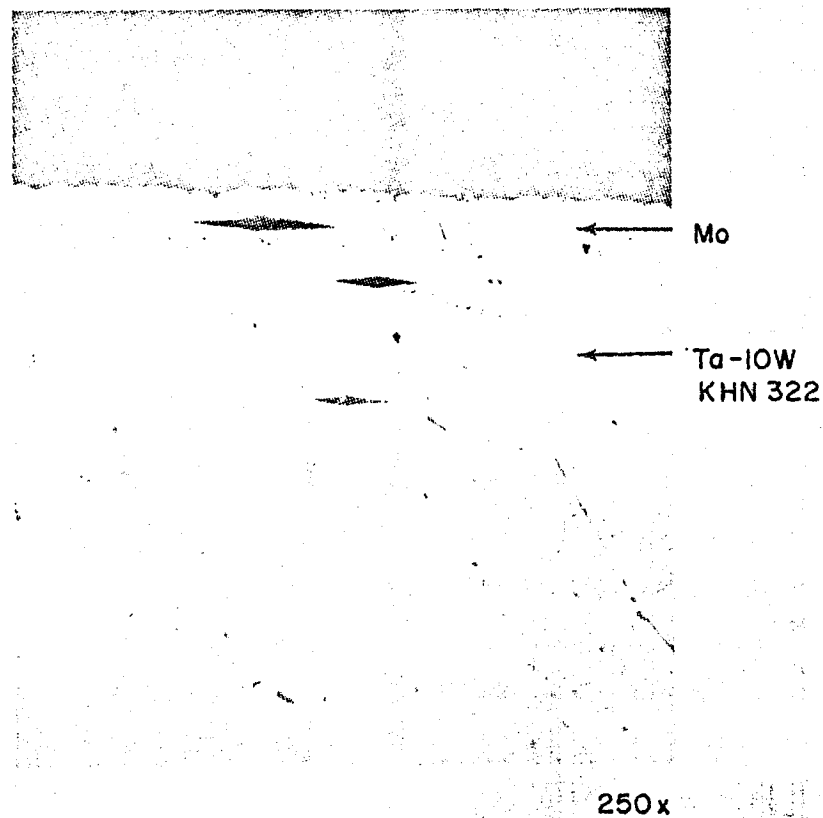


FIGURE 21

Mo COATING ON CHEMICALLY CLEANED Ta-10W
FIRED IN ARGON AT 1400°C FOR 2 HOURS

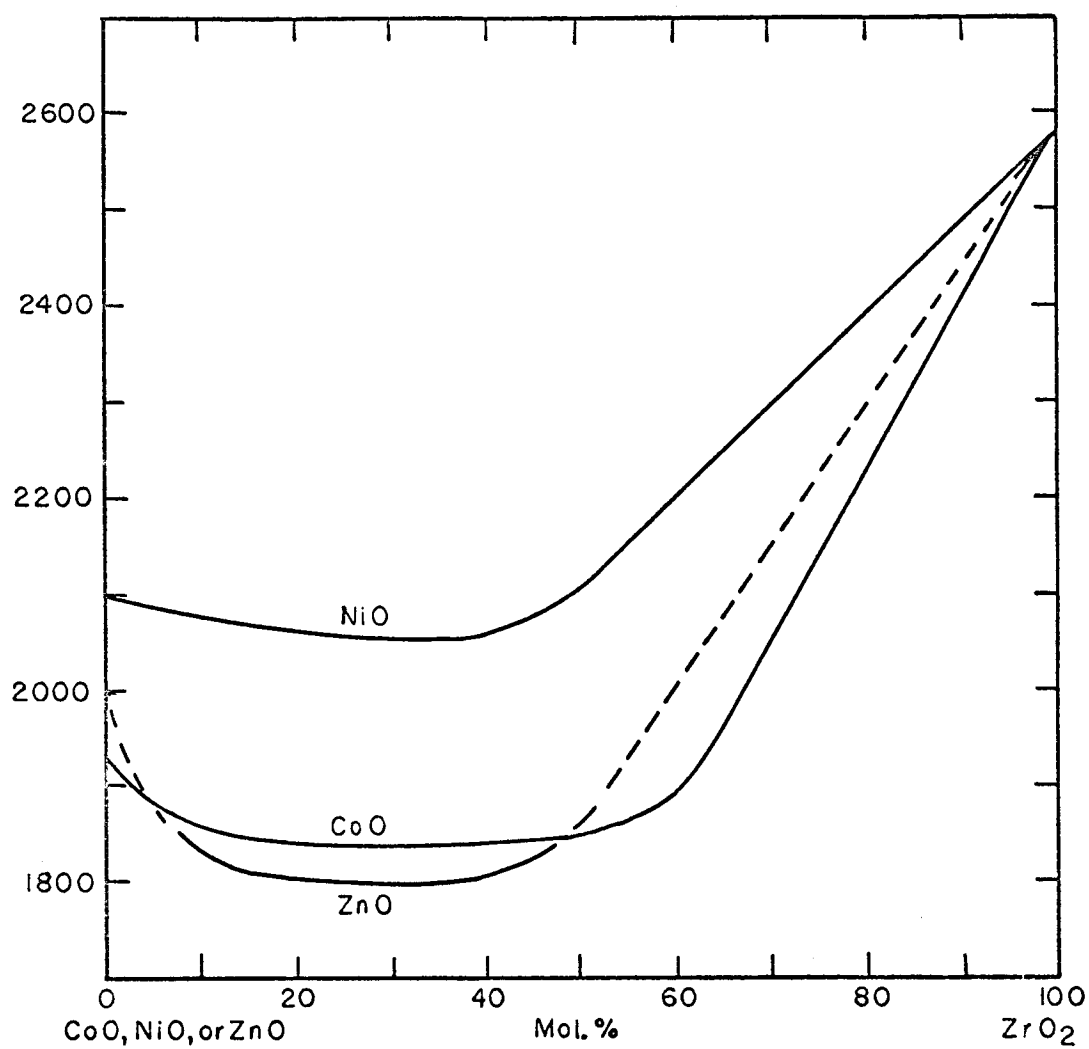


FIGURE 22
LIQUIDUS CURVES OF SYSTEMS
 $CoO-ZrO_2$, $NiO-ZrO_2$, and $ZnO-ZrO_2$



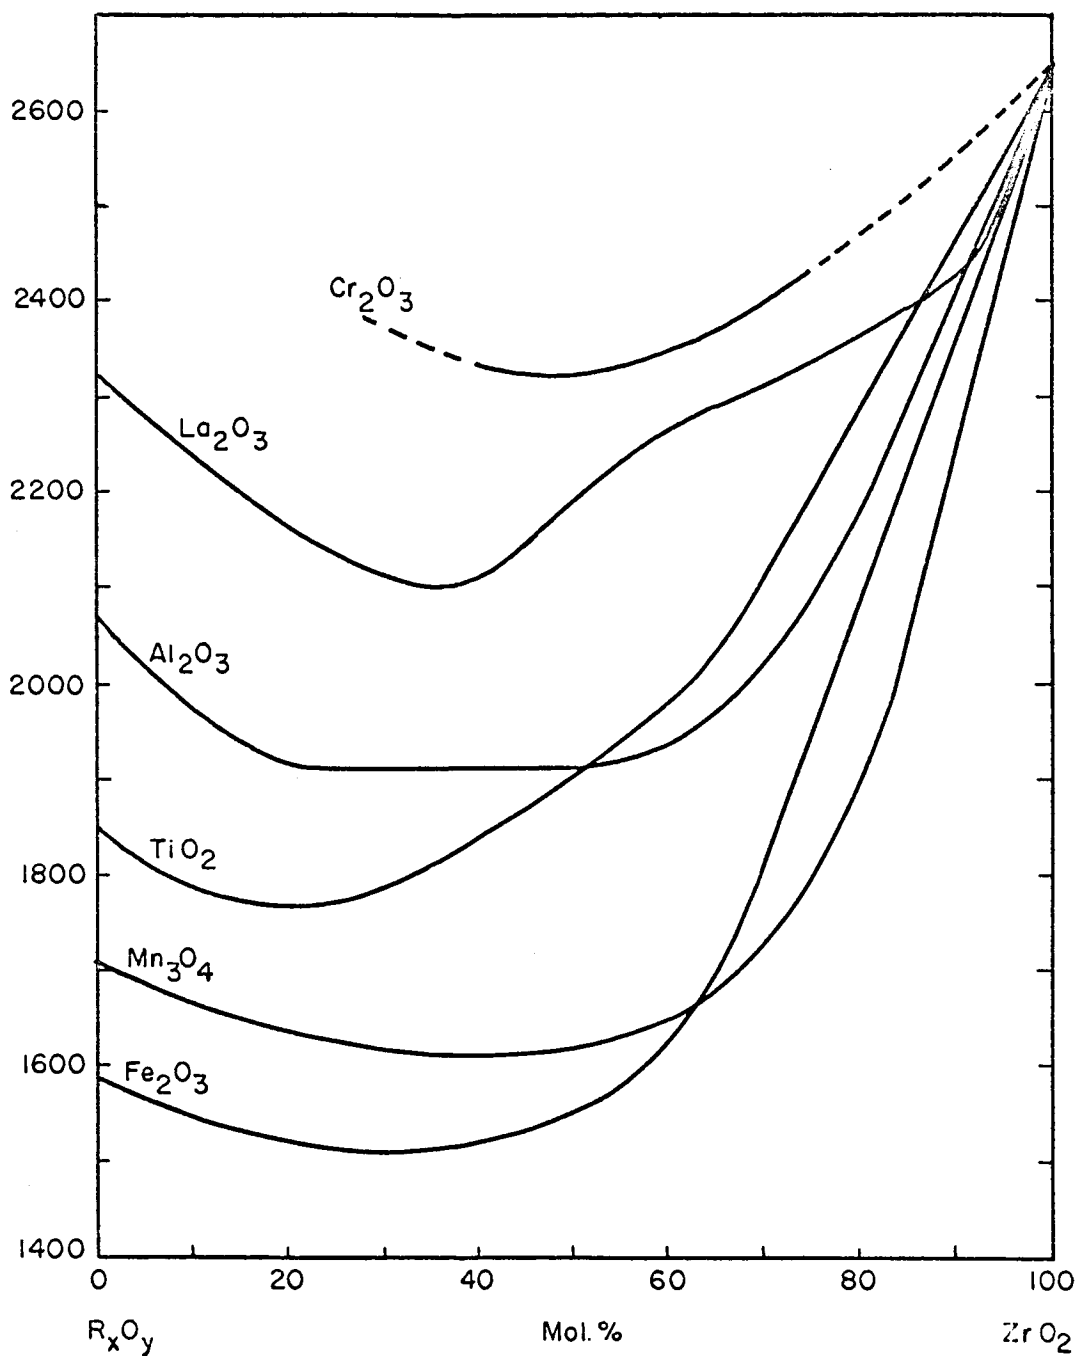


FIGURE 23
LIQUIDUS CURVES OF SYSTEMS Al_2O_3 - ZrO_2 , Cr_2O_3 - ZrO_2 , Fe_2O_3 - ZrO_2 , La_2O_3 - ZrO_2 , Mn_3O_4 - ZrO_2 , and TiO_2 - ZrO_2

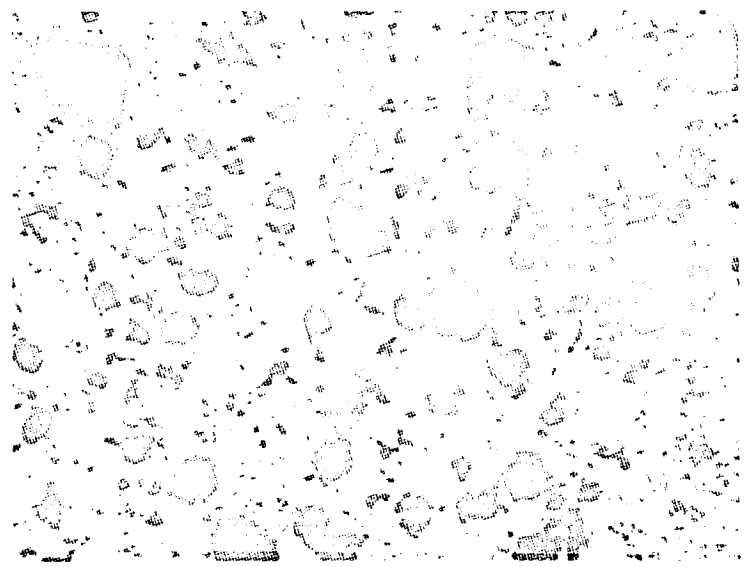

5W/O Al_2O_3

200X

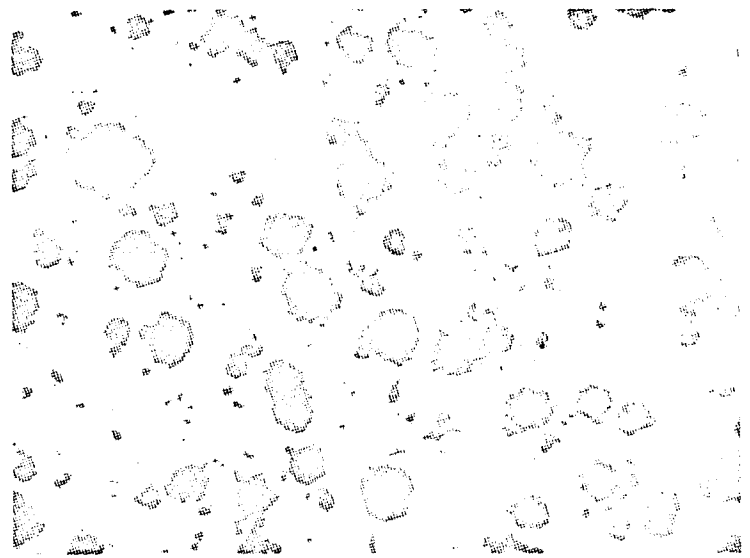

10W/O Al_2O_3

200X

FIGURE 24

CROSS SECTIONS OF Al_2O_3 MODIFIED
CaO STABILIZED ZrO_2 SPECIMENS

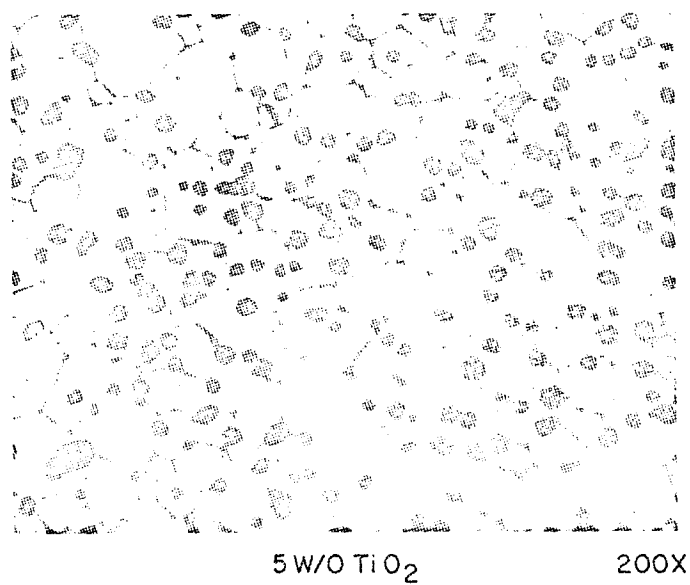
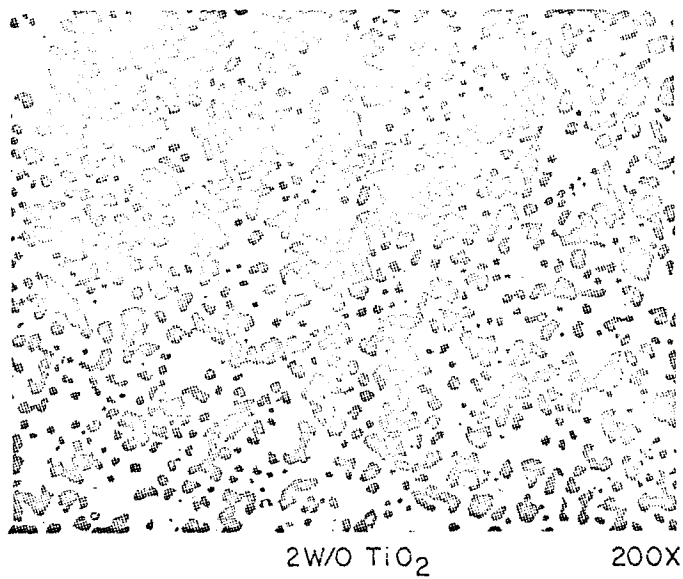


FIGURE 25
CROSS SECTIONS OF TiO_2 MODIFIED
 CaO STABILIZED ZrO_2 SPECIMENS

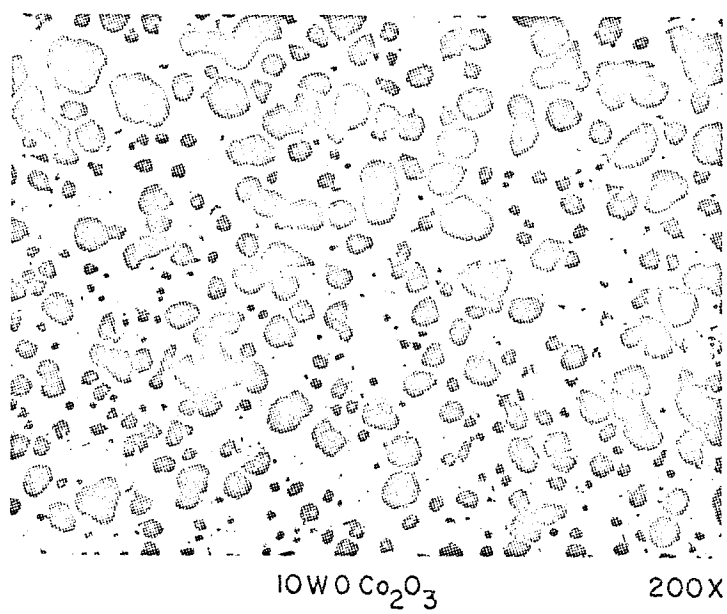
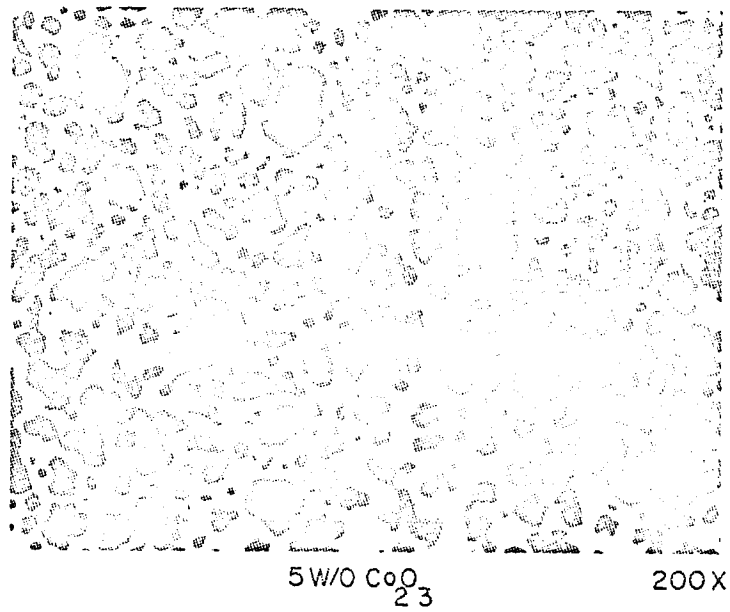


FIGURE 26
CROSS SECTIONS OF Co_2O_3 MODIFIED
CaO STABILIZED ZrO_2 SPECIMENS

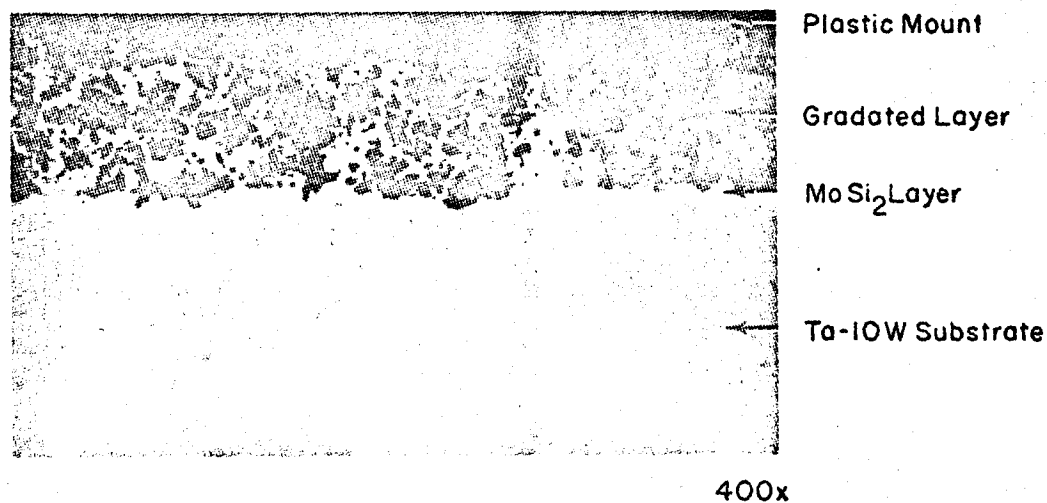


FIGURE 27

MoSi₂-ZrO₂ (3.5% CaO Stabilized)
GRADATED COATING OVER SINTERED MoSi₂
(Sintered 1400°C, 1 hour, Argon)

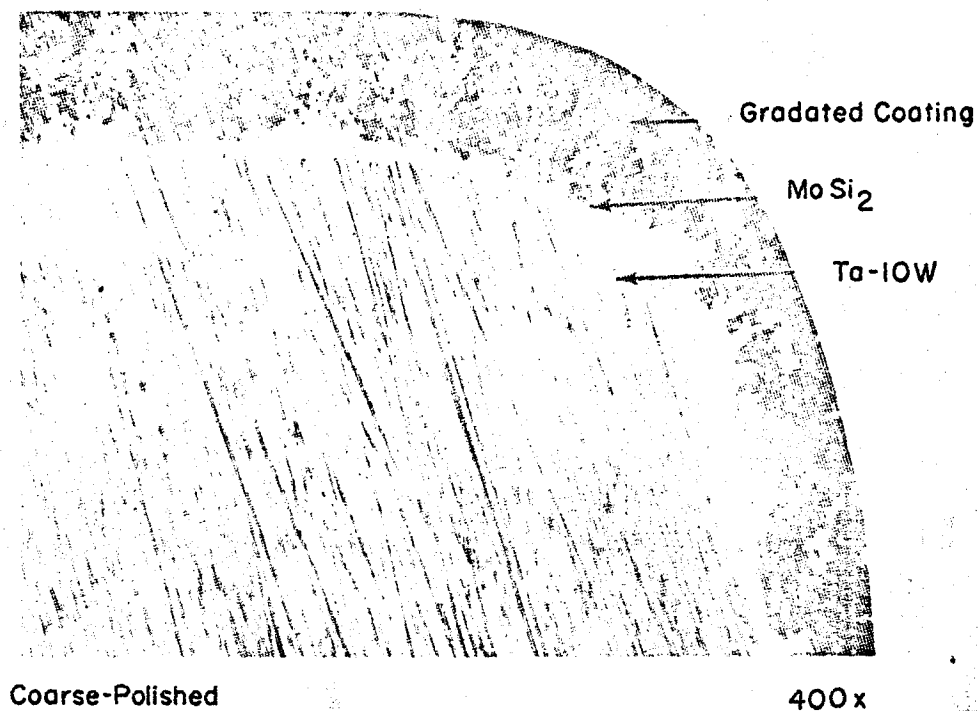


FIGURE 28

MoSi₂-ZrO₂ (3.5% CaO Stabilized)
GRADATED COATING OVER SINTERED MoSi₂
(Coating Sintered in Argon, 1400°C, 1 Hour
Resintered 1 Hour at 1700°C)

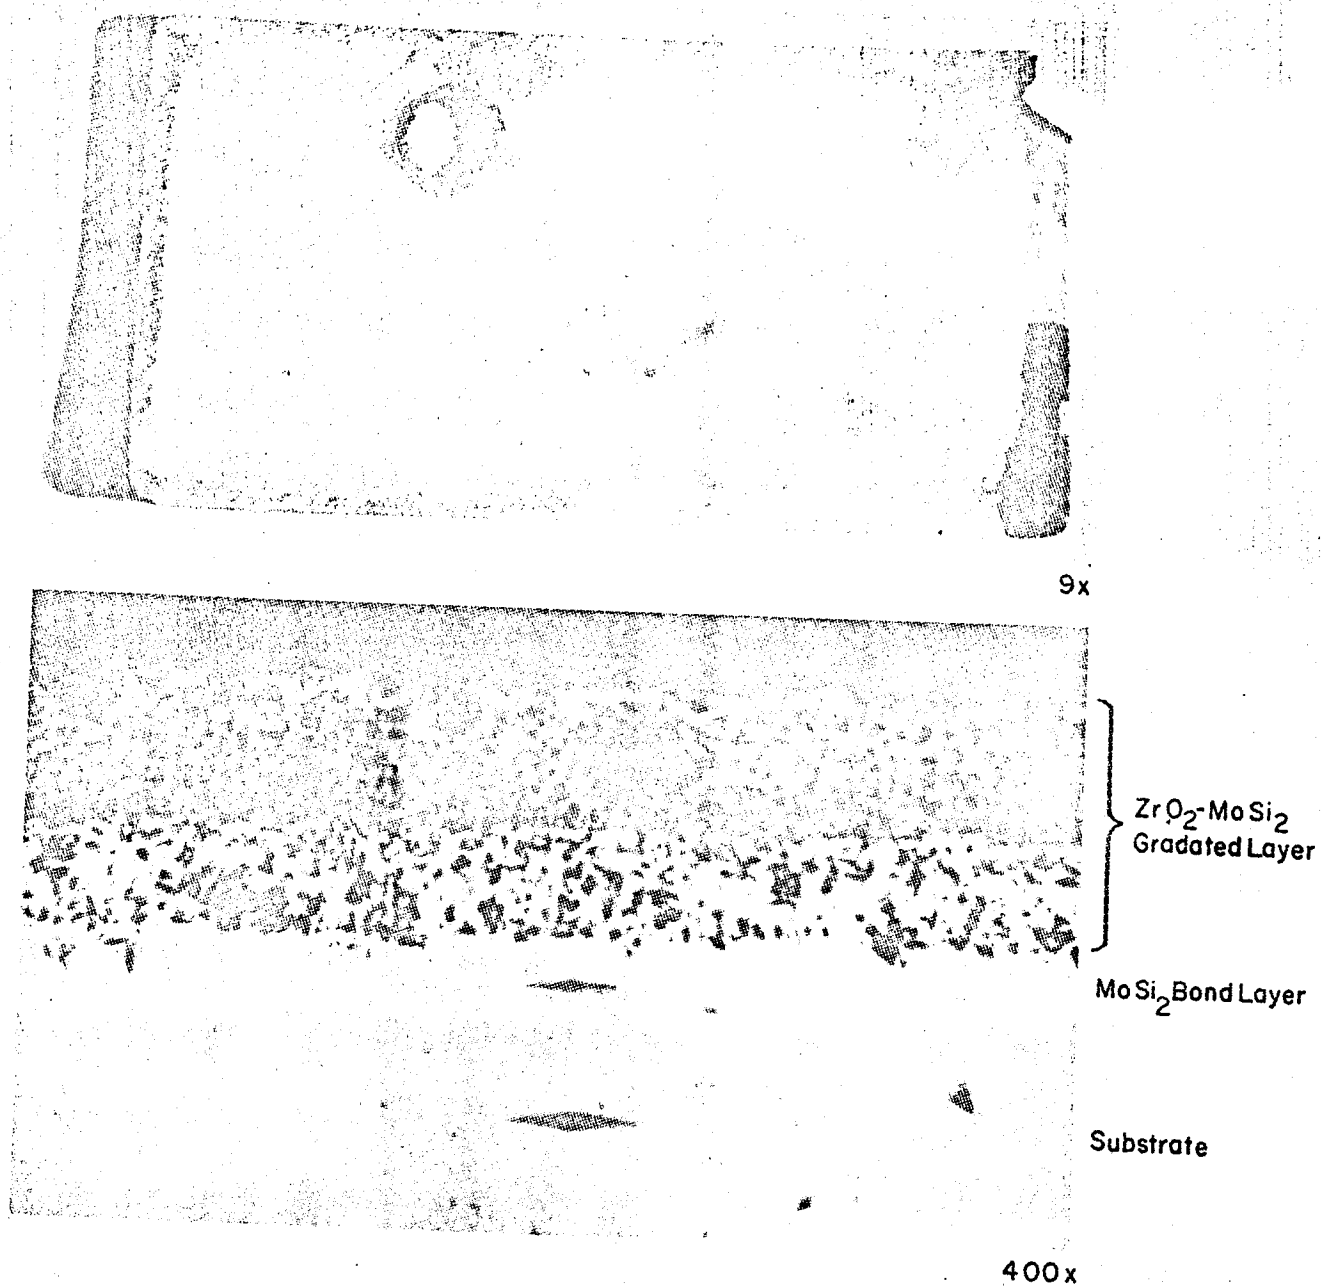


FIGURE 29
MoSi₂-ZrO₂ GRADATED COATING ON Ta-10W SPECIMEN
AFTER OXIDATION AT 1600°C - 1650°C FOR 20 MINUTES

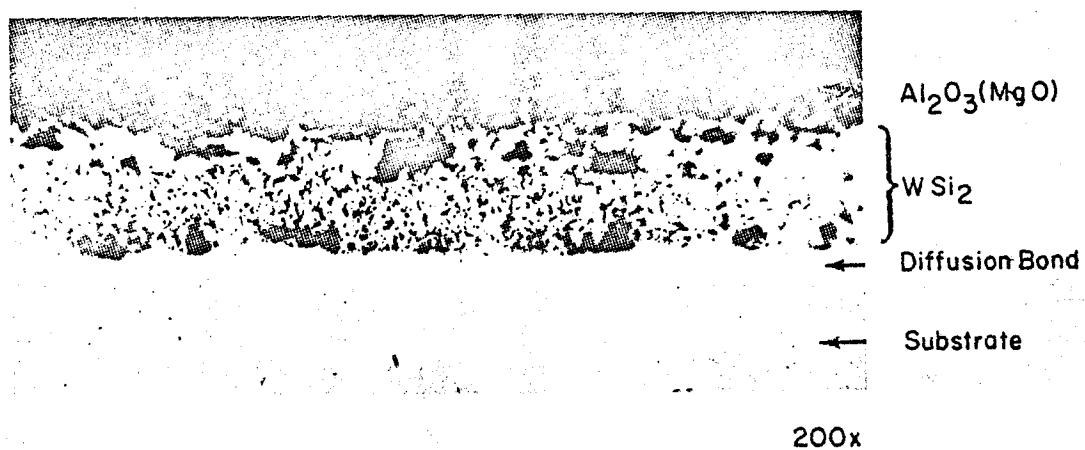


FIGURE 30
CROSS SECTION OF $\text{Al}_2\text{O}_3(\text{MgO})$ - WSi_2 GRADATED COATING
ON Ta-10W AFTER STATIC OXIDATION TEST AT 2912°F



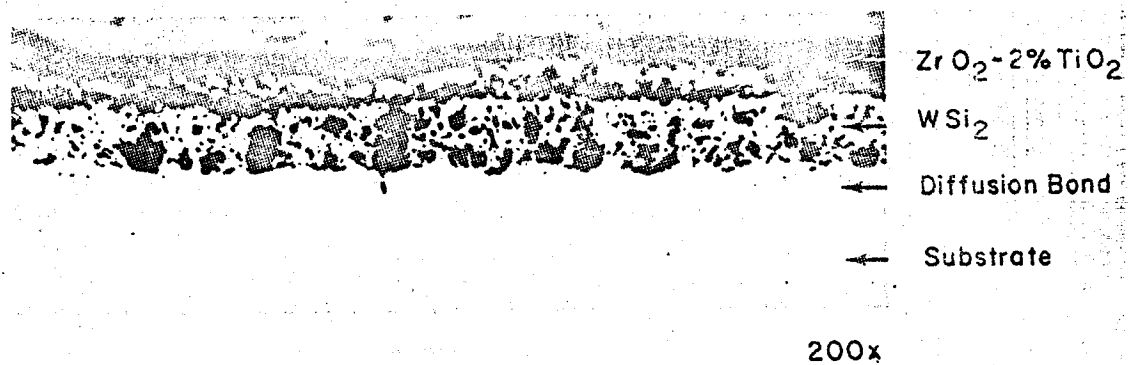



FIGURE 31
CROSS SECTION OF 3.5% CaO STABILIZED ($ZrO_2-2\%TiO_2$)- WSi_2
ON Ta-10W AFTER STATIC AIR OXIDATION
TEST AT 3000°F

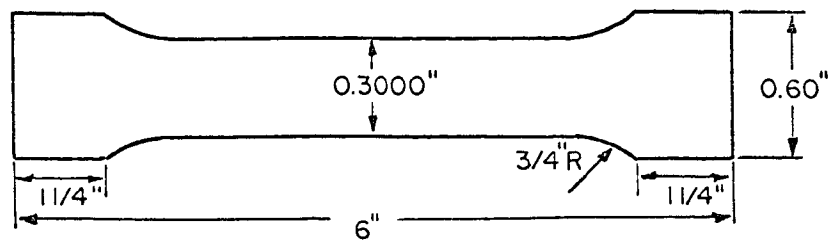

SHEET TENSILE SPECIMEN

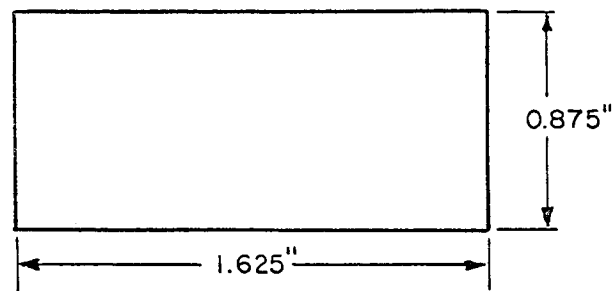

COUPON

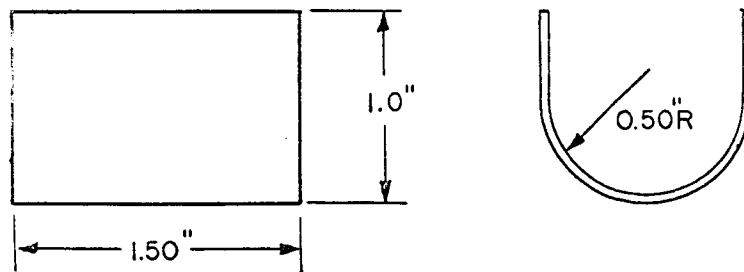

SIMULATED LEADING EDGE

Material - Ta-10W Foil, 0.008 in. Thick

FIGURE 32
SPECIMENS COATED FOR NASA EVALUATION