

AD 637531

USNRDL-TR-1037

23 June 1966

CHARGED PARTICLE TRACKS IN POLYMERS: Number 2 - Registration of Heavy Ions During the Flight of Gemini VI

by

E.V. Benton

M.M. Collver

FACILITY FORM 802	N66 39678	
	(ACCESSION NUMBER)	(THRU)
	20	3
	(PAGES)	(CODE)
AD-637531	29	
(NASA CR OR TMX OR AD NUMBER)	(CATEGORY)	
CR-79200		

GPO PRICE	\$	_____
CFSTI PRICE(S)	\$	_____
Hard copy (HC)		<u>1.00</u>
Microfiche (MF)		<u>.50</u>

ff 853 July 65

**U.S. NAVAL RADIOLOGICAL
DEFENSE LABORATORY**

SAN FRANCISCO · CALIFORNIA · 94135

RADIOLOGICAL PHYSICS BRANCH
E. Tochilin, Head

NUCLEONICS DIVISION
C. S. Cook, Head

ADMINISTRATIVE INFORMATION

This report was sponsored and funded by the National Aeronautics and Space Administration, Subtask A-65315.

ACKNOWLEDGMENTS

The authors are greatly indebted to Lieutenant J. F. Janni and other members of Bioastronautics Group of the Air Force Weapons Laboratory for including the polymer detectors as part of the passive dosimetry system aboard the Gemini VI spacecraft. The authors also wish to thank Dr. Harry H. Heckman of the University of California Lawrence Radiation Laboratory for his help in the estimation of the expected heavy ion flux during these measurements. The authors are indebted to R. P. Henke for his constructive comments on the manuscript.

DDC AVAILABILITY NOTICE

Distribution of this document is unlimited.

Eugene P. Cooper

Eugene P. Cooper
Scientific Director

D. C. Campbell

D. C. Campbell, CAPT USN
Commanding Officer and Director

ABSTRACT

Several small disks of cellulose nitrate plastic were included as a part of a dosimetry package aboard the Gemini VI spacecraft for the purpose of recording the heavy component of the primary cosmic radiation. An average of 10 tracks/cm²-day was found in the plastic detectors. Most of these were judged to be tracks of heavy recoil ions; about 1 track/cm²-day was judged to be due to the primary cosmic ray particles.

SUMMARY

The Problem

Conventional dosimeters do not accurately measure the dose from the multicharged component of the primary cosmic radiation. Since the contribution of such radiation to the total dose received will be considerable during the long range manned space flights, it is important to develop a heavy ion dosimeter for this purpose.

The Findings

An average of 10 tracks/cm²-day was found in the plastic detectors. Most of these were judged to be tracks of heavy recoil ions; about 1 track/cm²-day was judged to be due to the primary cosmic ray particles. Polymer detectors are best suited for registration of slow, heavy ions. For polar orbits or flights outside the vicinity of the earth, separation of heavy ion flux into (dE/dx) intervals and a subsequent estimate of the dose can be made.

Recommendations

Further development of polymer detectors is recommended. Improvement of surface characteristics and sensitivity, as well as longer duration equatorial and polar flights are clearly desirable.

INTRODUCTION

Cosmic rays above the earth's atmosphere produce about 25 mrad dose/24 hours or about 10 rads/year. The proton and alpha particles constitute all but about 1 per cent of the total particle flux. Nevertheless the remaining one per cent of heavy particles are responsible for about 40 per cent of the total dose. Most of the dose is produced through the action of slow, heavy ($Z \geq 6$) nuclei.

Probably the main feature of these heavy nuclei is their high (dE/dx) (rate of energy loss). The heaviest particles can produce up to a maximum of 100,000 ion pairs per micron of tissue, or a dose in excess of 1000 rads to a single cell of 10 microns diameter.⁽¹⁾ This is about 50 times the maximum value produced by a proton. The mode of action of such densely ionizing radiation has never been investigated to the point where its biological effectiveness relative to proton or electron beams could be established. Since direct damage to cellular systems have been observed for single heavy particles (effect on hair follicles, etc.), it becomes important to investigate the long term action of this type of radiation which is clearly different from our natural radiation environment. Thus, any manned space flight in excess of several weeks duration should contain heavy particle dosimeters

capable of defining the radiation environment within the vehicle. This cannot be accomplished with conventional dosimeters designed for monitoring the electron, proton and X-ray component of the cosmic ray environment.

Within the past two years a number of dielectric solids have been found which can serve as heavy charged particle detectors.^(2,3) Tracks are delineated in these materials as a result of a preferential removal, by etching, of the high chemical reactivity material along the particle trajectory. The most sensitive materials found to date are polymers. Cellulose nitrate plastic is one of the most sensitive of these, requiring for track formation a rate of energy loss, (dE/dx) , by the incident particle to be above $2 \frac{\text{MeV}}{\text{mg/cm}^2}$. Tracks of alpha particles with (dE/dx) greater than $2 \frac{\text{MeV}}{\text{mg/cm}^2}$ are observed as well as other particles having the (dE/dx) in excess of this minimum value. For particles with relativistic velocities only those with $Z \geq 26$ have a (dE/dx) above this value.^(2,3) Several other materials with different sensitivities are known to exist,⁽³⁾ and these together with cellulose nitrate can be used as low resolution (dE/dx) spectrometers. Subsequent estimates of the dose due to heavy cosmic ray particles can be made.

Polymer detectors have a number of characteristics that make them particularly attractive for space applications. They are light, rugged, compact, insensitive to temperature and humidity changes, have no latent image fading at ordinary temperatures and are simple to process. Since protons are not registered, the very long exposures needed to

record adequate numbers of heavy ions can be performed. Polymer detectors have the advantage of low weight over electronic systems, e.g., scintillation telescopes. A complete package can be made to weigh a fraction of one ounce. The system avoids a problem encountered with sensitive nuclear emulsions which during prolonged exposures become completely saturated with proton tracks, making it impossible to distinguish the heavy ion tracks from the background. The severe problems of latent image fading encountered with the use of the less sensitive emulsions during prolonged exposures is also avoided.

The orbit characteristics of the Gemini and the early Apollo flights are such that the geomagnetic cutoff for charged particles varies from about 5 to 10 BeV/amu. Thus, only particles with relativistic velocities reach the space craft.

EXPERIMENT

Packets consisting of 10 mil cellulose nitrate plastic and a 600 micron thick Ilford G.5 nuclear emulsion were assembled as in Fig. 1. Both the plastics and the emulsion were in the form of 16 mm diameter disks wrapped and sealed in heavy black paper. Five packets were distributed inside the Gemini VI capsule while the sixth was used as a ground control. The shielding varied from 1 gm/cm² for the packet mounted on the hatch to several gm/cm² for the others. The packets were

NRDL-326-66

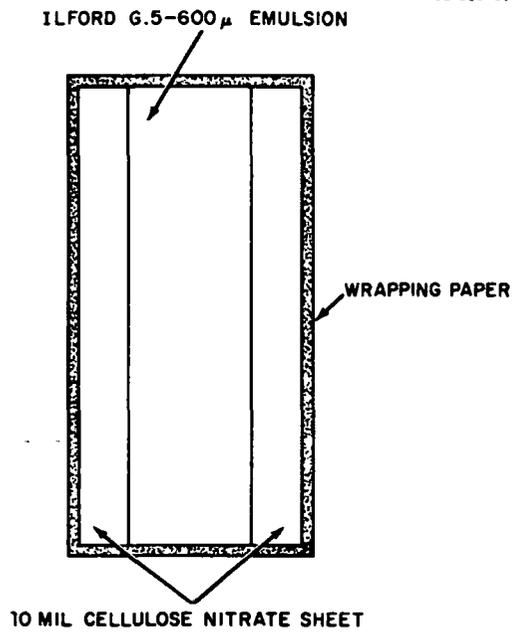


Fig. 1 Edge-on view of the polymer detector packet.

exposed to incident radiation during the 17 orbit flight of Gemini VI lasting 25.9 hours in an orbit with 28.9 degree inclination and having average perigee and apogee of 100 and 162 miles, respectively.

DISCUSSION

Track Registration

In Fig. 2 is shown the relation between the (dE/dx) and the atomic number Z of particles in cellulose nitrate with $\beta (= v/c)$ of 0.145 and 0.899, corresponding to particles with energies of 10 MeV/amu and 1200 MeV/amu respectively. The data were obtained from a computer range-energy program for heavy ions in materials of known composition.* The $\beta = 0.145$ curve corresponds to the low energy part of the cosmic ray spectrum present at high latitudes, but absent in the regions traversed during the flight of Gemini VI. The $\beta = 0.899$ curve represents the (dE/dx) of particles with relativistic velocities and is valid for higher β since the (dE/dx) of a particle does not change by more than 10 - 14 per cent of its value at $\beta = 0.899$. The horizontal line, $(dE/dx)_{\min.} = 1.2 \frac{\text{MeV}}{\text{mg/cm}^2}$, represents our experimental determination of the minimum value of (dE/dx) for track registration in cellulose nitrate. Figure 2 suggests that the lightest particle observable in

* To be published.

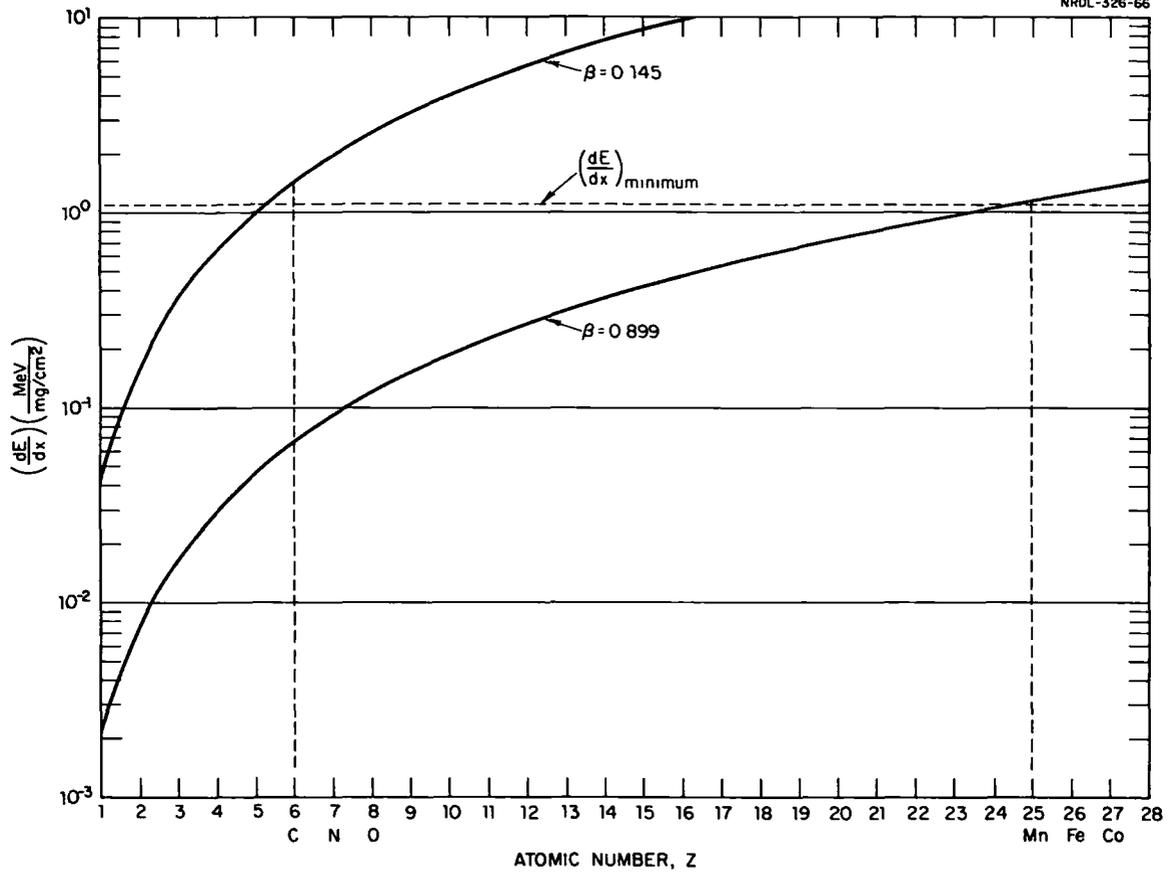


Fig. 2 Calculated rates of energy loss, (dE/dx) , in

$(\frac{\text{MeV}}{\text{mg/cm}^2})$ as a function of the atomic number Z of particles

with $\beta = (v/c) = 0.145$ and 0.899 in cellulose nitrate.

cellulose nitrate for $\beta = 0.145$ is carbon and for $\beta = 0.899$ is either manganese or iron.

In order for a track to be observable through the technique of chemical etching the particle must have a (dE/dx) which is above some minimum value that is characteristic of the material.^(2,3) However, it is felt by the authors that this is a necessary but may not be a sufficient condition for track registration; energy distribution must also be considered. The energy deposition per unit volume along the trajectory is a function of the particle velocity. Particles of relatively low velocity lose a major fraction of their energy through many, low energy transfer collisions, thus confining this energy to a very small volume along the trajectory. This is contrasted with the case of relativistic particles that lose energy through fewer, high energy transfer electron collisions; the struck electrons, having considerable range, distribute the energy over a much larger volume. Thus, the energy per unit volume deposited along the particle trajectory is significantly less for a relativistic than for a low velocity particle, even though both may have the same (dE/dx) . As an example, one can consider an alpha particle with $\beta = 0.036$ and an iron nucleus with $\beta = 0.899$. Although both have the required (dE/dx) for track registration in cellulose nitrate, i.e., $1.25 \frac{\text{MeV}}{\text{mg/cm}}$, the former are readily observable while the latter are not expected to register in cellulose nitrate. For track registration of relativistic particles in cellulose nitrate a considerably greater Z than 26 may be required.

The concept of $(dE/dx)_{\min.}$ for a given material as presented by Fleisher, et al.,⁽²⁾ appears to be useful for low velocity heavy ions, but may need modification when applied to relativistic particles.

The observed track length, ℓ , of a particle track in a polymer is a function of the etch rates along the particle trajectory, r_T , and the bulk etch rate of the polymer, r_B . For a particle incident at an angle θ to the surface ℓ is given by

$$\ell = \int (r_T - r_B \csc \theta) dt$$

where t is the time of etch. The above also holds for a particle traversing the entire thickness of the detector, e.g., a relativistic particle. If $r_T/(r_B \csc \theta) > 1$, then ℓ should increase with etch time. Therefore, it is desirable to have the ratio r_T/r_B as large as possible. It was found that $r_T/r_B \cong 20$ for fission fragment tracks in cellulose nitrate using 30 per cent NaOH etch solution at 60°C. At 23°C, r_T/r_B increases to over one hundred. Thus fission fragment tracks are easily observable, with the measured range closely corresponding to the theoretical range of the particles. For particles with (dE/dx) approaching the $(dE/dx)_{\min.}$ of the given material it appears that r_T/r_B becomes small, approaching unity, and tracks become more difficult to delineate.

A method of increasing r_T/r_B in cellulose nitrate has been found. In Fig. 3 is shown the observed track length, ℓ , as a function of the

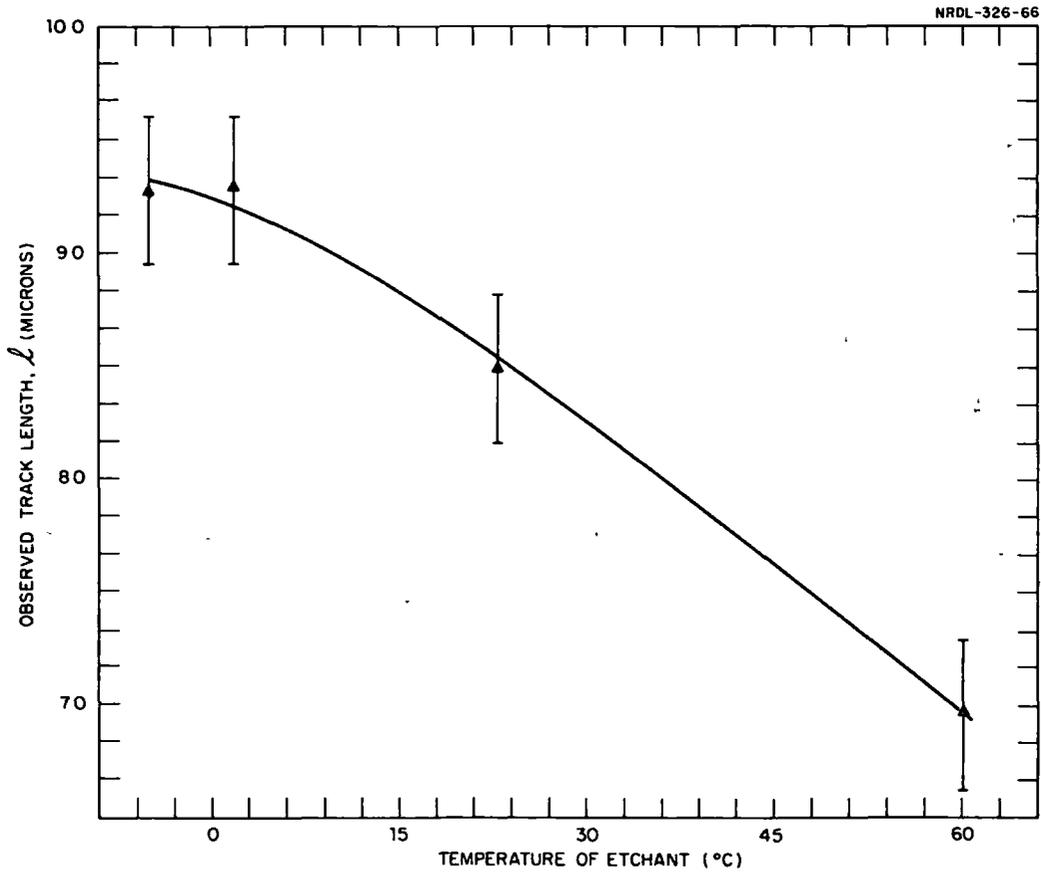


Fig. 3 Observed track length, L , as a function of temperature of etchant (30% NaOH) for 2.1 MeV alpha particles in cellulose nitrate. The theoretical range is 10 microns.

etchant temperature for 2.1 MeV alpha particles. It is seen that by etching at low temperatures for longer etch times (~ 100 hours) l is increased and at 0°C approaches the theoretical range of the particles. This effect is also demonstrated in Fig. 4a,b. Here are shown tracks of ^{40}Ar ions in cellulose nitrate. The particles having energies of 10.4 MeV/nucleon enter the picture at the right. The tracks are about 70 microns long and represent only the initial portion of the total range, which is 181 microns. Tracks in Fig. 4a,b were etched for 13 min at 60°C and 57 hr at 2°C , respectively. It is noted that tracks etched at lower temperatures have a narrower cone angle suggesting that $(r_T/r_B)_{2^\circ\text{C}} > (r_T/r_B)_{60^\circ\text{C}}$. The ratio r_T/r_B can be even further increased by stimulating the diffusion of etchant in the long, narrow cavity of the track by the use of ultrasonic vibrations (see Fig. 5).

Results

Upon recovery, the plastics and emulsions were given a standard processing and examined with the aid of an optical microscope. In plastics the tracks were observed at regular etch intervals. The number and positions of heavy ion tracks were noted in each. In emulsion, track width and delta-ray density were used as track identification criteria.

The mean geomagnetic cutoff for the orbit was estimated to be 6.3 GeV/amu.⁽⁴⁾ Assuming the mean thickness of material surrounding the detector was 10 gm/cm^2 of aluminum, the expected incident heavy ion

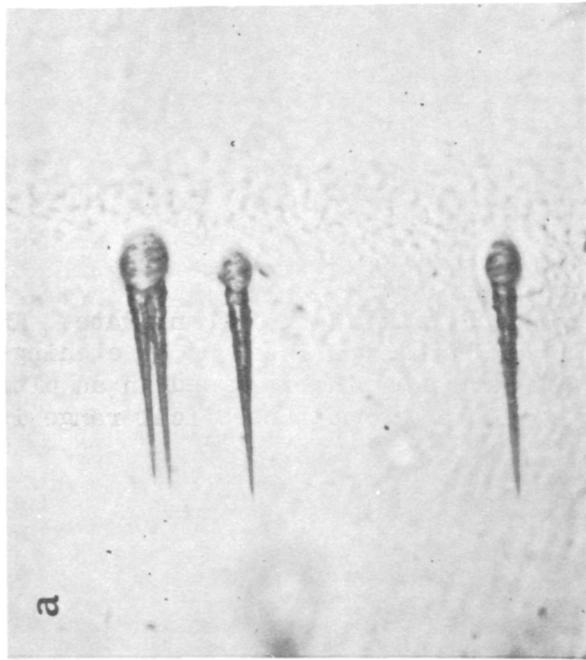


Fig. 4a,b Initial 70 micron portions of 10.4 MeV/nucleon ^{40}Ar ion tracks in cellulose nitrate. Particles traveled from right to left. Tracks in (a) and (b) were etched for 13 min at 60°C , and 57 hrs at 2°C respectively, in a 30% NaOH solution. Tracks in (a) have a cone angle of about twice that of tracks in (b), suggesting a different r_T/r_B for the two etch processes. The sharp terminal end of the track indicates that further etching would increase the track length. Note that the surface of the polymer is pitted in (a), making track observation difficult.

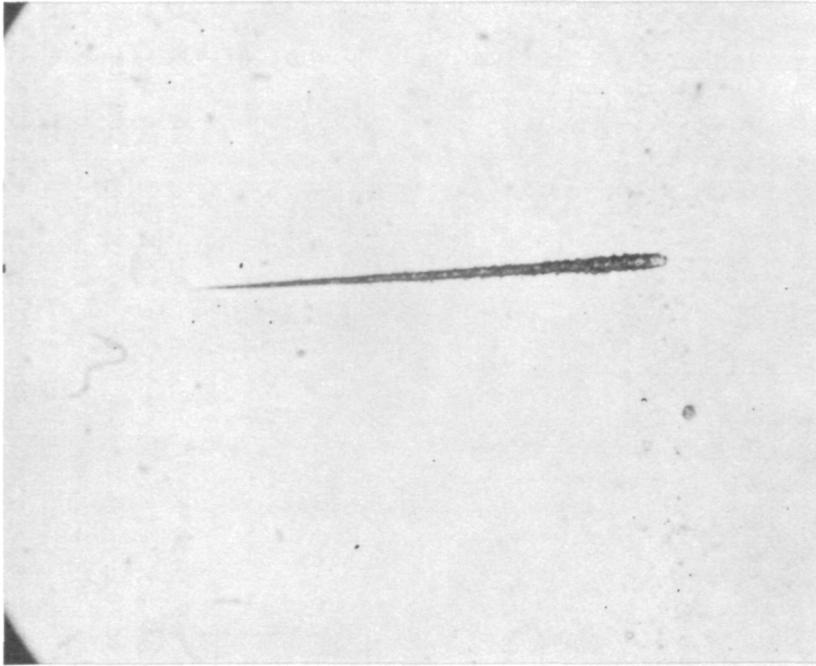


Fig. 5 Track of 10.4 MeV/nucleon ^{40}Ar ion in cellulose nitrate. The particle entered from the right. The track was obtained by etching for 2 hrs at room temperature in a 30% NaOH solution immersed in an ultrasonic bath. The track is 145 microns long; the theoretical range is 181 microns.

flux on the detector for particles with $Z \geq 20$ was estimated to be about $4.1 \text{ ions/cm}^2\text{-day}$.⁽⁵⁾ Examination of emulsions yielded $3.0 \text{ tracks/cm}^2\text{-day}$, a value within the limits of experimental error. An average of $10 \text{ tracks/cm}^2\text{-day}$ was found in the plastic detectors. The track length varied from 5 to 35 microns. Most of the tracks were short, about 10 - 15 microns, and were judged to be due to either imperfections in the polymer surface which upon etching gave track-like appearance, or heavy recoil ions resulting from the interaction of incident protons and the nuclei of the emulsion-plastic interface. About $1 \text{ track/cm}^2\text{-day}$ was judged to be due to the primary cosmic ray particles. These were the longest tracks found and were judged to be too long for recoils. Upon repeated etching they maintained sharp endings in the polymer while increasing in length with etch time. These tracks may possibly be the result of heavy particles, such as the C,N,O group, that have been highly degraded in energy by the material of the space craft, or they may be due to relativistic particles with Z greater than 26. Because of the very short exposure time and limited detector area (10 cm^2) only a few tracks were available. Several of them were steeply dipping tracks, thus further analysis was not possible.

CONCLUSIONS

Polymer detectors are best suitable for registration of slow, heavy ($Z \gg 2$) ions (see Figs. 4a,b and 5). With a possible exception of very heavy particles ($Z > 26$), most relativistic particles do not appear to possess sufficient (dE/dx) for track formation in cellulose nitrate.

A number of changes and improvements in the techniques have suggested themselves as a result of this flight:

1. Longer exposures are clearly necessary. For near equatorial orbits, where the heavy ion flux ($Z = \geq 20$) is approximately 4 ions/cm²-day, exposure periods of several weeks are desirable. The two to three week duration Gemini missions would probably suffice. Even longer exposures could be obtained by leaving the detectors aboard the Agena target vehicle and subsequently recovering them during the next mission.

2. Improvement in the surface characteristics of the detectors is desirable. Some imperfections in the surface are etched preferentially and sometimes have track-like appearances. Long etch times, necessary for delineation of long tracks, tend to degrade the polymer surface, making track observation and photomicrography difficult.

3. A study is being made to determine what Z a relativistic particle must have in order to produce a track in cellulose nitrate.

4. Examination of Fig. 2 reveals that the (dE/dx) of a relativistic iron nucleus is some 30 times greater than that of a comparable

velocity proton. Since nuclear emulsions record "minimum ionization particles," there exists at present a range of about three decades between the most sensitive emulsion and the most sensitive polymer detector. In fact the sensitivity of cellulose nitrate roughly corresponds to the sensitivity of Ilford K minus 1 nuclear emulsion, which is one of the least sensitive emulsions manufactured.^(6,7) It seems very improbable that the sensitivity of polymer detectors could be increased to the point where registration of minimum ionization tracks would be possible. However, a sensitivity increase by a factor of 2 or 3 does not appear improbable and would be highly desirable. In fact the $(dE/dx)_{\min.}$ of $1.2 \frac{\text{MeV}}{\text{mg/cm}^2}$ for cellulose nitrate quoted by us differs from the value of $2 \frac{\text{MeV}}{\text{mg/cm}^2}$ given earlier by Fleischer, et al.⁽²⁾

The $(dE/dx)_{\min.}$ of a material appears to be a function not only of the material itself but also of the etching process. The type of etchant and the temperature both play a role in determining the etch rate along the particle trajectory and the bulk etch rate and thus determine the $(dE/dx)_{\min.}$ of the material. With an optimum combination of polymer material and etching process, it is probable that a detector of greater sensitivity can be achieved.

REFERENCES

1. H. S. Schaefer, Advances in Space Science, p. 267. Academic Press, New York (1959).
2. R. L. Fleischer, P. B. Price and R. M. Walker, Phys. Rev. 133, A1443 (1964).
3. R. L. Fleischer, P. B. Price and R. W. Walker, G.E. Report No. 65-RL-3933M (1965).
4. J. J. Quenby and W. J. Wenk, Phil. Mag. 7, 1457 (1962).
5. C. J. Waddington, Prog. in Nucl. Phys. 8 3 (1960).
6. W. H. Barkas, Nuclear Research Emulsions, Vol. X, p. 15. Academic Press, New York and London (1963).
7. E. V. Benton and E. Tochilin, Health Phys. 12, 49 (1966).

Physics

INITIAL DISTRIBUTION

Copies

NAVY

1 Chief of Naval Material (MAT 0331)
2 Commander, Naval Ship Systems Command (Code 2021)
1 Commander, Naval Ship Systems Command (SHIPS 03541)
1 Commander, Naval Air Systems Command (AIR 538)
1 Chief of Naval Operations (Op-07T)
1 Chief of Naval Operations (Op-75)
1 Director, Naval Research Laboratory
1 Chief of Naval Research (Code 420)
3 CO, Office of Naval Research, Branch Office, London
1 Supt., Naval Postgraduate School, Monterey

ARMY

1 Chief of Research and Development (Atomic Office)
1 CO, Army Electronic Research and Development Laboratory

AIR FORCE

1 Assistant Chief of Staff, Intelligence (AFNIE)
1 Director, USAF Project RAND
1 Director, Air University Library, Maxwell AFB
1 Commander, AF Cambridge Research Laboratories (CRMCLR)

OTHER DOD ACTIVITIES

3 Director, Defense Atomic Support Agency (Library)
1 Commander, FC/DASA, Sandia Base (FCTG5, Library)
20 Defense Documentation Center

AEC ACTIVITIES AND OTHERS

3 Atomic Energy Commission, Washington
1 NASA, Lewis Research Center
1 National Bureau of Standards

15 Division of Technical Information, Oak Ridge

USNRDL

40 Technical Information Division

DISTRIBUTION DATE: 26 August 1966

UNCLASSIFIED

Security Classification

DOCUMENT CONTROL DATA - R&D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1 ORIGINATING ACTIVITY (Corporate author) U. S. Naval Radiological Defense Laboratory San Francisco, California 94135		2a REPORT SECURITY CLASSIFICATION UNCLASSIFIED	
		2b GROUP	
3 REPORT TITLE CHARGED PARTICLE TRACKS IN POLYMERS: NUMBER 2 - REGISTRATION OF HEAVY IONS DURING THE FLIGHT OF GEMINI VI			
4 DESCRIPTIVE NOTES (Type of report and inclusive dates)			
5 AUTHOR(S) (Last name, first name, initial) Benton, Eugene V. Collver, Michael M.			
6 REPORT DATE 26 August 1966		7a TOTAL NO OF PAGES 26	7b NO OF REFS 7
8a CONTRACT OR GRANT NO. NASA Subtask A-65315		9a ORIGINATOR'S REPORT NUMBER(S) USNRDL-TR-1037	
b. PROJECT NO		9b OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
c			
d			
10 AVAILABILITY/LIMITATION NOTICES Distribution of this document is unlimited.			
11 SUPPLEMENTARY NOTES		12 SPONSORING MILITARY ACTIVITY National Aeronautics and Space Administration, Washington, D. C.	
13 ABSTRACT Several small disks of cellulose nitrate plastic were included as a part of a dosimetry package aboard the Gemini VI spacecraft for the purpose of recording the heavy component of the primary cosmic radiation. An average of 10 tracks/cm ² -day was found in the plastic detectors. Most of these were judged to be tracks of heavy recoil ions; about 1 track/cm ² -day was judged to be due to the primary cosmic ray particles.			

14	KEY WORDS	LINK A		LINK B		LINK C	
		ROLE	WT	ROLE	WT	ROLE	WT
Tracks Polymers Heavy ions							

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.