

NASA TECH BRIEF

NASA Pasadena Office




NASA Tech Briefs announce new technology derived from the U.S. space program. They are issued to encourage commercial application. Tech Briefs are available on a subscription basis from the National Technical Information Service, Springfield, Virginia 22151. Requests for individual copies or questions relating to the Tech Brief program may be directed to the Technology Utilization Office, NASA, Code KT, Washington, D.C. 20546.

Improved Insulating Materials Effective at Extremely High Temperatures

Two multilayer foil and fabric insulators, usable to 1367 K (2000° F) and up to 2478 K (4000° F), respectively, offer marked space saving and efficiency

tests, the foil and fabric were wrapped to a radial thickness of 1.47 cm (0.58 in.) around the combustion chamber of a graphite rocket engine. The

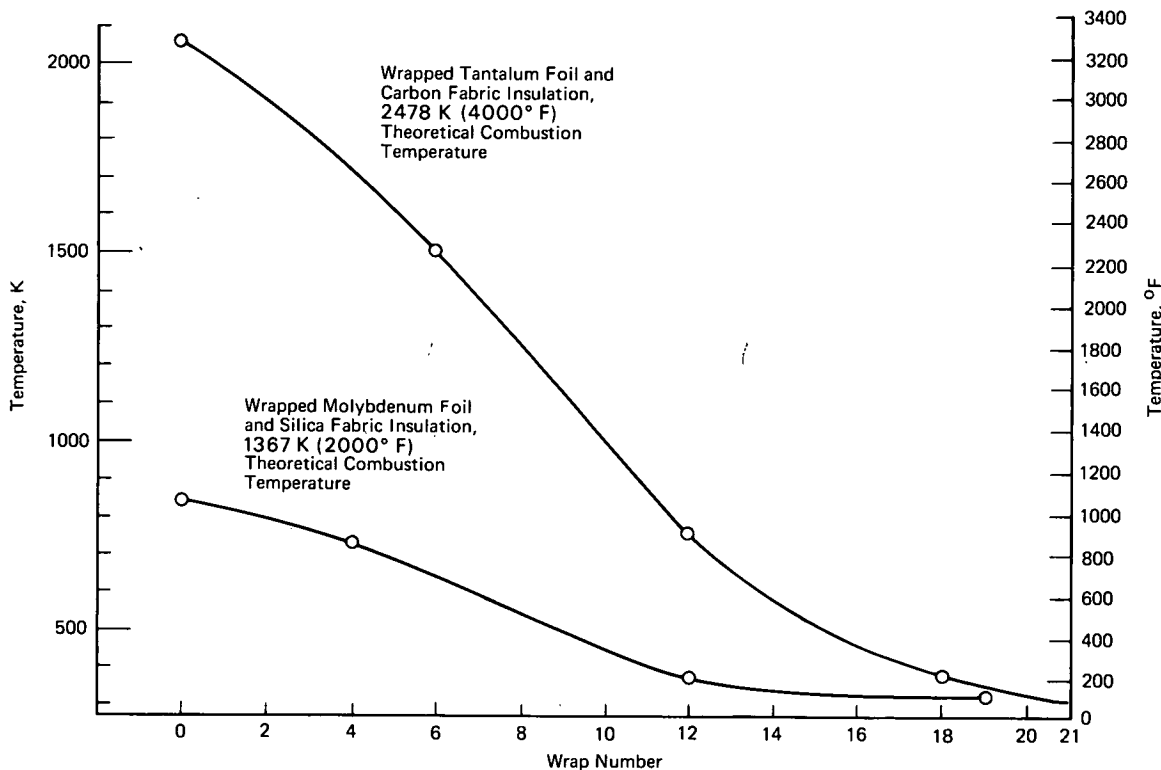

Typical Temperature Profiles at End of Firing Period

in nuclear power, plasmas, magnetohydrodynamics, and other high-temperature operations.

The lower-temperature configuration consists of molybdenum foil, 0.0254 mm (0.001 in.) thick, wrapped with an interleaved layer of silica cloth around the object to be insulated. In developmental

assembly was installed in a vacuum chamber which was taken down to an initial vacuum of 1.3×10^{-2} N/m² (10⁻⁴ torr). The engine was fired at a theoretical combustion temperature of 1367 K for a period of 1000 sec. A maximum heat load of 46 W of thermal energy was detected by the

(continued overleaf)

calorimeter which surrounded the insulation. Typical temperatures at various points in the wrapped insulation, as indicated at the end of the firing period, are shown in the figure.

The foil maintained its integrity during firing, although the surface near the combustion chamber was rough and discolored. The silica fabric was only slightly sintered in the layers closest to the chamber. The low effective thermal conductivity of this molybdenum-silica insulator at relatively low temperatures favors its use up to 1367 K.

A similar configuration of tantalum foil, 0.0254 mm thick, and carbon cloth is usable at even higher temperatures. During testing, the tantalum-carbon insulation materials were wrapped to a radial thickness of 2.54 cm (1.0 in.) around the combustion chamber. Despite an initial vacuum similar to that obtained in the molybdenum-silica tests, the pressure rose to between 2.66×10^2 to 1.64×10^3 N/m² due to extreme out-gassing during firing at a theoretical temperature of 2478 K. The maximum heat load was 113 W of thermal energy. Typical temperatures at the end of the firing period, as detected at various levels within the tantalum-carbon insulation package, are also shown in the figure.

The inner layers of tantalum foil combined chemically with the carbon cloth during firing, forming brittle tantalum carbide. This carbide, however, is itself an effective part of the insulator because of its reflective surface. The strength of the carbon cloth was not significantly affected, although

the cloth was somewhat changed in appearance in the hotter regions. The tantalum-carbon insulation essentially retained its integrity throughout the firing and soakback period.

Above 1367 K, the effective thermal conductivity of the tantalum-carbon insulator is lower than that of the molybdenum-silica one. The tantalum-carbon insulator is therefore recommended for use at temperatures above 1367 K up to 2478 K.

Note:

Requests for further information may be directed to:

Technology Utilization Officer
NASA Pasadena Office
4800 Oak Grove Drive
Pasadena, California 91103
Reference: TSP71-10289

Patent status:

Inquiries about obtaining rights for the commercial use of this invention may be made to:

Patent Counsel
Mail Code 1
NASA Pasadena Office
4800 Oak Grove Drive
Pasadena, California 91103

Source: L. W. Carlson of
North American Rockwell Corp.
under contract to
NASA Pasadena Office
(NPO-12067)