


Direct

File as AD-738880

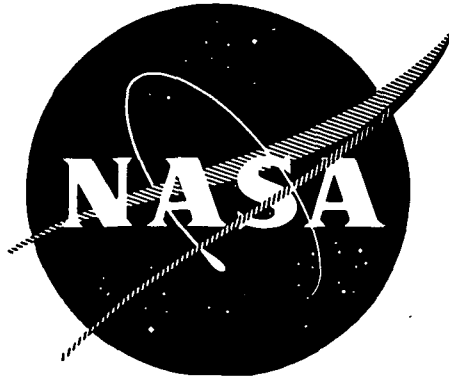

(NASA-CR-126531) EVALUATION PROGRAM FOR
SECONDARY SPACECRAFT CELLS Eighth Annual
Report of Cycle Life Test D.E. Christy
(Naval Ammunition Depot) 9 Feb. 1972
302 p

N72-24038

Unclas
15291

CSSL 10A G3/03

EVALUATION PROGRAM
for
SECONDARY SPACECRAFT CELLS

EIGHTH ANNUAL REPORT
OF
CYCLE LIFE TEST



prepared for
GODDARD SPACE FLIGHT CENTER
CONTRACT W12,397

QUALITY EVALUATION LABORATORY
NAD CRANE, INDIANA

NAVAL AMMUNITION DEPOT
QUALITY EVALUATION AND ENGINEERING LABORATORY
CRANE, INDIANA 47522

EVALUATION PROGRAM
FOR
SECONDARY SPACECRAFT CELLS

EIGHTH ANNUAL REPORT
OF
CYCLE LIFE TEST

QEEL/C 72-1

9 FEBRUARY 1972

PREPARED BY

D. E. Christy
D. E. CHRISTY

PREPARED UNDER THE DIRECTION OF

D. E. Mains
D. E. MAINS
Manager, Space Satellite
Cell Program Branch

APPROVED BY

D. G. Miley
D. G. MILEY
By direction

Enclosure (1)

TABLE OF CONTENTS

	PAGE NO.
REPORT BRIEF	i
INTRODUCTION	1
SPACE ORIENTED TESTS IN ADDITION TO LIFE CYCLING TESTS	7
DEFINITIONS	9

SECTION I

I. CELLS ON ORIGINAL TEST PROGRAM STILL CYCLING (GE 12.0 ah, Nickel-Cadmium)	13

SECTION II

I. CELLS USING CONSTANT CURRENT CHARGE WITH VOLTAGE LIMIT CONTROL (CELLS PRESENTLY CYCLING WHICH FOLLOWED THE ORIGINAL PROGRAM)	18
A. General Description:	19
B. Nickel-Cadmium Types	19
1. Gulton 3.5 ah (Polymerized Neoprene Seal)	19
2. Gulton 4.0 ah (Commercial)	25
3. Gulton 5.0 ah (Cobalt additive with pellaon or polypropylene separator)	29
4. Gulton 5.0 ah (NIMBUS)	36
5. Gulton 5.6 ah (Neoprene Seal)	39
6. Gulton 6.0 ah (Improved)	45
7. Gulton 6.0 ah	48
8. Gulton 6.0 ah (TETR)	51
9. Gulton 12.0 ah (OGO)	53
10. Gulton 20.0 ah (OAO)	57

11. GE 5.0 ah (NIMBUS)	59
12. GE 6.0 ah (Nickel-Braze)	63
13. Sonotone 3.0 ah (Triple Seal)	72
14. Sonotone 3.5 ah	75
15. NIFE 3.9 ah	78
C. Silver-Cadmium Types	80
1. Yardney 5.0 ah	80
2. Electromite 7.0 ah	83
D. Silver-Zinc Types	85
1. Astropower, McDonnell Douglas, 40.0 ah, (Venus Orbiter)	85
II. CELLS USING SOPHISTICATED CHARGE METHODS AND DEVICES	88
A. General Description	88
B. High Overcharge Current Capabilities	92
1. Gulton 1.25 ah (Nickel-Cadmium)	92
C. Auxiliary Electrode	94
1. Eagle-Picher, 6.0 ah (Nickel-Cadmium)	94
2. Eagle-Picher, 6.0 ah (Nickel-Cadmium, Separator Test)	99
3. Gulton 6.0 ah (Nickel-Cadmium)	112
4. Gulton 6.0 ah (Nickel-Cadmium)	115
5. Gulton 6.0 ah (Nickel-Cadmium, Overcharge)	118
6. Gulton 12.0 ah (Nickel-Cadmium)	122
7. Gulton 20.0 ah (OAO), (Nickel-Cadmium)	125

PAGE NO.

8. Gulton 20.0 ah (OAO), (Nickel-Cadmium, Precharge)	129
9. Gulton 20.0 ah (OAO), (Nickel-Cadmium)	132
10. Gulton 20.0 ah (OAO), (Nickel-Cadmium)	135
11. Gulton 20.0 ah (OAO)	137
12. GE 6.0 ah (Nickel-Cadmium)	139
13. GE 6.0 ah (Auxiliary and Recombination Electrodes)	144
14. GE 20.0 ah (Nickel-Cadmium)	149
15. Yardney 11.0 ah (Silver-Cadmium)	152
D. Coulometer	155
1. Gulton 6.0 ah (With Gulton Plates)	155
2. Gulton 6.0 ah (Nickel-Cadmium)	161
E. Internal Pressure Devices	165
1. Sonotone 20.0 ah (Nickel-Cadmium)	165
F. Thermister	170
1. Gulton 6.0 ah (Nickel-Cadmium) (SAS A)	170
2. GE 6.0 ah (Nickel-Cadmium) (SAS B)	172

SECTION III

I. CELLS ON ORIGINAL TEST PROGRAM WHICH HAVE COMPLETED TEST	175
II. DESCRIPTION OF CYCLE TEST	175
III. TEST RESULTS	175

SECTION IV

I. COMPLETED TESTS OF CELLS WHICH FOLLOWED THE ORIGINAL PROGRAM	183
II. CELLS USING CONSTANT CURRENT CHARGE WITH VOLTAGE LIMIT CONTROL	183
A. Nickel-Cadmium Types	183
1. Gulton 6.0 ah	183
2. Gulton 50.0 ah	185
3. GE 12.0 ah	187
B. Silver-Zinc Types	189
1. Astropower, McDonnell Douglas, 5.0 ah	189
2. Delco-Remy 25.0 ah	191
3. Delco-Remy 25.0 ah	191
4. Delco-Remy 40.0 ah	192
5. Yardney 12.0 ah	193
C. Silver-Cadmium Types	194
1. ESB 8.0 ah	194
2. Yardney 3.0 ah (FR-1)	196
3. Yardney 5.0 ah (C-3 Separator)	197
4. Yardney 5.0 ah (Cellophane Separator)	199
5. Yardney 5.0 ah (Pellon Control Separator)	200
6. Yardney 5.0 ah (Pellon and Cellophane Separator)	201
7. Yardney 10.0 ah	203

8. Yardney 11.0 ah	204
9. Yardney 11.0 ah	205
10. Yardney 12.0 ah	206
11. Yardney 12.0 ah	207
III. CELLS USING SOPHISTICATED CHARGE CONTROL METHODS AND DEVICES	209
A. Auxiliary Electrode	209
1. Gulton 6.0 ah (Nickel-Cadmium)	209
2. Gulton 10.0 ah (Nickel-Cadmium)	211
3. Gulton 20.0 ah (OAO), (Nickel-Cadmium)	212
4. Gulton 20.0 ah (OAO), (Nickel-Cadmium)	214
5. Gulton 20.0 ah (OAO), (Nickel-Cadmium, Precharge)	216
6. GE 6.0 ah (Nickel-Cadmium)	218
7. GE 6.0 ah (Nickel-Cadmium)	220
8. GE 12.0 ah (Nickel-Cadmium)	222
9. GE 12.0 ah (Nickel-Cadmium)	224
10. Sonotone 5.0 ah (Nickel-Cadmium)	226
11. Yardney 12.0 ah (Silver-Cadmium)	227
B. Stabistor	228
1. Sonotone 5.0 ah (Nickel-Cadmium)	228
C. Coulometer	231
1. Gulton 3.6 ah (Nickel-Cadmium with Neoprene Seal)	231

2. Gulton 4.0 ah (Nickel-Cadmium)	233
3. Sonotone 5.0 ah (Nickel-Cadmium)	235
D. Sherfey Upside-Down Cycling	237
1. Test Equipment	237
2. Gulton 3.6 ah (Nickel-Cadmium)	237
E. Two-Step Charge Regulator	238
1. Test Equipment	238
2. Delco-Remy 25.0 ah (Silver-Zinc)	238
3. Yardney 16.0 ah (Silver-Zinc)	240
F. Internal Pressure Devices	241
1. Sonotone 20.0 ah (Nickel-Cadmium)	241

SECTION V

I. TEST FACILITIES	244
A. Environmental Chambers	244
B. Charge and Discharge Control Units	244
C. Upper and Lower Voltage Limit Monitoring System	245
D. Data Logging System	245
E. Central Wiring Panel	248
F. Pack Selector Switch	248
G. Block Diagram of Entire Test Setup	248
H. Photograph of Test Area	248

SECTION VI

I. EQUIPMENT AND PROGRAMS TO BE ADDED TO THE CYCLE LIFE TEST PROGRAM	258
A. New Equipment	258
B. New Programs	258

LIST OF TABLES

TABLE NUMBERS	CAPTIONS	PAGE NUMBERS
I	Physical Characteristics of Cells	180
II	Summary of Test Parameters	181

LIST OF PHOTOGRAPHS

PHOTOGRAPH NUMBERS	CAPTIONS	PAGE NUMBERS
1	Charge and Discharge Control Units	251
2	Pack Voltage Monitoring Panel	252
3	Individual Cell Voltage Scanning System	253
4	Data Logging System	254
5	Portion of Central Wiring Panel	255
6	Test Area	256
7	Automatic Data Acquisition and Control System	259

LIST OF FIGURES

FIGURE NUMBERS	CAPTIONS	PAGE NUMBERS
1-2	Capacity, at Cycle Rate, to 1.20, 1.10 and 1.00 Volts	5
3	Precycling and Capacity Check Cycles	14
	VOLTAGE AND PERCENT OF RECHARGE CHARACTERISTICS ON CYCLING VERSUS CYCLE NUMBER	
4-6	GE 12 ah, Nickel-Cadmium	15
7-9	Gulton 3.5 ah, Ni-Cd, Polymerized Neoprene Seal	22
10-11	Gulton 4.0 ah, Nickel-Cadmium, Commercial	27
12-16	Gulton 5.0 ah, (Cobalt additive with pellaon or polypropylene separator)	31
17	Gulton 5.0 ah, Nickel-Cadmium, NIMBUS	38
18	Gulton 5.6 ah, Nickel-Cadmium, Neoprene Seal (Cross Section of Neoprene Seal)	41
19-21	Gulton 5.6 ah, Nickel-Cadmium, Neoprene Seal	42
22	Gulton 6.0 ah, Nickel-Cadmium, Improved	47
23	Gulton 6.0 ah, Nickel-Cadmium	50
24	Gulton 6.0 ah, Nickel-Cadmium	52
25-26	Gulton 12.0 ah, Nickel-Cadmium, OGO	55
27	Gulton 20.0 ah, Nickel-Cadmium, OAO	59
28-29	GE 5.0 ah, Nickel-Cadmium, NIMBUS	61
30-37	GE 6.0 ah, Nickel-Cadmium, Nickel-Braze	64
38	Sonotone 3.0 ah, Nickel-Cadmium, Triple Seal	74
39	Sonotone 3.5 ah, Nickel-Cadmium	77

FIGURE NUMBERS	CAPTIONS	PAGE NUMBERS
	VOLTAGE AND PERCENT OF RECHARGE CHARACTERISTICS ON CYCLING VERSUS CYCLE NUMBER	
40	NIFE 3.9 ah, Nickel-Cadmium	79
41	Yardney 5.0 ah, Silver-Cadmium	82
42	Electromite 7.0 ah, Silver-Cadmium, IMP	84
43-44	Astropower (McDonnell-Douglas) 40.0 ah, Silver- Zinc, VENUS ORBITER	86
45-47	Gulton 1.25 ah, Nickel-Cadmium, High Overcharge	91
48-50	Eagle-Picher 6.0 ah, Ni-Cd, Auxiliary Electrode	96
51-60	Eagle-Picher 6.0 ah, Ni-Cd, Separator Test	102
61	Gulton 6.0 ah, Ni-Cd, Auxiliary Electrode	114
62-63	Gulton 6.0 ah, Ni-Cd, Auxiliary Electrode	116
64-66	Gulton 6.0 ah, Ni-Cd, Overcharge	119
67	Gulton 12.0 ah, Ni-Cd, Auxiliary Electrode	124
68-69	Gulton 20 ah, Ni-Cd, Auxiliary Electrode	127
70	Gulton 20 ah, Ni-Cd, Auxiliary Electrode, OAO, Precharge	131
71	Gulton 20 ah, Ni-Cd, Auxiliary Electrode, OAO	134
72	Gulton 20 ah, Ni-Cd, Auxiliary Electrode, OAO	136
73	Gulton 20 ah, Ni-Cd, Auxiliary Electrode, OAO	138
74-76	GE 6.0 ah, Ni-Cd, Auxiliary Electrode	141
77-79	GE 6.0 ah, Ni-Cd, Signal and Recombination Electrodes	146
80-81	GE 20.0 ah, Ni-Cd, Auxiliary Electrode	150

FIGURE NUMBERS	CAPTIONS	PAGE NUMBERS
	VOLTAGE AND PERCENT OF RECHARGE CHARACTERISTICS ON CYCLING VERSUS CYCLE NUMBER	
82	Yardney 11.0 ah, Ag-Cd, Auxiliary Electrode	154
83-86	Gulton 6.0 ah, Ni-Cd, (with Gulton plates)	157
87-88	Gulton 6.0 ah, Nickel-Cadmium	163
89-91	Sonotone 20.0 ah, Nickel-Cadmium, Internal Mechanical Pressure Devices	167
92	Gulton 6.0 ah, Ni-Cd, Thermistor, SAS A	171
93	GE 6.0 ah, Ni-Cd, Thermistor, SAS B	173
	BLOCK DIAGRAM OF TEST EQUIPMENT	
94	Data Logging System	249
95	Test Setup	250

REPORT BRIEF
CYCLE LIFE TEST
OF
SECONDARY SPACECRAFT CELLS

- Ref: (a) NASA Purchase Order Number W12-397
(b) NASA ltr BRA/VBK/pad of 25 Sep 1961 w/BUWEPS first end
FQ-1:WSK of 2 Oct 1961 to CO NAD Crane
(c) Preliminary Work Statement for Battery Evaluation Program
of 25 Aug 1961
(d) NAD Crane report QE/C 70-687 of 20 Sep 1970

I. TEST ASSIGNMENT

A. In compliance with references (a) and (b), evaluation of secondary spacecraft cells was begun according to the program outline of reference (c). This eighth annual report covers the cycle life test of the evaluation program of secondary spacecraft cells, through 14 December 1971. The acceptance tests and general performance tests of the evaluation program were reported earlier where applicable. The purpose of the acceptance tests is to insure that all cells put into the life cycle program meet the specifications outlined in the respective purchase contracts. A sample number of cells of each type (usually five) are subjected to the general performance tests to determine the limit of their actual capabilities. All reports may be obtained from National Aeronautics and Space Administration, Scientific and Technical Information Division (Code US), Washington, D. C. and from Director, Defense Documentation Center, Cameron Station, Alexandria, Virginia 22314.

B. This evaluation program gathers statistical information concerning cell performance characteristics and limitations which is used by spacecraft power systems planners, designers, and integration teams. Weaknesses discovered in cell design are reported and aid in research and development efforts toward improving the reliability of space batteries. Battery weaknesses encountered in satellite programs such as IMP, NIMBUS, OGO, OAO, SAS, and TETR have been studied and remedied through special tests performed at NAD Crane.

II. TEST OUTLINE

A. On 5 December 1963 this activity began the cycle life test on 660 sealed, nickel-cadmium cells purchased by NASA. The cells were from four manufacturers, and consisted of seven sample classifications ranging from 3.0 to 20 ampere-hours. Since then 1054

nickel-cadmium, 178 silver-cadmium and 125 silver-zinc cells from several manufacturers have been added to the program. The capacities of the nickel-cadmium cells ranged from 1.25 to 50 ampere-hours; that of the silver-cadmium cells ranged from 3.0 to 12.0 ampere-hours; and that of the silver-zinc cells ranged from 5 to 40 ampere-hours. The purpose of the cycle life program is to determine the cycling performance capabilities of packs of cells (5 or 10 cell packs) under different load, charge control and temperature conditions. The load conditions include cycle length (orbit periods) of 1.5, 3.0, 8.0, 12 and 24 hours; and depth of discharge ranging from 10 to 75 percent. The charge control methods used are voltage limit, auxiliary electrode, coulometer, stabistor, a two-step regulator, thermistor controlled voltage limit, and the Sherfey upside-down cycling regime. Specially constructed cells to apply internal pressure against the face of the plate stack, and a type to permit high charge rates were also tested. Environmental conditions include ambient temperatures of -20°C , 0°C , 20°C , 25°C , 40°C , 50°C , and a cycling temperature of 0° to 40°C within a period of 48 hours. A "Summary in Brief of Test Parameters" is listed on page iv.

III. TEST RESULTS

A. Life cycling data shows that nickel-cadmium cells tested at 0°C give longer cycle life, higher end-of-discharge voltages and less degradation of ampere-hour capacities than cells tested at 25°C or 40°C . Overall performance decreases with increase in the depth of discharge at all test temperatures. Cell cycle life is extended when the amount of recharge is limited to the following amounts: 105 percent at 0°C , 115 percent at 25°C and 125 percent at 40°C . Operating performance can also be improved by recharging at rates between $c/2$ and $c/10$ with the amount of recharge controlled by auxiliary electrodes or cadmium-cadmium coulometers. A statistical analysis of the life cycle prediction and cause of failure versus test conditions are given in reference (d).

B. Cycle life data is more limited on silver-cadmium cells. However the silver-cadmium data leads to the following generalizations:

1. Depth of Discharge: Longest life is found at 18 to 25 percent depth of discharge, while 40 to 50 percent depth shortens life.

2. Temperature: Cells giving longest life have operated at 0° to 25° C. Temperatures of 40° C are detrimental. Only one of five packs operating at 40° C (33C) has exceeded 400 days of cycling. Limited data at -20° C indicates short life at this temperature. This is exemplified in pack 85B which cycled 148 days.

3. Orbit Period: The orbit period for silver-cadmium cells is predominately 8 or 24 hours. The failures are not common to either regime until the packs exceed 660 days (approximately 2 years) of testing. Failures prior to this time on test are randomly distributed between the orbit regimes. Four of five packs (57D, 77B, 33B and 113B) exceeding 660 days have operated under a 24-hour orbit regime. Thus the longevity of the silver-cadmium cells is favored by the 24-hour orbit period.

C. The silver-zinc packs were predominantly 24-hour orbit, 40 percent depth of discharge at 25° C. Thus comparison of operational characteristics of the cells at different parameters is not possible. The basic conclusion is that silver-zinc has very short life under these conditions ranging from 32 to 325 days of cycling--the average being 120 days.

D. Cell failure analyses have shown several failure modes such as little or no insulation around tabs and busses, ceramic shorts across the terminals, and leaks around the terminals which since have been corrected. A better separator material is still needed to extend cycle life of cells. Better quality control programs in the manufacturers' plants would do much to eliminate or minimize failure due to misaligned separator material, blistering of positive plates, ragged plate edges, and extraneous material, both active and foreign.

E. Carbonate analyses of a limited number of nickel-cadmium separator tests have revealed extremely high percentages (equivalence) of carbonate. The average is slightly over 60 percent of the total equivalence.

F. All active and completed packs are listed on pages vii through xix. The symbols used are explained on pages v and vi.

SUMMARY IN BRIEF OF TEST PARAMETERS

MANUFACTURER	CAPACITIES TESTED	ORBIT PERIOD	PERCENT DEPTH OF DISCHARGE	TEST TEMPERATURES	SPECIAL CHARGE CONTROL	TOTAL NO. OF CELLS
NICKEL-CADMIUM						
GE	3.0, 5.0, 6.0, 12.0, 20.0	1.5, 3.0, 24.0	15, 21, 25, 40, 50	0°, 20°, 25°, 40°, 50°-40°, *	AE, AE14, AE14, THER	403
Gould	3.5, 20.0	1.5, 3.0	15, 25, 40	0°, 25°, 50°-40°		180
Gulton	1.25, 3.5, 3.6, 4.0, 5.0, 5.6, 6.0, 10.0, 12.0, 20.0, 50.0	1.5, 3.0, 24.0	10, 15, 21, 25, 40, 50, 60	-20°, 0°, 20°, 25°, 50°-40°, 40°, *	AE, CLM, MULTI THER	714
NIFE						
	3.9	1.5	25	0°, 25°		10
Sonotone	3.0, 3.5, 5.0, 20.0	1.5, 3.0	15, 25, 40, 75	-20°, 0°, 20°, 25°, 50°-40°, 40°	ST, AE, IPD	305
Eagle-Picher						
	6.0	1.5	25	0°, 20°	AE	76
SILVER-CADMIUM						
ESB	8.0	8.0	25	25°	AE	5
Yardney	3.0, 5.0, 10.0, 11.0, 12.0, 24.0	1.5, 8.0, 24.0	16, 20, 27, 30, 40, 43	-20°, 0°, 25°, 40°	AE-GE	169
Electromite	7.0	8.0	30	20°		3
SILVER-ZINC						
Delco	25.0, 40.0	3.0, 24.0	25, 40	25°	25R	45
Mc-Donnell Douglas	5.0, 40.0	1.5, 12.0, 4.0	25	20°, 40°		60
Yardney	12.0, 16.0	24.0	31, 42	25°	25R	20

EXPLANATION OF SYMBOLS

1. Temperature:

- * Ambient temperature which varies sinusoidally from 0° to 40° C once per 48-hour period.

2. Special Symbols:

AE: Auxiliary electrode cells.

AE-GE: General Electric type.

AE-GU: Gulton type.

AE13: General Electric type AB13.

AE14: General Electric type AB14.

ASTRO: Astropower Laboratory, McDonnell-Douglas.

CC: Commercial cells.

CHSP: "Chemsorb" separator.

CLM: Coulometer in series with cells to effect charge control.

CO-NI: Nickel-cadmium cells with cobalt additive to nickel-plate.

CPSP: Cellophane separator.

C3SP: C3 separator.

FRS: Folded, vulcanized neoprene, terminal to cover seal.

IM: Cells with improved material and methods used in construction.

IPD: Cells containing an internal pressure device.

MULTI: Pack contains coulometer and cell with and without auxiliary electrodes.

MULTI*: Pack contains cells with and without auxiliary electrodes.

NB: NIMBUS cells.

NBPT: NIMBUS cells with pressure transducers.

PLSP: Pellon separator.

PS: Polymerized neoprene terminal to cover seal.

RC-AE: Recombination and auxiliary electrodes.

RCPSP: Radiated cellophane separator.

RS: Vulcanized neoprene terminal to cover seal.

SAS: Small astronomical satellite.

ST: Stabistors used for charge control of cells.

TETR: Test and training satellite.

THER: Thermistor controlled voltage limit.

WNSP: Woven nylon separator.

2SR: Two-step regulator used for charge control of cells.

3S: Triple seal between terminals and cover (ceramic between glass).

3. Date Completed:

D: Discontinued

F: Failed

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED
NICD	3.00	1.5	15%	0°	GE		63A	0.52	0.90	10	12-6-63	22,923	2-15-68 D
NICD	3.00	3.0	15%	0°	GE		67A	0.21	0.90	10	12-20-63	11,532	2-15-68 D
NICD	3.00	1.5	25%	0°	GE		64A	0.86	1.50	10	12-5-63	23,441	2-14-68 D
NICD	3.00	3.0	25%	0°	GE		68A	0.34	1.50	10	12-20-63	11,740	2-13-68 D
NICD	3.00	1.5	25%	25°	GE		15A	0.94	1.50	10	12-6-63	10,382	11-6-65 F
NICD	3.00	3.0	25%	25°	GE		19A	0.38	1.50	10	12-20-63	10,768	2-12-68 D
NICD	3.00	1.5	40%	25°	GE		16A	1.50	2.40	10	12-5-63	5,014	11-18-64 F
NICD	3.00	3.0	40%	25°	GE		20A	0.60	2.40	10	12-20-63	5,410	1-8-66 F
NICD	3.00	1.5	15%	40°	GE		39A	0.72	0.90	10	12-12-63	8,109	6-19-65 F
NICD	3.00	3.0	15%	40°	GE		43A	0.29	0.90	10	12-20-63	2,656	12-26-64 F
NICD	3.00	1.5	25%	40°	GE		40A	1.20	1.50	10	12-12-63	2,511	7-9-64 F
NICD	3.00	3.0	25%	40°	GE		44A	0.48	1.50	10	12-20-63	4,487	9-14-65 F
NICD	5.00	1.5	15%	0°	GE	NB	103A	0.83	1.50	5	4-24-65	37,545	
NICD	5.00	1.5	25%	0°	GE	NBPT	107A	1.38	2.50	5	6-5-65	36,914	
NICD	5.00	1.5	15%	25°	GE	NB	106A	0.90	1.50	5	4-24-65	26,013	12-31-69 F
NICD	5.00	1.5	25%	25°	GE	NBPT	104B	1.50	2.50	5	6-10-65	13,149	11-15-67 F
NICD	5.00	1.5	15%	40°	GE	NB	113A	0.98	1.50	5	4-24-65	4,998	3-15-66 F
NICD	5.00	1.5	25%	40°	GE	NBPT	114A	1.63	2.50	5	6-12-65	8,273	12-19-66 F
NICD	6.00	1.5	25%	0°	GE	AE-13	52C	3.00	3.00	5	6-3-68	9,954	2-25-70 F
NICD	6.00	1.5	25%	0°	GE	AE-14	50B	3.00	3.00	5	5-20-68	20,731	
NICD	6.00	1.5	25%	25°	GE	AE-13	5B	3.00	3.00	5	5-20-68	13,254	11-3-70 D
NICD	6.00	1.5	25%	25°	GE	AE-14	17B	3.00	3.00	5	5-20-68	15,938	2-21-71 F
NICD	6.00	1.5	25%	40°	GE	AE-13	6C	3.00	3.00	5	6-3-68	8,072	11-10-69 F
NICD	6.00	1.5	25%	40°	GE	AE-14	42C	3.00	3.00	5	5-20-68	9,047	1-16-70 D
NICD	6.00	1.5	25%	*	GE	AE-13	62B	3.00	3.00	5	7-3-68	6,284	
NICD	6.00	1.5	25%	*	GE	AE-14	65B	3.00	3.00	5	7-3-68	14,392	1-31-71 D

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED
NICD	6.00	1.5	15%	0°	GE	AE	53B	1.80	1.80	5	7-18-68	9,230	2-23-70 F
NICD	6.00	1.5	15%	25°	GE	AE	28C	1.80	1.80	5	7-18-68	9,987	4-8-70 F
NICD	6.00	1.5	15%	40°	GE	AE	47C	1.80	1.80	5	7-18-68	5,842	7-28-69 F
NICD	6.00	1.5	25%	40°	GE	CHSP	9G	4.80	4.80	5	11-7-68	143	11-21-68 F
NICD	6.00	1.5	25%	40°	GE	PLSP	27C	4.80	4.80	5	11-7-68	559	12-16-68 D
NICD	6.00	1.5	21%	25°	GE	SAS B	1C	3.50	2.50	8	7-22-70	8,110	
NICD	6.00	1.5	25%	20°	EP	AE	2D	1.80	3.00	6	2-15-71	376	3-23-71 D
NICD	6.00	1.5	25%	20°	EP	AE	14E	1.80	3.00	6	2-15-71	997	4-18-71 D
NICD	6.00	1.5	25%	20°	EP	AE	26D	1.80	3.00	6	2-15-71	25	3-07-71 D
NICD	6.00	1.5	25%	20°	EP	AE	22C	1.80	3.00	6	2-16-71	4,509	
NICD	6.00	1.5	25%	20°	EP	AE	25D	1.80	3.00	8	2-17-71	4,511	
NICD	6.00	1.5	25%	20°	EP	AE	31C	1.80	3.00	6	2-17-71	4,484	
NICD	6.00	1.5	25%	20°	EP	AE	38F	1.80	3.00	6	2-17-71	4,474	
NICD	6.00	1.5	25%	20°	EP	AE	46C	1.80	3.00	6	2-17-71	4,454	
NICD	6.00	1.5	25%	20°	EP	AE	49B	1.80	3.00	6	2-17-71	4,514	
NICD	6.00	1.5	25%	-20°	GE		81B	3.00	3.00	5	3-14-71	3,784	
NICD	6.00	1.5	25%	20°	GE		95B	3.00	3.00	5	3-14-71	4,404	
NICD	6.00	1.5	25%	0°	GE		92B	3.00	3.00	5	3-14-71	4,370	
NICD	6.00	1.5	25%	40°	GE		106B	3.00	3.00	5	3-14-71	4,382	
NICD	6.00	24.0	60%	40°	GE		91B	0.30	3.60	5	3-18-71	281	
NICD	6.00	24.0	60%	20°	GE		109B	0.30	3.60	5	3-18-71	279	
NICD	6.00	24.0	60%	0°	GE		123B	0.30	3.60	5	3-18-71	265	
NICD	6.00	24.0	60%	-20°	GE		75E	0.30	3.60	5	3-18-71	272	
NICD	6.00	1.5	40%	40°	GE	RC-AE	6D	4.80	4.80	5	4-25-71	2,268	10-11-71 F
NICD	6.00	1.5	40%	20°	GE	RC-AE	64B	4.80	4.80	5	4-25-71	2,095	
NICD	6.00	1.5	40%	0°	GE	RC-AE	30C	4.80	4.80	5	4-25-71	3,436	

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED
NICD	6.00	1.5	25%	20°	EP	AE	2E	1.65	3.00	5	5-2-71	3,208	
NICD	6.00	1.5	40%	40°	EP	AE	42D	4.80	4.80	5	9-1-71	95	9-13-71 D
NICD	6.00	1.5	40%	20°	EP	AE	65C	4.80	4.80	5	9-1-71	1,662	
NICD	6.00	1.5	40%	0°	EP	AE	53C	4.80	4.80	5	9-1-71	1,652	
NICD	12.00	1.5	15%	0°	GE		110A	2.07	3.60	5	1-4-64	43,508	
NICD	12.00	3.0	15%	0°	GE		111A	0.83	3.60	5	1-4-64	21,993	
NICD	12.00	1.5	25%	0°	GE		124A	3.45	6.00	5	1-4-64	34,343	11-5-69 F
NICD	12.00	3.0	25%	0°	GE		125A	1.38	6.00	5	1-4-64	22,279	
NICD	12.00	1.5	25%	25°	GE		82A	3.75	6.00	5	1-4-64	10,878	12-30-65 F
NICD	12.00	3.0	25%	25°	GE		83A	1.50	6.00	5	1-4-64	13,897	1-24-69 F
NICD	12.00	1.5	40%	25°	GE		96A	6.00	9.60	5	1-4-64	4,020	10-2-64 F
NICD	12.00	3.0	40%	25°	GE		97A	2.40	9.60	5	1-4-64	5,002	11-8-65 F
NICD	12.00	1.5	15%	40°	GE		85A	2.88	3.60	5	1-9-64	9,710	11-8-65 F
NICD	12.00	3.0	15%	40°	GE		86A	1.15	3.60	5	1-4-64	10,661	1-2-68 F
NICD	12.00	1.5	25%	40°	GE		99A	4.80	6.00	5	1-9-64	4,853	1-5-65 F
NICD	12.00	3.0	25%	40°	GE		100A	1.92	6.00	5	1-4-64	4,424	9-24-65 F
NICD	12.00	24.0	50%	25°	GE		93A	0.52	6.00	5	3-28-64	349	4-28-65 D
NICD	12.00	1.5	25%	0°	GE	AE	60A	6.00	6.00	5	10-6-65	5,650	10-20-66 D
NICD	12.00	1.5	25%	25°	GE	AE	12A	6.00	6.00	5	7-20-65	1,698	12-1-65 D
NICD	12.00	1.5	40%	25°	GE	AE	24A	9.60	9.60	5	10-2-65	665	11-19-65 D
NICD	12.00	1.5	40%	0°	GE	AE	48A	9.60	9.60	5	10-12-65	5,110	2-10-67 D
NICD	12.00	1.5	25%	0°	GE	AE	58A	6.00	6.00	5	1-20-67	136	2-10-67 D
NICD	12.00	1.5	40%	0°	GE	AE	72A	6.00	9.60	5	1-20-67	304	2-2-67 D
NICD	12.00	1.5	25%	25°	GE	AE	12B	6.00	6.00	5	1-6-67	404	2-10-67 D
NICD	12.00	1.5	40%	25°	GE	AE	24B	6.00	9.60	5	1-5-67	38	2-10-67 D
NICD	12.00	1.5	25%	40°	GE	AE	36A	6.00	6.00	5	1-27-67	75	2-3-67 D

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED	
NICD	12.00	1.5	40%	40°	GE	AE	34A	6.00	9.60	5	1-27-67	65	2-3-67	D
NICD	20.00	1.5	15%	0°	GE	AE	7B	8.00	6.00	5	2-27-70	10,439		
NICD	20.00	1.5	15%	0°	GE	AE	67B	8.00	6.00	5	2-27-70	10,412		
NICD	3.50	1.5	15%	0°	GOULD		51A	0.60	1.05	10	12-5-63	22,364	2-15-68	D
NICD	3.50	3.0	15%	0°	GOULD		55A	0.24	1.05	10	12-20-63	11,546	2-15-68	D
NICD	3.50	1.5	25%	0°	GOULD		52A	1.00	1.75	10	12-5-63	13,730	6-11-66	F
NICD	3.50	3.0	25%	0°	GOULD		56A	0.40	1.75	10	12-20-63	11,897	2-15-68	D
NICD	3.50	1.5	25%	25°	GOULD		3A	1.09	1.75	10	12-6-63	4,751	10-31-64	F
NICD	3.50	3.0	25%	25°	GOULD		7A	0.44	1.75	10	12-20-63	4,173	7-26-65	F
NICD	3.50	1.5	40%	25°	GOULD		4A	1.75	2.80	10	12-5-63	3,164	7-9-64	F
NICD	3.50	3.0	40%	25°	GOULD		8A	0.70	2.80	10	12-20-63	2,494	11-29-64	F
NICD	3.50	1.5	15%	40°	GOULD		27A	0.84	1.05	10	12-12-63	4,485	11-6-64	F
NICD	3.50	3.0	15%	40°	GOULD		31A	0.34	1.05	10	12-20-63	2,517	1-3-65	F
NICD	3.50	1.5	25%	40°	GOULD		28A	1.40	1.75	10	12-12-63	1,811	5-29-64	F
NICD	3.50	3.0	25%	40°	GOULD		32A	0.56	1.75	10	12-20-63	975	6-10-64	F
NICD	20.00	1.5	15%	0°	GOULD		84A	3.45	6.00	5	1-16-64	22,448	2-13-68	D
NICD	20.00	3.0	15%	0°	GOULD		80A	1.38	6.00	5	1-21-64	11,378	2-13-68	D
NICD	20.00	1.5	25%	0°	GOULD		98A	5.75	10.00	5	1-21-64	10,641	1-14-66	F
NICD	20.00	3.0	25%	0°	GOULD		94A	2.30	10.00	5	1-24-64	11,162	2-13-68	D
NICD	20.00	1.5	25%	25°	GOULD		104A	6.25	10.00	5	1-16-64	2,980	8-20-64	F
NICD	20.00	3.0	25%	25°	GOULD		105A	2.50	10.00	5	1-21-64	5,690	3-17-66	F
NICD	20.00	1.5	40%	25°	GOULD		118A	10.00	16.00	5	2-1-64	2,937	9-7-64	F
NICD	20.00	3.0	40%	25°	GOULD		119A	4.00	16.00	5	2-1-64	1,793	9-27-64	F
NICD	20.00	1.5	15%	40°	GOULD		112A	4.80	6.00	5	1-16-64	5,213	2-15-65	F
NICD	20.00	3.0	15%	40°	GOULD		108A	1.92	6.00	5	1-24-64	4,237	8-31-65	F

QEEL/C 72-1

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED
NICD	20.00	1.5	25%	40°	GOULD		126A	8.00	10.00	5	1-16-64	1,574	5-23-64 F
NICD	20.00	3.0	25%	40°	GOULD		122A	3.20	10.00	5	1-24-64	983	7-2-64 F
NICD	1.25	1.5	25%	-20°	GULTON		74B	1.00	0.63	5	3-3-66	31,227	
NICD	1.25	1.5	60%	-20°	GULTON		88D	1.00	0.63	5	3-3-66	30,449	
NICD	1.25	1.5	25%	0°	GULTON		108B	1.25	0.63	5	3-4-66	31,313	
NICD	1.25	1.5	60%	0°	GULTON		98B	1.25	1.50	5	3-4-66	12,247	5-28-68 F
NICD	3.50	1.5	25%	-20°	GULTON	PS	89C	0.96	1.75	5	12-24-66	23,832	3-13-71 F
NICD	3.50	1.5	40%	-20°	GULTON	PS	75D	1.54	2.80	5	12-24-66	14,197	9-28-69 F
NICD	3.50	1.5	25%	0°	GULTON	PS	122C	1.01	1.75	5	12-24-66	35,234	
NICD	3.50	1.5	40%	0°	GULTON	PS	99C	1.61	2.80	5	12-24-66	28,172	
NICD	3.50	1.5	25%	25°	GULTON	PS	87C	1.09	1.75	5	12-23-66	20,866	9-2-70 F
NICD	3.50	1.5	25%	40°	GULTON	PS	112C	1.40	1.75	5	1-2-67	11,155	1-3-69 F
NICD	3.50	1.5	40%	25°	GULTON	PS	73C	1.75	2.80	5	12-23-66	9,978	10-28-68 F
NICD	3.60	1.5	40%	25°	GULTON	CLM	39B	3.60	2.88	10	11-11-65	5,399	12-6-66 F
NICD	4.00	1.5	15%	0°	GULTON	CC	115B	0.69	1.20	5	7-25-64	39,890	
NICD	4.00	1.5	25%	0°	GULTON	CC	126B	1.15	2.00	5	7-25-64	41,813	
NICD	4.00	1.5	25%	25°	GULTON	CC	4B	1.25	2.00	5	8-4-64	35,111	10-13-70 F
NICD	4.00	1.5	40%	25°	GULTON	CC	14B	2.00	3.20	5	8-4-64	8,474	3-19-66 F
NICD	4.00	1.5	15%	40°	GULTON	CC	28B	0.96	1.20	5	8-4-64	20,227	7-6-68 F
NICD	4.00	1.5	25%	40°	GULTON	CC	40B	1.60	2.00	5	8-4-64	10,360	6-22-66 F
NICD	4.00	1.5	25%	-20°	GULTON	CLM	40C	2.00	2.00	5	3-4-67	2	3-4-67 F
NICD	4.00	1.5	25%	0°	GULTON	CLM	52B	2.00	2.00	5	3-3-67	5,685	3-5-68 F
NICD	4.00	1.5	15%	25°	GULTON	CLM	26C	1.20	1.20	5	2-18-67	11,455	2-28-69 F
NICD	4.00	1.5	25%	25°	GULTON	CLM	14C	2.00	2.00	5	3-3-67	2,428	8-8-67 F
NICD	4.00	1.5	40%	25°	GULTON	CLM	37C	4.80	4.80	5	3-4-67	790	5-5-67 F
NICD	4.00	1.5	60%	25°	GULTON	CLM	38D	3.20	3.20	5	2-18-67	1,927	6-25-67 F

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED	
NICD	4.00	1.5	25%	40°	GULTON	CLM	39C	2.00	2.00	5	3-3-67	1,508	6-20-67	F
NICD	5.00	1.5	15%	0°	GULTON	NB	117A	0.83	1.50	5	5-8-65	37,125		
NICD	5.00	1.5	25%	0°	GULTON	NBPT	121A	1.38	2.50	5	6-5-65	20,861	3-5-69	F
NICD	5.00	1.5	15%	25°	GULTON	NB	120A	0.90	1.50	5	5-2-65	29,753	11-03-70	F
NICD	5.00	1.5	25%	25°	GULTON	NBPT	118B	1.50	2.50	5	6-10-65	8,108	11-22-66	F
NICD	5.00	1.5	15%	40°	GULTON	NB	127A	0.98	1.50	5	4-29-65	10,638	5-24-67	F
NICD	5.00	1.5	25%	40°	GULTON	NBPT	128A	1.63	2.50	5	6-21-65	6,345	8-18-66	F
NICD	5.00	1.5	25%	0°	GULTON	CO-NI	21E	1.40	2.50	10	9-2-70	7,392		
NICD	5.00	1.5	25%	25°	GULTON	CO-NI	45E	1.40	2.50	10	9-2-70	7,449		
NICD	5.00	1.5	40%	25°	GULTON	CO-NI	69C	2.20	4.00	10	9-2-70	7,448		
NICD	5.00	1.5	25%	40°	GULTON	CO-NI	9H	1.40	2.50	10	9-2-70	7,449		
NICD	5.00	1.5	40%	40°	GULTON	CO-NI	33D	2.20	4.00	10	9-2-70	4,523	6-18-71	D
NICD	5.60	1.5	25%	-20°	GULTON	FRS	44B	1.61	2.80	5	1-2-66	31,907	8-30-71	F
NICD	5.60	1.5	25%	-20°	GULTON	RS	32B	1.61	2.80	5	1-2-66	23,303	3-4-70	F
NICD	5.60	1.5	25%	0°	GULTON	FRS	100B	1.61	2.80	5	12-17-65	28,758	2-5-71	F
NICD	5.60	1.5	25%	0°	GULTON	RS	90C	1.61	2.80	5	12-17-65	31,623	7-20-71	F
NICD	5.60	1.5	25%	25°	GULTON	FRS	76B	1.75	2.80	5	12-10-65	11,158	1-2-68	F
NICD	5.60	1.5	25%	25°	GULTON	RS	96C	1.75	2.80	5	12-10-65	9,791	9-19-67	F
NICD	5.60	1.5	25%	40°	GULTON	FRS	42B	2.24	2.80	5	12-3-65	3,798	9-10-66	F
NICD	5.60	1.5	25%	40°	GULTON	RS	30B	2.24	2.80	5	12-3-65	1,275	3-8-66	F
NICD	6.00	1.5	15%	0°	GULTON		61A	1.04	1.80	10	12-31-63	10,146	12-17-65	F
NICD	6.00	3.0	15%	0°	GULTON		65A	0.41	1.80	10	12-31-63	11,208	2-15-68	D
NICD	6.00	1.5	25%	0°	GULTON		62A	1.72	3.00	10	12-30-63	22,779	2-15-68	D
NICD	6.00	3.0	25%	0°	GULTON		66A	0.69	3.00	10	12-31-63	4,414	8-31-65	F
NICD	6.00	1.5	25%	25°	GULTON		13A	1.88	3.00	10	12-31-63	4,021	11-11-64	F
NICD	6.00	3.0	25%	25°	GULTON		17A	0.75	3.00	10	12-20-63	2,885	1-31-65	F

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED	
NICD	6.00	1.5	25%	25°	GULTON		14A	3.00	4.80	10	12-30-63	2,086	6-19-64	F
NICD	6.00	3.0	40%	25°	GULTON		18A	1.20	4.80	10	12-31-63	1,500	8-18-64	F
NICD	6.00	1.5	15%	40°	GULTON		37A	1.44	1.80	10	12-31-63	6,064	4-14-65	F
NICD	6.00	3.0	15%	40°	GULTON		41A	0.58	1.80	10	12-31-63	1,689	9-14-64	F
NICD	6.00	1.5	25%	40°	GULTON		38A	2.40	3.00	10	12-30-63	1,377	5-22-64	F
NICD	6.00	3.0	25%	40°	GULTON		42A	0.96	3.00	10	12-31-63	4,133	8-23-65	F
NICD	6.00	24.0	50%	25°	GULTON		79A	0.20	3.00	5	3-28-64	545	10-13-65	F
NICD	6.00	1.5	25%	0°	GULTON	IM	13B	1.73	3.00	5	2-22-65	37,650	10-27-71	F
NICD	6.00	1.5	40%	25°	GULTON	IM	18B	3.00	4.80	5	2-22-65	7,577	7-21-66	F
NICD	6.00	1.5	25%	40°	GULTON	IM	38B	2.40	3.00	5	2-22-65	5,766	3-31-66	F
NICD	6.00	1.5	10%	0°	GULTON		61B	0.66	1.20	10	6-7-67	24,890		
NICD	6.00	1.5	25%	0°	GULTON	AE	59A	3.00	3.00	5	4-15-65	14,863	2-28-68	F
NICD	6.00	1.5	40%	0°	GULTON	AE	71A	4.80	4.80	5	4-15-65	5,753	5-18-66	F
NICD	6.00	1.5	25%	25°	GULTON	AE	23A	3.00	3.00	5	2-5-65	15,713	1-24-68	F
NICD	6.00	1.5	40%	25°	GULTON	AE	11A	4.80	4.80	5	2-5-65	7,743	7-9-66	F
NICD	6.00	1.5	15%	40°	GULTON	AE	35A	1.80	1.80	5	6-28-65	12,511	11-30-67	F
NICD	6.00	1.5	25%	40°	GULTON	AE	47A	3.00	3.00	5	5-16-65	5,502	5-11-66	F
NICD	6.00	1.5	15%	*	GULTON	AE	60B	1.80	1.80	5	4-25-67	26,763		
NICD	6.00	1.5	25%	*	GULTON	AE	24C	3.00	3.00	5	4-25-67	17,328	5-24-70	F
NICD	6.00	1.5	40%	*	GULTON	AE	48B	4.80	4.80	5	4-25-67	6,156	6-27-68	F
NICD	6.00	3.0	25%	-20°	GULTON	CLM	41B	3.00	3.00	5	11-18-66	12,389		
NICD	6.00	3.0	25%	0°	GULTON	CLM	66B	3.00	3.00	5	11-18-66	11,602		
NICD	6.00	3.0	25%	25°	GULTON	CLM	18C	3.00	3.00	5	11-18-66	9,633	6-3-70	F
NICD	6.00	3.0	25%	40°	GULTON	CLM	29B	3.00	3.00	5	11-18-66	7,941	9-17-69	F
NICD	6.00	1.5	15%	*	GULTON	AE	36D	1.80	1.80	5	1-8-69	16,332		
NICD	6.00	1.5	25%	*	GULTON	AE	58D	3.00	3.00	5	1-8-69	16,318		

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED
NICD	6.00	1.5	0.8%	20°	GULTON	TETR	51B	0.30	0.10	10	2-26-69	15,846	
NICD	6.0	1.5	50%	-20°	GULTON	CLM	39D	6.00	6.00	5	9-21-70	1,376	5-10-71 F
NICD	6.0	1.5	50%	0°	GULTON	CLM	63B	6.00	6.00	5	9-21-70	6,868	
NICD	6.0	1.5	50%	20°	GULTON	CLM	3C	6.00	6.00	5	9-21-70	7,001	
NICD	6.0	1.5	50%	40°	GULTON	CLM	27D	6.00	6.00	5	9-21-70	6,808	11-6-71 F
NICD	6.0	1.5	21%	25°	GULTON	SAS A	18D	3.50	2.50	8	7-22-70	8,110	
NICD	6.0	1.5	25%	20°	GULTON	AE	28D	3.00	3.00	5	6-9-70	8,610	
NICD	6.0	1.5	25%	20°	GULTON	AE	40D	3.00	3.00	5	6-9-70	8,653	
NICD	6.0	1.5	25%	20°	GULTON	AE	52D	3.00	3.00	5	6-9-70	8,253	
NICD	10.00	1.5	25%	0°	GULTON	AE	20B	5.00	5.00	5	1-15-69	2	1-15-69 F
NICD	10.00	1.5	25%	25°	GULTON	AE	8B	5.00	5.00	5	11-27-67	2,414	5-6-68 F
NICD	10.00	1.5	25%	40°	GULTON	AE	6B	5.00	5.00	5	11-27-67	602	3-14-68 F
NICD	12.00	1.5	15%	0°	GULTON		16B	2.07	3.60	5	2-20-65	38,461	
NICD	12.00	1.5	25%	0°	GULTON		101B	3.45	6.00	5	12-19-64	38,110	10-5-71 F
NICD	12.00	1.5	25%	25°	GULTON		27B	3.75	6.00	5	1-28-65	14,250	9-5-67 F
NICD	12.00	1.5	40%	25°	GULTON		96B	6.00	9.60	5	12-2-64	5,152	11-9-65 F
NICD	12.00	1.5	15%	40°	GULTON		78A	2.88	3.60	5	12-22-64	11,081	1-4-66 F
NICD	12.00	1.5	25%	40°	GULTON		90B	8.00	10.00	5	12-5-64	5,124	11-10-65 F
NICD	12.00	1.5	25%	0°	GULTON	AE	70A	6.00	6.00	5	2-10-67	27,399	
NICD	12.00	1.5	40%	0°	GULTON	AE	71B	6.00	9.60	5	1-6-67	15,275	10-6-69 F
NICD	12.00	1.5	40%	25°	GULTON	AE	11B	6.00	9.60	5	10-17-66	11,933	12-31-68 F
NICD	12.00	1.5	25%	40°	GULTON	AE	47B	6.00	6.00	5	1-5-67	6,537	6-19-68 F
NICD	20.00	1.5	15%	0°	GULTON		101A	3.45	6.00	5	1-16-64	3,629	9-20-64 F
NICD	20.00	3.0	15%	0°	GULTON		102A	1.38	6.00	5	1-21-64	11,212	2-13-68 D
NICD	20.00	1.5	15%	10°	GULTON		23B	8.00	6.00	10	2-4-71	4,919	
NICD	20.00	1.5	15%	10°	GULTON	AE-PT	35B	8.00	6.00	5	2-4-71	4,938	

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED
NICD	20.00	1.5	25%	0°	GULTON		115A	5.75	10.00	5	1-16-64	2,291	6-24-64 F
NICD	20.00	3.0	25%	0°	GULTON		116A	2.30	10.00	5	2-11-64	10,971	2-13-68 D
NICD	20.00	1.5	25%	25°	GULTON		73A	6.25	10.00	5	1-16-64	7,763	6-30-65 F
NICD	20.00	3.0	25%	25°	GULTON		74A	2.50	10.00	5	1-21-64	1,754	9-27-64 F
NICD	20.00	1.5	40%	25°	GULTON		87A	10.00	16.00	5	2-1-64	627	4-7-64 F
NICD	20.00	3.0	40%	25°	GULTON		88A	4.00	16.00	5	2-1-64	358	3-21-64 F
NICD	20.00	1.5	15%	40°	GULTON		76A	4.80	6.00	5	1-18-64	9,348	10-15-65 F
NICD	20.00	3.0	15%	40°	GULTON		77A	1.92	6.00	5	1-21-64	6,032	4-20-66 F
NICD	20.00	1.5	25%	40°	GULTON		90A	8.00	10.00	5	1-18-64	4,045	11-12-64 F
NICD	20.00	3.0	25%	40°	GULTON		91A	3.20	10.00	5	1-24-64	4,480	10-14-65 F
NICD	20.00	1.5	15%	0°	GULTON	AE	58B	5.00	6.00	5	4-8-67	4,026	1-25-68 U
NICD	20.00	1.5	15%	25°	GULTON	AE	12C	5.00	6.00	5	3-9-67	4,934	1-25-68 U
NICD	20.00	1.5	15%	40°	GULTON	AE	36B	5.00	6.00	5	3-11-67	2,740	9-5-67 U
NICD	20.00	1.5	15%	*	GULTON	MULTI	12D	10.00	6.00	5	2-8-68	7,262	5-13-69 U
NICD	20.00	1.5	25%	*	GULTON	MULTI	36C	10.00	10.00	5	2-8-68	966	8-14-68 F
NICD	20.00	1.5	40%	*	GULTON	MULTI	58C	10.00	16.00	5	2-8-68	131	3-2-68 F
NICD	20.00	1.5	15%	0°	GULTON	AE	54B	8.00	6.00	5	3-23-68	21,611	
NICD	20.00	1.5	15%	25°	GULTON	AE	19B	8.00	6.00	5	3-23-68	21,649	
NICD	20.00	1.5	15%	40°	GULTON	AE	38E	8.00	6.00	5	3-23-68	4,943	2-12-69 D
NICD	20.00	1.5	25%	*	GULTON	MULTI	48C	10.00	10.00	6	5-26-69	1,948	3-24-70 F
NICD	20.00	1.5	25%	20°	GULTON	MULTI*	48D	10.00	10.00	6	7-9-70	7,835	
NICD	20.00	1.5	15%	20°	GULTON	MULTI*	12E	8.00	6.00	5	5-13-70	9,119	
NICD	20.00	1.5	15%	0°	GULTON	MULTI*	68B	8.00	6.00	5 ⁰	10-18-70	6,736	
NICD	50.00	1.5	25%	0°	GULTON		95A	14.38	25.00	5	6-8-64	3,227	2-9-65 F
NICD	50.00	1.5	15%	40°	GULTON		123A	12.00	15.00	5	6-8-64	1,873	11-11-64 F

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED
NICD	3.90	1.5	25%	0°	NIFE		97C	1.07	2.00	5	9-29-67	20,009	4-6-71 F
NICD	3.90	1.5	25%	25°	NIFE		85C	1.07	2.00	5	9-29-67	9,356	6-19-69 F
NICD	3.00	1.5	15%	0°	SONOTONE	3S	43B	0.52	0.90	5	6-24-65	36,011	
NICD	3.00	1.5	25%	0°	SONOTONE	3S	31B	0.86	1.50	5	6-24-65	28,074	8-10-70 F
NICD	3.00	1.5	25%	25°	SONOTONE	3S	3B	0.94	1.50	5	6-25-65	11,726	8-23-67 F
NICD	3.00	1.5	40%	25°	SONOTONE	3S	2B	1.50	2.40	5	7-10-65	5,399	7-26-66 F
NICD	3.00	1.5	15%	40°	SONOTONE	3S	26B	0.72	0.90	5	7-10-65	6,289	10-4-66 F
NICD	3.00	1.5	25%	40°	SONOTONE	3S	37B	1.20	1.50	5	7-10-65	5,625	8-4-66 F
NICD	3.50	1.5	10%	0°	SONOTONE		15B	0.39	0.70	10	6-7-67	23,707	
NICD	5.00	1.5	15%	0°	SONOTONE		49A	0.86	1.50	10	12-31-63	23,112	2-15-68 D
NICD	5.00	3.0	15%	0°	SONOTONE		53A	0.35	1.50	10	12-31-63	11,427	2-13-68 D
NICD	5.00	1.5	25%	0°	SONOTONE		50A	1.44	2.50	10	12-17-63	22,525	2-15-68 D
NICD	5.00	3.0	25%	0°	SONOTONE		54A	0.58	2.50	10	12-31-63	11,331	2-7-68 D
NICD	5.00	1.5	25%	25°	SONOTONE		1A	1.56	2.50	10	12-17-63	11,745	2-27-66 F
NICD	5.00	3.0	25%	25°	SONOTONE		5A	0.62	2.50	10	12-31-63	11,092	2-12-68 D
NICD	5.00	1.5	40%	25°	SONOTONE		2A	2.50	4.00	10	12-17-63	6,671	4-24-65 F
NICD	5.00	3.0	40%	25°	SONOTONE		6A	1.00	4.00	10	1-2-64	5,211	12-13-65 F
NICD	5.00	1.5	15%	40°	SONOTONE		25A	1.20	1.50	10	12-17-63	9,328	10-31-65 F
NICD	5.00	3.0	15%	40°	SONOTONE		29A	0.48	1.50	10	12-31-63	5,975	4-17-66 F
NICD	5.00	1.5	25%	40°	SONOTONE		26A	2.00	2.50	10	12-17-63	3,625	10-15-64 F
NICD	5.00	3.0	25%	40°	SONOTONE		30A	0.80	2.50	10	12-31-63	4,141	8-7-65 F
NICD	5.00	1.5	25%	-20°	SONOTONE	ST	75C	5.00	2.50	5	10-24-65	2,145	4-5-66 F
NICD	5.00	1.5	40%	-20°	SONOTONE	ST	89B	5.00	4.00	5	10-24-65	1,530	2-26-66 F
NICD	5.00	1.5	25%	0°	SONOTONE	ST	92A	5.00	2.50	5	9-5-65	8,774	5-10-67 F
NICD	5.00	1.5	40%	0°	SONOTONE	ST	122B	5.00	4.00	5	9-5-65	5,190	9-24-66 F
NICD	5.00	1.5	25%	25°	SONOTONE	ST	73B	5.00	2.50	5	8-12-65	3,742	4-15-66 F

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED	
NICD	5.00	1.5	40%	25°	SONOTONE	ST	87B	5.00	4.00	5	8-12-65	2,392	1-27-66	F
NICD	5.00	1.5	25%	40°	SONOTONE	ST	99B	5.00	2.50	5	8-23-65	4,388	7-9-66	F
NICD	5.00	1.5	15%	40°	SONOTONE	ST	112B	5.00	1.50	5	8-23-65	3,294	4-1-66	F
NICD	5.00	1.5	25%	25°	SONOTONE	AE	14D	2.50	1.47	5	11-7-67	1,179	2-7-68	F
NICD	20.00	1.5	25%	25°	SONOTONE	IPD	22A	20.00	10.00	10	9-20-67	6,664	10-7-69	D
NICD	20.00	1.5	25%	25°	SONOTONE	IPD	10A	7.00	10.00	10	9-20-67	7,188	10-7-69	D
NICD	20.00	1.5	40%	25°	SONOTONE	IPD	34B	20.00	16.00	10	9-20-67	5,634	7-3-69	F
NICD	20.00	3.0	40%	25°	SONOTONE	IPD	46A	20.00	16.00	10	9-20-67	3,501	10-7-69	D
NICD	20.00	1.5	75%	25°	SONOTONE	IPD	72B	20.00	30.00	10	9-20-67	1,143	4-5-69	F
NICD	20.00	1.5	25%	20°	SONOTONE	IPD*	10B	7.00	10.00	10	5-13-70	9,018		
NICD	20.00	1.5	25%	20°	SONOTONE	IPD*	22B	15.00	10.00	10	5-13-70	3,419	11-23-70	D
NICD	20.00	1.5	40%	20°	SONOTONE	IPD*	34C	15.00	16.00	10	5-13-70	8,357	11-2-71	F
NICD	20.00	3.0	40%	20°	SONOTONE	IPD*	46B	15.00	16.00	10	5-13-70	686	11-23-70	D
NICD	20.00	1.5	75%	20°	SONOTONE	IPD*	72C	20.00	30.00	10	5-13-70	4,381	2-22-71	F
AGCD	7.00	8.0	30%	20°	ELECTROMITE		104C	0.40	2.10	3	12-23-70	1,068		
AGCD	8.00	8.0	25%	25°	ESB	AE	1B	0.50	2.00	5	9-9-66	3,875	6-8-70	F
AGCD	3.00	1.5	16%	25°	YARDNEY		2C	1.30	1.00	9	9-16-66	7,039	12-12-67	F
AGCD	5.00	24.0	20%	0°	YARDNEY	C3SP	57B	0.30	1.00	5	9-17-65	267	6-17-66	F
AGCD	5.00	24.0	20%	25°	YARDNEY	C3SP	21A	0.30	1.00	5	9-17-65	98	12-25-65	F
AGCD	5.00	24.0	20%	40°	YARDNEY	C3SP	45A	0.30	1.00	5	9-27-65	61	11-16-65	F
AGCD	5.00	24.0	20%	25°	YARDNEY	RCSP	9C	0.30	1.00	10	10-27-65	34	12-1-65	D
AGCD	5.00	24.0	20%	25°	YARDNEY	CPSP	33B	0.30	1.00	5	10-17-65	720	11-4-67	F
AGCD	5.00	24.0	20%	25°	YARDNEY	PLSP	69A	0.30	1.00	5	10-27-65	595	7-17-67	F
AGCD	5.00	24.0	20%	0°	YARDNEY		113B	0.30	1.00	5	1-22-67	2,542	2-19-71	F
AGCD	5.00	24.0	20%	25°	YARDNEY		77B	0.30	1.00	5	1-12-67	661	11-12-68	F
AGCD	5.00	24.0	20%	25°	YARDNEY		105B	0.30	1.00	5	1-12-67	77	4-19-67	F

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED	
AGCD	5.00	24.0	20%	40°	YARDNEY		128B	0.30	1.00	5	1-19-67	269	11-4-67	F
AGCD	5.00	8.0	20%	0°	YARDNEY	PLCPSP	114B	0.30	1.00	5	1-22-67	1,496	6-25-68	F
AGCD	5.00	8.0	20%	25°	YARDNEY	PLCPSP	118C	0.30	1.00	5	1-17-67	1,505	7-9-68	F
AGCD	10.00	8.0	30%	25°	YARDNEY		45D	0.50	3.00	5	5-3-67	1,759	11-19-68	F
AGCD	11.00	24.0	40%	0°	YARDNEY		45B	0.30	4.40	10	11-5-66	121	3-13-67	F
AGCD	11.00	24.0	40%	25°	YARDNEY		21B	0.30	4.40	10	11-5-66	69	1-13-67	F
AGCD	11.00	8.0	27%	25°	YARDNEY	PLSP	21C	0.50	3.00	5	3-28-67	37	4-9-67	F
AGCD	11.00	8.0	27%	25°	YARDNEY	WNSP	45C	0.50	3.00	5	3-28-67	70	4-22-67	F
AGCD	11.00	24.0	18%	0°	YARDNEY	AE-GU	57D	0.25	2.00	5	2-14-68	1,365		
AGCD	11.00	24.0	18%	25°	YARDNEY	AE-GU	69B	0.25	2.00	5	2-14-68	507	7-13-69	F
AGCD	11.00	24.0	18%	40°	YARDNEY	AE-GU	33C	0.25	2.00	5	2-14-68	447	5-15-69	F
AGCD	12.00	24.0	50%	0°	YARDNEY		57A	0.60	6.00	10	2-14-64	168	9-3-64	F
AGCD	12.00	24.0	50%	40°	YARDNEY		33A	0.60	6.00	10	2-14-64	210	9-20-64	F
AGCD	12.00	1.5	25%	-20°	YARDNEY		85B	3.90	6.00	5	1-19-66	2,375	3-25-67	F
AGCD	12.00	1.5	25%	0°	YARDNEY		97B	3.90	6.00	5	1-19-66	4,481	3-15-67	F
AGCD	12.00	1.5	25%	25°	YARDNEY		82B	3.90	6.00	5	1-17-66	4,559	11-27-66	F
AGCD	12.00	24.0	43%	0°	YARDNEY	AE-GE	21D	0.50	5.20	5	6-16-67	60	8-13-67	F
AGCD	12.00	24.0	43%	40°	YARDNEY	AE-GE	9F	0.50	5.20	5	6-16-67	310	5-28-68	F
AGZN	5.00	1.5	25%	20°	ASTRO		25B	1.60	2.50	10	12-4-69	681	2-1-70	F
AGZN	5.00	12.0	25%	20°	ASTRO		25C	0.35	2.50	10	2-8-70	567	11-27-70	F
AGZN	5.00	12.0	25%	40°	ASTRO		37D	0.35	2.50	10	2-8-70	391	9-4-70	F
AGZN	5.00	1.5	25%	40°	ASTRO		47D	1.60	2.50	10	12-4-69	2,013	4-19-70	F
AGZN	40.00	4.0	20%	20°	ASTRO		20C	3.00	5.00	10	10-25-71	307		
AGZN	40.0	4.0	20%	20°	ASTRO		33E	3.00	5.00	10	10-25-71	307		
AGZN	25.00	24.0	40%	25°	DELCO-REMY		89A	15.00	10.00	5	9-18-64	80	12-8-64	D
AGZN	25.00	24.0	40%	25°	DELCO-REMY		75A	15.00	10.00	5	8-18-64	32	9-18-64	F

QEEL/C 72-1

TYPE	AMPERE- HOUR	ORBIT PERIOD	DEPTH OF DISCHARGE	TEMP (°C)	MANUFACTURER	SPECIAL SYMBOL	PACK NO.	CHARGE CURRENT	DISCHARGE CURRENT	NO. CELLS IN PACK	DATE STARTED	CYCLES COMPLETED	DATE COMPLETED	
AGZN	25.00	3.0	40%	25°	DELCO-REMY		88B	15.00	20.00	5	3-1-65	120	3-16-65	D
AGZN	25.00	3.0	40%	25°	DELCO-REMY		88C	15.00	20.00	5	3-26-65	325	5-6-65	D
AGZN	25.00	24.0	40%	25°	DELCO-REMY		9D	1.00	10.00	10	12-13-65	121	4-18-66	D
AGZN	25.00	24.0	40%	25°	DELCO-REMY	2SR	9E	1.00	10.00	10	10-5-66	90	1-4-67	D
AGZN	40.00	24.0	25%	25°	DELCO-REMY		75B	25.00	10.00	5	10-28-64	139	3-15-65	D
AGZN	12.00	24.0	42%	25°	YARDNEY		9A	0.50	5.00	10	5-7-65	58	7-7-65	D
AGZN	16.00	24.0	31%	25°	YARDNEY	2SR	57C	0.50	5.00	10	12-2-66	281	8-30-67	D

INTRODUCTION

Considerable research is being done to find more efficient and reliable means of storing electrical energy for orbiting satellites. Rechargeable cells offer one such means. The test program at NAD Crane has been established in order to further the evaluation of certain types of cells and to obtain performance and failure data as an aid to their continued improvement.

This eighth annual report covers the cycle life test, the third phase of the evaluation program of secondary spacecraft cells, through 14 December 1971. The purpose of the cycle program is to determine the cycling performance capabilities of packs of cells under different load and temperature conditions. The acceptance tests and general performance tests, the first and second phases of the evaluation program, were reported earlier.

A summary of the results of the life cycling program is given in this report. Complete data and graphs are available upon application via NASA Technical Officer. The application will include information on exactly what data is required; the use to which the data will be put; application details including orbital description, charge control methods, load requirements, etc., as appropriate; name and address of the activity that stands to benefit; name and telephone number of the responsible individual concerned; and the affiliation with any Government agency as contractual arrangement.

During December 1963, this activity began the cycle test on 660 sealed, nickel-cadmium cells purchased by NASA. The cells were from four manufacturers, and consisted of seven sample classifications ranging from 3.0 to 20 ampere-hours. Since then 1054 nickel-cadmium, 178 silver-cadmium and 125 silver-zinc sealed cells from several manufacturers have been added to the program. The capacities of the nickel-cadmium cells ranged from 1.25 to 50 ampere hours; that of the silver-cadmium ranged from 3.0 to 12.0 ampere-hours; and that of the silver-zinc cells ranged from 5 to 40.0 ampere-hours. These cells are cycled under different load, charge control and temperature conditions. The load conditions include cycle length (orbit periods) of 1.5, 3.0, 8.0, 12, and 24 hours; and depths of discharge ranging from 10 to 75 percent. Unless otherwise specified, all cell packs are recharged by using a pack voltage limit as given in the pack's test program. All charging is constant current until the voltage limit is reached; at this time the charge current is automatically reduced to protect the cells during overcharge. The charge current is determined by the theoretical percent of recharge returned to the cells following each constant current discharge.

The time at which voltage limiting occurs varies slightly with cycling. Thus the percent of recharge is not constant from cycle to cycle as illustrated in graphs accompanying such voltage limited packs. Other charge control methods used are auxiliary electrode, coulometer, stabistor, two-step regulator, thermistor controlled voltage limit, and Sherfey upside-down cycling regime. Specially constructed cells to apply internal pressure against the face of the plate stack, and a type to permit high charge rates were also tested. Environmental conditions include ambient temperatures of -20° , 0° , 20° , 25° , 40° , 50° C; and a sinusoidal cycling temperature of 0° to 40° C within a period of 48 hours.

The ampere-hour capacity of each pack, at its specified test temperature, is measured initially and every 88 days of continuous cycling unless otherwise specified. Each pack being checked is discharged immediately after the end of the regular cycle charge period, at the c/2 rate (c being the manufacturer's rated capacity) to a cutoff of 1.0 volt per cell average, or to a low of 0.5 volt on any one cell, or a combination of the two. The pack is then recharged at the c/10 rate for 16 hours and then discharged again as above. Before being returned to regular cycling, the pack is given a 16-hour charge (48-hour prior to 14 December 1969) at the c/10 rate, with the regular on-charge cycling voltage limit. The summary of the capacity check results will list only the amount obtained on the second discharge (Disch #2) unless otherwise noted. All other capacity checks not noted this way receive only one discharge which is run at the cycle rate to 1.0 volt per cell or 0.5 volt on any one cell, or a combination of the two, and then recharged at the regular cycle rate prior to being returned to automatic cycling. By direction of Goddard Space Flight Center capacities to 1.20 and 1.10 volts per cell average have been interpolated from existing data. This has been done for five packs (24C, 48B, 60B, 78A and 101B; see Figures 1 and 2). The first three packs (Figure 1) were 6.0 ampere-hour nickel-cadmium cells in a temperature cycling regime. The other cells were 12 ampere-hour nickel-cadmium cells operating at 40° and 0° C respectively. All these cells were manufactured by Gulton. (See report brief, pages vii through xviii for further information on parameters.)

A cell is considered a failure when its terminal voltage drops below 0.5 volt at any time during a regular discharge-charge cycle. It is removed from the pack upon completion of a recorded cycle unless otherwise specified. The cells remaining in the pack continue test until 60 percent of the cells have failed constituting a pack failure. By direction of Goddard Space Flight Center cell failure analysis is performed at NAD Crane. The manufacturer is invited to participate as an observer in the analysis of his cells.

In order to clarify the discussion that follows, all failure terms are defined according to their use in this report. These are our definitions, and they may differ somewhat from usage elsewhere.

Data is recorded by the Tally Data Collection System and consists of individual cell voltage, individual cell temperature, total voltage, current, and ambient temperature. Also when appropriate, data is collected on auxiliary electrode voltage, gas recombination electrode voltage, coulometer voltage, and pressure transducer voltage. It is then converted to absolute values and stored on magnetic tape for data analysis and future reference. As of 3 May 1970, a new data collection format went into effect. An outline of this format is as follows:

FREQUENCY OF RECORDINGS DURING CYCLE LIFE

Discharge/Charge Cycles		Frequency of Recordings	Number of Recordings	
<u>1.5-Hour</u>	<u>3.0-Hour</u>		<u>1.5-Hour</u>	<u>3.0-Hour</u>
1-16	1-8	2-minute readings each cycle for 1 day	16	8
17-976	9-488	2-minute readings one cycle every second day	30	30
977-2384	489-1192	2-minute readings one cycle every fourth day	22	22
<u>8.0-Hour</u>		<u>Recordings*</u>	<u>8.0-Hour</u>	
1		first cycle	1	
2-48		one cycle every 2 days	8	
49-120		one cycle every 6 days	4	
<u>24-Hour</u>		<u>Recordings*</u>	<u>24-Hour</u>	
1		first cycle	1	
2-56		one cycle every week	8	
57-112		one cycle every 2 weeks	4	

* 2-minute readings during the discharge and hourly readings during the charge portions of the cycle.

On succeeding cycles, 2-minute readings are recorded on one cycle every 30 days. Following a cell low voltage signal, 2-minute readings are recorded on one cycle every second day to cell failure. After removal of failed cell, recording frequency returns to one cycle every 30 days.

TEMPERATURE CYCLING--0° to 40° C

Data of a complete 48-hour temperature cycle is recorded every 30 days. During this time, data recordings of the 90-minute cycles are every 2 minutes for cycles 1, 16, and 32; and every 10 minutes for all intervening cycles as shown below:

<u>Discharge/Charge Cycles</u>	<u>Frequency of Recordings</u>
1	2 minutes
2-15	10 minutes
16	2 minutes
17-31	10 minutes
32	2 minutes

Each succeeding recording has the starting time of the "32-cycle period" advanced by one cycle (90 minutes); thereby requiring a total of 16 monthly recordings for a complete coverage of 2-minute readings throughout the temperature cycle.

Prior to 3 May 1970, data was recorded on each pack every 32 cycles for the 1.5- and 3.0-hour orbit periods, every 24 cycles for the 8.0-hour orbit period, every 16 cycles for the 12-hour orbit period, and every 8 cycles for the 24-hour orbit period.


All graphs are computer printed with cycle numbers automatically scaled and "staggered" (to allow room for printing) at the bottom of each graph. They are printed in multiples of 10 or 100 depending on the total cycles and room available. Thus the computer is programmed to round as follows:

Multiples of 10

0-4 Cycles, 0
5-14 Cycles, 1
15-24 Cycles, 2
25-34 Cycles, 3

Multiples of 100

0-49 Cycles, 0
50-149 Cycles, 1
150-249 Cycles, 2
250-349 Cycles, 3

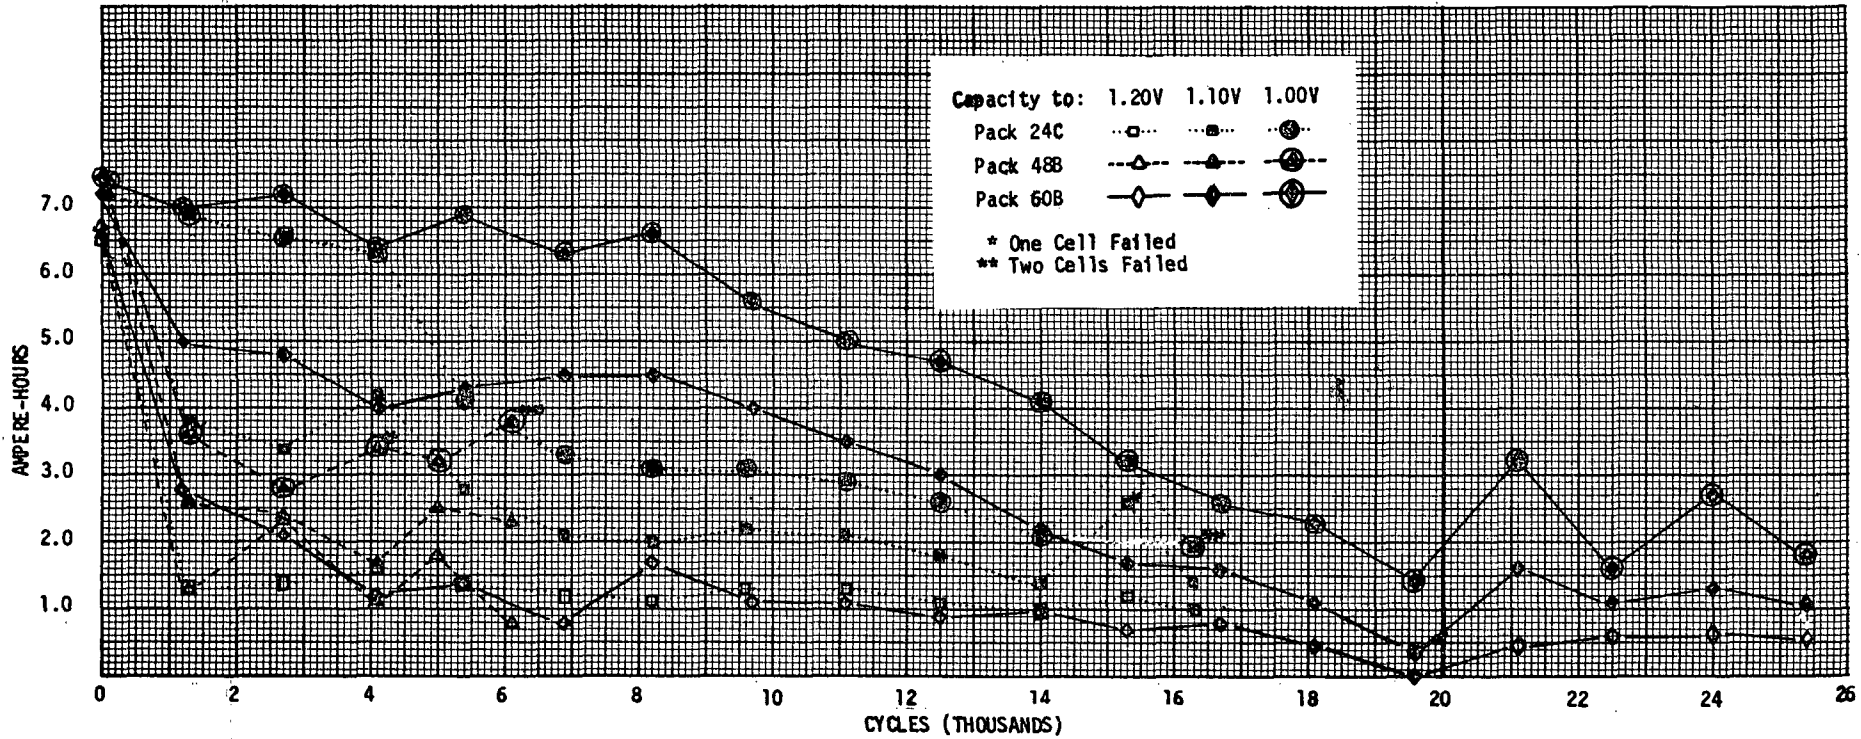

CAPACITY, AT CYCLE RATE, TO 1.20, 1.10 AND 1.00 VOLTS

FIGURE 1

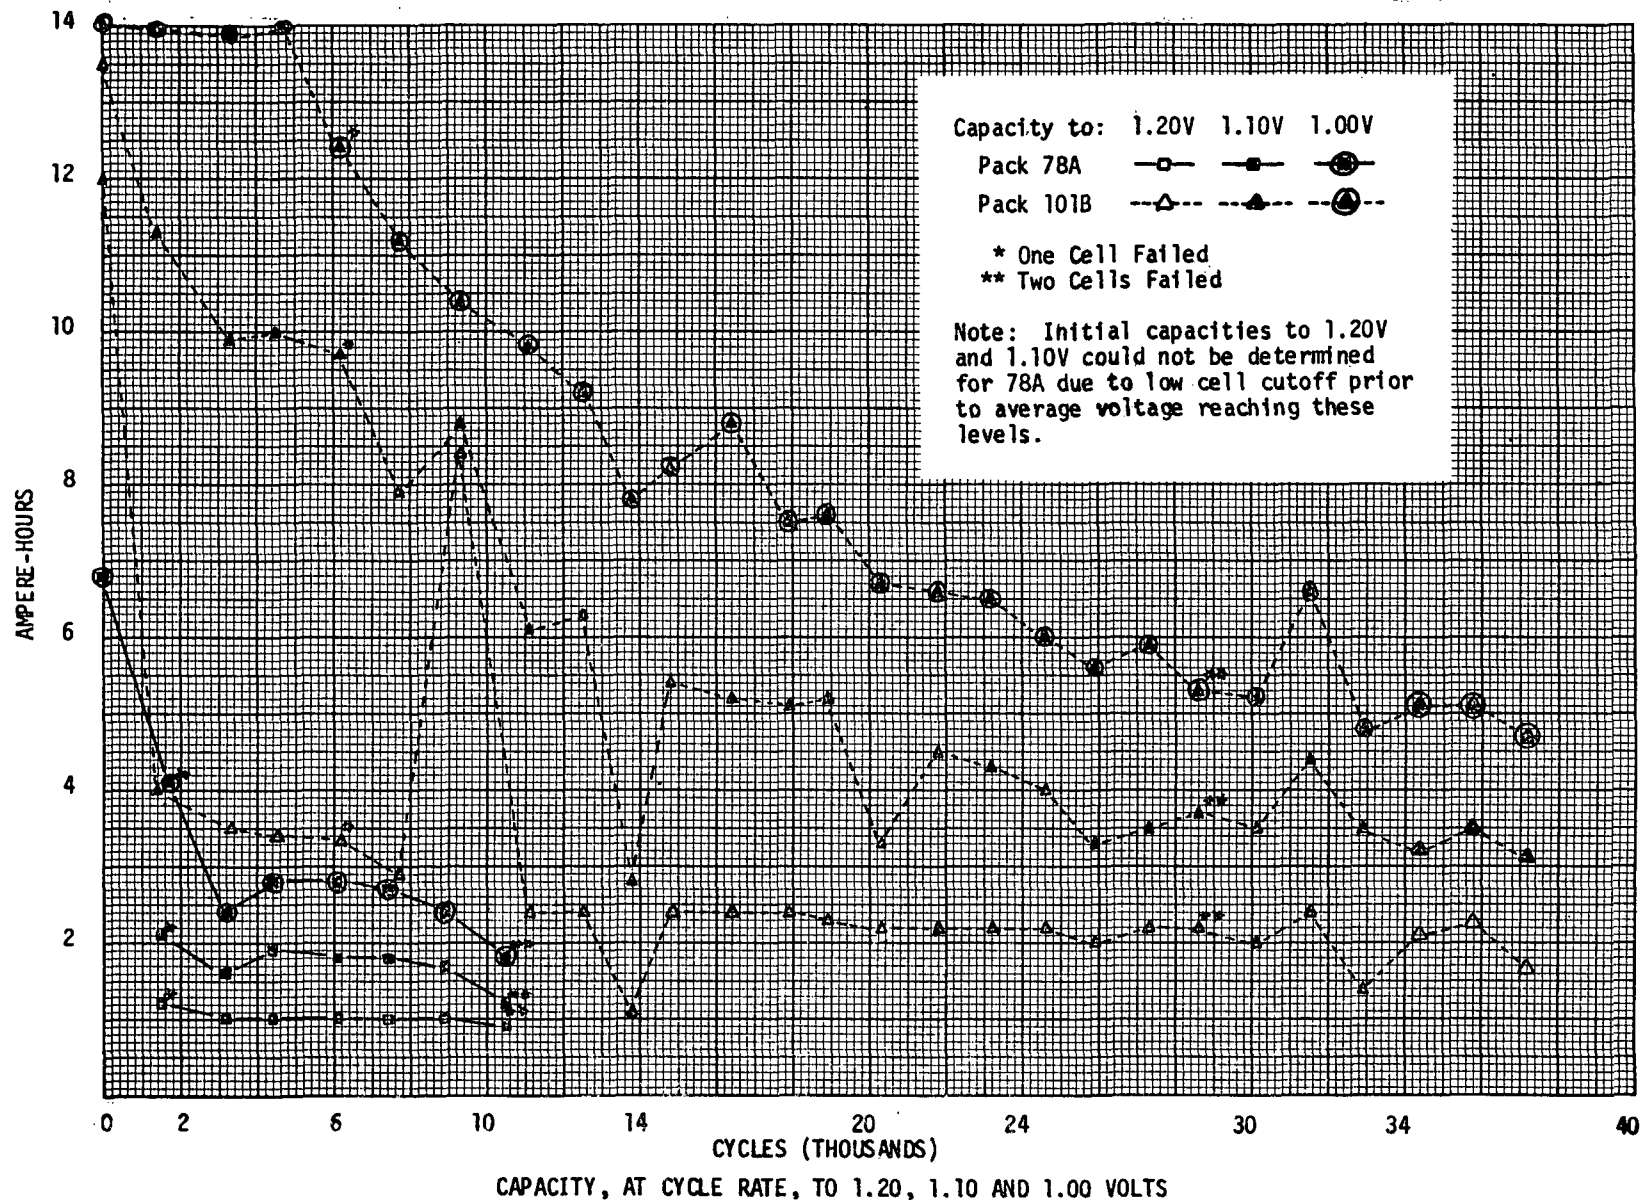


FIGURE 2

SPACE ORIENTED TESTS IN ADDITION TO LIFE CYCLING TESTS

The following tests have been, or are being performed at NAD Crane. The results are reported by Crane unless otherwise specified and copies of data are available on request to the NASA Technical Officer.

A. Acceptance Testing: These tests are conducted on cells ranging in capacity from 1.25 to 100 ampere-hours. The tests consist of: (1) general inspection, weighing and leak checks, (2) three capacity checks, (3) cell short test, (4) overcharge test, and (5) internal resistance test.

B. Separator Testing: Separator tests are conducted on all types of separators including pellaon, cellophane, polypropylene, various materials by RAI, and ceramic material. The tests are performed in three modes: (1) constant current charge, (2) constant potential charge, and (3) 30-day stand while in a charged state. To date these tests have been limited to silver-zinc and silver-cadmium cells of the various manufacturers. The cells undergoing separator tests are reported by Goddard Space Flight Center.

C. General Performance Testing: General performance testing has been conducted on cells ranging in capacity from 1.25 to 20 ampere-hours. To date these tests have been limited to nickel-cadmium cells. All major manufacturers have been represented. The test consists of: (1) random vibration, (2) sinusoidal vibration, (3) mechanical shock, (4) acceleration, (5) charge at varying rates from $c/10$ to $2c$ with discharge rate constant at $c/2$, (6) charge at constant rate previously determined to give maximum capacity at individual temperatures ranging from -20° to 40° C with discharge rate varying from $c/20$ to $2c$, and (7) overcharge test.

D. Synchronous Orbit Testing: These tests have been performed on 6 and 12 ampere-hour nickel-cadmium cells and 5 ampere-hour silver-zinc. The test has a 180-day cycle consisting of 140 days of trickle charge and 40 days of discharge-charge. The discharge time is 12 minutes the first day, increasing 3 to 4 minutes each succeeding day, reaching its maximum of 72 minutes on the 18th day which is maintained each day through the 25th. Beginning with the 26th day the discharge time is decreased 3 to 4 minutes per day until it has returned to the 12-minute minimum on the 40th day.

E. Interplanetary Monitoring Platform (IMP) Testing: These tests were performed on batteries identical to the flight batteries aboard the IMP satellites E, F, G and I. The test conditions simulate those aboard the respective satellites and are basically a 12-hour orbit. The cells making up the batteries are silver-cadmium varying in capacity from 3 to 10 ampere-hours. Summary reports have been written by Goddard Space Flight Center.

F. Jet Propulsion Laboratory (JPL) Testing: These tests involve silver-zinc and silver-cadmium cells and consist of three distinct programs.

1. Program involving storage at different temperatures: This series of tests include: (a) capacity check upon receipt, (b) recharge and storage at temperatures ranging from -51° to $+49^{\circ}$ C, (c) discharge following removal from storage and temperature stabilization at room temperature (25° C), and (d) life cycling at room temperature.

2. Program involving life cycling only: This series of tests included: (a) general inspection, weighing and leak test, (b) measurement of internal resistance, (c) capacity tests, and (d) automatic cycling.

3. Program involving sustained high g-levels: This test consists of subjecting silver-zinc cells of varying capacity to charge-discharge cycles while being subjected to high g-levels. The tests are conducted on both the sealed and vented types of cells. Further the testing is performed on cells that are starved and also on those containing normal amounts of electrolyte. Sustained g-levels applied to the cells during charge-discharge are 1.0g, 10g, 20g, 30g, 50g and 75g.

DEFINITIONS

Weight Loss: The weight loss in grams between the weight at the time of acceptance and that at the time of failure. Gains or losses of less than one gram are not considered (slight gains may occur from traces of solder left on the cell terminals).

Deposits: Carbonate deposits, at a point of leakage such as at a terminal or seam; or corrosive deposits located under the top portion of the cell case around the seam and the terminal tabs. Deposits are removed prior to weighing as of 14 December 1969.

High Pressure: Signified by a bulged cell case or by a hissing of escaped gas when cell is opened. It may not be present at the time the cell is opened although the bulge indicates its presence at some earlier time.

Concave Sides: Refers to rectangular cells only. The sides of the can are made permanently concave by the higher pressure of neighboring cells in the pack. This sometimes causes a short between the case and internal elements.

Weak Weld: An inadequate weld, as determined by the mechanical strength of the bond. The pieces separate, without tearing of the metal, when pulled apart by the fingers. This may be at a tab-to-plate connection, a tab-to-cell case connection, or a tab-to-terminal connection.

Loosened Active Material: Positive plate active material which separates from the grid in large intact pieces. This condition is often noticed in cylindrical cells due to the fact that the plates are unrolled during failure analysis. However rectangular plates often show the positive material to flake off at the edges or be extremely brittle and crumbly.

Extraneous Active Material: Pieces of loose active material found pressed between the plates. These are thought to have crumbled off the plate edges when the cell was being assembled, since there are no holes or bare spots on the plate itself. These pieces put pressure on the separator material and often cause a short circuit between the plates at that point.

Pierced Separator: Refers to short circuits between plates, which may be caused by plates having rough edges, foreign material between the plates, a grid wire or a tab at the tab-to-plate connection piercing the separator and contacting the adjacent plate.

Excess Scoring: Indentations of the cell case which may put increased pressure on the plates and separators which may cause a short circuit between the case and plates.

Positive Tab Deterioration: The positive tab, above the plates, may be corroded, burned and sometimes broken. The broken tab may fall against the case and cause a short circuit. At times the corrosion is such that the tab crumbles when the cell is opened, so that its prior configuration cannot be determined. A burned positive tab has been attributed to an insufficient area of welding between the tab and the positive terminal, causing a high-resistance contact.

Short Separator: Related to a burned positive tab. The separator material just below the burned tab has pulled back, apparently from the heat generated, so that the plates are exposed. Usually a short between adjacent plates results.

Ceramic Short: It is a dark colored, conducting deposit which causes an electrical short across the ceramic insulator at the terminal, and is a result of silver brazing used in the cells' manufacture. It is determined by measuring the resistance between the insulated material and the cell case after the plates have been cut off the buses. Its presence is fairly well defined, the measured resistance being on the order of 20 ohms or less.

Migration: Active material deposited on the surface of the separator, appearing as a uniform dark coating on the separator material. In small areas the plate material may penetrate completely through the separator and be visible as small, dark spots on the positive plate side, usually resulting in a high-resistance short circuit. Where this condition is more pronounced there are burned spots on the separator at the point of penetration. Migration is always by the negative plate material except in two very advanced cases, where there was also slight migration from the positive plate. Migration is accelerated at points of localized pressure on the separator, especially around the edge of the pressure area. For example in the round cells, where a pressure area is produced by a piece of tape covering the tab-to-plate connection, there is no migration at the taped area but a very dark line of migrated material outlines the tape's location. In addition, there may be brownish spots of discoloration around the edge of the tape and usually a small hole in the center of each spot. A similar situation, due to the scoring of the Sonotone 3.5 ampere-hour cell case, also occurs.

Blisters: Raised areas of active material, which have pulled away from the grid. Typically, they ranged from pinhead size to 3/8 inch in diameter, and were invariably found on the positive plates. While blistering has not been shown to have a direct bearing on cell failures, it is included here because it was common in some cell types, but rare or absent in others, and because in at least two cases the separator was burned slightly where blisters had compressed the separator material.

Separator Deterioration: Decomposition of the separator material, exclusive of visible burned spots. Deteriorated separator material, as defined here, is decidedly thinner than normal, adheres to the negative plate, and has lost virtually all tensile strength. Shorts between the plates may result. In some of the round cells this condition may be absent at the outermost portion of the separator, but become progressively worse toward the center of the core. Shorts between the plates may result at the center of the core.

QEEL/C 72-1

SECTION I

CELLS ON ORIGINAL TEST PROGRAM STILL CYCLING

I. CELLS ON ORIGINAL TEST PROGRAM STILL CYCLING

A. At the start of the original cycling program there was a total of 84 packs and as of January 1968, 25 of these packs were still cycling. At the request of Goddard Space Flight Center, tests on 20 of these packs were discontinued to make room for newly developed space cells being procured for evaluation. Five of the best performing packs of the original group, were maintained on cycling for life capability determination purposes. Of these five packs, two have failed. Thus only three of the original 84 packs continue to cycle. The results of all but these three remaining packs (110A, 111A and 125A) have been summarized in Section III of this report. The results of the remaining packs are contained in Figures 3 through 6 at the end of this section.

B. The three packs maintained on cycling contain five GE 12 ampere-hour, nickel-cadmium, cells per pack. These cells are rectangular. The cell containers and covers are made of stainless steel. Both terminals are insulated from the cell cover by ceramic seals and protrude as 1/4-20 threaded posts.

C. These packs are being tested under the following parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
110A*	0° C	15
111A	0° C	15
125A	0° C	25

* This pack is cycled at the 1.5-hour orbit period; the others are at the 3.0-hour orbit period.

D. Cycling was started in January 1964. Packs 110A, 111A, and 125A have completed 43,544, 22,010, and 22,319 cycles, respectively. Only one cell failure has occurred to date. This was in pack 125A after 19,645 cycles.

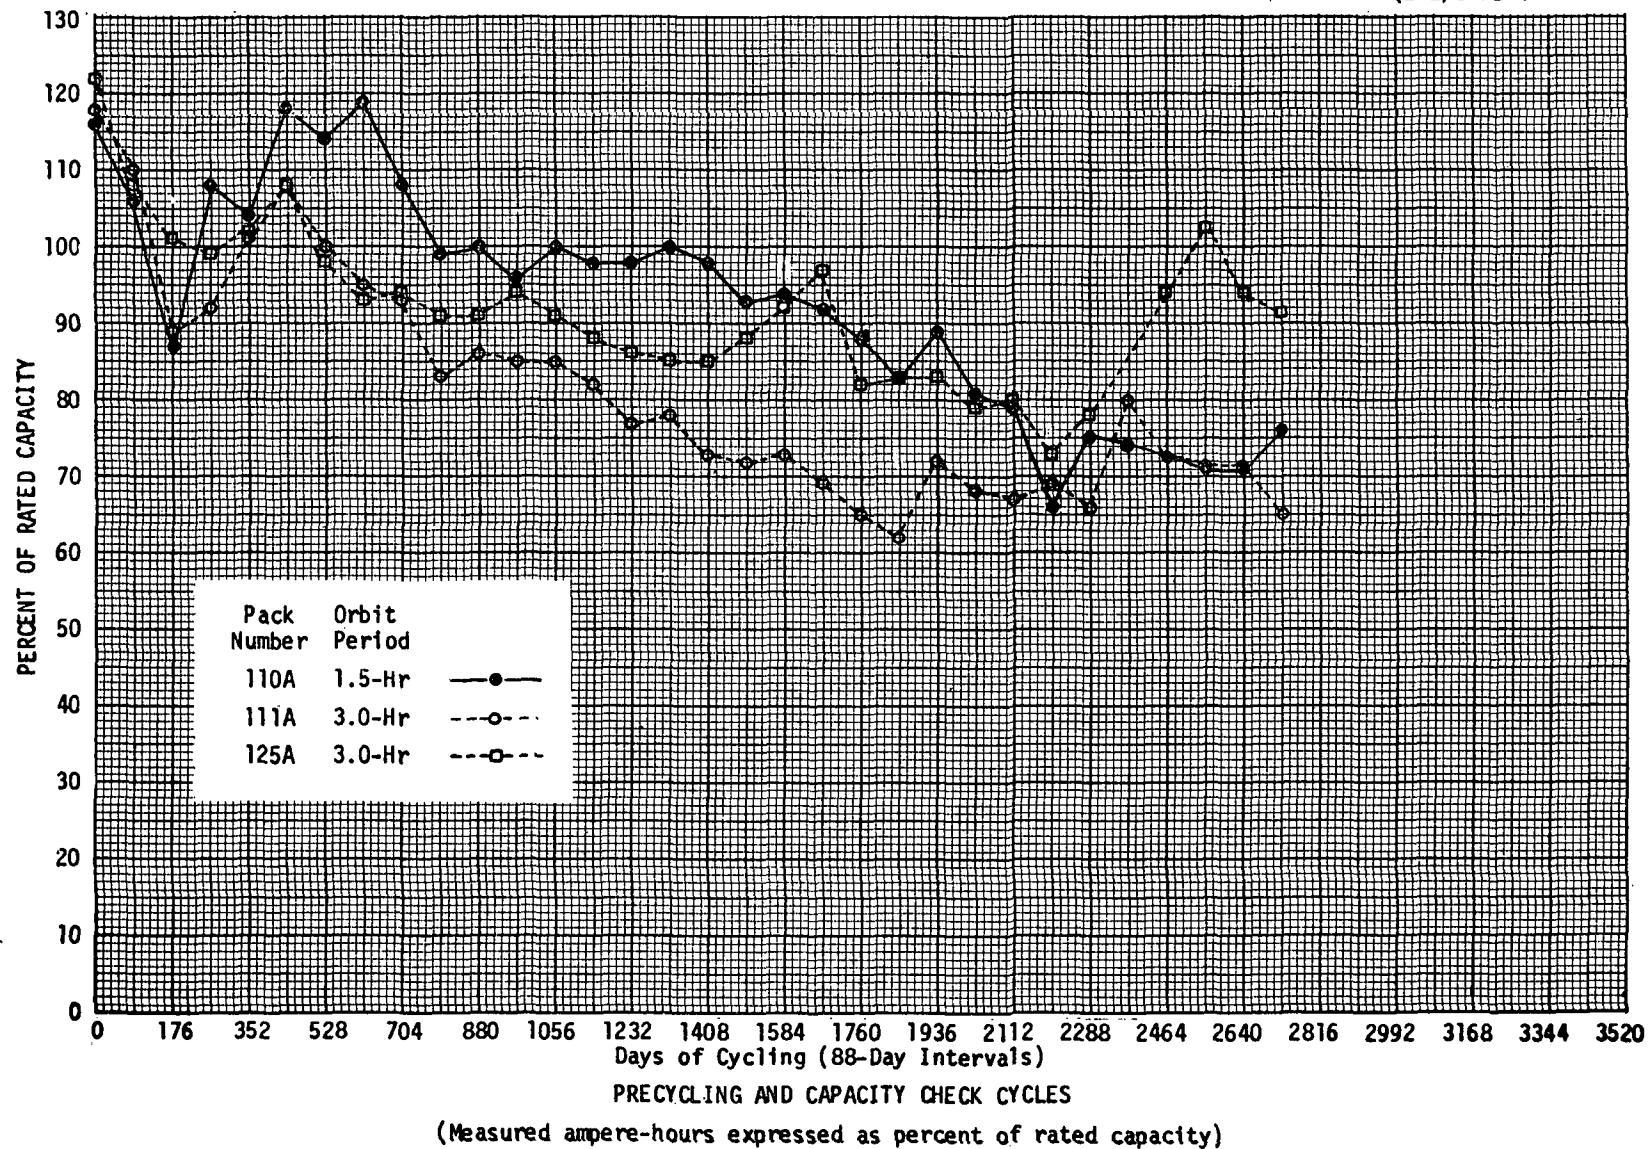


FIGURE 3

PACK 110A	MANF. GE
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	2.07
DEPTH OF DISCHARGE %	15

PACK 110A	MANF. GE
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	2.07
DEPTH OF DISCHARGE %	15



KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 111A MANF. GE
 ORBIT PERIOD HOURS 03.0
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 0.83
 DEPTH OF DISCHARGE % 15

QEEL/C 72-1
 12.0 AH

CELLS CYCLING


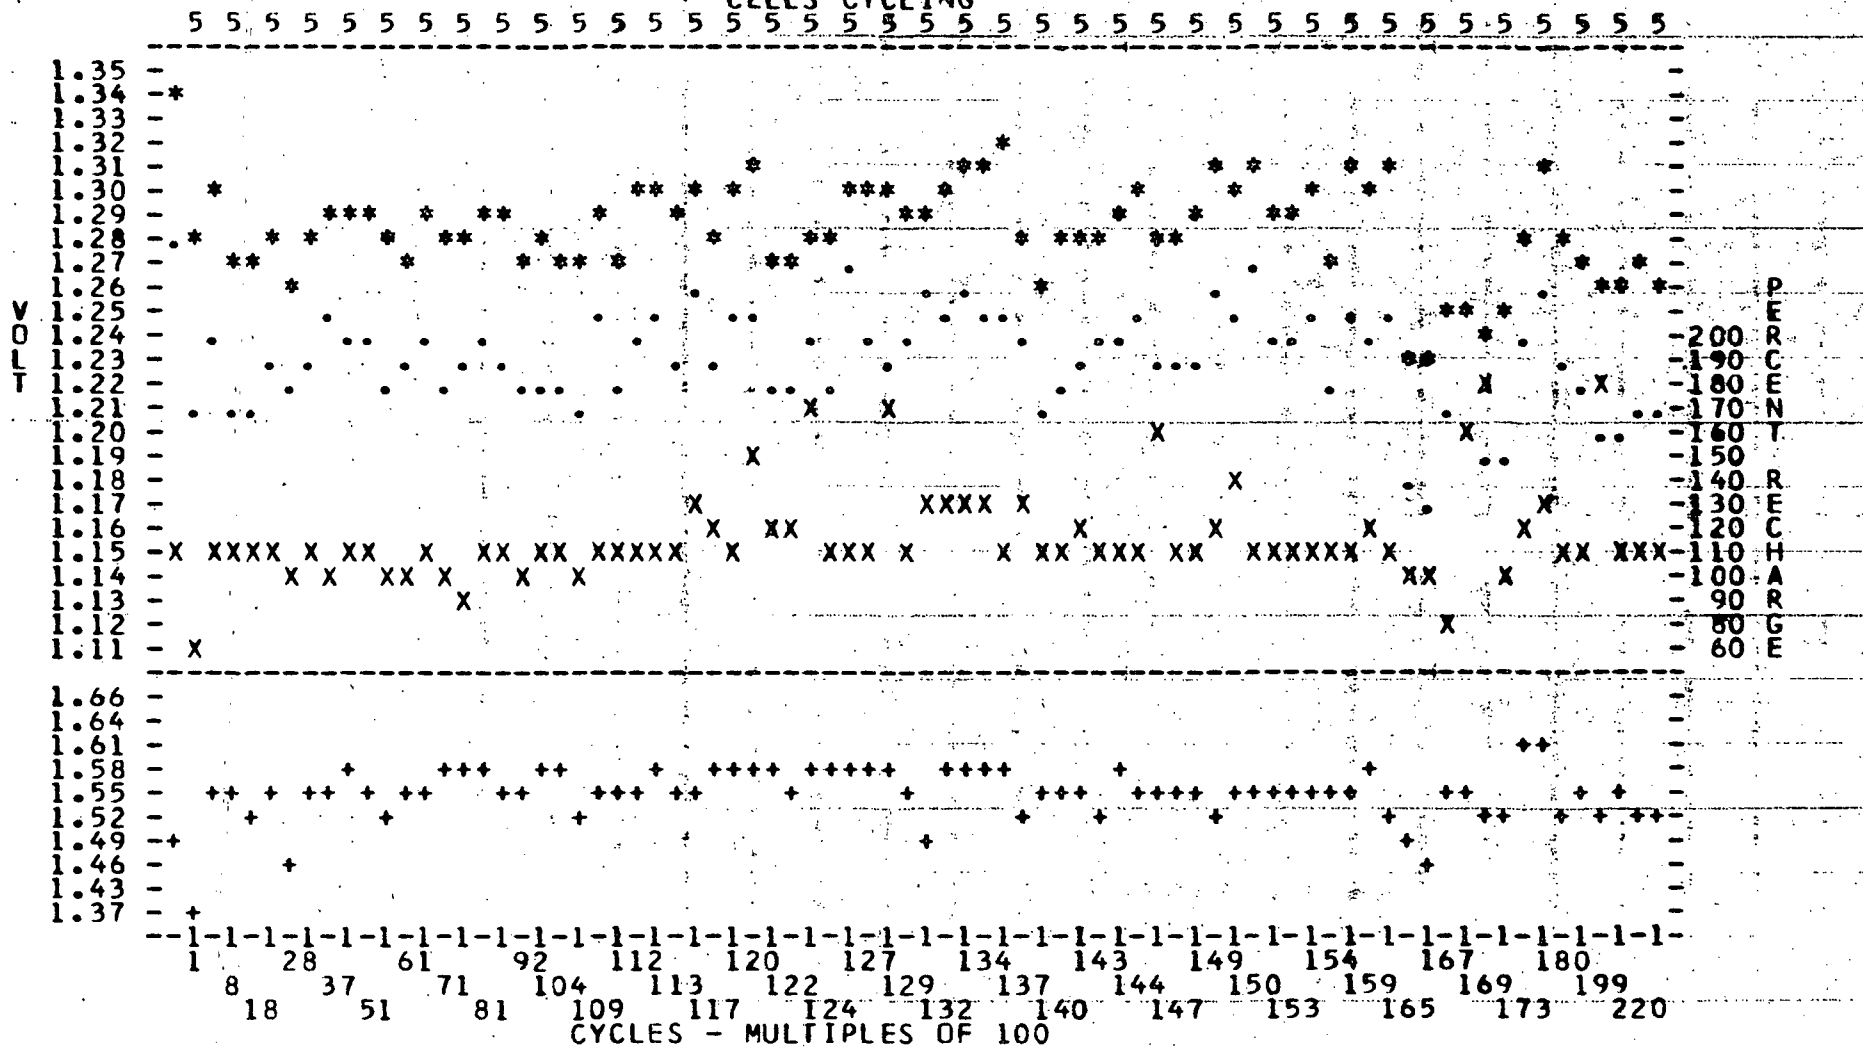


FIGURE 5
 16

PACK 125A	MANF. GE
ORBIT PERIOD HOURS	03.0
TEMP. DEGREES C.	00
CHARGE RATE AMPS	1.38
DEPTH OF DISCHARGE %	25

CELLS CYCLING



SECTION II

CELLS USING CONSTANT CURRENT CHARGE WITH VOLTAGE
LIMIT CONTROL (CELLS PRESENTLY CYCLING WHICH
FOLLOWED THE ORIGINAL PROGRAM)

I. CELLS USING CONSTANT CURRENT CHARGE WITH VOLTAGE LIMIT CONTROL

Because of the continuing effort to extend the performance life, new cells, with modifications such as nickel plating the silver braze area or new type seals, are added to the program for evaluation. New cells are also added to the cycle program for evaluation under new environmental conditions such as cycling at -20°C , or cycling during temperature cycling. Each pack is cycled until 60 percent of the cells have failed. A cell is considered a failure when its terminal voltage drops below 0.5 volt during cycling.

A. General Description:

1. The majority of the nickel-cadmium cells tested for use in space, or related programs, are of one basic type. They are rectangular with stainless steel containers and covers; both terminals are insulated from the cover by a ceramic seal and protrude through the cover as solder type terminals. Where the cells differ from this description, a separate description has been written in the sections to follow.

B. Nickel-Cadmium Types:

1. Gulton 3.5 ah (Polymerized Neoprene Seal), Seven 5-cell Packs:

a. An additional 5-cell pack was put on continuous charge at the c/10 rate in an ambient temperature of 25°C in order to evaluate the new seal. This pack was not assigned a pack number as were those appearing in the table.

b. Cell Description: These cells are cylindrical with cell containers and covers made of stainless steel. The positive terminal is insulated from the cell cover by a polymerized neoprene bushing and protrudes through the bushing as a 8-32 threaded post. The negative lead is soldered to the cell container.

c. Parameters and Capacity Checks:

Orbit Period		1.5-hour					
Temperature		-20°	-20°	0°	0°	25°	25° 40°
Depth of Discharge		25%	40%	25%	40%	25%	40% 25%
Pack Number		89C	75D	122C	99C	87C	73C 112C
Precycling Capacity		3.12	3.79	3.70	4.38	4.14	4.26 4.32
88 Days	Disch #2	2.39	3.50	3.33	4.23	3.62	3.50 1.20
264 Days	Disch #2	2.25	2.80	3.00	4.03	2.95	2.33 1.23
440 Days	Disch #2	2.33	3.30	2.65	3.65	2.01	1.87 1.05
616 Days	Disch #2	1.72	2.77	2.45	3.12	1.17	1.60 1.08
792 Days	Disch #2	1.60	2.80	2.33	2.97	1.11	F F
968 Days	Disch #2	1.25		2.27	2.97	0.93	
1144 Days	Disch #2	1.55		2.19	2.51	0.93	F
1320 Days	Disch #2	1.17		2.07	2.54		
1496 Days	Disch #2			1.98	2.30		
1672				2.19	2.01		

F - Failed.

d. Test Results:

(1) Performance on Cycling: (Figures 7 through 9)
Cycling was started in December 1966. Packs 122C and 99C (one cell failure), have completed 35,234 and 28,172 cycles respectively. Packs 75D, 73C, 112C, 87C, and 89C failed on cycles 14,197, 9978, 11,155, 20,866, and 23,832 respectively.

(2) Failure Analysis:

(a) Analysis of the 17 failed cells showed the major cause to be migration of the negative plate material and separator deterioration. Other conditions found were high internal pressure and electrolyte leakage.


(b) The pack that was put on continuous charge had one cell that developed high internal resistance and was removed from test after 1066 days. The high internal resistance was caused by corrosion of the positive tab. The cell also had electrolyte leakage and high internal pressure. The second cell failed after 1335 days of testing. The positive tab-to-terminal connection had corroded in two. The positive active material was very loose and brittle. Phenolphthalein indicated electrolyte leakage around the positive terminal.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 089C MANF. GULTON 03.5 AH
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. -20
 CHARGE RATE AMPS 0.96
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1

CELLS CYCLING

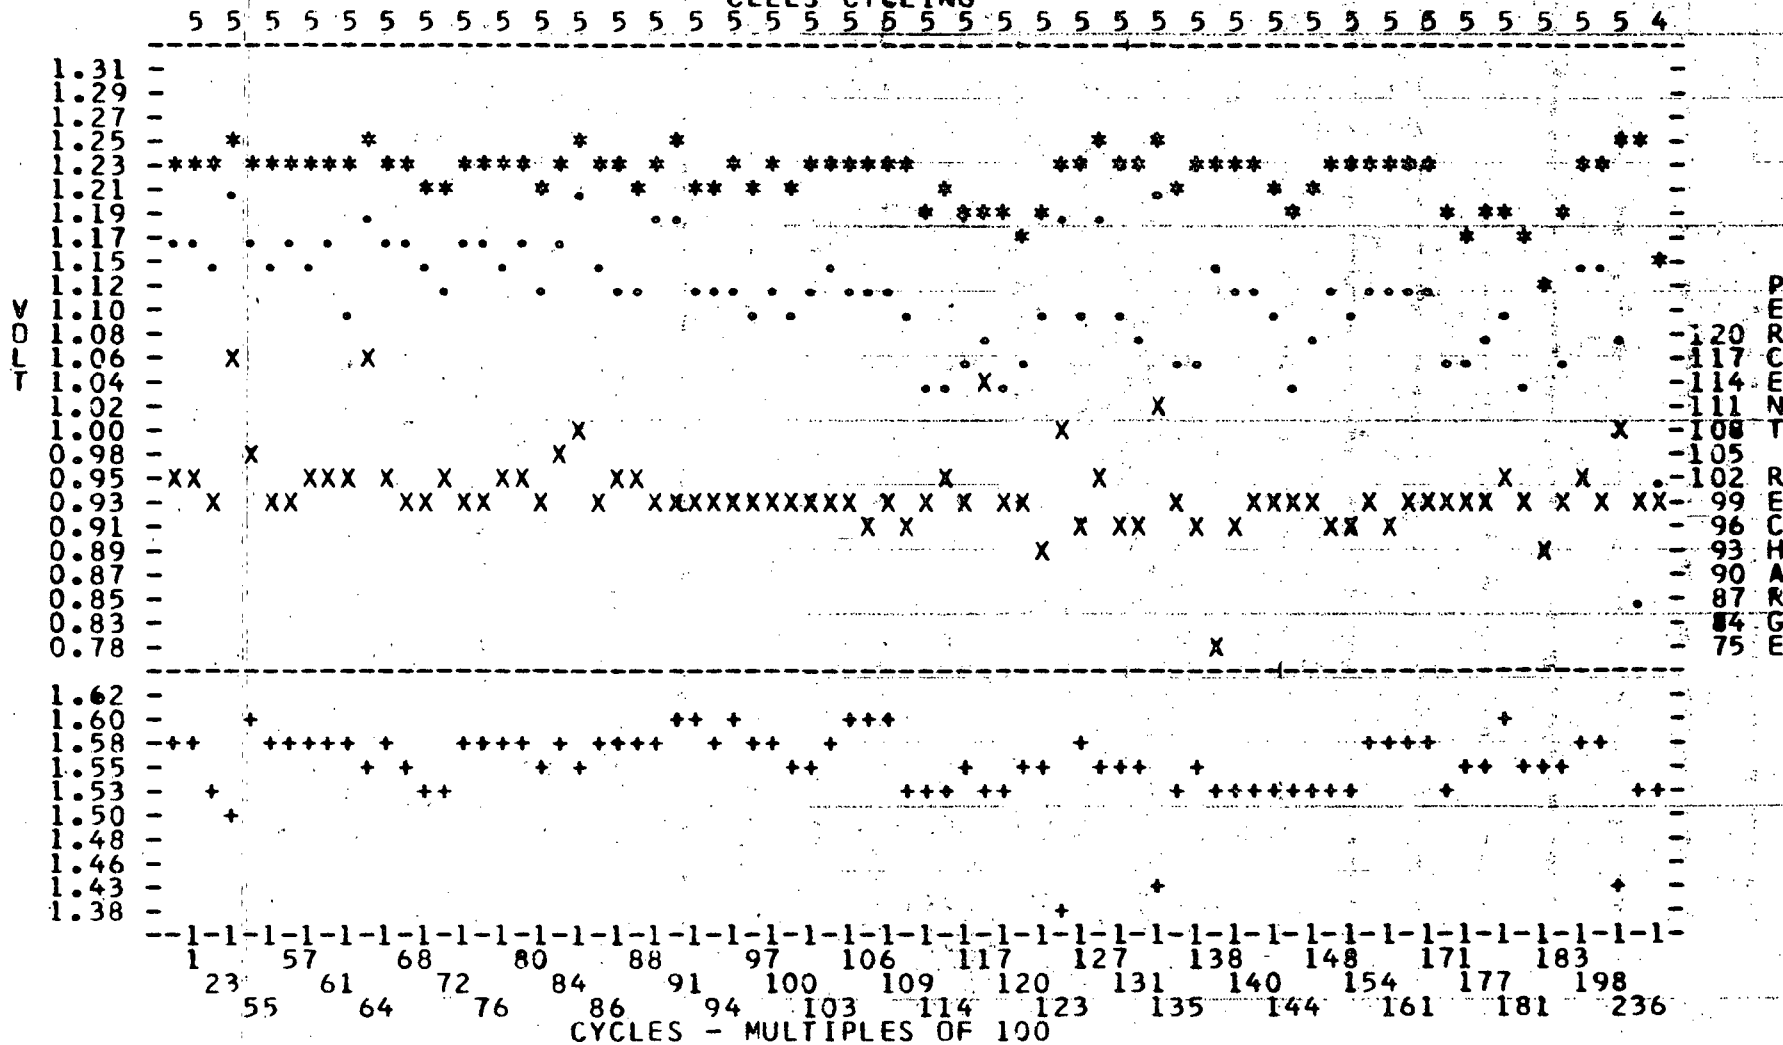

X-----PERCENT RECHARGE

DEPTH OF DISCHARGE % 25



FIGURE 8

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 099C MANF. GULTON 03.5 AH
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 1.61
 DEPTH OF DISCHARGE % 40

QEEL/C 72-1

CELLS CYCLING

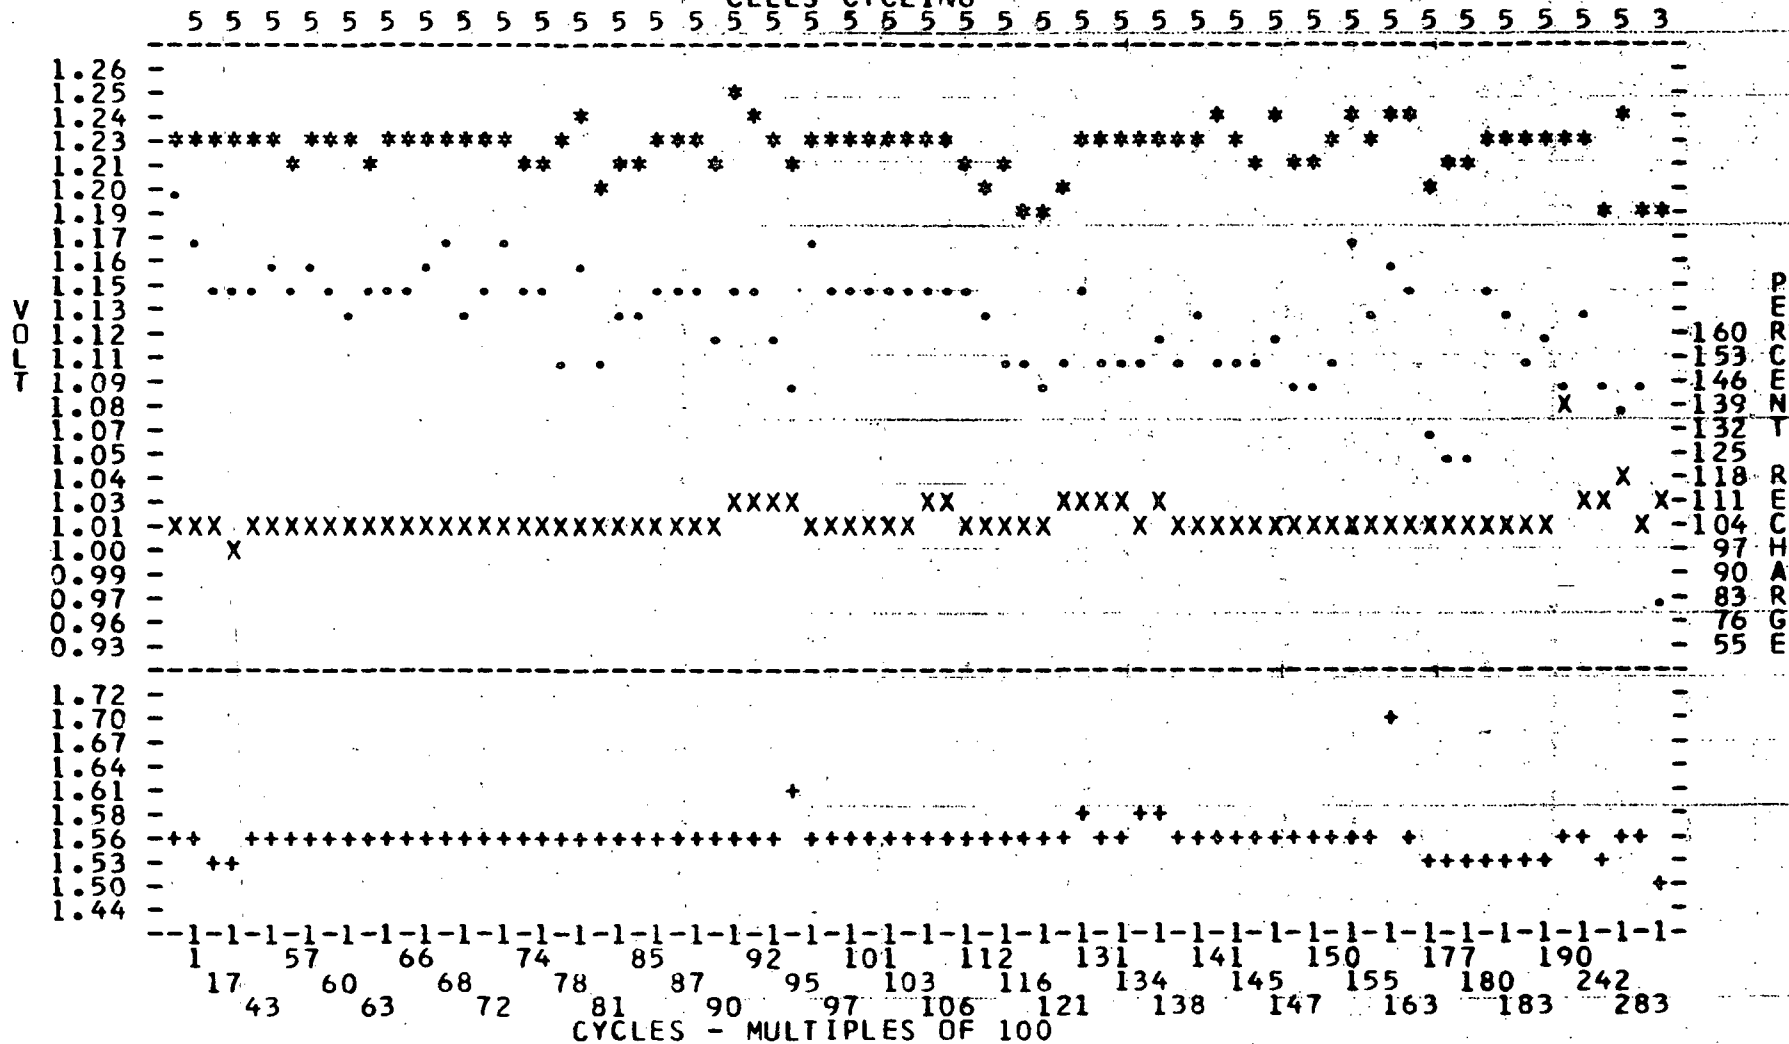


FIGURE 9
 24

2. Gulton 4.0 ah (Commercial), Six 5-Cell Packs:

a. Cell Description: These are rectangular sealed cells of commercial grade, but were not hermetically sealed as supplied. They were epoxy potted into 5-cell packs at the Goddard Space Flight Center in order to hermetically seal the cells before test.

b. Parameters and Capacity Checks:

Orbit Period		1.5-hour				
Temperature		0°	0°	25°	25°	40°
Depth of Discharge		15%	25%	25%	40%	15%
Pack Number		115B	126B	4B	14B	28B
Precycling Capacity		5.04	4.87	4.63	5.00	4.20
88 Days	Disch #2	3.57	4.00	2.47	2.00	1.70
264 Days	Disch #2	4.00	3.73	1.80	1.87	1.43
440 Days	Disch #2	4.07	3.60	1.67	1.93	1.53
616 Days	Disch #2	4.60	--	1.60	F	1.67
792 Days	Disch #2	4.33	3.63	1.67		0.76
968 Days	Disch #2	4.03	3.50	1.67		F
1144 Days	Disch #2	3.67	3.30	1.30		1.77
1320 Days	Disch #2	3.63	3.37	1.47		2.07
1496 Days	Disch #2	3.40	3.33	1.33		0.47
1672 Days	Disch #2	3.17	3.03	1.70		1.73
1848 Days	Disch #2	3.07	3.63	1.40		F
2024 Days	Disch #2	3.17	3.87	0.97		
2200 Days	Disch #2	2.80	3.04	F		
2373 Days	Disch #2	2.20				

F -- Failed.

c. Test Results:

(1) Performance on Cycling: (Figures 10 and 11)
Cycling was started in August 1964. Packs 115B and 126B (two cell failures in 126B) have completed 39,890 and 41,813 cycles, respectively. Pack 14B failed on cycle 8474, pack 28B on cycle 20,227, pack 40B on cycle 10,360 and pack 4B on cycle 35,111.

(2) Failure Analysis: The analysis of 13 failed cells showed the major cause to be due to separator deterioration and migration. Other conditions found were weak tab-to-terminal welds, high internal pressure and electrolyte leakage. Failure analysis has not been performed on two cells of pack 126B because of the pack construction.

QEEL/C 72-1

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 115B MANF. GULTON 04.0 AH
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 0.69
 DEPTH OF DISCHARGE % 15

CELLS CYCLING

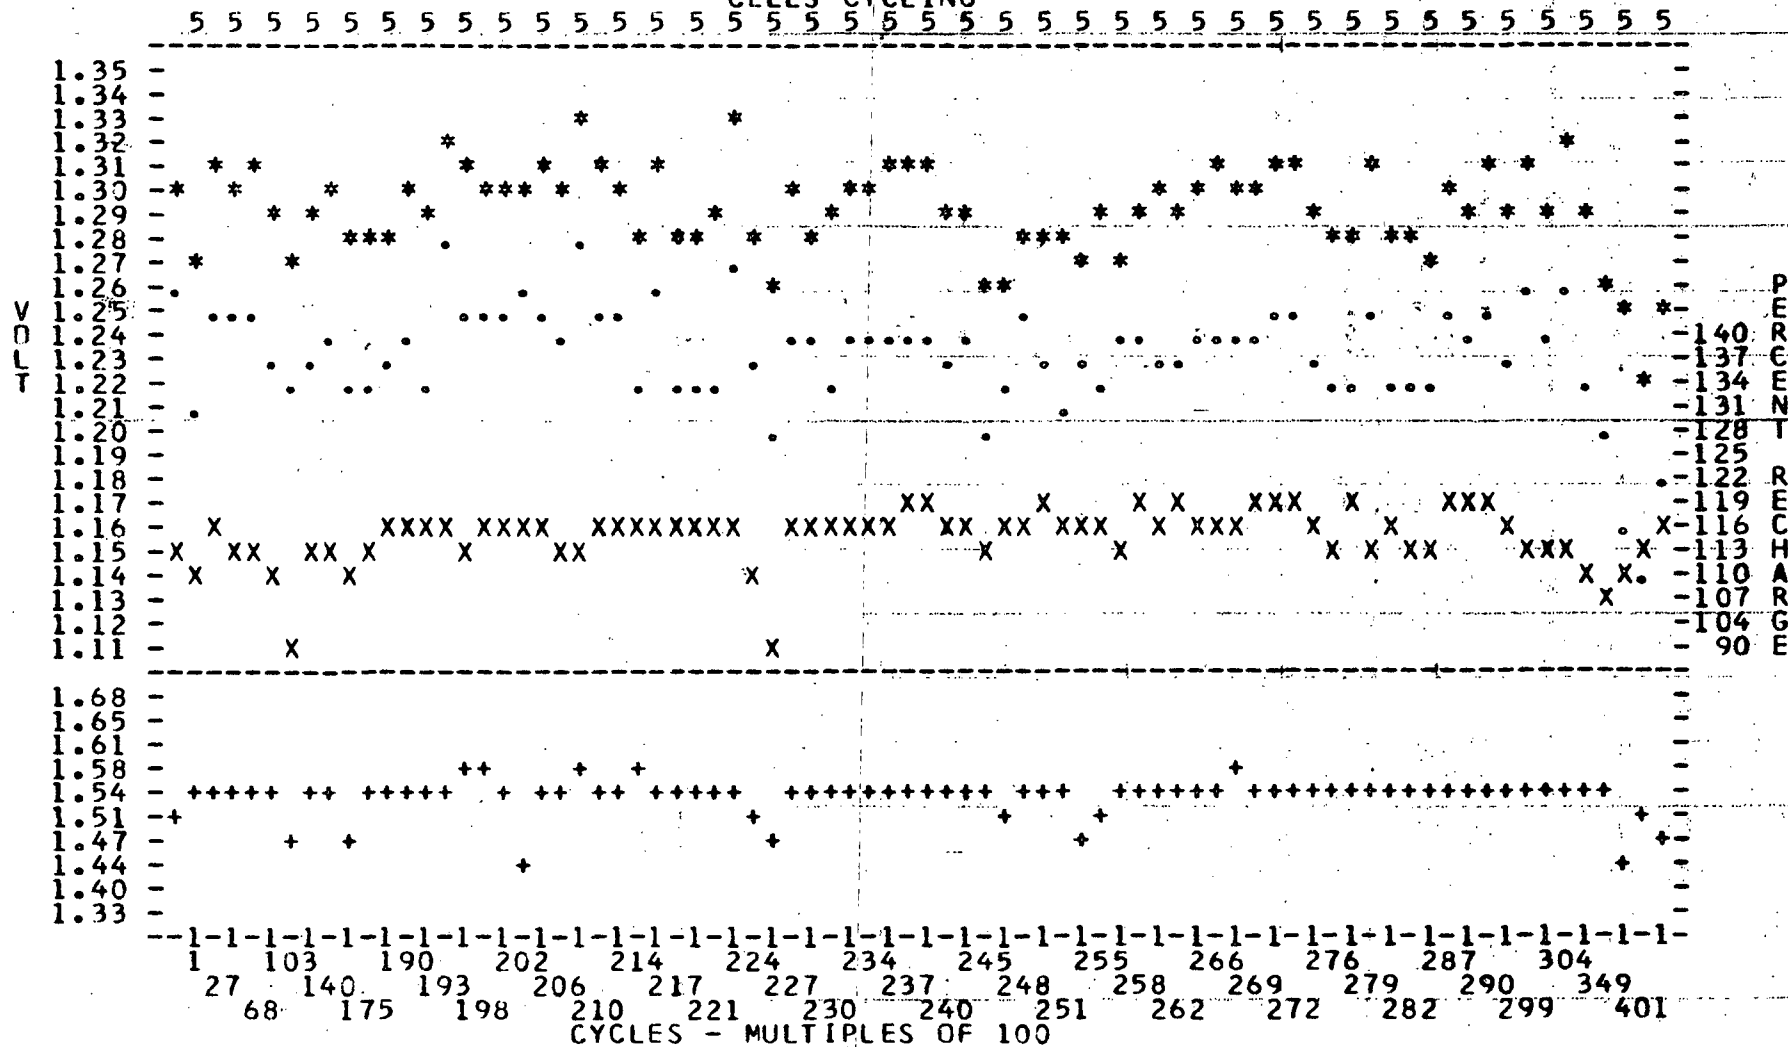


FIGURE 10

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 126B MANF. GULTON 04.0 AH
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 1.15
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1

CELLS CYCLING

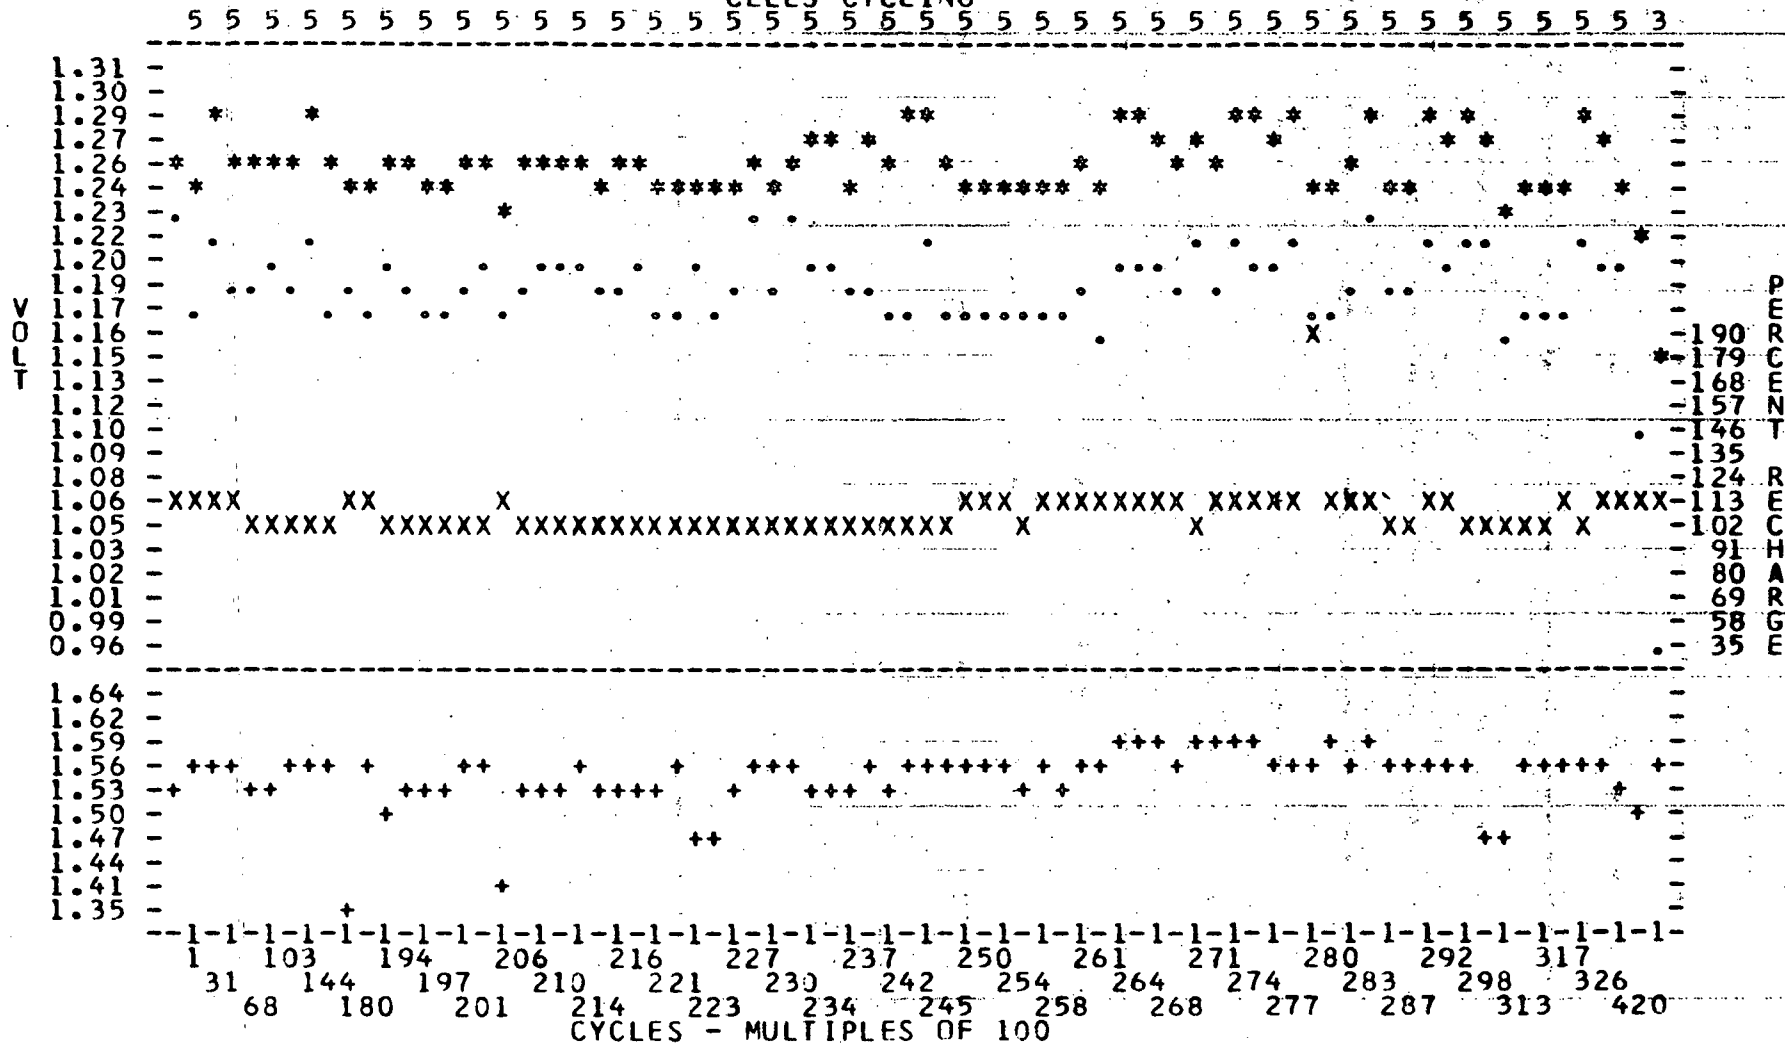


FIGURE 11
 28

3. Gulton 5.0 ah (Cobalt Additive with Pellon or Polypropylene Separator), Five 10-cell Packs:

a. Cell Description: These cells are rectangular. The cell containers and covers are made of stainless steel. The positive terminal is insulated from the cell cover by a ceramic seal. The negative terminal is welded to the cover. Both terminals protrude through the cover as solder type terminals. Twenty-five cells contain positive plates with cobalt additive; 25 cells are without the cobalt additive and are designated as control cells. Twenty-four cells contain pellon separator and 26 cells contain a polypropylene separator (PPL). The cells were divided into packs as indicated in the table below.

Pack Number	Type and Number of Cells per Pack			
	Cobalt-Pellon	Control-Pellon	Cobalt-PPL	Control-PPL
21E	5	5		
45E	2	2	3	3
69C	5	5		
9H			5	5
33D			5	5

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour				
Temperature	0°	25°	25°	40°	40°
Depth of Discharge	25%	25%	40%	25%	40%
Pack Number	21E	45E	69C	9H	33D
Precycling Capacity	4.83	5.70	5.70	3.33	3.30
88 Days	5.08	2.75	3.52	2.38	3.92
264 Days	5.08	2.93	3.08	3.50	F
440 Days	5.00	2.80	4.72	2.88	

c. Test Results:

(1) Performance on Cycling: (Figures 12 through 16) Cycling was started in June 1970. Packs 21E, 45E, 69C and 9H have completed 7392, 7449, 7448 and 7449 cycles, respectively with no failures to date. Pack 33D failed on cycle 4523 and no failure analysis was performed as per instructions from NASA, Lewis Research Center. These cells will be returned to NASA, Lewis.

PACK 021E	MANF.	GULTON
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		00
CHARGE RATE AMPS		1.40
DEPTH OF DISCHARGE %		25

PACK 021E	MANF. GULTON	05.0
ORBIT PERIOD HOURS	01.5	
TEMP. DEGREES C.	00	
CHARGE RATE AMPS	1.40	
DEPTH OF DISCHARGE %	25	

[illegible]

PACK 045E	MANF.	ASTRO
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		25
CHARGE RATE AMPS		1.40
DEPTH OF DISCHARGE %		25

ASTRO 05.0 AH
01.5
25
1.40
25

[illegible]


32

X-----PERCENT RECHARGE

DEPTH OF DISCHARGE %

QEEL/C 72-1

CELLS CYCLING

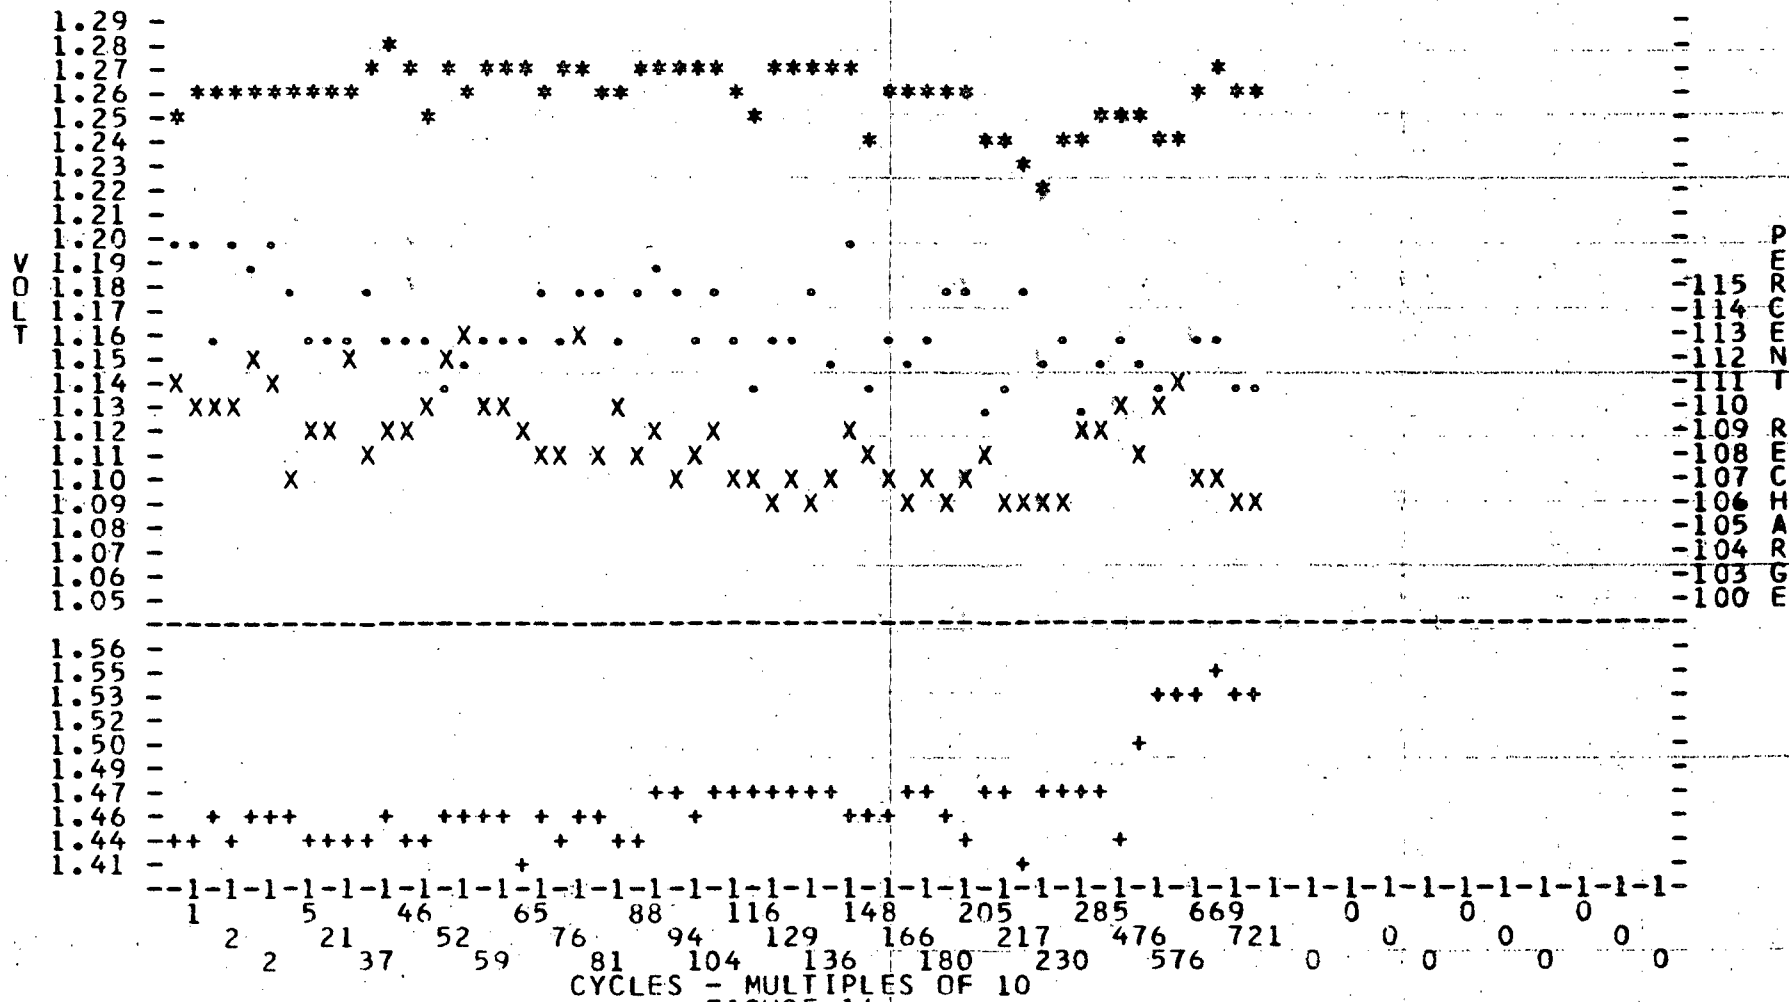
[illegible]

CYCLES - MULTIPLES OF 10

FIGURE 14

PACK 009H	MANF.	GULTON	05.0 AH
ORBIT PERIOD HOURS		01.5	
TEMP. DEGREES C.		40	
CHARGE RATE AMPS		1.40	
DEPTH OF DISCHARGE %		25	

PACK 009H	MANF.	GULTON	05.0 AH
ORBIT PERIOD HOURS		01.5	
TEMP. DEGREES C.		40	
CHARGE RATE AMPS		1.40	
DEPTH OF DISCHARGE %		25	

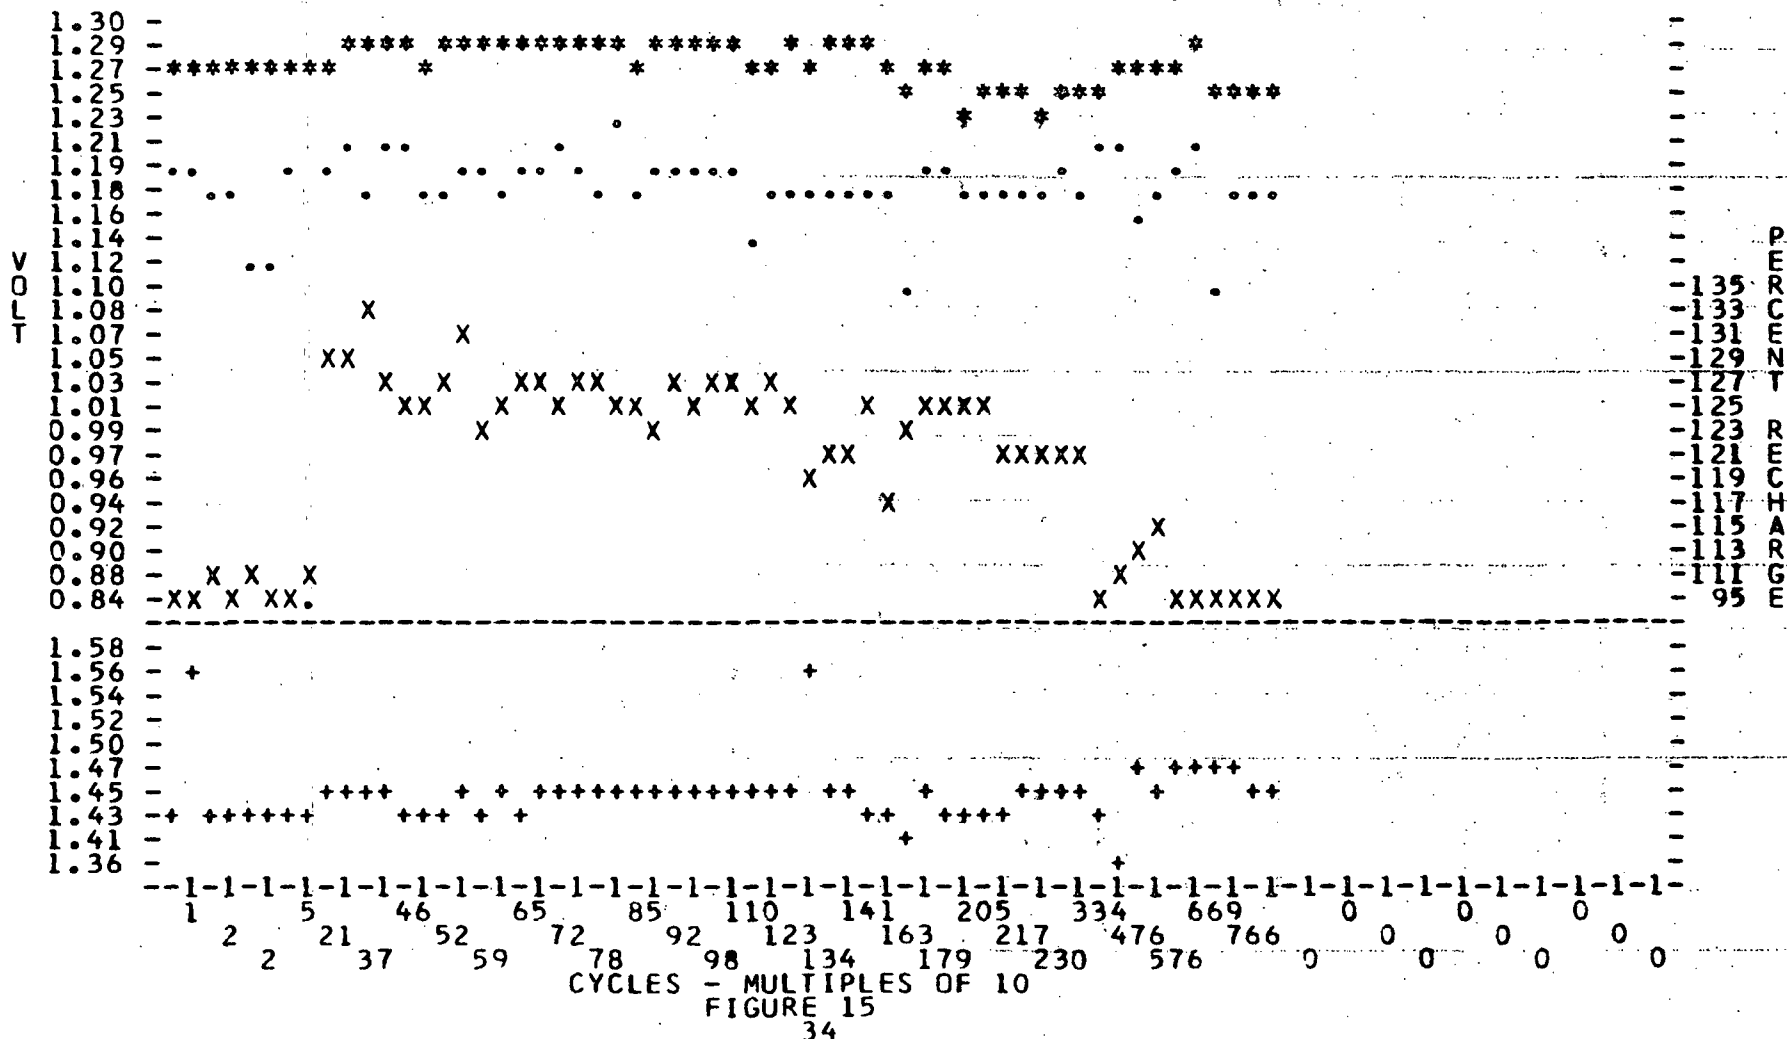[illegible]

PACK 033D	MANF.	GULTON	05.0 AH
ORBIT PERIOD: HOURS		01.5	
TEMP. DEGREES C.		40	
CHARGE RATE AMPS		2.20	
DEPTH OF DISCHARGE %		40	

QEEL/C 72-1

CELLS CYCLING

[illegible]

4. Gulton 5.0 ah (NIMBUS), Six 5-cell Packs:

a. Cell Description: These cells are cylindrical with a convex base. A threaded stud is fastened to the base to facilitate heat sink mounting. The cell container and the cell cover are made of stainless steel. Two stainless steel tabs, welded to the cover, serve as the contacts for the negative terminal. The positive terminal is insulated from the cell cover by a ceramic seal and protrudes through the cover as a solder type terminal. Two solder tabs are welded to the terminal. Three cells have pressure transducers which are used to read internal pressure in pounds per square inch absolute. These cells were manufactured to the NIMBUS specifications.

b. Parameters and Capacity Checks:

Orbit Period		1.5-hour					
Temperature		0°	0°	25°	25°	40°	40°
Depth of Discharge		15%	25%	15%	25%	15%	25%
Pack Number		117A	121A*	120A	118B*	127A	128A*
Precycling Capacity		5.00	5.38	5.25	5.46	3.29	3.04
88 Days	Disch #2	5.17	5.38	5.40	2.55	1.67	1.42
264 Days	Disch #2	5.17	5.00	2.79	1.50	1.38	1.71
440 Days	Disch #2	4.75	4.29	2.08	2.00	1.71	F
616 Days	Disch #2	4.70	3.96	**	F	2.04	F
792 Days	Disch #2	4.08	4.08	3.21			
968 Days	Disch #2	4.17	3.79	2.58			
1144 Days	Disch #2	3.83	3.67	2.37			
1320 Days	Disch #2	4.46	F	2.12			
1496 Days	Disch #2	4.50		1.79			
				F			

* One cell in each pack is equipped with a pressure transducer.

** Capacity check not performed.

F - Failed.

b. Parameters and Capacity Checks:

Orbit Period			1.5-hour					
Temperature			0°	0°	25°	25°	40°	40°
Depth of Discharge			15%	25%	15%	25%	15%	25%
Pack Number			117A	121A*	120A	118B*	127A	128A*
1320 Days	Disch #2	4.46			2.12			
1496 Days	Disch #2	4.50			1.79			
					F			
1672 Days	Disch #2	4.33						
1848 Days	Disch #2	4.12						
2024 Days	Disch #2	4.11						
2200 Days	Disch #2	4.45						

* One cell in each pack is equipped with a pressure transducer.

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figure 17) Cycling was started in May 1965. Pack 117A has completed 37,125 cycles, with one cell failure. Packs 121A, 120A, 118B, 127A and 128A failed on cycles 20,861, 29,753, 8108, 10,638 and 6345, respectively.

(2) Failure Analysis: Analysis of the 16 failed cells showed the major causes to be separator deterioration and migration of the negative plate material. Other conditions found were electrolyte leakage, ceramic shorts, weak tab-to-plate welds, burned positive tabs, extraneous active material, pierced separator material by the positive tab, short (vertical height) separators, high internal pressure, corrosive deposits internally at the positive tab and dry separator material.

PACK 117A	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	0.83
DEPTH OF DISCHARGE %	15

05.0 AH



5. Gulton 5.6 ah (Neoprene Seal), Eight 5-cell Packs:

a. Cell Description: These cells are cylindrical in shape. The cell container and the cell cover are made of cold rolled steel. The positive terminal is insulated from the cell cover by a vulcanized neoprene bushing and protrudes through the bushing as a 1/8 inch projection. The vulcanized neoprene bushings used in the folded cover to terminal seals are longer than those used in the nonfolded cover to terminal seals to protrude through the sleeve formed by the inward fold at the center of the cover (see Figure 18). This design results in a greater length of seal and affords greater protection to the seal from heat during welding of the cover to the can. The possible damage to the neoprene seal of either type cover to terminal seal, by attempting to solder electrical connections to the 1/8 inch positive terminal made it necessary to spot weld metal tabs to these terminals. Metal tabs were also spot welded to the bottom of the cans to serve as the negative terminals.

b. Parameters and Capacity Checks:

Orbit Period		1.5-hour							
Temperature		-20°	-20°	0°	0°	25°	25°	40°	40°
Depth of Discharge		25%	25%	25%	25%	25%	25%	25%	25%
Pack Number		44B (FD)	32B (NF)	100B (FD)	90C (NF)	76B (FD)	96C (NF)	42B (FD)	30B (NF)
Precycling Capacity		4.01	4.53	6.25	6.58	5.60	6.30	4.39	4.90 F
88 Days	Disch #2	*	4.57	5.32	5.88	1.63	2.33	1.49 F	
264 Days	Disch #2	4.34	3.64	4.85	5.27	1.59	1.87		
440 Days	Disch #2	*	3.64	4.25	4.48	2.10	2.33 F		
616 Days	Disch #2	3.64	3.17	3.64	3.64	1.17 F			
792 Days	Disch #2	3.41	2.85	2.75	3.08				
968 Days	Disch #2	3.87	2.10	2.61	2.57				

* Capacity Check Not Performed.

FD - Folded.

NF - Nonfolded.

F - Failed.

Orbit Period		1.5-hour							
Temperature		-20°	-20°	0°	0°	25°	25°	40°	40°
Depth of Discharge		25%	25%	25%	25%	25%	25%	25%	25%
Pack Number		44B (FD)	32B (NF)	100B (FD)	90C (NF)	76B (FD)	96C (NF)	42B (FD)	30B (NF)
1144 Days	Disch #2	2.66	2.33	2.05	3.17				
			F						
1320 Days	Disch #2	2.72		2.01	2.43				
1496 Days	Disch #2	2.66		2.10	2.74				
1672 Days	Disch #2	3.59		2.46	1.90				
				F					
1848 Days	Disch #2	2.72			2.01				
		F			F				

FD - Folded.

NF - Nonfolded.

F - Failed.


c. Test Results:

(1) Performance on Cycling: (Figures 19 through 21)

Cycling was started in December 1965. Pack 44B failed on cycle 31,907, pack 110B on cycle 28,758, pack 90C on cycle 31,623, pack 32B on cycle 23,303, pack 76B on cycle 11,158, pack 96C on cycle 9791, pack 42B on cycle 3798 and pack 30B on cycle 1275.

(2) Failure Analysis: Failure analysis of the 24 failed cells showed the major cause to be separator deterioration, migration of the negative plate material, electrolyte leakage, and burned positive tabs. Other conditions found were weak positive tab-to-plate welds, burned positive tabs, high internal pressure, corrosive deposits internally at the positive terminal, carbonate deposits externally at positive terminal, and dry separator material.

QEEL/C 72-1

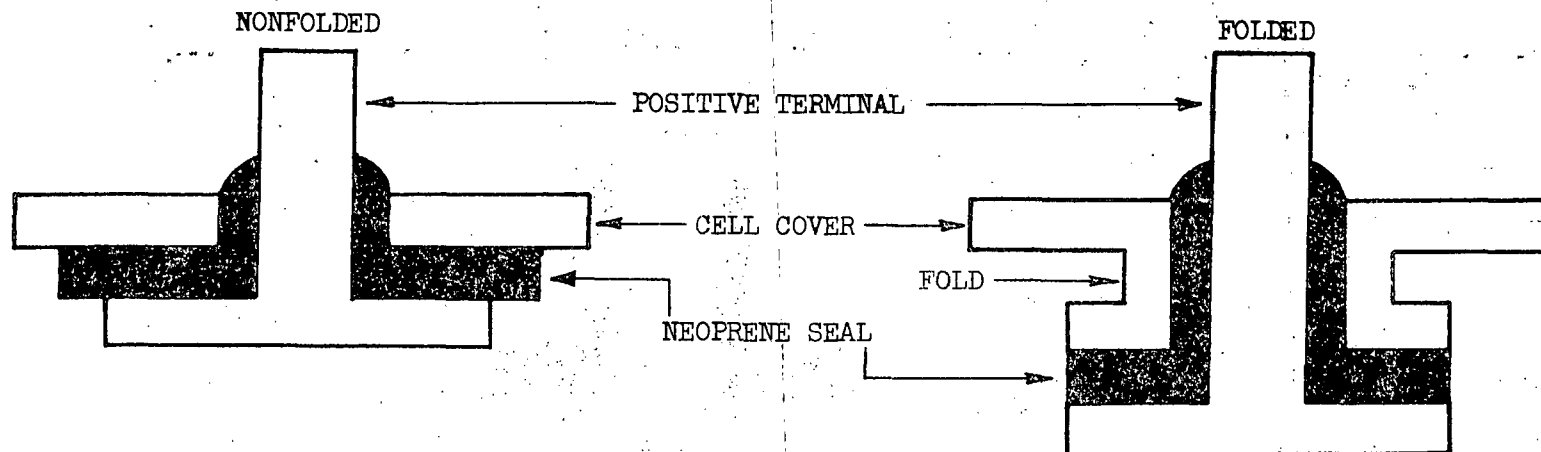

CROSS SECTION OF NEOPRENE SEAL


FIGURE 13

```

KEY  AVERAGE CELL VOLTAGE
*----MIDDLE DISCHARGE
+----END OF DISCHARGE
.----END OF CHARGE
X----PERCENT RECHARGE

```

PACK 0448	MANF. GULTON	05.6 AH
ORBIT PERIOD HOURS	01.5	
TEMP. DEGREES C.	-20	
CHARGE RATE AMPS	1.61	
DEPTH OF DISCHARGE %	25	

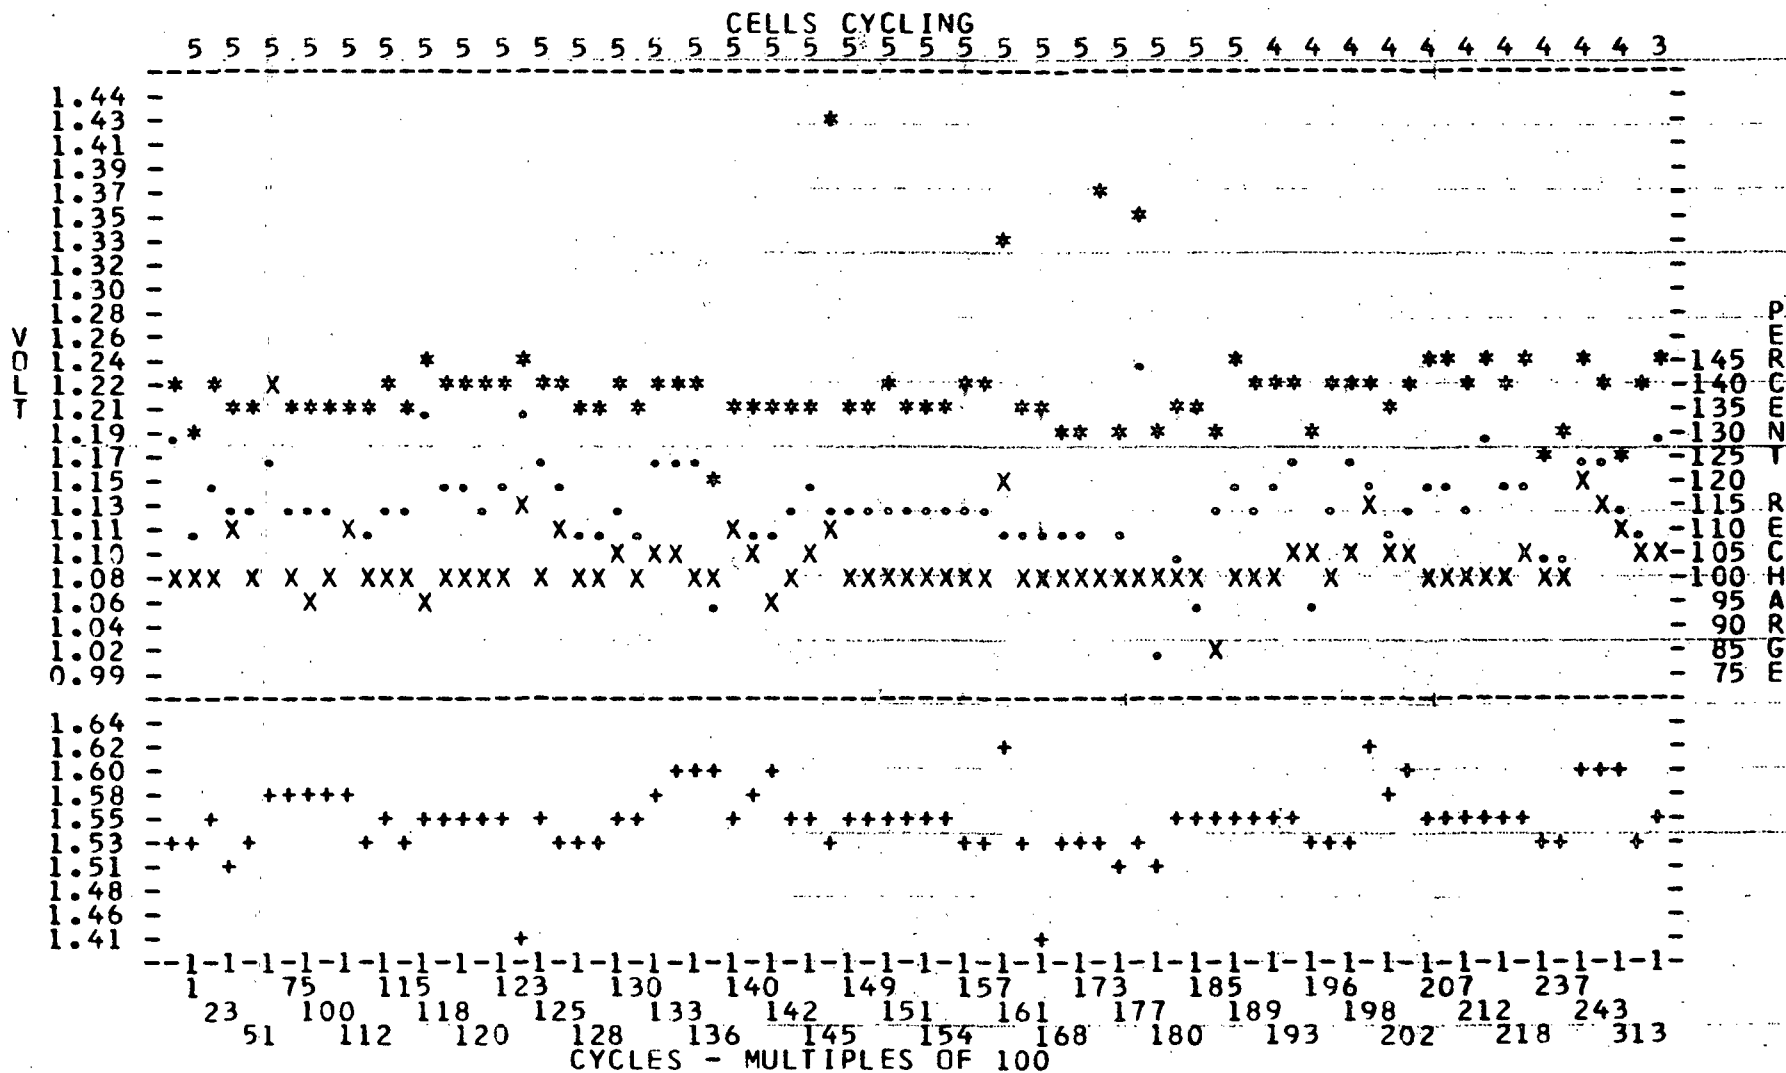

PACK 1008	MANF. GULT
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	1.61
DEPTH OF DISCHARGE %	25

05.6 AH

[illegible]

PERCENTAGE OF

CYCLES - MULTIPLES OF 100
FIGURE 20

43

PACK 090C	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	1.61
DEPTH OF DISCHARGE %	25

05.6 AH

[illegible]

6. Gulton 6.0 ah (Improved), Three 5-cell Packs:

a. Cell Description: The cells are rectangular in shape. The cell container and the cell cover are made of stainless steel. The positive terminal is insulated from the cell cover by a ceramic seal, while the negative terminal is welded to the cover. Both are solder type terminals. The silver braze of the ceramic seal is nickel plated to prevent internal cell shorting by silver migration to the cover.

b. Parameters and Capacity Checks:

Orbit Period		1.5-hour		
Temperature		0°	25°	40°
Depth of Discharge		25%	40%	25%
Pack Number		13B	18B	38B
Precycling Capacity		7.30	6.90	5.00
88 Days	Disch #2	6.95	3.00	1.75
264 Days	Disch #2	7.20	3.80 F	1.50 F
440 Days	Disch #2	6.75		
616 Days	Disch #2	*		
792 Days	Disch #2	6.25		
968 Days	Disch #2	5.15		
1144 Days	Disch #2	4.80		
1320 Days	Disch #2	4.15		
1496 Days	Disch #2	*		
1672 Days	Disch #2	4.00		
1848 Days	Disch #2	3.90		
2024 Days	Disch #2	3.55		
2200 Days	Disch #2	3.74 F		

* Capacity Check Not Performed.
F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figure 22) Cycling started in February 1965. Packs 18B, 38B, and 13B failed on cycles 7577, 5766, and 37,650, respectively.

(2) Failure Analysis: Failure analysis of nine cells showed the major causes of failure to be separator deterioration and migration of the negative plate material. Other conditions found were blistering on the positive plates, ceramic shorts, burned positive tabs, electrolyte leakage, high internal pressure, and corrosive deposits internally underneath the positive terminal.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 0138 MANF. GULTON
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 1.73
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1

CELLS CYCLING
 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 4 4 4 4 4 4 4 4 4 4 3 3 3 3

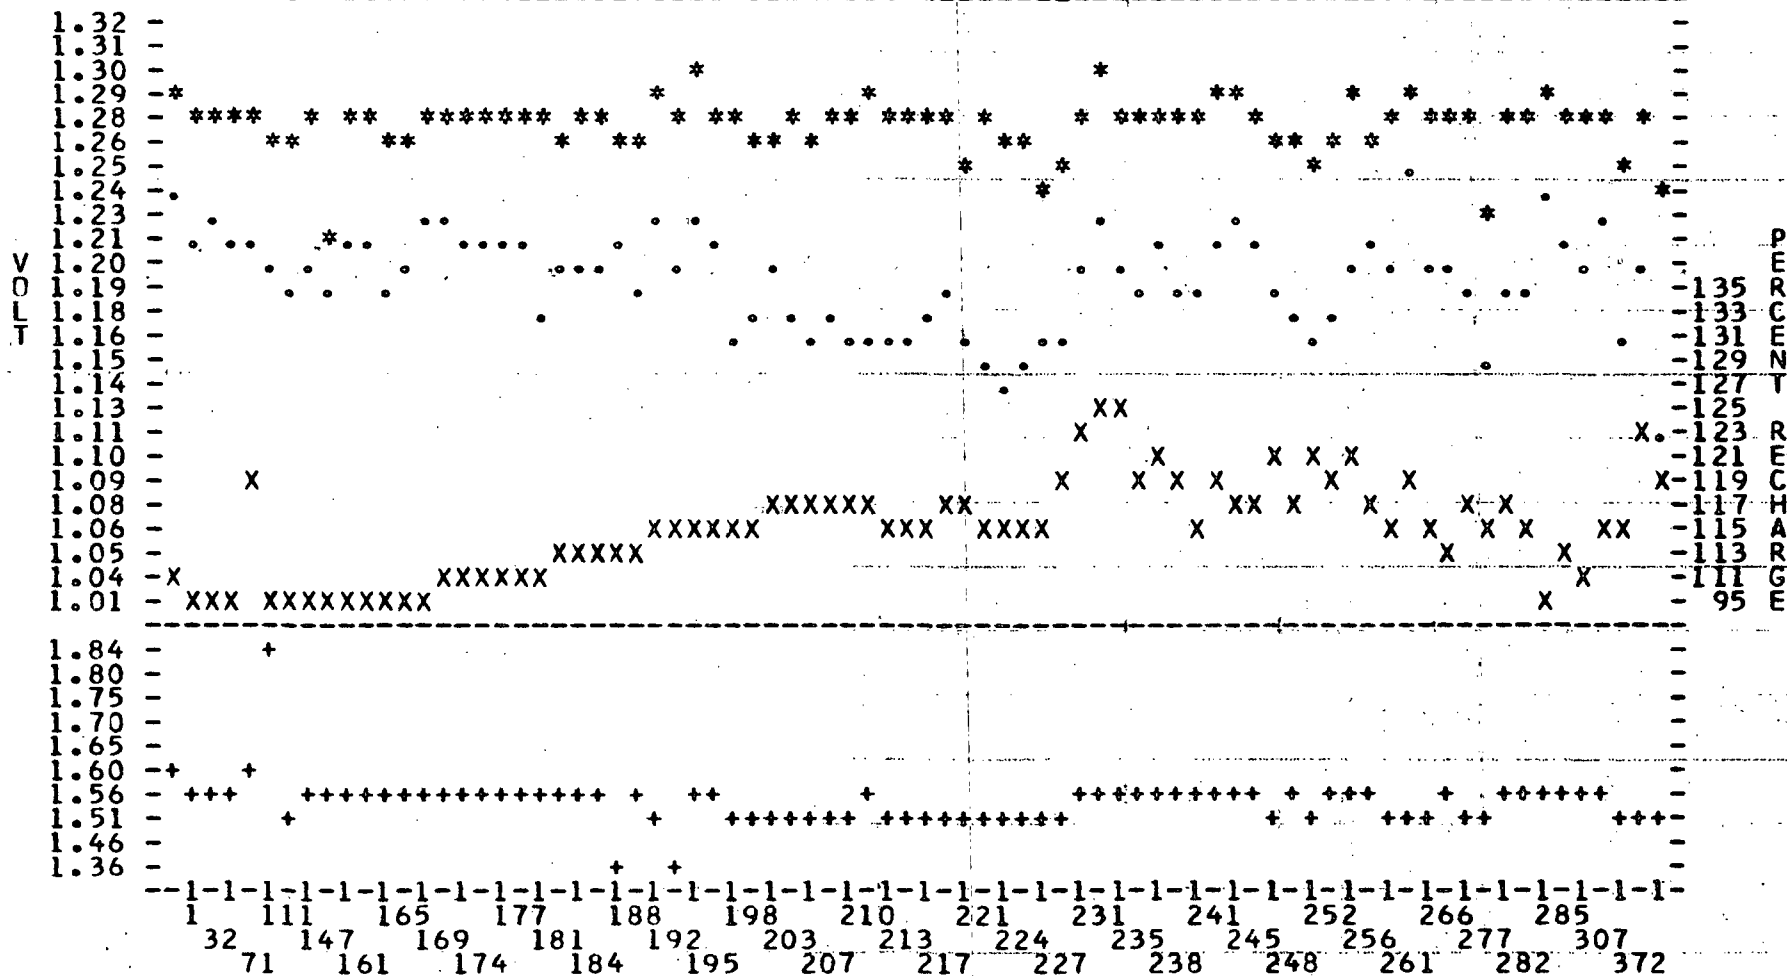


FIGURE 22

7. Gulton 6.0 ah, One 10-cell Pack (Pack 61B):

a. Cell Description: These cells are rectangular in shape. The cell container and the cell cover are made of stainless steel. The positive terminal is insulated from the cell cover by a ceramic seal, while the negative terminal is welded to the cover. Both are solder type terminals.

b. Test Parameters:

(1) Initial Test Parameters (at another test facility):

(a) Test Temperature: -10°C .

(b) Depth of Discharge: 10%.

(c) Orbit Period: 1.5 hour.

(2) Change in Test Parameters: The test temperature was raised to 0°C after 22,900 cycles at -10°C at another test facility.

c. Parameters and Capacity Checks:

Orbit Period	1.5-hour
Temperature	0°
Depth of Discharge	10%
Pack Number	61B
Precycling Capacity	5.30
88 Days Disch #2	5.40
264 Days Disch #2	5.45
440 Days Disch #2	4.70
616 Days Disch #2	3.75
792 Days Disch #2	3.40
968 Days Disch #2	2.46
1144 Days Disch #2	3.45

Orbit Period	1.5-hour
Temperature	0°
Depth of Discharge	10%
Pack Number	61B
Precycling Capacity	5.30
1320 Days Disch #2	2.45
1496 Days Disch #2	2.76

d. Test Results:

(1) Performance on Cycling: (Figure 23) Cycling started at NAD Crane in June 1967. This pack has completed 24,890 additional cycles at 0° C with one cell failure. Failure analysis was not performed because of possible swelling of other cells if this cell was removed.

(a) The end of discharge voltage is 1.27 volts per cell and the percent of recharge is approximately 105 percent.

PACK 0618	MANF.	GULT
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		00
CHARGE RATE AMPS		0.66
DEPTH OF DISCHARGE %		10

06.0 AH

[illegible]

RECREATION

CYCLES - MULTIPLES OF 100

FIGURE 23

50

8. Gulton 6.0 ah, One 10-cell Pack, 1.5-hour Orbit Period (Pack 51B):

a. Cell Description: Four of the 10 cells are from the same lot of cells used for the Test and Training (TETR) satellite. These four cells are TETR-B type cells and the other six are RAE type cells. All cells fit the general description of paragraph 1.A., page 19.

b. Test Parameters:

(1) Cycling Test Parameters:

(a) Test Temperature: 20° C.

(b) Discharge Current: 0.10 amperes.

(c) Charge Current: 0.30 amperes.

(2) Special Test: At random times the cycling had a 1.5-ampere discharge superimposed upon the regular cycle. This was done to simulate the type of operation encountered by the TETR Satellite.

c. Test Results:

(1) Performance on Cycling: (Figure 24) Cycling started in February 1969. This pack has completed 15,846 cycles. The 1.5-ampere discharge has been superimposed on the regular cycling condition at random times and for various lengths of time to simulate the conditions encountered in space. Limiting conditions were encountered on the four cells from the TETR satellite, indicating a deficiency in these cells; thus permitting the TETR project office to predict the performance that could be expected from the satellite. Because of the simulation of the satellite performance, no capacity checks are run on these cells.

(2) Five of the RAE type cells were replaced with TETR-C type cells in February 1970.

PACK 0518 M
ORBIT PERIOD HOURS
TEMP. DEGREES C.
CHARGE RATE AMPS
DEPTH OF DISCHARGE

MANF. GULTON 06.0 AH
RS 01.5
20
0.30
GE % .8

[illegible]

9. Gulton 12.0 ah (OGO), Six 5-cell Packs:

a. Cell Description: See paragraph I.A., page 19.

b. Parameters and Capacity Checks:

Orbit Period		1.5-hour					
Temperature		0°	0°	25°	25°	40°	40°
Depth of Discharge		15%	25%	25%	40%	15%	25%
Pack Number		16B	101B	27B	96B	78A	90B
Precycling Capacity		14.86	14.20	14.10	13.30	6.80	11.40
88 Days	Disch #2	13.50	14.50	5.90	3.20	4.30	5.40
264 Days	Disch #2	14.20	12.90	4.10	5.00 F	3.30	3.70 F
440 Days	Disch #2	13.70	11.90	4.80		3.40	
616 Days	Disch #2	13.10	10.60	4.00		5.30 F	
792 Days	Disch #2	12.70	9.00	3.90 F			
968 Days	Disch #2	11.80	9.00				
1144 Days	Disch #2	11.50	8.80				
1320 Days	Disch #2	10.50	8.10				
1496 Days	Disch #2	10.30	7.80				
1672 Days	Disch #2	9.00	8.00				
1848 Days	Disch #2	10.20	7.68				
2024 Days	Disch #2	9.50	6.78				
2200 Days	Disch #2	9.20	6.20 F				

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figures 25 and 26)
Cycling was started in January 1966. Pack 16B has completed 38,461 cycles with no cell failures. Packs 27B, 96B, 78A, 90B, and 101B failed on cycles 14,250, 5152, 11,081, 5124, and 38,110, respectively.

(2) Failure Analysis: Analysis of the 16 failed cells showed the major cause of failure to be separator deterioration and migration of the negative plate material. Other conditions found were high internal pressure, blistering on the positive plates, electrolyte leakage, extraneous active material and external carbonate deposits on the negative terminal.

PACK 016B	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	2.07
DEPTH OF DISCHARGE %	15

12.0 AH

5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5



CYCLES - MULTIPLES OF 100

FIGURE 25

55

QEEL/C 72-1

CELLS CYCLING



10. Gulton 20 ah (OAO), One 10-cell Pack:

a. Cell Description: See paragraph I.A., page 19.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour
Temperature	10°
Depth of Discharge	15%
Pack Number	23B
88 Days	22.1


c. Test Results:

(1) Performance on Cycling: (Figure 27) Cycling was started in February 1971. The pack has completed 4919 cycles with no failures.

(2) Capacity Checks: After the first capacity check this pack was placed on a special schedule in which approximately every 5 months two different cells will receive a capacity check; and at the end of 2 years, when cells 9 and 10 are scheduled, the whole pack will receive the capacity check.

PACK 023B	MANF. GULT
ORBIT PERIOD HOURS	1.5
TEMP. DEGREES C.	15
CHARGE RATE AMPS	8.00
DEPTH OF DISCHARGE %	10

MANF. GULTON 20.0 AH

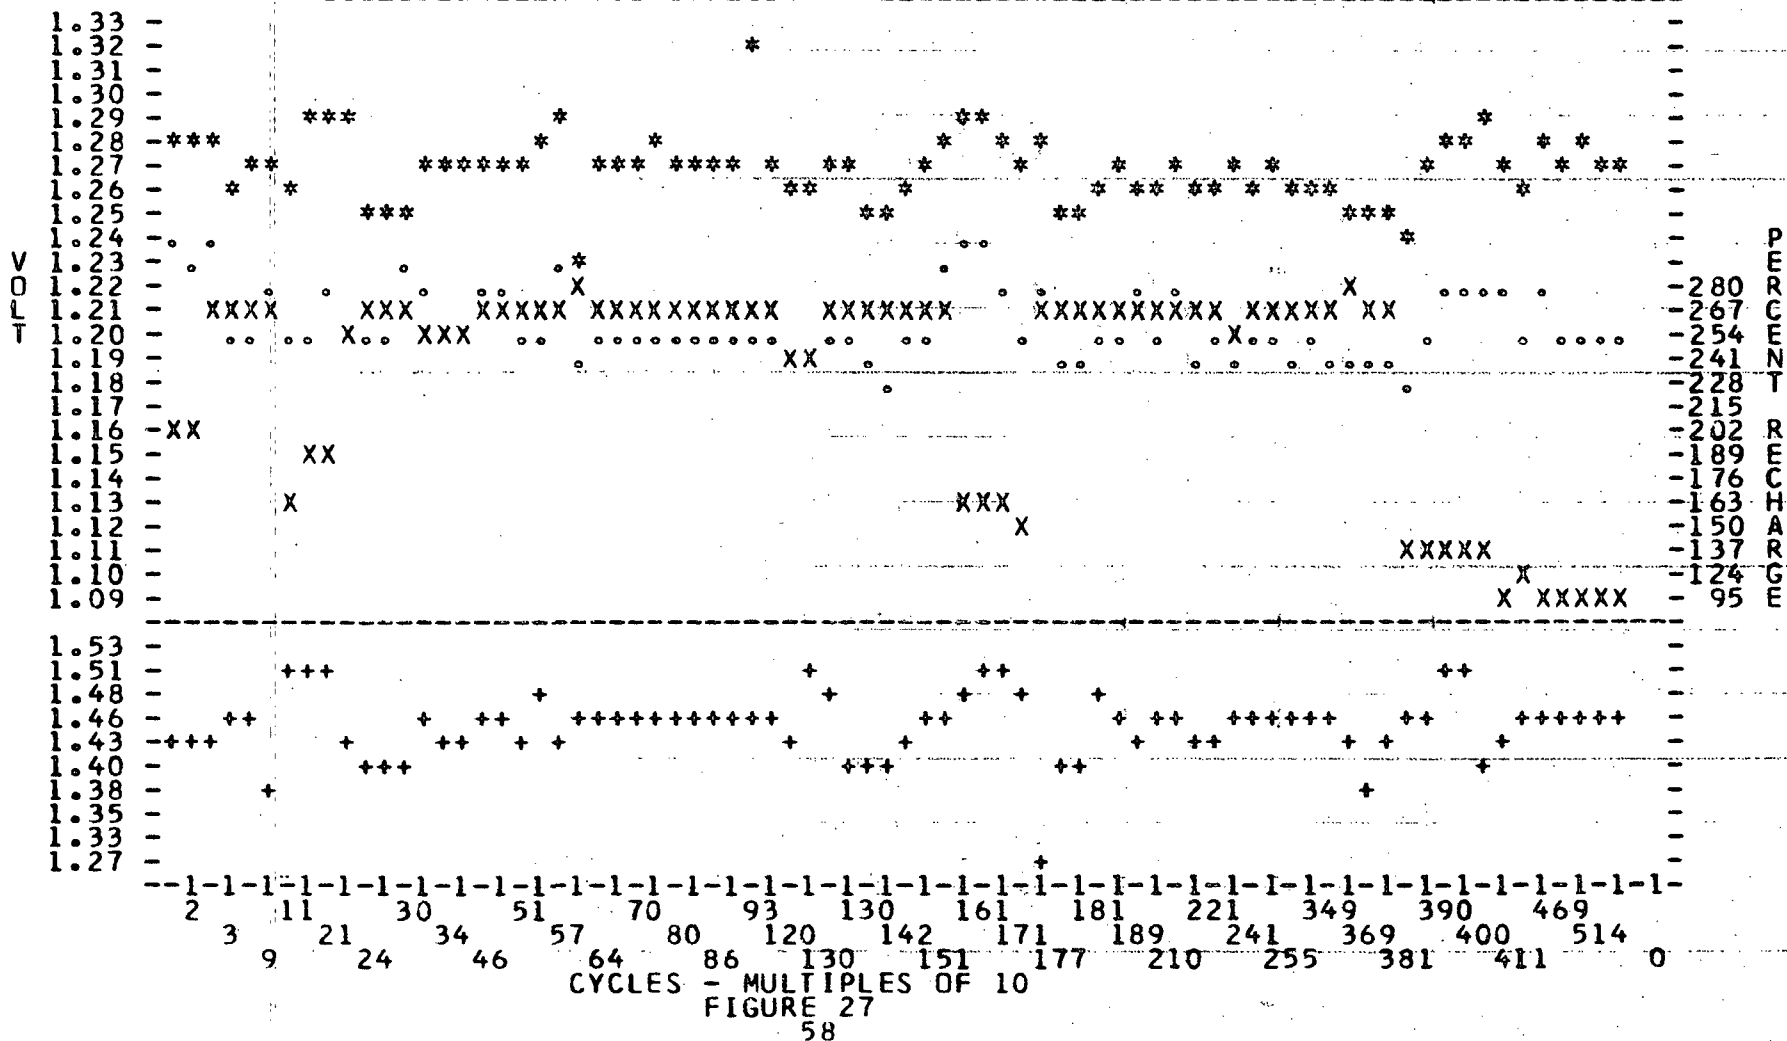[illegible]

11. GE 5.0 ah (NIMBUS), Six 5-cell Packs:

a. Cell Description: These cells are cylindrical with a convex base. A threaded stud is fastened to the base to facilitate heat sink mounting. The cell container and the cell cover are made of stainless steel. Two stainless steel tabs, welded to the cover, serve as the contacts for the negative terminal. The positive terminal is insulated from the cell cover by a ceramic bushing and protrudes through the bushing with a solder tab welded to the terminal. Three cells have pressure transducers mounted on the cell to read internal pressure in pounds per square inch absolute. These cells were manufactured to NIMBUS specifications.

b. Parameters and Capacity Checks:

Orbit Period		1.5-hour					
Temperature		0°	0°	25°	25°	40°	40°
Depth of Discharge		15%	25%	15%	25%	15%	25%
Pack Number		103A	107A*	106A	104B*	113A	114A*
Precycling Capacity		5.42	5.21	4.67	5.58	3.67	3.83
88 Days	Disch #2	5.08	5.50	4.00	3.58	2.42	2.25
264 Days	Disch #2	5.58	5.33	3.50	1.75	1.83	1.63
440 Days	Disch #2	5.54	5.42	3.08	2.00	F	1.00
616 Days	Disch #2	4.75	4.58	3.25	1.83	F	F
792 Days	Disch #2	5.08	5.25	3.13			
968 Days	Disch #2	5.17	4.46	2.92			
1144 Days	Disch #2	5.08	4.21	2.58			
1320 Days	Disch #2	4.75	4.42	2.46			
1496 Days	Disch #2	4.67	4.37	1.21			
1672 Days	Disch #2	4.29	4.21				

* One cell in each pack is equipped with a pressure transducer.
F - Failed.

Orbit Period		1.5-hour				
Temperature		0°	0°	25°	25°	40°
Depth of Discharge		15%	25%	15%	25%	15%
Pack Number		103A	107A*	106A	104B*	113A
1848 Days	Disch #2	4.42	1.33			114A*
2024 Days	Disch #2	4.33	3.58			
2200 Days	Disch #2	4.75	2.70			

* One cell in each pack is equipped with a pressure transducer.
F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figures 28 and 29)

Cycling was started in May 1965. Packs 103A and 107A have completed 37,545 and 36,914 cycles, respectively with two cell failures in pack 107A. Packs 106A, 104B, 113A and 114A failed on cycles 26,148, 13,149, 4988 and 8273, respectively.

(2) Failure Analysis: Analysis of the 14 failed cells showed the major causes of failure to be separator deterioration and migration of the negative plate material. Other conditions found were high internal pressure, electrolyte leakage, pierced separator by the negative tab, blistering on the positive plates and corrosive deposits internally at the positive terminals. In addition to the above failures one pack of five cells was destroyed by thermal runaway caused by the shorting of the positive tab to the top edge of the negative plate. This happened because the insulating material wrapped around the positive tab came loose. In order to prevent a recurrence of this problem in the flight battery a piece of insulating tubing was used to cover the positive tab.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 o-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 103A MANF. GE
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 0.83
 DEPTH OF DISCHARGE % 15

QEEL/C. 72-1
 05.0 AH

CELLS CYCLING

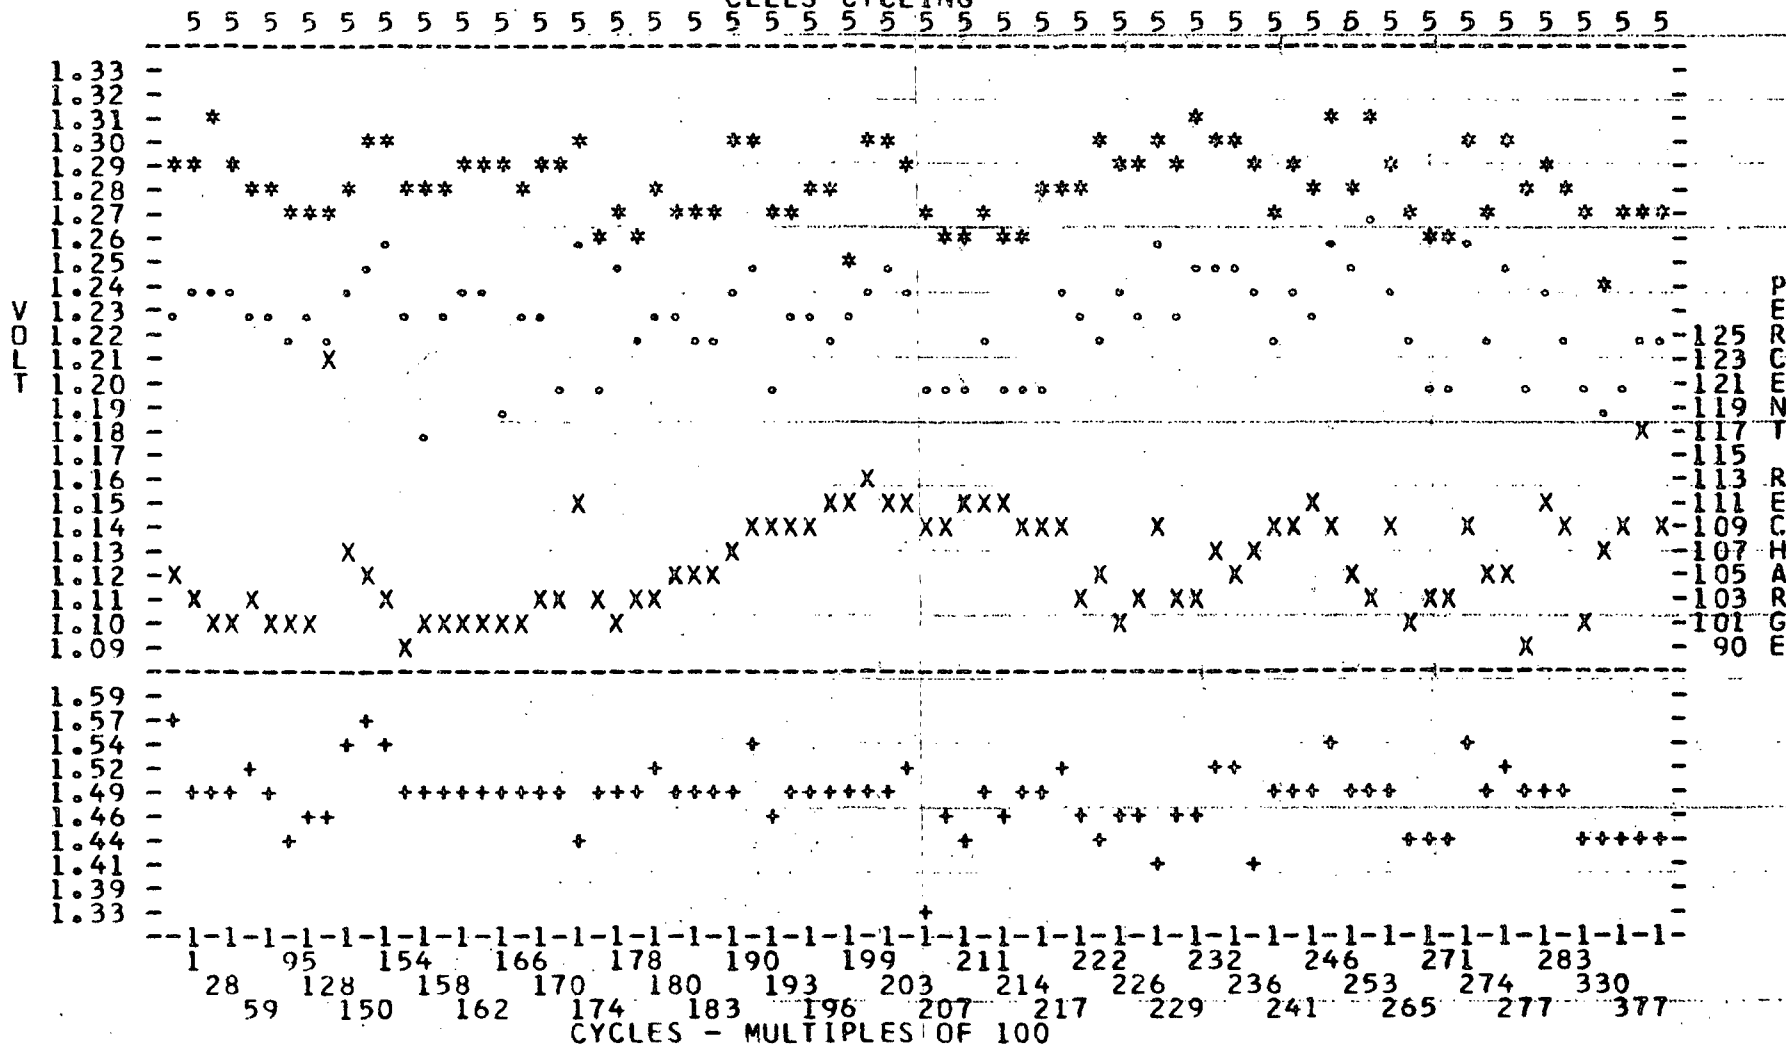


FIGURE 28

PACK 107A	MANF. GE
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	1.38
DEPTH OF DISCHARGE	25

CELLS CYCLING



12. GE 6.0 ah (Nickel-Braze), Eight 5-cell Packs:

a. Cell Description: The cell case fits the description of all nickel-cadmium stainless steel cases. The ceramic to metal seal has an all nickel braze construction to eliminate ceramic shorting through silver migration.

b. Parameters and Capacity Checks:


Orbit Period (Hrs)	1.5	1.5	1.5	1.5	24	24	24	24
Temperature	-20°	0°	20°	40°	-20°	0°	20°	40°
Depth of Discharge	25%	25%	25%	25%	60%	60%	60%	60%
Pack Number	81B	92B	95B	106B	75E	123B	109B	91B
88 Days	2.46	6.90	6.99	2.25				
264 Days	2.61	4.71	8.64	2.34				

c. Test Results:

(1) Performance on Cycling: (Figures 30 through 37)
Cycling was started in March 1971. Packs 81B, 92B, 95B and 106B have completed 3784, 4370, 4404 and 4382 cycles, respectively, with one cell, each, removed from packs 95B and 106B and shipped to Goddard Space Flight Center as instructed by that activity. Packs 75E, 123B, 109B and 91B have completed 272, 265, 279 and 281 cycles, respectively, with no failures or cell removals to date.

PACK 081B	MANF. GE
ORBIT PERIOD HOURS	1.5
TEMP. DEGREES C.	-20
CHARGE RATE AMPS	3.00
DEPTH OF DISCHARGE	3 25

6.00 AH QEEL/C 72-1

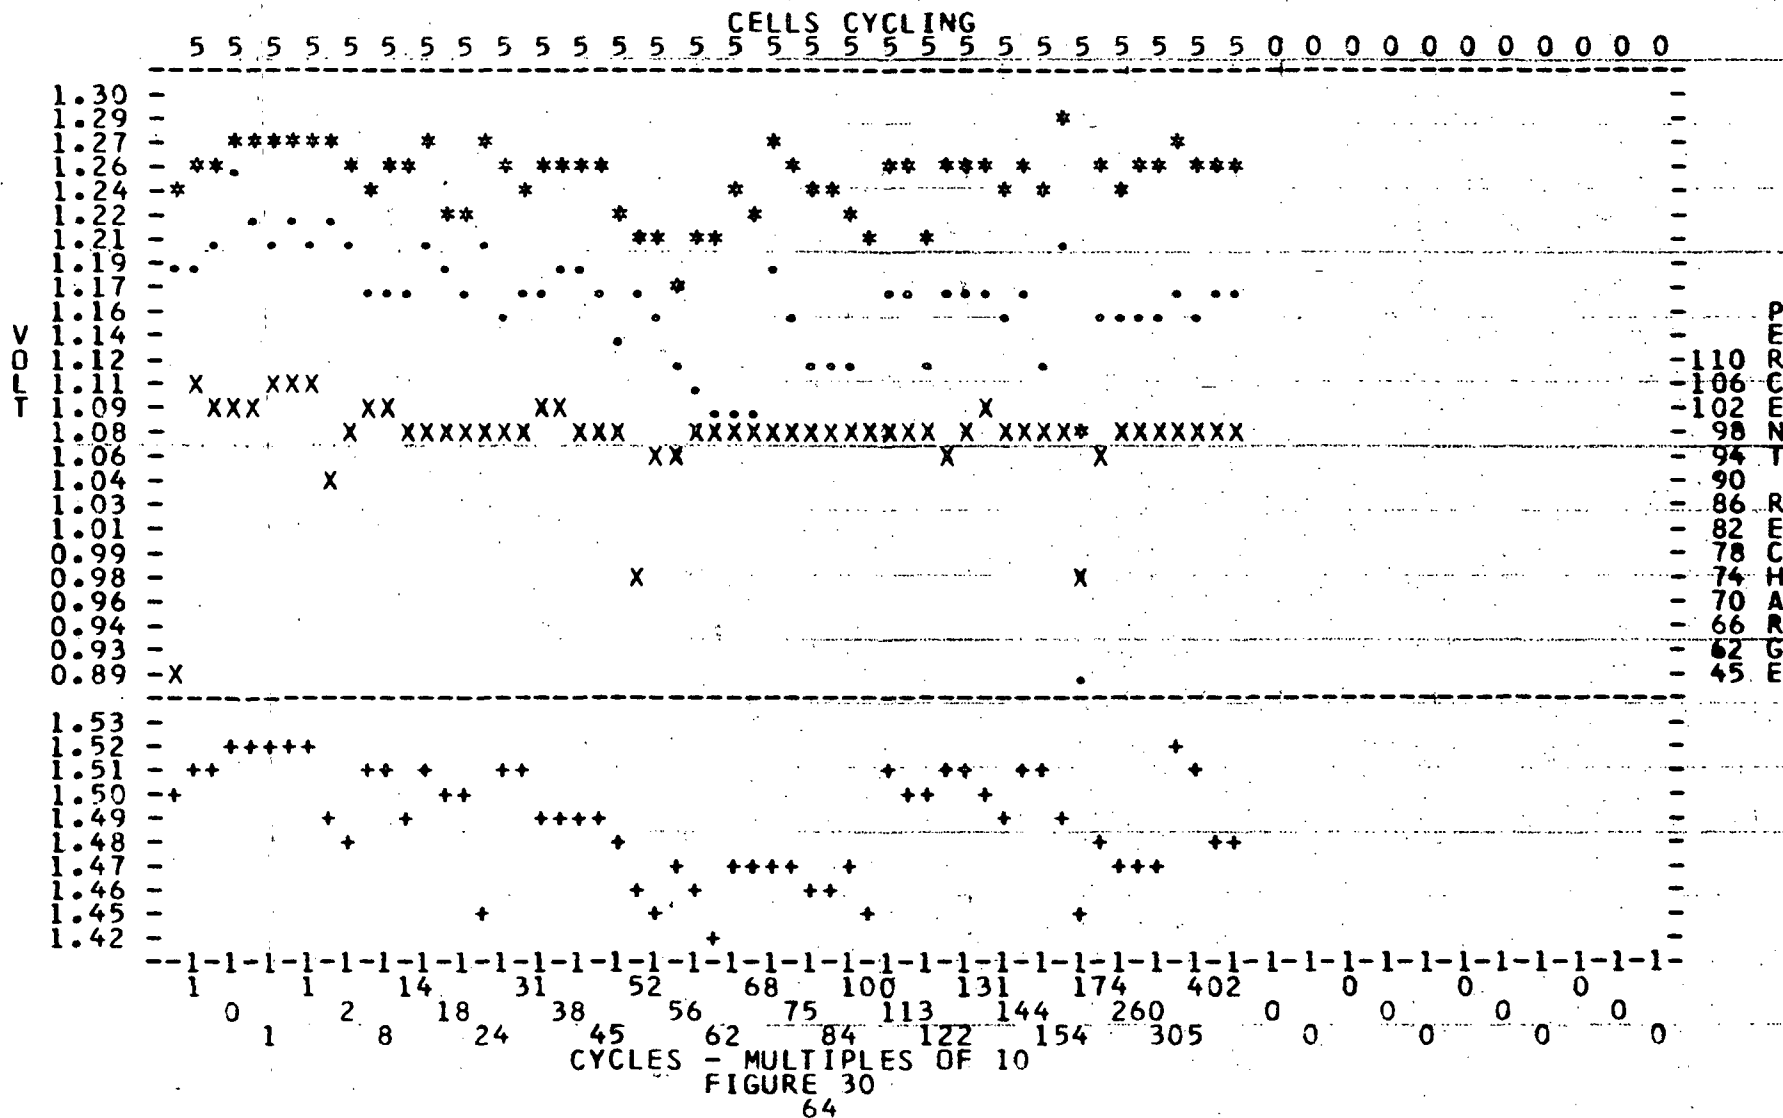

6.00 QEEL/C 72-1
AH

5 5 5 5 5 5 5 5 5 5 5 5 5 1 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 0 0 0 0 0 0 0




PACK 095B	MANF. GE
ORBIT PERIOD HOURS	1.5
TEMP. DEGREES C.	20
CHARGE RATE AMPS	3.00
DEPTH OF DISCHARGE %	25

DEPTH OF DISCHARGE % 25



PACK 075E	MANF. GE
ORBIT PERIOD HOURS	4.0
TEMP. DEGREES C.	-20
CHARGE RATE AMPS	0.30
DEPTH OF DISCHARGE %	60

CELLS CYCLING

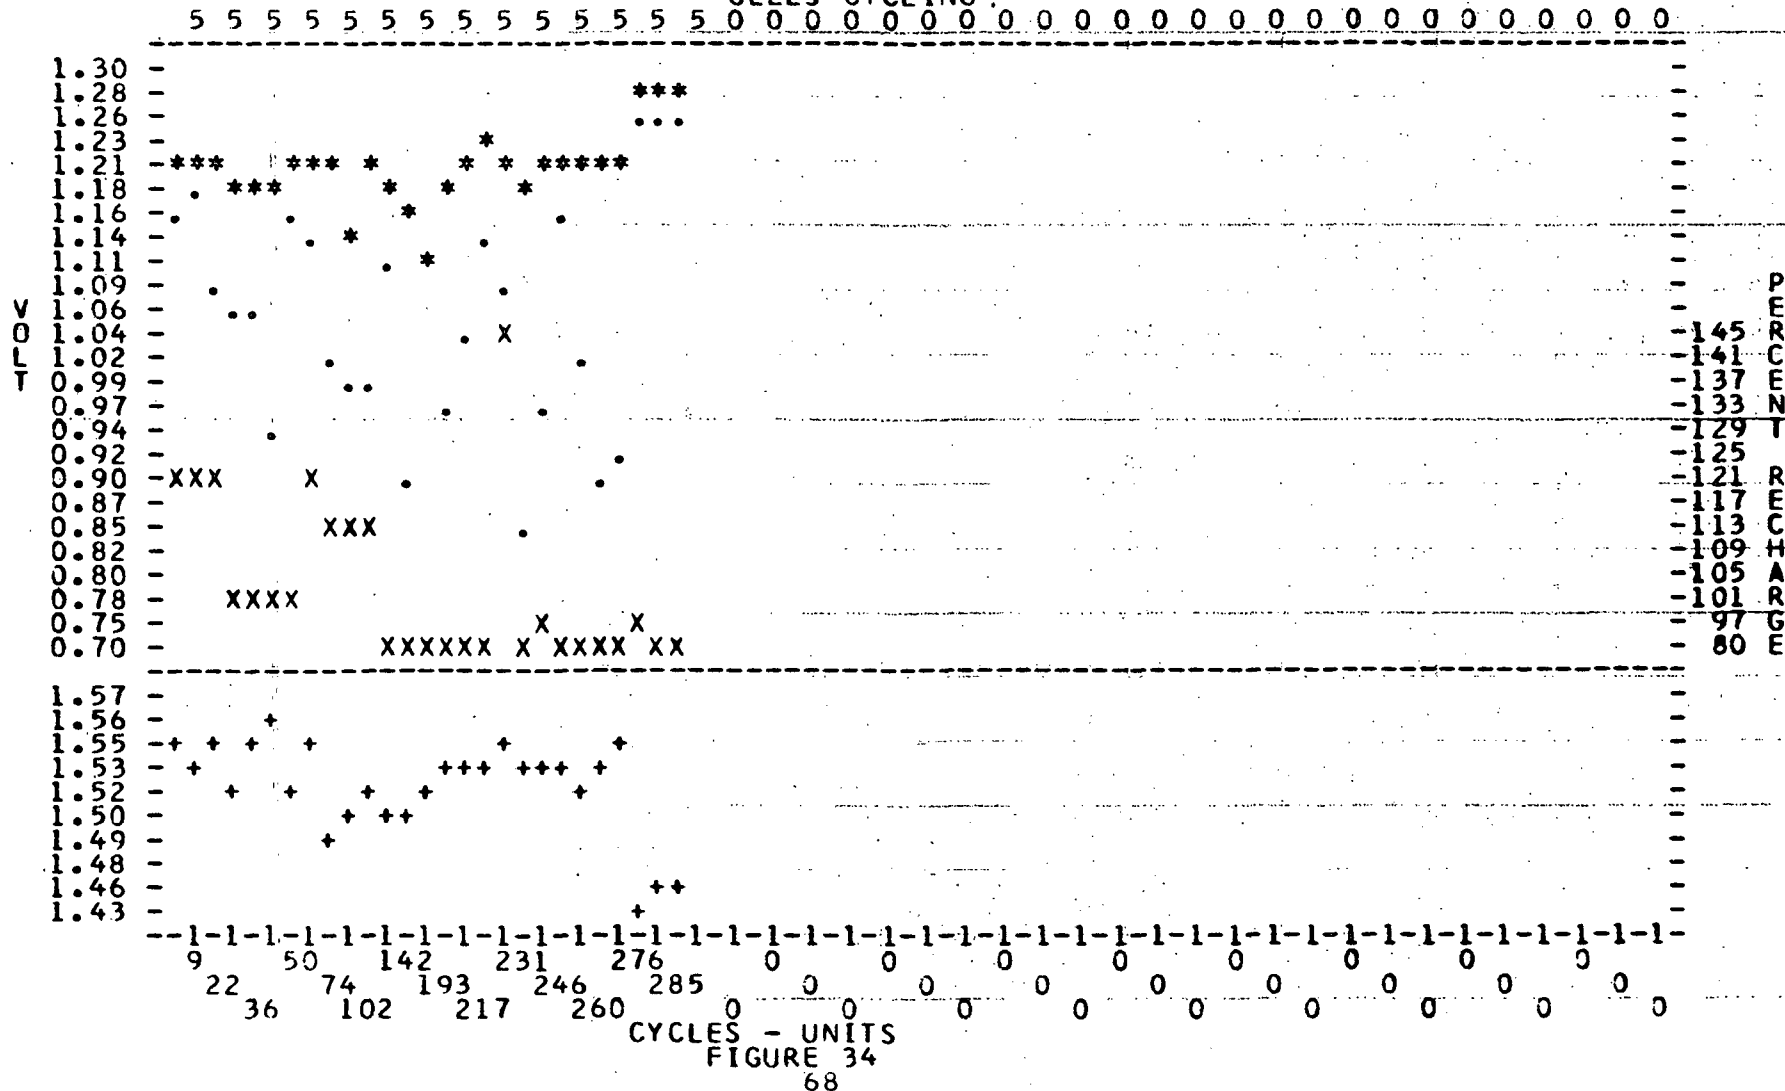

```

#-----MIDDLE DISCHARGE
*-----END OF DISCHARGE
+-----END OF CHARGE
X-----PERCENT RECHARGE

```

ORBIT PERIOD HOURS

4.0

TEMP. DEGREES C.

00

CHARGE RATE AMPS

0.30

DEPTH OF DISCHARGE %


60

QEEL/C 72-1

6.00 AM


CELLS CYCLING

5 5 5 5 5 5 5 5 5 5 5 5 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0

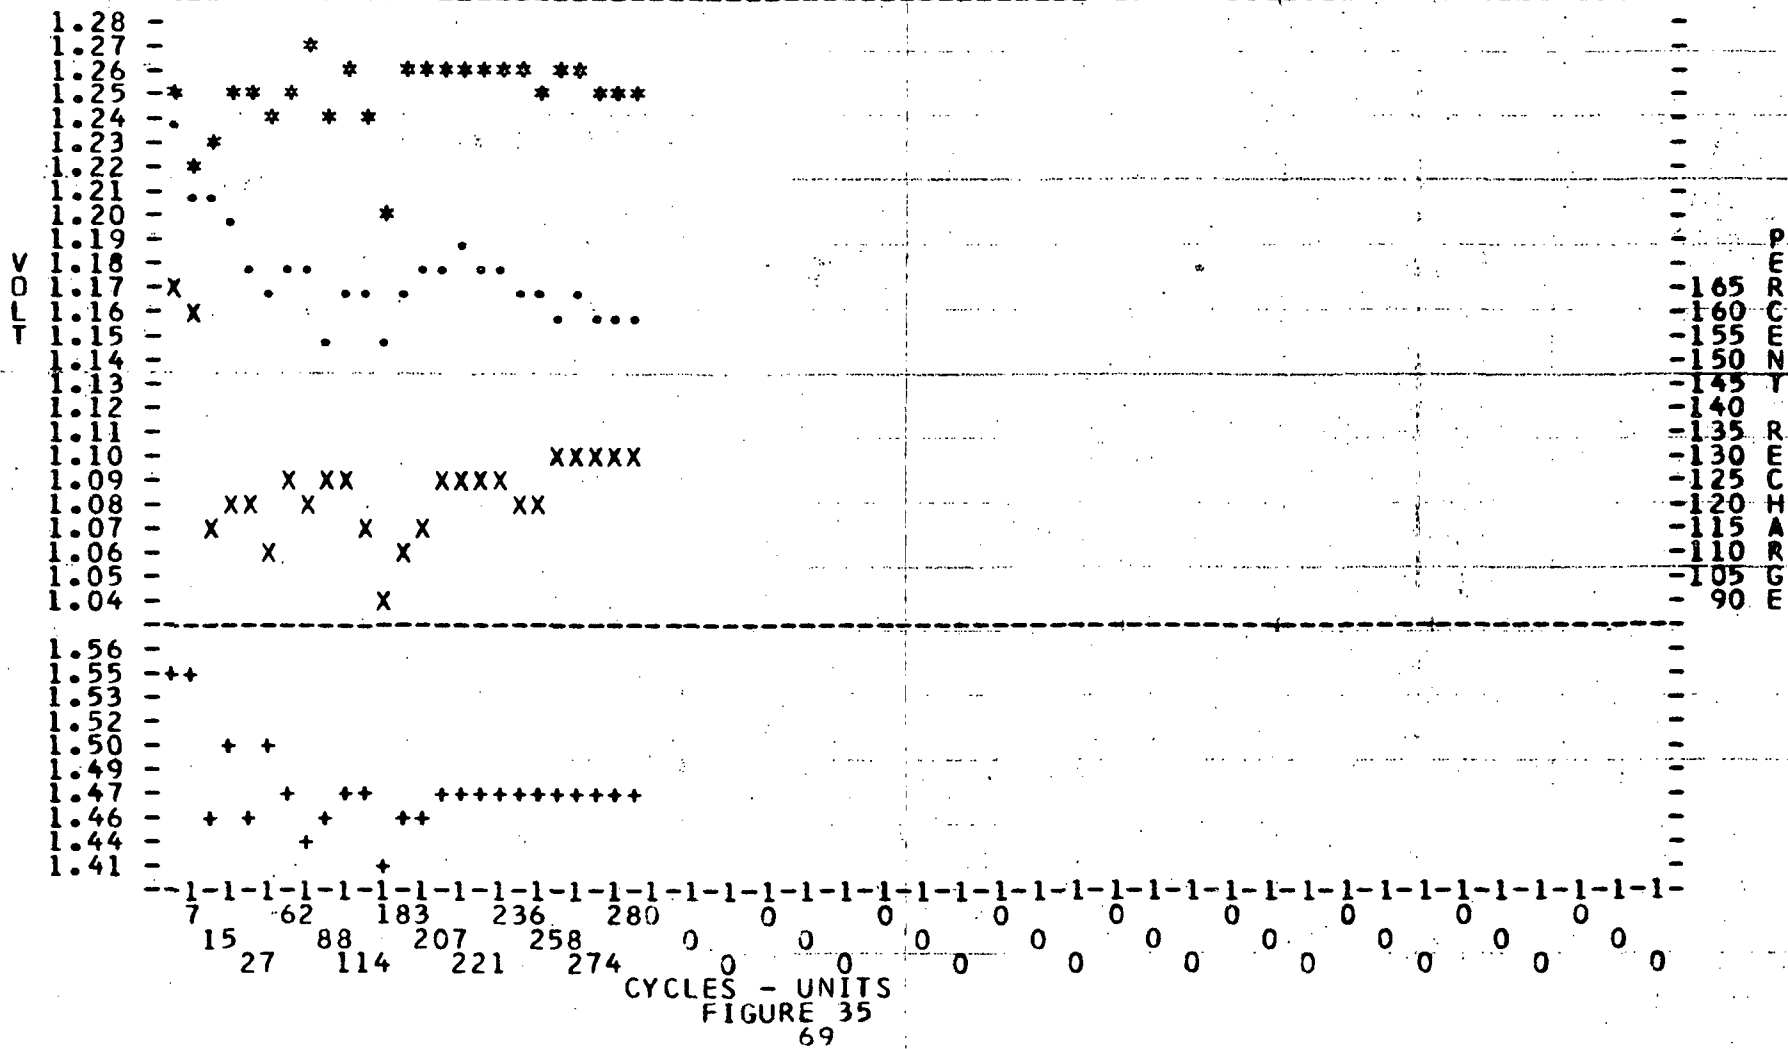

PACK 109B	MANF. GE
ORBIT PERIOD HOURS	4.0
TEMP. DEGREES C.	20
CHARGE RATE AMPS	0.30
DEPTH OF DISCHARGE %	60

CELLS CYCLING



```
*-----MIDDLE DISCHARGE
.------END OF DISCHARGE
+-----END OF CHARGE
X-----PERCENT RECHARGE
```

ORBIT PERIOD HOURS

4.0

6.00 AH

TEMP. DEGREES C.

40

CHARGE RATE AMPS


0.30

DEPTH OF DISCHARGE %

60

CELLS CYCLING

5 5 5 5 5 5 5 5 5 5 5 5 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0

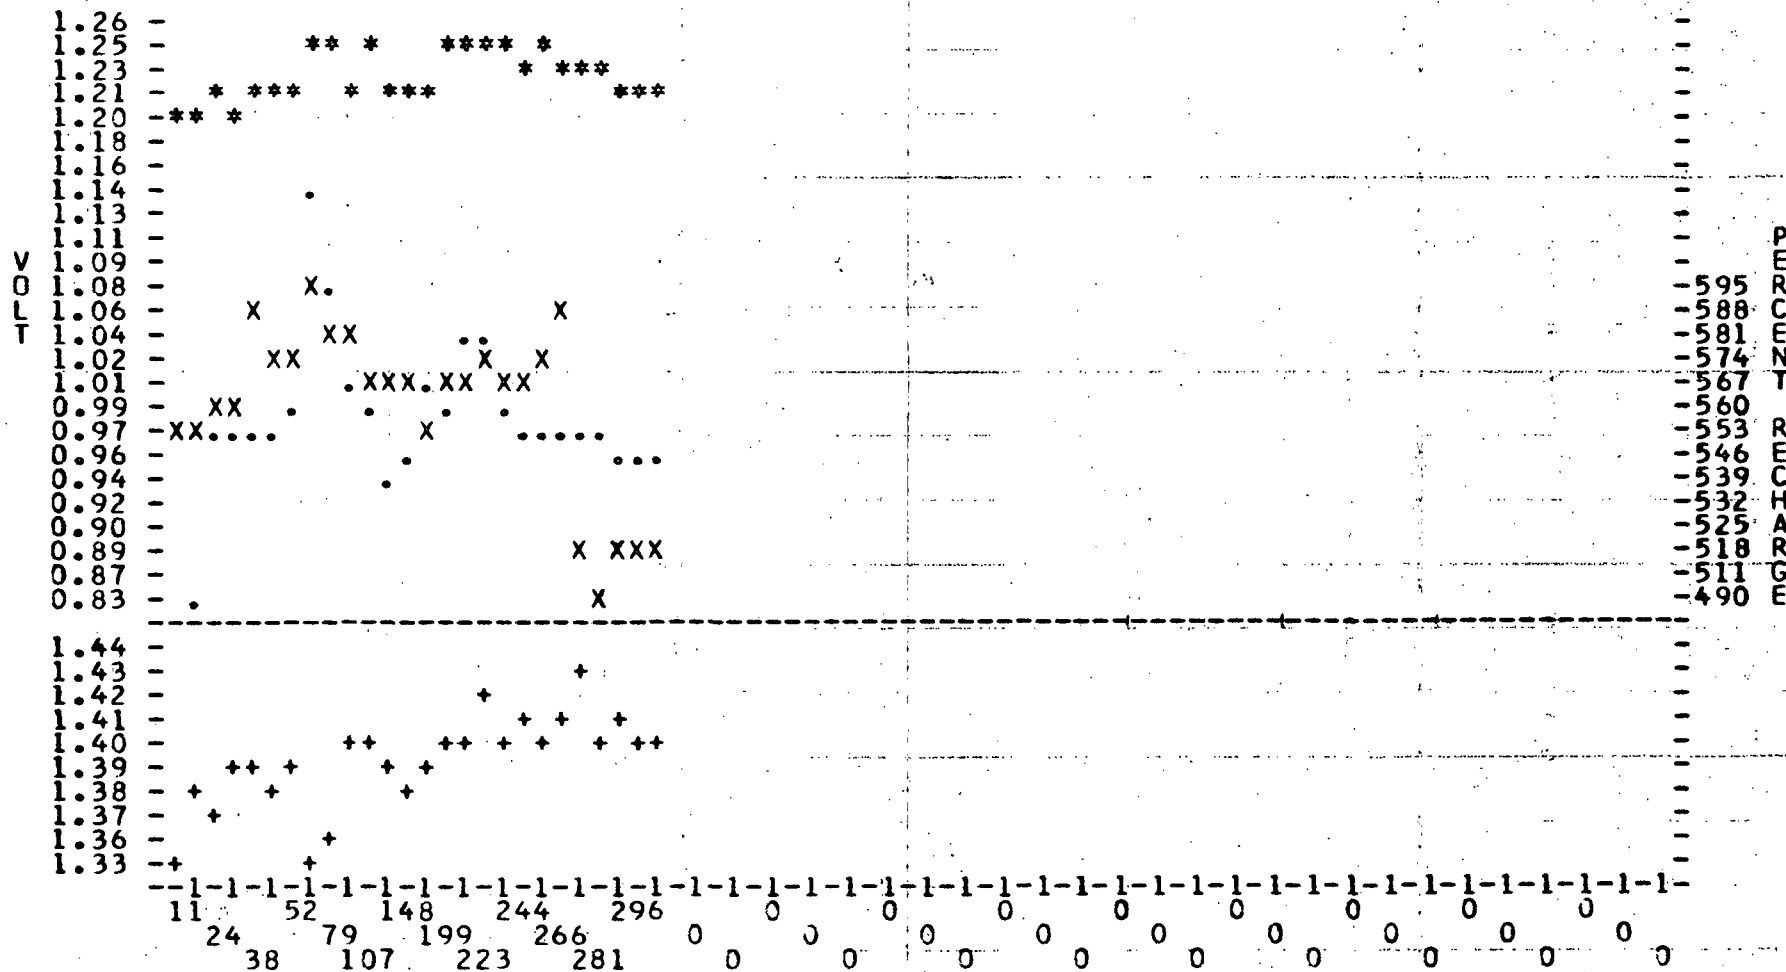

CYCLES - UNITS
FIGURE 37

13. Sonotone 3.0 ah (Triple Seal), Six 5-cell Packs:

a. Cell Description: The cell container and the cell cover of these cylindrical cells are made of stainless steel. Two stainless steel tabs, welded to the cover, serve as the contacts for the negative terminal. The positive terminal is a solder type extension of the positive plate tab extending through the "negative" cover and insulated by a ceramic seal between two glass to metal seals to form a triple seal. Two ring indentations, about 1/32 inch deep, located about 1/2 inch from each end of the cell, were crimped after cell assembly to hold the element snugly in the cylindrical can to withstand vibration.

b. Parameters and Capacity Checks:

Orbit Period		1.5-hour					
Temperature		0°	0°	25°	25°	40°	40°
Depth of Discharge		15%	25%	25%	40%	15%	25%
Pack Number		43B	31B	3B	2B	26B	37B
Precycling Capacity		3.23	2.88	3.35	3.60	3.53	3.48
88 Days	Disch #2	3.55	3.05	1.40	1.32	1.10	1.05
264 Days	Disch #2	2.63	2.67	1.50	1.62	0.90	1.05
					F	F	F
440 Days	Disch #2	3.27	2.12	1.28			
616 Days	Disch #2	3.00	2.67	1.30			
				F			
792 Days	Disch #2	2.50	2.37				
968 Days	Disch #2	2.32	2.27				
1144 Days	Disch #2	2.10	2.10				
1320 Days	Disch #2	2.35	1.85				
1496 Days	Disch #2	2.70	1.95				
1672 Days	Disch #2	2.37	1.37				
			F				

F - Failed.

Orbit Period		1.5-hour				
Temperature	0°	0°	25°	25°	40°	40°
Depth of Discharge	15%	25%	25%	40%	15%	25%
Pack Number	43B	31B	3B	2B	26B	37B
1848 Days	Disch #2	2.30				
2024 Days	Disch #2	2.40				
2200 Days	Disch #2	2.10				

c. Test Results:

(1) Performance on Cycling: (Figure 38) Cycling was started in July 1965. Pack 43 B has completed 36,011 cycles with one cell failure. Packs 31B, 3B, 2B, 26B and 37B failed on cycles 28,074, 11,726, 5399, 6289, and 5625, respectively.

(2) Failure Analysis: Analysis of the 16 failed cells showed that the major causes of failure were due to separator deterioration, migration of negative plate material and excessive scoring. Other conditions found were weak positive tab-to-plate welds, electrolyte leakage, pierced separator by grid wires and plate tabs, high internal pressure and loosened positive active material.

PACK 043B	MANF. SONOTONE03.0 AH
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	0.52
DEPTH OF DISCHARGE %	15

CELLS CYCLING



14. Sonotone 3.5 ah, One 10-cell Pack:

a. Cell Description: These are cylindrical cells made of stainless steel. One stainless steel tab is welded to the cover for the negative connection. The positive terminal is an extension of the positive tab and is insulated from the negative cover by a ceramic seal. Two ring indentations, about 1/32 inch deep, located approximately 1/2 inch from either end of the cell can, were crimped after cell assembly to hold the element snugly in the cylindrical can.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour
Temperature*	0°
Depth of Discharge	10%
Pack Number	15B
Precycling Capacity	3.18

88 Days	Disch #2	3.09
264 Days	Disch #2	2.95
440 Days	Disch #2	2.60
616 Days	Disch #2	2.77
792 Days	Disch #2	3.06
968 Days	Disch #2	2.73
1144 Days	Disch #2	2.68
1320 Days	Disch #2	2.60


* The test temperature was raised to 0° C after 22,900 cycles at -10° C at another test facility.

c. Test Results:

(1) Performance on Cycling: (Figure 39) This pack has completed 23,707 additional cycles at 0° C with no cell failures.

(a) The end-of-discharge voltage is 1.25 volts per cell but the percent of recharge shows some variations between 100 and 105 percent with a corresponding variation in the end-of-charge voltage.

PACK 0158 MANF. SONOTONE03.5 AH
ORB IT PERIOD HOURS 01.5
TEMP. DEGREES C. 00
CHARGE RATE AMPS 0.39
DEPTH OF DISCHARGE % 10

[illegible]

15. NIFE 3.9 ah, Two 5-cell Packs:

a. Cell Description: The cell container and the cell cover of these cylindrical cells are made of stainless steel. The cell container serves as the negative terminal. The positive terminal is a button extension of the positive plate tab through the center of the cover. The positive terminal is isolated from the negative container by means of a membrane seal. Connections are made by soldering directly to the container and the positive terminal.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour	
Temperature	0°	25°
Depth of Discharge	25%	25%
Pack Number	97C	85C
Precycling Capacity	4.10	3.90
88 Days Disch #2	3.93	3.57
264 Days Disch #2	3.33	3.33
440 Days Disch #2	3.27	2.90
616 Days Disch #2	3.60	2.20
792 Days Disch #2	3.50	F
968 Days Disch #2	3.23	
1144 Days Disch #2	3.03	F

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figure 40) Cycling was started in September 1967. Pack 85C and 97C failed on cycles 9356 and 20,000, respectively.


(2) Failure Analysis: The six failed cells showed separator deterioration, migration, shorting across the membrane seal, several weak welds, and leakage of electrolyte as indicated by deposits around the positive terminal.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 097C MANF. NIFE
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS - 1.07
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 03.9 AH

CELLS CYCLING

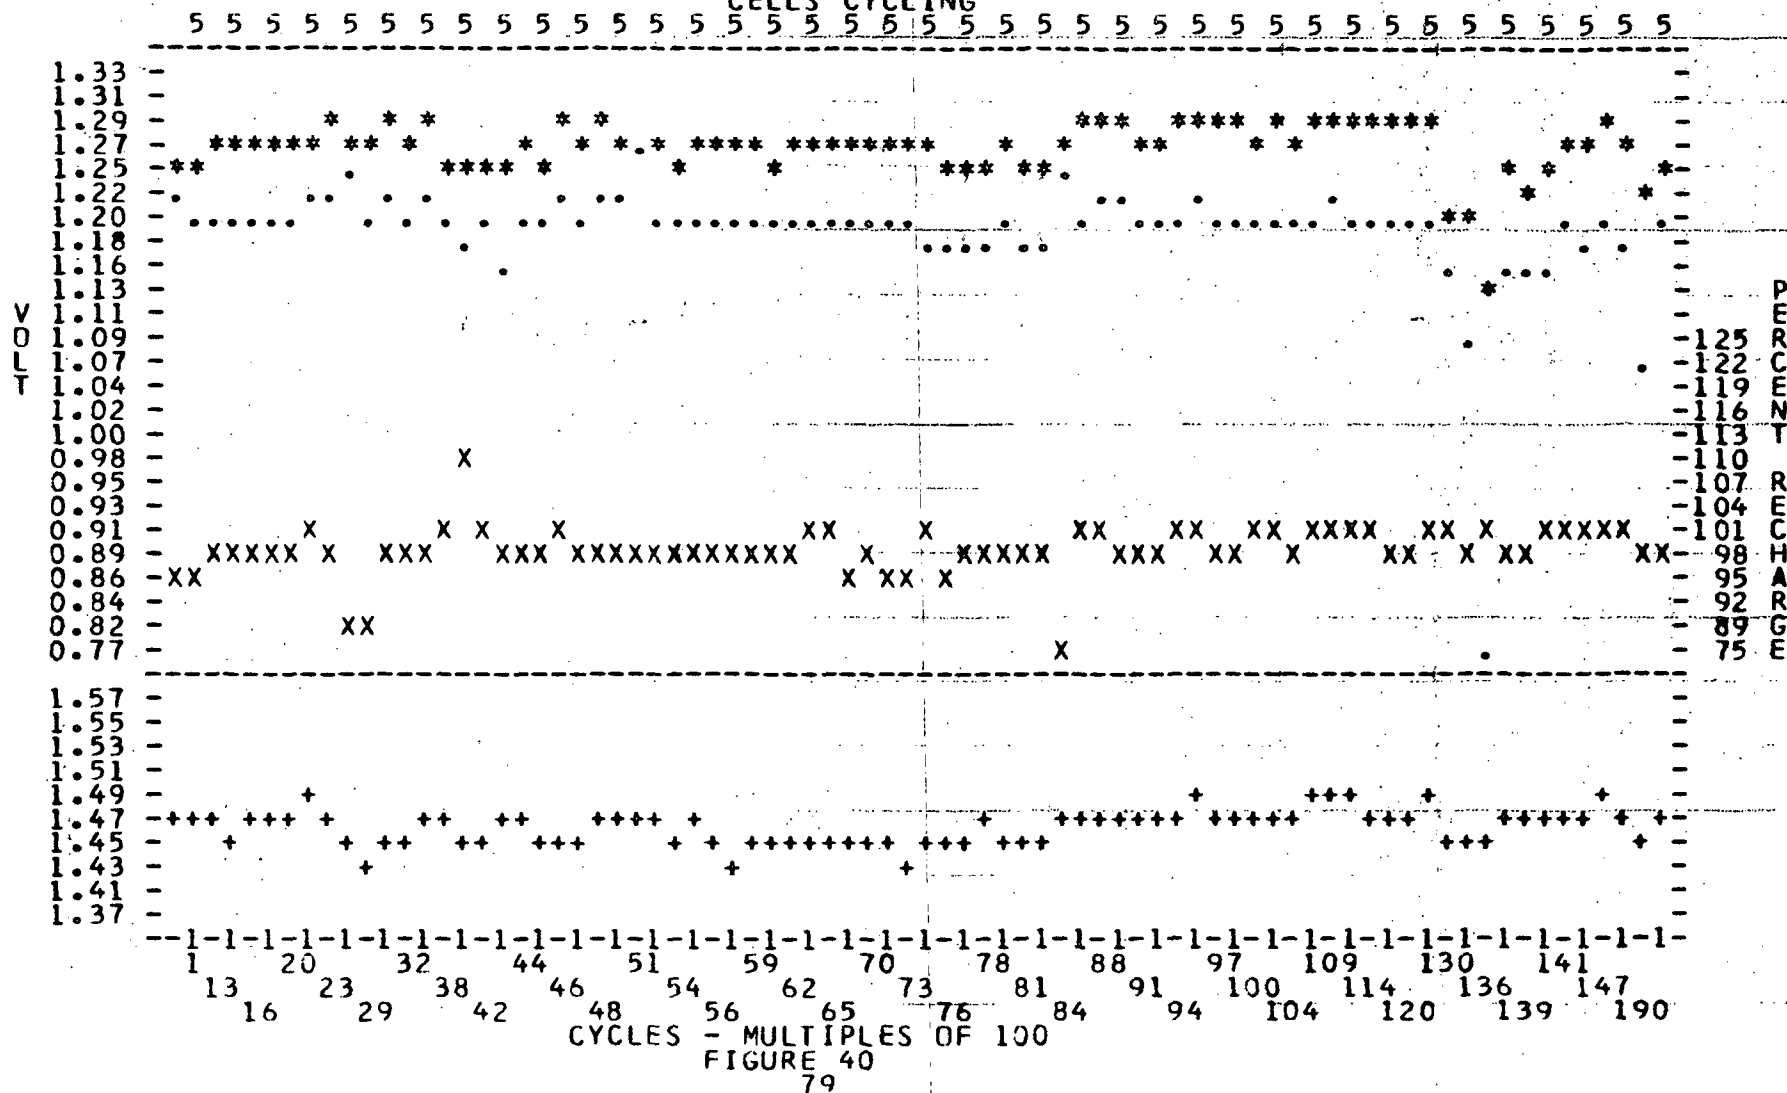

C. Silver-Cadmium Types:

1. Yardney 5.0 ah, Four 5-cell Packs:

a. Cell Description: These are vented cells, rectangular in shape, with cell jars and cell covers molded of a plastic material. The separator material is pellen and cellophane. The cells were individually epoxy potted at the Goddard Space Flight Center to hermetically seal them.

b. Parameters and Capacity Checks:

Orbit Period	24-hour			
Temperature	0°	25°	25°	40°
Depth of Discharge	20%	20%	20%	20%
Pack Number	113B	77B	105B	128B
Precycling Capacity	4.08	5.02	4.95 F	6.47
100 Days	5.27	4.92		5.53 F
300 Days	4.67	4.67		
500 Days	4.03	1.25 F		
700 Days	4.03			
900 Days	5.42			
1100 Days	4.75			
1300 Days	6.10 F			

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figure 41) Cycling was started in January 1967. Packs 113B, 77B, 105B and 128B failed on cycles 661, 77, 269, and 2542, respectively. (Prior to start of this test, Packs 77B and 105B were cycled at Goddard Space Flight Center for about 1 year. Most of that "cycling" was continuous float.)


(2) Failure Analysis: Analysis of the 12 failed cells showed that the failures were due to silver migration and separator deterioration which resulted in internally shorted cells.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 113B MANF. YARDNEY 05.0 AH
 ORBIT PERIOD HOURS 24.0
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 0.30
 DEPTH OF DISCHARGE % 20

QEEL/C 72-1

CELLS CYCLING

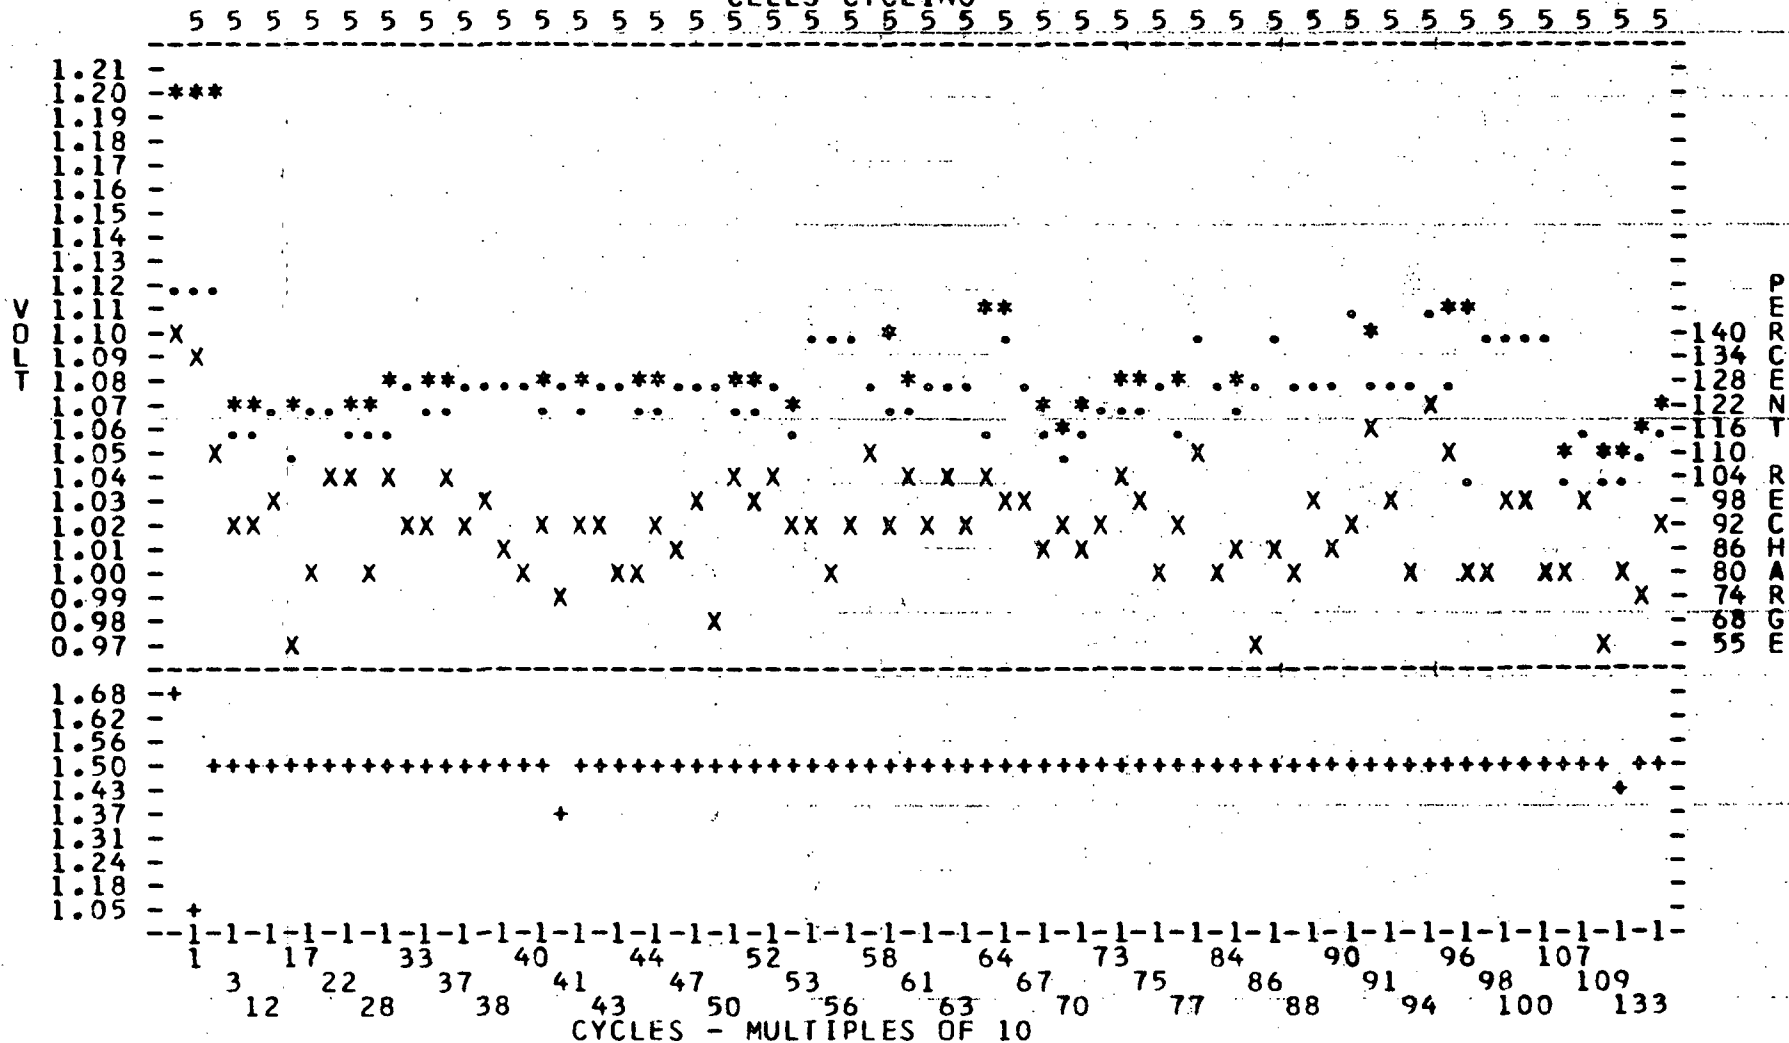

2. Electromite 7.0 ah (IMP), One 4-cell Pack:

a. Cell Description: The cells are rectangular in shape. The cells' containers are made of polystyrene and have a metal/plastic type of seal around their terminals. The cells were epoxy potted into a 4-cell pack.

b. Parameters and Capacity Checks:

Orbit Period	8-hour
Temperature	20°
Depth of Discharge	30%
Pack Number	104C
88 Days	4.10
264 Days	7.47
352 Days	8.13

c. Test Results:

(1) Cell number 3 was found to have a high internal resistance and did not start life cycling.


(2) Performance on Cycling: (Figure 42) This pack has completed 1068 cycles with no cell failures.

```

KEY  AVERAGE CELL VOLTAGE
*----MIDDLE DISCHARGE
.----END OF DISCHARGE
+----END OF CHARGE
X----PERCENT RECHARGE

```

PACK 104C MANF. ELECTRO- 7.0 AH
ORBIT PERIOD HOURS 8.0
TEMP. DEGREES C. 30
CHARGE RATE AMPS 0.40
DEPTH OF DISCHARGE % 20

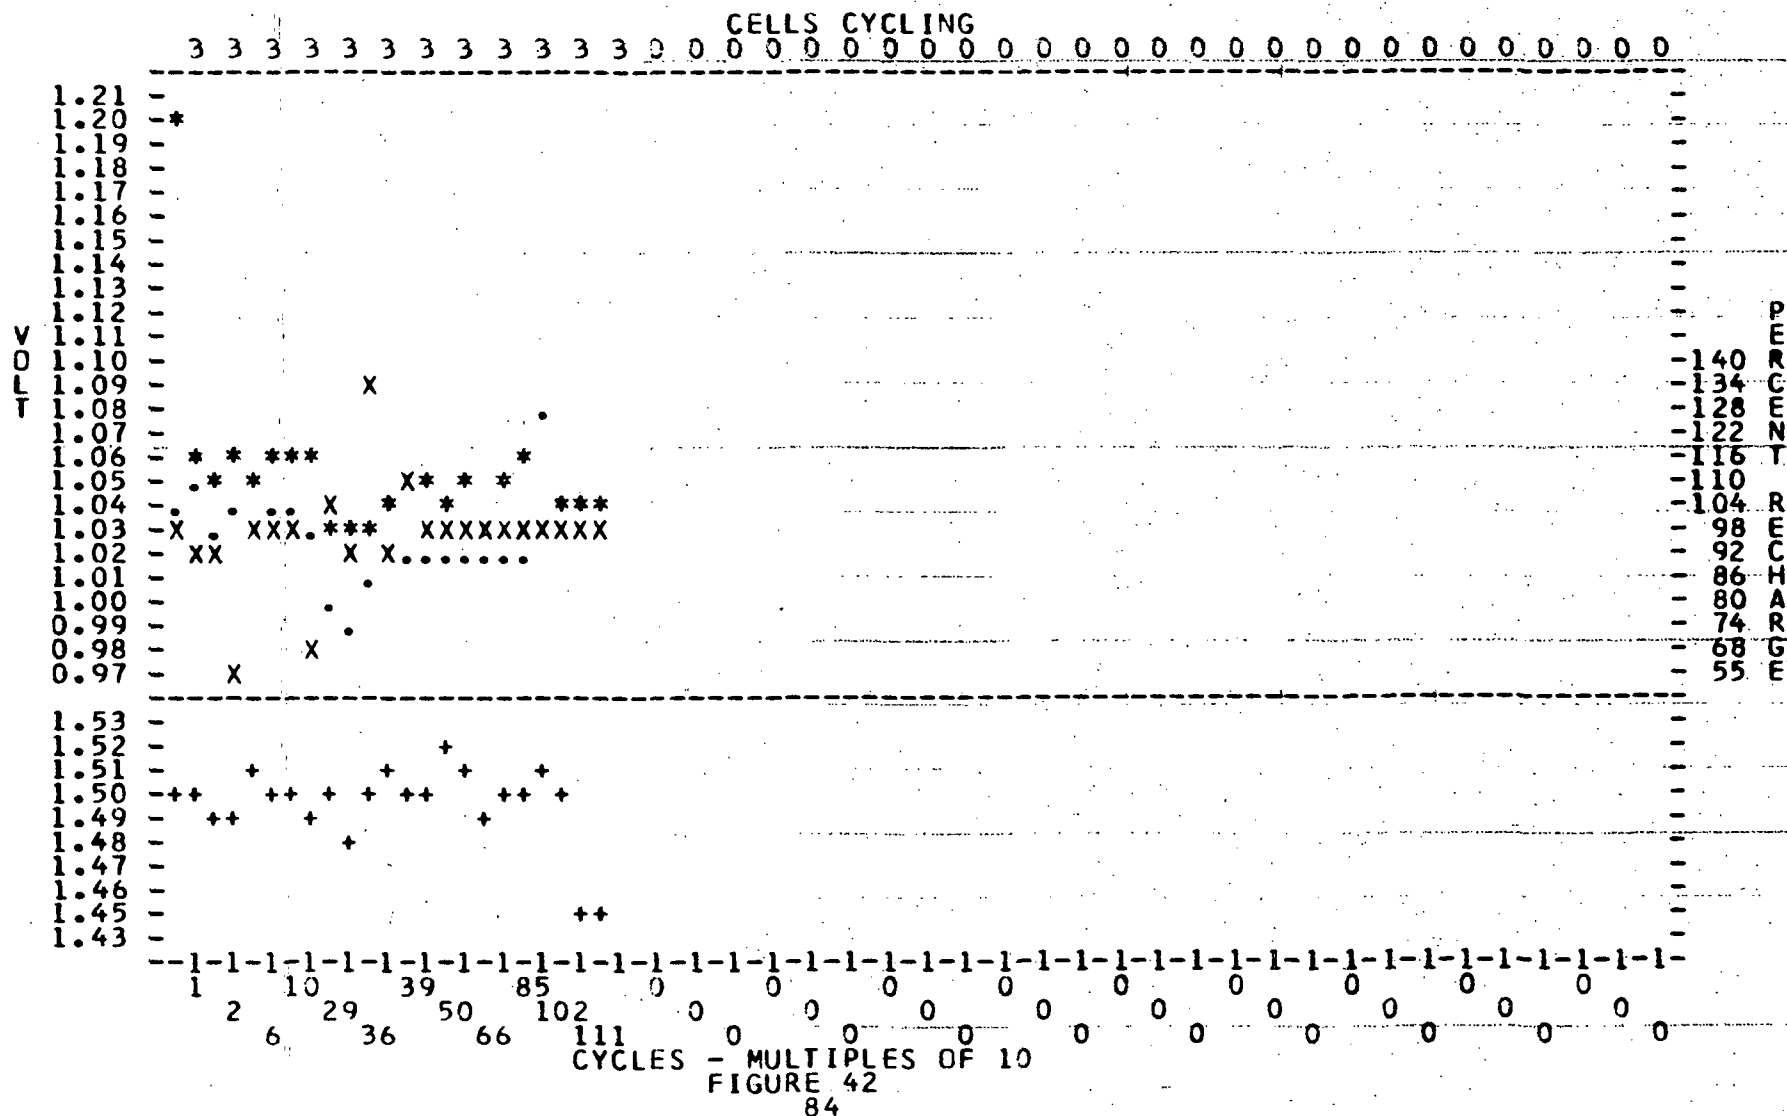

D. Silver-Zinc Types:

1. Astropower Division of McDonnell-Douglas (VENUS Orbiter),
40 ah, Two 10-cell Packs:

a. Cell Description: These heat sterilized cells are sealed in moulded epoxy cases with threaded terminals protruding through the tops. The zinc electrodes are encapsulated in an inorganic separator. The silver electrodes are separated from the inorganic separator by pellow. Prior to testing, electrolyte leakage was noted around the threaded terminals. To further seal the cells, the terminals were extended upward by attaching metal tabs to the threaded studs and then pouring another 0.5-inch layer of epoxy over the cell top.

b. Parameters and Capacity Checks:

Orbit Period	4-hour	
Temperature	20°	20°
Depth of Discharge	20%	20%
Charge Control	*	*
Pack Number	20C	33E
Precycling Capacity	28.58	28.94

* Pack charges at 3.0 amperes to an upper voltage limit of 19.8 volts; then the current trips at 400 milliamperes and the voltage limit goes to 18.6 volts.

c. Test Results:

(1) Performance on Cycling: (Figures 43 and 44)
Cycling was started in October 1971. Both packs have completed 307 cycles with no cell failures to date. However considerable electrolyte has been noted where it forced its way up the original threaded terminals and outward beneath the layer of epoxy potting that was formed over the cell top.

KEY AVERAGE CELL VOLTAGE

*-----	MIDDLE DISCHARGE
.-----	END OF DISCHARGE
+-----	END OF CHARGE
X-----	PERCENT RECHARGE

PACK 020C MANF. ASTRO 40.0 AH
ORBIT PERIOD HOURS 4.0
TEMP. DEGREES C. 20
CHARGE RATE AMPS 3.00
DEPTH OF DISCHARGE % 20

CELLS CYCLING

1010101010101010 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0 0

Figure 43 is a graph showing the relationship between Voltage (VOLT) and Cycles - Units. The graph is divided into two sections by a dashed line at 1.95 VOLT. The top section shows data points for cycles 195 to 220, with voltage values ranging from 1.22 to 1.46. The bottom section shows data points for cycles 0 to 195, with voltage values ranging from 1.94 to 2.00. The x-axis is labeled 'CYCLES - UNITS' and the y-axis is labeled 'VOLT'.

Cycles - Units	Voltage (VOLT)
195	1.22
200	1.23
205	1.24
210	1.25
215	1.26
216	1.27
217	1.31
218	1.32
219	1.33
220	1.34
221	1.35
222	1.36
223	1.37
224	1.38
225	1.39
226	1.40
227	1.41
228	1.42
229	1.43
230	1.44
231	1.45
232	1.46

Cycles - Units	Voltage (VOLT)
0	1.94
1	1.95
2	1.96
3	1.96
4	1.96
5	1.96
6	1.96
7	1.96
8	1.96
9	1.96
10	1.96
11	1.96
12	1.96
13	1.96
14	1.96
15	1.96
16	1.96
17	1.96
18	1.96
19	1.96
20	1.96
21	1.96
22	1.96
23	1.96
24	1.96
25	1.96
26	1.96
27	1.96
28	1.96
29	1.96
30	1.96
31	1.96
32	1.96
33	1.96
34	1.96
35	1.96
36	1.96
37	1.96
38	1.96
39	1.96
40	1.96
41	1.96
42	1.96
43	1.96
44	1.96
45	1.96
46	1.96
47	1.96
48	1.96
49	1.96
50	1.96
51	1.96
52	1.96
53	1.96
54	1.96
55	1.96
56	1.96
57	1.96
58	1.96
59	1.96
60	1.96
61	1.96
62	1.96
63	1.96
64	1.96
65	1.96
66	1.96
67	1.96
68	1.96
69	1.96
70	1.96
71	1.96
72	1.96
73	1.96
74	1.96
75	1.96
76	1.96
77	1.96
78	1.96
79	1.96
80	1.96
81	1.96
82	1.96
83	1.96
84	1.96
85	1.96
86	1.96
87	1.96
88	1.96
89	1.96
90	1.96
91	1.96
92	1.96
93	1.96
94	1.96
95	1.96
96	1.96
97	1.96
98	1.96
99	1.96
100	1.96
101	1.96
102	1.96
103	1.96
104	1.96
105	1.96
106	1.96
107	1.96
108	1.96
109	1.96
110	1.96
111	1.96
112	1.96
113	1.96
114	1.96
115	1.96
116	1.96
117	1.96
118	1.96
119	1.96
120	1.96
121	1.96
122	1.96
123	1.96
124	1.96
125	1.96
126	1.96
127	1.96
128	1.96
129	1.96
130	1.96
131	1.96
132	1.96
133	1.96
134	1.96
135	1.96
136	1.96
137	1.96
138	1.96
139	1.96
140	1.96
141	1.96
142	1.96
143	1.96
144	1.96
145	1.96
146	1.96
147	1.96
148	1.96
149	1.96
150	1.96
151	1.96
152</	

PACK 033E	MANF. ASTRO
ORBIT PERIOD HOURS	4.0
TEMP. DEGREES C.	20
CHARGE RATE AMPS	3.00
DEPTH OF DISCHARGE %	20

PACK 033E	MANF. ASTRO
ORBIT PERIOD HOURS	4.0
TEMP. DEGREES C.	20
CHARGE RATE AMPS	3.00
DEPTH OF DISCHARGE %	20

[illegible]

VOLT	PERCENT
1.68	-
1.67	-*
1.66	-
1.65	-
1.64	-
1.63	-
1.62	-
1.61	-
1.60	-
1.59	-
1.58	-
1.57	-
1.56	-X
1.55	-
1.54	-
1.53	-
1.52	-X XXX
1.51	-
1.50	-
1.49	-XX * **
1.48	-..* **
1.47	-..****X* XXX
1.46	-..XX..
1.45	-..
1.44	-XX
2.01	-
2.00	-++ +++++
1.98	-+ +
1.96	-
1.94	-
1.92	-
1.91	-
1.89	-
1.87	-+ +++++
1.83	-

FIGURE 44

II. CELLS USING SOPHISTICATED CHARGE CONTROL METHODS AND DEVICES:

As a continuous effort to improve cells and cell life, new types of charge control methods and devices are being developed. Charge control methods being tested at NAD Crane are as follows: high overcharge current capabilities, auxiliary electrode, thermistor, voltage limit dependent upon auxiliary electrode trip level, coulometer, the two-step regulator and internal mechanical pressure devices. Sherfey upside-down cycling and stabistor charge control methods have been used in the past.

A. General Description:

1. The majority of the nickel-cadmium cells tested for use in space, or related programs, are of one basic type. They are rectangular with stainless steel containers and covers; both terminals are insulated from the cover by a ceramic seal and protrude through the cover as solder type terminals. Where auxiliary electrodes are present, the terminal is a stainless steel tab welded to the cell cover. Any cells differing from this description are separately described as they are encountered in the following paragraphs.

B. High Overcharge Current Capabilities: These cells were constructed to withstand continuous charge rates as high as c/1 for extended periods of time.

1. Gulton 1.25 ah, (Nickel-Cadmium), Four 5-cell Packs:

a. Cell Description: These cells are rectangular. The cell container and cell cover are made of stainless steel. The positive terminal is insulated from the cell cover by a ceramic seal whereas the negative terminal is common to the can. Both are solder type terminals. Each cell was equipped with a pressure gage.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour			
Temperature	-20°	-20°	0°	0°
Depth of Discharge	25%	60%*	25%	60%
Pack Number	74B	88D	108B	98B
Precycling Capacity	1.43	1.28	1.78	1.83
88 Days Disch #2	0.39	0.36	1.76	1.60
264 Days Disch #2	0.40	0.35	1.43	0.95
440 Days Disch #2	0.36	0.35	1.32	0.87
616 Days Disch #2	0.41	0.36	0.92	0.99
792 Days Disch #2	0.29	0.28	1.01	F
968 Days Disch #2	0.27	0.28	0.66	
1144 Days Disch #2	0.25	0.28	0.42	
1320 Days Disch #2	0.38	0.39	0.47	
1496 Days Disch #2	0.27	0.27	0.54	
1672 Days Disch #2	0.30	0.29	0.41	
1848 Days Disch #2	0.33	0.37	0.39	

* Depth of discharge was reduced to 25% after 46 cycles.

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figures 45 through 47)
Cycling was started in March 1966. Packs 74B (one cell failure), 88D (two cell failures) and 108B have completed 31,227, 30,499 and 31,313 cycles, respectively. Pack 98B failed on cycle 12,247. All four packs have experienced high pressure (some in excess of 150 psig). The cells operating at -20° C required a reduction in charge current from 1.25 to 1.00 ampere in order to cycle and avoid high

internal pressure. After this reduction in charge current, packs 74B and 88D averaged 10,500 cycles before high pressure was noticed and released. Pressure again developed in packs 74B and 88D after 13,400 cycles and was released.

(2) Failure Analysis: Analysis of the six failed cells shows severe migration of negative material, blistering of the positive plates, high internal pressure, and external carbonate deposits around the terminals.

```

*-----MIDDLE DISCHARGE
+-----END OF DISCHARGE
+-----END OF CHARGE
X-----PERCENT RECHARGE

```

DEPTH OF DISCHARGE %

QEEL/C 72-1

1.0 AH

01.5

- 20

1.00

25

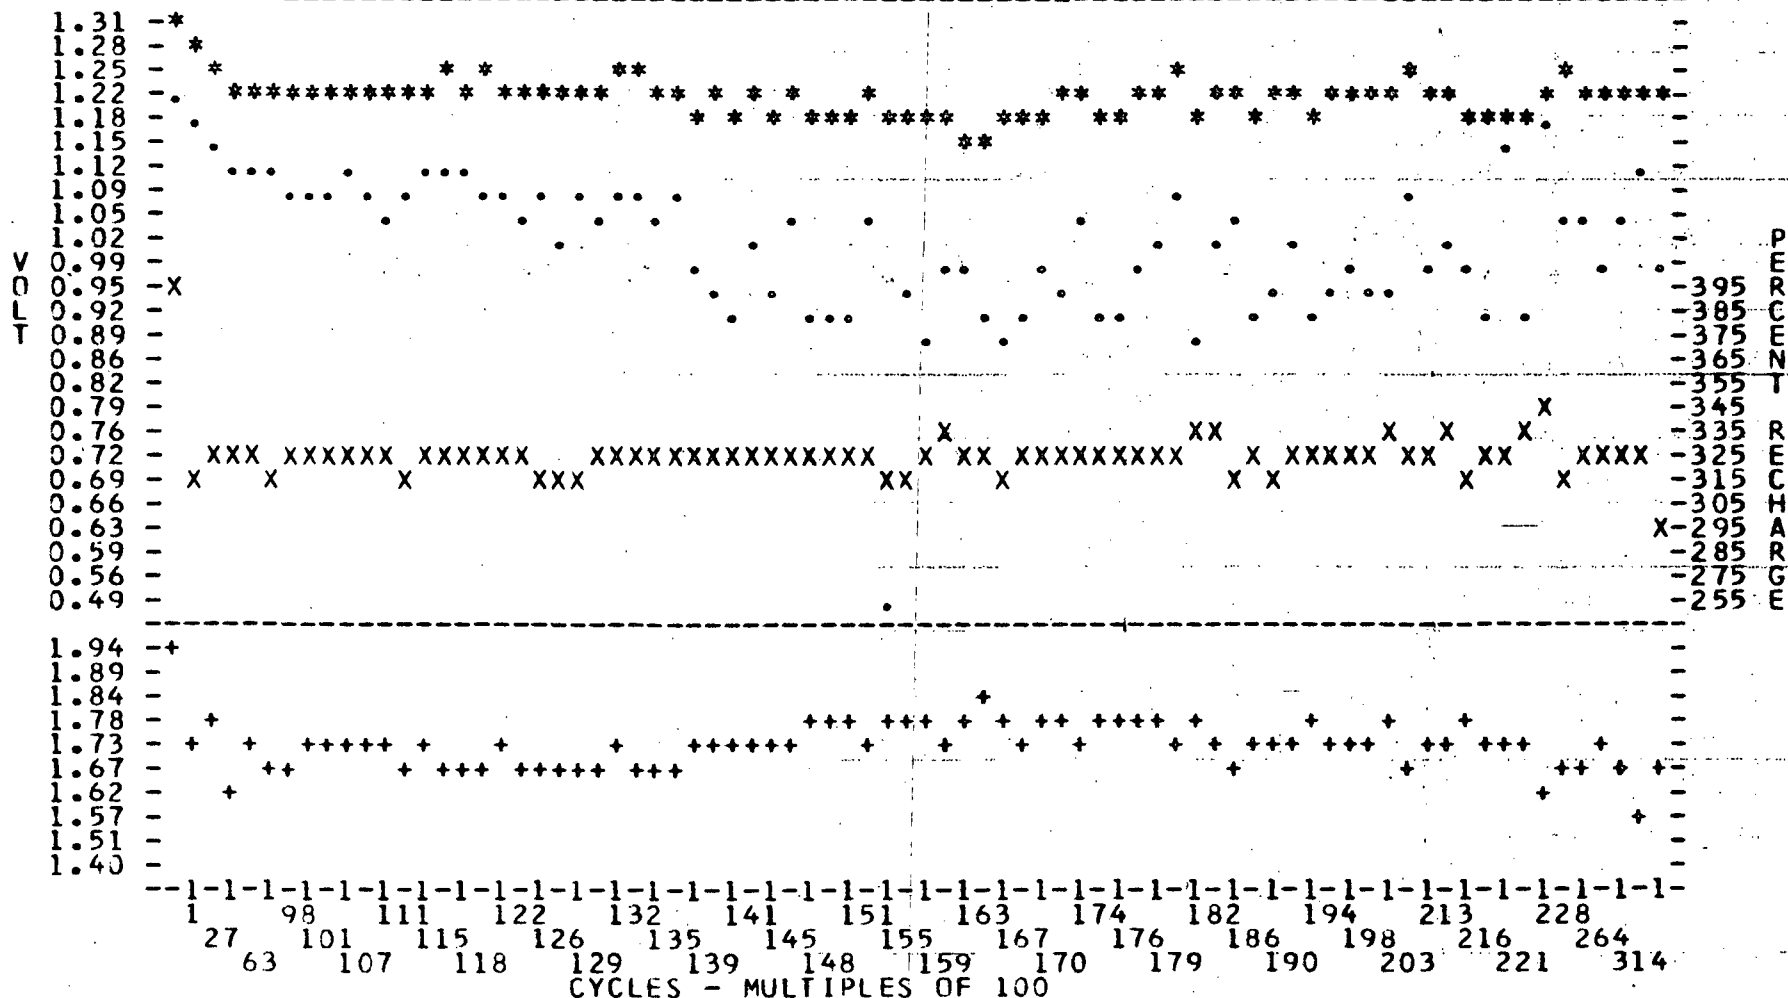
[illegible]

FIGURE 45


PACK 088D	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	-20
CHARGE RATE AMPS	10.05
DEPTH OF DISCHARGE %	60

1.25 AH



PACK 108B	MANF.	GULTON
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		00
CHARGE RATE AMPS		1.25
DEPTH OF DISCHARGE %		25

PACK 108B	MANF.	GULTON
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		00
CHARGE RATE AMPS		1.25
DEPTH OF DISCHARGE %		25

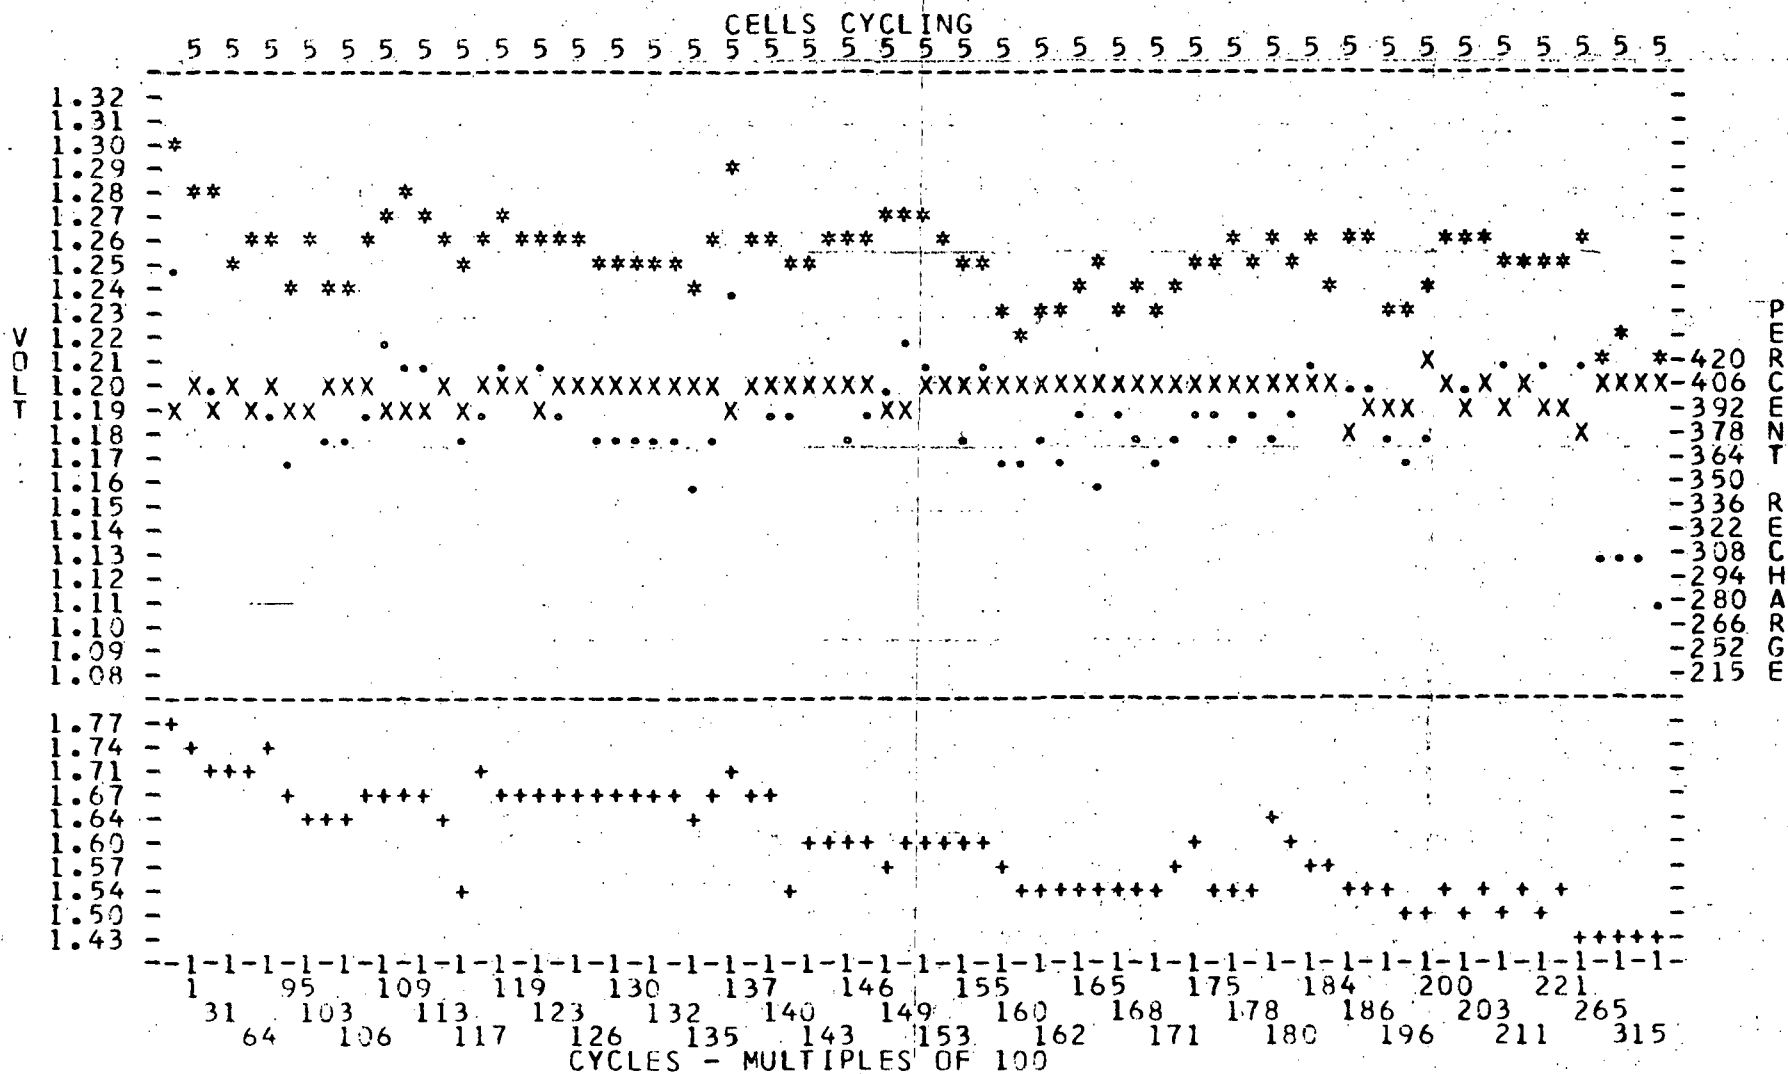

C. Auxiliary Electrode: Nickel-cadmium cells have been developed with an auxiliary electrode whose voltage, with respect to the negative terminal, is dependent upon the partial pressure of oxygen in the cell. When a nickel-cadmium cell is being charged, it generates oxygen very slowly until it nears 80 percent of the required recharge; then suddenly, the amount of oxygen generated internally increases rapidly. The increased oxygen pressure causes a fast rise in voltage between the auxiliary electrode and the negative terminal. This increasing voltage is used to signal a control circuit to reduce or terminate the charge current. The charge-current control circuit utilizes the auxiliary electrode voltage of each cell in the pack to reduce the charging rate after the cells have received the desired amount of recharge. The circuit is designed to monitor the auxiliary electrode voltage of each cell while the 5-cell pack is being charged. As the auxiliary electrode voltage of any one cell of the pack approaches a preset value, the circuit begins to reduce the charge current. When the auxiliary electrode voltage of any cell reaches the predetermined voltage (trip voltage), the charge current will be reduced to a preset trickle or to zero.

1. Eagle-Picher 6.0 ah, Three 5-cell Packs:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour		
Temperature	0°	20°	40°
Depth of Discharge	40%	40%	40%
Auxiliary Electrode Trip Voltage (MV)	500	500	500
Auxiliary Electrode Resistors (Ohms)	680	680	680
Pack Number	53C	65C*	42D
Precycling Capacity	8.26	8.40	8.54

* Percent recharge set at 102.5.

c. Test Results:


(1) Performance on Cycling: (Figures 48 through 50)
Cycling was started in September 1971. Pack 42D failed after 95

cycles. Packs 53C and 65C have completed 1652 and 1662 cycles, respectively, with no cell failures.

(a) Pack 42D, cycling at 40° C, could not exceed 105 percent recharge without experiencing high pressures and this amount of recharge would not sustain the cells at this temperature.

(2) Failure Analysis: Analysis of the three cells in pack 42D only showed weak negative tab-to-plate welds. Although no shorts were noted, these cells were failed because they would not accept charge.

6.00 GEEL/C 72-1
AH

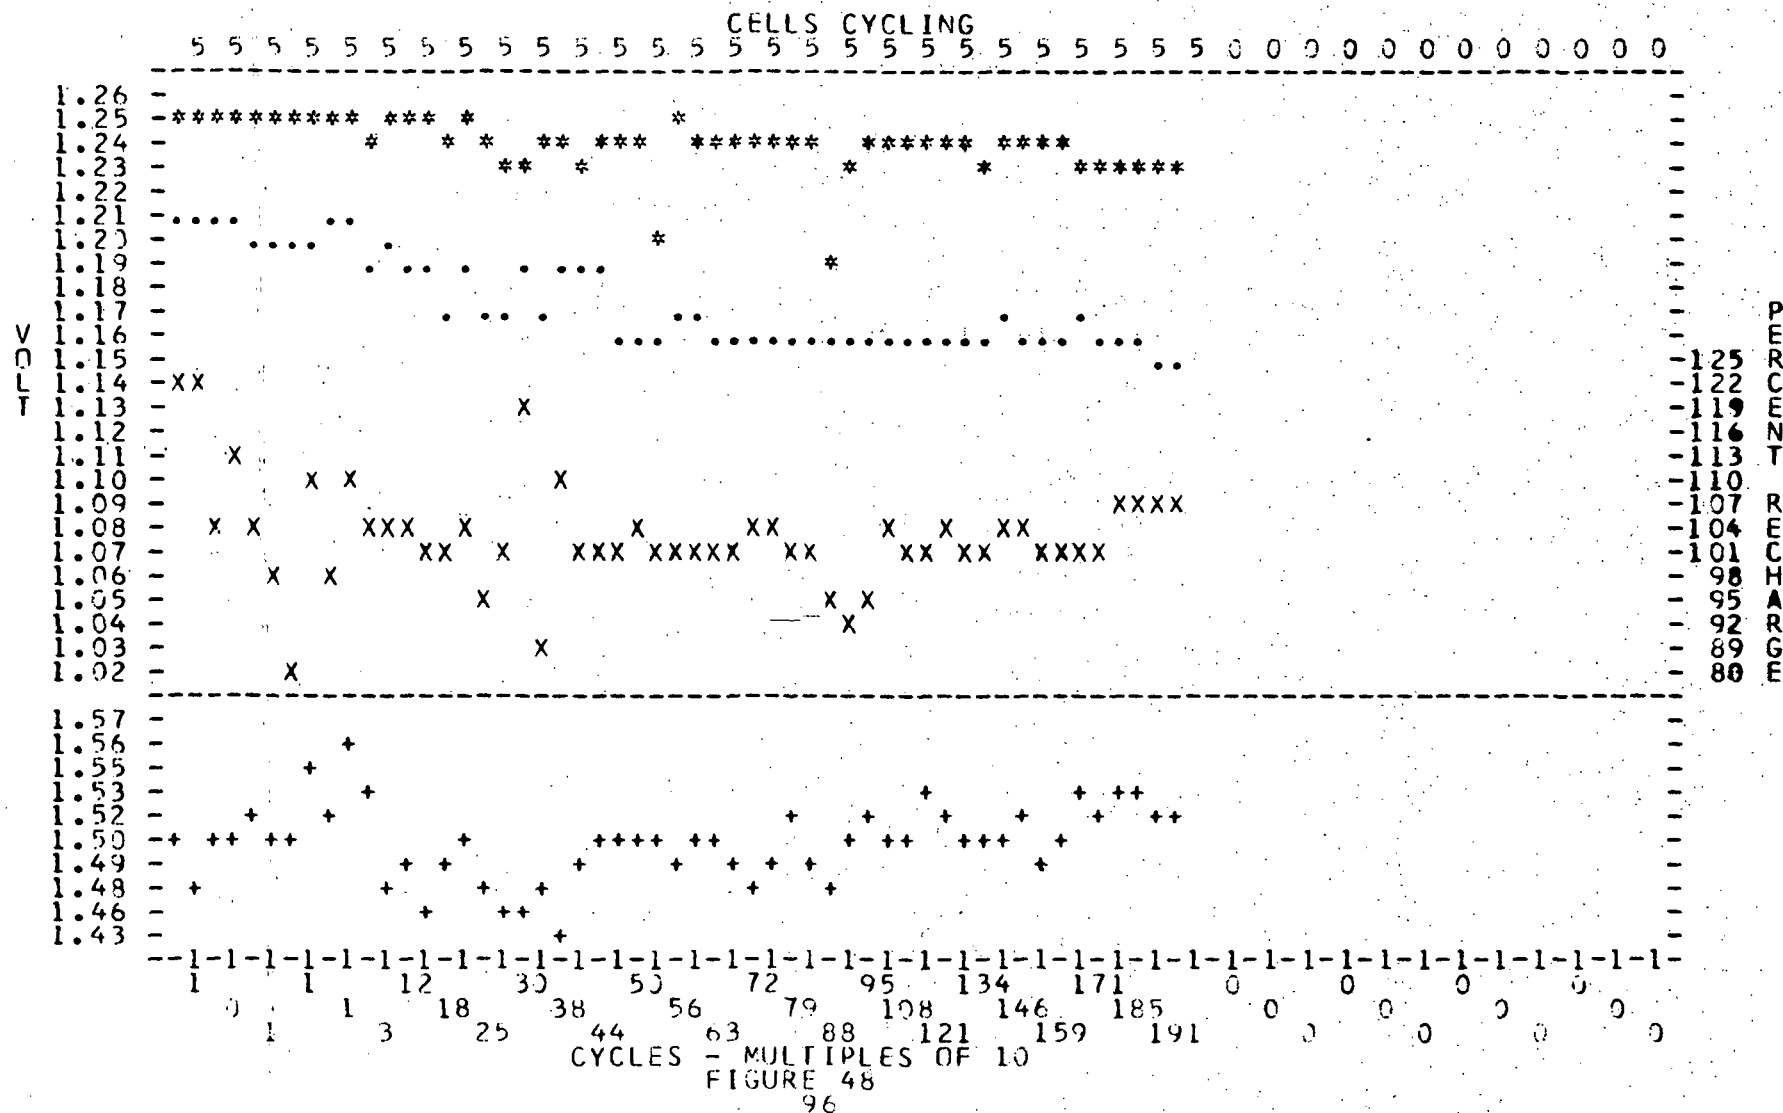

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 065C MANF. EP
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 4.80
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 6.00 AH

CELLS CYCLING


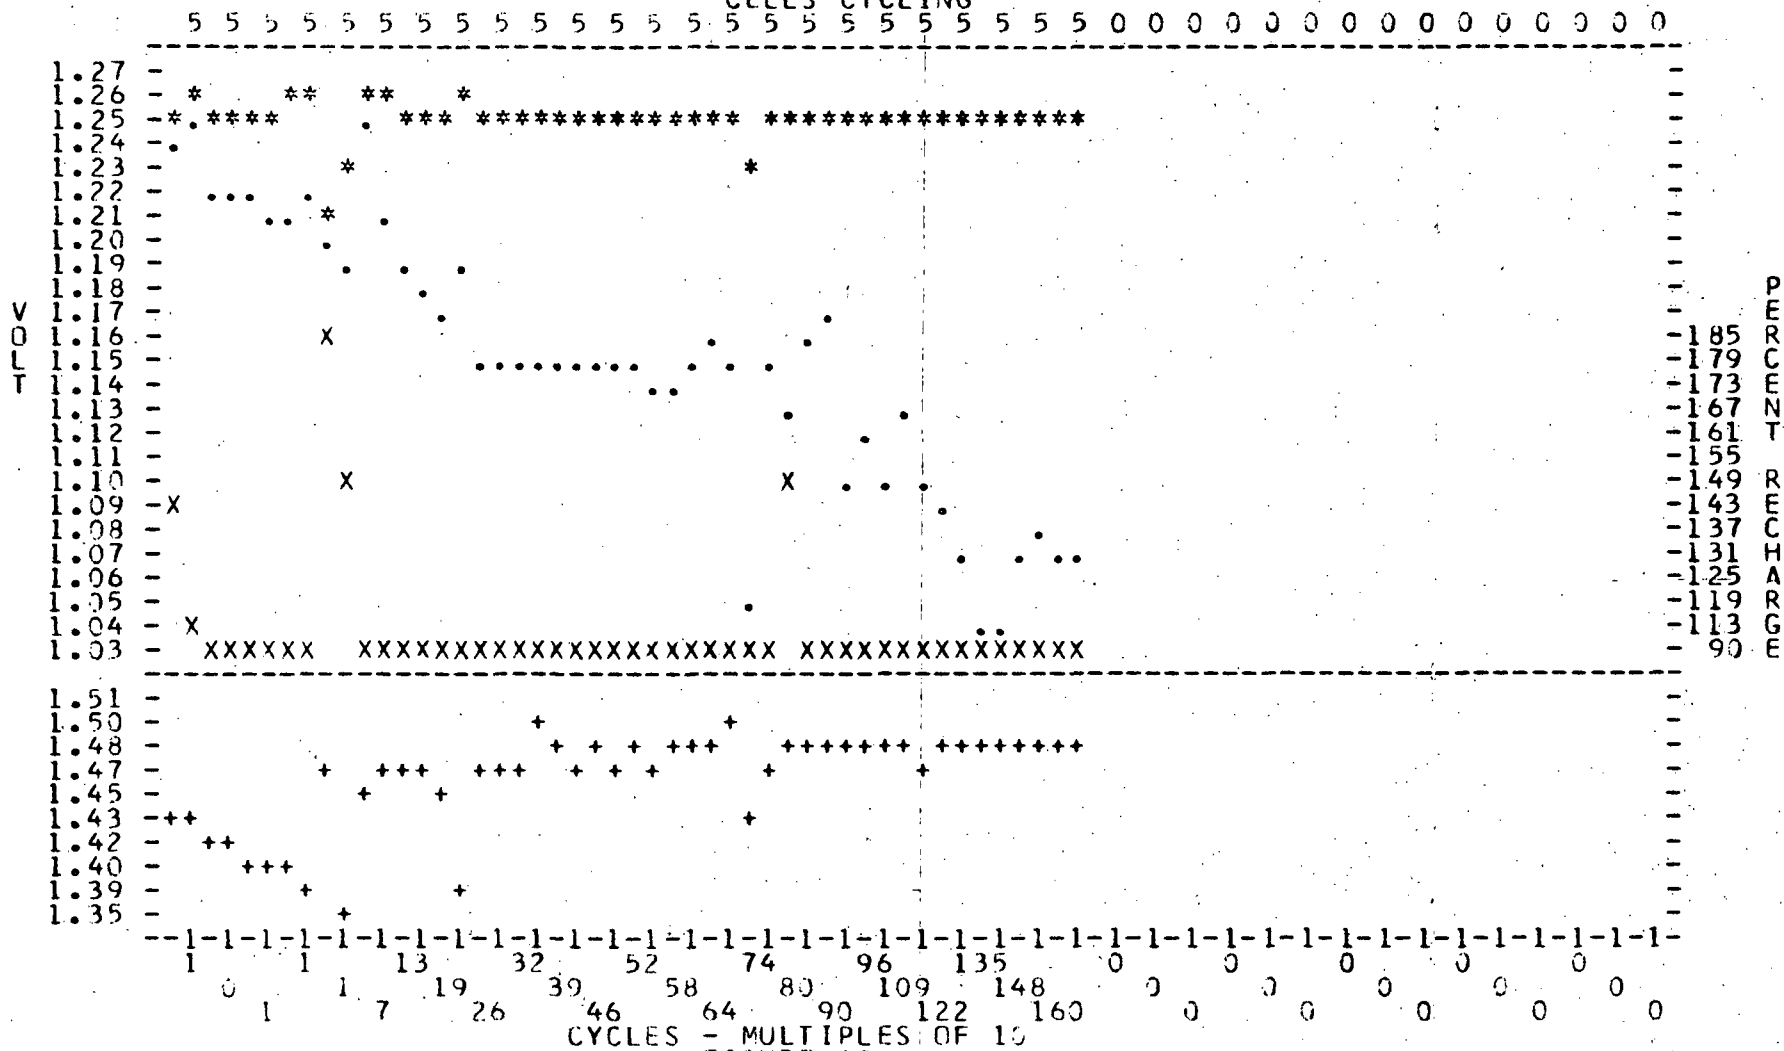


FIGURE 49

PACK 042D	MANF. EP
ORBIT PERIOD HOURS	1.5
TEMP. DEGREES C.	40
CHARGE RATE AMPS	4.80
DEPTH OF DISCHARGE %	25

CELLS CYCLING



2. Eagle-Picher 6.0 ah, (Nickel-Cadmium, Separator Test),
Eight 6-cell Packs, One 8-cell Pack and One 6-cell Replacement Pack:

a. Cell Description: See paragraph II.A., page 88.

b. Purpose of Test: This experiment is designed to
test various types of separator material (listed in the table below)
while on life cycling. All the usual parameters (temperature, depth
of discharge, and orbit period) are held constant.

c. Parameters and Capacity Checks:

Orbit Period	1.5-hour									
Temperature	20°	20°	20°	20°	20°	20°	20°	20°	20°	20°
Depth of Discharge	25%	25%	25%	25%	25%	25%	25%	25%	25%	25%
Trip Voltage (MV)	No auxiliary electrode control, 1.55 volt limit for protection.									
Auxiliary Electrode Resistors (Ohms)	200	200	200	200	200	200	200	200	200	200
Type of Separator	(1)	(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)
Pack Number	2D	2E*	14E	26D	38F	22C	46C	49B	31C	25D
88 Days	F	6.45	F	F	6.54	7.05	7.50	7.32	7.14	7.50
264 Days					4.80	6.33	7.59	7.08	7.53	7.47

- (1) Kendall, E1451AR, ppl.
- (2) Kendall, E1451W, ppl.
- (3) Kendall, E1451T, ppl.
- (4) GAF, Wex 1242AR, ppl.
- (5) GAF, Wex 1242W, ppl.
- (6) Pellon, 2505 K4 AR, nylon.
- (7) Pellon, 2505 K4 W, nylon.
- (8) Pellon, FT 2140 AR, ppl.
- (9) Hercules, RT-37-2665-15, ppl.

* Replaced 2D which failed early.

F - Failed.

d. Test Results:

(1) Performance on Cycling: (Figures 51 through 60)
Cycling was started in February 1971. Packs 2D, 14E and 26D have failed and have been sent to Goddard Space Flight Center after completing 376, 997 and 25 cycles respectively. Packs 2E, 38F, 22C, 46C, 49B, 31C and 25D have completed 3208, 4474, 4509, 4454, 4484, and 4511 cycles, respectively. Packs 38F, 22C, 46C, 49B, 31C, and 25D have had two cells, each, removed for chemical analysis following each respective capacity check. Pack 2E has had one cell removed for chemical analysis. The analyses have shown the following:

(a)

Days	Carbonate Percentage Range	Carbonate Average Percentage
88	47.2 - 71.2	61.8
176	0.00 - 77.7	60.1

(b) In general, extremely high carbonate percentages (equivalence percentages) have been noted in the analysis thus far.


(c) There is no significant difference in the average carbonate percentages from the first to the second chemical analysis at the end of each 88 days.

(d) On the second analysis, one of the four samples taken from packs 31C and 38F, respectively, indicated no carbonate whatsoever. The "zero-carbonate" sample removed from pack 38F was taken from an area where a negative plate had been connected to the positive bus. Though not so noted, the "zero-carbonate" sample of pack 31C is believed to have resulted from a similar condition.

(e) Excepting the "zero-carbonate" sample of the second analysis, all carbonate percentages of pack 31C showed a sharp increase over the first analysis.

PACK 0020	MANF.	
ORBIT PERIOD HOURS		1.5
TEMP. DEGREES C.		20
CHARGE RATE AMPS		1.80
DEPTH OF DISCHARGE %		25

PACK 0020	MANF.	
ORBIT PERIOD HOURS		1.5
TEMP. DEGREES C.		20
CHARGE RATE AMPS		1.80
DEPTH OF DISCHARGE %		25

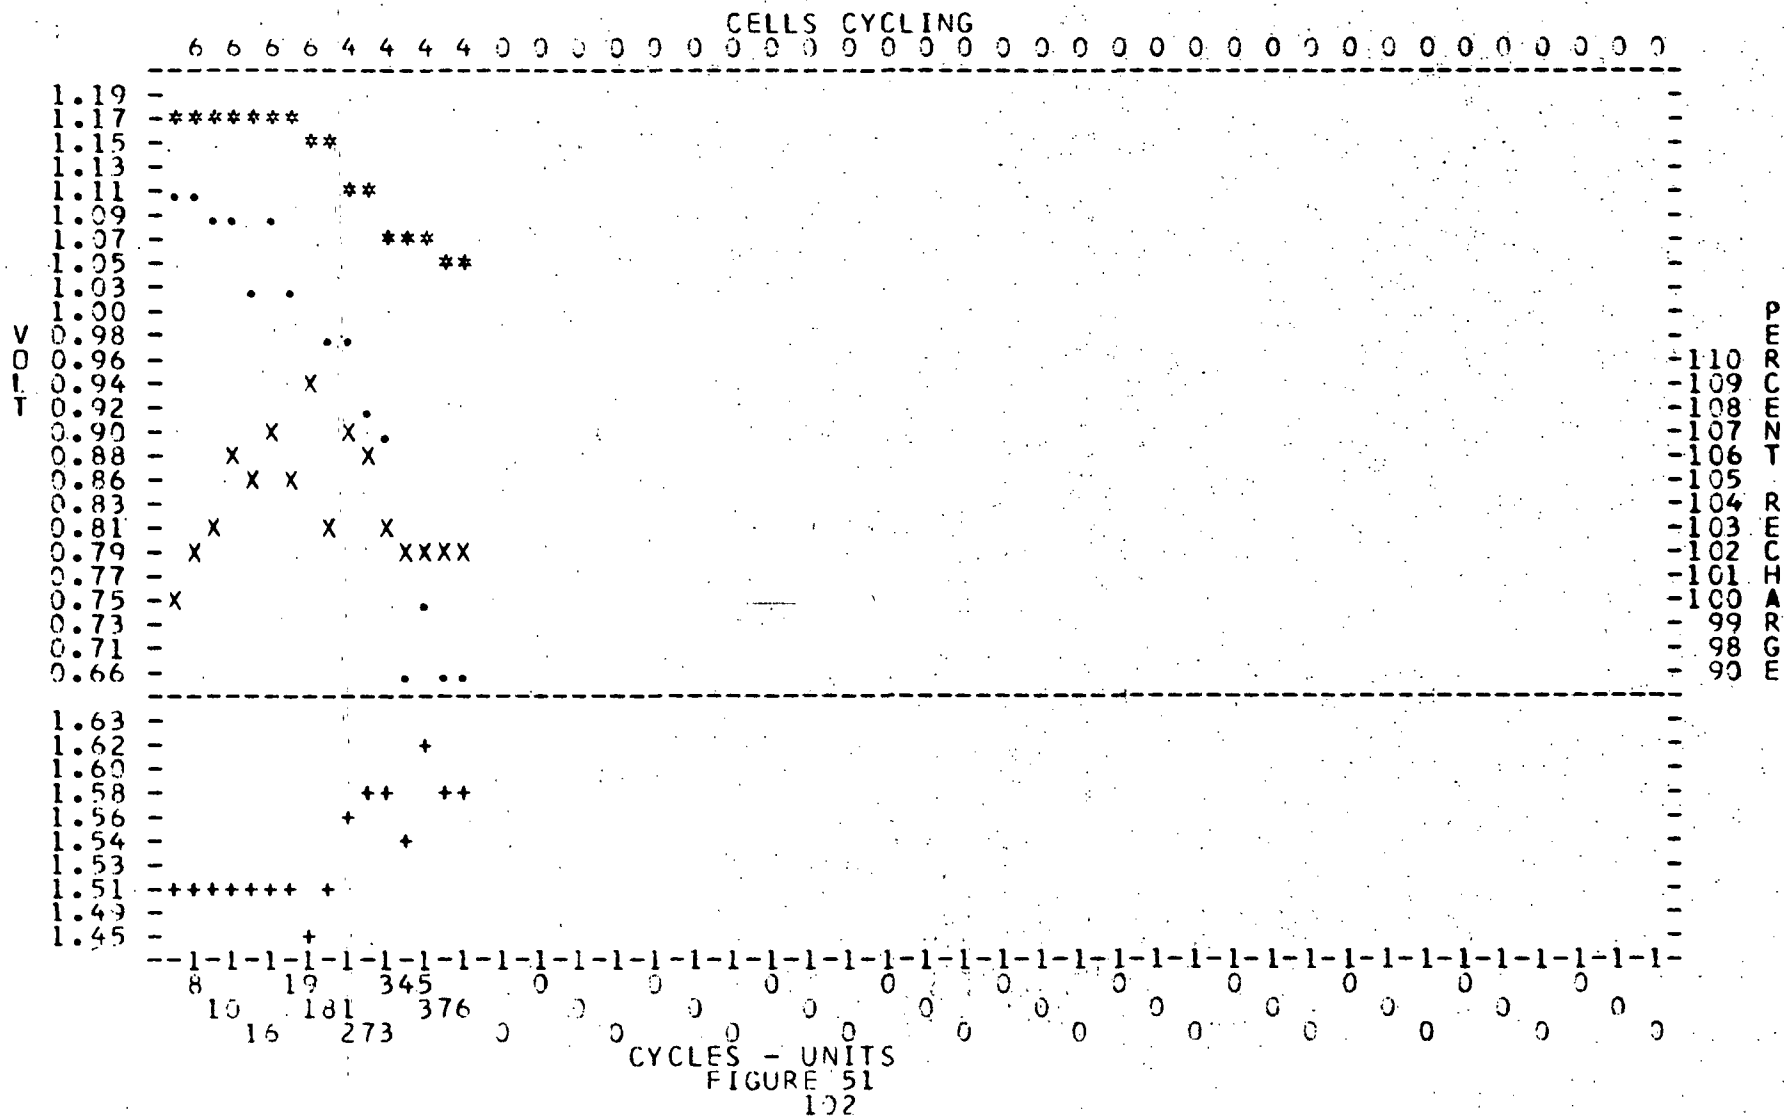

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 002E MANF. EP
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 1.65
 DEPTH OF DISCHARGE % 25

GEEL/C 72-1
 6.00 AH

CELLS CYCLING
 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 4 4 4 4 4 4 4 3 3 0 0 0 0 0 0


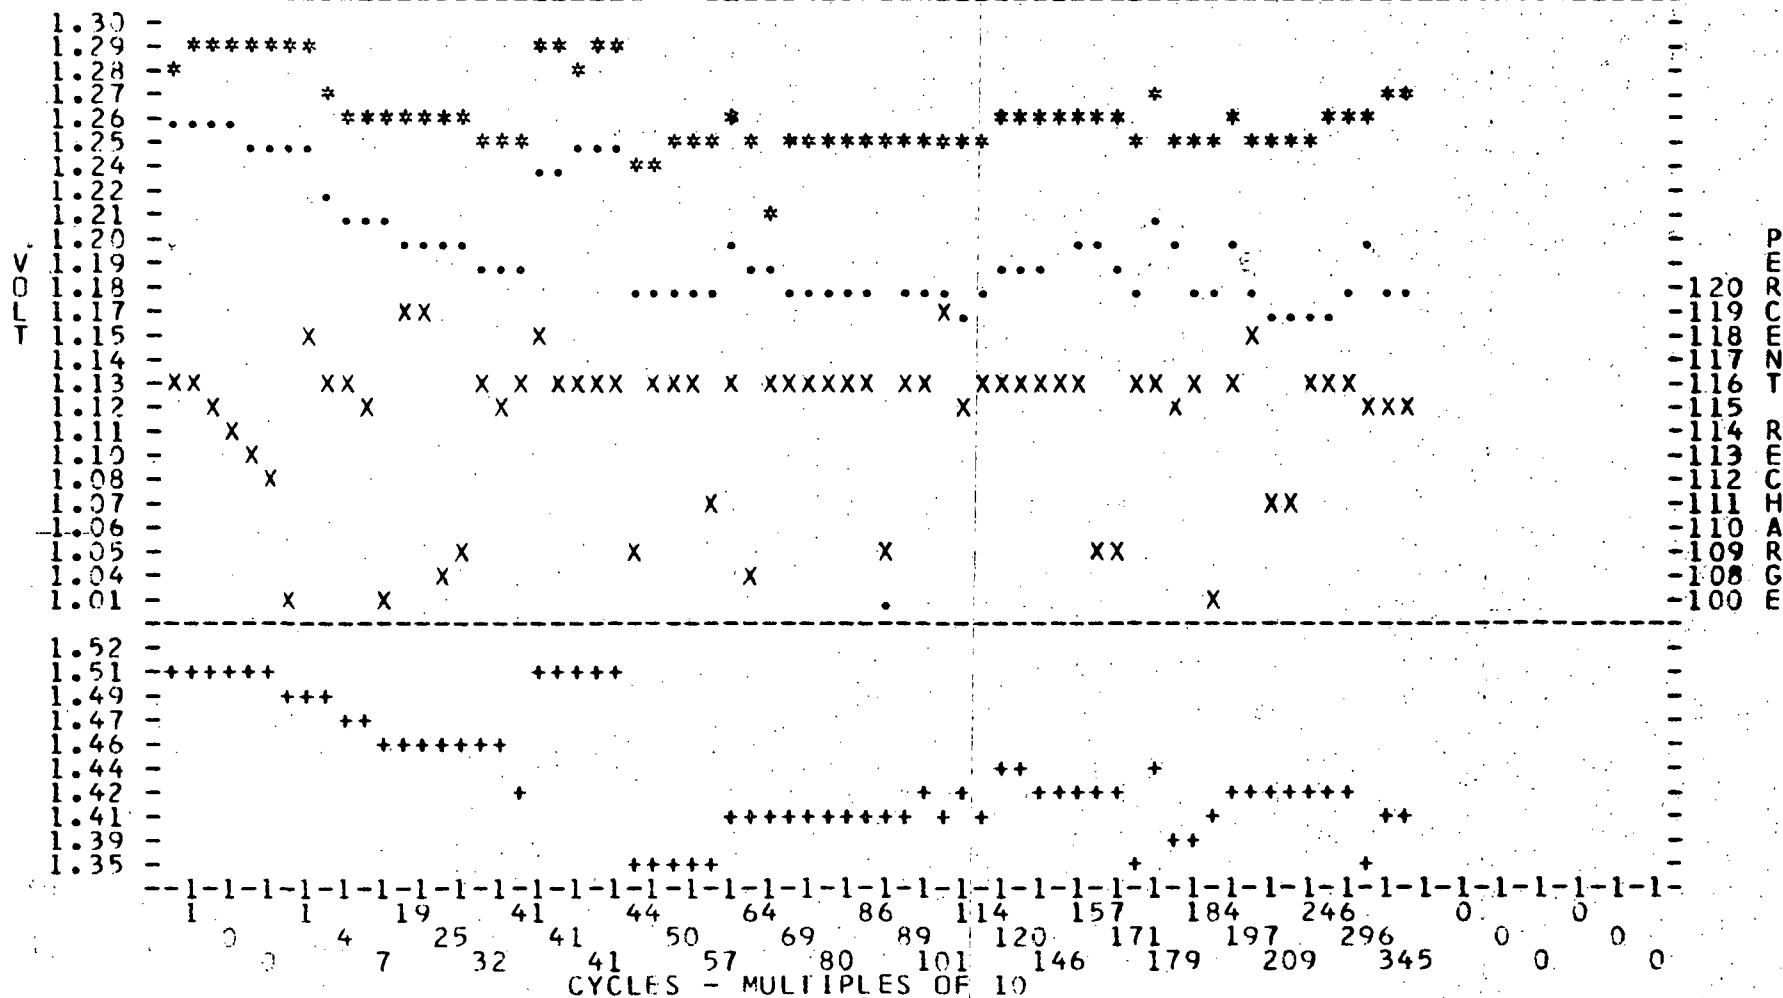


FIGURE 52

6.90 AH

PACK 014E	MANF. EP
ORBIT PERIOD HOURS	1.5
TEMP. DEGREES C.	20
CHARGE RATE AMPS	1.80
DEPTH OF DISCHARGE %	25

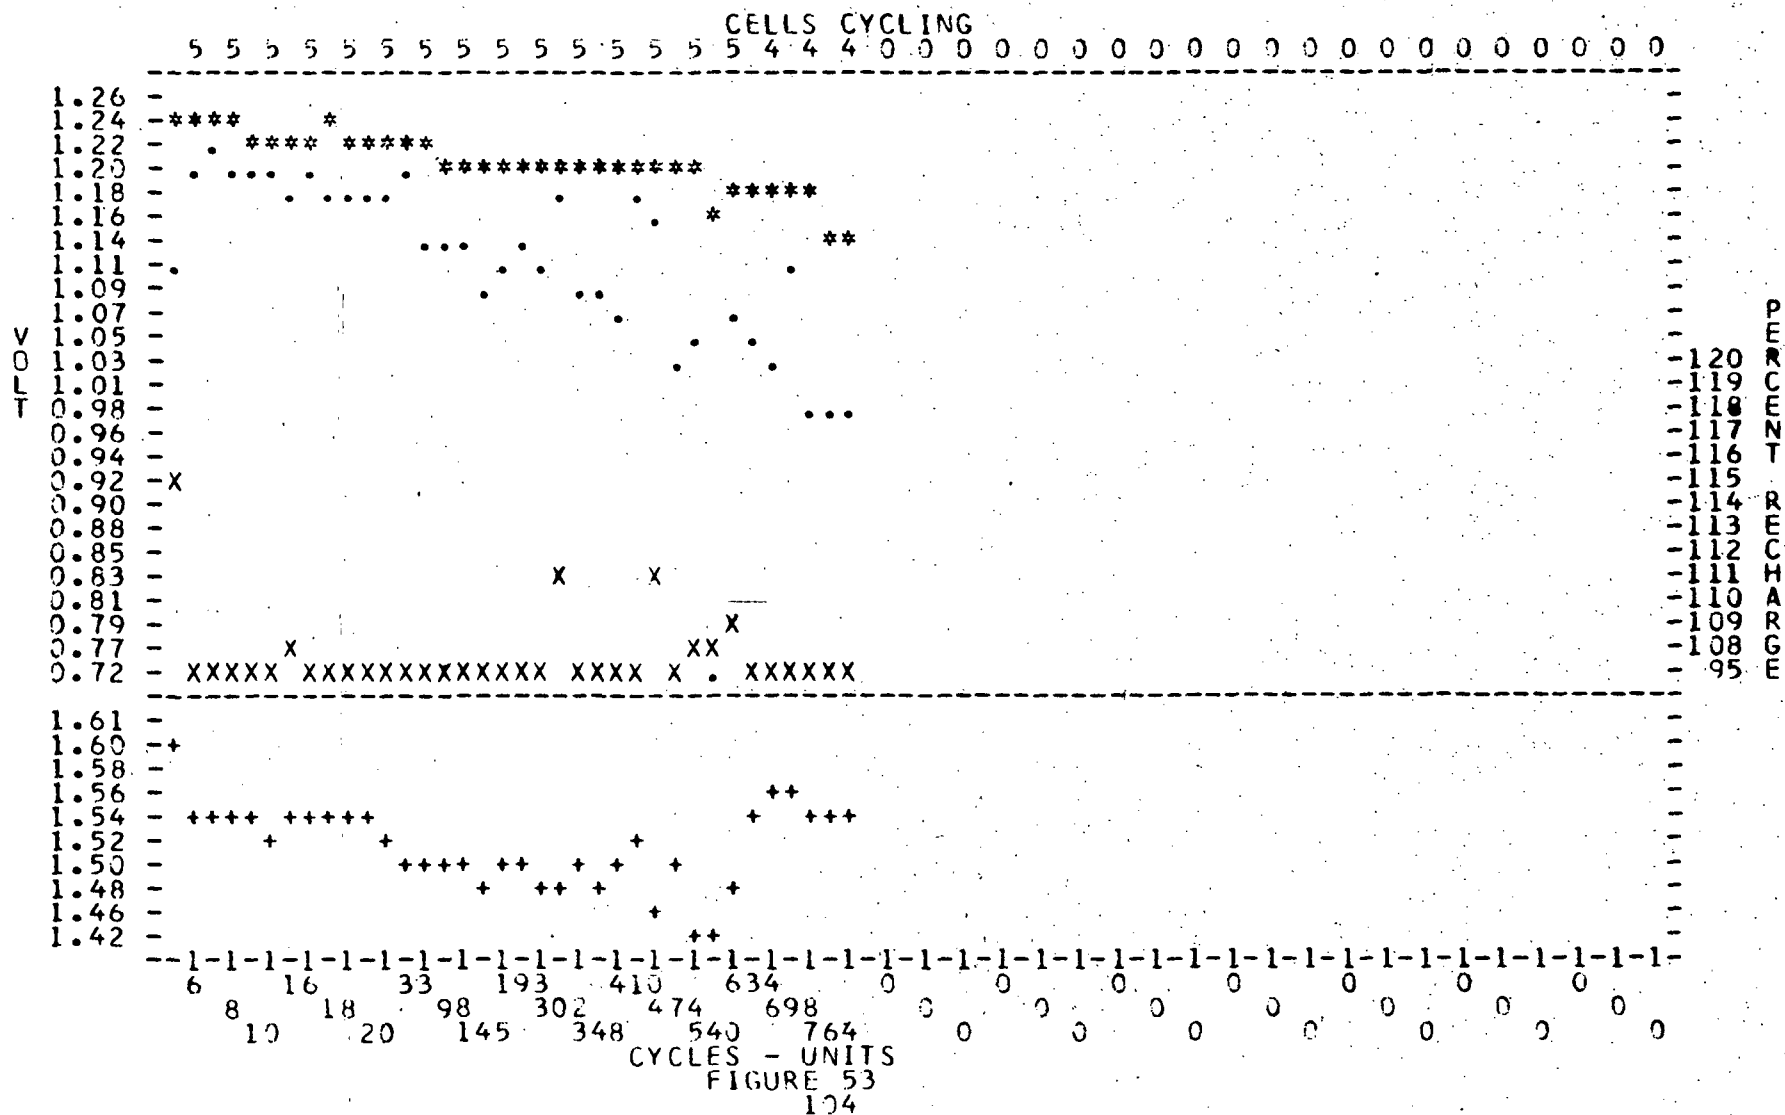


```
*-----MIDDLE DISCHARGE
+-----END OF DISCHARGE
+-----END OF CHARGE
X-----PERCENT RECHARGE
```

PACK 026D	MANF. EP
ORBIT PERIOD HOURS	1.5
TEMP. DEGREES C.	20
CHARGE RATE AMPS	1.80
DEPTH OF DISCHARGE	25

MANF. EP

6.00 QEEL/C 72-1
AH

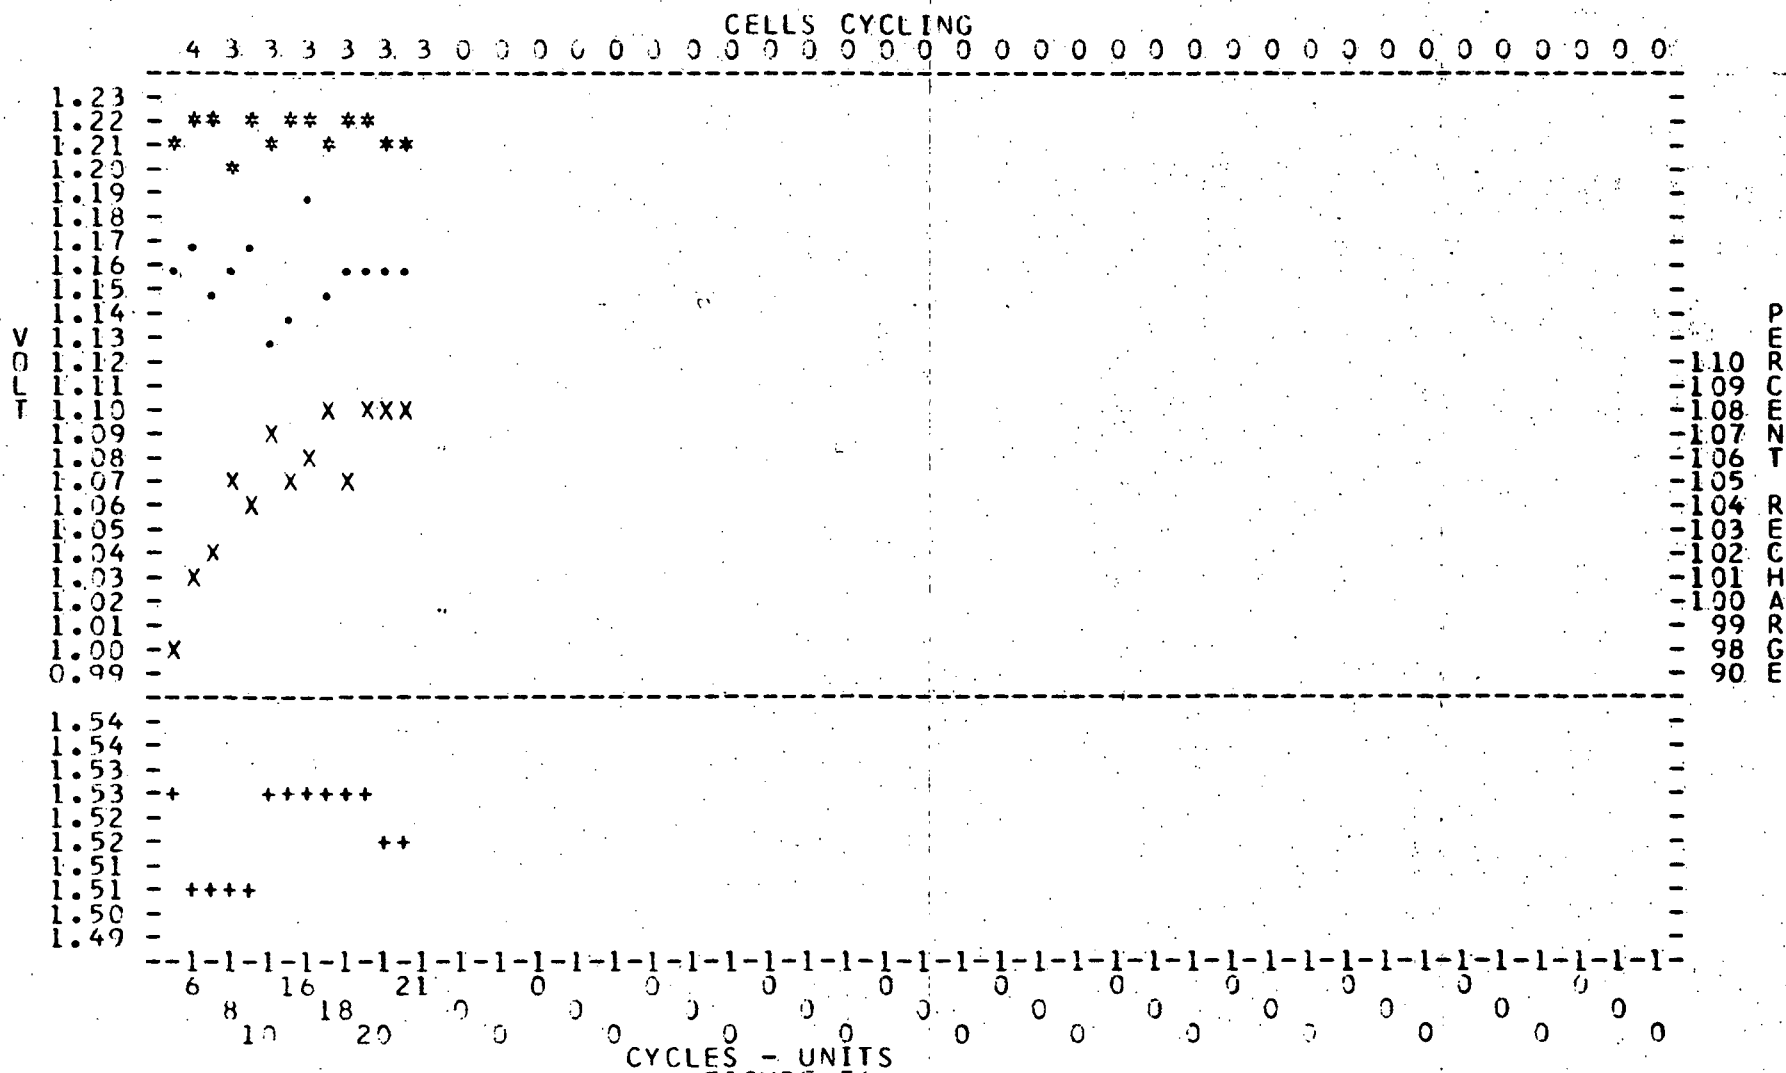


CYCLES - UNITS
FIGURE 54
105

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 038F MANF. EP
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 1.80
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 6.00 AH

CELLS CYCLING

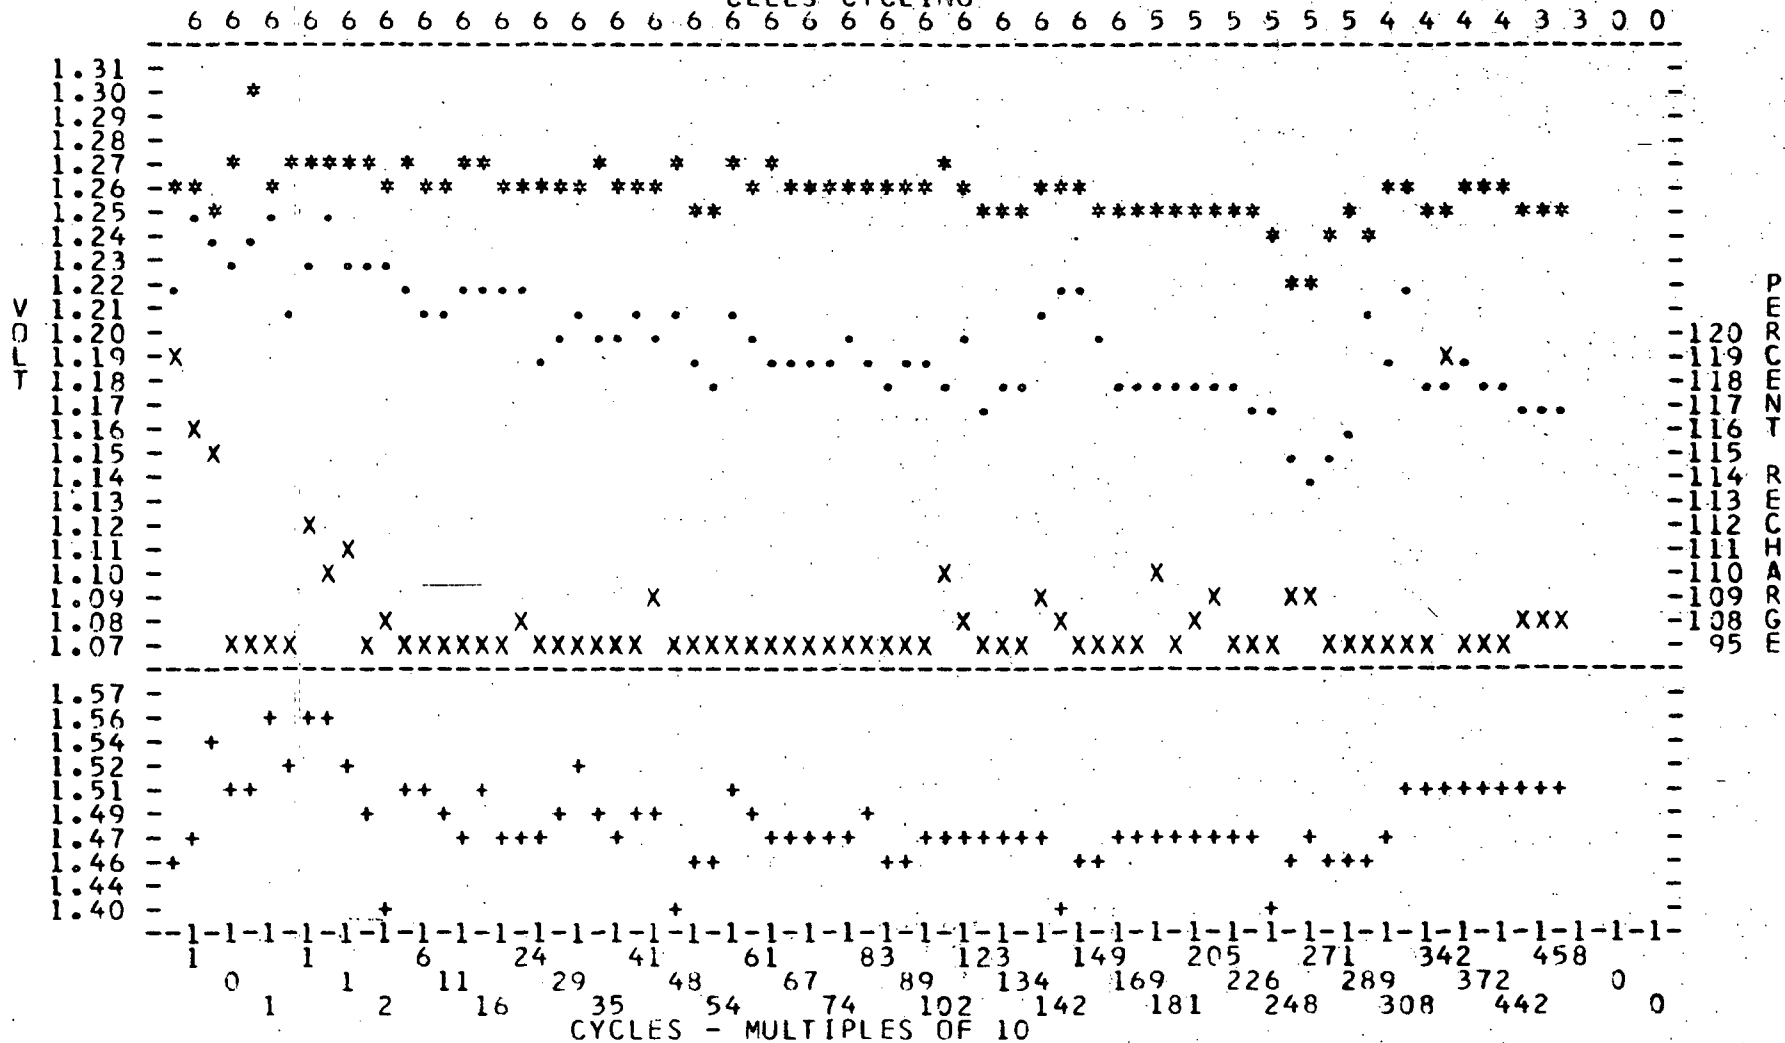

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 022C MANF. EP
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 1.80
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 6.00 AH

CELLS CYCLING

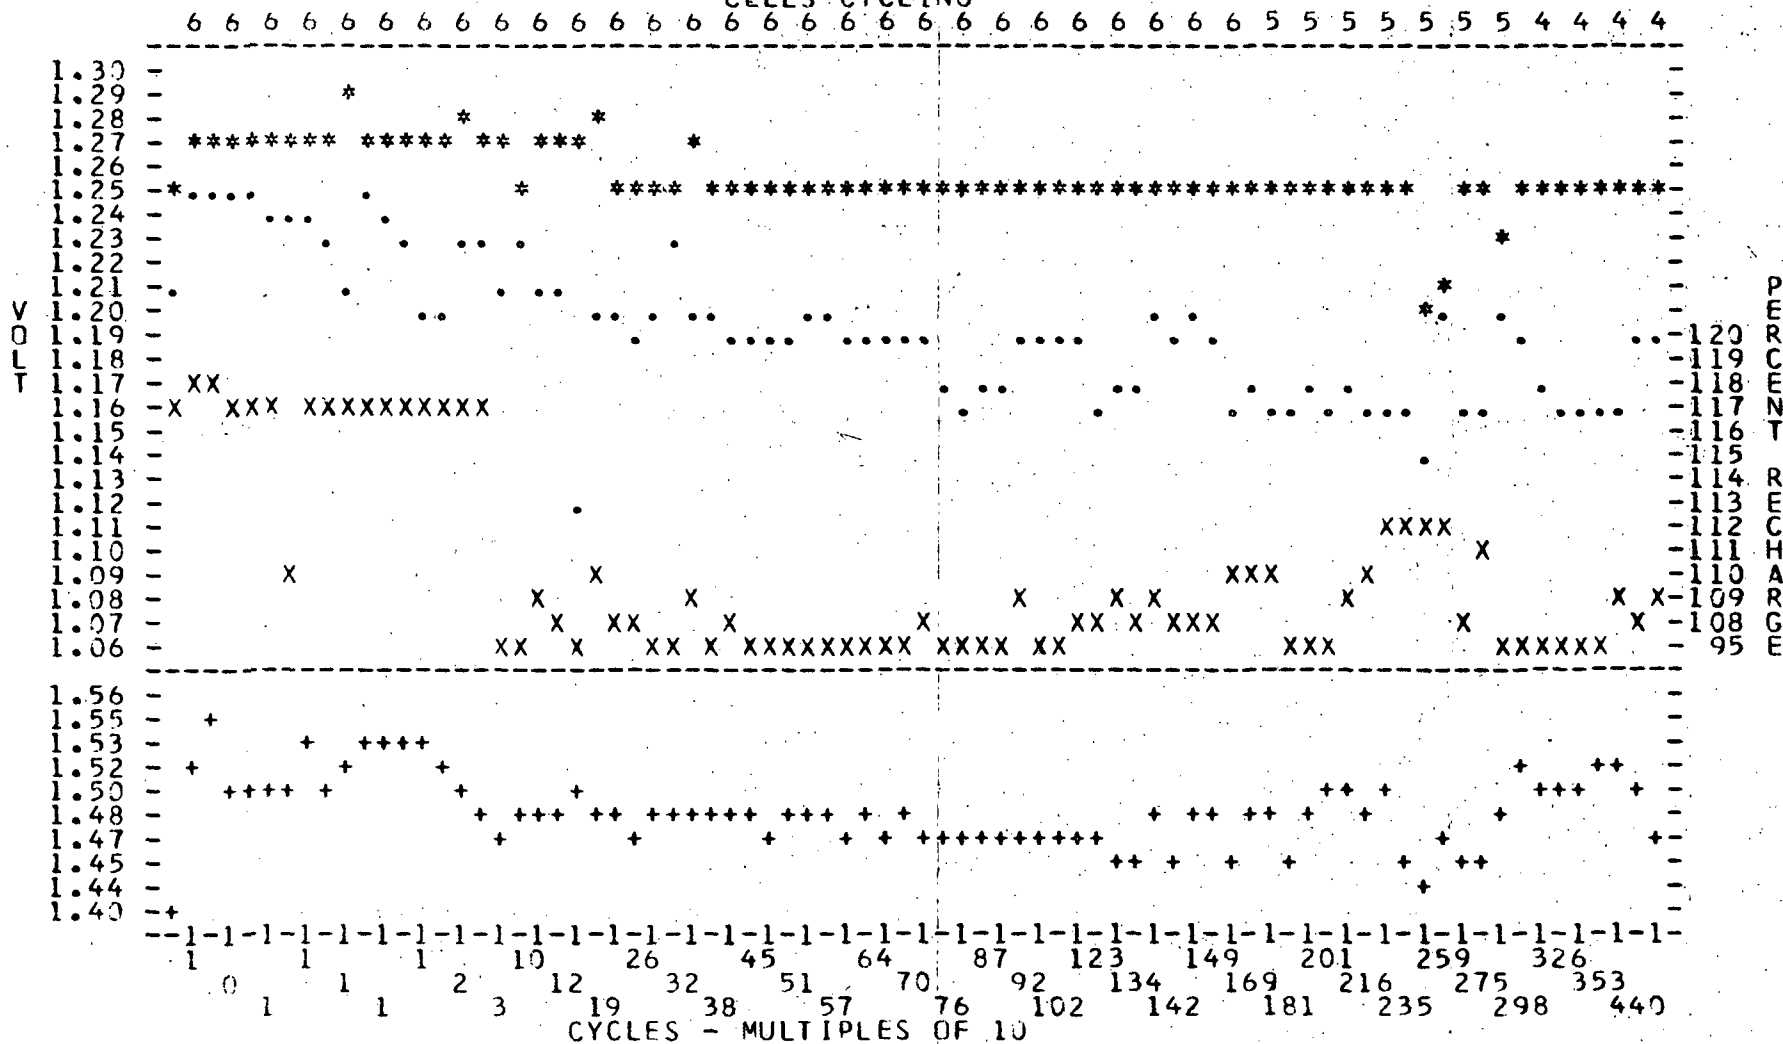


FIGURE 56


KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 046C MANF. EP
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 1.80
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 6.00 AH

CELLS CYCLING

6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 5 5 5 5 5 5 5 4 4 4 4 3 3 0 0 0 0 0 0

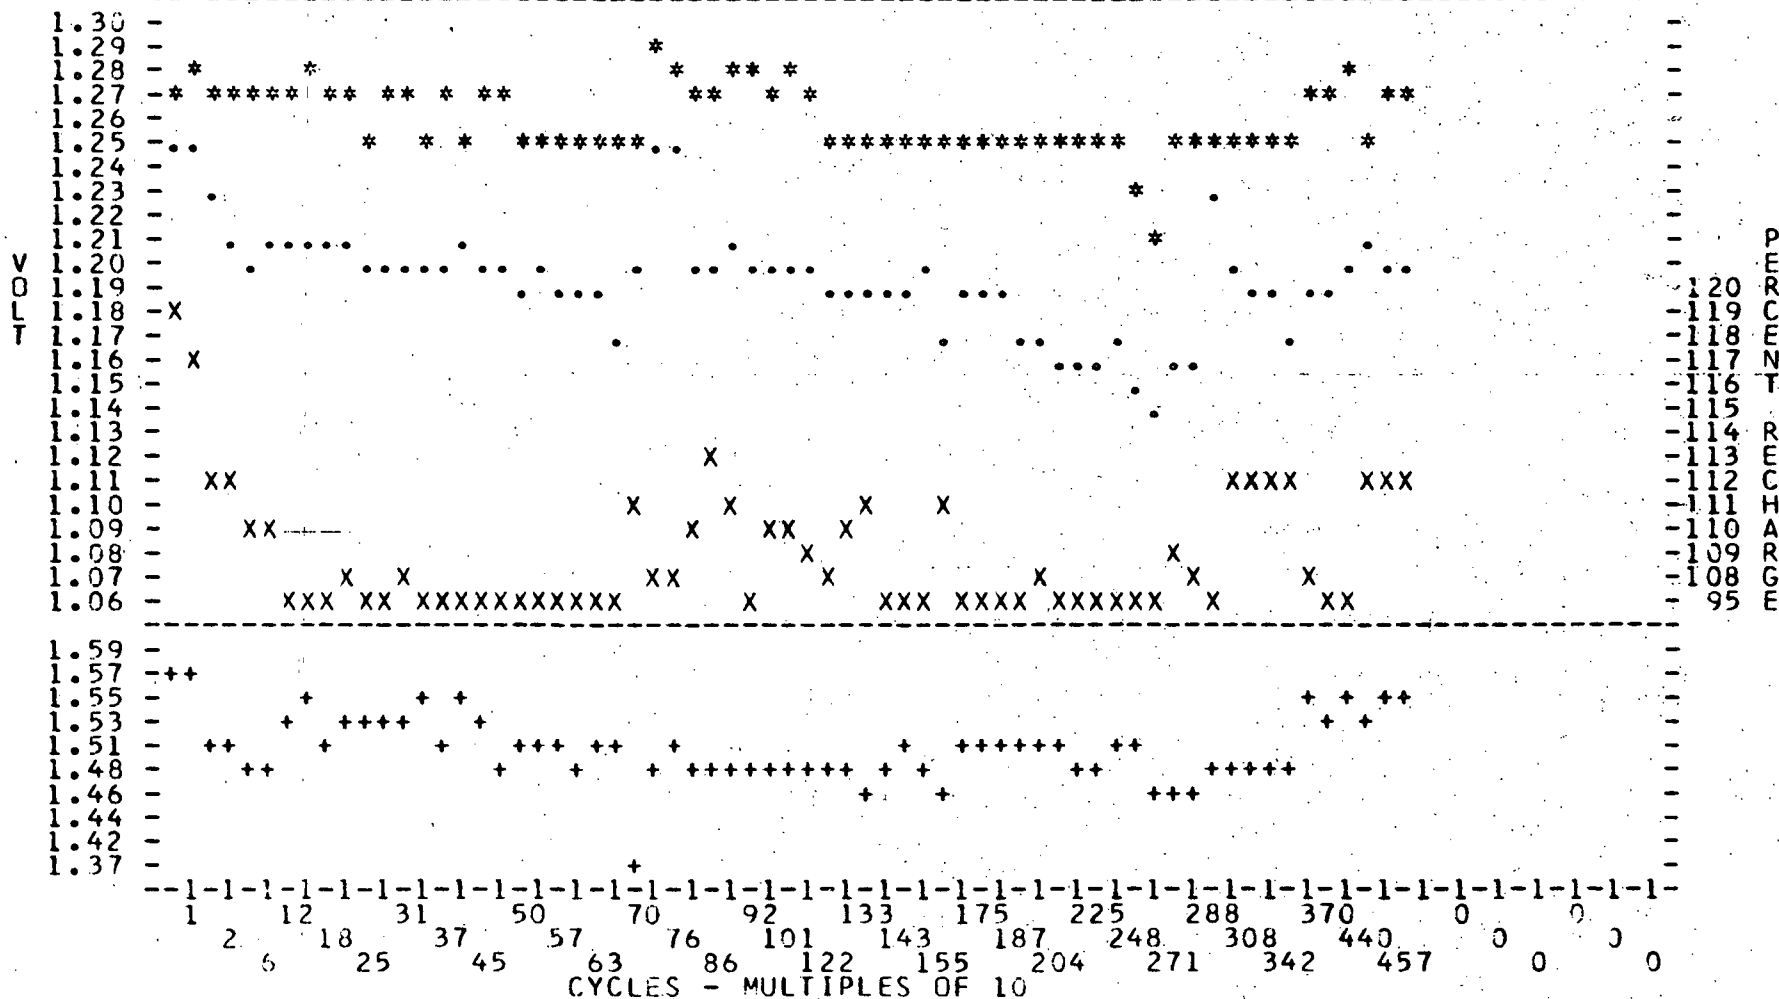

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 049B MANF. EP
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 1.80
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 6.00 AM

CELLS CYCLING

6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 6 5 5 5 5 5 5 5 4 4 4 4 3 0 0

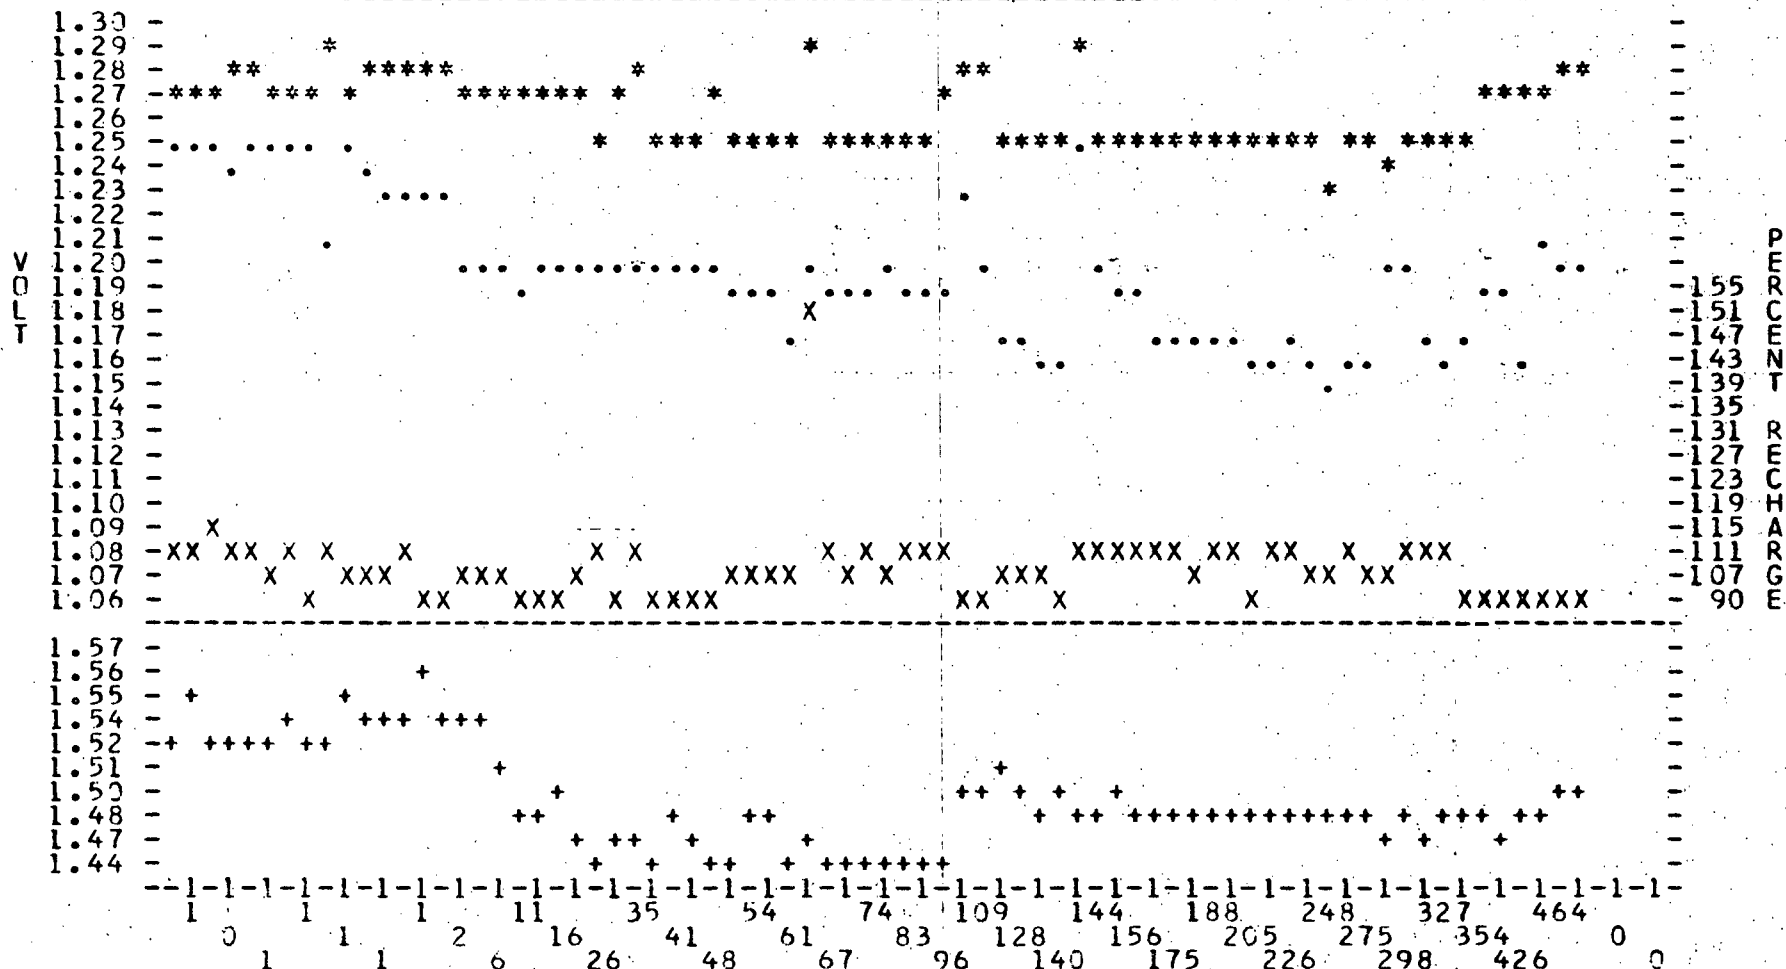



FIGURE 58

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 031C MANF. EP
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 1.80
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 6.00 AH

CELLS CYCLING

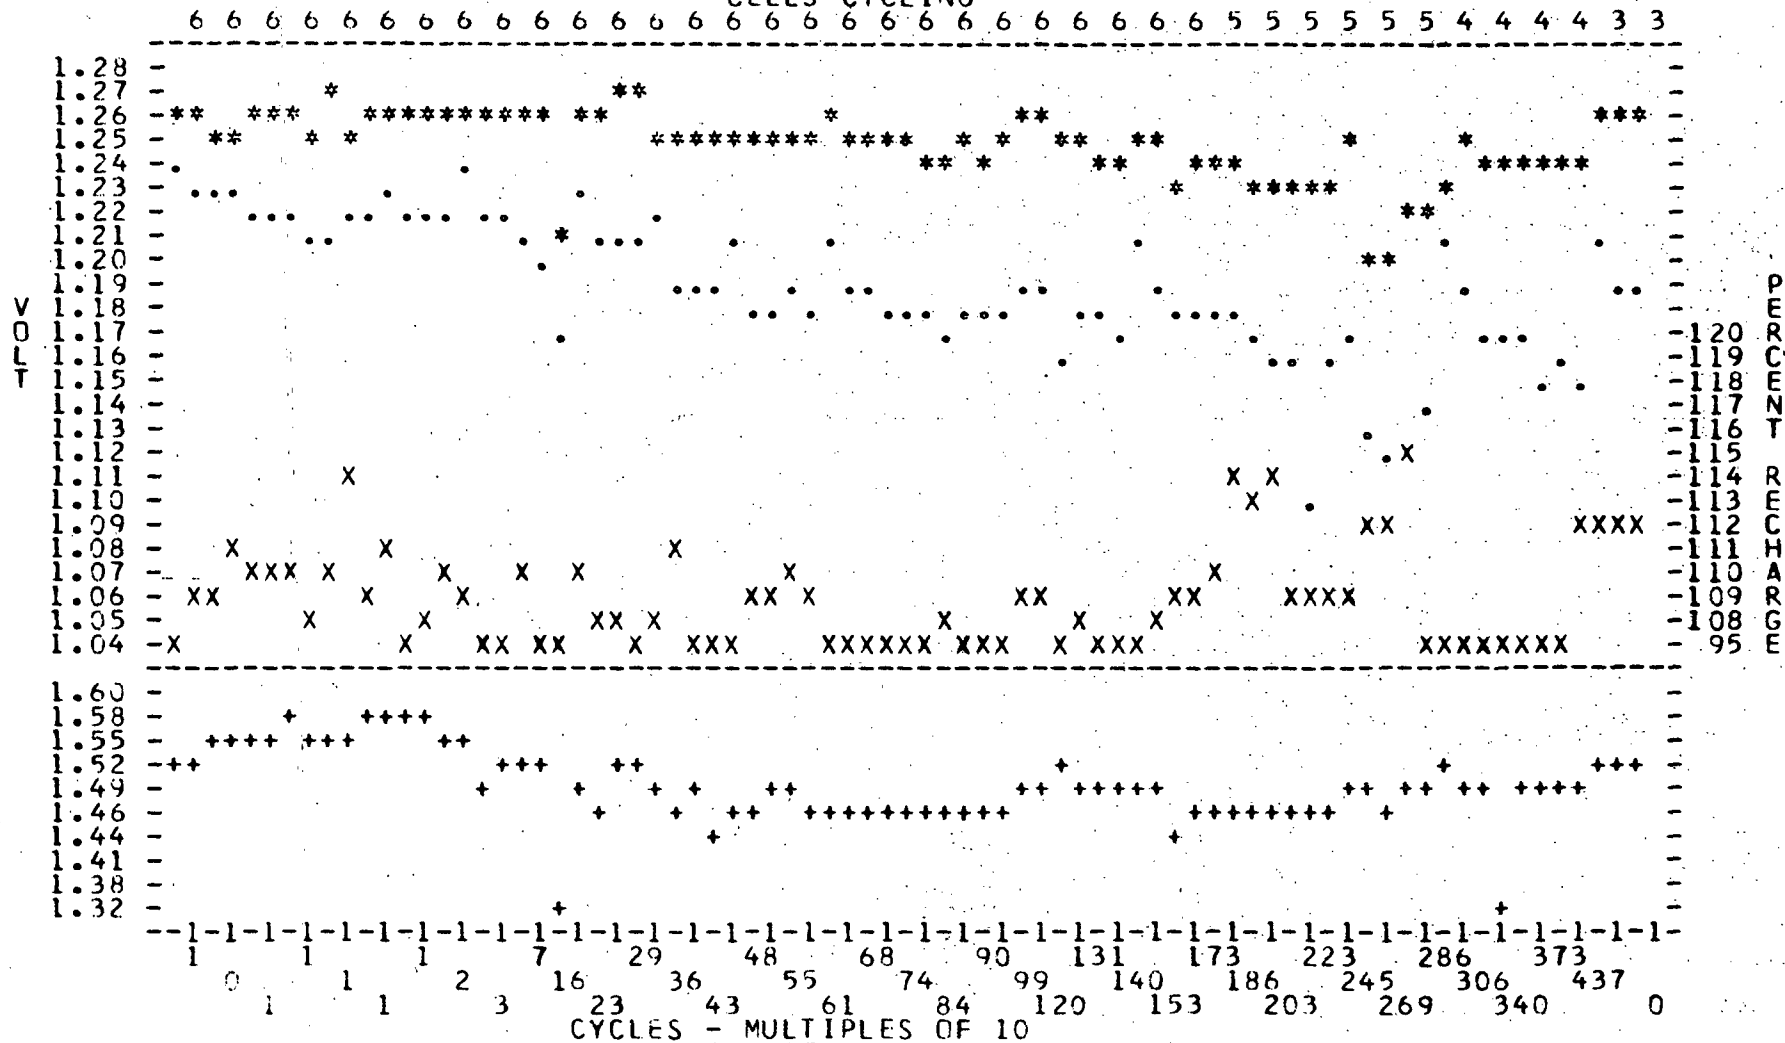


KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 0250 MANF. EP
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 1.80
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 6.00 AH

CELLS CYCLING

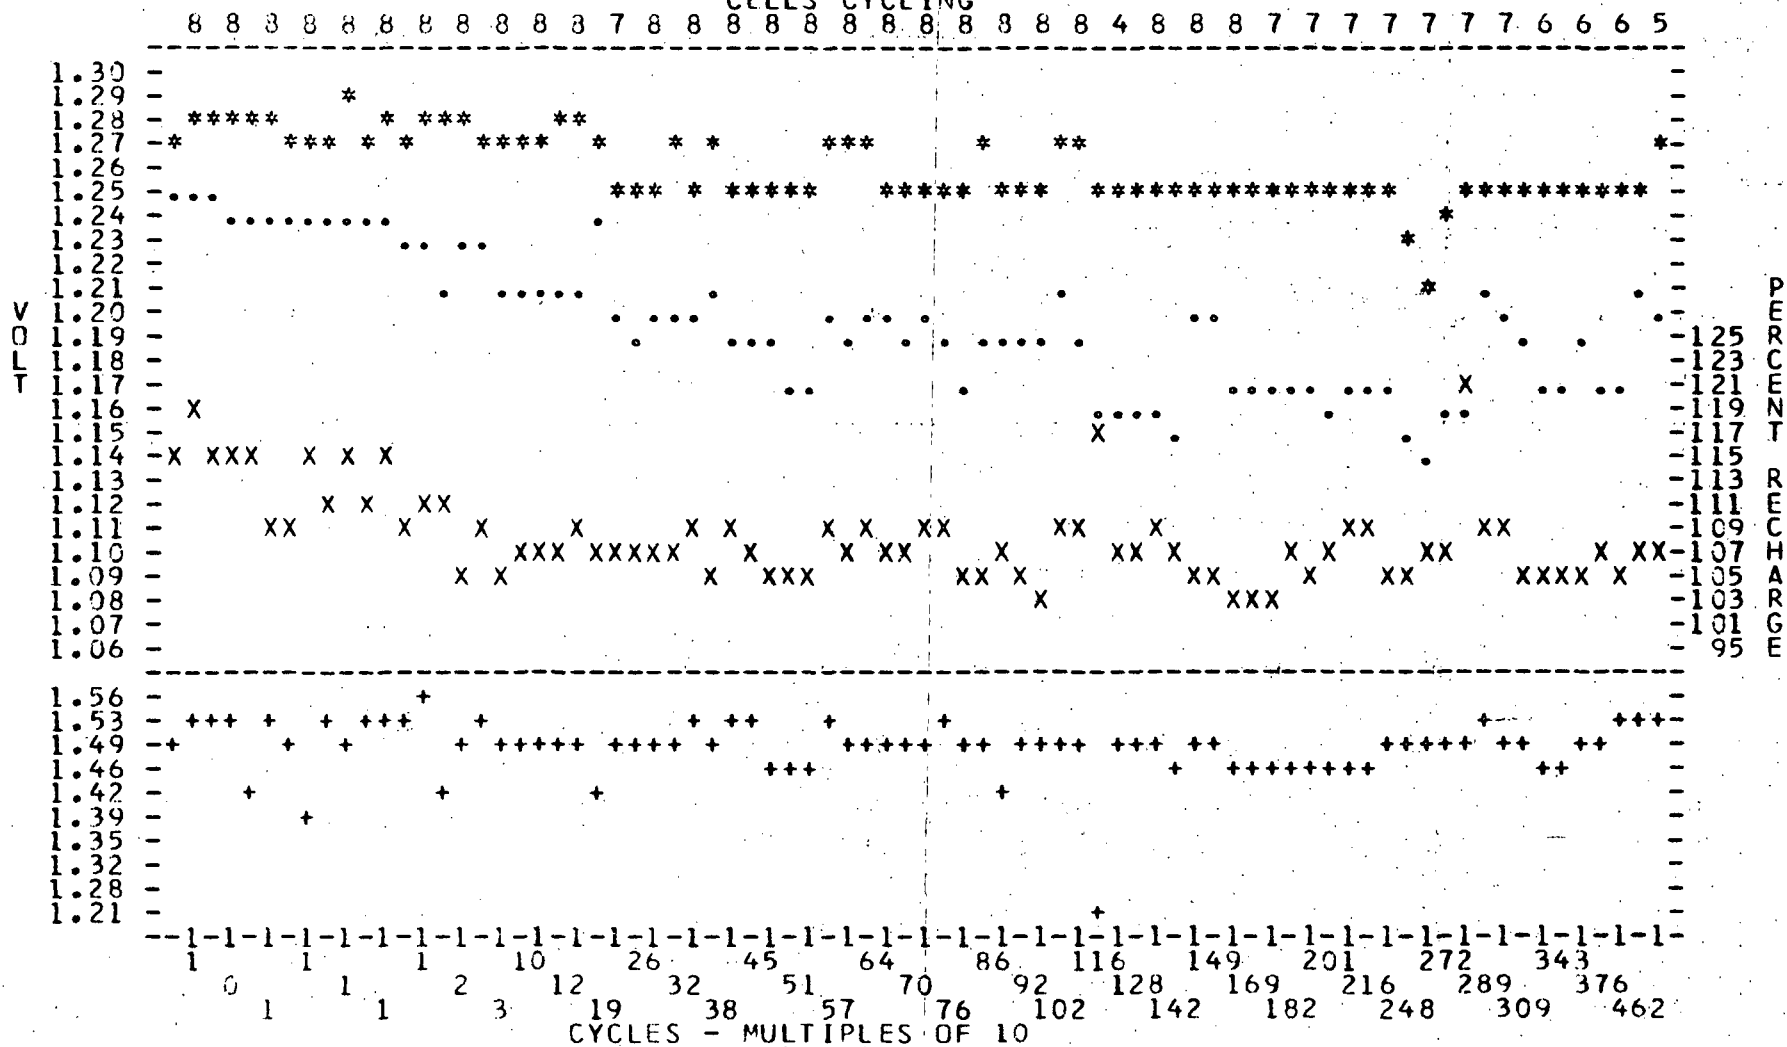

3. Gulton 6.0 ah (Nickel-Cadmium), Three 5-cell Packs:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour		
Temperature	*	*	*
Depth of Discharge	40%	25%	15%
Trip Voltage	170	170	170
Auxiliary Electrode Resistors (Ohms)	6.8	6.8	6.8
Pack Number	48B	24C	60B**
Precycling Capacity	7.40	7.20	7.45
88 Days	3.68	6.90	7.02
264 Days	3.76	6.30	6.45
440 Days	3.84	3.25	6.33
616 Days	F	3.10	5.61
792 Days		2.55	4.68
968 Days		3.15	3.21
1144 Days		F	2.25
1320 Days			3.02
1496 Days			2.07

F - Failed.

* These cells are in an ambient temperature which varies sinusoidally from 0° to 40° C within a period of 24 hours. After 260 days, the temperature cycle period was increased to 48 hours; all other parameters remained the same. The temperature cycle is stopped at 25° C for capacity checks.

** Test temperature was changed to a constant 20° C on 3-18-71 after more than 23,000 cycles.

c. Test Results:

(1) Performance on Cycling: (Figure 61) Cycling was started in April 1967. Packs 48B and 24C failed on cycles 6156 and 17,328, respectively. Pack 60B has completed 26,763 cycles with one cell failure.

(a) From the test data obtained to date the indications are that the auxiliary electrode, when used for charge control, operates satisfactorily over the range of temperatures under which these packs were operated, without temperature compensation.

(2) Failure Analysis: Analysis of the seven failed cells showed the major causes of failure to be shorting between the positive and auxiliary electrodes due to insufficient separator material between the edge of the positive plates and the auxiliary electrode. Separator deterioration, migration of negative material and blistered positive plates also were major reasons for failure. Other conditions found were high pressure, electrolyte leakage, weak weld between the auxiliary electrode and the bracket on the inside wall of the cell, and shorting between plates within the cell stack. This latter shorting is due to separator deterioration. The weak welds may result from failure to remove active material from the grid of the auxiliary electrode prior to welding to the bracket.

KEY	AVERAGE	CELL VOLTAGE	PACK 0608	MANF. GULTON	QEEL/C 72-1
*	-----	DISCHARGE	PERIOD HOURS	06.0 AH	
.	-----	END OF DISCHARGE	TEMP. DEGREE S C.	01.5	
+	-----	END OF CHARGE	CHARGE RATE AMPS	0/40	
x	-----	PERCENT RECHARGE	DEPTH OF DISCHARGE %	1.80	
				1.15	

CELLS CYCLING

VOFT

ԲԱՔՆԱՆԻ ԲԱՍԻԱՔՆԱ

2209118751659151435271190

CYCLES - MULTIPLES OF 100

FIGURE 61.

114

4. Gulton 6.0 ah (Nickel-Cadmium), Two 5-cell Packs:

a. Cell Description: See paragraph II.A., page 88.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Auxiliary Electrode Resistors (Ohms)
58D	*	25	170	6.8
36D	*	15	170	6.8

* These cells were in an ambient temperature which varied sinusoidally from 0° to 40° C within a period of 48 hours until 3-1-71; at which time the test temperature was changed to 20° C.

c. Test Results:

(1) Performance on Cycling: (Figures 62 and 63)

Cycling was started in January 1969. Packs 58D and 36D have completed 16,318 and 16,332 cycles, respectively, with no cell failures, although one cell from each pack was removed after approximately 2 years of cycling and sent to Goddard Space Flight Center. These packs are being cycled without interruption for capacity check. The cycle life results will later be compared to packs that do receive capacity checks every 88 days.

PACK 058D	MANF. GULT
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	0/40
CHARGE RATE AMPS	3.00
DEPTH OF DISCHARGE %	25

MANF. GULTON 06.C AH



RESEARCH
INFORMATION

CYCLES - MULTIPLES OF 100

FIGURE 62

116

X-----PERCENT RECHARGE

DEPTH OF DISCHARGE %

GE % 15

QEEL/C 72-1

CELLS CYCLING

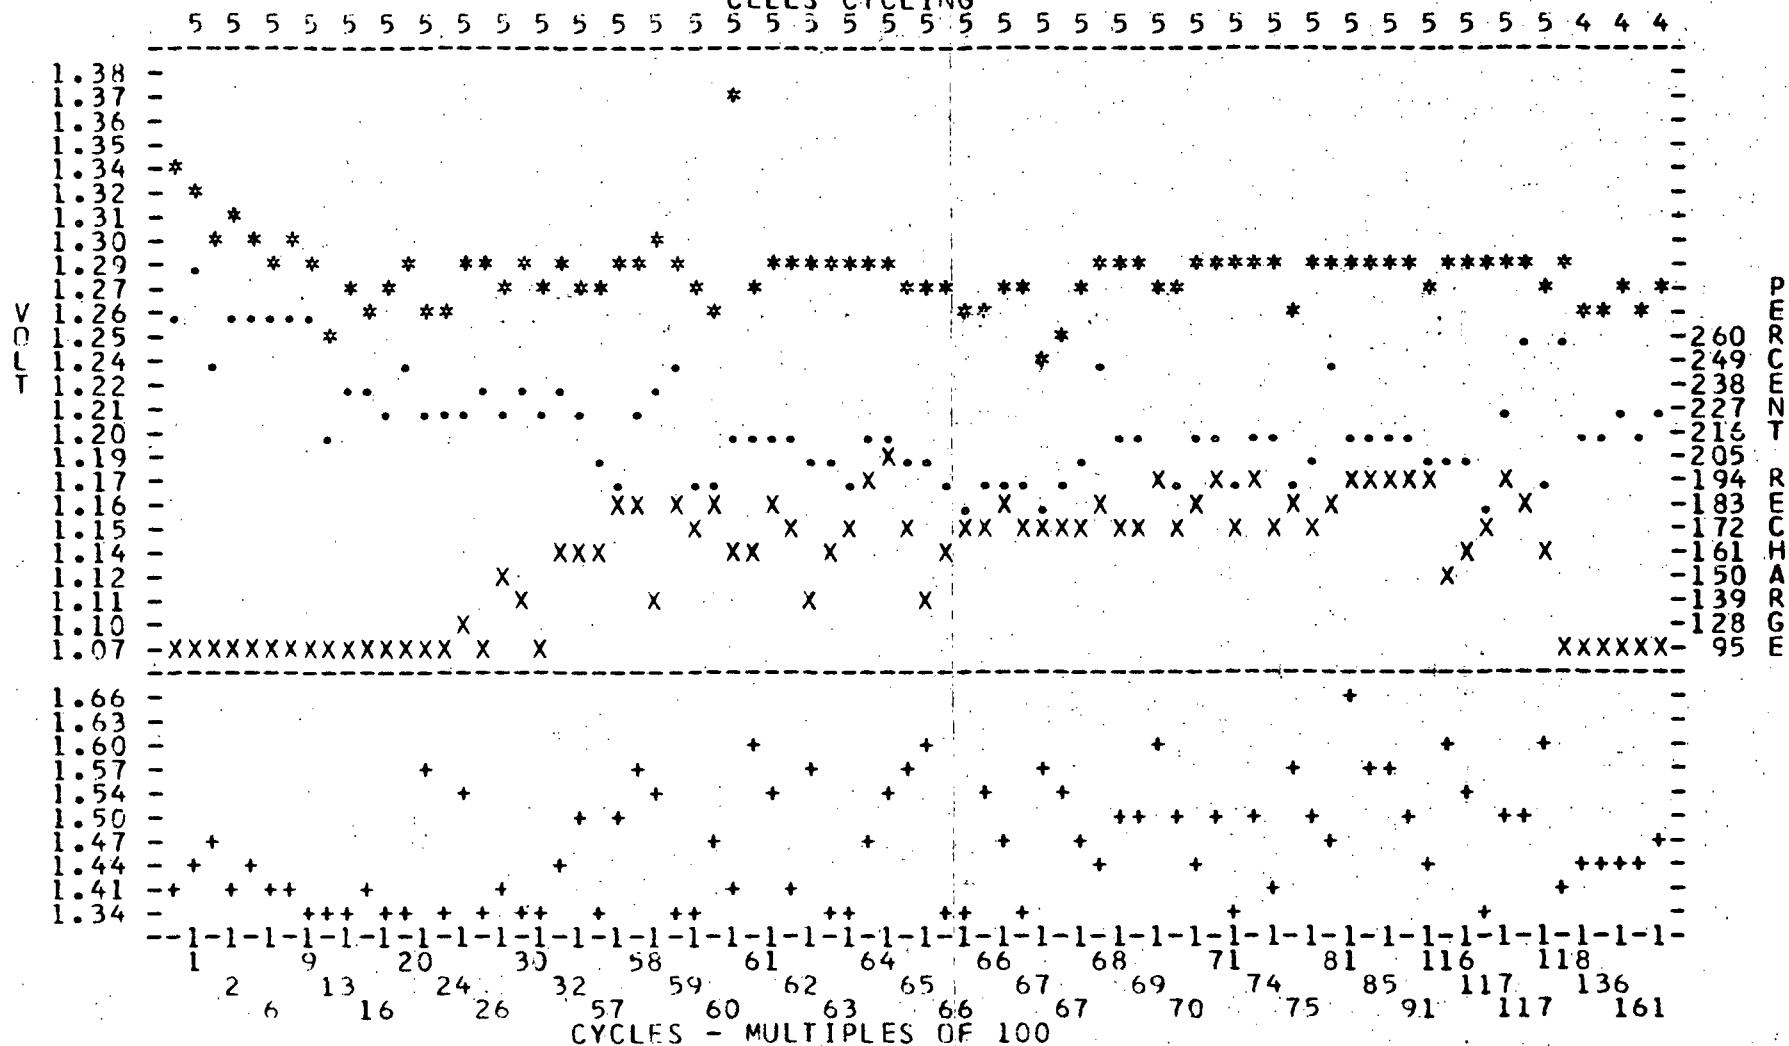


FIGURE 63

117

5. Gulton 6.0 ah (Nickel-Cadmium), Three 5-cell Packs:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour		
Temperature	20°	20°	20°
Depth of Discharge	25%	25%	25%
Trip Voltage (MV)*	150	300	450
Resistors (Ohms)	6.8	6.8	6.8
Pack Number	28D	40D	52D
Precycling Capacity	7.65	7.74	7.65
88 Days	6.96	8.60	7.65
264 Days	4.35	8.95	7.95
440 Days	6.25	8.45	6.15

* The trip voltage levels of packs 40D and 52D were changed to 250 and 300 MV, respectively.

Packs were placed on voltage limit control 6-20-71.

c. Test Results:

(1) Performance on Cycling: (Figures 64 through 66)
Cycling was started in April 1970. Packs 28D, 40D and 52D have completed 8610, 8653 and 8253 cycles, respectively, with no cell failures.

```

*-----MIDDLE DISCHARGE
+-----END OF DISCHARGE
+-----END OF CHARGE
X-----PERCENT RECHARGE

```

ORBIT PERIOD HOURS

TEMP. DEGREES C.

20

CHARGE RATE AMPS

3.00

DEPTH OF DISCHARGE. %

25

QEEL/C 72-1

06.0 AH

CELLS CYCLING

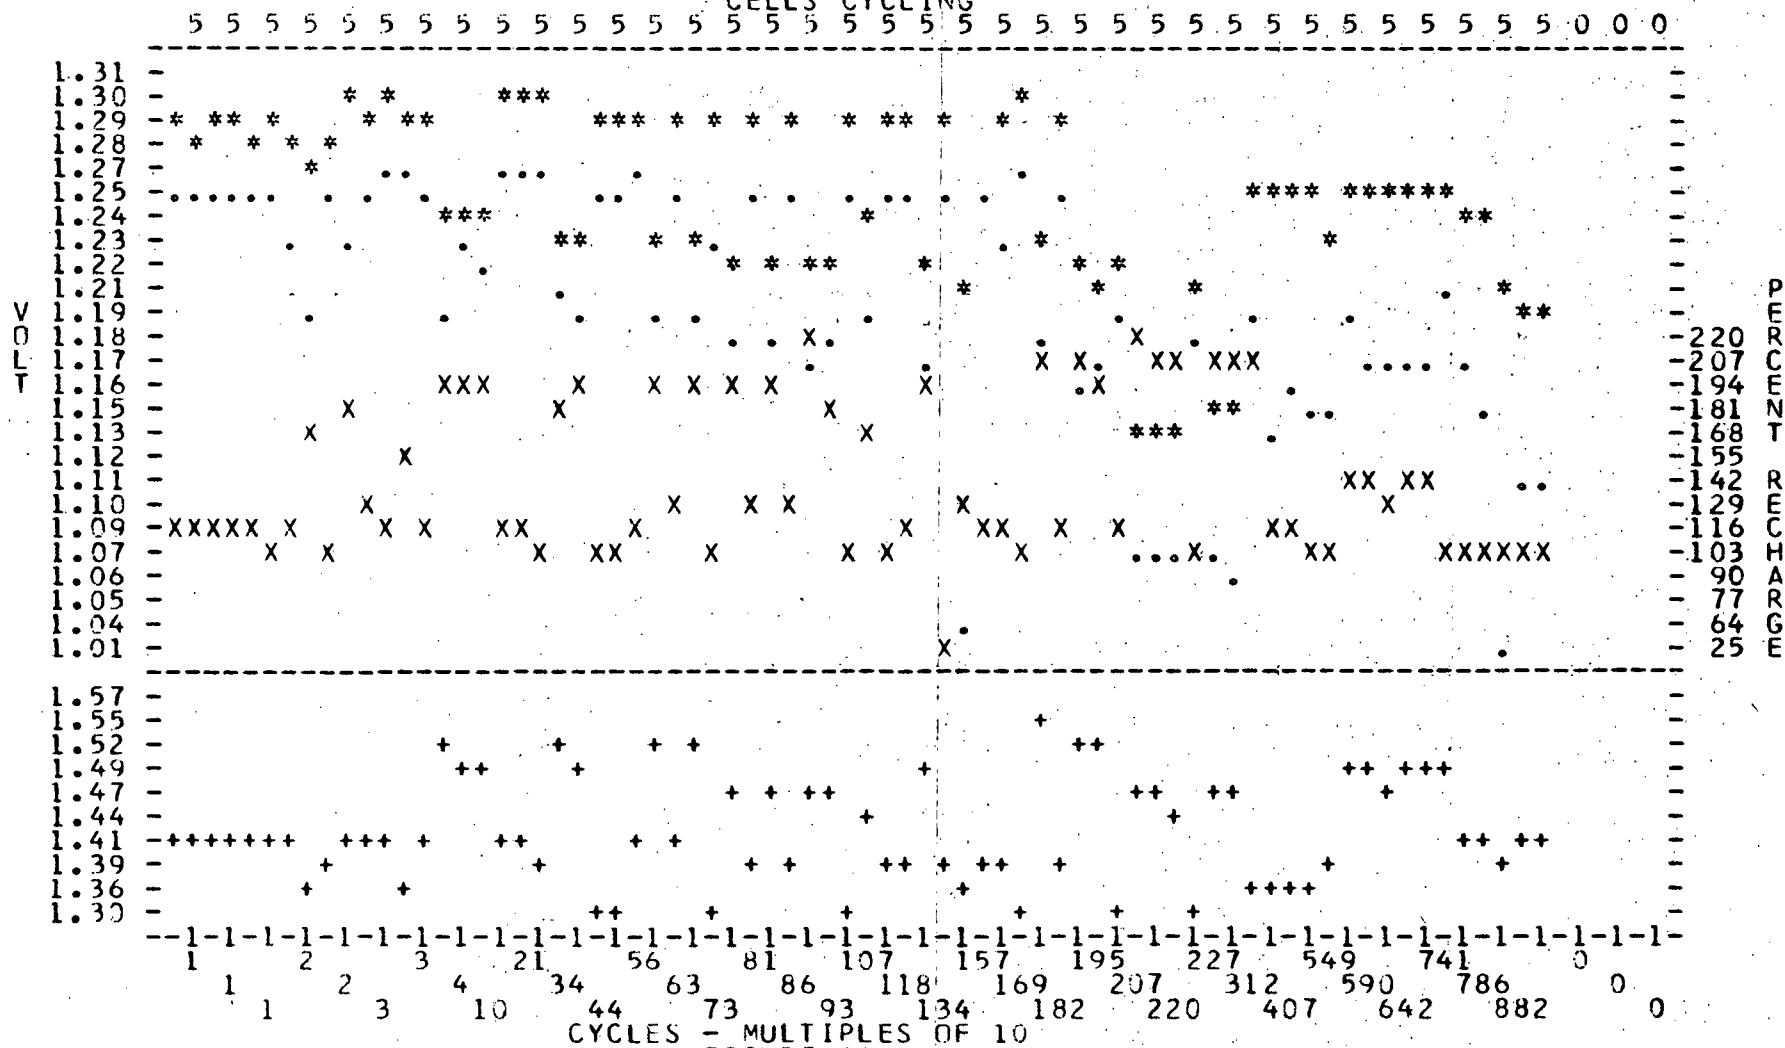



FIGURE 64

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 040D MANF. ASTRO
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 3.00
 DEPTH OF DISCHARGE % 25


QEEL/C 72-1
 06.0 AH

CELLS CYCLING

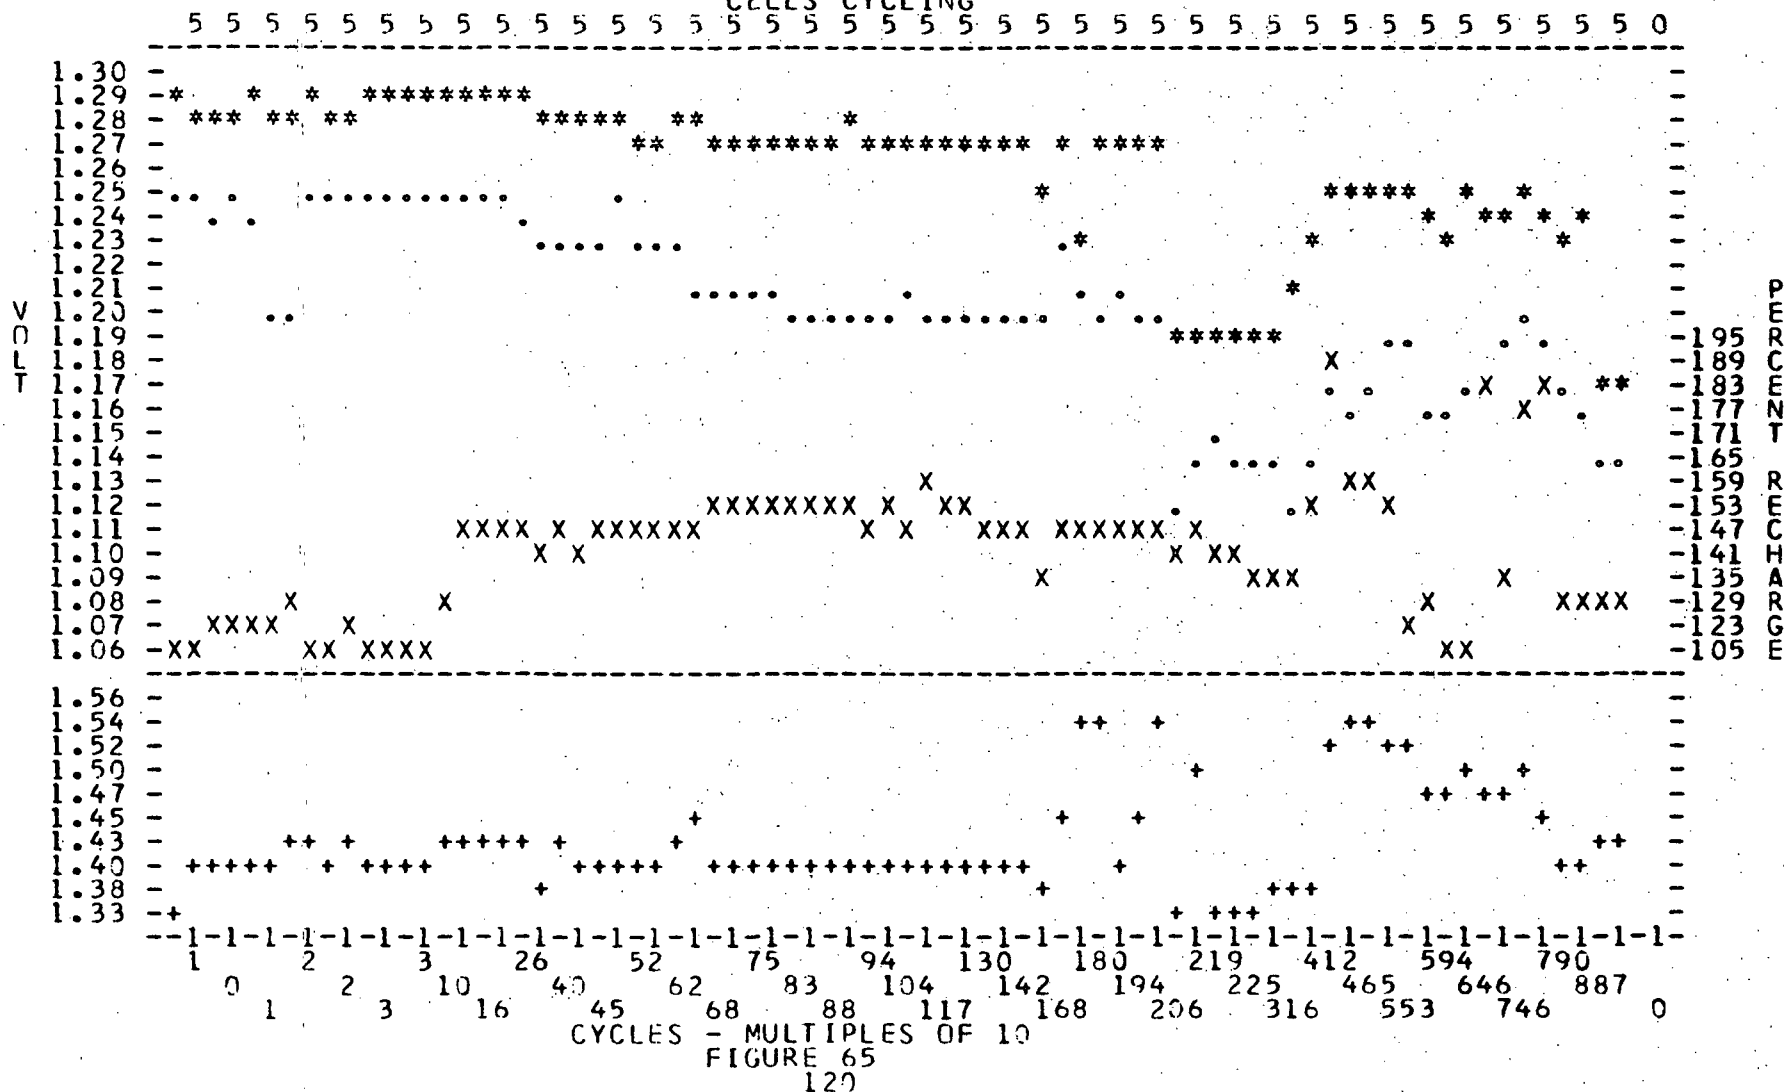

PACK 0520	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	20
CHARGE RATE AMPS	3.00
DEPTH OF DISCHARGE %	25

PACK 0520	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	20
CHARGE RATE AMPS	3.00
DEPTH OF DISCHARGE %	25

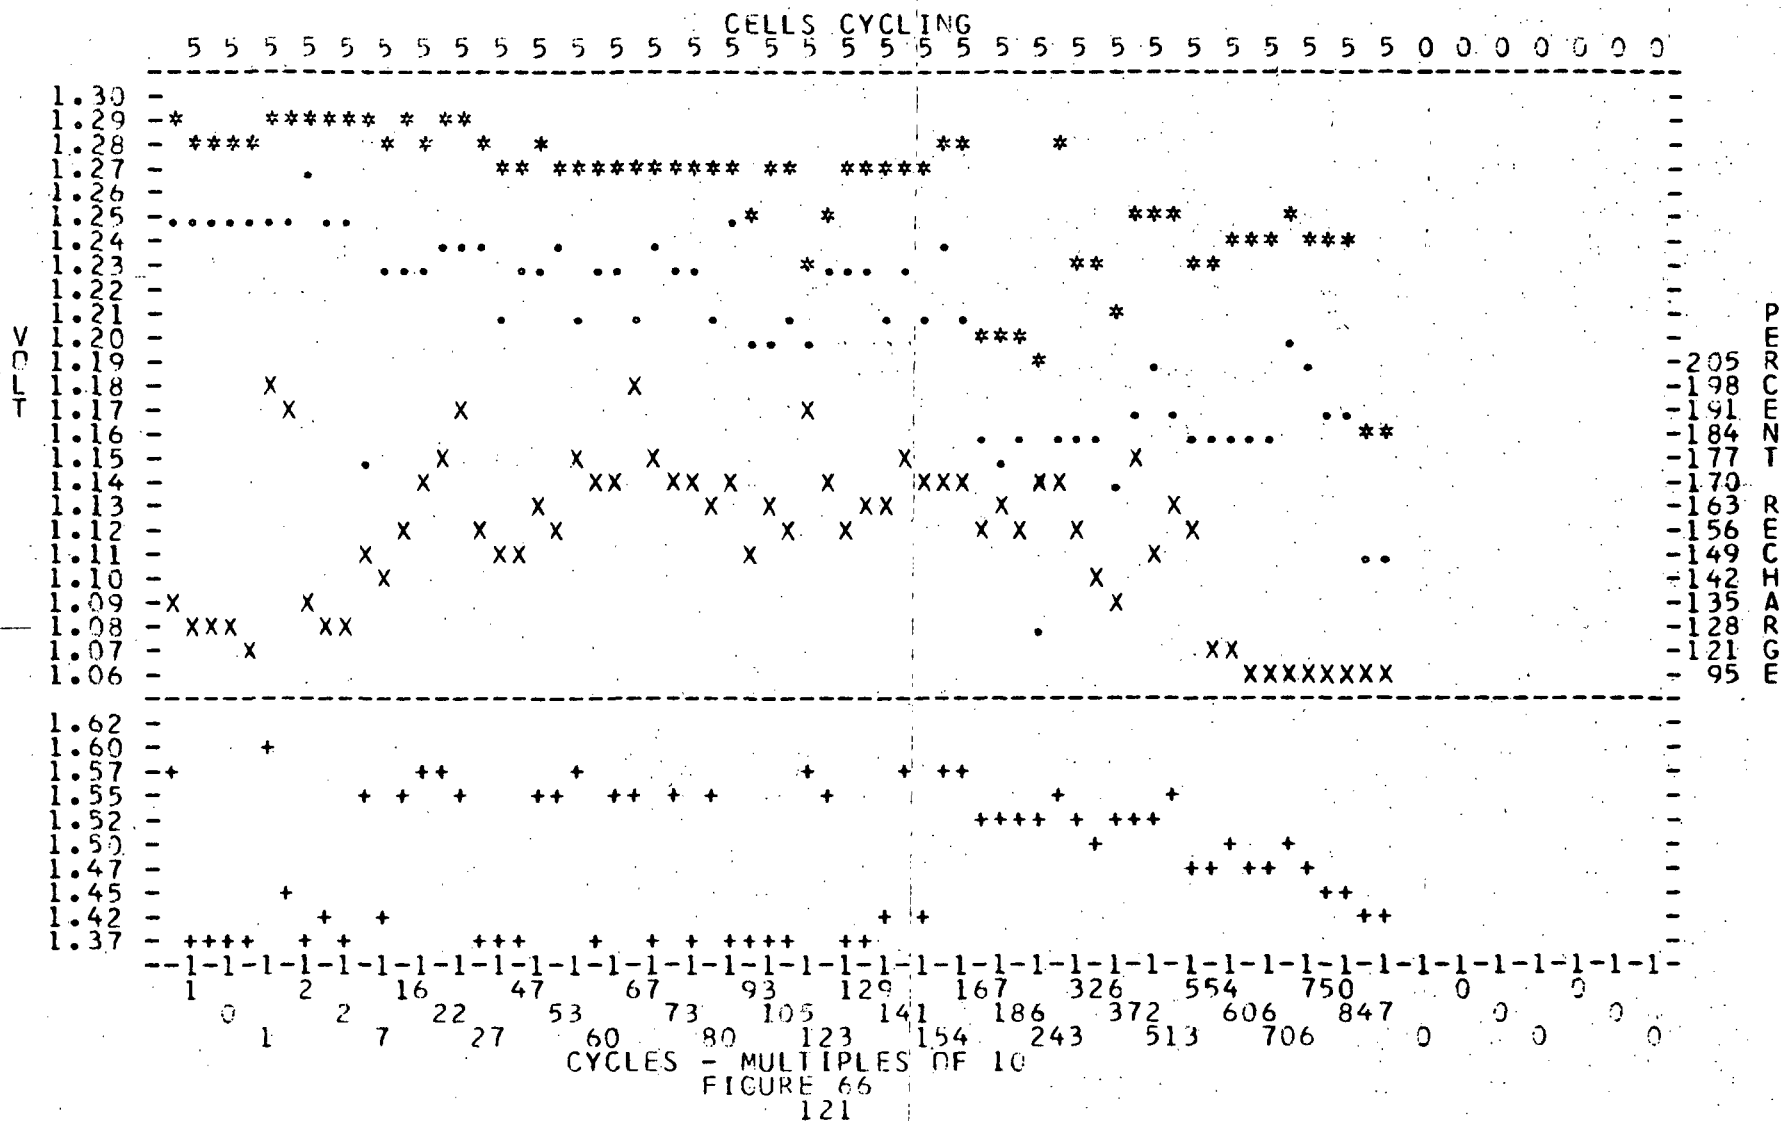

6. Gulton 12.0 ah (Nickel-Cadmium), Four 5-cell Packs:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour			
Temperature	0°	0°	25°	40°
Depth of Discharge	25%	40%	40%	25%
Trip Voltage (MV)	70	70	150	230
Resistors (Ohms)	6.2	6.2	6.2	6.2
Pack Number	70A	71B	11B	47B
Precycling Capacity	15.0	15.4	15.9	14.3
88 Days Disch #2	14.9	15.2	14.0	3.7
264 Days Disch #2	14.7	14.4	6.5	3.2
440 Days Disch #2	11.6	11.5	9.0	3.4
616 Days Disch #2	9.5	9.1	7.4	F
792 Days Disch #2	9.1	10.4	F	
968 Days Disch #2	8.1	7.8		
1144 Days Disch #2	*	D		
1320 Days Disch #2	6.4			
1496 Days Disch #2	5.7			
1672 Days Disch #2	6.0			

* Capacity check not performed.

D - Discontinued.

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figure 67) Cycling was started on Pack 11B in October 1966, on packs 47B and 71B in January 1967 and on pack 70A in February 1967. Pack 70A has completed 27,399 cycles to date with no failures. Packs 71B, 11B and 47B failed on cycles 15,275, 11,933 and 6536, respectively.


(2) Failure Analysis: Analysis of the nine failed cells showed that the failure was due to separator deterioration and migration of the negative plate material. Other conditions found in these cells were high internal pressure and electrolyte leakage.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 070A MANF. GULTON 12.0 AH
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 6.00
 DEPTH OF DISCHARGE % 25

WHEEL/C 72-1

CELLS CYCLING

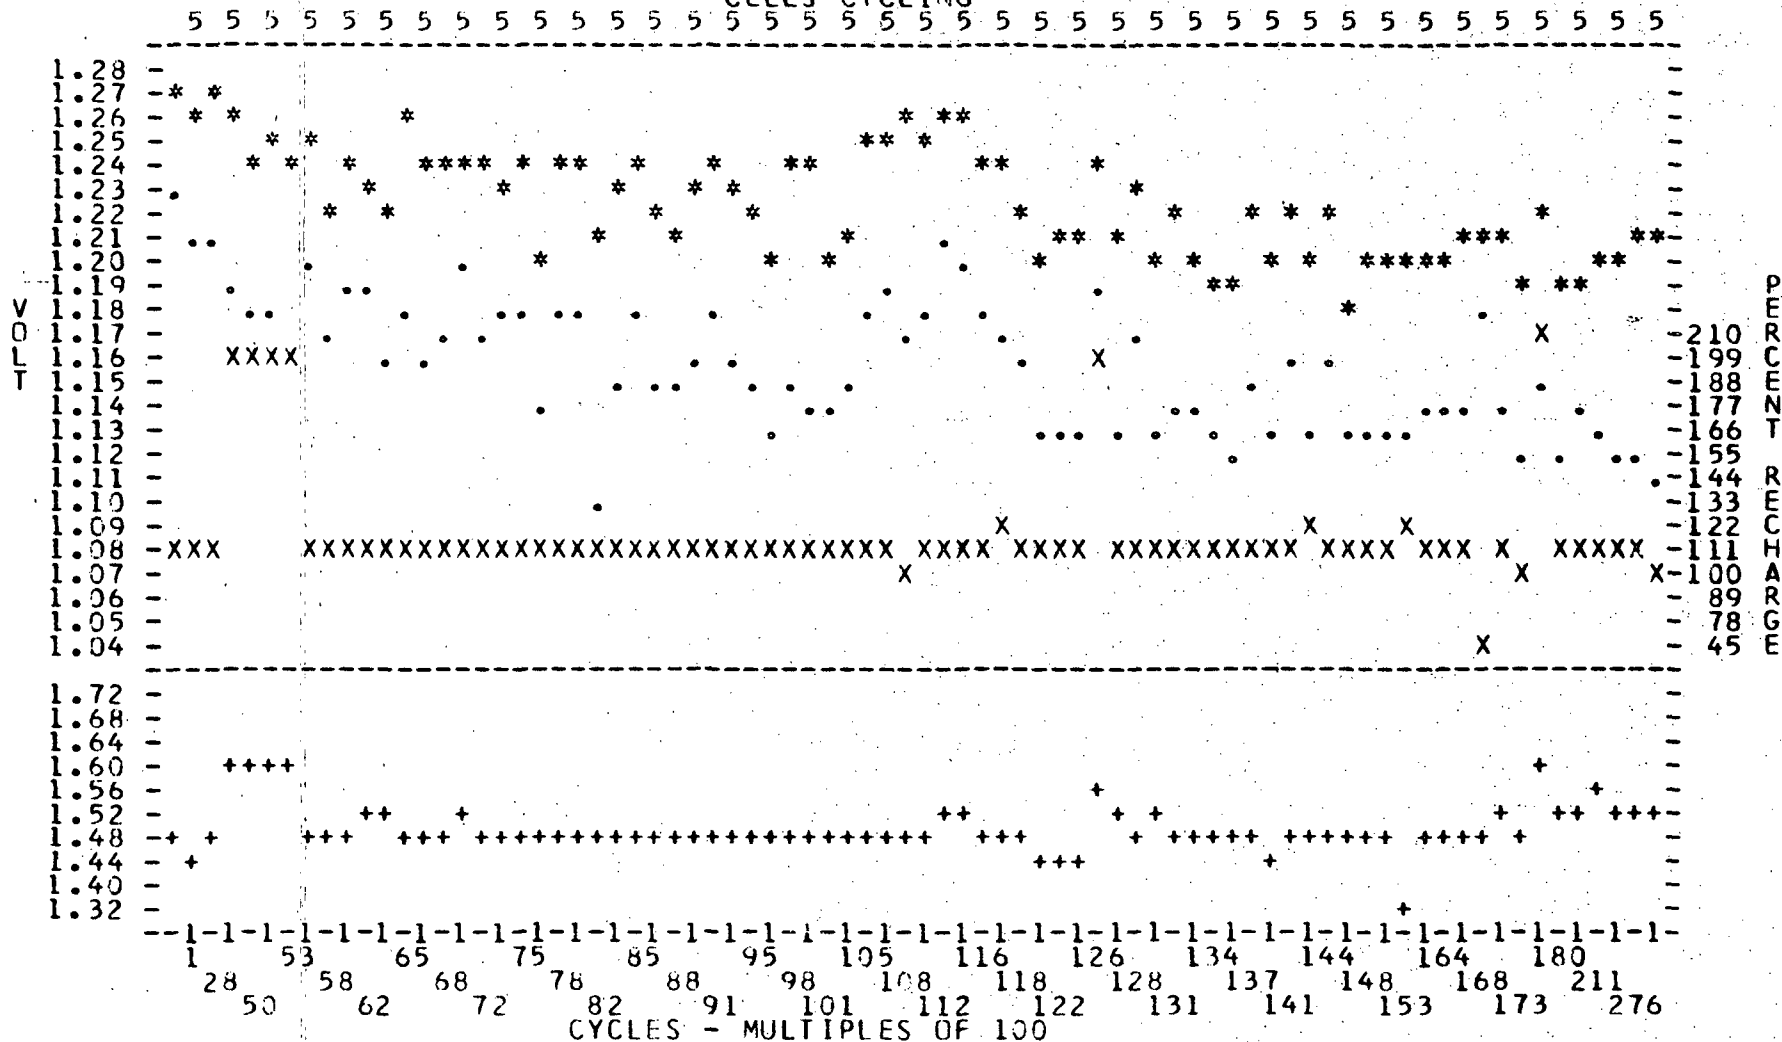

7. Gulton 20 ah (0A0), (Nickel-Cadmium), Three 5-cell Packs:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour		
Temperature	0°	25°	40°
Depth of Discharge	15%	15%	15%
Trip Voltage (MV)	250	250*	300
Resistors (Ohms)	47	47	47
Pack Number	54B	19B	38E
Precycling Capacity	22.7	23.3	17.3
88 Days	25.1	19.8	5.6
264 Days	24.7	14.9	2.9 F
440 Days	24.8	8.7	
616 Days	22.1	9.4	
792 Days	6.7	8.2	
968 Days	17.1	8.4	
1144 Days	16.9	11.9	
1320 Days	14.9	5.9	

* Placed on voltage limit control (3-4-71) due to both auxiliary electrode cells in the pack failed.

F - Failed.


c. Test Results:

(1) Performance on Cycling: (Figures 68 and 69)
Cycling was started in March 1968. Packs 54B and 19B have completed 21,611 and 21,649 cycles, respectively, with two failures in pack 19B. Pack 38E failed after 4943 cycles due to loss of capacity at high temperature.


(2) Failure Analysis: Analysis of the five failed cells showed that failure was due largely to separator deterioration. Migration was not as extensive as that seen in most failed cells. Other conditions included blistering and high pressure as evidenced by gas escaping from the punctured cell.

PACK 054B	MANF. GULTON
ORBIT PERIOD HOURS	1.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	8.00
DEPTH OF DISCHARGE %	15

20.0 AH

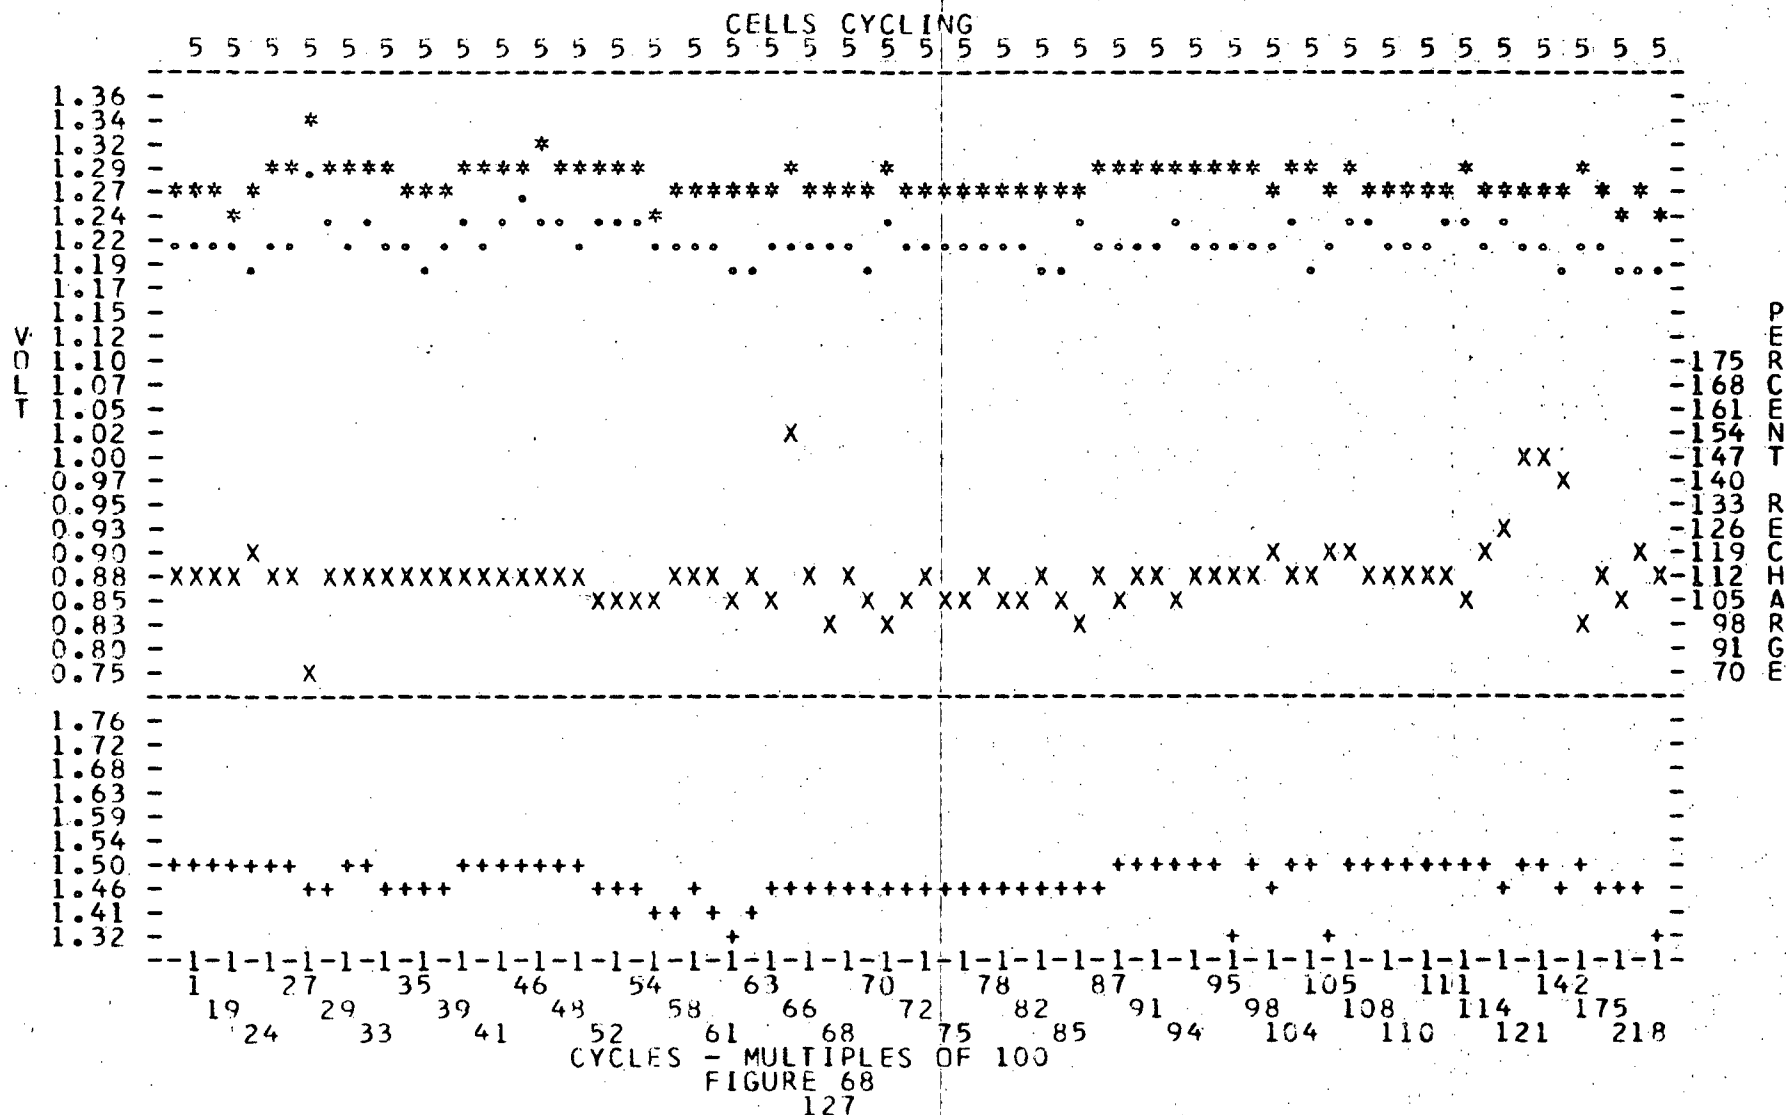

PACK 019B MANF. GULTON 20.0 AH QEE/L/C 72-1
ORBIT PERIOD HOURS 01.5
TEMP. DEGREES C. 25
CHARGE RATE AMPS 8.00
DEPTH OF DISCHARGE % 15

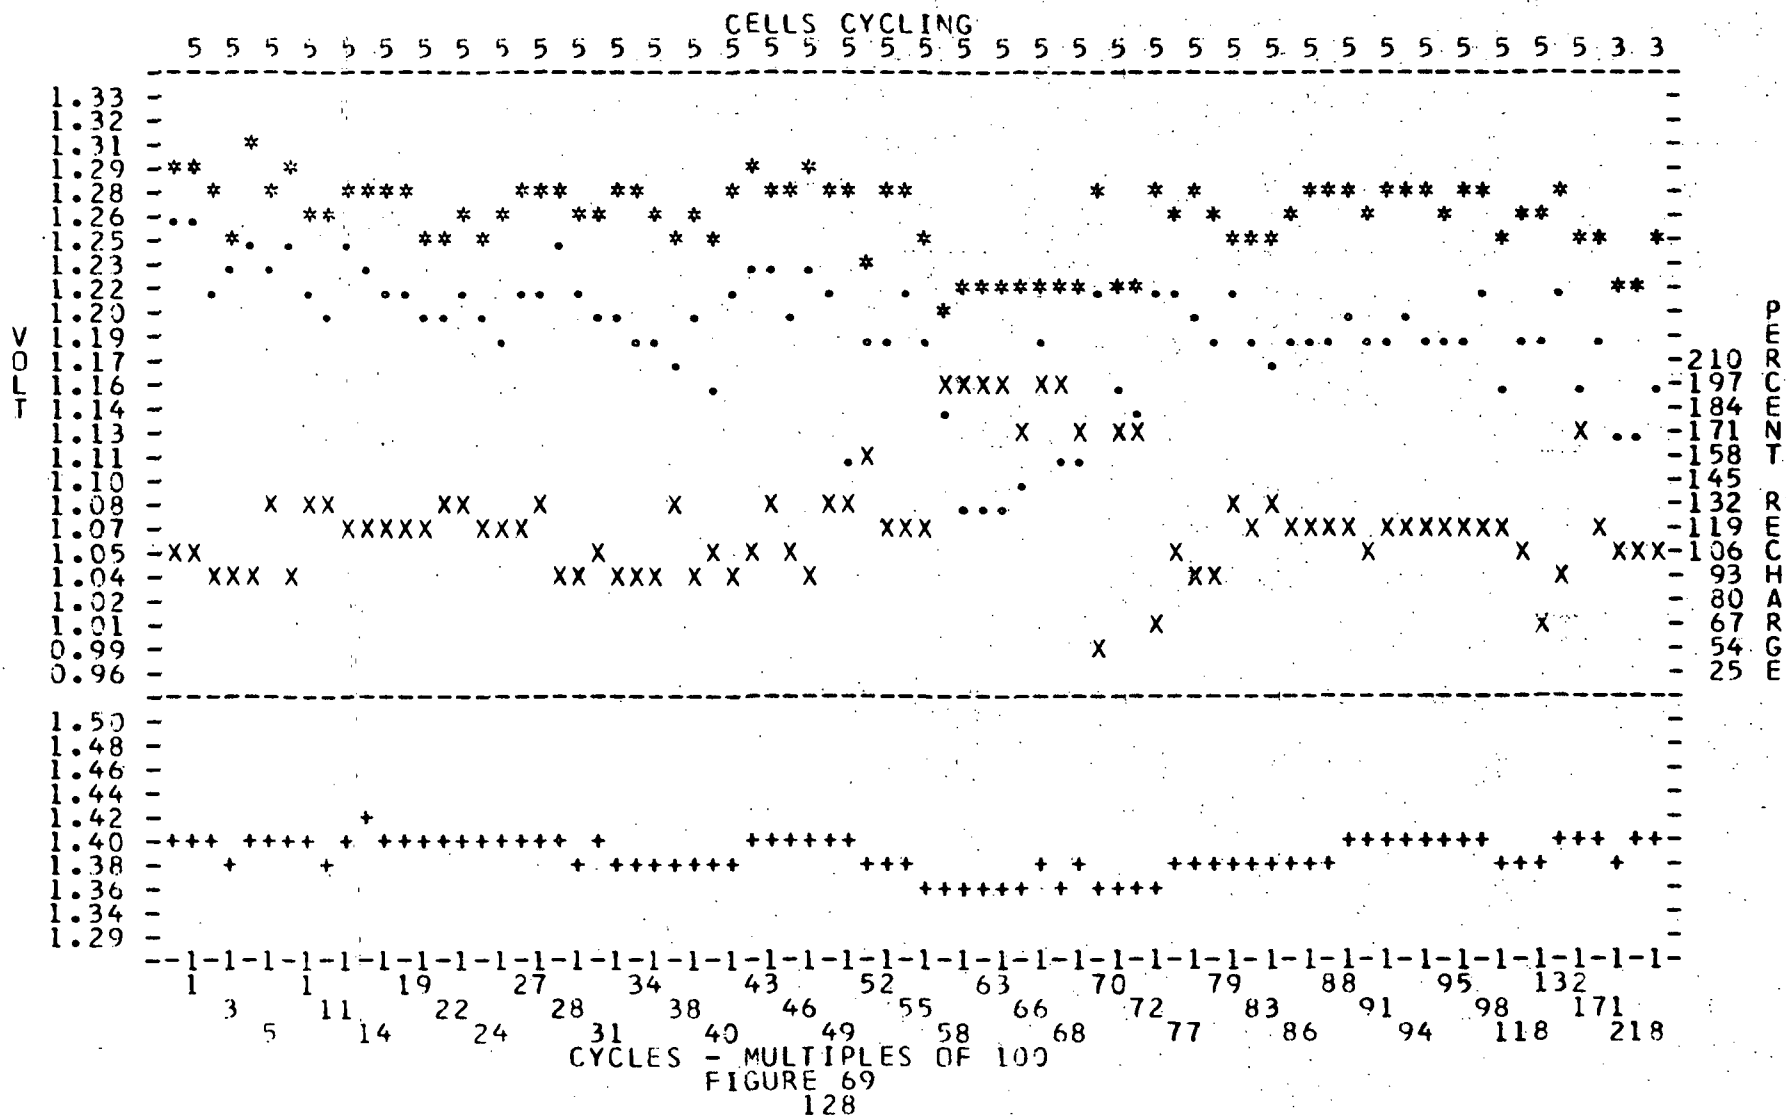

8. Gulton 20 ah (OAO, Nickel-Cadmium, Precharge), One 6-cell Pack:

a. Cell Description: Each cell was fitted with a pressure gage, and a pressure transducer. Prior to cycling, the cells were subjected to a series of tests including conditioning, capacity calibration, and overcharge. The final step of the series was an adjustment of precharged cadmium material. Two cells had -3.0 ah, two had 0.0 ah and two had +3.0 ah of precharge. In negative precharging, the desired ampere-hour equivalent of oxygen is added to fully charged cells. In positive precharging, the desired ampere-hour equivalent of oxygen is removed from the cells as they charge. This preliminary procedure was specified by Goddard Space Flight Center. The methods of precharge adjustment were developed by NAD Crane.

b. Parameters and Capacity Checks:

(1) Precycling capacity was determined prior to precharge adjustment. The capacity of each cell is determined by the time to reach 0.5 volt.

(2) Pack Number: 48D.

(3) Orbit Period: 1.5-hour.

(4) Test Temperature: 20° C.

(5) Depth of Discharge: 25%.

(6) Trip Voltage Level: 300 Millivolts. (Placed on voltage limit control 2-4-71 per instructions from Goddard Space Flight Center.)

(7) Auxiliary Electrode Resistors: 47 Ohms.

	Negative Precharge		Zero Precharge		Positive Precharge	
	Cell #1	Cell #4	Cell #2	Cell #5	Cell #3	Cell #6
	S/N 475	S/N 953	S/N 481	S/N 961	S/N 493	S/N 959
Precycling Capacity	25.60	25.60	25.50	24.80	25.50	25.10
88 Days	14.17	11.17	12.67	14.33	12.50	15.00
176 Days	9.20	6.80	8.80	9.00	8.30	10.20
352 Days	6.70	5.80	8.50	7.30	7.50	11.50

c. Test Results:

(1) Performance on Cycling: (Figure 70) Cycling was started in July 1970. Pack 48D has completed 7835 cycles.

PACK 048D	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	20
CHARGE RATE AMPS	10.00
DEPTH OF DISCHARGE %	25

PACK 048D MANF. GULTON 06.0 AH

ORBIT PERIOD. HOURS 01.5

TEMP. DEGREES C. 20

CHARGE RATE AMPS	10.00
PERCENT OF DISCHARGE	25

DEPTH OF DISCHARGE 4 2



VOLT

PERCENT RECHARGE

CYCLES - MULTIPLES OF 10

FIGURE 70

9. Gulton 20 ah (OAO), (Nickel-Cadmium), One 5-cell Pack:

a. Cell Description: The first, third and fifth cells were fitted with pressure transducers. The first cell has the only auxiliary electrode of the pack. The physical description may be found in paragraph II.A., page 88.

b. Parameters and Capacity Checks:

(1) Pack Number: 12E.

(2) Orbit Period: 1.5-hour.

(3) Test Temperature: 20° C.

(4) Depth of Discharge: 15%.

(5) Auxiliary Electrode Resistor: 47 Ohms.

(6) Capacity Checks: The ampere-hour capacities during precycling were determined by discharging each cell at 6.0 amperes to 0.5 volt per cell. The capacity checks during cycling are determined by that time required for the first cell in the pack to reach 0.5 volt. Further the capacity checks during cycling are not run on a regular 88-day cycle, but only when instructed by Goddard Space Flight Center; and when run, the capacities are determined by the time for the first cell in the pack to reach 0.5 volt.

	Cell #1	Cell #2	Cell #3	Cell #4	Cell #5
Precycling Capacity	25.26	25.38	25.38	24.96	25.56
58 Days*	29.80	29.50	27.60	27.50	28.60
97 Days	25.80				

* This capacity check was run at the c/2 discharge rate as opposed to precycling data and that at 97 days which was run at the cycle rate of 6.0 amperes. When only one column is used (97 days), the capacity is determined by the low cell reaching 0.5 volt.


c. Test Results:

(1) Performance on Cycling: (Figure 71) Cycling started in May 1970. Pack 12E has completed 9119 cycles with two cells removed.

(2) Analysis: After 2522 cycles, the cells showed a large amount of imbalance at the end of charge. The cell showing the highest end-of-charge voltage was removed at the request of Goddard Space Flight Center. Analysis showed excessive migration and moderate separator deterioration. Samples of positive and negative (adjacent) plates were removed, and individual plate capacities were measured. The positive capacity exceeded the negative capacity in each case by as much as 13 percent. This leads to high voltage (unusually high pressure also, though not noted in this case) during charge. The second cell was removed after 2729 cycles and sent to Goddard Space Flight Center.

PACK 012E	MANF.	GULTON	20.0 AH
ORBIT PERIOD HOURS		01.5	
TEMP. DEGREES C.		20	
CHARGE RATE AMPS		8.00	
DEPTH OF DISCHARGE %		15	

PACK 012E	MANF.	GULTON	20.0 AH
ORBIT PERIOD HOURS		01.5	
TEMP. DEGREES C.		20	
CHARGE RATE AMPS		8.00	
DEPTH OF DISCHARGE %		15	

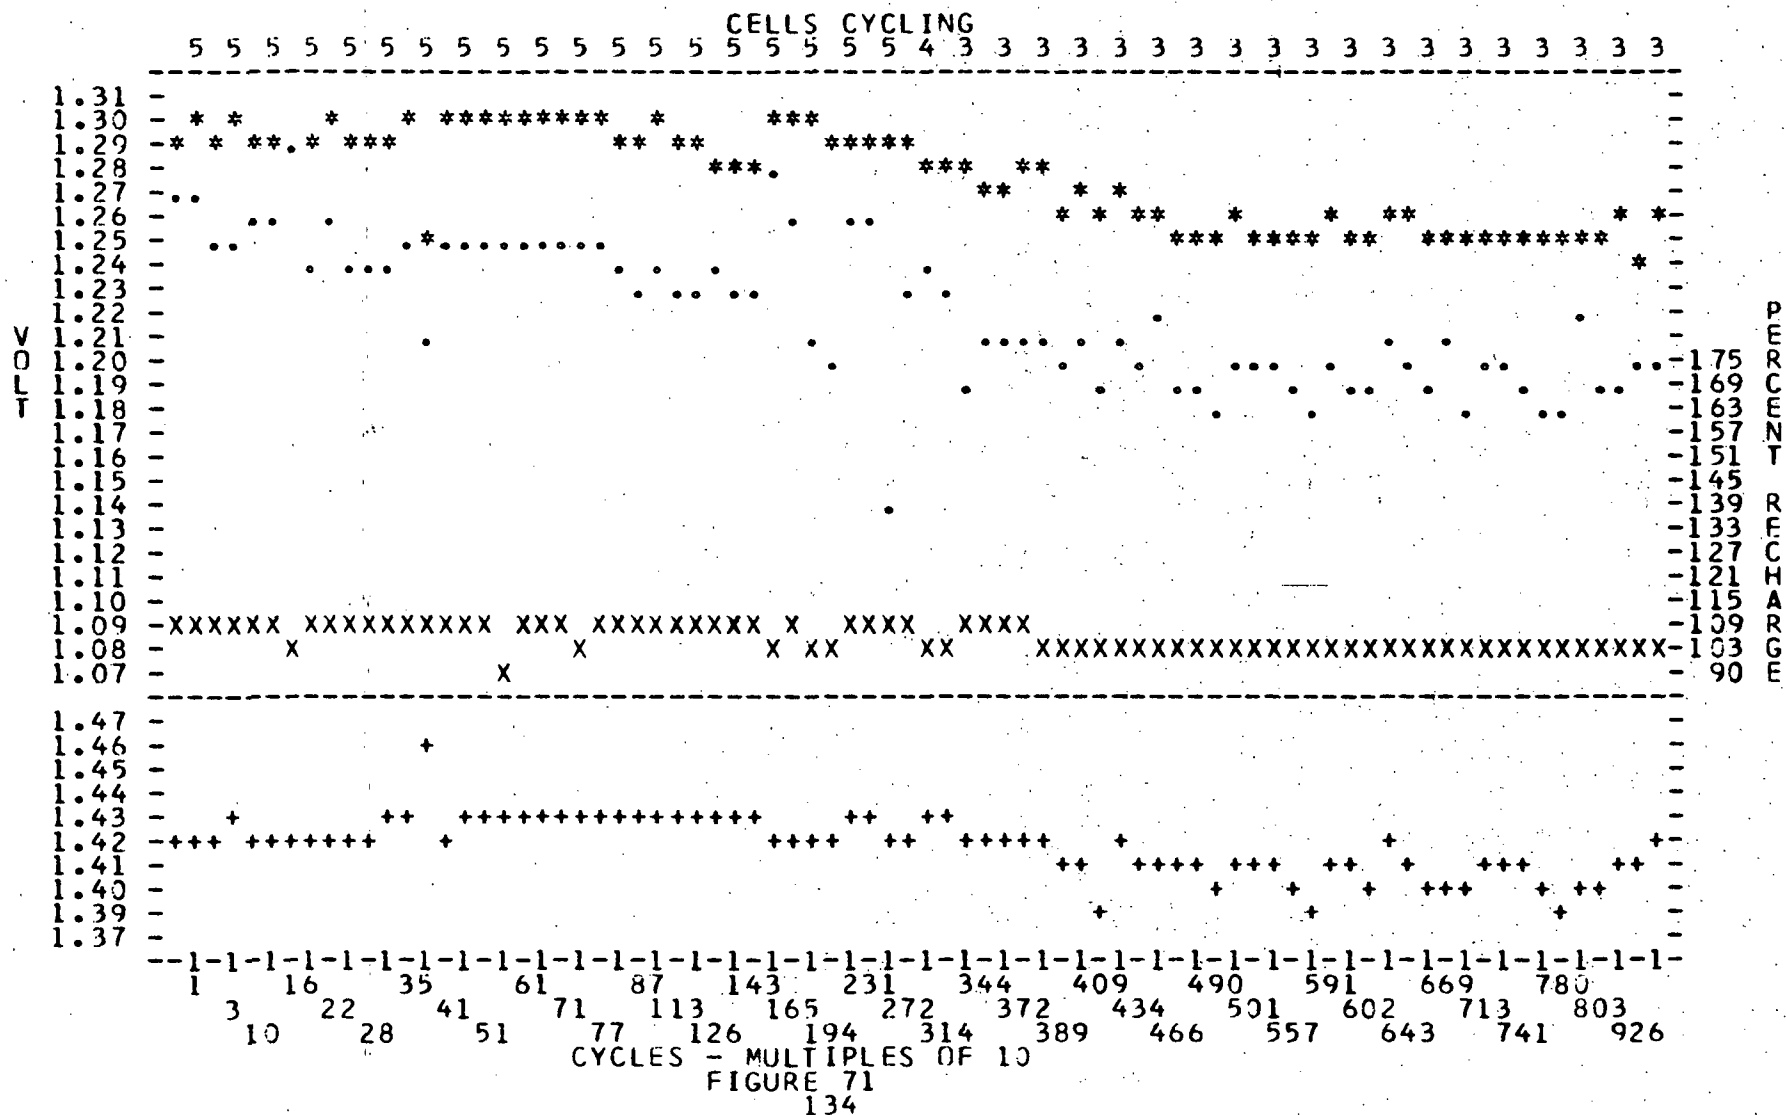

10. Gulton 20 ah (OAO), (Nickel-Cadmium), One 5-cell Pack:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

(1) Orbit Period: 1.5-hour.

(2) Test Temperature: 0° C.

(3) Depth of Discharge: 15%.

(4) Auxiliary Electrode Resistor: 47 Ohms.

(5) Pack Number: 68B.

(6) Capacity Checks: The ampere-hour capacities during precycling was determined by discharging each cell at 6.0 amperes to 0.5 volt per cell. The capacity checks are not run on a regular 88-day schedule; they are scheduled by Goddard Space Flight Center. When only one column is used (88 days), the capacity is determined by the low cell reaching 0.5 volt.

	Cell #1	Cell #2	Cell #3	Cell #4	Cell #5
Precycling Capacity	27.00	26.82	27.30	27.12	27.12
88 Days	27.00				

c. Test Results:

(1) Performance on Cycling: (Figure 72) Cycling was started in October 1970. Pack 68B has completed 6736 cycles.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 068B MANF. GULTON
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 8.00
 DEPTH OF DISCHARGE % 15

QEEL/C 72-1

CELLS CYCLING

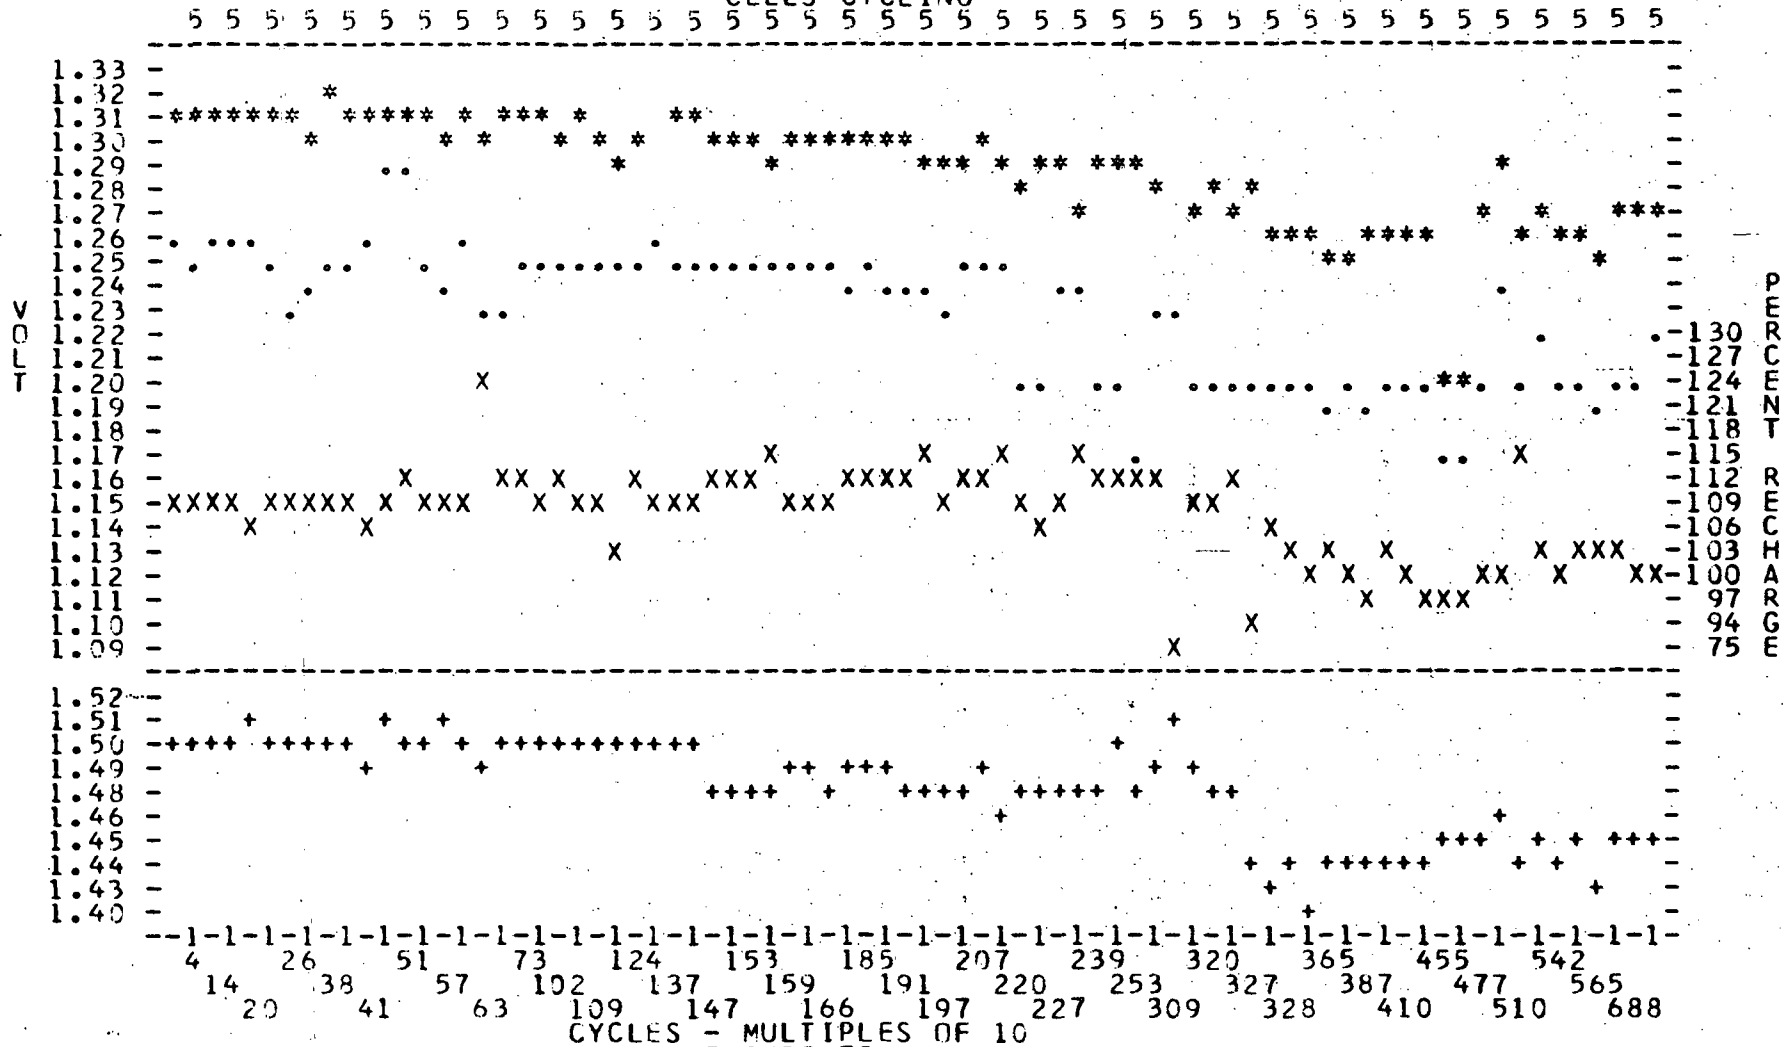


FIGURE 72
 136

11. Gulton 20 ah (0A0), One 5-cell Pack:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

(1) Orbit Period: 1.5-hour.

(2) Test Temperature: 10° C.

(3) Depth of Discharge: 15%.

(4) Pack Number: 35B.

(5) Capacity Checks: The capacity checks are not run on a regular 88-day schedule; they are scheduled by Goddard Space Flight Center.

c. Test Results:

(1) Performance on Cycling: (Figure 73) Cycling was started in February 1971. This pack has completed 4938 cycles with no cell failures.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 0358 MANF. GULTON
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 15
 CHARGE RATE AMPS 8.00
 DEPTH OF DISCHARGE % 10

QEEL/C 72-1
 20.0 AH

CELLS CYCLING

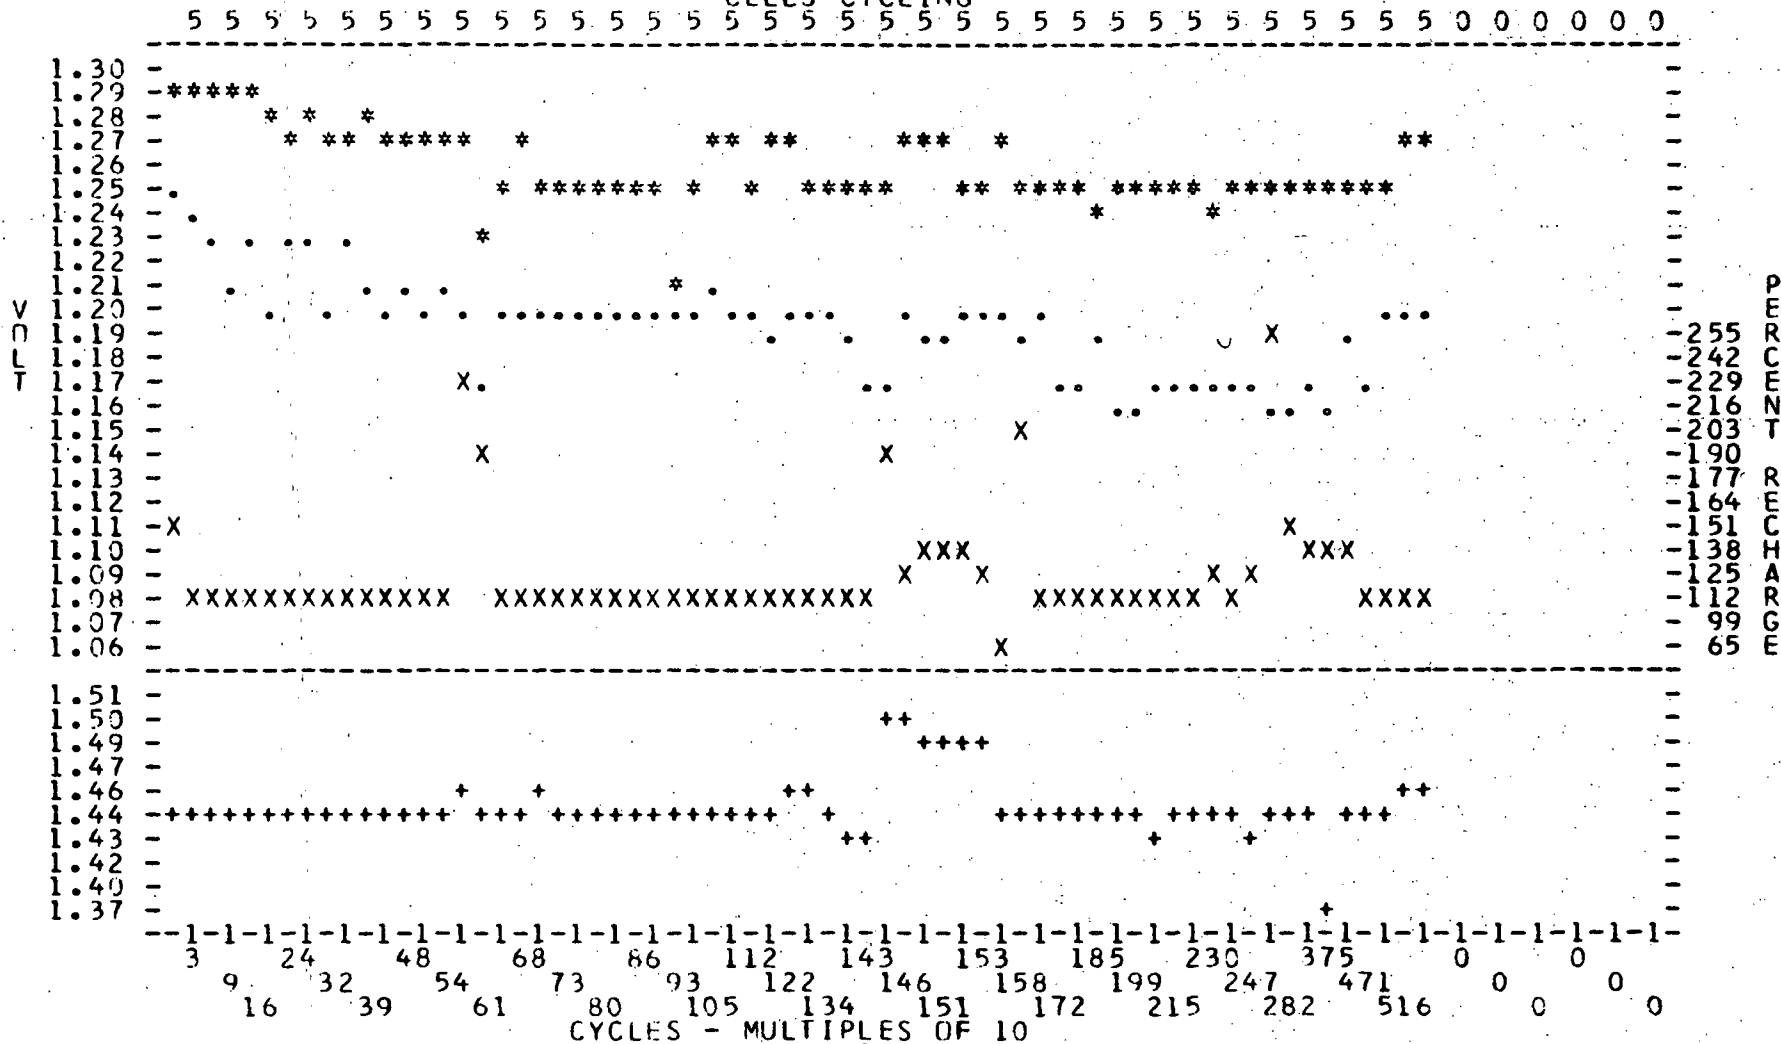


FIGURE 73
 138

12. GE 6.0 ah (Nickel-Cadmium), Eight 5-cell Packs:

a. Cell Description: The cells of four packs contain Type C auxiliary electrode (Code AB13), which is a sintered nickel plaque with a Teflon coating; whereas those of the other four packs contain Type B auxiliary electrode (Code AB14), which is a platinum loaded sintered nickel plaque with no Teflon coating.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour							
Temperature	0°	0°	25°	25°	40°	40°	*	*
Depth of Discharge	25%	25%	25%	25%	25%	25%	25%	25%
Trip Voltage (MV)	250	250	250	250	250	250	250	250
Resistors (Ohms)	82	82	82	82	82	82	82	82
Pack Number	52C	50B	5B	17B	6C	42C	62B	65B
Auxiliary Electrode	C	B	C	B	C	B	C	B
Precycling Capacity	7.05	7.20	7.50	7.38	5.55	5.10	7.40	7.70
88 Days	6.50	7.40	3.20	4.70	1.50	1.50	1.15 D**	5.80
264 Days	3.10	7.25	1.50	2.20	2.10	2.20	5.55 ***	2.65
440 Days	3.35	7.05	1.75	1.90	2.50 F	2.10 D**		2.00
616 Days	1.45 F	6.60	2.00	1.00				3.35
792 Days		6.35	2.45 D**	1.77				1.71 D
968 Days		6.00		1.65 F				
1144 Days		5.65						

* These cells are in an ambient temperature which varies sinusoidally from 0° to 40° C within a cycle period of 48 hours. The temperature cycle is stopped at 25° C for each capacity check cycle.

** These cells were removed from automatic cycling for a series of special tests as instructed by Goddard Space Flight Center.

*** Placed on voltage limit control (4-6-71) at 20° C due to auxiliary electrode allowing cell voltage to go too high.

D - Discontinued.

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figures 74 through 76) Cycling started in June 1968. Pack 50B has completed 20,731 cycles with no failures. Pack 62B was discontinued after 2367 cycles and then started again using a voltage limit control and has completed 6284 total cycles. Packs 6C, 52C, and 17B failed after 8072, 9954 and 15,938 cycles, respectively. Packs 42C, 5B and 65B were discontinued after 9047, 13,254 and 14,392 cycles, respectively, due to low capacity. Failures and discontinuations have accounted for a total of 13 cells.


(2) Failure Analysis: Analysis of seven cells showed that the major causes of failure were due to separator deterioration, migration of the negative material, and high internal pressure resulting in case distortion. Other problems included ceramic shorting, dryness of separator, ragged edges on positive plates and blistering of positive plates.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 050B MANF. GE
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 3.00
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 06.0 AH

CELLS CYCLING

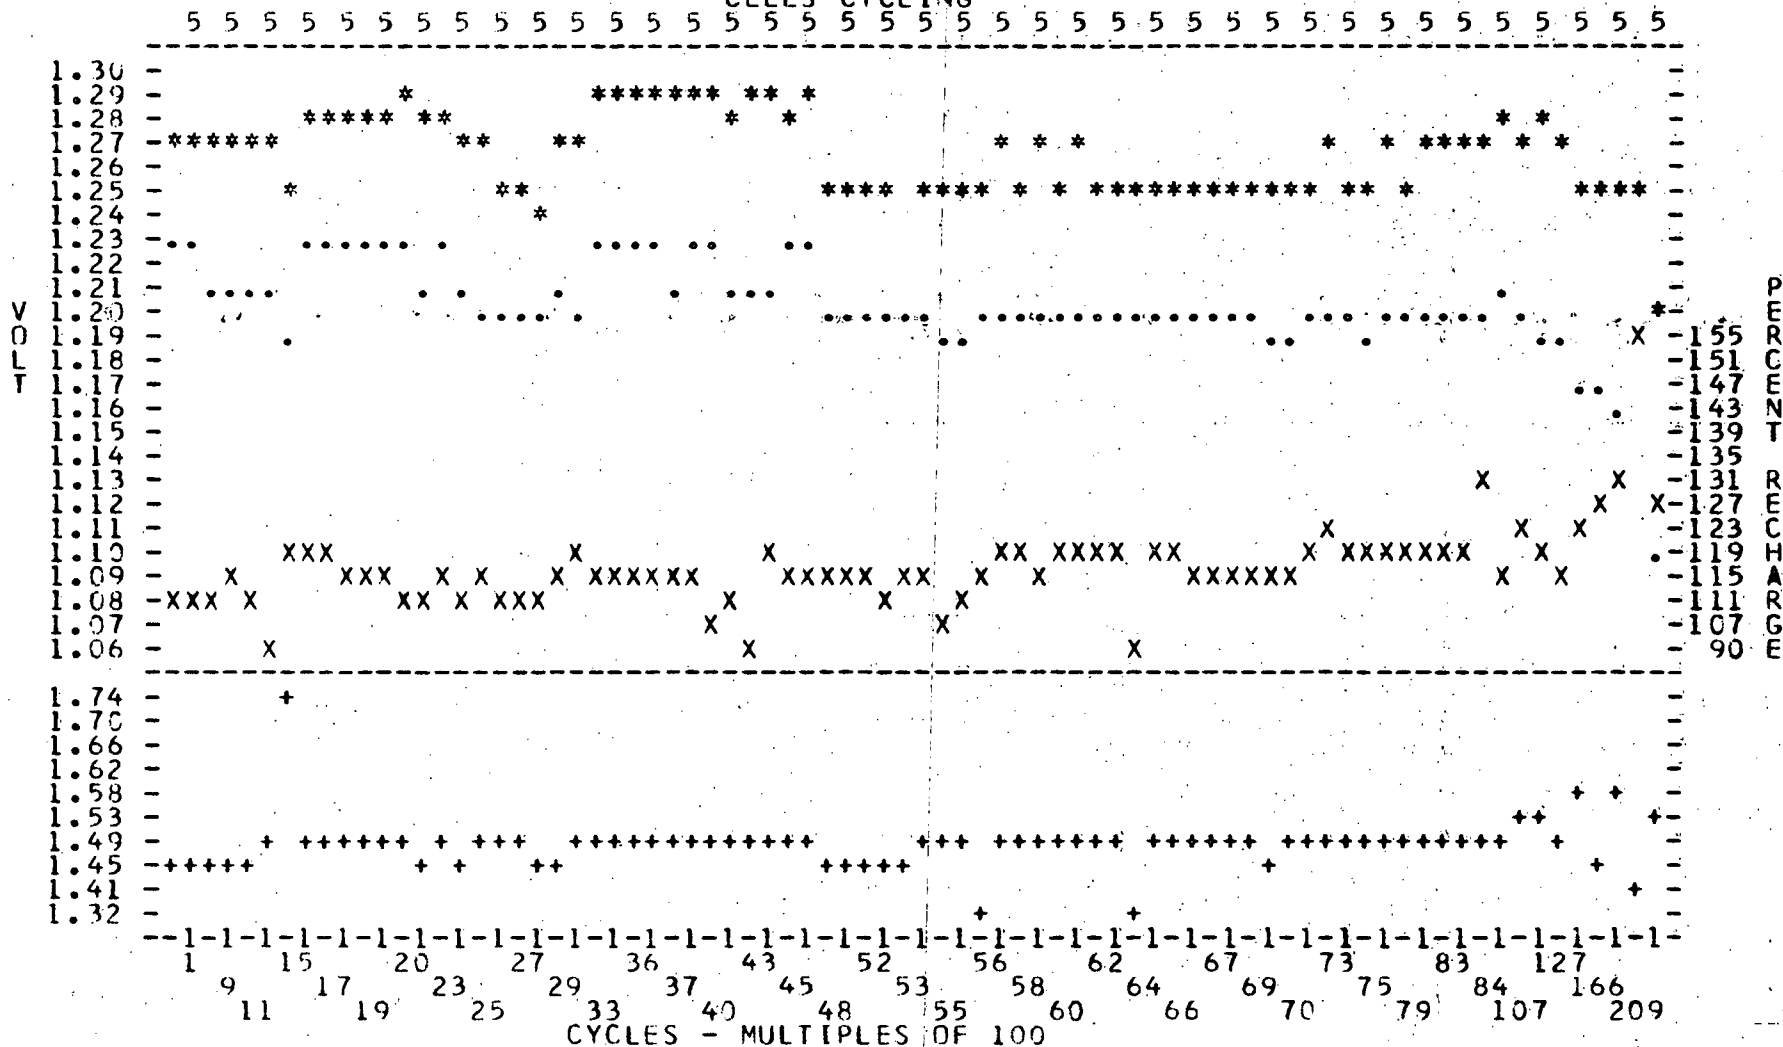


CYCLES - MULTIPLES OF 100

FIGURE 74

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 017B MANF. GE
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 25
 CHARGE RATE AMPS 3.00
 DEPTH OF DISCHARGE % 25


GEEL/C 72-1
 6.0 AH

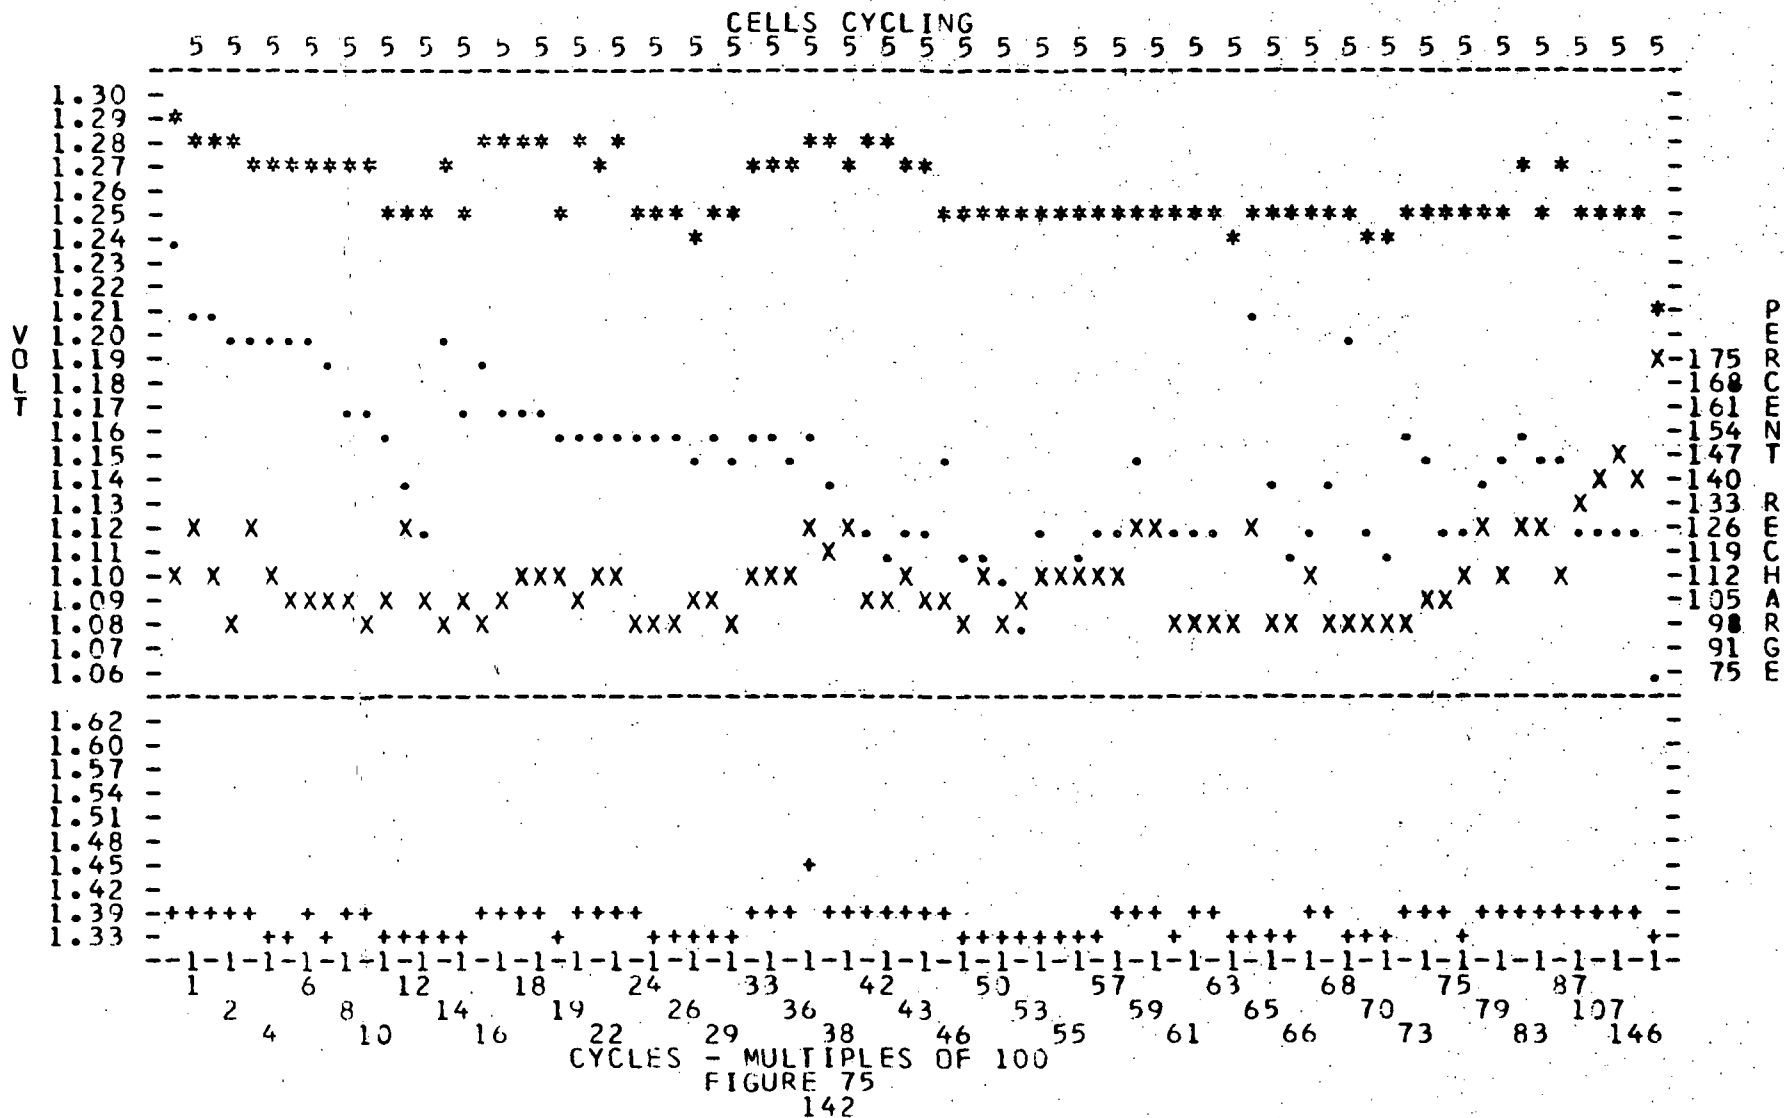

```
*-----MIDDLE DISCHARGE
+-----END OF DISCHARGE
+-----END OF CHARGE
X-----PERCENT RECHARGE
```

PACK 362B MANF.
ORBIT PERIOD HOURS
TEMP. DEGREES C.
CHARGE RATE AMPS 0.0
DEPTH OF DISCHARGE %

QEEL/C 72-1
AH

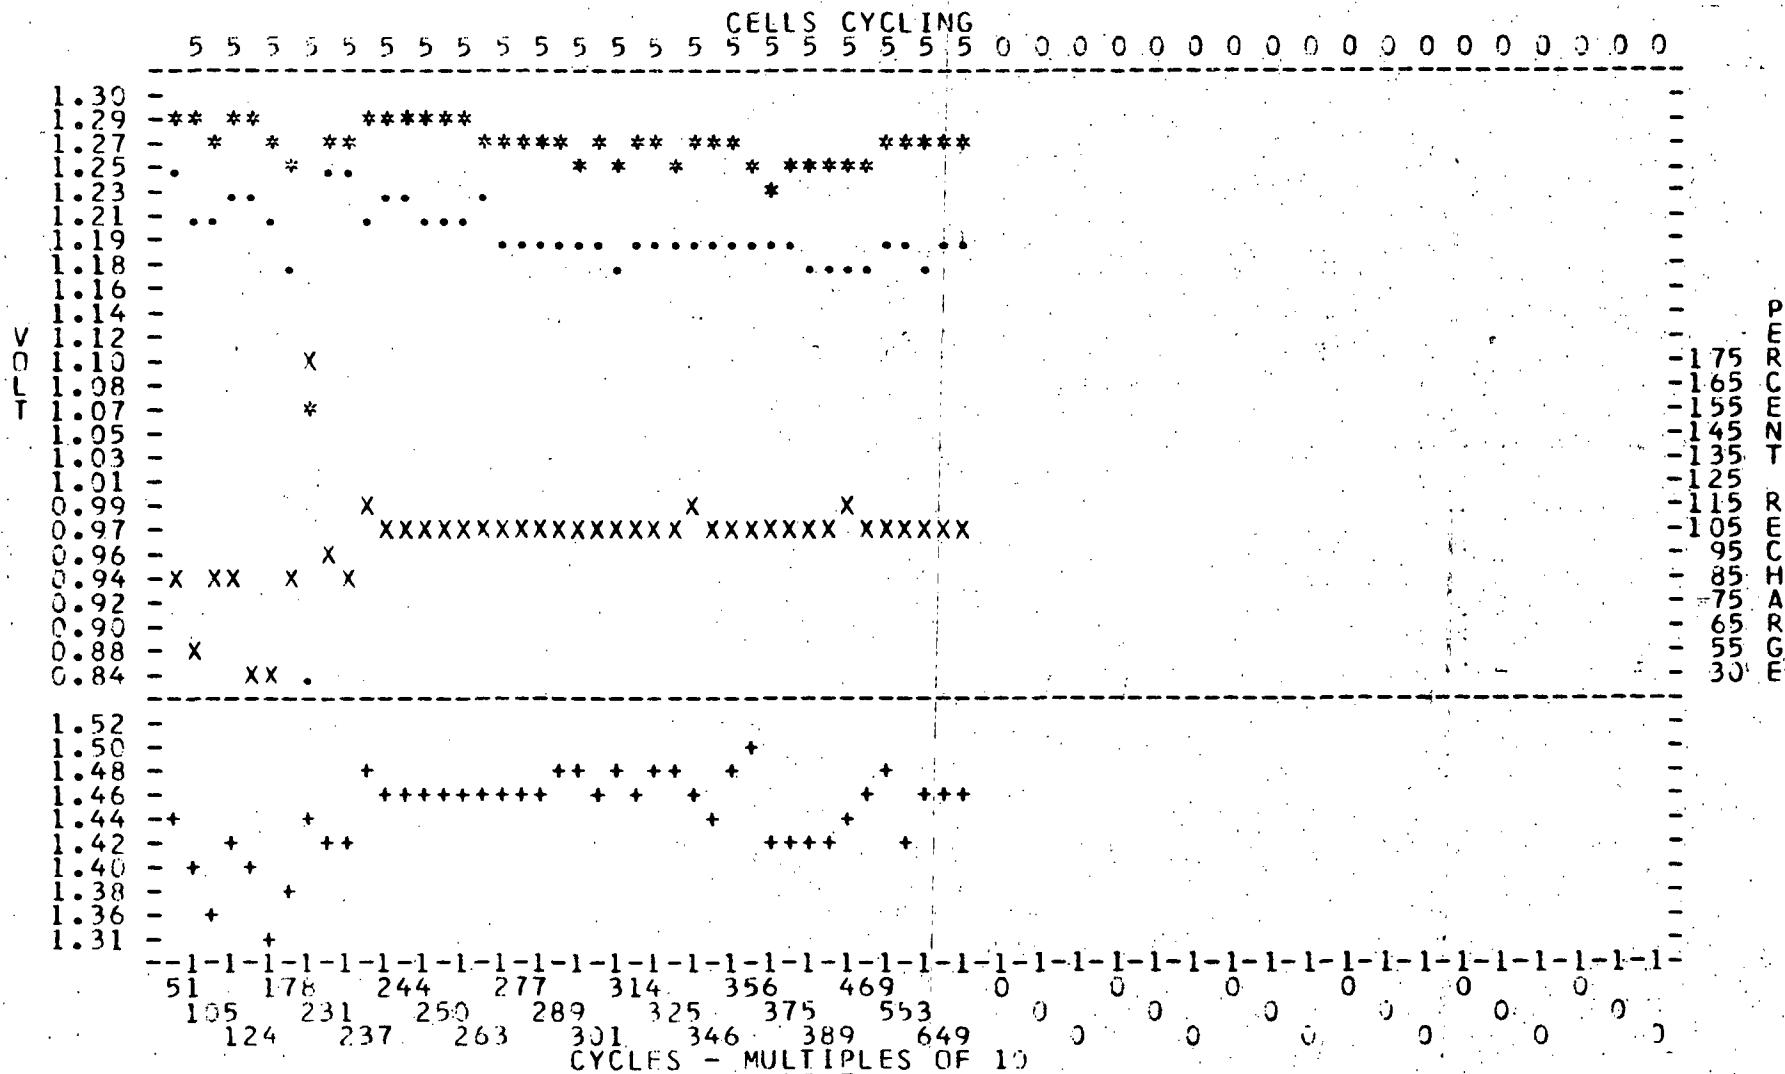

13. GE 6.0 ah (Nickel-Cadmium with Signal and Recombination Electrodes), Three 5-cell Packs:

a. Cell Description: These cells are rectangular with stainless steel containers and covers. Both terminals are insulated from the cell cover by ceramic seals and protrude through the cover as solder type terminals. There are two auxiliary electrodes in each cell; the signal and the gas recombination electrodes. The recombination electrode is welded to the inside of the container, and its terminal is a stainless steel tab welded to the outside. The signal electrode, which is used for charge control, is welded to a wire that protrudes through a hole in the cell cover. This hole is potted to seal the cell.

b. Parameters and Capacity Checks:

Orbit Period	1.5-hour		
Temperature	0°	20°	40°
Depth of Discharge	40%	40%	40%
Trip Voltage (MV)	150	200	600
Signal Electrode Resistors (Ohms)	330	330	330
Recombination Electrode Resistors	2.2	2.2	2.2
Pack Number	30C	64B	6D
88 Days	6.96	4.18	3.75
176 Days	6.73		F

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figures 77 through 79) Cycling was started in April 1971. Packs 30C and 64B have completed 3436 and 2095 cycles respectively. Pack 6D failed on cycle 2268.

(2) Failure Analysis: Chemical Analysis of cell 1 from pack 6D revealed a high equivalence percentage of potassium carbonate--averaging 47.2 percent. Physical analysis of the same cell showed blistering of positive plates, ragged plate edges and uneven distribution of electrolyte--highest moisture content toward the center of the plates.

$$\text{Equivalence \% CO}_3 = \frac{\text{Meq CO}_3}{\text{Meq CO}_3 + \text{Meq KOH}} \times 100$$


where Meq = milliequivalence.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 030C MANF. GE
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 4.80
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 6.00 AH

CELLS CYCLING

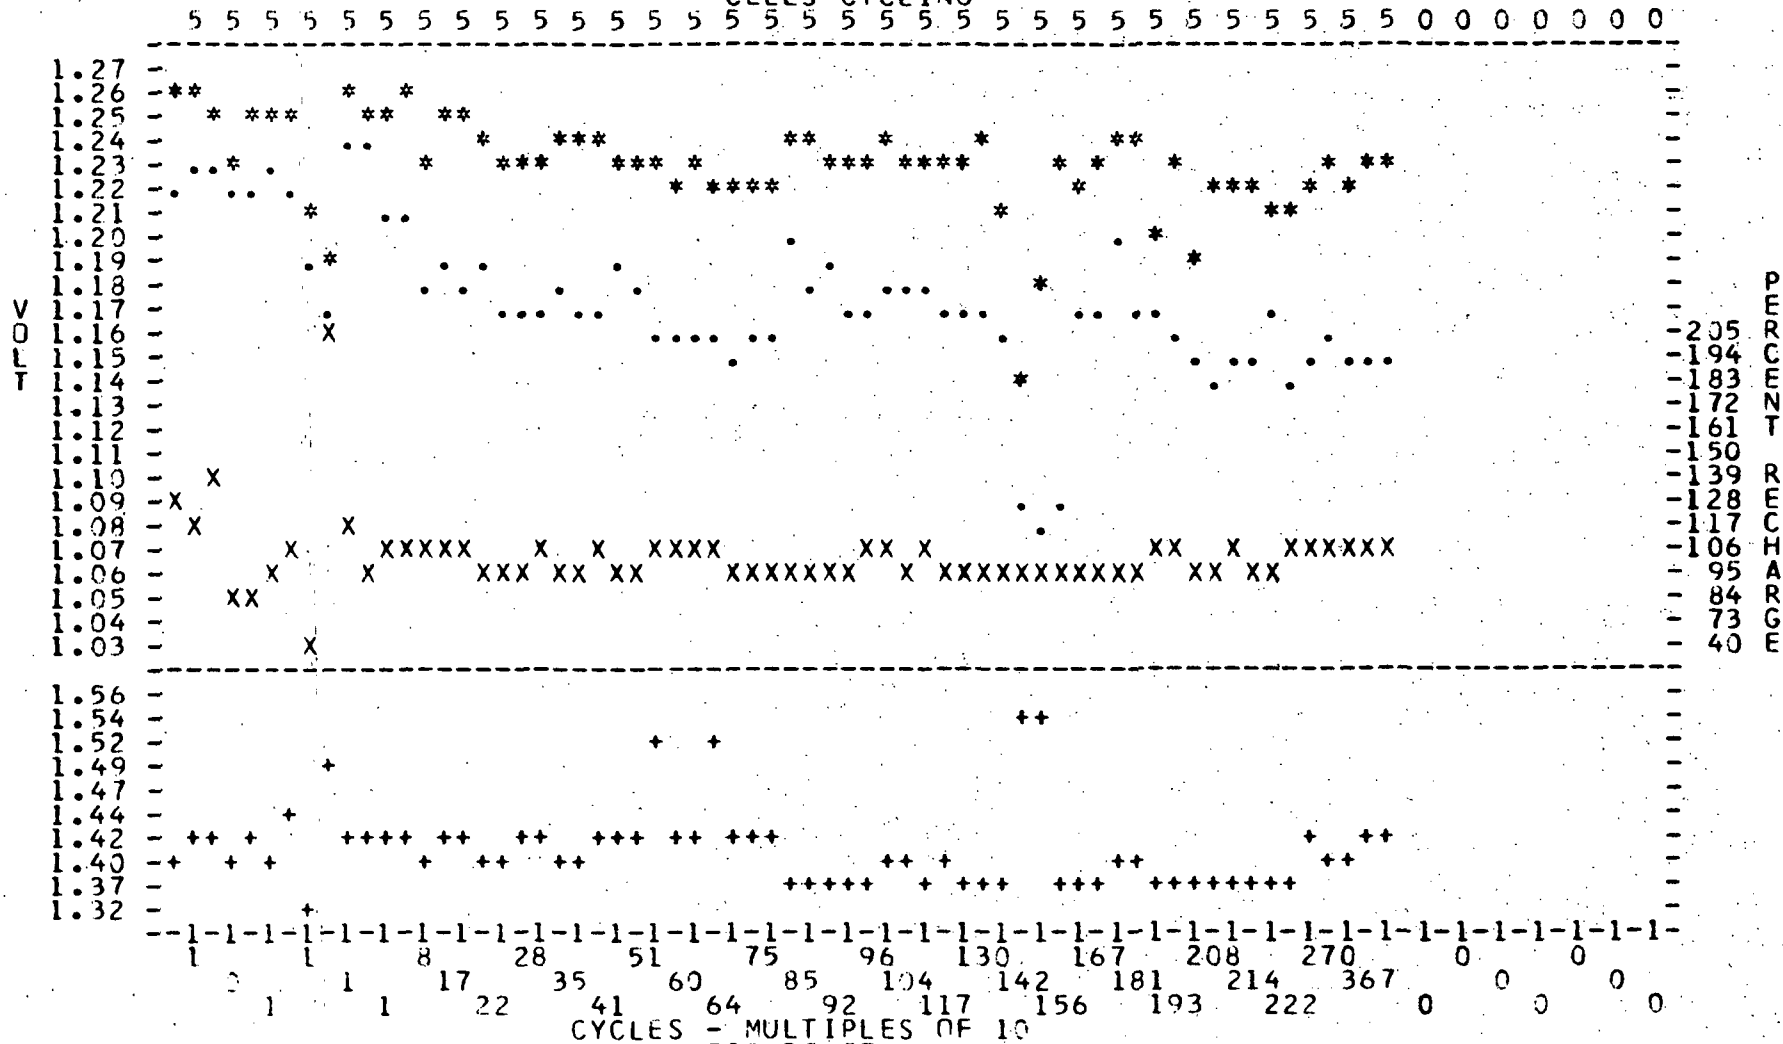


CYCLES - MULTIPLES OF 10
 FIGURE 77
 146

KEY: AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 0648 MANF. GE
 ORBIT PERIOD HOURS 1.5
 TEMP. DEGREES C. 20
 CHARGE RATE AMPS 4.80
 DEPTH OF DISCHARGE % 25




QEEL/C 72-1
 6.00 AH

CELLS CYCLING

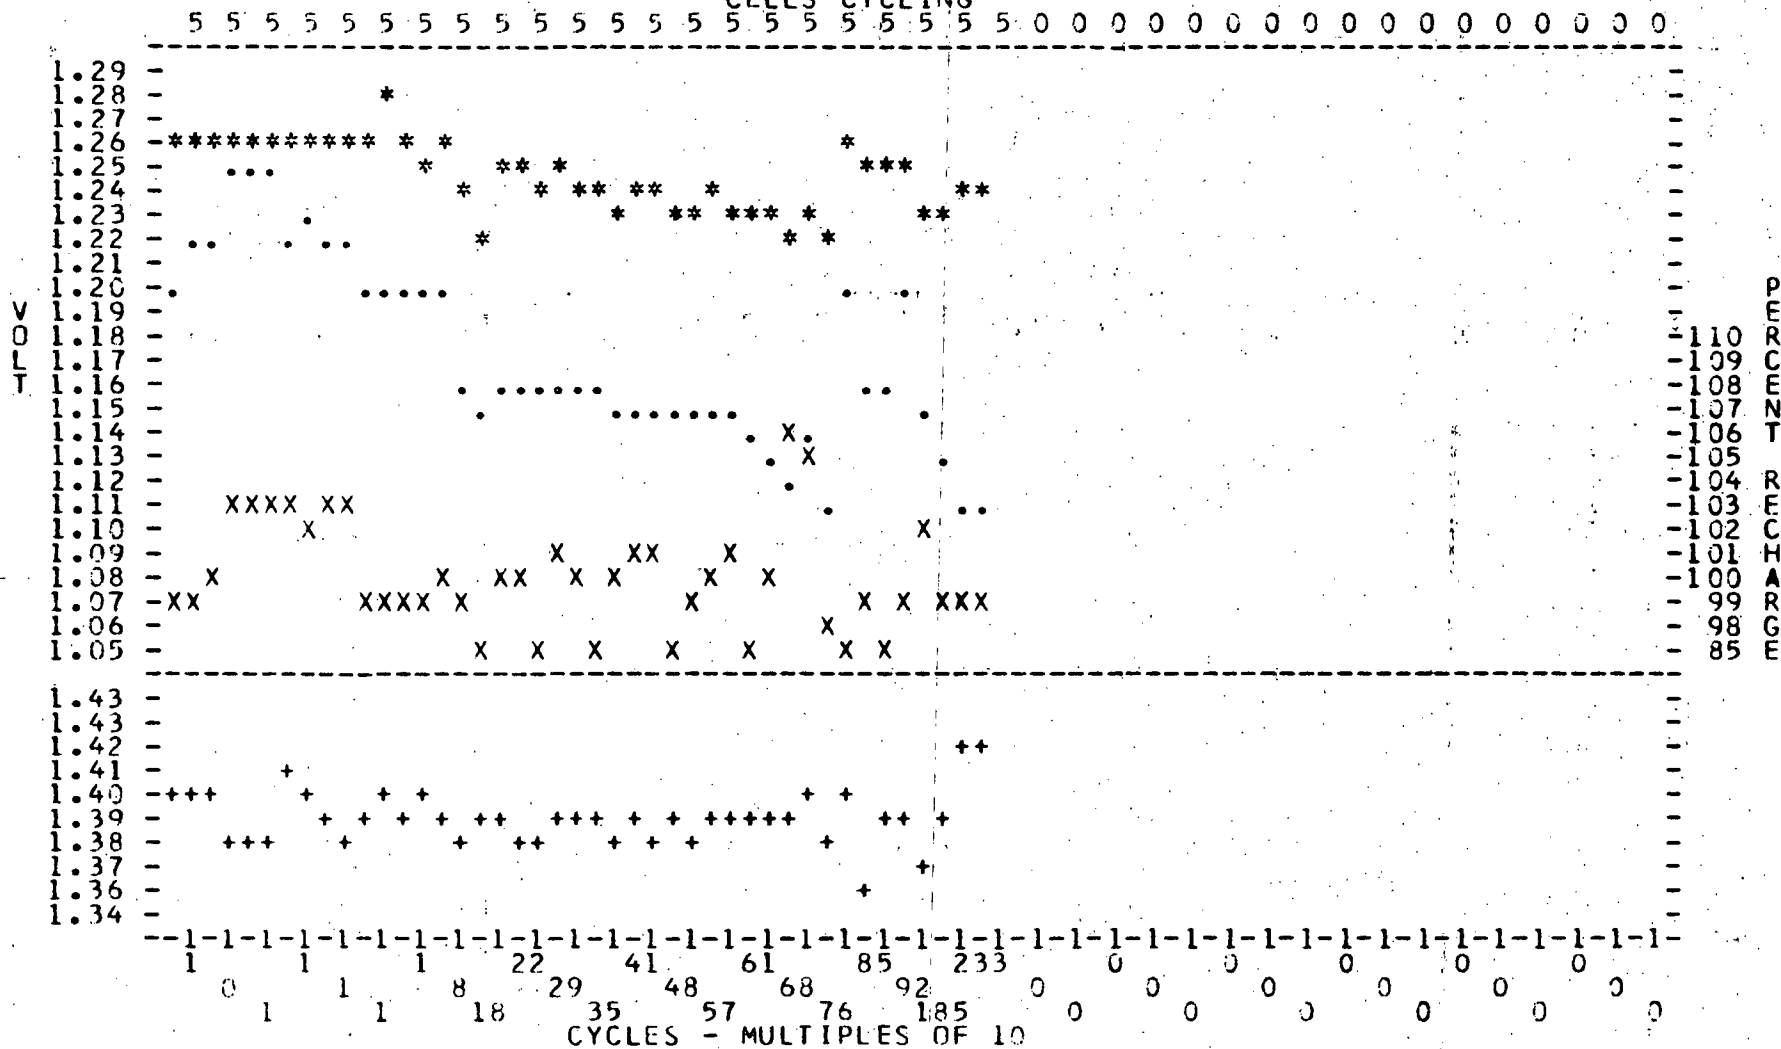

PACK 006D	MANF. GE
ORBIT PERIOD HOURS	1.5
TEMP. DEGREES C.	40
CHARGE RATE AMPS	4.80
DEPTH OF DISCHARGE %	25

CELLS CYCLING

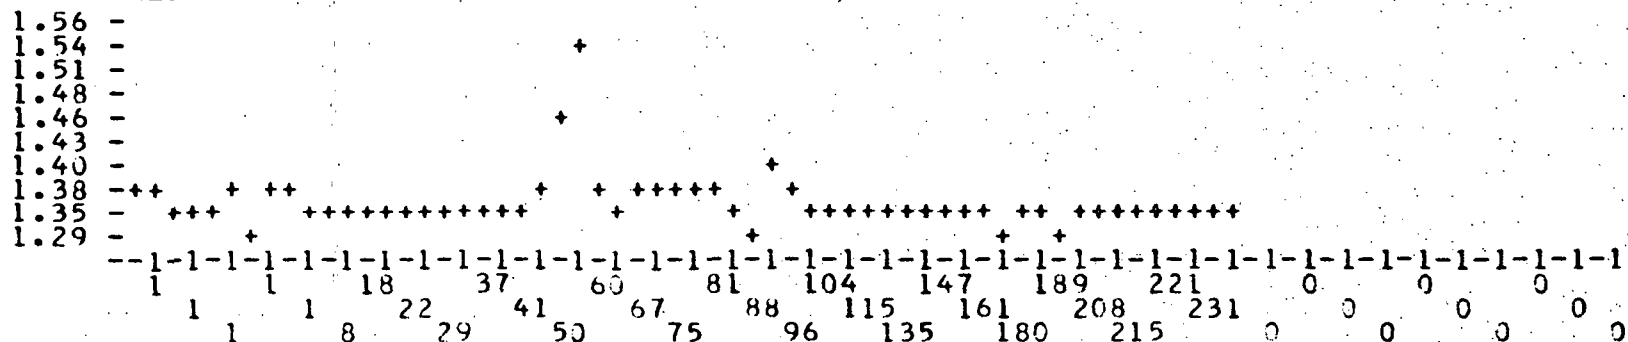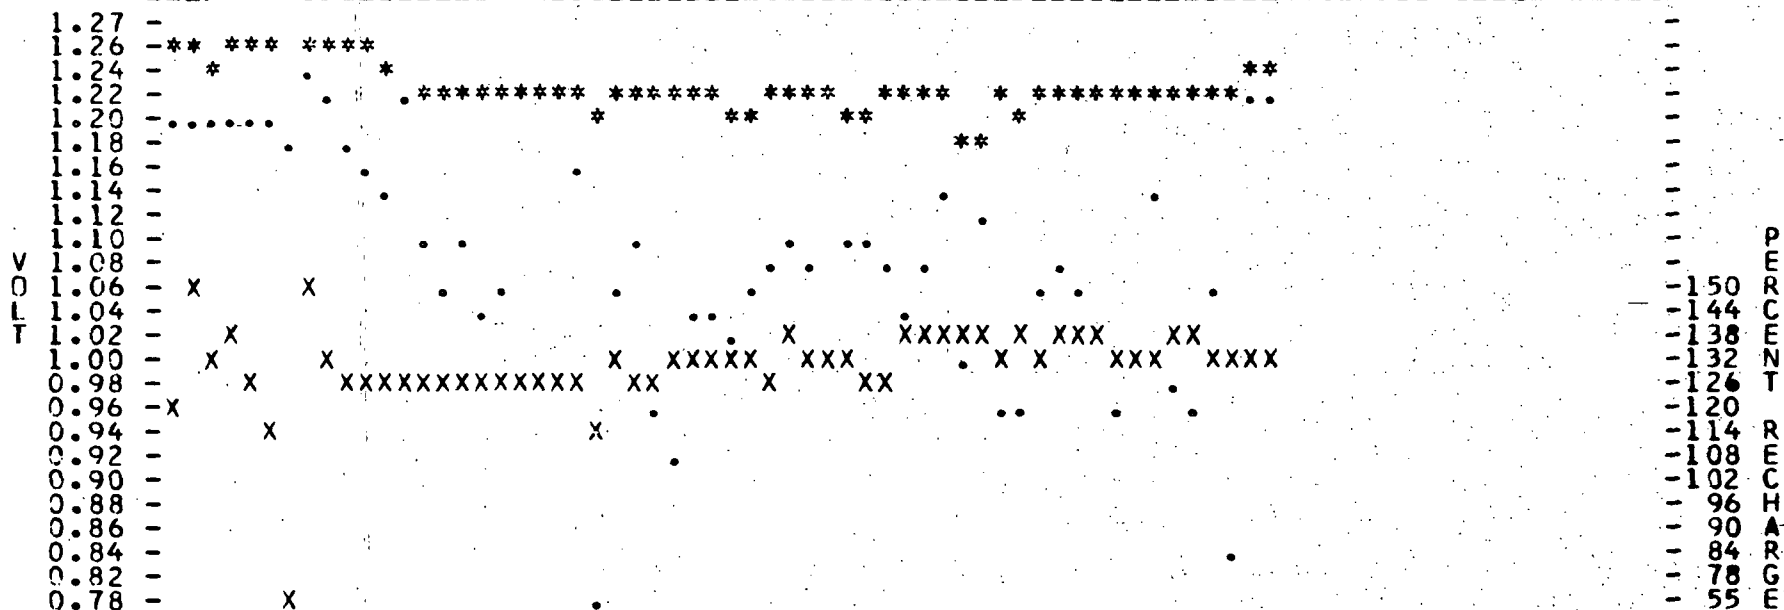

CYCLES - MULTIPLES OF 10
 FIGURE 79
 148

14. GE 20 ah (Nickel-Cadmium), Two 5-cell Packs:

a. Cell Description: See paragraph II.A., page 88.


b. Parameters and Capacity Checks:

Orbit Period	1.5-hour	
Temperature	0°	0°
Depth of Discharge	15%	15%
Trip Voltage (MV)	300	300
Resistors (Ohms)	300	300
Pack Number	7B	67B
Precycling Capacity	22.7	21.8
88 Days	27.3	29.3
176 Days	24.9	28.8
264 Days	27.3	30.0
352 Days	27.0	29.8
440 Days	27.9	30.4
528 Days	28.5	28.1

c. Test Results:

(1) Performance on Cycling: (Figures 80 and 81)
Cycling was started in February 1970. Packs 7B and 67B have completed 10,438 and 10,412 cycles, respectively.

20.0 QEEL/C 72-1
AH

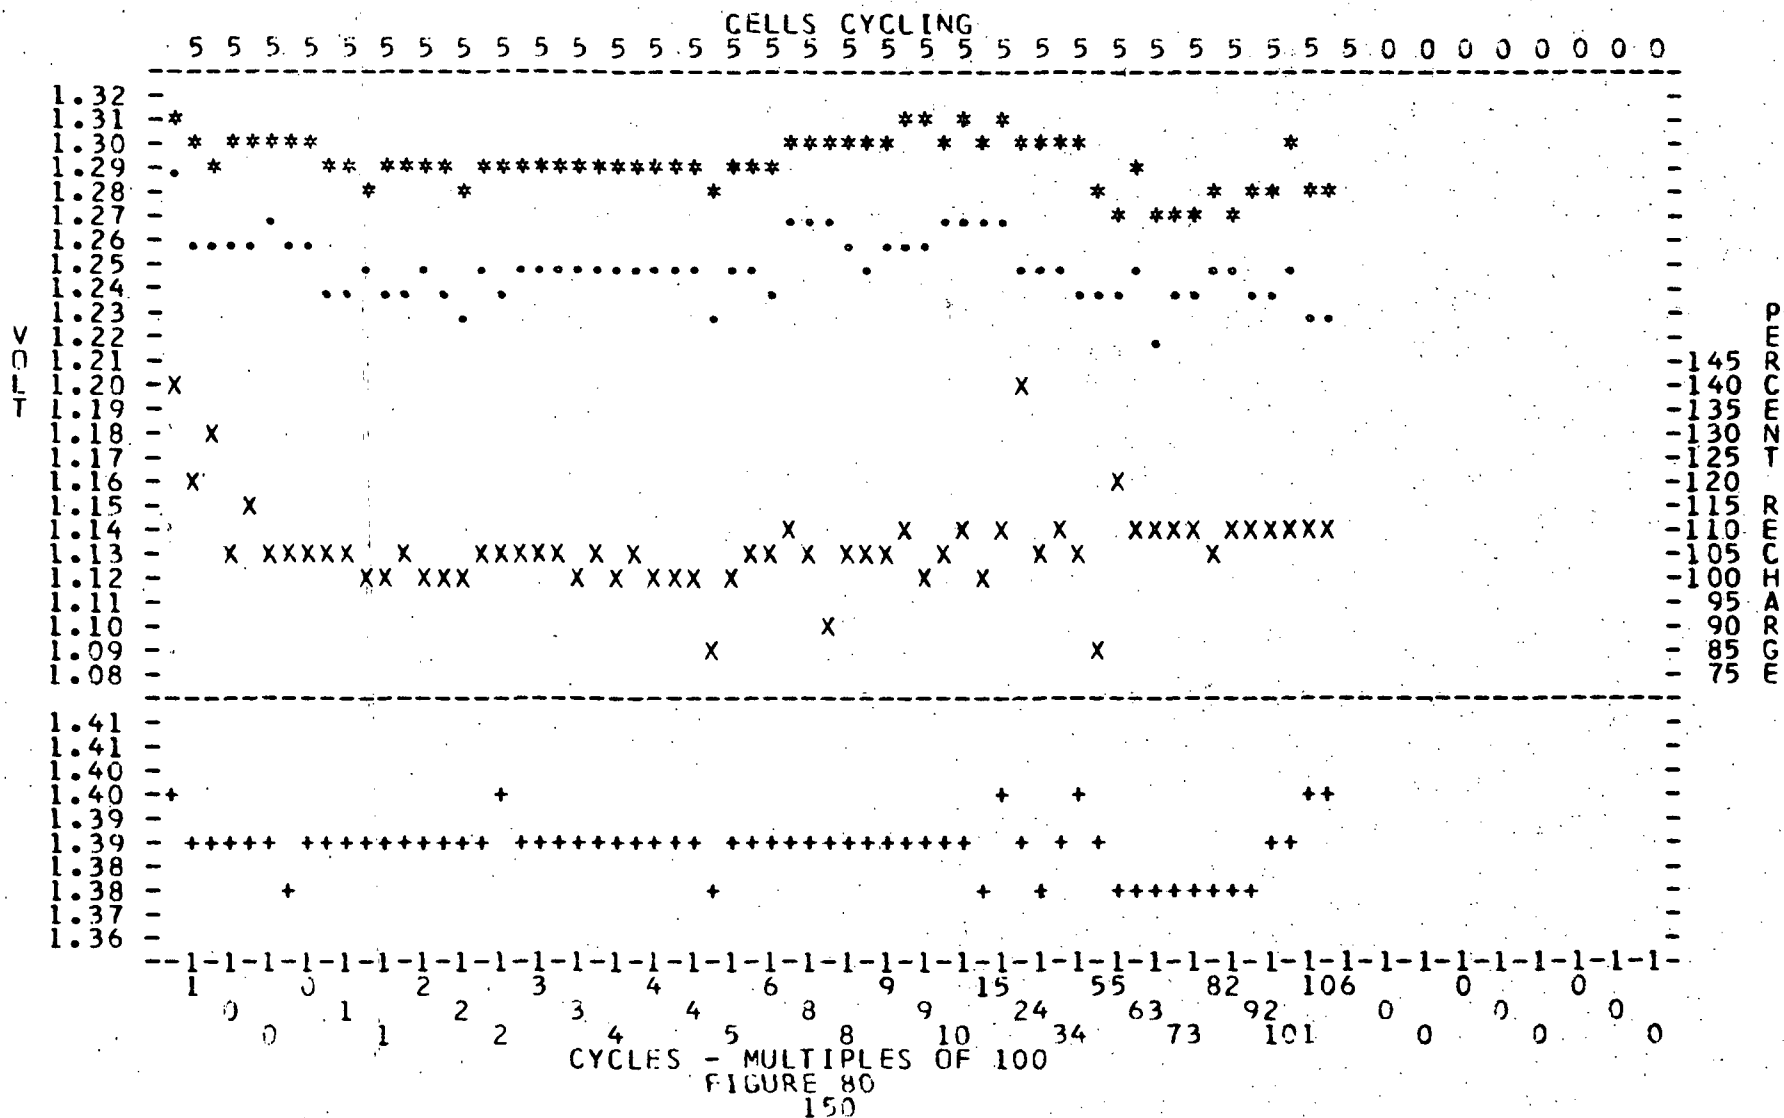


KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 0678 MANF. GE
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 8.00
 DEPTH OF DISCHARGE % 15

QEEL/C 72-1
 20.0 AH

CELLS CYCLING

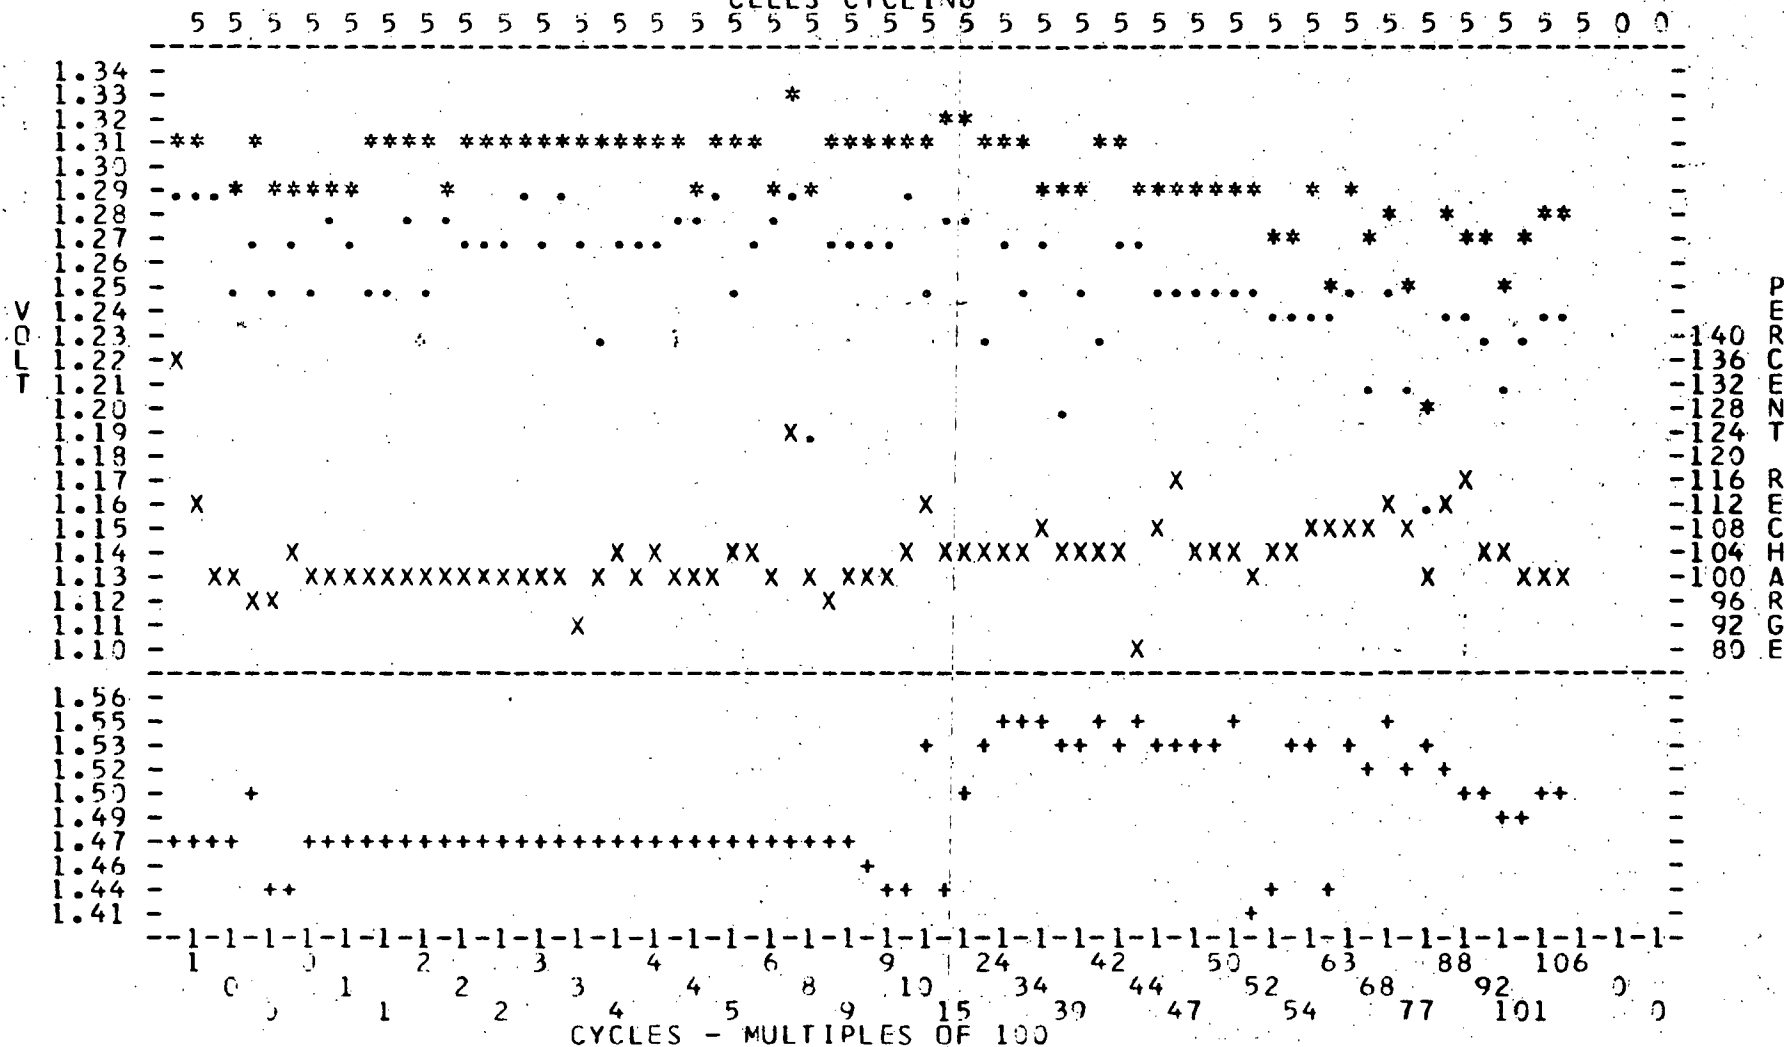

CYCLES - MULTIPLES OF 100

15. Yardney 11.0 ah (Silver-Cadmium), Three 5-cell Packs:

a. Cell Description: These cells are rectangular in shape. The cell jars and covers are made of a plastic material. An auxiliary electrode (adhydrode type) was installed in each cell by Goddard Space Flight Center before being individually epoxy potted with a wrap of fiberglass material to hermetically seal and strengthen them. The auxiliary electrode is used for gas recombination only.

b. Parameters and Capacity Checks:

Orbit Period	24-hour		
Temperature	0°	25°	40°
Depth of Discharge	18%	18%	18%
Resistors (Ohms)	1	1	1
Pack Number	57D	69B	33C
100 Days	4.10	7.55	8.70
300 Days	4.10	3.50	5.15 F
450 Days	8.35	1.85 F	
600 Days	3.95		
800 Days	2.90		
1000 Days	6.75		
1200 Days	3.00		

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figure 82) Cycling was started in February 1968. Pack 57D has completed 1365 cycles to date with one cell failure. Packs 69B and 33C failed on cycles 507 and 447 respectively.


(2) Failure Analysis: Analysis of the seven failed cells showed the major cause of failure to be loose negative material, migration of the negative plate material and separator deterioration. Other conditions found were weak tab-to-plate welds and electrolyte leakage.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 057D MANF. YARDNEY 11.0 AH
 ORBIT PERIOD HOURS 24.0
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 0.25
 DEPTH OF DISCHARGE % 18

QEEL/C 72-1

CELLS CYCLING

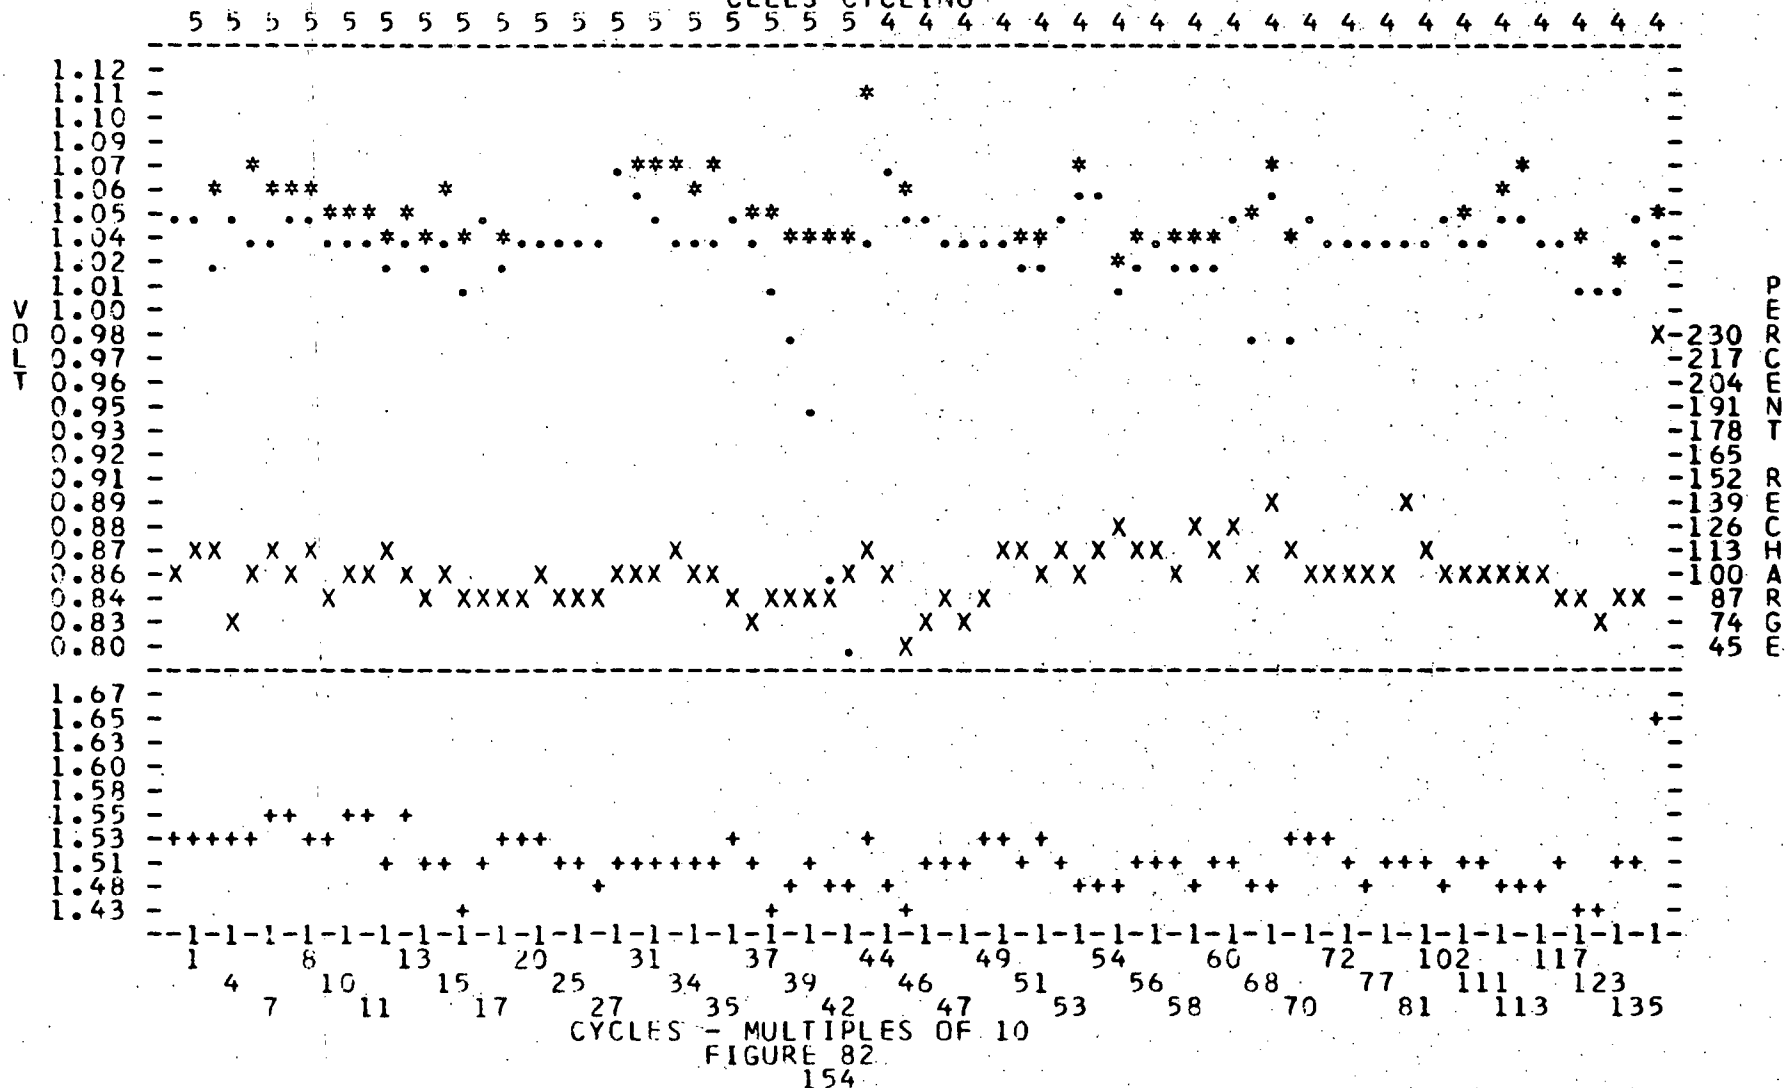

D. Coulometer: The coulometer is a device which measures the amount of electrical charge (coulombs or ampere-hours) passed through it. It accomplishes this by means of an electrochemical reaction which is directly proportional to the product of the magnitude of the current and the time for which it is passed. The coulometer used with nickel-cadmium cells is made from two sets of cadmium hydroxide plates bathed in KOH electrolyte, and constructed in a manner similar to that of a nickel-cadmium cell. Coulometer action is obtained by imbalancing the two sets of plates, so that when one set is reduced to cadmium by the passage of charge, the other set is oxidized to cadmium hydroxide. This reaction continues at a low voltage on the coulometer until the imbalance is complete. Then the coulometer voltage rises very sharply. The coulometer reaction can take place in either direction, charge or discharge, because the coulometer reaction is completely reversible. Thus it is easy to detect when 100 percent of the discharge has been returned to the cells.

1. Gulton 6.0 ah (Nickel-Cadmium with Gulton Plates),
Four 5-cell Packs:

a. Cell Description: These cells are different from previous Gulton cells in that the plates were manufactured by Gulton rather than SAFT of France.

Orbit Period	1.5-Hour			
Temperature	-20°	0°	20°	40°
Depth of Discharge*	50%	50%	50%	50%
Pack Number	39D	63B	3C	27D
Precycling Capacity	6.30	5.70	6.09	6.00
88 Days	5.00 F	6.08	4.96	2.96
176 Days		6.08	3.60	3.76
264 Days		5.92	4.08	5.44
352 Days		6.32	3.36	2.64 F

* Depth of Discharge was changed to 40% on 9-29-70 by NASA, Goddard Space Flight Center Technical Monitor. This change occurred within the first 75 cycles for all packs.

F - Failed.


c. Test Results:

(1) Performance on Cycling: (Figures 83 through 86)
Cycling was started in September 1970. Packs 63B and 3C have completed 6868 and 7001 cycles, respectively, with no cell failures. Packs 27D and 39D failed after 6869 and 1376 cycles, respectively.

(2) Failure Analysis: Analysis of the six failed cells showed extreme pitting of both the negative and positive plates throughout the plate stack. The cell cases were bulged due to internal pressure. Ultimate failure resulted in low capacity due to pitting and loosened active material.


PACK 039D	MANF. ASTRO
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	-20
CHARGE RATE AMPS	6.00
DEPTH OF DISCHARGE %	50

PACK 039D	MANF. ASTRO
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	-20
CHARGE RATE AMPS	6.00
DEPTH OF DISCHARGE %	50




PACK 063B	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	00
CHARGE RATE AMPS	6.00
DEPTH OF DISCHARGE %	50

06.0 AH

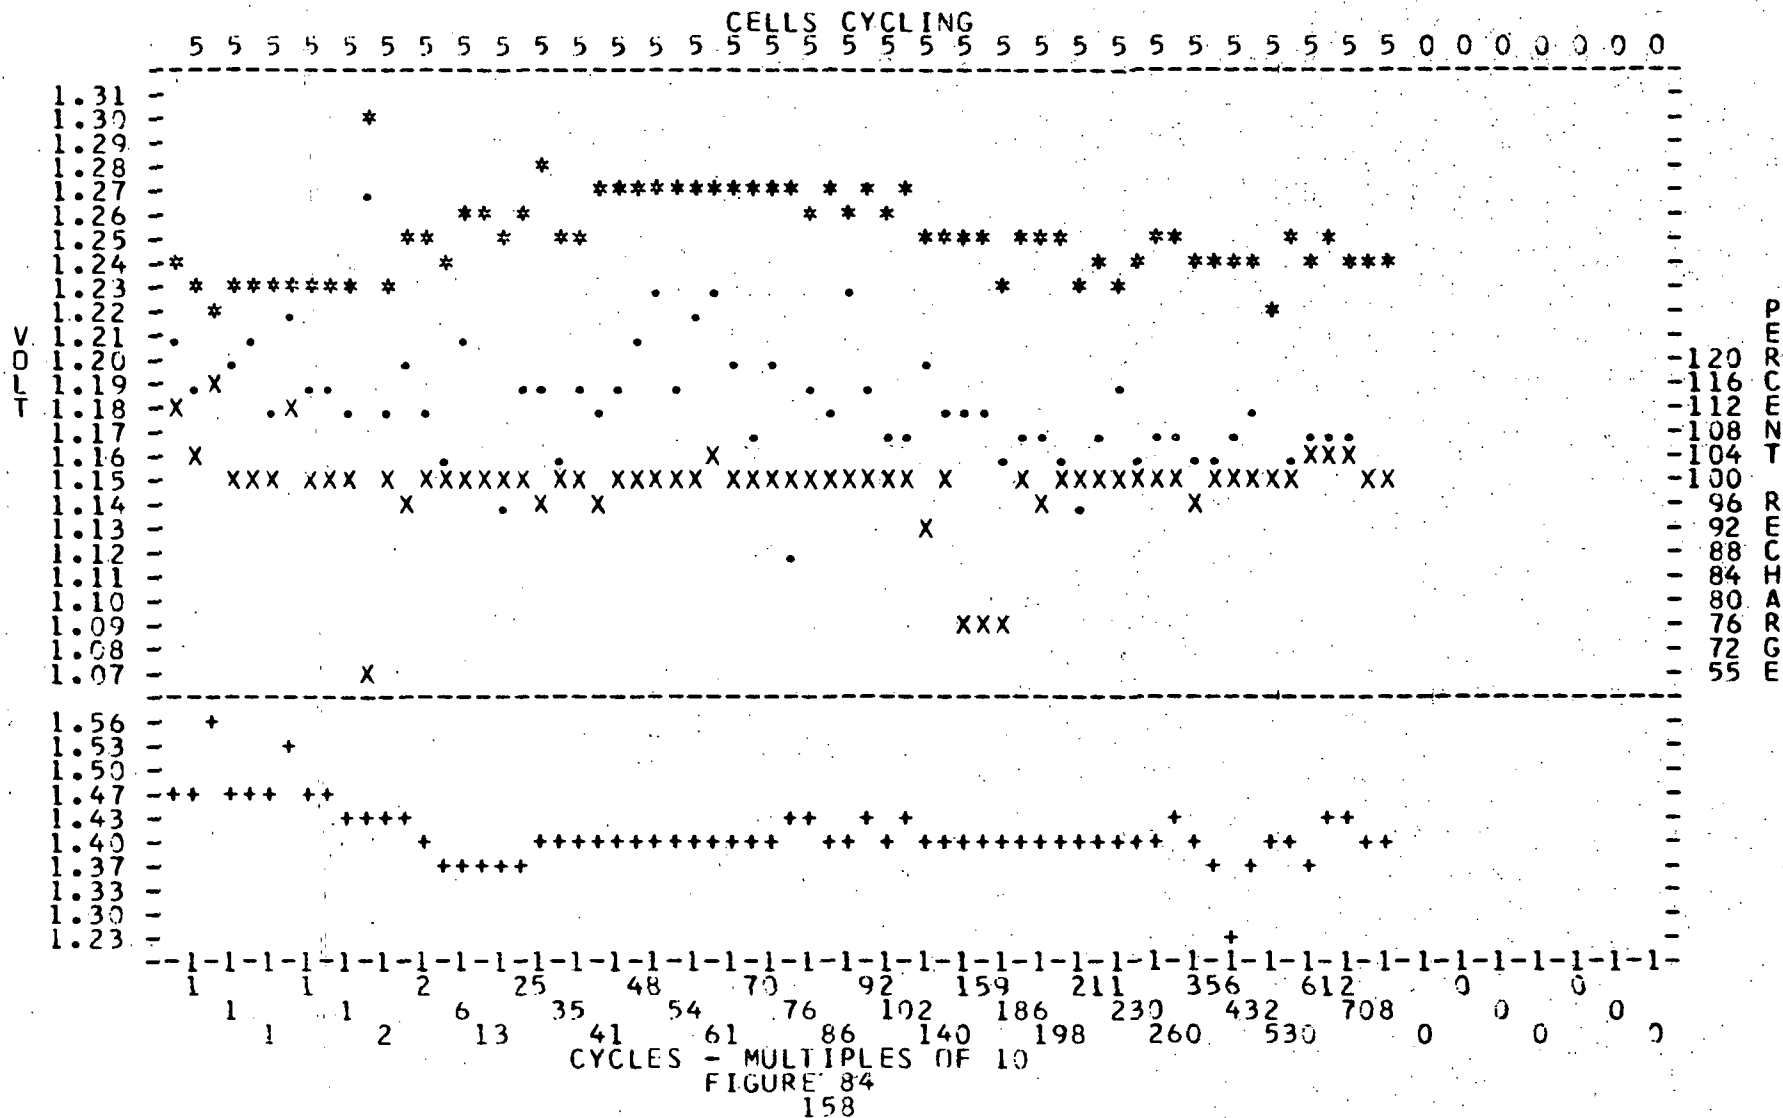

PACK 003C	MANF. GULTON
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	20
CHARGE RATE AMPS	6.00
DEPTH OF DISCHARGE %	50

PACK 003C	MANF. GULTON	06.0 AH
ORBIT PERIOD HOURS	01.5	
TEMP. DEGREES C.	20	
CHARGE RATE AMPS	6.00	
DEPTH OF DISCHARGE %	50	

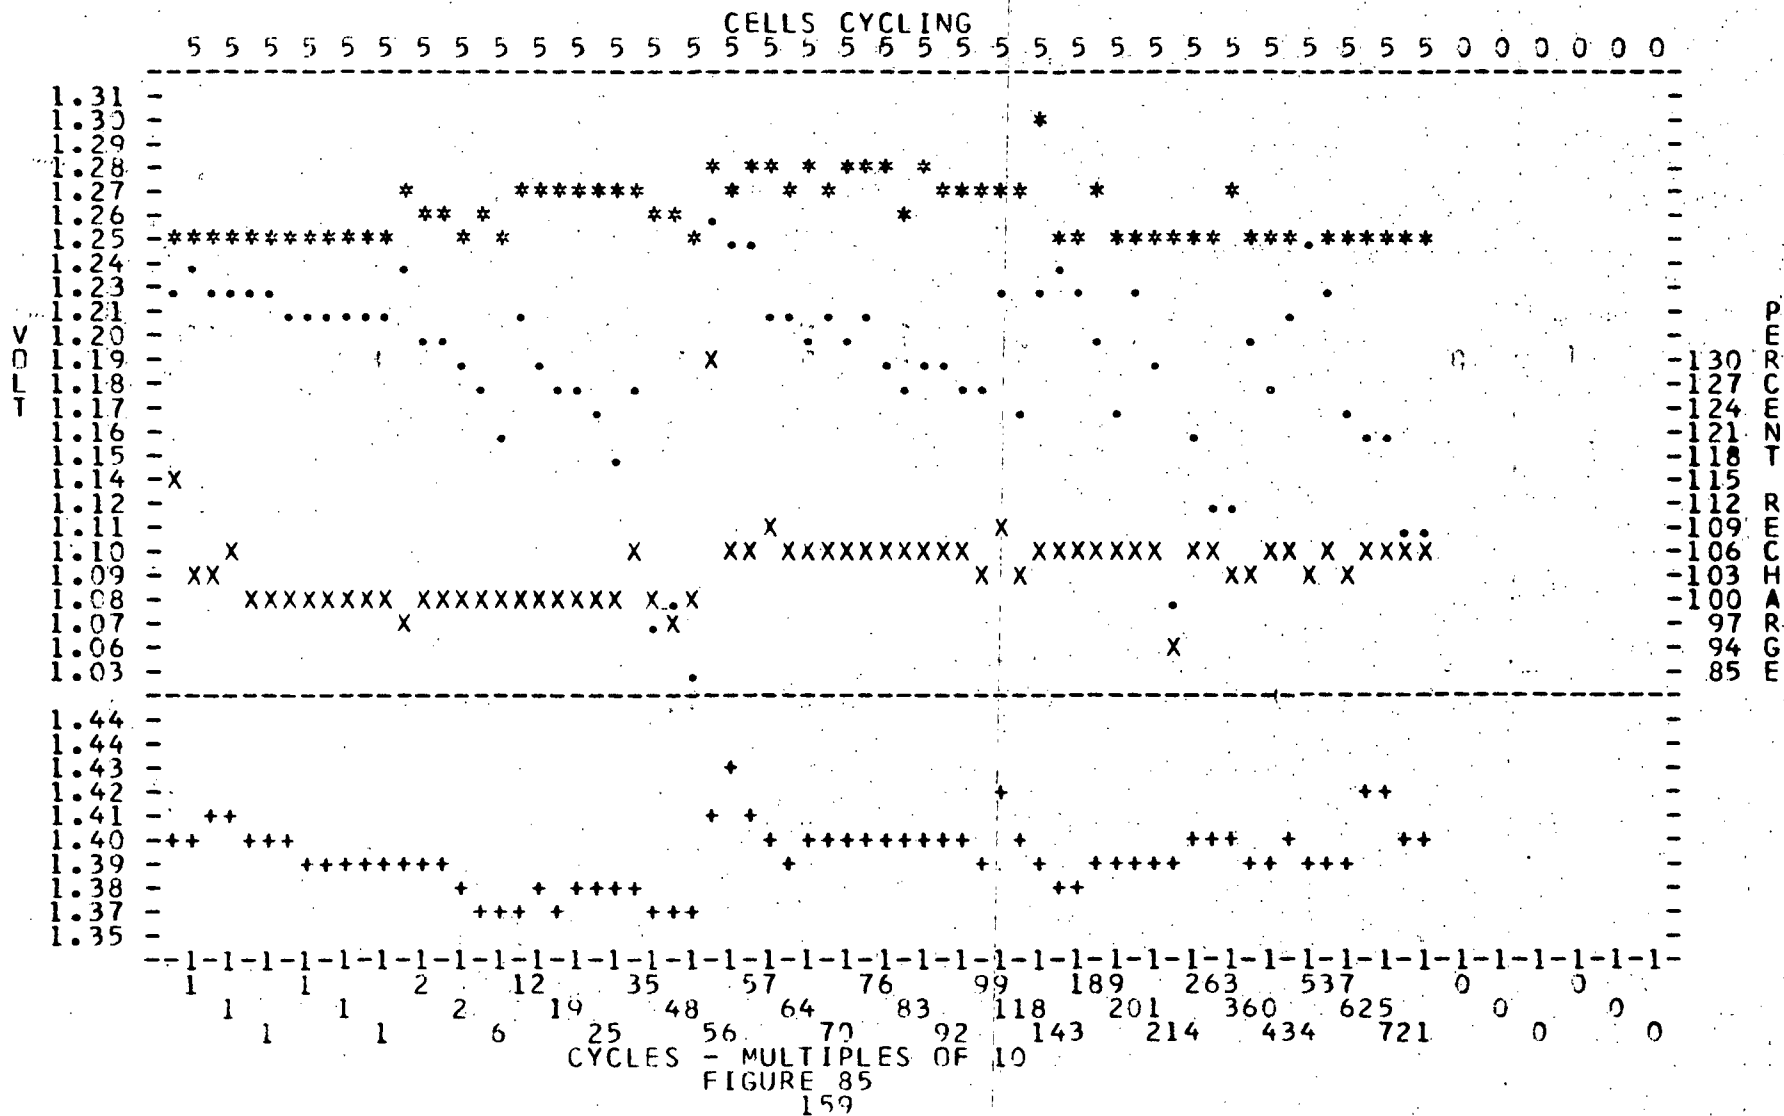


KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 027D MANF. GULTON
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 40
 CHARGE RATE AMPS 6.00
 DEPTH OF DISCHARGE % 50

QEEL/C 72-1 06.0 AH

CELLS CYCLING

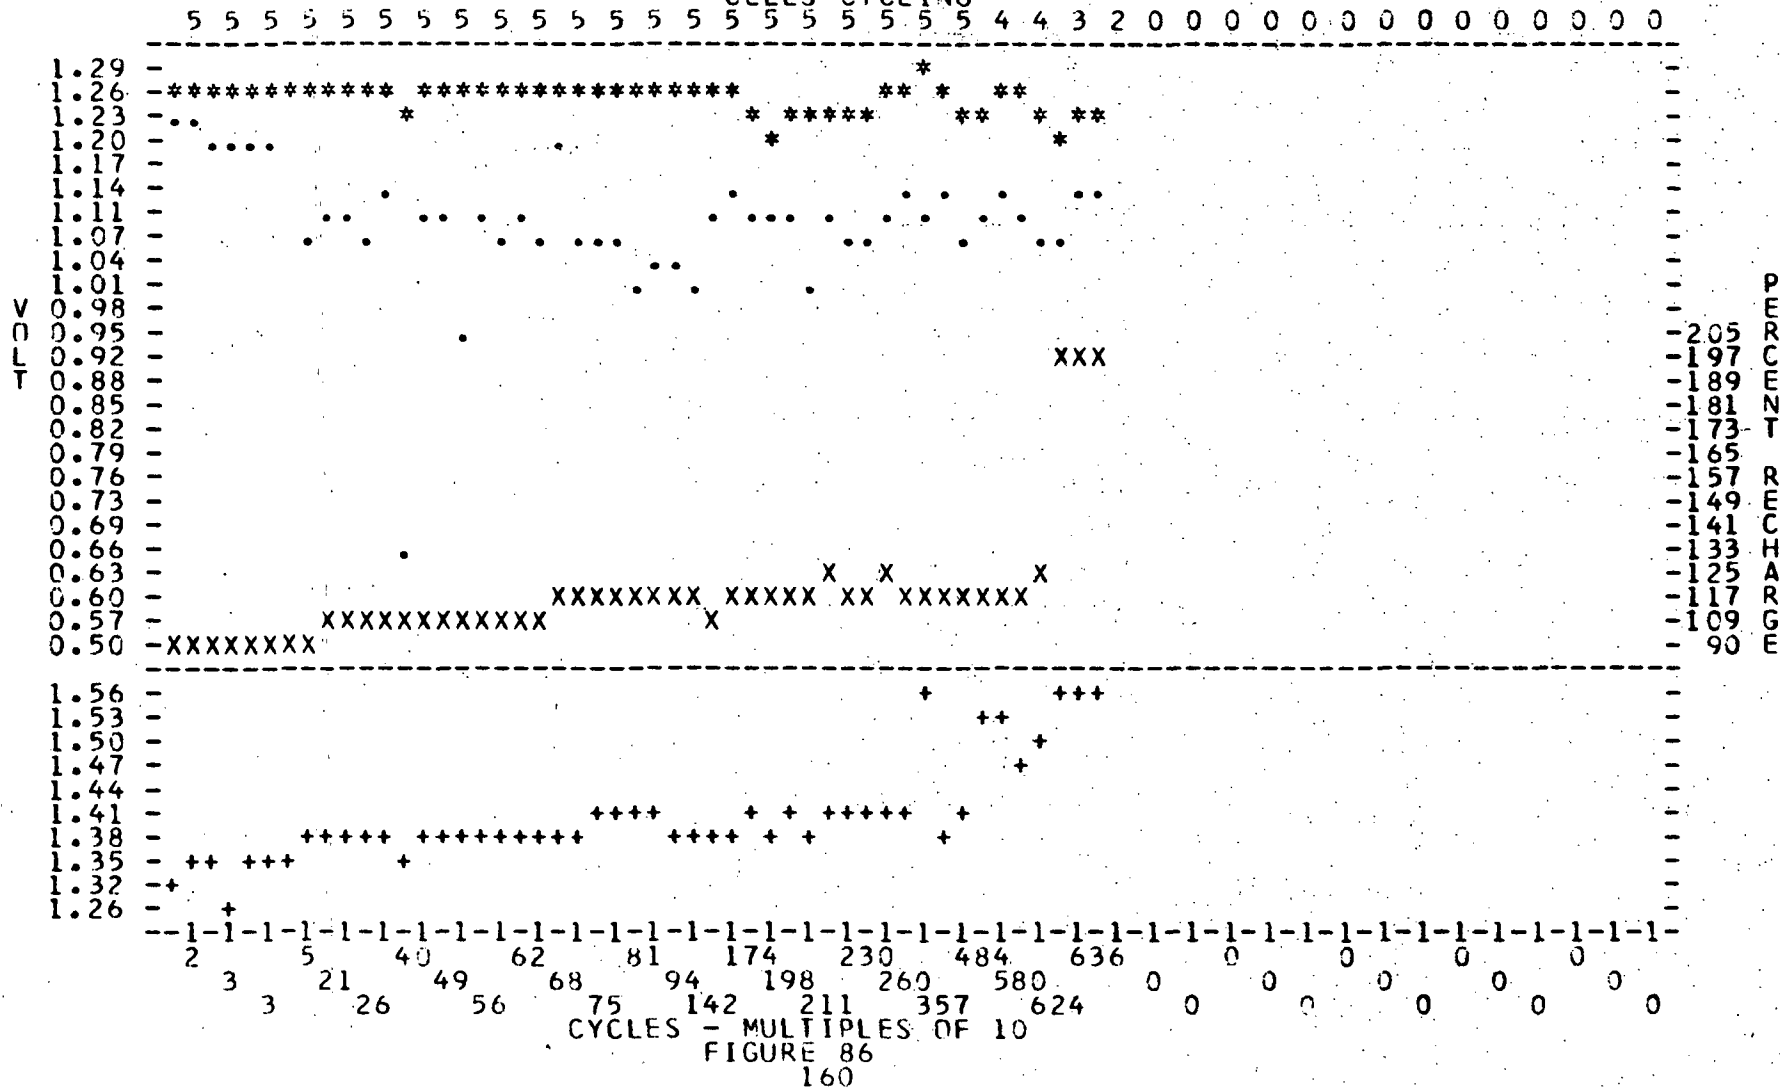

2. Gulton 6.0 ah (Nickel-Cadmium), RAE, Four 5-cell Packs:

a. Cell Description: See paragraph I.A., page 19.

b. Parameters and Capacity Checks:

Orbit Period		3.0-hour			
Temperature		-20°	0°	25°	40°
Depth of Discharge		25%	25%	25%	25%
Pack Number		41B	66B	18C	29B
Precycling Capacity		6.60	7.15	7.00	6.25
88 Days	Disch #2	6.45	6.90	2.75	2.35
264 Days	Disch #2	4.50	5.70	1.50	1.80
440 Days	Disch #2	3.05	4.75	1.35	1.55
616 Days	Disch #2	2.40	4.00	1.50	1.50
792 Days	Disch #2	1.45	4.25	1.55	1.60
968 Days	Disch #2	2.15	6.25	1.60	F
1091 Days*	Disch #2	3.30	*	*	F
1232 Days	Disch #2	2.00	6.10		
1408 Days	Disch #2	2.25	6.05		
1584 Days	Disch #2		1.15		F

* Number of days does not fit into 88-day sequence due to loss of time with numerous coulometer changes on Pack 41B.

F - Failed.

c. Test Results:

(1) Performance on Cycling: (Figures 87 and 88)
Cycling was started in November 1966. Pack 41B has completed 12,389 cycles with one cell failure. Packs 29B, 18C and 66B failed after 7941, 9633, and 13,396 cycles, respectively.

(2) Failure Analysis:

(a) Analysis of nine failed cells showed the major causes to be separator deterioration, ceramic short, and migration of the negative plate material. Other conditions found were high internal pressure, blistering of the positive plate material and electrolyte leakage. Due to the swollen condition and danger of damage to the rest of pack 41B, this cell has not been removed and analyzed.


(b) It was necessary to replace the coulometer in pack 41B, operating at -20°C , on nine occasions; and on one occasion in pack 66B operating at 0°C because each coulometer had shorted internally. The number of cycles between failures range from 193 to 3698 cycles for an average of 965 cycles. These failures were due to inadequate plate separation having one layer of nonwoven nylon. The failure mode being combated is cadmium migration. It has been found that coulometers require twice the effectiveness of plate separation as that found in its nickel-cadmium counterpart. These results have lead to the use of two layers of nonwoven nylon in RAE coulometers.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 041B MANF. GULTON 06.0 AH
 ORBIT PERIOD HOURS 03.0
 TEMP. DEGREES C. -20
 CHARGE RATE AMPS 3.00
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1

CELLS CYCLING

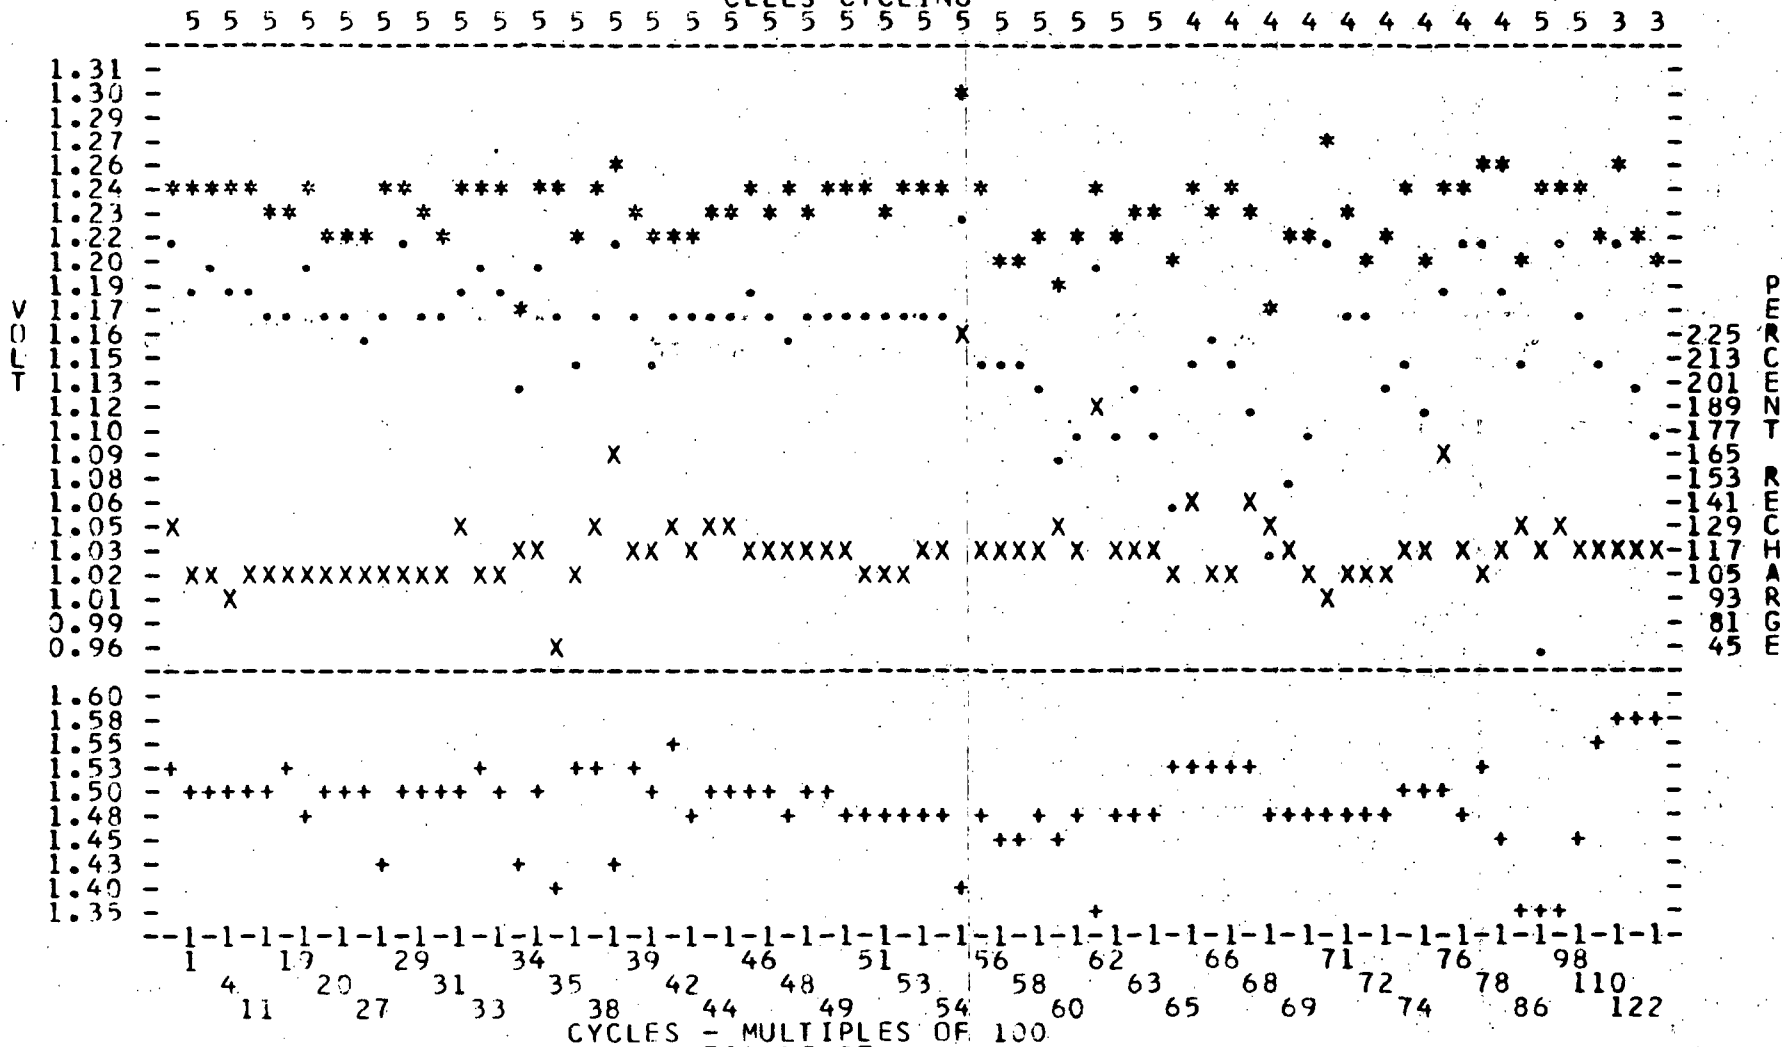

CYCLES - MULTIPLES OF 100


FIGURE 87

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 0668 MANF. GULTON 06.0 AH
 ORBIT PERIOD HOURS 03.0
 TEMP. DEGREES C. 00
 CHARGE RATE AMPS 3.00
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1

CELLS CYCLING

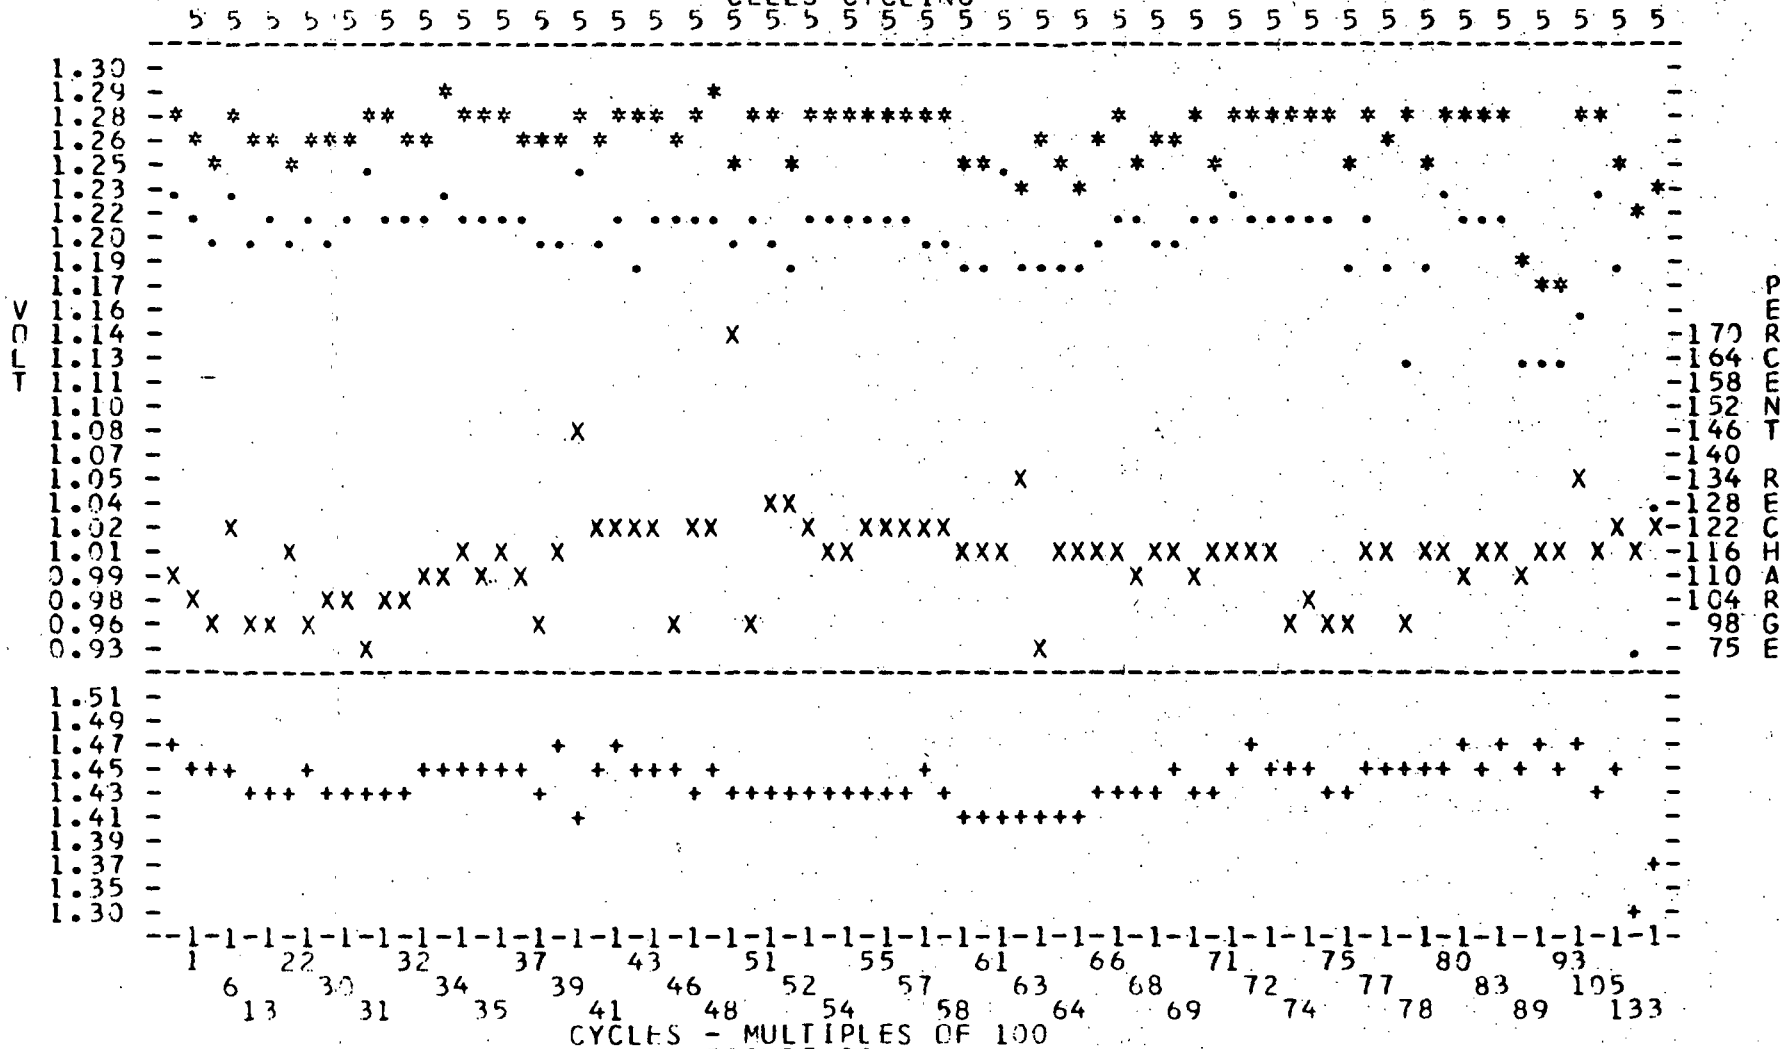

E. Internal Mechanical Pressure Devices: In certain instances the capacity output of a cell can be improved by applying pressure to the face of the plate stack. This test is designed to determine what effect, if any, a constant mechanical pressure has on the life of the cell.

1. Sonotone 20.0 ah (Nickel-Cadmium), Five 10-cell Packs, 1.5-hour and 3-hour Orbit Periods:

a. Cell Description: These cells are rectangular. The cell container and cell cover are made of stainless steel. Both terminals are insulated from the cell cover by a teflon seal and protrude through the cover as a threaded terminal. Each cell is also fitted with a pressure relief valve. Cells 1 through 5 in each pack are standard cells; cells 6 through 10 contain a stainless steel elliptical spring which supplies the pressure to the face of the plates.

b. Parameters and Capacity Checks:

Orbit Period	1.5	1.5	1.5	1.5	3.0
Temperature	20°	20°	20°	20°	20°
Depth of Discharge	25%	25%	40%	75%	40%
Pack Number	10B	22B	34C	72C	46B
Precycling Capacity	20.80	20.70	20.50	23.10	21.70
88 Days	21.67	20.00	19.70	22.70	20.20
176 Days	22.20	7.00 D	18.30	22.00	9.00 D
264 Days	22.17		18.00	16.18 F	
352 Days	9.33		16.00		
440 Days	8.67		14.16 F		

D - Discontinued.

F - Failed.


c. Test Results:

(1) Performance on Cycling: (Figures 89 through 91) Cycling was started in May 1970. Packs 22B and 46B were discontinued after 3419 and 1686 cycles, respectively, with two cell failures in pack 46B. Pack 10B has completed 9018 cycles with three cell failures. Packs 34C and 72C failed on cycles 8357 and 4381 respectively.

(2) Failure Analysis: Analysis of four failed cells revealed that separator deterioration and migration of the negative material were the major causes of failure. High pressure, weak tab-to-plate welds, extraneous active material, and blistering on the positive plates were also in evidence. Packs 22B and 46B were discontinued when they failed to reach the voltage limit on cycling thereby receiving a recharge in excess of 200 percent which was causing the cell cases to become exceedingly hot. These packs were sent to NASA, Lewis Research Center, for further testing and/or failure analysis.


PACK 010B	MANF.	SONO
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		20
CHARGE RATE AMPS		7.00
DEPTH OF DISCHARGE %		25

PACK 010B	MANF.	SONO
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		20
CHARGE RATE AMPS		7.00
DEPTH OF DISCHARGE %		25

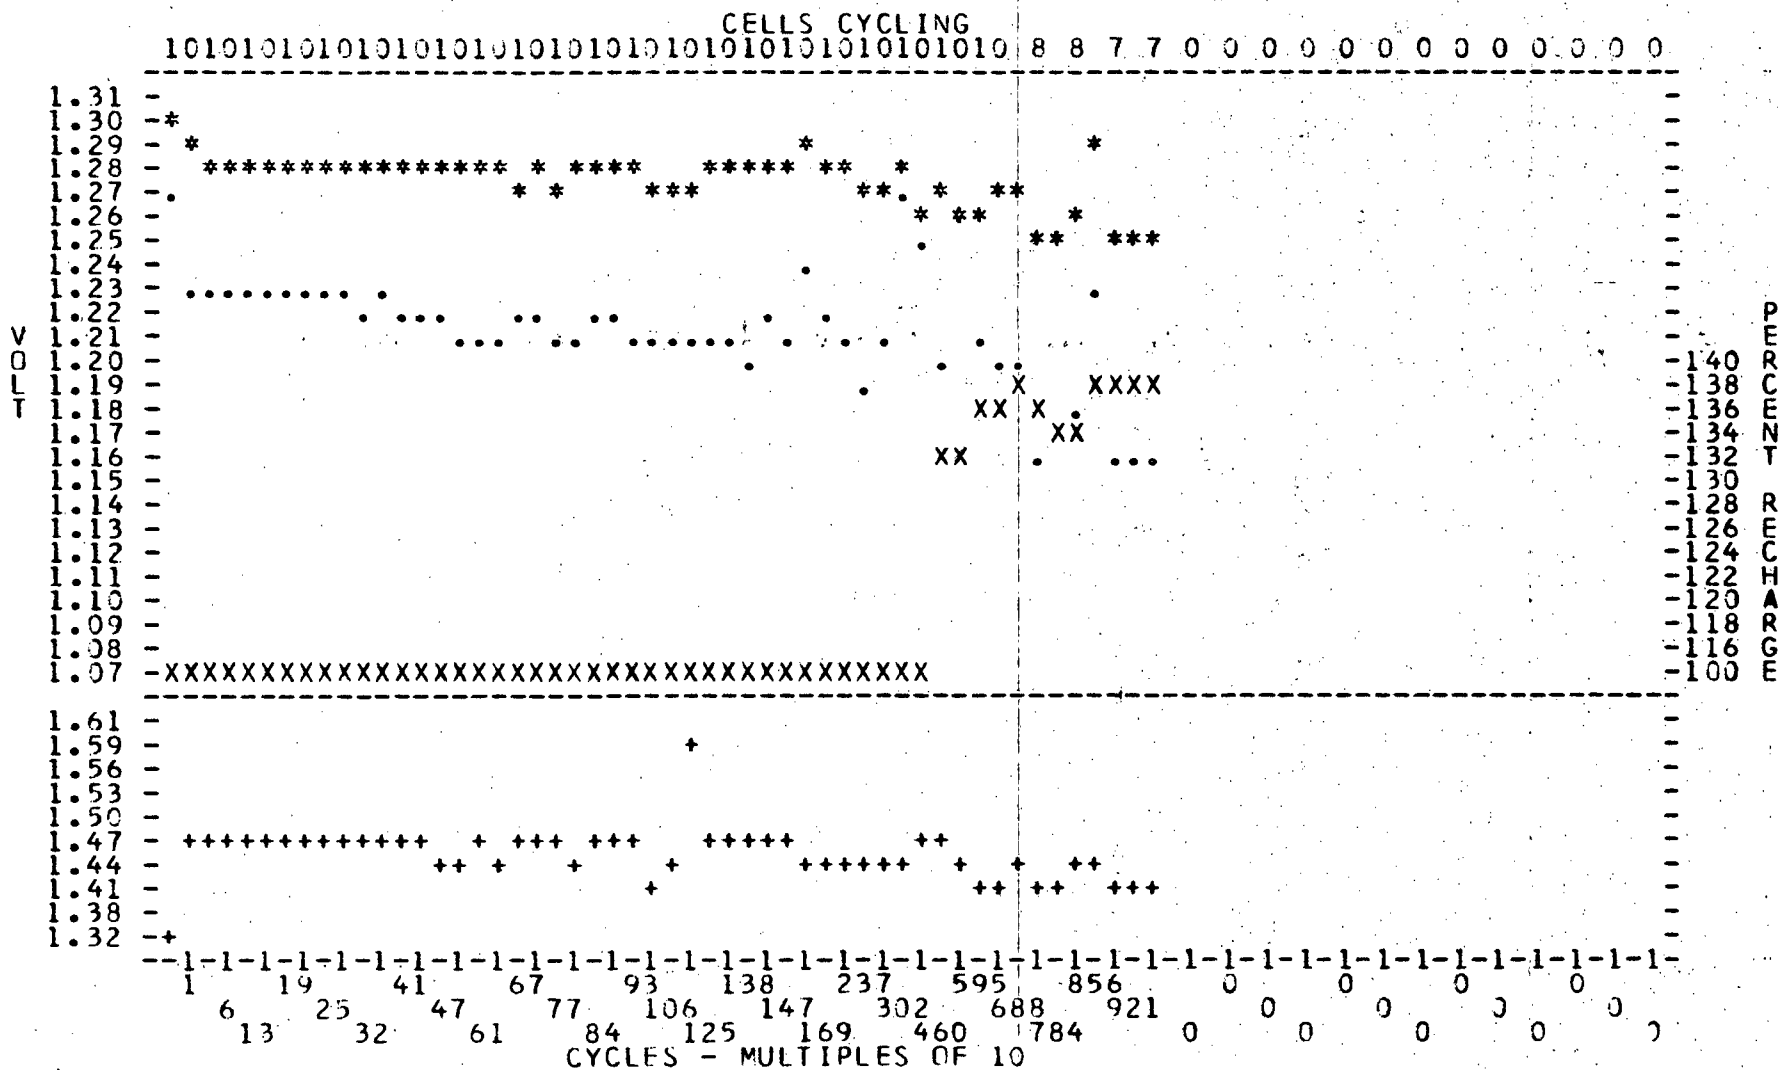


PACK 034C	MANF.	SONO
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		20
CHARGE RATE AMPS		15.00
DEPTH OF DISCHARGE %		40

PACK 034C	MANF.	SONO
ORBIT PERIOD HOURS		01.5
TEMP. DEGREES C.		20
CHARGE RATE AMPS		15.00
DEPTH OF DISCHARGE %		40

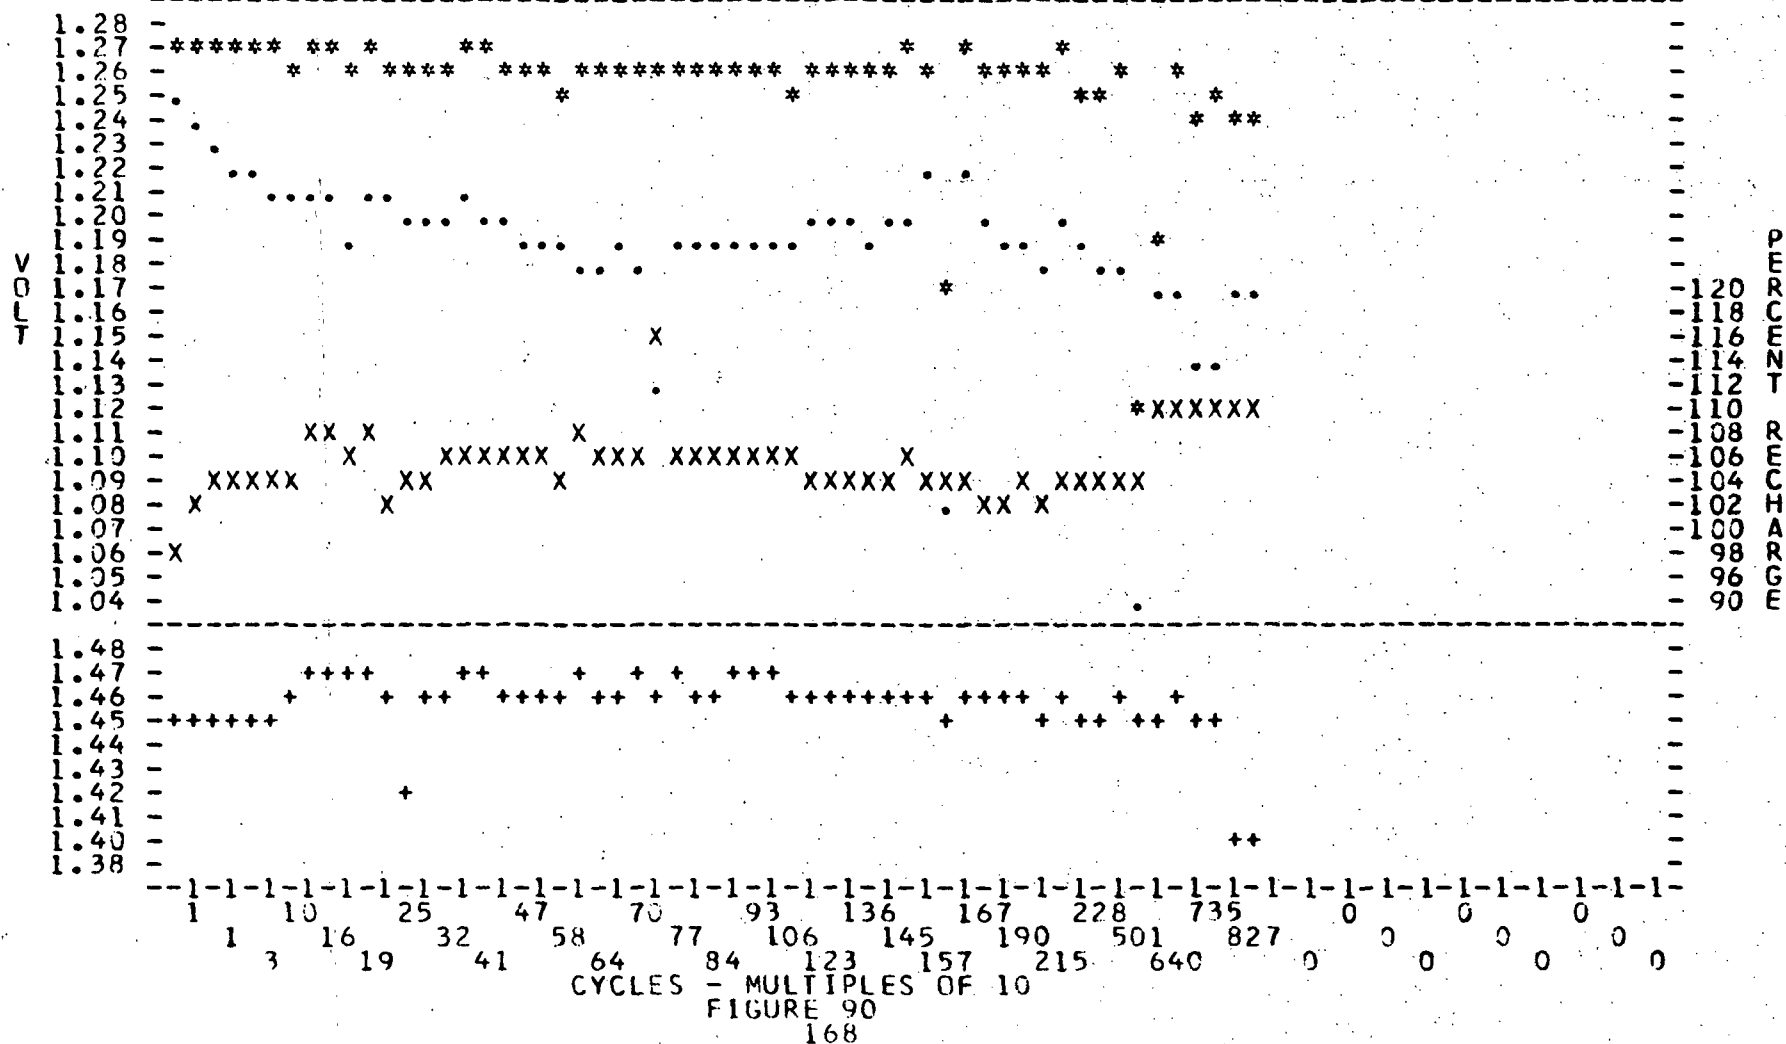[illegible]

PACK 072C	MANF. SNO
ORBIT PERIOD HOURS	01.5
TEMP. DEGREES C.	20
CHARGE RATE AMPS	20.00
DEPTH OF DISCHARGE %	75

CELLS CYCLING

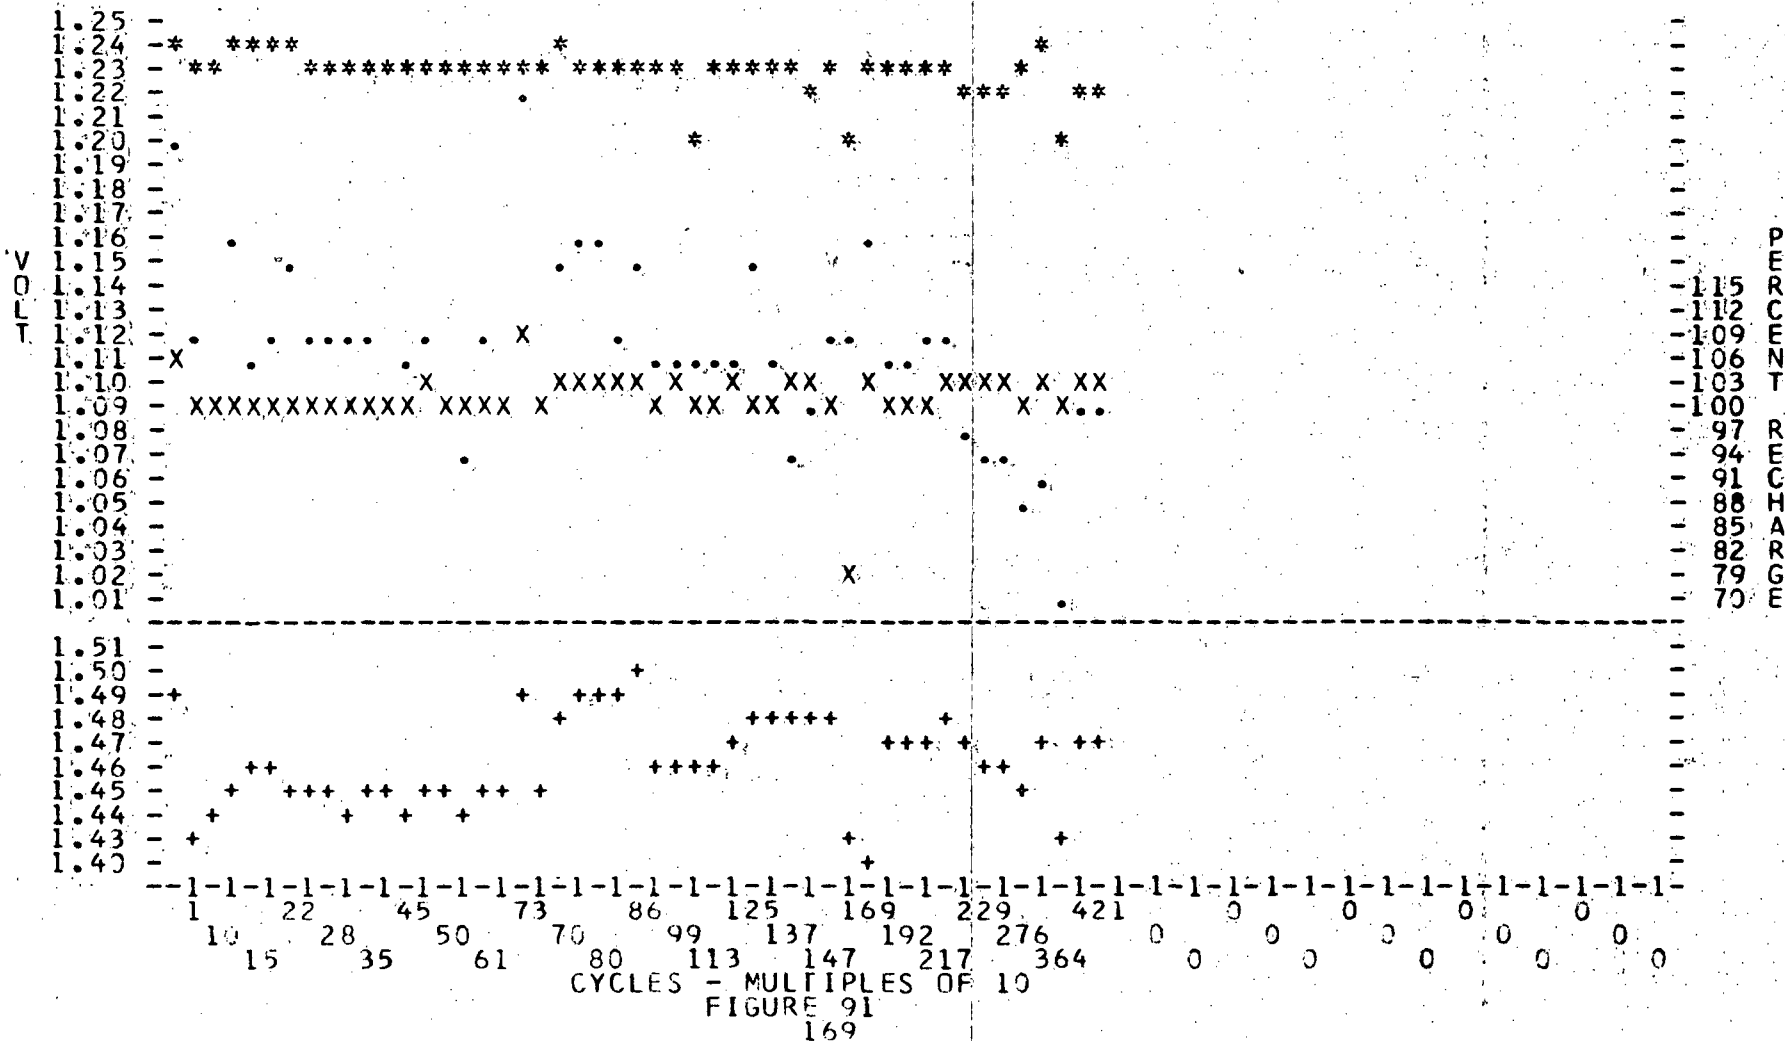[illegible]

F. Thermistor: This method of charge control utilizes a thermistor to maintain a constant total voltage on a cell pack at a specified temperature. Should the specified temperature be exceeded or lowered, the resistance of the thermistor is correspondingly changed. The charging circuitry then establishes a new voltage limit and the charge current is automatically adjusted to maintain the new limit.

1. Gulton 6.0 ah (SAS A), One 8-cell Pack:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

Pack Number	180
Orbit Period	1.5
Test Temperature	25°
Depth of Discharge	21%
Precycling Capacity	6.99
88 Days	7.75
176 Days	7.33
264 Days	6.08
352 Days	6.88
440 Days	5.75


c. Test Results:

(1) Performance on Cycling: (Figure 92) Cycling started in July 1970. This pack has completed 8110 cycles with no cell failures; although one cell was removed for analysis and replaced with a cell of the same type. Analysis showed the equivalence percentage of carbonate to range from 37.4 percent to 40.9 percent, averaging 39.6 percent.

X-----PERCENT RECHARGE

DEPTH OF DISCHARGE %

GE % 25

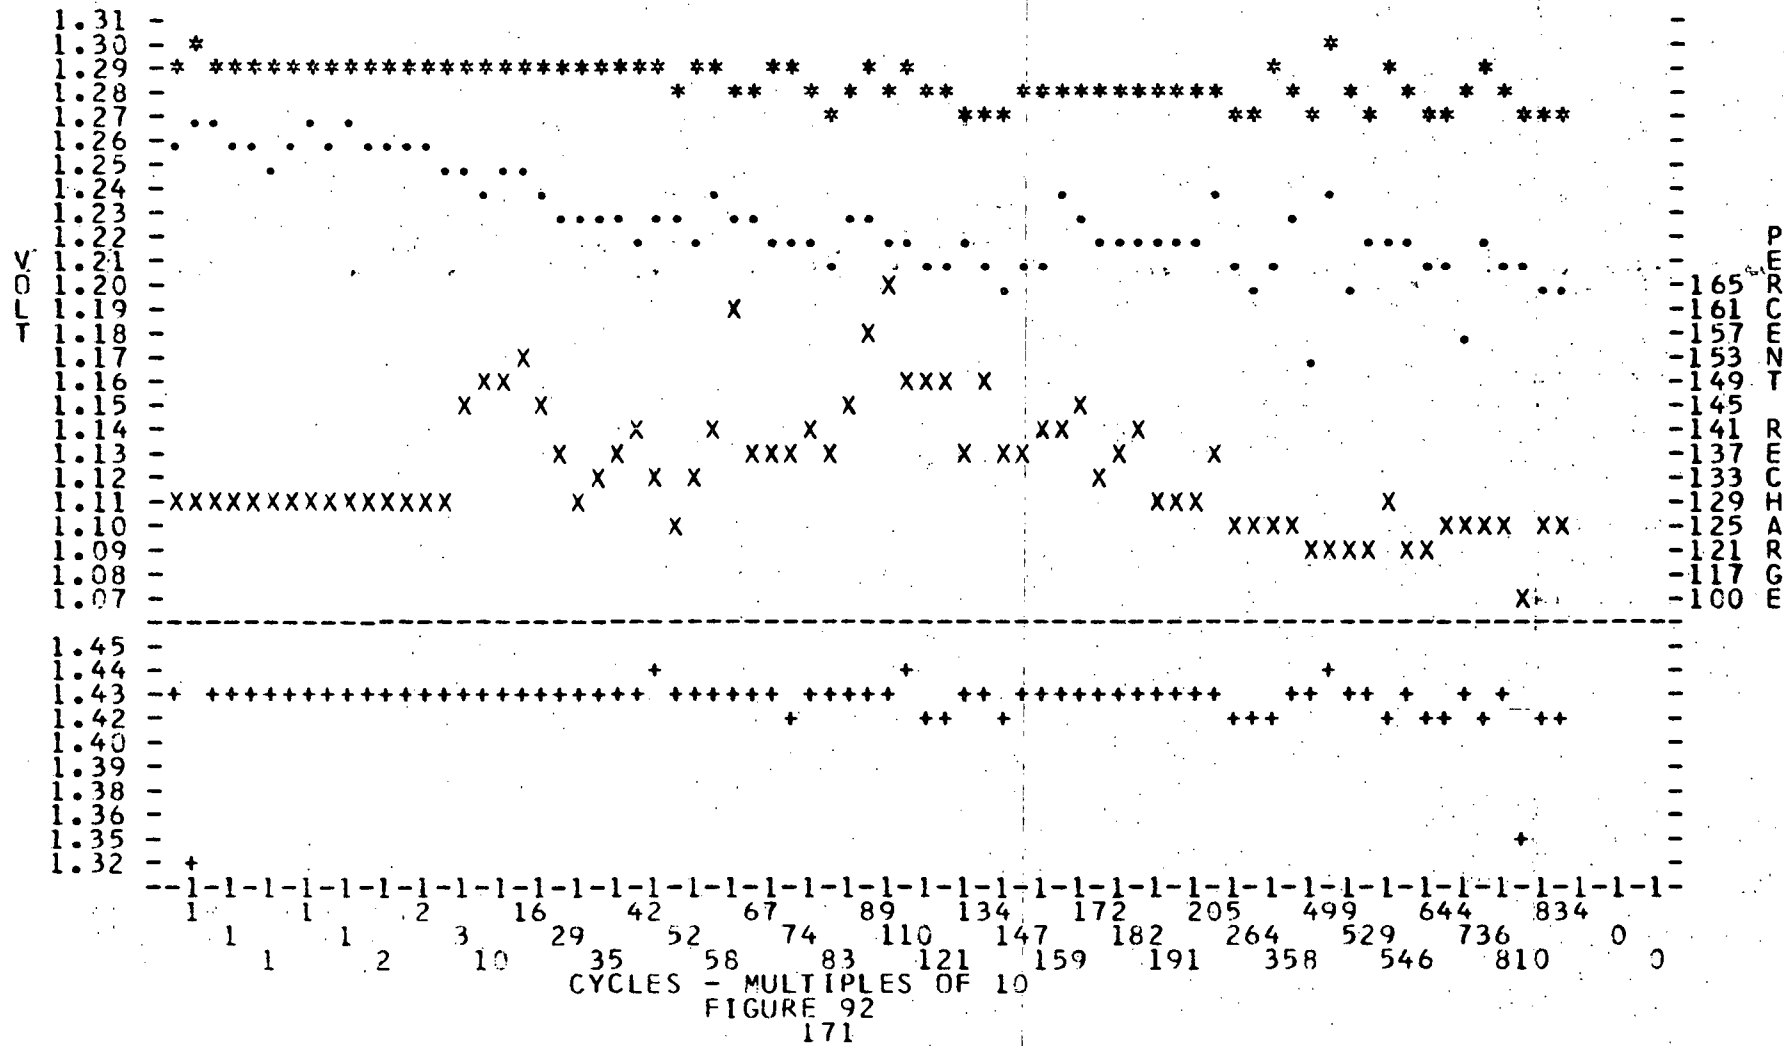[illegible]

2. GE 6.0 ah (SAS B), One 8-cell Pack:

a. Cell Description: See paragraph II.A., page 88.

b. Parameters and Capacity Checks:

Pack Number	1C
Orbit Period	1.5
Test Temperature	25°
Depth of Discharge	21%
Precycling Capacity	6.99
88 Days	6.13
176 Days	6.17
264 Days	5.95
352 Days	5.18
440 Days	5.13

c. Test Results:


(1) Performance on Cycling: (Figure 93) Cycling started in July 1970. This pack has completed 8110 cycles with no cell failures; although one cell was removed for analysis and replaced with a cell of the same type. Analysis showed the equivalence percentage of carbonate to range from 53.2 percent to 64.9 percent, averaging 58.2 percent. Also noted was migration and blistering of positive plates.

KEY AVERAGE CELL VOLTAGE
 *-----MIDDLE DISCHARGE
 .-----END OF DISCHARGE
 +-----END OF CHARGE
 X-----PERCENT RECHARGE

PACK 001C MANF. GE
 ORBIT PERIOD HOURS 01.5
 TEMP. DEGREES C. 25
 CHARGE RATE AMPS 3.50
 DEPTH OF DISCHARGE % 25

QEEL/C 72-1
 06. AH

CELLS CYCLING
 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 5 8 8 8 8 8 8 8 8 8 8 8 8 8 8 8 8 0 0 0

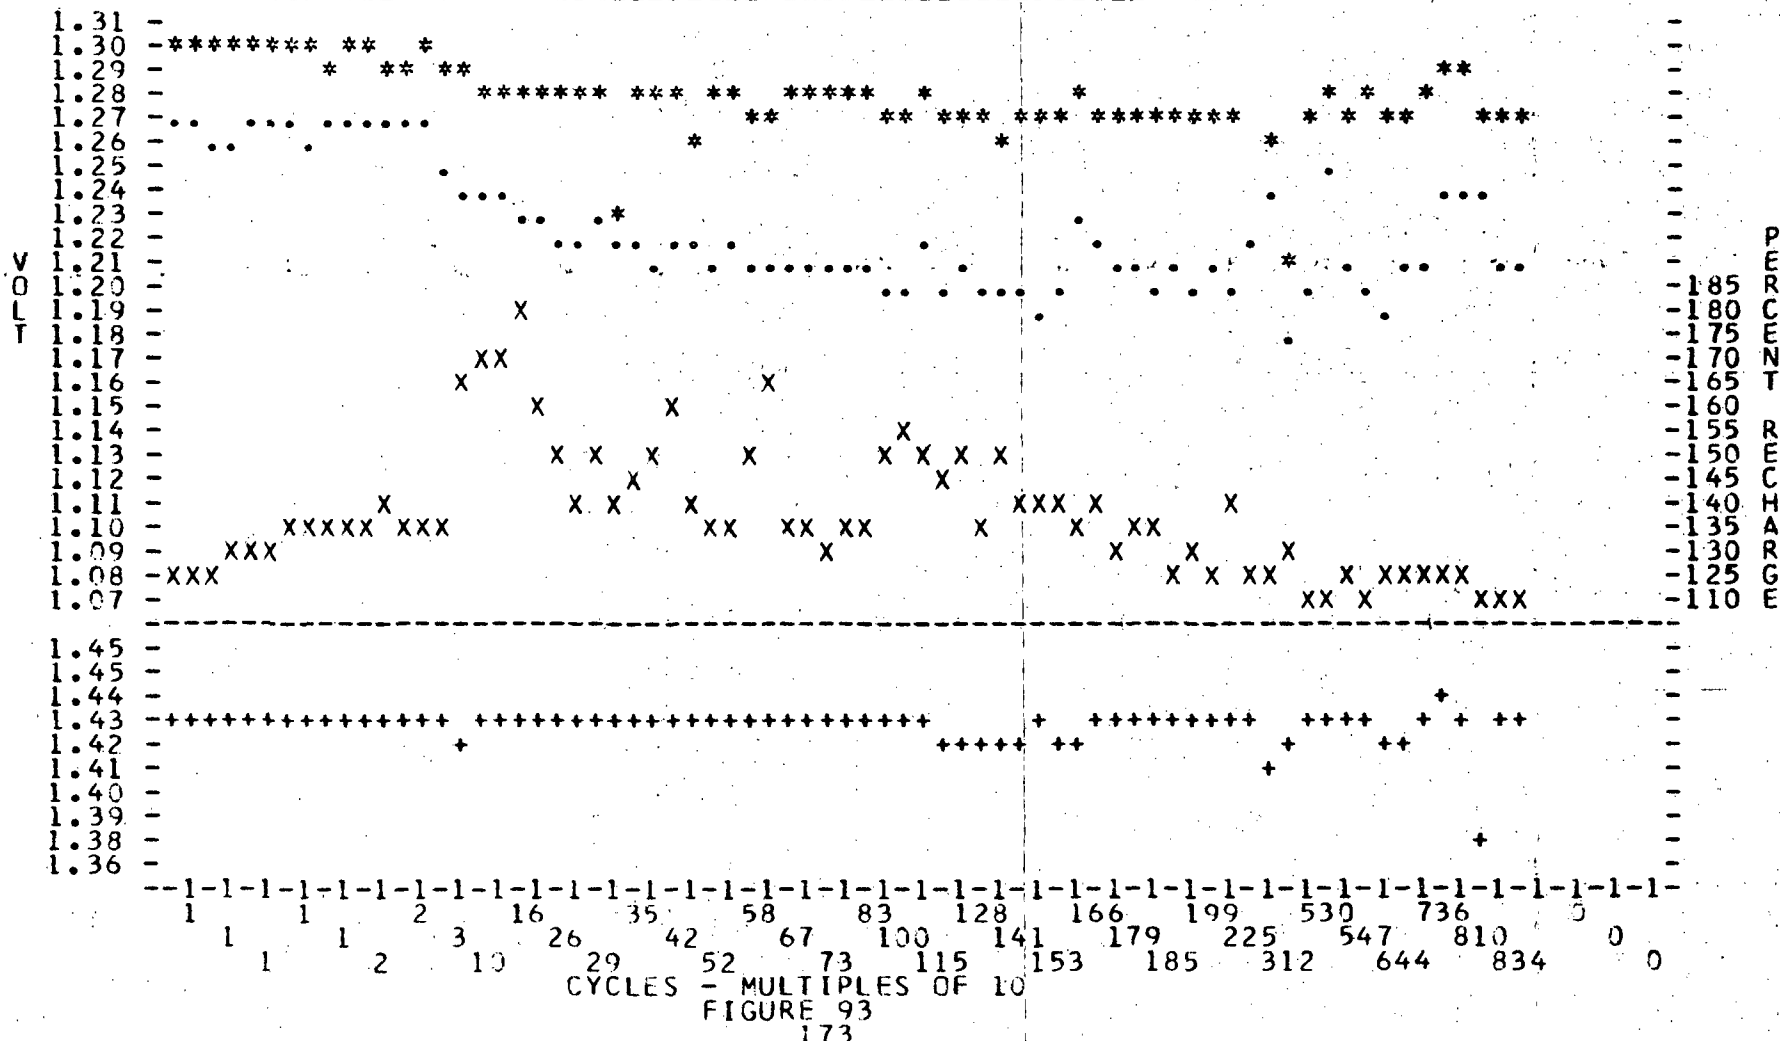

SECTION III

CELLS ON ORIGINAL TEST PROGRAM WHICH HAVE
COMPLETED TEST

I. CELLS ON ORIGINAL TEST PROGRAM WHICH HAVE COMPLETED TEST

A. In order to gather sufficient data to indicate the performance of nickel-cadmium cells cycled at various test conditions; 660 cells were placed on test during December 1963 and January 1964. These cells were from four manufacturers and consisted of seven different types as shown in Table I.

B. The cells were grouped in packs of 5 or 10 cells depending upon the ampere-hour capacity. All cells rated above 6.0 ampere-hours were grouped into 5-cell packs; the remainder were placed in 10-cell packs.

II. DESCRIPTION OF CYCLE TEST

A. The cells were operated at three temperatures and three depths of discharge, which are summarized in Table II. Each pack was cycled under its respective conditions until 60 percent or more of the cells failed. A cell was considered failed when its terminal voltage dropped below 0.5 volt at any time during cycling.

III. TEST RESULTS

A. The cycling results show that discharge voltages tend to drop slightly or remain the same during the life test. The drop is usually not more than 0.04 volt per active cell. The exceptions to this are immediately after a capacity check when there is an increase in the discharge voltage and when a cell is about to fail, the average voltage drops more rapidly. The least overall change is seen at 0° C. For a given temperature and cell type, the discharge voltage is generally from 0.02 to 0.08 volt per cell lower at the greater depths of discharge, that is, at the higher rate, as expected. The discharge voltage tends to decrease no more than 0.1 volt per cell with increases in test temperature from 0° C to 40° C for each depth of discharge. The amount of decrease depends on the cell type. The orbit period seems to have little effect on the discharge characteristics of normally functioning cells (the 1.5-hour and 3-hour orbit periods both have 30-minute discharge periods).

B. When pronounced long term changes in percent of recharge and end-of-charge voltage occurred, they were almost always in the direction of lower percent of recharge and higher voltage although some of the packs did have an increase in the percent of recharge. On the average, packs operating at 0° C had an

early percent of recharge of 107 percent and after 5 years it was 105 percent. While at 25° C, the early percent of recharge was 120 percent and after 4 years it was 118 percent. At 40° C, the early percent of recharge was 153 percent and after 4 years it was 146 percent. At all temperatures the percent of recharge is, on the average, below the specified percent of recharge indicating that the amount of recharge need not be as high as was originally set for the testing program--approximately 10 percent less.

C. Capacity Check Results:

1. The ampere-hour capacity was checked approximately every 88 days. These capacity checks showed that temperature had a very definite effect on the loss of capacity. The packs cycled at 40° C showed a very rapid drop in capacity until failure occurred. The loss of capacity was not as severe for the packs at 25° C while those operated at 0° C showed very little capacity loss. Orbit periods and depths of discharge also have a small effect but these do not show any definite trends.

2. The ampere-hour capacity checks also show how the cells degrade during life cycling.

D. Cell Failures:

1. The analysis of the failed cells is a very important phase of the testing program. From these analyses manufacturing defects, poor design, and material weakness can be detected and an effort made to correct or improve them. This in turn will lead to a better product with better performance characteristics.

2. Special Considerations:

a. The charge rates specified in the cycling program usually exceeded the maximum rates recommended by the manufacturers. For example, packs which are cycling in a 1.5-hour orbit at 25° C, 40 percent depth of discharge are being charged at the $c/2$ rate, although the maximum charge rate recommended by the manufacturers is $c/10$. The only charge rates below $c/10$ are those for the 3-hour orbit, 15 percent depth of discharge combinations, the rates for which are calculated to be $c/14.5$ at 0° C and $c/10.4$ at 40° C.

b. These cells were manufactured prior to January 1963. Because of subsequent changes in construction, newer cells of the same capacity and manufacturer may not show the characteristics discussed here. Also, the manufacturers have reported that corrective action has been taken to eliminate the sources of premature mechanical failure.

3. Discussion of Failures:

a. General Observations:

(1) Most of the cell failures occurred at the higher ambient temperatures. The cell failures were earlier and more frequent at the greater depths of discharge and shorter orbit periods. A detailed summary of the failure analysis for each cell may be obtained by request to the NASA Technical Officer (See Introduction).

(2) Many of the cell failures may be considered premature because they resulted from a defect in manufacture or design. This is in contrast to an end-of-life failure, in which a basic component, such as a separator, has reached the end of its normal life span at the particular cycling conditions. Some examples of premature failures are those due to leakage, pierced separators, burned tab, ceramic short, or extraneous active material.

(3) It is frequently difficult to isolate the exact cause of failure for a particular cell. In some cases several factors may have been responsible. In others, it is not obvious why the conditions found should have resulted in failure. For this reason, unless otherwise stated, this report will not attempt to isolate the direct cause of failure; the conditions noted in the discussions are included because they are abnormalities and because they may have contributed to the cell failure.

b. Discussion of Failures by Cell Type:

(1) GE:

(a) 3.0 ah Cells: There were 48 cell failures, of which four were at 0° C, 19 were at 25° C, and 25 were at the 50°-40° C ambient temperature.

1. Migration was present at all test conditions except 25 percent depth of discharge, 40° C and 1.5-hour orbit period. This was probably because of the burned tabs, along with short separators, which occurred early in life, only 157 days of cycling. Separator deterioration began to appear in failures that occurred after 287 days of cycling. Blistering on the positive plates was very common at 25° C after 436 days of cycling.

(b) 12 ah Cells: There were 27 failures, of which three were at 0° C, 12 were at 25° C and 12 were at 50°-40° C.

1. Migration was present in most of the cell failures that occurred after 239 days of cycling. Cell failures began to show signs of separator deterioration after 240 days of cycling. High internal pressures occurred in a few cell failures at all ambient temperatures.

(2) Gould:

(a) 3.5 ah Cells: There were 63 cell failures, of which eight were at 0° C, 26 were at 25° C and 29 were at 50°-40° C ambient temperature.

1. Weight loss was one of the main conditions found in these failures. Losses ranged from 1.0 gram to 7.1 grams. Deposits were always present with the weight loss which occurred earlier at 25° C and 40° C but did not appear in the cell failures at 0° C until after 687 days of cycling. Migration and separator deterioration were present at all conditions. The number of weak welds inside of the cells analyzed varied with temperature as indicated by 14 weak welds out of 29 failed cells at 40° C; 11 weak welds out of 26 failed cells at 25° C; and 1 weak weld out of 8 failed cells at 0° C.

(b) 20 ah Cells: There were 29 cell failures, of which five were at 0° C, 12 were at 25° C and 12 were at 50°-40° C ambient temperature.

1. High internal pressure was present in almost all failures. Pierced separator was more predominant at the 1.5-hour orbit period at all ambient temperatures. Blisters were present on the positive plates at 25° C for the 3-hour orbit period and the 1.5-hour and 3-hour orbit periods at 40° C.

(3) Gulton:

(a) 6.0 ah Cells: There were 68 cell failures, of which 20 were at 0° C, 24 were at 25° C and 24 were at 50°-40° C ambient temperature.

1. Ceramic shorts were the most common mode of failure. Weight losses were also very common and ranged from 1.0 gram to 12.0 grams. Most of the cells that lost weight did not show signs of leakage in the form of deposits around the seals. Most of the failures due to ceramic short did not show signs of migration or separator deterioration because the failures occurred early in life.

(b) 20 ah Cells: There were 36 cell failures, of which eight were at 0° C, 15 were at 25° C and 13 were at 50°-40° C ambient temperature.

1. Weight losses were very common at 0° C and 25° C and ranged from 6.8 grams to 26.9 grams. Most of the cells that lost weight did not show signs of leakage in the form of deposits around the seals. Several cell failures were caused by the sides of the case being pushed against the buses at the top of the plates. Migration and separator deterioration were found at 40° C but not very common at 0° C or 25° C.

(4) Sonotone:

(a) 5.0 ah Cells: There were 51 cell failures, of which six were at 0° C, 21 were at 25° C and 24 were at 50°-40° C ambient temperature.

1. Excess scoring, along with migration, was present in most of the cell failures at all ambient temperatures. Separator deterioration was more frequent at 25° C and 40° C. High internal pressure and leakage as shown by deposits around the seal were present at 25° C and 40° C.

TABLE I
PHYSICAL CHARACTERISTICS OF CELLS

<u>Manufacturer and Manufacturer's Rated Capacity</u>	<u>Shape</u>	<u>Average Dimensions (Inches)</u>			<u>Average Weight (Grams)</u>	<u>Case Polarity</u>
		<u>Height Base to Top of Terminal</u>	<u>Width or Diameter</u>	<u>Length or Depth</u>		
GE 3.0 ah	Cylindrical	3.10	1.25 D	--	155.0	Negative
*Gould 3.5 ah	Cylindrical	2.22	1.28 D	--	135.2	Positive
Sonotone 5.0 ah	Cylindrical	3.67	1.31 D	--	237.4	Negative
Gulton 6.0 ah	Rectangular	3.68	2.09 W	0.81	267.0	Negative
GE 12.0 ah	Rectangular	4.59	3.02 W	1.11	562.0	--
Gould 20.0 ah	Rectangular	*7.95	3.05 W	0.97	1045.0	--
		**8.10	3.56 W	1.49	1423.0	--
Gulton 20.0 ah	Rectangular	7.10	2.98 W	0.90	871.6	--

* Before Epoxy Cover

** After Epoxy Cover

TABLE II

SUMMARY OF TEST PARAMETERS

For each orbit period, one pack of each of the seven cell types is cycling at each of the six temperature-depth of discharge combinations.

ORBIT PERIODS: 1.5 Hours and 3.0 Hours			
Discharge Time	Charge Time	Temperature °C	Percent Depth of Discharge
30 Minutes	60 Minutes and 2.5 Hours	(50*)	(15) (25)
		40	15 25
		25	25 40
		0	15 25

* All packs changed to 40° C ambient.

SECTION IV

COMPLETED TESTS OF CELLS WHICH FOLLOWED THE
ORIGINAL PROGRAM

I. COMPLETED TESTS OF CELLS WHICH FOLLOWED THE ORIGINAL PROGRAM

These packs were added to the cycling program to obtain information either on new cell types or new test parameters. Each pack was cycled until 60 percent or more of the cells failed. A cell is considered a failure when its terminal voltage drops below 0.5 volt during cycling. Testing has been terminated on all packs covered in this section of the report.

II. CELLS USING CONSTANT CURRENT CHARGE WITH VOLTAGE LIMIT CONTROL

A. Nickel-Cadmium Types:

1. Gulton 6.0 ah, One 5-cell Pack, 24-hour Orbit Period (Pack 79A):

a. Cell Description: The cells are rectangular in shape. The cell container and cell cover are made of stainless steel. The positive terminal is insulated from the cell cover by a ceramic seal; while the negative terminal is welded to the cover. Both are solder type terminals.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 50%.

c. Test Results:

(1) Performance on Cycling: Cycling was started in March 1964. The pack failed on cycle 545 with four cell failures.

(a) All cell voltages dropped below 1.0 volt at the end of discharge with the original 150 percent of recharge. Increase of the recharge to 200 percent after cycle 57, caused the end-of-discharge voltages of all five cells to remain fairly constant at about 0.9 volt. Two cells failed at 149 and 168 cycles; then the end-of-discharge voltages of the remaining three cells climbed to an average of 1.08 volts per cell. The end-of-charge voltages remained fairly constant, between 1.39 and 1.40 volts per cell, average, throughout life cycling.

(b) Cell Failures: Analyses of the four cell failures showed that all had separator deterioration and blistering on the positive plates. The first two failures had high internal pressure as indicated by outgassing when opened. The last two failures had pinpoint migration which caused shorts through the separator.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Precycling		6.60
88 Days	Disch #2	3.55
176 Days	Disch #2	4.40
264 Days	Disch #2	4.25
352 Days	Disch #2	4.05
440 Days	Disch #2	3.50

2. Gulton 50 ah, Two 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Description: These are rectangular, hermetically sealed, nickel-cadmium cells.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
95A	0° C	25
123A	40° C	25

c. Test Results:

(1) Performance on Cycling: Cycling was started in June 1964.

(a) Pack 95A failed on cycle 3227. The end-of-charge voltage increased and the end-of-charge current decreased steadily until the first cell failed on cycle 2643. The end-of-charge voltage then decreased and the end-of-charge current increased. The second cell failure occurred on cycle 2938 but this did not affect the operation of the pack. The separator in each of the first two failed cells was very dry and short circuits had occurred between the plates. Large blisters were present on the positive plates of the first failed cell and slight migration of material from the negative plates was evident in the second failed cell. The positive plates of the third failed cell showed large blisters, and separators impregnated with negative plate material.

(b) Pack 123A completed 1873 cycles when the first cell failure occurred. It had low voltage during the discharge and the recharge. Two additional cells shorted out while the pack was off cycling to remove the first failed cell. The separators of all three cells had deteriorated, resulting in shorts between the plates in two of these cells. The outside negative plates of two cells were stuck to the case. The three failed cells had bulged cases from high internal pressure; two of which were still under pressure, and the third had a carbonate deposit at the positive terminal.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

(a) Pack 95A:

Precycling	54.6

88 Days Disch #2	59.6

176 Days Disch #2	45.4

(b) The precycling capacity of pack 123A at 40° C was 27.9 ampere-hours. An equipment failure interrupted the first capacity check. The pack was then allowed to complete an additional month of cycling in order to let the cells stabilize again before receiving a capacity check, but the pack failed shortly before the capacity check was to have begun.

3. GE 12.0 ah, One 5-cell Pack, 24-hour Orbit Period
(Pack 93A):

a. Cell Description: The cells are rectangular in shape. The cell container and the cell cover are made of stainless steel. Both terminals are insulated from the cell cover by ceramic seals and protrude as 1/4-20 threaded posts.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 50%.

c. Test Results:

(1) Performance on Cycling: Cycling was started in March 1964. This pack failed on cycle 349.

(a) Average end-of-discharge voltage fell to less than 1.0 volt per cell under the original test parameters, but satisfactory operation was obtained when the percent of recharge was changed to 200 percent after cycle 57.

(b) In order to gain additional information the environmental temperature was raised from 25° C to 40° C after 173 cycles, with the charge voltage limit lowered to 1.45 volts per cell, average. At 40° C the pack did not operate as well. End-of-discharge voltages of the pack were low and quite variable. Two cells appeared to have failed on cycle 266. Since the first cell showed no defects upon failure analysis, the second cell was discharged completely and shorted overnight. It was then charged for 16 hours at the c/10 rate, and discharged again at the c/2 rate, all at 25° C. Its capacity was thus found to be 12.9 ampere-hours. It was returned to the pack and continued to cycle until the pack failed on cycle 349. The cycling behavior of these two cells was attributed to insufficient charge acceptance. At no time was the on-charge voltage limit reached. The end-of-charge voltage remained close to 1.39 volts per cell at both temperatures.

(c) The four remaining cells (including the one returned cell) failed on cycle 349. All of the cells showed

separator deterioration and migration of the negative plate material. All cells showed signs of leakage around the terminals but no weight loss was detected.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Precycling		25° C	13.0
100 Days	Disch #2	25° C	7.60
231 Days	Disch #2	40° C	6.50
339 Days	Disch #2	40° C	5.00

B. Silver-Zinc Types:

1. Astropower Division of McDonnell-Douglas 5.0 ah, Four 10-cell Packs:

a. These cells are sealed, but are provided with vent caps designed to vent the cell at a pressure of 40 psig. The cells are rectangular, with cell jars and cell covers molded of plastic. The zinc electrodes are encapsulated in an inorganic separator. The silver electrodes are separated from the inorganic separator by pellant. A small volume of epoxy potting material is poured into the cell jars just prior to the insertion of the electrodes and prevents movement of the electrodes. The cell top is then sealed to the cell jar by means of epoxy potting. The fill port is sealed by means of a screw and rubber O-ring.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Orbit Period
25B	20° C	25	1.5
25C	20° C	25	12.0
37D	40° C	25	12.0
47D	40° C	25	1.5

c. Test Results:

(1) Performance on Cycling: Cycling was started in December 1969 for Packs 25B and 47D; and in February 1970 for packs 25C and 37D. Packs 25B, 47D, 25C, and 37D failed on cycles 681, 2013, 567 and 391 cycles, respectively. As requested by NASA, Lewis Research Center, each pack was cycled until all cells failed.

(2) Failure Analysis: Analysis of the 40 failed cells showed that 22 cells had cracked inorganic separators due to a shape change of the zinc plate. Cells that were life-cycled at 40° C were dry compared to cells that were cycled at 20° C. The zinc plates of all the cells were found in a discharged condition. Only 10 cells had charged silver plates of which eight had been life-cycled at the 90-minute orbit period. Twenty-seven cells had carbonate deposits either around the negative or positive terminals, fill hole, or pressure relief valve.

(3) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Orbit Period	1.5-hour	
Temperature	20°	40°
Depth of Discharge	25%	25%
Pack Number	25B	47D
30 Days	1.18	3.50
60 Days	F	1.25
90 Days		1.25
120 Days		1.21
		F

Orbit Period	12-hour	
Temperature	20°	40°
Depth of Discharge	25%	25%
Pack Number	25C	37D
50 Days	4.29	4.50
100 Days	0.12	1.75
150 Days	1.25	2.50
200 Days	4.07	1.25
250 Days	2.50	F
	F	

F - Failed

2. Delco-Remy 25.0 ah, Two 5-cell Packs, 24-hour Orbit
Period:

a. Cell Description:

(1) Pack 89A: Manufacturer's Standard Model.

These cells are rectangular in shape with the cell containers and cell covers of nylon. The cells were epoxy potted into 5-cell packs by the manufacturer.

(2) Pack 75A: Same as standard model, Pack 89A, except for the addition of one percent of palladium to the positive plate material.

b. Test Parameters: Both packs were cycled at the test parameters listed below:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 40%.

(3) Orbit Period: 24 hours.

c. Test Results: Cycling was started in September 1964.

(1) Pack 89A (Standard Model) failed on cycle 80.

(2) Pack 75A (Palladium in Positive Plates) failed on cycle 32.

(3) Both packs were returned to the manufacturer for failure analysis.

3. Delco-Remy 25.0 ah, Two 5-cell Packs, 3-hour Orbit
Period:

a. Cell Description:

(1) Pack 88B: Standard model as Pack 89A, except for the addition of one percent palladium in the positive plate material and the use of 2.2xH Radiation Application Company's separators.

(2) Pack 88C: Standard model as Pack 89A, except for the addition of one percent palladium in the positive plate material, and the use of a 45 percent NaOH solution as the electrolyte.

b. Test Parameters: Both packs were cycled at the test parameters listed below:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 40%.

(3) Orbit Period: 3 hours.

c. Test Results: Cycling was started in March 1965.

(1) Pack 88B: One cell failed on cycle 100. The remaining cells still functioned on cycle 120; at which time the pack was removed from test.

(2) Pack 88C: Pack 88C was discontinued on cycle 325.

(3) Both packs were returned to the manufacturer for analysis.

4. Delco-Remy 40.0 ah, One 5-cell Pack, 24-hour Orbit Period (Pack 75B):

a. Cell Description: Manufacturer's Standard Model. These cells are rectangular in shape with the cell containers and cell covers of nylon. These cells were epoxy potted into one 5-cell pack by the manufacturer.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 40%.

(3) Orbit Period: 24 hours.

c. Test Results: Cycling was started in October 1964. One cell failed while the pack was being prepared for test; a second cell failed on cycle 34. The remaining three cells still functioned on cycle 139, at which time the pack was removed from test.

5. Yardney 12.0 ah, One 10-cell Pack, 24-hour Orbit Period (Pack 9A):

a. Cell Description: These are vented cells, rectangular in shape, with the containers and covers of plastic material. They contained a limited amount of electrolyte. The cells were individually epoxy potted to hermetically seal them.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 42%.

(3) Orbit Period: 24 hours.

c. Test Results: Cycling was started in May 1965. One cell failed on cycle 53. Three additional cells failed on cycle 58. Following removal of the failed cells, the remaining cells did not respond to cycling; thus failing the pack.

C. Silver-Cadmium Types:

1. ESB, Inc. 8.0 ah (Silver-Cadmium), One 5-cell Pack, 8-hour Orbit Period (Pack 1B):

a. Cell Description: These cells are rectangular in shape. The cell jars and cell covers are molded of a plastic material. Each cell is equipped with a pressure gage, auxiliary electrode, and cellophane bellows. The auxiliary electrode is used for gas recombination only. The plastic bellows, located in the bottom of the cell, is used to control the electrolyte level inside the cell.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 25%.

(3) Charge Voltage Limit: 1.51 ± 0.03 volts per cell, average.

(4) Orbit Period: 8 hours.

c. Test Results:

(1) Performance on Cycling: Cycling was started in September 1966. This pack failed in June 1970 after completing 3875 cycles.

(2) Failure Analysis: Analysis of the three cells showed one to develop high pressure resulting in the rupture of the plastic case. All cells showed excessive migration, loose active (mushy) material, separator deterioration, carbonate deposits around the outside negative terminal, and extreme brittleness of the positive plates.

(3) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

PRECYCLING AND CAPACITY CHECKS

Precycling		8.20 ah			
Days	ah	Days	ah	Days	ah
80	12.67	106	10.17	175	12.27
211	11.63	238	12.43	290	12.23
304	11.50	332	9.07	365	4.77
392	3.73	425	2.87	453	4.83
475	5.90	506	7.53	533	7.77
568	2.40	601	6.73	629	6.77
661	6.40	694	5.17	722	4.80
754	3.57	787	3.40	815	4.03
841	3.90	868	3.33	902	4.43
935	4.20	999	3.63	1027	3.77
1094	2.67	1125	0.67	1158	6.63
1186	2.63	1213	4.00	1239	2.27
1277	2.47 (Failed)				

2. Yardney 3.0 ah (FR-1), One 9-cell Pack, 1.5-hour Orbit Period (Pack 2C):

a. Cell Description: These are vented cells, rectangular in shape, with the cell jars and cell covers molded of a plastic material. The cells were epoxy potted, by the manufacturer, into a metal container like that used in the French satellite FR-1.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 16.67%.

c. Test Results:

(1) Performance on Cycling: Cycling was started in September 1966. This pack completed 7039 cycles before several cells blew up destroying the pack. The end-of-discharge voltage had been very consistent at 1.08 volts per cell, average. The percent of recharge was very close to 100 percent.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Precycling Capacity	2.52
88 Day Discharge	*
176 Day Discharge	0.85
264 Day Discharge	0.87
352 Day Discharge	0.67

* First 88 day capacity check not performed because of equipment malfunction.

3. Yardney 5.0 ah (C-3 Separator), Three 5-cell Packs, 24-hour Orbit Period:

a. Cell Description: These are vented cells, rectangular in shape, with the cell containers and cell covers of plastic material. The plates were insulated with C-3 separators. The cells were epoxy potted into 5-cell packs, at the Goddard Space Flight Center, in order to hermetically seal them.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
57B	0° C	20
21A	25° C	20
45A	40° C	20

c. Test Results:

(1) During cycle life, the end-of-discharge voltage of the packs, remained around 1.09 volts per cell, average; whereas the approximate percentage of recharge increased from 105 to 115 percent.

(2) Performance on Cycling: Cycling was started in September 1965. Packs 57B, 21A and 45A failed on cycles 267, 98 and 61 respectively.

(a) Pack 57B: One cell failed on cycle 138, and two on cycle 267.

(b) Pack 21A: One cell failed on cycle 90, and two on cycle 98.

(c) Pack 45A: The pack failed on cycle 61 because of severe leakage.

(d) The three packs were returned to Goddard Space Flight Center for analysis.

(3) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

PRECYCLING AND CAPACITY CHECKS

Orbit Period	24-hour		
Temperature	0°	25°	40°
Depth of Discharge	20%	20%	20%
Pack Number	57B	21A	45A
Precycling Capacity	3.67	5.80	6.00
100 Days	1.83	0.76	
200 Days	1.33		

4. Yardney 5.0 ah (Cellophane Separator), Two 5-cell Packs, 24-hour Orbit Period:

a. Cell Description: These are vented cells, rectangular in shape, with the cell jars and cell covers molded of a plastic material. The separator material is cellophane (C-19). One of the 5-cell packs (Pack 9C) had been subjected to gama radiation (2×10^7 rads). The cells were epoxy potted into 5-cell packs at the Goddard Space Flight Center.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
9C	25° C	20
33B*	25° C	20

* Control Pack

c. Test Results:

(1) Performance on Cycling: Cycling was started in October 1965. Cycling on Pack 9C was discontinued on cycle 34, and Pack 33B failed on cycle 720.

(a) Pack 9C: One cell failed on cycle 34. Since the separator material of the cells in this pack had been subjected to gama radiation, the pack was returned to Goddard Space Flight Center for analysis.

(b) Pack 33B: Two cells failed on cycle 720. While the pack was removed from cycling to disconnect the two failed cells, the three remaining cells failed. The pack was returned to Goddard Space Flight Center for analysis.

(2) Capacity Checks: The ampere-hour capacities of Pack 33B on the capacity check cycles are as follows:

100 Days	5.85	200 Days	6.13
300 Days	6.35	400 Days	5.48
500 Days	2.08	600 Days	1.88
700 Days	1.00		

5. Yardney 5.0 ah (Pellon Control Separator), One 5-cell Pack, 24-hour Orbit Period (Pack 69A):

a. Cell Description: These are vented cells, rectangular in shape, with the cell jars and cell covers molded of a plastic material. The plates of the cells are insulated with Pellon control separator material. Each cell has a pressure gage for monitoring internal cell pressure. The cells are individually epoxy potted to hermetically seal them.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 20%.

c. Test Results:

(1) Performance on Cycling: Cycling was started in October 1965. This pack failed on cycle 595 with its third cell failure, and was returned to Goddard Space Flight Center for analysis. There was very little variation in both the average end-of-discharge and end-of-charge cell voltages until the first cell failure at cycle 494. Also the internal pressure as read on the gages was very low.

(2) Capacity Checks: The ampere-hour capacities on the capacity check cycles are as follows:

100 Days	4.95
200 Days	4.17
300 Days	3.20
400 Days	4.42
500 Days	1.02
600 Days	2.08

6. Yardney 5.0 ah, Two 5-cell Packs, 8-hour Orbit Period:

a. Cell Description: These are vented cells, rectangular in shape, with cell jar and cell cover molded of a plastic material. The separator material is pellen and cellophane. The cells were individually epoxy potted at the Goddard Space Flight Center to hermetically seal them.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
114B	0° C	20
118C	25° C	20

c. Test Results:

(1) Performance on Cycling: Cycling was started in January 1967. Packs 114B and 118C failed on cycles 1496 and 1505 respectively.

(a) Pack 114B: Failure of three cells, all on cycle 1496 was due to silver migration and separator deterioration.

(b) Pack 118C: Failure of three cells, all due to silver migration and separator deterioration, occurred relatively close together--at cycles 1468, 1491 and 1505.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

PRECYCLING AND CAPACITY CHECKS

Orbit Period	8-hour	
Temperature	0°	25°
Depth of Discharge	20%	20%
Pack Number	114B	118C
Precycling Capacity	4.08	5.70
30 Days	4.00	5.37
60 Days	3.10	5.42
90 Days	2.50	5.32
120 Days	2.90	6.48
150 Days	2.98	6.25
180 Days	3.45	5.20
210 Days	2.48	6.55
240 Days	1.55	6.35
270 Days	1.75	5.83
300 Days	1.17	5.07
330 Days	1.65	6.33
360 Days	1.18	5.73
390 Days	2.40	5.68
420 Days	1.00	5.97
450 Days	0.90	3.32

7. Yardney 10 ah, One 5-cell Pack, 8-hour Orbit Period,
(Pack 45D):

a. Cell Description: These are vented cells, rectangular in shape, with cell jars and cell covers molded of a plastic material. The cells were individually epoxy potted at the Goddard Space Flight Center in order to hermetically seal them.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 30%.

c. Test Results:

(1) Performance on Cycling: Cycling was started in May 1967. This pack failed on cycle 1759. Failure of the three cells, all due to silver migration and separator deterioration, occurred at cycles 1666, 1756 and 1759.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Precycling Capacity 13.50					
30 Days	8.90	60 Days	9.60	90 Days	7.10
120 Days	8.45	150 Days	9.25	180 Days	8.50
210 Days	7.70	240 Days	10.00	270 Days	9.55
300 Days	10.60	330 Days	8.75	360 Days	5.60
390 Days	4.35	420 Days	5.60	450 Days	4.65
480 Days	3.15	510 Days	6.05	540 Days	3.15

8. Yardney 11.0 ah, Two 10-cell Packs, 24-hour Orbit Period:

a. Cell Description: These are vented cells, rectangular in shape, with the cell jars and cell covers molded of a plastic material. The cells were epoxy potted into 10-cell packs at the Goddard Space Flight Center in order to hermetically seal them.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
45B	0° C	40
21B	25° C	40

c. Test Results:

(1) Performance on Cycling: Cycling was started in November 1966. Packs 45B and 21B were considered as having failed on cycles 121 and 69 respectively since three of the 10 cells in each pack had by then developed internal shorts. At the request of Goddard Space Flight Center, the packs were returned for analysis.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Temperature	0°	25°
Pack Number	45B	21B
Precycling Capacity	9.26	11.46
100 Days	5.91	

9. Yardney 11 ah, Two 5-cell Packs, 8-hour Orbit Period:

a. Cell Description: These are vented cells, rectangular in shape, with the cell jars and cell covers molded of a plastic material. The cells were epoxy potted into 5-cell packs at the Goddard Space Flight Center in order to hermetically seal them. The cells of pack 21C have pellen (2505K) separators, and those of pack 45C have woven nylon separators.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
21C	25° C	27
45C	25° C	27

c. Test Results:

(1) Performance on Cycling: Cycling was started in March 1967. Packs 21C and 45C failed on cycles 37 and 70 respectively. Several cells in each pack developed high internal pressure which resulted in breakage of those cell jars and the epoxy potting.

(2) Capacity Checks: The precycling capacities for Packs 21C and 45C were 8.40 and 9.45 ampere-hours respectively.

10. Yardney 12.0 ah, Two 10-cell Packs, 24-hour Orbit Period:

a. Cell Description: These are double sealed rectangular cells. That is, each sealed polystyrene cell is encased in a hermetically sealed stainless steel container.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
57A	0° C	50
33A	40° C	50

c. Test Results:

(1) Performance on Cycling: Cycling was started in February 1964. These packs failed on cycles 168 and 210.

(a) Pack 57A: Low end-of-discharge cell voltages began on cycle 31 and continued erratically until the pack failed on cycle 168. Although cell voltages had frequently fallen below the 0.5 volt failure point, they had not been classed as failures earlier because of their erratic behavior. After completion of 162 cycles, electrolyte had leaked out and formed a pool over the tops of the cells, thus shorting them out. The 10 cells were cleaned, after which seven were returned to cycling. All seven cells leaked again after six additional cycling.

(b) Pack 33A: The plateau voltage of the non-failing cells on discharge was fairly steady at about 1.06 volts per cell for the first 110 cycles with little or no drop off at the end of discharge. Thereafter, the plateau voltage began to drop steadily and the end-of-discharge voltage became quite erratic. This pack failed on cycle 210. All of the failed cells had dried out because of electrolyte leakage.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Pack Number	57A	33A
Precycling Capacity	13.8	13.5
140 Days Disch #2	8.6	12.0

11. Yardney 12.0 ah, Three 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Discription: These are vented cells, rectangular in shape, with cell jars and cell covers molded of a plastic material. The cells were individually epoxy potted to hermetically seal them.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
85B	-20° C	25
97B	0° C	25
82B	25° C	25

c. Test Results:

(1) Performance on Cycling: Cycling was stated in January 1966. Pack 85B failed on cycle 2375, pack 97B on cycle 4481, and pack 82B on cycle 4559. Due to poor charge acceptance at -20° C the end-of-discharge voltage dropped below 0.8 volt per cell. On cycle 214, the test temperature of pack 85B was increased to 40° C with a voltage limit of 1.55 volts per cell, average. The pack then cycled satisfactorily with the end-of-discharge voltage being approximately 1.06 volts per cell. The end-of-discharge voltage of pack 97B and 82B was also approximately 1.06 volts per cell.

(2) Failure Analysis: Analysis of the 10 failed cells showed the cause of failure to be silver penetration of the separator resulting in an internally shorted cell.

(3) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

PRECYCLING AND CAPACITY CHECKS

Orbit Period	1.5-hour		
Temperature	-20°*	0°	25°
Depth of Discharge	25%	25%	25%
Pack Number	85B	97B	82B
Precycling Capacity	5.40	9.00	13.30
88 Days	13.80	**	4.50
176 Days	8.70	3.50	2.90
264 Days	13.70	5.70	3.30
352 Days	9.60	3.70	

* Cycle 214 changed to 40° C

** Capacity check not performed due to low voltage on several cells.

III. CELLS USING SOPHISTICATED CHARGE CONTROL METHODS AND DEVICES:

A. Auxiliary Electrode:

1. Gulton 6.0 ah (Nickel-Cadmium), Six 5-cell Packs,
1.5-hour Orbit Period:

a. Cell Description: These cells are rectangular in shape. The cell container and cell cover are made of stainless steel. Both terminals are insulated from the cell cover by ceramic seals and protrude through the cover as solder type terminals. A stainless steel tab is welded to the cell cover for the auxiliary electrode terminal. The auxiliary electrode is welded to the inner surface of the cell container. A resistor is mounted externally between the auxiliary electrode and the negative terminal. Recharge percentage may be adjusted by adjusting the voltage level of the auxiliary electrode detector circuit and/or varying the auxiliary electrode resistance while maintaining a fixed voltage to the detector circuit. (See Section II, Paragraph II.B., for description of control unit.)

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Auxiliary Electrode Resistors (Ohms)				
				1	2	3	4	5
59A	0° C	25	150	10	10	10	10	10
71A	0° C	40	150	10	10	10	10	10
23A	25° C	25	300	12	12	20	29	24
11A	25° C	40	300	24	24	10	8	24
35A	40° C	15	70	47	47	47	47	47
47A	40° C	25	300	11	11	12	11	11

c. Test Results:

(1) Performance on Cycling: Cycling was started in February 1965. Pack failures occurred on cycle 14,863 for pack 59A, on cycle 5753 for pack 71A, on cycle 15,713 for pack 23A, on cycle 7743 for pack 11A, on cycle 12,511 for pack 35A and on cycle 5502 for pack 47A.

(2) Failure Analysis: Analysis of 19 failed cells showed that the major cause of failure was due to separator deterioration, migration of the negative plate material, and electrolyte leakage which ranged from 1.3 to 8.7 grams. Other conditions found in the cell were high internal pressure, blisters on the positive plates, extraneous positive material, ceramic short, and weak tab-to-plate welds.

(3) Capacity Checks: The ampere-hour capacities on the capacity check cycles are as follows:

Orbit Period		1.5-hour					
Temperature		0°	0°	25°	25°	40°	40°
Depth of Discharge		25%	40%	25%	40%	15%	25%
Pack Number		59A	71A	23A	11A	35A	47A
100 Cycles		7.15	7.25	3.40	4.12	2.95	3.65
88 Days	Disch #2	7.00	7.50	5.95	5.50	2.25	2.10
176 Days	Disch #2	3.50	7.00	3.85	3.15	1.60	1.70
264 Days	Disch #2	6.75	5.65	5.20	6.20	1.85	2.25
352 Days	Disch #2	6.50		4.00	4.35	2.00	
440 Days	Disch #2	6.85		4.45	3.95	2.75	
528 Days	Disch #2	7.00		4.20	2.75	2.80	
616 Days	Disch #2	6.35		3.85		2.20	
704 Days	Disch #2	6.10		4.40		1.50	
792 Days	Disch #2	5.50		2.45		2.55	
880 Days	Disch #2	2.50		1.50			
968 Days	Disch #2			1.00			
1056 Days	Disch #2			0.78			

2. Gulton 10.0 ah (Nickel-Cadmium), Three 5-cell Packs,
1.5-hour Orbit Period:

a. Cell Description: These cells are rectangular in shape. The cell container and cover are made of plastic. Each cell is fitted with a pressure gage. Both terminals protrude through the cell cover as solder type terminals. Each cell contains an adhydrode as a signal electrode and an American Cyanamid type AB-6X electrode for a scavenger electrode. The adhydrode is located in the center of the plate stack and welded to the base of the pressure gage fitting. The scavenger electrode is located on the side of the plate stack and connected internally to the negative material. Each 5-cell pack was epoxy potted into a metal container by Gulton Industries in order to hermetically seal the cells. The cells were developed under Contract NAS 5-10241. (See Section II, Paragraph II.B., for description of control unit.)

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Auxiliary Electrode Resistors (Ohms)
20B	0° C	25	250	47
8B	25° C	25	250	47
6B	40° C	25	250	47

c. Test Results:

(1) Performance on Cycling: Cycling was started in November 1967. Pack 20B failed during the precycling capacity, pack 8B on cycle 2414, and pack 6B on cycle 602. All three packs were returned to Goddard Space Flight Center for analysis.

3. Gulton 20 ah (OAO), (Nickel-Cadmium), Three 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Description: These cells are rectangular in shape. The cell container and cell cover are made of stainless steel. Both terminals are insulated from the cover by ceramic seals and protrude through the cover as solder type terminals. Each ceramic seal is set in an expansion joint to remove the stress placed on the seal by the movement of the plates or cell cover. A stainless steel tab is welded to the cover for the auxiliary electrode terminal. The auxiliary electrode is welded to the inner surface of the cell container. A resistor is mounted externally between the auxiliary electrode and negative terminal. This type cell was used in the OAO satellites. (See Section II, Paragraph II.B., for description of control unit.)

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Auxiliary Electrode Resistors (Ohms)
58B	0° C	15	40	6.8
12C	25° C	15	200	6.8
36B	40° C	15	200	6.8

(1) The following changes in the charge current were made in order to obtain more data on the auxiliary electrode control.

Pack Number	Cycle	Current	Cycle	Current	Cycle	Current
58B	234	9.5 Amps	794	19.5 Amps	1518	10 Amps
12C	85	9.6 Amps	262	19.5 Amps	629	10 Amps
36B	51	9.6 Amps	226	19.6 Amps	698	10 Amps

c. Test Results:

(1) Performance on Cycling: Cycling was started in March 1967. Pack 36B completed cycle 2740 on 5 September 1967 without any cell failures, at which time cycling was discontinued. Packs 58B and 12C completed 4026 and 4934 cycles respectively on

25 January 1968 without any cell failures, at which time cycling was discontinued on both packs. The three packs were returned to Goddard Space Flight Center for evaluation.

(2) Capacity Checks: The ampere-hour capacities on the capacity check cycles are as follows:

Orbit Period	1.5-hour		
	0°	25°	40°
Temperature	0°	25°	40°
Depth of Discharge	15%	15%	15%
Pack Number	58B	12C	36B
30 Days	*	14.7	*
88 Days	20.0	20.6	10.7
176 Days	22.0	20.5	
264 Days		22.4	

* Capacity checks were not run due to the changes in charge rate.

4. Gulton 20 ah (OAO), (Nickel-Cadmium), Three 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Description:

(1) Each pack consists of three conventional cells, two cells with an auxiliary electrode, and a coulometer. Both types of cells, used in OAO satellites, are rectangular in shape. The cell container and cell cover are made of stainless steel. Both terminals are insulated from the cover by ceramic seals and protrude through the cover as solder type terminals. Each ceramic seal is set in an expansion joint to remove the stress placed on the seal by the movement of the plates or cell covers.

(a) The cells with auxiliary electrode have a stainless steel tab welded to the cover for the auxiliary electrode terminal. The auxiliary electrode is welded to the inner surface of the cell container. A resistor is mounted externally between the auxiliary electrode and the negative terminal.

(b) The coulometers are of the cadmium-cadmium type and are rated at 20 ampere-hours. They are of the same case construction as the cells described above.

(2) These packs are cycled with auxiliary electrode control. A coulometer on each pack is monitored to note how well the two charge control devices in the pack function.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Auxiliary Electrode Resistors (Ohms)
58C	*	40	250	47
36C	*	25	250	47
12D	*	15	250	47

* These cells are in an ambient temperature which varies sinusoidally from 0° to 40° C within a cycle period of 48 hours.

c. Test Results:

(1) Performance on Cycling: Cycling was started in February 1968. Packs 58C and 36C failed on cycles 131 and 966, respectively; but Pack 12D was discontinued on cycle 7262. All three packs were returned to Goddard Space Flight Center for failure analysis.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Pack Number	58C	36C	12D
Temperature	*	*	*
Precycling Capacity	22.7	22.9	25.3
88 Days			13.7
176 Days			6.3
264 Days			5.8
352 Days			5.7
440 Days			6.9

* The temperature cycle is stopped at 25° C for each capacity check cycle.

5. Gulton 20 ah (OAO), (Nickel-Cadmium, Precharge), One 6-cell Pack, 1.5-hour Orbit Period (Pack 48C):

a. Cell Description:

(1) These cells are rectangular in shape. The cell container and cell cover are made of stainless steel. Both terminals are insulated from the cover by ceramic seals and protrude through the cover as solder type terminals. Each ceramic seal is set in an expansion joint to remove the stress placed on the seal by the movement of the plates or cell cover. A stainless steel tab is welded to the cover for the auxiliary electrode terminal. The auxiliary electrode is welded to the inner surface of the cell container. A resistor is mounted externally between the auxiliary electrode and negative terminal. This type cell was used in OAO satellites.

(2) Each cell was fitted with either a pressure gage or pressure transducer. Before cycle was started, the amount of precharged cadmium material was adjusted so that cells 2 and 3 had 0.0 ah, cells 4 and 5 had 4.0 ah and cells 1 and 6 had 8.0 ah. This was accomplished by a procedure specified by Goddard Space Flight Center.

b. Test Parameters:

(1) Test Temperature: These cells are in an ambient temperature which varies sinusoidally from 0° to 40° C within a period of 48 hours.

(2) Depth of Discharge: 25%.

(3) Trip Voltage Level: 300 Millivolts.

(4) Auxiliary Electrode Resistors: 51 Ohms.

c. Test Results:

(1) Performance on Cycling: Cycling started in May 1969. Pack 48C was terminated after completing 1984 cycles. On cycles 586 and 627 cell number 1 (8.0 ah of precharged cadmium) developed high internal pressure. In both cases the gas pressure was allowed to decrease while the cells were on open circuit. On cycle 627, four ampere-hours of precharged cadmium were removed and the cell returned to cycling. No further difficulties with high pressure were encountered with this cell. Cell number 5 failed after 1733 cycles, and cell 2 failed after 1984 cycles.

(2) Failure Analysis: Failure analysis was performed on three cells. The analysis showed migration of negative material, separator deterioration, high pressure, carbonate deposits at the positive terminal, and blistering of the positive plates. In addition, samples of positive and negative plates were removed from these three cells plus a fourth, nonfailed, cell. Individual plate capacities on these four samples showed the positive plates to equal or exceed the capacity of the adjacent negative plates in 75 percent of the samples. The cadmium to nickel ratio in such samples ranged from 0.74 to 1.00. Such negative limiting leads to high pressure during charge due to hydrogen evolution which cannot be recombined.

(3) Capacity Checks: The ampere-hour capacity, after 461 cycles, was 8.67 ampere-hours.

6. GE 6.0 ah (Nickel-Cadmium), Two 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Description: These cells are rectangular in shape. The cell container and the cell cover are made of stainless steel. Both terminals are insulated from the cell cover by ceramic seals and protrude through the cover as solder type terminals. A stainless steel tab, welded to the cover, provides the terminal for the auxiliary electrode. The auxiliary electrode (Type C) is welded to the inner surface of the cell container. A resistor is mounted externally between the auxiliary electrode and the negative terminal. The plates of the cells of Pack 9G are separated with a material called "Chemsorb" whereas those of the cells of Pack 27C are separated with "Pellon" used as the standard for this test. (See Section II, Paragraph II.B., for description of control unit.)

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Auxiliary Electrode Resistors	Separator
9G	40° C	25	500	510 Ohms	Chemsorb
27C	40° C	25	500	510 Ohms	Pellon

c. Test Results:

(1) Performance on Cycling: Cycling was started in November 1968.

(a) Pack 9G: This pack failed on cycle 143 at which time three cells shorted internally. In one of these cells the auxiliary electrode shorted to the positive terminal.

1. One of the failed cells was returned to Goddard Space Flight Center for detailed analysis of the separator material "Chemsorb".

2. Failure analysis of the other two cells showed that distortion of the cases and covers, caused by high internal pressure, moved the corner of the plates opposite the tabs in one cell into the bus of the plates of opposite polarity; and in the other cell the positive plates came into contact with the cell case, thereby shorting the auxiliary electrode to the positive terminal. Both cells also showed separator deterioration.

(b) Pack 27C: The two cells which failed on cycle 496 showed signs of high internal pressure and migration of negative plate material. Cycling was discontinued on cycle 559.

(2) Capacity Checks:

(a) Precycling consisted of a charge at the cycling rate until the auxiliary electrode voltage of any of the five cells reached 500 millivolts followed by a discharge at the cycling rate to 1.00 volt per cell, average. Each pack delivered 3.15 ampere-hours on precycling.

(b) Capacity check cycles were to be identical to the precycling check cycle but none were made because of failure or discontinuance of cycling before first scheduled capacity check.

7. GE 6.0 ah (Nickel-Cadmium), Three 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Description: These cells are rectangular. The cell container and cover are made of stainless steel. Both terminals are insulated from the cell cover by ceramic seals and protrude through the cover as solder type terminals. There are two auxiliary electrodes in each cell; the signal and the gas recombination electrodes. The recombination electrode is welded to the inside of the container, and its terminal is a stainless steel tab welded to the outside. The signal electrode, which is used for charge control, is welded to a wire that protrudes through a hole in the cell cover. This hole is potted to seal the cell. Different values of resistance are used to connect the signal and gas recombination electrodes to the negative terminal. The cells were developed under contract NAS 5-10261.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Signal Electrode Resistors (Ohms)*
53B	0° C	15	185	300
28C	25° C	15	70	10
47C	40° C	15	58	10

* Gas Recombination Electrode Resistors: 1 Ohm

c. Test Results:

(1) Performance on Cycling: Cycling was started in July 1968. Packs 53B and 28C failed on cycles 9230 and 9987, respectively. Pack 47C was discontinued on cycle 5842. One cell was removed from each pack and returned to the manufacturer for analysis. These cell removals occurred on cycle 4039 for 53B, on cycle 4095 for 28C and on cycle 4063 for 47C. Two additional cells (one failed and one nonfailed) from 47C were returned to the manufacturer for analysis as outlined in the NASA contract.

(2) Failure Analysis: Analysis of the eight failed cells from the three packs showed the major cause of failure to be separator deterioration, migration of negative plate material and high internal pressure. Additional problems included electrolyte

leakage, corrosive internal deposits, blistering of positive plates, ragged edges of positive plates, and dry separator material. One cell from 47C which did not fail was analyzed for comparison with the failed cell. The conditions found in this cell were similar to the failed cell except that the separator deterioration and migration were not as severe.

(2) Capacity Checks: The ampere-hour capacities on the capacity check cycles are as follows:

Pack Number	53B	28C	47C
Temperature	0°C	25°C	40°C
88 Days	6.96	7.74	5.22
176 Days	6.80	6.50	1.50
264 Days	6.75	6.30	1.75
352 Days	6.05	5.50	
440 Days	1.71	3.00	
528 Days	1.59	0.90	
616 Days		0.96	

8. GE 12.0 ah (Nickel-Cadmium), Four 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Description: These cells are rectangular in shape. The cell container and the cell cover are made of stainless steel. Both terminals are insulated from the cell cover by ceramic seals and protrude through the cover as 1/4-20 threaded posts. A stainless steel tab is welded to the cell cover for the auxiliary electrode terminal. The auxiliary electrode is a fuel cell type electrode and is welded to the inner surface of the cell container. A resistor is mounted externally between the auxiliary electrode and the negative terminal. (See Section II, Paragraph II.B., for description of control unit.)

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Auxiliary Electrode Resistors (Ohms)
60A	0° C	25	400	3
12A	25° C	25	400	1
24A	25° C	40	400	1
48A	40° C	25	400	0.5

(1) Pack 48A was changed to 0° C after 528 cycles with the following parameters: Depth of Discharge, 40 percent; Resistors, 3 ohms on each cell.

c. Test Results:

(1) Performance on Cycling: Cycling was started in October 1965. Cycling of Packs 60A, 12A, 24A and 48A was discontinued on cycles 5650, 1698, 665 and 5110 cycles respectively.

(a) Pack 12A, at 25° C: The end-of-discharge voltage fell below 1.0 volt per cell, average, on cycle 486. The pack was reconditioned and returned to cycling. At cycle 872 the voltage again dropped below 1.0 volt per cell, average. The pack was again reconditioned. At cycle 1051 the pack again lost capacity and was reconditioned for the third time. Cycling of this pack was discontinued at cycle 1698 because of loss of capacity.

(b) Pack 24A, at 25° C: The end-of-discharge voltage fell below 1.0 volt per cell, average, on cycle 410. The pack was reconditioned and returned to cycling. At cycle 537, the voltage again dropped below 1.0 volt per cell, average. The control unit was then set to charge at 2.5 amperes for the remaining portion of the 60-minute charge period after the trip point had been reached. This overcharge did not improve the capacity of the pack so the test was discontinued on cycle 665.

(c) Pack 48A completed 528 cycles at 40° C at which time the test temperature was reduced to 0° C and the depth of discharge was increased from 25 to 40 percent. Cycling was discontinued after cycle 5110 because the cells would not operate satisfactorily over the entire temperature range of 0° to 40° C. Additional data at 0° C would be of little value in evaluating the cells for space application.

(d) Pack 60A, at 0° C, completed 5650 cycles before it was discontinued for the same reasons given for Pack 48A.

(e) Failure Analysis: Consultation with Goddard Space Flight Center and the manufacturer resulted in the decision to forego failure analyses of these cells since it was believed their poor performance was the result of questionable processing.

(2) Capacity Checks: The ampere-hour capacities on the capacity check cycles are as follows:

Orbit Period	1.5-hour			
Temperature	0°	0°	25°	25°
Depth of Discharge	25%	40%	25%	40%
Pack Number	60A	48A	12A	24A
100 Cycles	15.00	5.30*	8.90	9.10
88 Days Disch #2	15.10	15.20	**	**
176 Days Disch #2	14.60	15.10		
264 Days Disch #2		11.50		

* Pack 48A capacity test discharges at this point were at ambient temperature of 40° C.

** Capacity check at 88 days (1440 cycles) was not run because of earlier losses of capacity.

9. GE 12.0 ah (Nickel-Cadmium), Six 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Description: These cells are rectangular in shape. The cell container and cell cover are made of stainless steel. Both terminals are insulated from the cell cover by ceramic seals and protrude through the cover as 1/4-20 threaded posts. A stainless steel tab is welded to the cell cover for the auxiliary electrode terminal. One auxiliary electrode was welded internally to the negative terminal and the other one was welded to the cell container. A resistor is mounted externally between the auxiliary electrode and the negative terminal. (See Section II, Paragraph II.B., for description of control unit.)

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Trip Voltage Level (Millivolts)	Auxiliary Electrode Resistors (Ohms)
58A	0° C	25	500	6.8
72A	0° C	40	500	6.8
12B	25° C	25	500	6.8
24B	25° C	40	500	6.8
36A	40° C	25	500	6.8
34A	40° C	40	500	6.3

c. Test Results:

(1) Performance on Cycling: Cycling was started in January 1967. Packs 58A, 72A, 12B, 24B, 36A and 34A were discontinued on cycles 136, 304, 404, 38, 75 and 65 respectively. These packs showed excessive capacity losses in relatively few cycles as reflected in the capacity check data.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

(a) Pack 58A, at 0° C: Precycling capacities were 17.4 ampere-hours on the first discharge and 16.6 ampere-hours on the second discharge. After 133 cycles the pack was again given a capacity check and delivered 16.0 ampere-hours on the first discharge and 15.7 ampere-hours on the second discharge.

(b) Pack 72A, at 0° C: Precycling capacities were 17.4 ampere-hours on the first discharge and 16.4 ampere-hours on the second discharge. After 177 cycles the pack was again given a capacity check and delivered 15.6 ampere-hours on the first discharge and 15.6 ampere-hours on the second discharge.

(c) Pack 12B, at 25° C: Precycling capacities were 15.9 ampere-hours on the first discharge and 10.5 ampere-hours on the second discharge. After 401 cycles the pack was again given a capacity check and delivered 6.8 ampere-hours on the first discharge and 7.2 ampere-hours on the second discharge.

(d) Pack 24B, at 25° C: Precycling capacities were 17.2 ampere-hours on the first discharge and 15.1 ampere-hours on the second discharge. After 38 cycles the pack was again given a capacity check and delivered 4.6 ampere-hours on the first discharge and 6.8 ampere-hours on the second discharge.

(e) Pack 36A, at 40° C: Precycling capacities were 12.1 ampere-hours on the first discharge and 6.3 ampere-hours on the second discharge. After 56 cycles the pack was again given a capacity check and delivered 3.5 ampere-hours on the first discharge and 2.6 ampere-hours on the second discharge.

(f) Pack 34A, at 40° C: Precycling capacities were 13.0 ampere-hours on the first discharge and 6.7 ampere-hours on the second discharge. After 43 cycles the pack was again given a capacity check and delivered 4.1 ampere-hours on the first discharge and 3.2 ampere-hours on the second discharge.

(g) Failure Analyses: Consultation with Goddard Space Flight Center and the manufacturer resulted in the decision to forego failure analyses of these cells since it was believed their poor performance was the result of questionable processing.

10. Sonotone 5.0 ah (Nickel-Cadmium), One 5-cell Pack, 1.5-hour Orbit Period (Pack 14D):

a. Cell Description: These cells are rectangular in shape. The cell jars and cell covers are made of a plastic material. Each cell is equipped with an auxiliary electrode which is used for gas recombination. The cells were constructed at the Goddard Space Flight Center from parts supplied by Sonotone. The cells were then individually epoxy potted in order to hermetically seal them.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 25%.

(3) Auxiliary Electrode Resistors: All 1 ohm.

(a) Following the low end-of-discharge voltage condition of one cell between cycles 1110 and 1136, the auxiliary electrode resistors on each of the five cells were changed to 50 ohms, at the request of Goddard Space Flight Center, to note any changes in the cell voltage characteristics.

c. Test Results:

(1) Performance on Cycling: Cycling was started in November 1967. This pack failed on cycle 1179 due to failure of three cells at that time as a result of severe migration of negative plate material. The positive plates of one cell were blistered; and imbedded in one was a piece of extraneous plastic material.

(2) Capacity Checks: The ampere-hour capacity on precycling was 3.99 ampere-hours.

11. Yardney 12.0 ah (Silver-Cadmium), Two 5-cell Packs,
24-hour Orbit Period:

a. Cell Description: The cells are rectangular in shape. The cell jars and covers are molded of a plastic material. A fuel cell type auxiliary electrode for gas recombination was installed in each cell by Goddard Space Flight Center before being individually epoxy potted with a wrap of fiberglass material to hermetically seal and strengthen them.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge	Auxiliary Electrode Resistor (Ohms)
21D	0° C	43	1
9F	40° C	43	1

c. Test Results:

(1) Performance on Cycling: Cycling was started in June 1967.

(a) Pack 21D: This pack failed on cycle 60 due to low capacity of several cells.

(b) Pack 9F: The first of four cell failures occurred on cycle 258, the second on cycle 288, and the remaining two on cycle 310.

(c) The two packs were returned to Goddard Space Flight Center for analysis.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Pack Number	21D	9F
Precycling Capacity	4.33	5.53
100 Days		8.33
200 Days		7.60
273 Days		5.33

B. Stabistor: The stabistor is a semiconductor device that is used to shunt current around a fully charged cell. The stabistor will pass current when the voltage across it has reached the breakdown value. The breakdown voltage depends upon the temperature of the stabistor. At higher temperatures the breakdown voltage is lower than at cold temperatures. Across the terminals of each cell is mounted a 5-ampere stabistor to limit the charge current, and an antireversal diode to prevent cell reversal on discharge.

1. Sonotone 5.0 ah (Nickel-Cadmium), Eight 5-cell Packs, 1.5-hour Orbit Period:

a. Cell Description: These are cylindrical cells made of stainless steel. Two stainless steel tabs are welded to the cover for the negative connections. The positive terminal is an extension of the positive plate tab and is insulated from the "negative" cover by a ceramic seal. Two ring indentations, about 1/32 inch deep, located approximately 7/8 inch from either end of the cell can, were crimped after cell assembly to hold the element snugly in the cylindrical can. This type cell was used in the TIROS (Television Infrared Observation Satellite) satellite.

b. Test Parameters:

(1) Initial Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
75C	-20° C	25
89B	-20° C	40
92A	0° C	25
122B	0° C	40
73B	25° C	25
87B	25° C	40
99B	40° C	25
112B	40° C	40

(1) Pack 112B did not cycle satisfactorily at 40 percent depth of discharge so at cycle 48 the depth of discharge was reduced to 15 percent, with all other parameters unchanged.

(2) It was necessary to recharge all packs at the c/1 rate (5 amperes) since the 5-ampere stabistor (with heat sink) in parallel with each cell was designed to maintain the proper stabistor temperature for the correct breakdown voltage when shunting the 5 amperes.

c. Test Results:

(1) Performance on Cycling: Cycling was started in August 1965. Pack 75C failed on cycle 2145, pack 89B on cycle 1530, pack 92A on cycle 3774, pack 122B on cycle 5190, pack 73B on cycle 4742, pack 87B on cycle 2392, pack 99B on cycle 4399, and pack 112B on cycle 3294. The breakdown voltage of the stabistors was too high for proper voltage limiting, thereby resulting in excessive gassing and high internal pressure. This in turn caused leakage as evidenced by carbonate deposits around the ceramic seal of the terminal of 26 of the 29 failed cells, of which the containers of 23 cells were bulged. Other conditions found during the failure analysis were excess scoring, migration of the negative plate material, weak tab-to-plate welds, ceramic shorts, separator deterioration, blistering on the positive plates, loosened active material, and extraneous active material.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

PRECYCLING AND CAPACITY CHECKS

Orbit Period		1.5-hour							
Temperature		-20°	-20°	0°	0°	25°	25°	40°	40°
Depth of Discharge		25%	40%	25%	40%	25%	40%	25%	40%
Pack Number		75C	89B	92A	122B	73B	87B	99B	112B
Precycling Capacity		4.92	4.96	3.38	4.13	5.33	5.50	4.21	3.71
88 Days	Disch #2	1.21	2.58	2.75	2.33	2.33	3.66	1.88	1.04
176 Days	Disch #2			1.71	1.50	1.29		1.50	
264 Days	Disch #2			0.75	0.79			1.17	
352 Days	Disch #2			*	*				
440 Days	Disch #2			1.38					

* Cell failure occurred during capacity check.

C. Coulometer: (See Section II, Paragraph II.C., for description of cadmium-cadmium coulometer.)

1. Gulton 3.6 ah (Nickel-Cadmium with Neoprene Seal), One 10-cell Pack, 1.5-hour Orbit Period (Pack 39B):

a. Cell Description: These are cylindrical cells with a folded neoprene seal as described in Section II, Paragraph I.A.5.a.

b. The coulometer used was built by GE with a capacity of 6.0 ampere-hours.

c. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 40%.

d. Test Results:

(1) Performance on Cycling: Cycling was started in November 1965. This pack completed 5399 cycles before failure by self destruction. During recharge following the first capacity check after cycle 5399, one or more cells of the seven cells cycling shorted and caught fire. All seven cells were completely destroyed thereby preventing failure analysis. The coulometer failed after 1868 cycles due to loss of capacity. The end-of-discharge voltage improved after a new coulometer was placed in the pack.

(a) The first three cell failures occurred at cycles 2182, 4949 and 4976. The three cells showed migration of negative plate material and separator deterioration. The positive plates of the three cells had loosened active material and were blistered. The welded seam of each of the three cells showed leakage as evidenced by deposits.

(b) The cadmium-cadmium coulometer failed due to internal shorting caused by cadmium migration through the single layer of nonwoven nylon separator. Because of this cadmium migration, the coulometer must have at least twice the amount of plate separation as regular nickel-cadmium cells also requiring the cells to be operated in the flooded state to keep the internal resistance down.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Precycling	3.06
88 Days	2.07
176 Days	2.01
264 Days	2.55
352 Days	1.71

2. Gulton 4.0 ah (Nickel-Cadmium), Seven 5-cell Packs,
1.5-hour Orbit Period:

a. Cell Description: These are rectangular sealed cells of commercial grade. The containers and covers are of a plastic material. They were epoxy potted into 5-cell packs with a coulometer at the Goddard Space Flight Center in order to hermetically seal the cells and the coulometer before test.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
40C	-20° C	25
52B	0° C	25
26C	25° C	15
14C	25° C	25
37C	25° C	40
38D	25° C	60
39C	40° C	25

c. Test Results:

(1) Performance on Cycling: Pack 40C failed during precycling capacity checks at -20° C. Cycling of the remaining six packs started in March 1967. The first cell failure occurred on cycle 5685 for pack 52B, on cycle 11,455 for pack 26C, on cycle 2428 for 14C, on cycle 790 for 37C, on cycle 1927 for 38D and on cycle 1508 for 39C. At the request of Goddard Space Flight Center, cycling of any pack was stopped upon failure of any cell within the pack since there was no way of physically or electrically removing the failed cells from the pack. No failure analyses were performed because failure of these commercial cells was due to high internal pressure because too much electrolyte in the cells prevented gas recombination to occur which caused the cells to rupture.

(2) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

PRECYCLING AND CAPACITY CHECKS

Orbit Period	1.5-hour						
Temperature	-20°	0°	25°	25°	25°	25°	40°
Depth of Discharge	25%	25%	15%	25%	40%	60%	25%
Pack Number	40C	52B	26C	14C	37C	38C	39C
Precycling Capacity	*	4.43	4.67	4.23	5.03	4.57	3.30
88 Days Disch #2		4.10	3.10	3.50		1.87	1.13
176 Days Disch #2		3.37	2.43				
264 Days Disch #2		2.33	3.37				
352 Days Disch #2		3.80	3.37				
440 Days Disch #2			3.40				
528 Days Disch #2			2.33				
616 Days Disch #2			1.33				
704 Days Disch #2			0.93				

* Pack failure occurred during precycling capacity check.

3. Sonotone 5.0 ah, One 5-cell Pack, 1.5-hour Orbit Period:

a. Cell Description:

(1) The cell container and the cell cover are made of stainless steel. Two stainless steel tabs, welded to the cover, serve as contacts for the negative terminal. The positive terminal is a solder type extension of the positive plate tab through the center of the cover. The positive terminal is insulated from the "negative" cover by a glass to metal seal. Two ring indentations, about 1/32 inch deep, located approximately 7/8 inch from either end of the cell can, were crimped after cell assembly to hold the element snugly in the cylindrical can.

b. The coulometer used was built by the Goddard Space Flight Center.

c. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: Started at 80 percent but was lowered by steps of 10 percent until the pack operated satisfactorily at 30 percent depth of discharge.

d. Test Results: Cycling was started in August 1964. Upon completion of a total of 13,540 cycles at the various depths of discharge listed below, cycling was stopped because the coulometer developed a short and could not control the cycling operation any longer.

(1) At 80 percent, the pack completed 59 cycles. The end-of-discharge voltage dropped below 1.0 volt.

(2) At 70 percent, the pack completed 61 cycles. The end-of-discharge voltage again dropped below 1.0 volt.

(3) At 60 percent, the pack completed 55 cycles before the end-of-discharge voltage fell below 1.0 volt.

(4) At 50 percent, the pack completed 90 cycles before the end-of-discharge voltage fell below 1.0 volt.

(5) At 40 percent, the pack completed 250 cycles before the end-of-discharge voltage fell below 1.0 volt.

(6) At 30 percent, the pack completed 13,025 cycles before the coulometer developed a short. The end-of-discharge voltage was about 1.07 volts per cell, average, with an end-of-charge voltage of 1.42 volts per cell, average, over the entire cycle life. The percent of recharge, as controlled by the coulometer, ranged from 104 to 111 percent with an average value of 106 percent.

D. Sherfey Upside-Down Cycling: This type of cycling starts with the cells in a completely discharged condition. Each cycle consists of a charge of 60 percent followed by a discharge of 40 percent of the cell's rated capacity. Upon completion of each fifth cycle, the cells are discharged through resistors for 90 additional minutes to return the cells to the completely discharged condition (bleed portion of cycle) for the start of the next sequence of five cycles. In this manner, the cells operate below the 100 percent charged state much of the time thereby preventing overcharging and buildup of excessive gas pressure.

1. Test Equipment: The charge and discharge currents for the pack are supplied by a power supply. The rates and cycling regimen are controlled by the Sherfey cycling unit which contains the resistors used to completely discharge the cells after each fifth cycle. The cycle timing is done by using a synchronous motor timer.

2. Gulton 3.6 ah (Nickel-Cadmium with Neoprene Seal), One 10-cell Pack, 1.5-hour Orbit Period:

a. Cell Description: These are cylindrical cells with a folded neoprene seal as described in Section II, Paragraph II.A.4.a.

b. Test Parameters:

(1) Test Temperature: 25° C.

(2) Depth of Discharge: 40%.

c. Test Results: Cycling was started in September 1965. This pack failed on cycle 5505. Each of the cell failures was caused by the loss of electrolyte around the weld between the cell container and cell cover. Because of this leakage, which began at the start of cycling, the cells began to dry out and the charge voltage began to increase. The end-of-charge voltage gradually increased from 1.44 volts initially to 1.60 volts per cell, average, at the end of cycle life reflecting the effects of the drying out of the cells. On each successive discharge following the bleeding of every fifth cycle, the end-of-discharge voltage increased about 0.02 volt per cell.

E. Two-Step Charge Regulator: When silver-cadmium and silver-zinc cells are put on a long charge period with only a voltage limit, the cells begin to unbalance when the pack goes into overcharge. A new method of charging cells of these types was developed at Goddard Space Flight Center. Charging of the battery is by constant current to the upper voltage limit, then is automatically crossed over to constant potential. When the current decreases to a predetermined level, the constant potential charge is reset to the lower voltage limit which is equal to the open circuit voltage of the battery. The unit will not return to the upper voltage limit until the charge current goes above the predetermined value. This method prevents the cells from becoming unbalanced during long charge periods.

1. Test Equipment: The charge and discharge currents are supplied by a unit described in Section VI, Paragraph I.B.1. The two-step regulator, designed by the Goddard Space Flight Center, is used to control the rate of charge and the voltage limits.

2. Delco-Remy 25.0 ah (Silver-Zinc), Two 10-cell Packs, 24-hour Orbit Period:

a. Cell Description: These cells are rectangular in shape with sealed nylon cases. Each cell was individually epoxy potted by the manufacturer. The positive plates have one percent of palladium added to the active material.

b. Test Parameters:

- (1) Test Temperature: 25° C.
- (2) Depth of Discharge: 40%.
- (3) Upper Voltage Limit: 1.97 ± 0.03 volts per cell, average.
- (4) Low Current Level: 0.35 amps.
- (5) Lower Voltage Limit: 1.87 ± 0.03 volts per cell, average.

c. Test Results:

(1) Performance on Cycling:

(a) Cycling was started on Pack 9D in December 1965. This pack completed 121 cycles with two cell failures.

The test was discontinued, at the request of Goddard Space Flight Center when the two cells failed, because the voltage limit settings could not be lowered. The failed cells were returned to the manufacturer for analysis. This analysis indicated that the zinc plates were in better condition (very little shape change) than plates of previous samples, but that silver penetration was still a problem.

(b) Cycling of pack 9E was started in October 1966. This pack completed 90 cycles with three cell failures. The test was discontinued at that time. The cells were returned to the manufacturer; no report on the failure analysis has been received.

3. Yardney 16.0 ah (Silver-Zinc), One 10-cell Pack,
24-hour Orbit Period (Pack 57C):

a. Cell Description: These are vented cells, rectangular in shape, with the cell jars and cell covers molded of a plastic material. They contain a limited amount of electrolyte. The cells were individually epoxy potted to hermetically seal them.

b. Test Parameters:

- (1) Depth of Discharge: 31%.
- (2) Upper Voltage Limit: 1.98 ± 0.03 volts per cell, average.
- (3) Low Current Level: 0.10 amperes.
- (4) Lower Voltage Limit: 1.86 ± 0.03 volts per cell, average.
- (5) Test Temperature: 25° C for 100 cycles; then 0° C for 100 cycles. Repeat until pack failure occurs.

c. Test Results:

(1) Performance on Cycling: Cycling was started in December 1966. This pack completed 281 cycles with one cell failure. The failed cell began leaking electrolyte after 137 cycles. The cells operated very well at both temperatures. Because of the difficulty in changing the voltage limits, as set by the two-step regulator, Goddard Space Flight Center requested that the test be discontinued.

(2) Capacity Checks: Each cell was discharged to the cutoff voltage of 1.30 volts and the ampere-hour capacities determined. After 80 days of cycling the capacities ranged from 6.67 to 20.0 ampere-hours. After 203 days of cycling the capacity range was 0.67 to 18.5 ampere-hours.

F. Internal Mechanical Pressure Devices: (See Section II, Paragraph II.D., for description of internal mechanical pressure devices.)

1. Sonotone 20.0 ah (Nickel-Cadmium), Five 10-cell Packs, 1.5-hour and 3-hour Orbit Periods:

a. Cell Description: These cells are rectangular in shape. The cell container and cell cover are made of stainless steel. Both terminals are insulated from the cell cover by a teflon seal and protrude through the cover as a threaded terminal. Each cell is also fitted with a pressure relief valve. Cells 1 through 5 in each pack are standard cells; cells 6 through 10 contain a stainless steel elliptical spring which supplies the pressure to the face of the plates.

b. Test Parameters:

Pack Number	Test Temperature	Percent Depth of Discharge
10A	25° C	25
22A	25° C	25
34B	25° C	40
46A*	25° C	40
72B	25° C	75

* This pack has an orbit period of 3 hours; all others are 1.5 hours.

c. Test Results:

(1) Performance on Cycling: Packs 34B and 72B failed on cycles 5634 and 1143, respectively. In order to use the same equipment for replacement cells pack 10A was discontinued on cycle 7188, pack 22A on cycle 6664, and pack 46A on cycle 3501.

(a) Shortly after the start of cycling in September 1967, high internal pressure developed in all cells as evidenced by bulged case and the rupture of four. Cycling was stopped in November 1967 with 1170 cycles on pack 10A, 599 cycles on pack 22A, 943 cycles on pack 34B, 427 cycles on pack 46A, and 609 cycles on pack 72B.

(b) A representative from NASA, Lewis Research Center, and one from the manufacturer reviewed the results in order to determine what steps should be taken before continuation of the cycling test. Five of the 14 failed cells were analyzed at NAD Crane, the manufacturer's representative took the remaining nine failed cells with him in order to determine the cause for the excessive pressure buildup in both the control and spring loaded cells.

(c) After completion of his testing, the manufacturer recommended that new relief valves be installed, the cells be reconditioned, and the charge current be reduced from 20 to 15 amperes on packs 22A, 34B and 46A. It was necessary that the charge rate on pack 72B remain at 20 amperes because of the deep depth of discharge. The packs were then returned to cycling.

(2) Failure Analysis:

(a) Analysis of five of the first 14 failed cells showed the major cause to be the plates shorting against the cell case because of the high internal pressure.

(b) Analysis of the 24 cells that failed after the test modification showed the major cause of failure to be migration of the negative plate material and separator deterioration in both the control and spring loaded cells.

(3) Capacity Checks: The ampere-hour capacities on the precycling and capacity check cycles are as follows:

Orbit Period (Hr)	1.5	1.5	1.5	3.0	1.5
Temperature	25°	25°	25°	25°	25°
Depth of Discharge	25%	25%	40%	40%	75%
Pack Number	10A	22A	34B	46A	72B
Precycling Capacity	28.7	28.8	29.7	25.7	26.2
38 Days Disch #2	22.5	21.3	20.0	24.3	
176 Days Disch #2	22.2	7.7	13.5	15.2	
264 Days Disch #2	21.3	10.8	11.3	23.5	
352 Days Disch #2	18.2	21.2		4.7	

SECTION V

TEST FACILITIES

I. TEST FACILITIES

A. Environmental Chambers: Ambient test temperature conditions were obtained with the following equipment:

1. -20°C : A 12 cubic foot chamber manufactured by General Thermodynamics, Inc., Model UCH 322 C-B, temperature controls accurate to within $\pm 1.5^{\circ}\text{C}$.
2. 0°C : A 27 cubic foot chamber manufactured by the A. Webber Engineering Corporation, Model WF-27-40, temperature controls accurate to within $\pm 1.5^{\circ}\text{C}$.
3. 20°C : A 27 cubic foot chamber manufactured by Tenney Engineering, Inc., Model UF-40240, temperature controls accurate to within $\pm 1.5^{\circ}\text{C}$.
4. 25°C : Packs cycling at 25°C are located in an air conditioned room with other temperature critical equipment. The temperature is maintained at $25^{\circ} \pm 2^{\circ}\text{C}$.
5. 40°C : A 12 cubic foot chamber manufactured by Conrad, Inc., Model FB-12-510, temperature controls accurate to within $\pm 1.5^{\circ}\text{C}$.
6. $0^{\circ} - 40^{\circ}\text{C}$: A 12 cubic foot chamber manufactured by General Thermodynamics, Inc., Model UCH 322C-B, temperature controls accurate to within $\pm 1.5^{\circ}\text{C}$. The chamber operates on a 48-hour cycle in which the temperature increases from 0° to 40°C and then decreases to 0°C thereby completing the cycle.
7. Several small chambers are used as required for additional packs and for any special temperature requirements. They range in size from 1.5 to 2.5 cubic feet and have a temperature range of -75°C to 175°C .

B. Charge and Discharge Control Units:

1. Each cell pack is connected to its own, independent, solid state current limiting charging unit. These units control the charge rates and voltage limits by regulating the current supplied by a 28 VDC generator or by remote programming of a commercial power supply. They also discharge the cell packs by a relay switching system which changes the current lead connections within the units. Units, whose current is supplied by a 28 VDC generator, have a voltage divider in series with a

constant current circuit in order to obtain a reference voltage for the voltage limiting circuit. This type of unit has two ammeters rated at ± 1 percent accuracy for visual monitoring of the charge and discharge currents, and three separate controls for setting the currents and voltage limit at the desired values. A 3-position switch, on both types of units, selects between continuous charge, continuous discharge, and automatic cycling operating. Automatic cycling is controlled by a stepping relay which receives a pulse for each minute from a digital clock. The stepping relay is wired for both the 1.5-hour and 3-hour orbits. Each unit is connected to the corresponding output for its cycle period.

2. Photograph 1 shows a front view of several charge-discharge units.

C. Upper and Lower Voltage Limit Monitoring System:

1. Each pack is connected to its own lower limit voltmeter which sets off an alarm common to the system and turns on an identifying light for the particular pack when the terminal voltage of the pack falls below a preset limit. Photograph 2 is a picture of the lower voltage limit monitoring system.

2. An additional system is used to scan each individual cell voltage. When the voltage of any cell is found to be outside the preset upper or lower limits, the system automatically sets off the alarm and the identifying light in the lower voltage limit monitoring system and also disconnects the current leads of that pack by de-energizing a relay. The system includes a 900-point modified crossbar scanner which scans continuously at a rate of 330 designated cell voltage points per minute, so that each cell is scanned every 2 minutes. Voltages are measured by a DC to frequency converter and a frequency counter. The scanning system is shown in Photograph 3.

D. Data Logging System:

1. Brief Summary:

a. Recordings are made by means of a data logging system (Photograph 4) obtained from Gulf Aerospace Corporation. All monitoring leads from a given pack of cells are scanned, converted to digital form and fed to the Tally Mark 45P paper tape punch and programmed reader. The system enables the current, pack terminal voltage, all cell voltages and the thermocouple voltages for a given pack to be read and punched out within less

than 4 seconds. An additional switching arrangement permits recording up to six 10-cell packs and twelve 5-cell packs at one time.

2. Technical Description:

a. This system is designed to record data from 30 data channels by sampling and scanning the input voltages. The data is converted to binary code by a precision amplifier and a high speed analog to digital converter and is presented serially by character to the paper tape punch for storage of the data. Figure 86 is a block diagram of the data logging system.

b. The system measurements are either timed and controlled by the system's digital clock, or manually controlled by the operator. Additional features of the system provide for a typed report of the stored data.

c. The system has 30 input channels. Of these, channels 1 to 10 have a full scale input of 10 volts and measure cell voltages. Channels 11 and 13 have a full scale range of 20 volts and measure the total pack voltages. Channels 12 and 14 have a full scale range of 100 millivolts and measure the voltage across 100 millivolt current shunts.

d. All of these inputs, 1 to 14, are sample and hold type inputs. They are sampled simultaneously for 400 milliseconds. The attenuated input signal voltages, all of which are normalized to 100 millivolts full scale, are stored on high quality capacitors. The scanner then sequentially scans these capacitors for data readout. This technique is used to eliminate any difference in time between the first 14 input readings. The accuracy of these channels is ± 0.25 percent of full scale reading.

e. Channel 15 is used for cell pack identification. Another instrument, which provides selection for monitoring a given pack from a group of packs, provides an output from which the particular pack selected can be identified. This output voltage is read on channel 15 as the position identifying the pack. The operator or project leader correlates these readings with specific packs being tested.

f. Channels 16 through 30 are low level input channels (± 10 millivolts full scale) designed to monitor thermocouple inputs with an accuracy of ± 1 percent of full scale. These channels have a maximum common mode voltage that can exist between the signal and the system ground of ± 10 volts. If the common mode voltage exceeds

this value, accurate readings can no longer be taken. (Common mode voltages of over ± 20 volts may damage the differential amplifier.)

g. Cycle time for this system is less than 4 seconds for all 30 channels. The readout system, a Tally Mark 45P, is capable of receiving data from the analog to digital converter, from a prepunched paper tape, or from the Selectric typewriter by manual input and may be programmed to print out the data, off line, in any desired format.

3. System Operation:

a. During the scanning process each channel in turn is routed to the input of a high impedance differential amplifier, the gain of which is automatically switched between 100 (the amount used for the high level channels) and 1000 (the amount required for the low level channels). The sensing for the gain change is supplied by the relay drivers. Provisions are made to eliminate amplifier drift while sampling voltage across the storage capacitors. The output of the amplifier is applied through a low pass filter at the input of the analog to digital converter. The analog to digital converter is then given a command to read.

b. The analog to digital converter changes the analog signal to a binary coded decimal signal. A serializer sequentially sends one digit at a time from the output of the clock or from the analog to digital converter to the perforator driver. The zero generator and the parity generator maintain the proper digital format for punching paper tape and operating the Selectric typewriter in the Tally Mark 45P system. The punched-paper-tape code is compatible with IBM binary coded decimal code (Hollerith).

4. System Controls:

a. The 30-position data scanner has several modes of operation. Mode switch may be set to continuous cycling, preset cycle, single cycle, single step, and manual select. In the continuous cycling position the scanner continues to sample the data at a rate determined by the digital clock. In the preset cycle position the scanner takes a sample of the data at a time determined by the preset time selector. In the single cycle position the scanner samples the data once each time the step/cycle push button is depressed. In the single step position the scanner is advanced one channel at a time by depressing the step/cycle push button switch. In the manual select position the scanner remains at the channel selected by the manual select

switches. When in either of the two manual modes a reading is taken by pushing the print button. The scanner has two front panel displays, one for channel number and one for voltage. All system functions are timed by a unijunction oscillator and are controlled by logic circuits in the scanner assembly.

E. Central Wiring Panel:

1. All electrical connections are made through a centrally located wiring panel which houses the current shunts and a plug-in panel. Photograph 5 shows the front view of the central wiring panel.

F. Pack Selector Switch:

1. Up to six 10-cell packs and twelve 5-cell packs may be plugged into a selector system from the central wiring panel. Through reed relays operated by a selector switch, any of these packs may then be connected to the input of the data logging system. This arrangement allows all currents and cell and thermocouple voltages for all 18 packs to be recorded by the data logging system within 48 seconds.

2. The switching system also provides a voltage to identify the selected position and which is automatically recorded as part of the data for the pack selected.


3. Photograph 4 shows the pack selector switch located on top of the data logging system.

G. Block Diagram of Entire Test Setup:


Figure 87 shows the arrangement from the packs at each of the six ambient temperatures to the central wiring panel. Leads from the central wiring panel connect all packs and/or cells to the charge-discharge units and the 28 volt DC source or commercial power supplies, the circuit relay switching system, the voltage limiting monitoring system and the data logging system.

II. Photograph of Test Area:

Photograph 6 shows the overall arrangement of the test equipment described above.

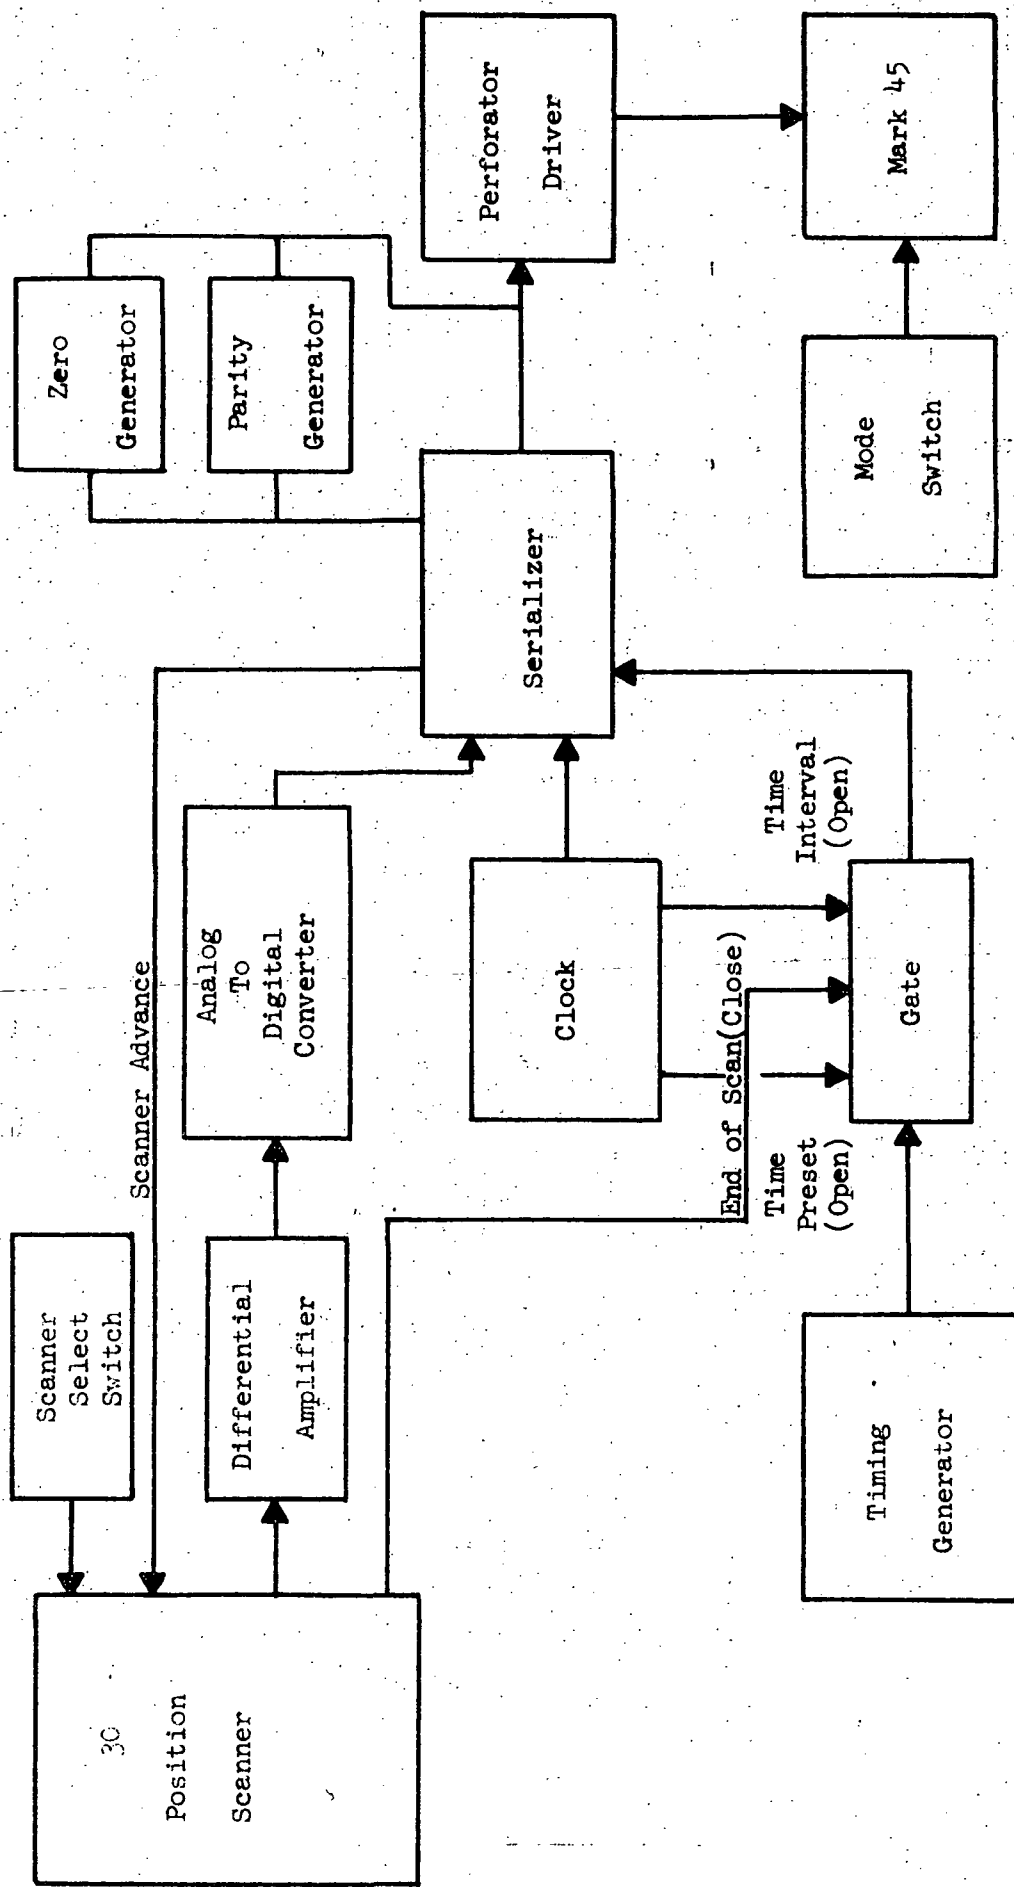


Block Diagram of Data Logging System

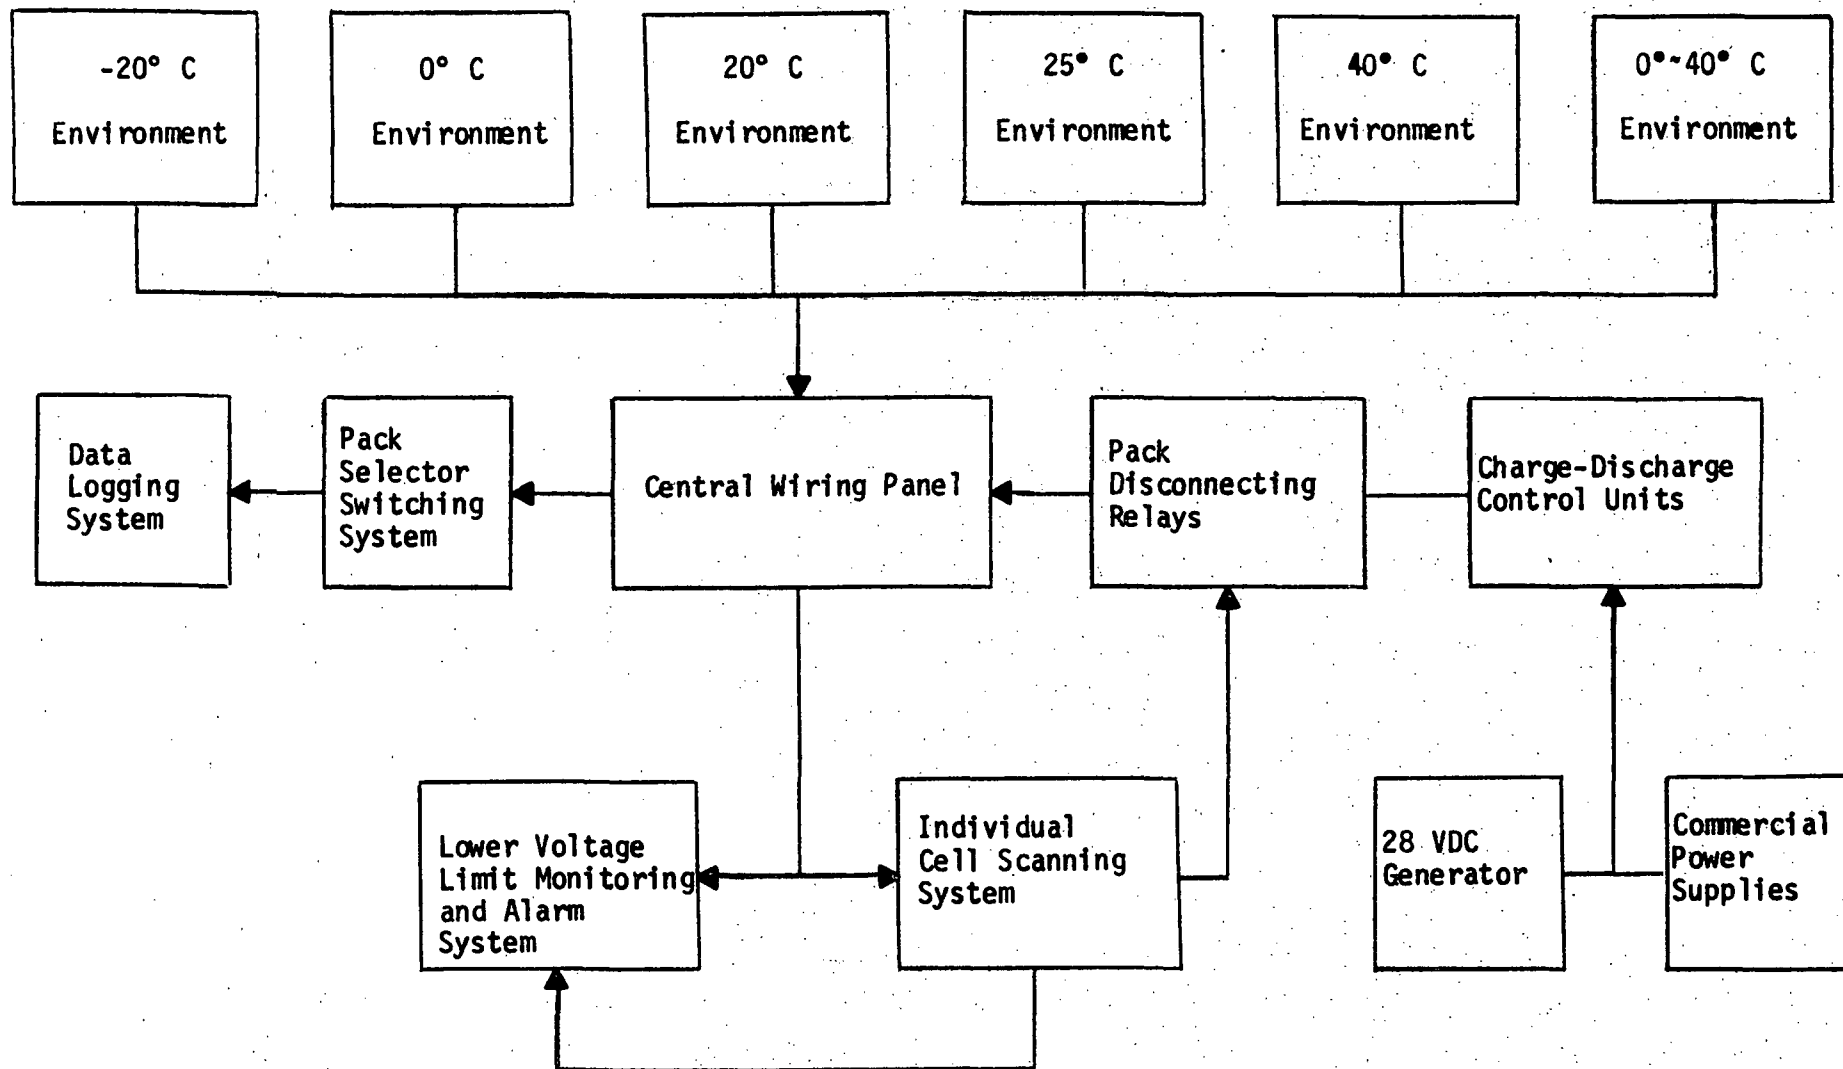


BLOCK DIAGRAM OF TEST SETUP

FIGURE 95

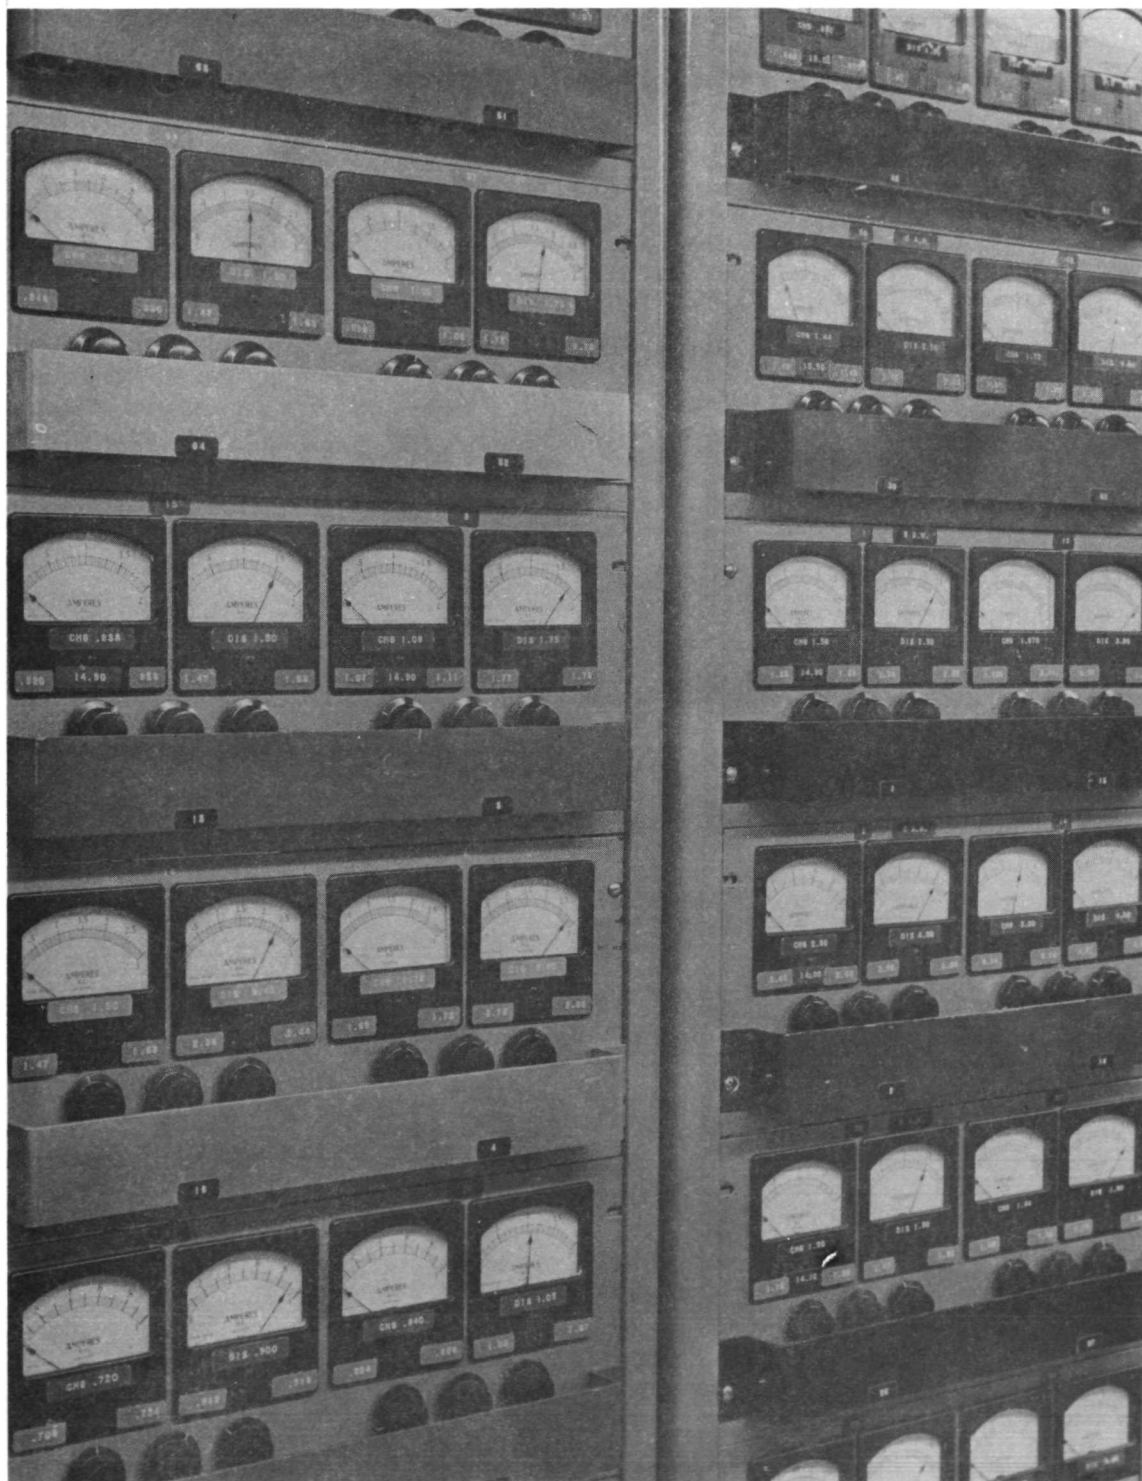


Several Charge and Discharge Control Units

PHOTOGRAPH 1

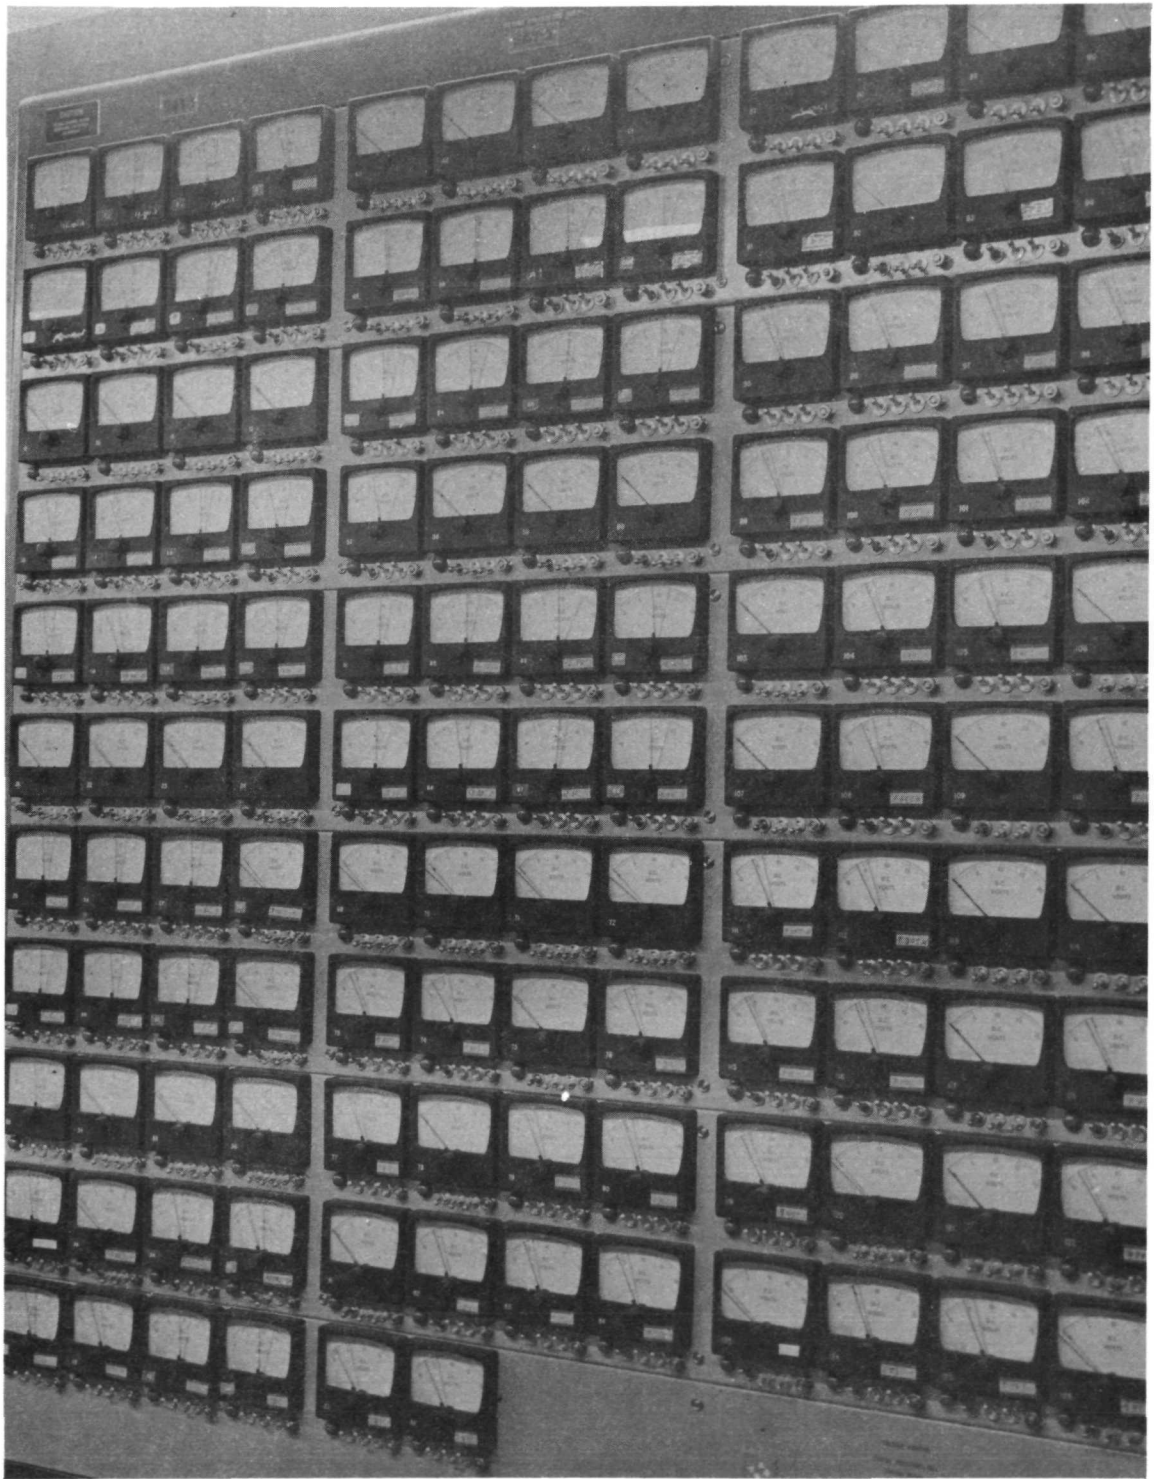

Pack Voltage Monitoring Panel

PHOTOGRAPH 2

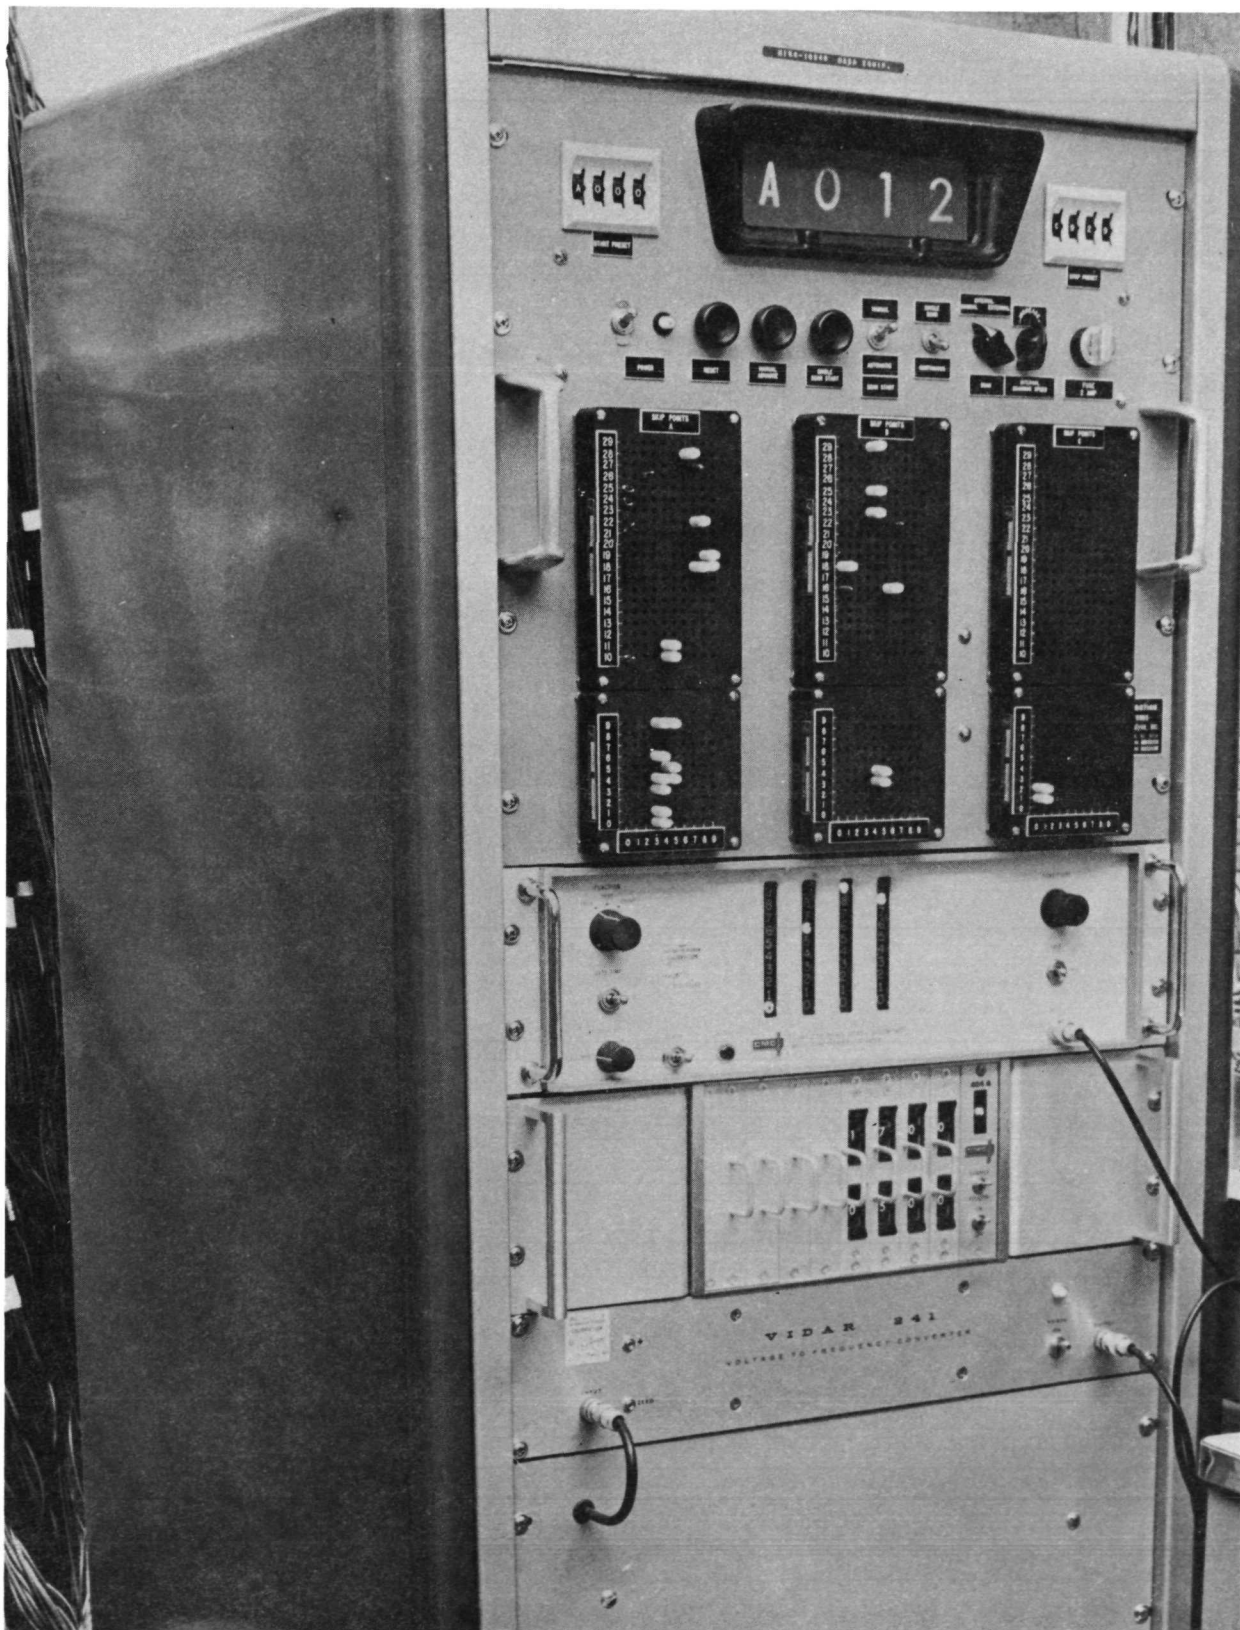


Individual Cell Voltage Scanning System

PHOTOGRAPH 3




Data Logging System

PHOTOGRAPH 4

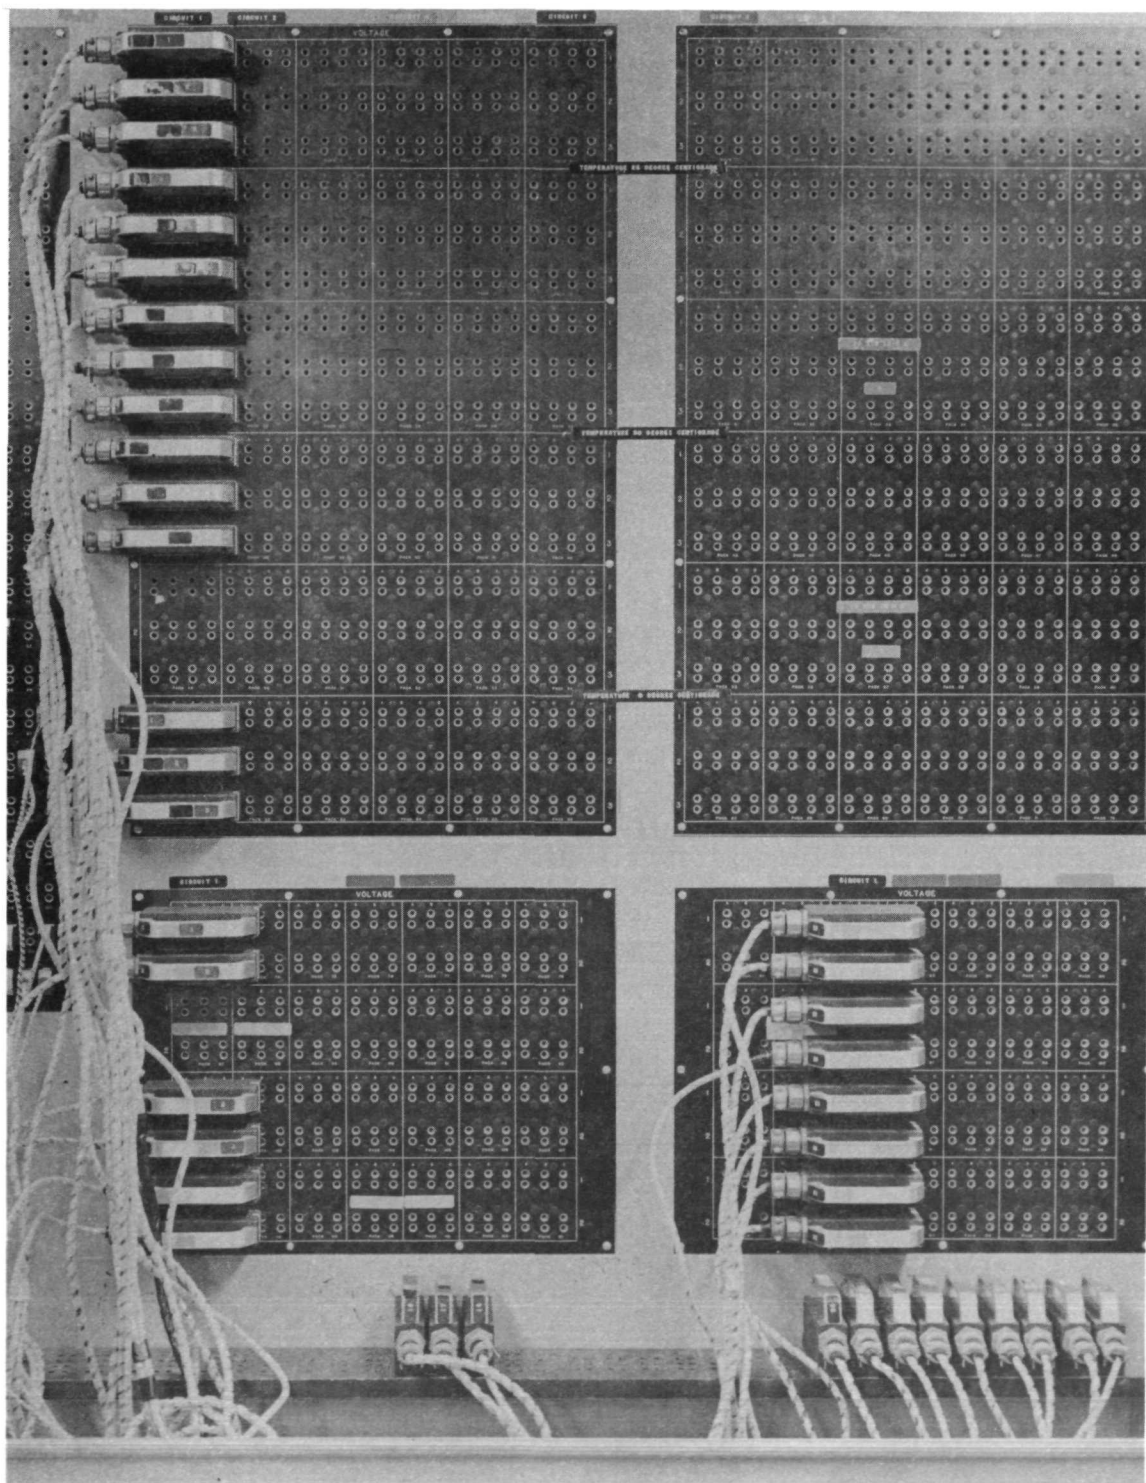

Portion of Central Wiring Panel

PHOTOGRAPH 5

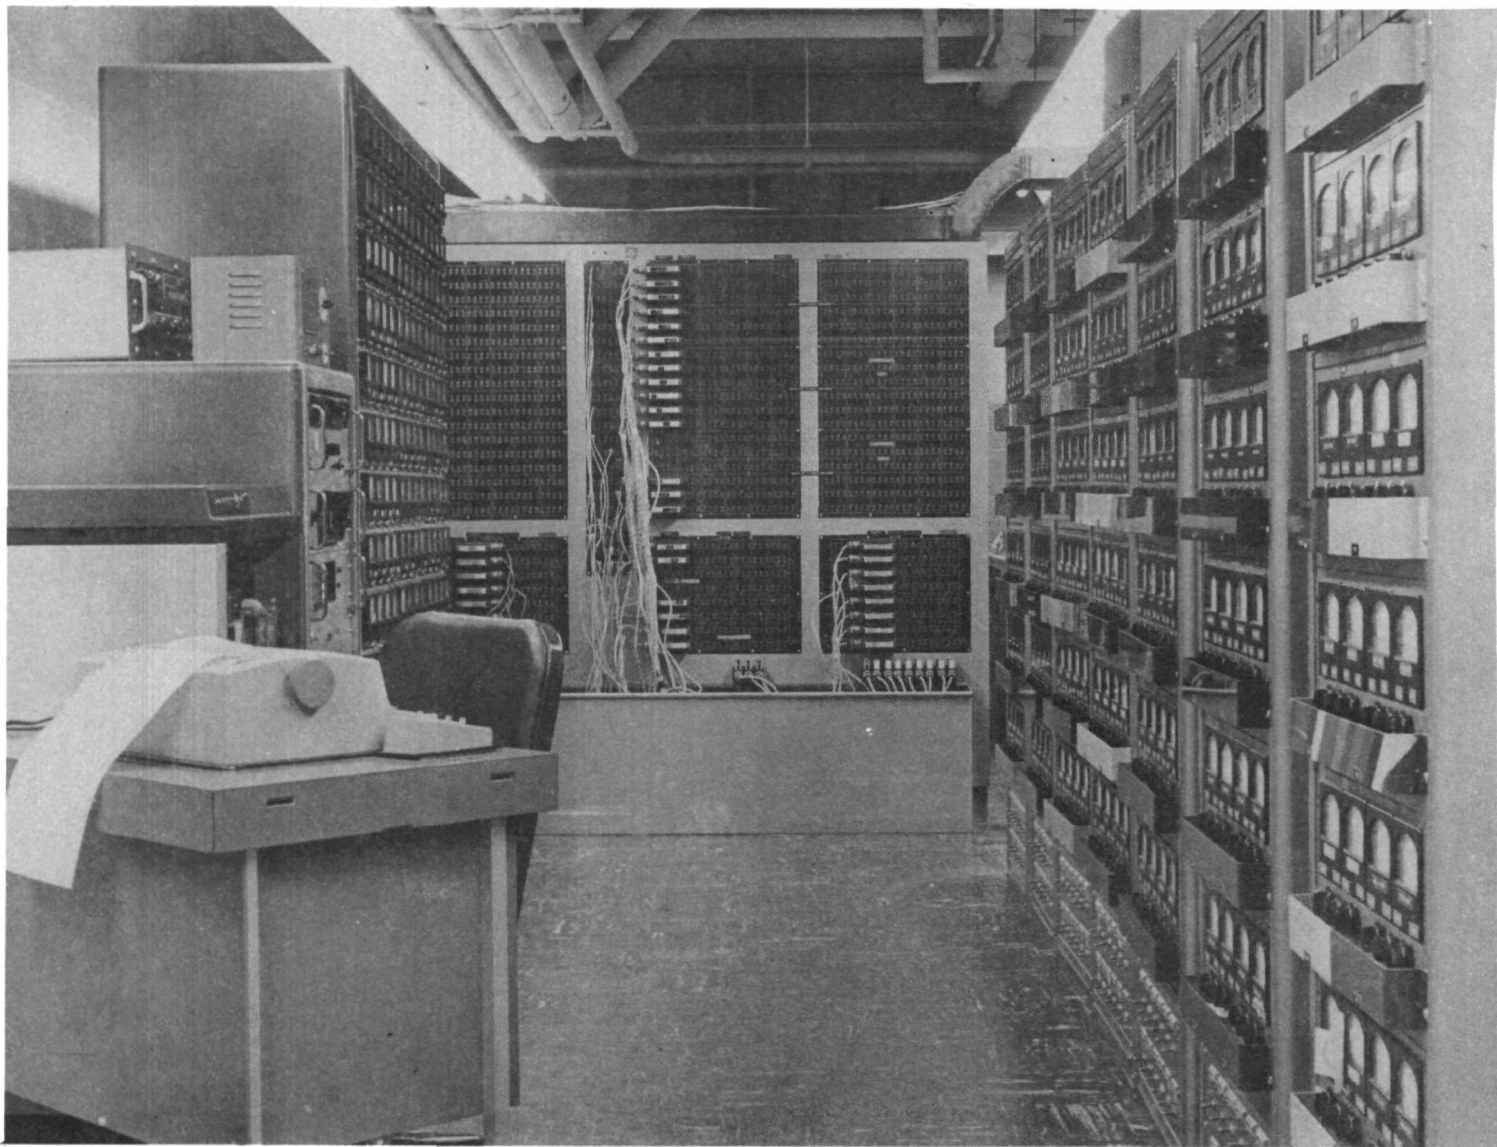

Test Area

PHOTOGRAPH 6

SECTION VI

EQUIPMENT AND PROGRAMS TO BE ADDED TO THE CYCLE
LIFE TEST PROGRAM


I. EQUIPMENT AND PROGRAMS TO BE ADDED TO THE CYCLE LIFE TEST PROGRAM

A. New Equipment:

1. A new Automatic Data Acquisition and Control System (Photograph 7) is currently being installed. This system is computer controlled and will have the capability to test and record data for 200 rechargeable packs. The system will control tests by means of operating programmable power supplies, contactors, and instructing laboratory personnel to perform manual functions. There will be 3000 data input channels, any of which may be used to measure voltage, current, temperature or pressure. Collection of data from the 3000 channels will be performed at constant intervals of 0.04 hours or less and will be recorded on magnetic tape, and upon request, will be displayed as numeric data on a Teletype printer.

B. New Programs:

1. GE, 6.0 ampere-hour, nickel-cadmium cells for evaluation on an accelerated type test.
2. GE, 20.0 ampere-hour, nickel-cadmium cells for evaluation of life-cycle capability.
3. Gulton, 20.0 ampere-hour, nickel-cadmium cells for evaluation of life-cycle capability.
4. Gulton, 100 ampere-hour, nickel-cadmium cells for evaluation of life-cycle capability.
5. Heliotek, 20.0 ampere-hour, nickel-cadmium cells for evaluation of life-cycle capability.
6. SAFT, 20.0 ampere-hour, nickel-cadmium cells for evaluation.
7. Eagle-Picher, 20.0 ampere-hour, nickel-cadmium cells for evaluation under the Process Control Program.
8. Eagle-Picher, 100 ampere-hour, nickel-cadmium cells for evaluation.
9. Yardney, 5.0 and 21.0 ampere-hour, silver-zinc cells for evaluation during deceleration test profiles.

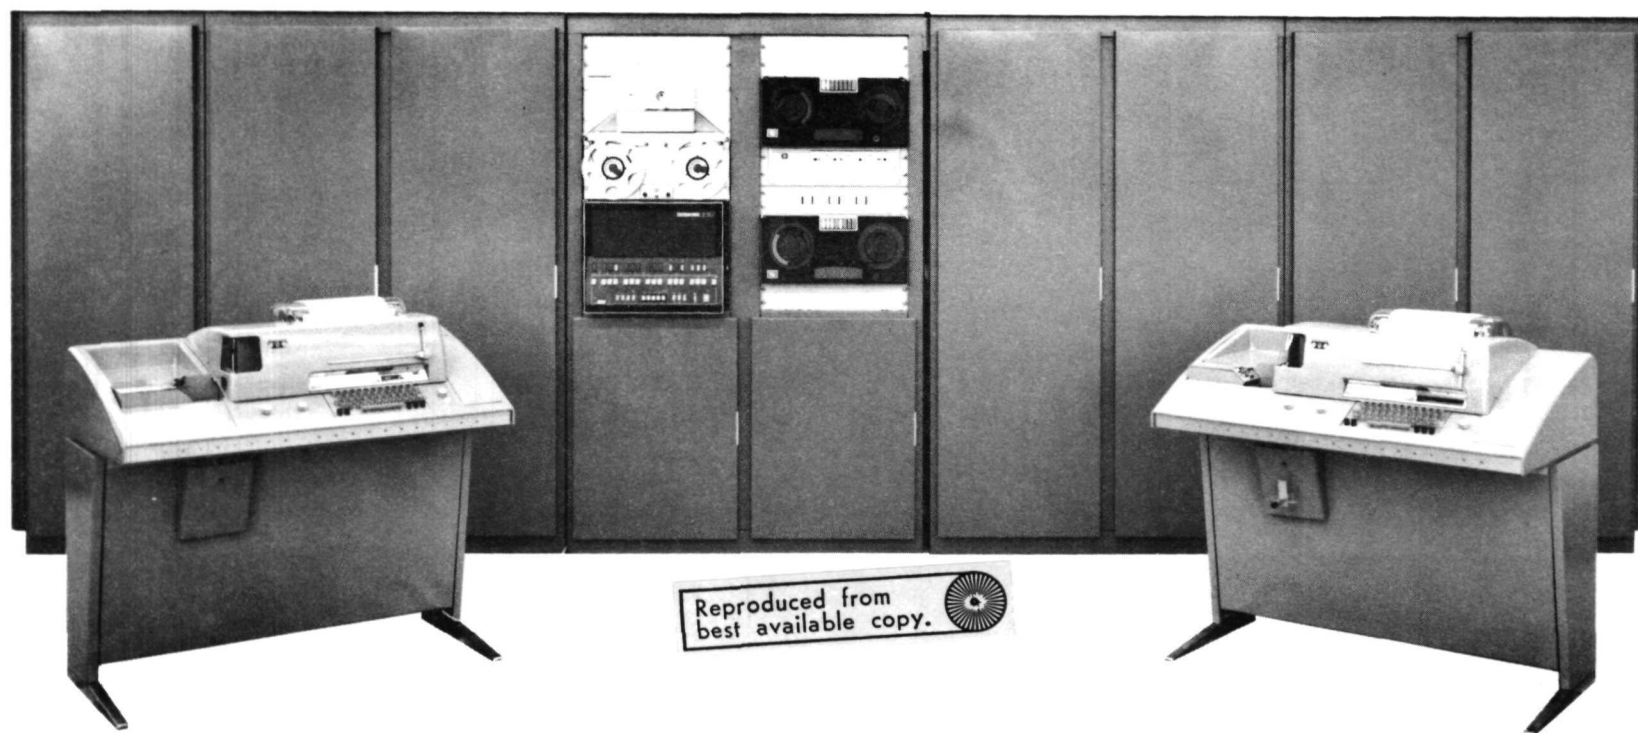

Reproduced from
best available copy. 

PHOTOGRAPH 7

Air Force Cambridge Research Laboratory (LCC, Mr. Edward Raskind, Wing F), L. G. Hanscom Field, Bedford, Massachusetts 01731

Rome Air Development Center (Code TSGD, Mr. Frank J. Mollura), Griffiss Air Force Base, New York 13440

Headquarters, SAMS0 (SMTAE, Lt. R. Ballard), Los Angeles Air Force Station, Los Angeles, California 90045

National Science Foundation (Dr. Jesse C. Denton), 1800 G Street, N.W., Washington, D. C. 20550

Director, Defense Documentation Center, Cameron Station, Alexandria, Virginia 22314 (20 copies)

Defence Research Establishment, Power Sources Division (Dr. Tom King), Shirley Bay, Ottawa, Ontario, Canada

Defence Research Establishment, Power Sources Division (Dr. Joseph Lackner), Shirley Bay, Ottawa, Ontario, Canada

Telesat Canada (Dr. M. A. Stott), 333 River Road, Ottawa, Ontario, Canada

Aerospace Corporation (Library Acquisition Group), P. O. Box 95085, Los Angeles, California 90045

Aerospace Corporation (Mr. Larry Gibson), P. O. Box 95085, Los Angeles, California 90045

American Cyanamid Company (Dr. R. A. Haldeman), 1937 W. Main Street, Stamford, Connecticut 06902

AMF, Inc. (Mr. R. A. Knight), 689 Hope Street, Stamford, Connecticut 06906

American University, Chemistry Department (Dr. R. T. Foley), Massachusetts & Nebraska Avenues, N. W., Washington, D. C. 20016

Artech, Inc. (Dr. Frank Swindell), 2316 Fallfax Drive, Falls Church, Virginia 22042

Atomics International Division, North American Aviation, Inc. (Dr. H. L. Recht), P. O. Box 309, Canoga Park, California 91304

Autonetics Division, NAR (Mr. R. F. Fogle, GF 18), P. O. Box 4181, Anaheim, California 92803

Harry Diamond Laboratories, Room 300, Building 92, Connecticut Ave.
& Van Ness Street, N.W., Washington, D. C. 20438

Chief of Naval Research (Code 473, Director, Power Program),
Department of the Navy, Arlington, Virginia 22217

Chief of Naval Research (Code 472, Mr. Harry Fox), Department of
the Navy, Arlington, Virginia 22217

Director, Naval Research Laboratory (Code 6160, Mr. S. Schuldiner),
4555 Overlook Avenue, S.W., Washington, D. C. 20360

Director, Naval Research Laboratory (Code 7975, Mr. Joe Yuen),
4555 Overlook Avenue, S.W., Washington, D. C. 20360

Officer In Charge, Annapolis Division, Naval Ship Research &
Development Center (Code A731, Mr. J. H. Harrison), Annapolis,
Maryland 21402

Commander, Naval Air Systems Command (AIR-310C, Dr. H. Rosenwasser),
Department of the Navy, Washington, D. C. 20360

Commander, Naval Air Systems Command (AIR-53643, Mr. E. White),
Department of the Navy, Washington, D. C. 20360

Commander, Naval Ordnance Laboratory, White Oak (Code 232,
Mr. Philip B. Cole), Silver Spring, Maryland 20910

Commander, Mare Island Naval Shipyard (Code 134.1, Chemical
Laboratory), Vallejo, California 94592

Commander, Naval Ship Engineering Center (Code 61570, Mr. Albert
Himy), Center Building, Prince George Center, Hyattsville,
Maryland 20782

Superintendent, Naval Observatory (STIC, Mr. Robert E. Trumbule),
4301 Suitland Road, Suitland, Maryland 20390

Commander, Naval Ship Systems Command (SHIP-03422, Mr. Bernard B.
Rosenbaum), Department of the Navy, Washington, D. C. 20360

Commander, AFAPL (POE-1, Mr. D. Pickett), Wright-Patterson Air
Force Base, Ohio 45433

Commander, AFAPL (POE-1, Mr. R. L. Kerr), Wright-Patterson Air
Force Base, Ohio 45433

Delco-Remy Division, General Motors Corporation (Mr. J. A. Keralla),
2401 Columbus Avenue, Anderson, Indiana 46011

Eagle-Picher Industries, Inc., Couples Department (Mr. E. P.
Broglia), P. O. Box 47, Joplin, Missouri 64801

E. I. du Pont DeNemours & Company, Engineering Materials Laboratory,
Experimental Station, Bldg 304 (Mr. J. M. Williams), Wilmington,
Delaware 19898

ESB, Inc. (Director of Engineering), P. O. Box 11097, Raleigh,
North Carolina 27604

ESB, Inc., Carl F. Norberg Research Center (Dr. A. J. Salkind),
19 West College Avenue, Yardley, Pennsylvania 19067

Electrochimica Corporation (Dr. Morris Eisenberg), 1140 O'Brien
Drive, Menlo Park, California 94025

Electromite Corporation (Mr. R. H. Sparks), 2117 South Anne Street,
Santa Ana, California 92704

Elpower Corporation (Mr. V. L. Best), 2117 South Anne Street,
Santa Ana, California 92704

Emhart Corporation (Dr. W. P. Cadogan), Box 1620, Hartford,
Connecticut 06102

Energetics Science, Inc. (Dr. H. G. Oswin), 4461 Bronx Boulevard,
New York, New York 10470

Energy Research Corporation (Mr. Martin Klein), 15 Durant Avenue,
Bethel, Connecticut 06801

Fairchild Industries, Inc., ATS Power Laboratory (Mr. Fred E. Betz),
Germantown, Maryland 20767

Federal City College (Dr. M. Savitz), 425 Second Street, N.W.,
Washington, D. C. 20001

Dr. Arthur Fleischer, 466 South Center Street, Orange,
New Jersey 07050

General Dynamics/Corvair (Dept. 967-50, Mr. R. P. Mikkelsen),
San Diego, California 92112

Battelle Memorial Institute (Dr. John McCallum), 505 King Avenue,
Columbus, Ohio 43201

Bellcom, Inc. (Mr. J. J. Sakolosky), 955 L'Enfant Plaza, North,
S.W., Washington, D. C. 20024

Bellcom, Inc. (Mr. W. W. Hough), 955 L'Enfant Plaza, North, S.W.,
Washington, D. C. 20024

Bell Telephone Labs, Inc. (Mr. D. O. Feder), Murray Hill,
New Jersey 07974

Bell Telephone Laboratories (Mr. R. L. Beauchamp), Murray Hill,
New Jersey 07974

Dr. Carl Berger, 13401 Kootenay Drive, Santa Ana, California 92705

The Boeing Company (MS 84-79, Mr. Sidney Gross), P. O. Box 3999,
Seattle, Washington 98124

Burgess Battery Division, Gould, Inc. (Mr. M. E. Wilke, Chief
Engineer), Freeport, Illinois 61032

C & D Batteries, Division of Electric Autolite Co. (Dr. Eugene
Willihnganz), 3043 Walton Road, Plymouth Meeting, Pennsylvania 19462

Calvin College (Prof. T. P. Dirkse), 3175 Burton Street, S. E.,
Grand Rapids, Michigan 49506

Catalyst Research Corporation (Mr. F. Tepper), 6101 Falls Road,
Baltimore, Maryland 21209

Ceramaseal, Inc. (Mr. Robert Turner), New Lebanon Center,
New York 12126

Chrysler Corporation, Space Division (Mr. C. E. Thomas),
P. O. Box 29200, New Orleans, Louisiana 70129

Communications Satellite Corp., Comsat Laboratories (Mr. Robert
Strauss), P. O. Box 115, Clarksburg, Maryland 20734

G. & W. H. Corson, Inc. (Dr. L. J. Minnich), Plymouth Meeting,
Pennsylvania 19462

Cubic Corporation (Librarian), 9233 Balboa Avenue, San Diego,
California 92123

Gulton Industries, Battery & Power Sources Division, 212 Durham Avenue, Metuchen, New Jersey 08840

Gulton Industries (Mr. Ed Kantner), 212 Durham Avenue, Metuchen, New Jersey 08840

Hercules, Inc. (Mr. Paul Cox), P. O. Box 12145, Research Triangle Park, North Carolina 27709

Honeywell, Inc., Livingston Electronic Laboratory (Librarian), Montgomeryville, Pennsylvania 18936

Dr. P. L. Howard, Centreville, Maryland 21617

Hughes Aircraft Corporation (M.S. 524, Bldg. 366, Mr. M. E. Ellion), El Segundo, California 90245

ITT Research Institute (Dr. H. T. Francis), 10 West 35th Street, Chicago, Illinois 60616

Idaho State University, Department of Chemistry (Dr. G. Myron Arcand), Pocatello, Idaho 83201

University of Illinois (306E Talbot Laboratory, Prof. Will J. Worley), Urbana, Illinois 61801

Institute for Defense Analyses (Mr. R. Hamilton), 400 Army-Navy Drive, Arlington, Virginia 22202

Institute for Defense Analyses (Dr. R. Briceland), 400 Army-Navy Drive, Arlington, Virginia 22202

International Nickel Company (Mr. N. A. Matthews), 1000-16th Street, N.W., Washington, D. C. 20036

Johns Hopkins University, Applied Physics Laboratory (Mr. Richard E. Evans), 8621 Georgia Avenue, Silver Spring, Maryland 20910

Leesona Moos Laboratories (Dr. A. Moos), Lake Success Park, Community Drive, Great Neck, New York 11021

Life Systems, Inc. (Dr. Richard A. Wynveen, Pres.), 23715 Mercantile Road, Cleveland, Ohio 44122

Arthur D. Little, Inc. (Dr. James D. Birkett), Acorn Park, Cambridge, Massachusetts 02140

General Electric Company, Research and Development Center
(Dr. R. P. Hamlen), P. O. Box 43, Schenectady, New York 12301

General Electric Company, Research and Development Labs
(Dr. F. Will), Schenectady, New York 12301

General Electric Company, Research and Development Labs
(Dr. J. L. Weininger), Schenectady, New York 12301

General Electric Company, Space Systems (Mr. K. L. Hanson, Room
14-2700), P. O. Box 8555, Philadelphia, Pennsylvania 19101

General Electric Company, Space Systems (Mr. Aaron Kirpich, Room
M-2614), P. O. Box 8555, Philadelphia, Pennsylvania 19101

General Electric Company, Missile and Space Division (Mr. H.
Thierfelder), P. O. Box 8555, Philadelphia, Pennsylvania 19101

General Electric Company, Battery Business Section (Mr. P. R.
Voyentzie), P. O. Box 114, Gainesville, Florida 32601

General Electric Corporation (Mr. Guy Rampel), Gainesville,
Florida 32601

General Electric Company (Whitney Library), P. O. Box 8,
Schenectady, New York 12301

General Electric Company (Mr. David F. Schmidt), 777-14th Street, N.W.,
Washington, D. C. 20005

Globe-Union, Inc. (Dr. R. Goodman), P. O. Box 591, Milwaukee,
Wisconsin 53201

Globe-Union, Inc. (Dr. Eugene Wissman), P. O. Box 591, Milwaukee,
Wisconsin 53201

Gould Ionics, Inc. (Dr. J. E. Oxley), P. O. Box 1377, Canoga Park,
California 91304

Gould, Inc. (Dr. C. J. Menard), 2630 University Avenue, S.E.,
Minneapolis, Minnesota 55414

Grumman Aerospace Corporation (Plant 35, Dept 567, Mr. Steve J.
Gaston), Bethpage, Long Island, New York 11714

National Aeronautics and Space Administration, Lewis Research Center
(MS 309-1, Mr. Harvey Schwartz), 21000 Brookpark Road, Cleveland,
Ohio 44135

National Aeronautics and Space Administration, Lewis Research Center
(MS 309-1, Dr. J. Stuart Fordyce), 21000 Brookpark Road, Cleveland,
Ohio 44135

National Aeronautics and Space Administration, George C. Marshall
Space Flight Center (S&E-ASTR-EP, Mr. Charles B. Graff), Huntsville,
Alabama 35812

National Aeronautics and Space Administration, Manned Spacecraft
Center (EP-5, Mr. W. E. Rice), Houston, Texas 77058

National Aeronautics and Space Administration, Ames Research Center
(M.S. 244-2, PBS, Mr. Jon A. Rubenzer), Moffett Field, California 94035

Jet Propulsion Laboratory (M.S. 198-220, Mr. Daniel Runkle),
4800 Oak Grove Drive, Pasadena, California 91103

Jet Propulsion Laboratory (M.S. 198-220, Mr. Aiji Uchiyama),
4800 Oak Grove Drive, Pasadena, California 91103

Jet Propulsion Laboratory (M.S. 198-220, Dr. R. Lutwack),
4800 Oak Grove Drive, Pasadena, California 91103

Jet Propulsion Laboratory (Mr. R. S. Bogner), 4800 Oak Grove
Drive, Pasadena, California 91103

Jet Propulsion Laboratory (M.S. 198-220, Mr. Stanley J. Krause),
4800 Oak Grove Drive, Pasadena, California 91103

Commanding General, U. S. Army Electro Technology Lab, Energy
Conversion Research Division (MERDC), Fort Belvoir, Virginia 22060

Commanding General, U. S. Army Electronics R&D Labs (AMSEL-TL-P),
Fort Monmouth, New Jersey 07703

Commanding General, U. S. Army Electronics Command (AMSEL-ME-NMP-TB-2,
Mr. A. Frink), Fort Monmouth, New Jersey 07703

Harry Diamond Laboratories (Mr. Nathan Kaplan), Room 300, Building 92,
Connecticut Ave. & Van Ness Street, N.W., Washington, D. C. 20438

DISTRIBUTION LIST

National Aeronautics and Space Administration, Goddard Space Flight Center (Code 761.2, Mr. T. J. Hennigan), Greenbelt, Maryland 20771 (12 copies)

National Aeronautics and Space Administration (Code RPP, Mr. Ernst M. Cohn), Washington, D. C. 20546

National Aeronautics and Space Administration (Code SCC, Dr. A. M. Greg Andrus), Washington, D. C. 20546

National Aeronautics and Space Administration, Scientific and Technical Information Center; Input, P. O. Box 33, College Park, Maryland 20740 (3 copies)

National Aeronautics and Space Administration (Code UT, Dr. E. N. Case), Washington, D. C. 20546

National Aeronautics and Space Administration (Code MTG, Mr. Richard Livingston), Washington, D. C. 20546

National Aeronautics and Space Administration, Goddard Space Flight Center (Code 764 Mr. Gerald Halpert), Greenbelt, Maryland 20771

National Aeronautics and Space Administration, Goddard Space Flight Center (Code 450, Mr. Louis Wilson), Greenbelt, Maryland 20771

National Aeronautics and Space Administration, Goddard Space Flight Center (Code 761, Mr. William Webster), Greenbelt, Maryland 20771

National Aeronautics and Space Administration, Goddard Space Flight Center (Code 761, Mr. Floyd Ford), Greenbelt, Maryland 20771

National Aeronautics and Space Administration, Goddard Space Flight Center (Code 761, Mr. Eugene R. Stroup), Greenbelt, Maryland 20771

National Aeronautics and Space Administration, Langley Research Center (MS-472, Mr. John L. Patterson), Hampton, Virginia 23365

National Aeronautics and Space Administration, Langley Research Center (MS-488, Mr. Jack E. Zanks), Hampton, Virginia 23365

National Aeronautics and Space Administration, Lewis Research Center (MS 302-1, Dr. Louis Rosenblum), 21000 Brookpark Road, Cleveland, Ohio 44135

Lockheed Aircraft Corporation (Bldg. 157, Dept. 62-25, Mr. Robert E. Corbett), P. O. Box 504, Sunnyvale, California 94088

Lockheed Aircraft Corporation (Bldg. 151, Dept. 62-25, Mr. M. G. Gandel), P. O. Box 504, Sunnyvale, California 94088

Mallory Battery Company (Mr. R. R. Clune), So. Broadway and Sunnyside Lane, Tarrytown, New York 10591

Mallory Battery Company (Mr. S. J. Angelovich, Chief Engineer), So. Broadway, Tarrytown, New York 10591

P. R. Mallory and Co., Inc. (Dr. Per Bro), Northwest Industrial Park, Burlington, Massachusetts 01801

P. R. Mallory and Co., Inc. (Library), P. O. Box 1115, Indianapolis, Indiana 46206

Marathon Battery Company (Mr. Lou Belove), P. O. Box 8233, Waco, Texas 76710

Martin-Marietta Corporation (M.S. 1620, Mr. William B. Collins & M.S. F8845, Mr. M. S. Imamura), P. O. Box 179, Denver, Colorado 80201

McDonnell Douglas Astronautics Company (Bldg 22-A3-830, MS 17, Mr. A. D. Tonelli), 5301 Bolsa Avenue, Huntington Beach, California 92647

McDonnell Douglas Astronautics Company, Headquarters Space Systems Center (Bldg 11-3-12, MS 12, Dr. George Moe), 5301 Bolsa Avenue, Huntington Beach, California 92647

Motorola, Inc. (Dr. Robert C. Shair), 8000 West Sunrise Boulevard, Ft. Lauderdale, Florida 33313

North American Rockwell Corp., Rocketdyne Division (Library), 6633 Canoga Avenue, Canoga Park, California 91304

Philco-Ford Corporation, Power and Control Engineering Department (M.S. R-26, Mr. D. C. Briggs), 3939 Fabian Way, Palo Alto, California 94303

Portable Power Sources Corporation (Mr. Leon Schulman), 166 Pennsylvania Avenue, Mt. Vernon, New York 10552

Power Information Center, University City Science Institute, Room 2210, 3401 Market Street, Philadelphia, Pennsylvania 19104

RAI Research Corporation, 225 Marcus Boulevard, Hauppauge, New York 11787

RCA Corporation, Astro Electronics Division (Mr. Paul Nekrasov), P. O. Box 800, Princeton, New Jersey 08540

SAFT Corporation of America (Mr. D. Verrier), 50 Rockefeller Plaza, New York, New York 10020

Mr. Joseph M. Sherfey, 5261 Nautilus Drive, Cape Coral, Florida 33904

Southwest Research Institute (Library), P. O. Drawer 28510, San Antonio, Texas 78228

Spectrolab, Inc. (Dr. Harvey Seiger), 12484 Gladstone Avenue, Sylmar, California 91342

Stanford Research Institute (Dr. Fritz R. Kalhammer), 19722 Jamboree Boulevard, Irvine, California 92664

Texas Instruments, Inc. (Dr. J. W. Ross), 34 Forest Street, Attleboro, Massachusetts 02703

TRW Systems, Inc. (Dr. W. R. Scott, M-2/2154), One Space Park, Redondo Beach, California 90278

TRW Systems, Inc. (Dr. Herbert P. Silverman, R-1/2094), One Space Park, Redondo Beach, California 90278

TRW, Inc. (Librarian, TIM 3417), 23555 Euclid Avenue, Cleveland, Ohio 44117

Tyco Laboratories, Inc. (Dr. Jose Giner), Bear Hill, Hickory Drive, Waltham, Massachusetts 02154

Tyco Laboratories, Inc. (Mr. Edward J. Rubin), 16 Hickory Drive, Waltham, Massachusetts 02154

Union Carbide Corporation, Development Laboratory, P. O. Box 6056, Cleveland, Ohio 44101

Union Carbide Corporation, Consumer Products Division, (Dr. Ralph Brodd), P. O. Box 6116, Cleveland, Ohio 44101

Union Carbide Corporation, Consumer Products Division (Dr. Robert Powers), P. O. Box 6116, Cleveland, Ohio 44101

University of Pennsylvania, Electrochemistry Laboratory
(Prof. John O'M. Bockris), Philadelphia, Pennsylvania 19104

Utah Research and Development Co., Inc. (Mr. William Boyd),
1820 South Industrial Road, Salt Lake City, Utah 84104

Westinghouse Electric Corporation, Research and Development Center
(Dr. C. C. Hein, Contract Admin.), Churchill Borough, Pittsburg,
Pennsylvania 15235

Whittaker Corporation, Power Sources Division, 3850 Olive Street,
Denver, Colorado 80207

Yardney Electric Co. (Mr. P. Deluca and Mr. M. Read), 82 Mechanic
Street, Pawcatuck, Connecticut 02891