

N75-29238

1. Report No. NASA CR - 134806		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle "Thrust Chamber Life Prediction" Volume I - Mechanical and Physical Properties of High Performance Rocket Nozzle Materials				5. Report Date March 1975	
				8. Performing Organization Code D180-18673-1	
7. Author(s) John J. Esposito and Ronald F. Zabora				8. Performing Organization Report No.	
9. Performing Organization Name and Address Boeing Aerospace Company (A Division of The Boeing Company) P.O. Box 3999 Seattle, Washington 98124				10. Work Unit No.	
				11. Contract or Grant No. NAS3 - 17838	
12. Sponsoring Agency Name and Address National Aeronautics & Space Administration Lewis Research Center				13. Type of Report and Period Covered Task I, Final Report	
				14. Sponsoring Agency Code	
15. Supplementary Notes R. J. Quentmeyer, NASA Technical Monitor					
16. Abstract Pertinent mechanical and physical properties of six high conductivity metals were determined. The metals include Amzirc, NARloy Z, OFHC copper, electroformed copper, fine silver, and electroformed nickel. Selection of these materials was based on their possible use in high performance reusable rocket nozzles. The typical room temperature properties determined for each material include tensile ultimate strength, tensile yield strength, elongation, reduction of area, modulus of elasticity, Poisson's ratio, density, specific heat, thermal conductivity, and coefficient of thermal expansion. Typical static tensile stress-strain curves, cyclic stress-strain curves, and low-cycle fatigue life curves are also presented. Properties versus temperature are presented in graphical form for temperatures from 27.6K (-410°F) to 810.9K (1000°F).					
17. Key Words (Suggested by Author(s)) Mechanical, Physical and Thermophysical Properties Tensile, Fatigue, Modulus of Elasticity - Amzirc, NARloy Z, OFHC Copper, EF Copper, Fine Silver, EF Nickel				18. Distribution Statement Unclassified - Unlimited	
19. Security Classif. (of this report) Unclassified		20. Security Classif. (of this page) Unclassified		21. No. of Pages 39	22. Price*

* For sale by the National Technical Information Service, Springfield, Virginia 22151



FOREWORD

This report was prepared by the Boeing Aerospace Company, a division of The Boeing Company, Seattle, Washington, for the Lewis Research Center of the National Aeronautics and Space Administration. The physical and mechanical properties of six candidate rocket nozzle materials are presented in accordance with the Task I requirements of Contract NAS3-17838, "Thrust Chamber Life Prediction." This program was under the cognizance of Gary R. Halford and R. J. Quentmeyer of the Lewis Research Center.

The literature search and documentation of the physical and mechanical properties was conducted by John J. Esposito and Ronald F. Zabora of the Structural Methods and Allowables organization. The technical leader was W. H. Armstrong, reporting to the Program Manager, J. S. Andrews.

TABLE OF CONTENTS

	<u>Page</u>
SUMMARY	1
1.0 INTRODUCTION	2
2.0 MATERIALS PROPERTIES	3
2.1 Amzirc	4
2.2 NARloy Z	12
2.3 OFHC Copper	19
2.4 Electroformed Copper	25
2.5 Fine Silver	30
2.6 Electroformed Nickel	35
3.0 REFERENCES	36

LIST OF FIGURES

<u>No.</u>	<u>Title</u>	<u>Page</u>
1	Density vs Temperature for Amzirc	5
2	Thermal Linear Expansion vs Temperature for Amzirc	5
3	Specific Heat vs Temperature for Amzirc	6
4	Thermal Conductivity vs Temperature for Amzirc	6
5	Tensile Strength vs Temperature for Amzirc-Half Hard	7
6	Modulus of Elasticity vs Temperature for Amzirc	7
7	Typical Tensile Stress-Strain Curves for Amzirc Half-Hard Condition	8
8	Room Temperature Cyclic Stress-Strain Curves for Amzirc-Half Hard Condition	9
9	810.9K (1000°F) Cyclic Stress-Strain Curves for Amzirc-Half Hard Condition	10
10	Typical Low-Cycle Fatigue Life of Amzirc-Half Hard Condition	11
11	Density vs Temperature for NARloy Z	13
12	Thermal Linear Expansion vs Temperature for NARloy Z	13
13	Specific Heat vs Temperature for NARloy Z	14
14	Thermal Conductivity vs Temperature for NARloy Z	14
15	Tensile Strength vs Temperature for NARloy Z	15
16	Modulus of Elasticity vs Temperature for NARloy Z	15
17	Typical Stress-Strain Curves for NARloy Z	16
18	810.9K (1000°F) Cyclic Stress-Strain Curves for NARloy Z	17
19	Typical Low-Cycle Fatigue Life of NARloy Z	18
20	Density vs Temperature for OFHC Copper	20
21	Thermal Linear Expansion vs Temperature for OFHC Copper	20
22	Specific Heat vs Temperature for OFHC Copper	21
23	Thermal Conductivity vs Temperature for OFHC Copper	21
24	Tensile Strength vs Temperature for OFHC Copper Annealed Condition	22
25	Modulus of Elasticity vs Temperature for OFHC Copper	22
26	Typical Stress-Strain Curves for OFHC Copper Annealed Condition	23

LIST OF FIGURES (Cont'd)

<u>No.</u>	<u>Title</u>	<u>Page</u>
27	Typical Low-Cycle Fatigue Life of OFHC Copper Annealed Condition	24
28	Density vs Temperature for Electroformed Copper	26
29	Thermal Linear Expansion vs Temperature for Electro- formed Copper	26
30	Specific Heat vs Temperature for Electroformed Copper	27
31	Thermal Conductivity vs Temperature for Electroformed Copper	27
32	Modulus of Elasticity vs Temperature for Electroformed Copper	28
33	Typical Stress-Strain Curves for Electroformed Copper-- As Formed Condition	28
34	Typical Low-Cycle Fatigue Life of Electroformed Copper-- As Formed Condition	29
35	Density vs Temperature for Fine Silver	31
36	Thermal Linear Expansion vs Temperature for Fine Silver	31
37	Specific Heat vs Temperature for Fine Silver-- As Drawn Condition	32
38	Thermal Conductivity vs Temperature for Fine Silver-- As Drawn Condition	32
39	Modulus of Elasticity vs Temperature for Fine Silver-- As Drawn Condition	33
40	Typical Stress-Strain Curves for Fine Silver-- As Drawn Condition	33
41	Typical Low-Cycle Fatigue Life of Fine Silver-- As Drawn Condition	34

SUMMARY.

Physical and mechanical properties of six candidate high performance rocket nozzle materials are documented in this report. Material properties used in life prediction studies were established for Amzirc, NARloy Z, OFHC copper, electroformed copper, fine silver, and electroformed nickel. Typical room temperature properties and typical properties at temperatures from 27.6K (-410°F) to 810.9K (1000°F) were determined for these materials.

A literature search was conducted and the data from the reference sources collected. The available data is from test programs, supplier literature, data compilations, materials handbooks and materials studies. The quantity of data available for the determination of the desired properties was very limited for these six materials. Due to this lack of data only typical properties were established for all the materials. The use of typical properties in the life analysis studies minimizes bias in the analytical results due to varying uncertainties in the input properties. To confidently establish minimum design properties, more test data, tighter material specification requirements and additional material service experience is required.

The typical mechanical properties and physical properties were established from the data base collected from the references, using suitable analysis procedures and engineering judgment to come up with the most representative properties for each of the materials.

1.0 INTRODUCTION

The advent of the Space Shuttle has brought a new era in the design and fabrication of rocket nozzles. The requirement of high-performance coupled with weight and volume limitations, has necessitated the design of rocket nozzles to operate at chamber pressures in excess of 3000 psia. This has elevated the throat heat flux from 20 Btu/in²-sec for present day high performance rocket nozzles to the range of 80-100 Btu/in²-sec for the Space Shuttle main engine. A further requirement for future high performance rocket nozzles is reusability. For example, the nozzle may have the requirement that it be capable of operating for 300 major thermal cycles for a total duration of 10 hours.

The combination of high performance and reusability has created major design problems. One of the critical aspects of the nozzle design is the fatigue life analysis. This has become a major design problem since a portion of the nozzle, particularly the throat section, is subjected to cyclic plastic strain due to the high temperature differential between the hot inner wall and the relatively cool outer shell during the engine start-stop transients as well as during steady state operation. This has a major impact on nozzle life and creates the need to accurately predict when an engine may fail.

An essential part of any life analysis program is the availability of the appropriate physical and mechanical properties, which are needed as functions of temperature, for the materials used in fabrication of high performance rockets. Section 2 defines those physical and mechanical properties necessary in predicting the rocket nozzle life.

2.0 MATERIALS PROPERTIES

Typical mechanical and physical properties data are presented in this section for six candidate high performance rocket nozzle materials. Room temperature properties are given in tabular form for all materials. The properties at temperature are presented in Figures 1 through 41.

2.1: *AMZIRC

General Information

Amzirc is a copper base alloy containing a nominal 0.15 percent zirconium. This zirconium-copper alloy combines high electrical and thermal conductivity with good strength retention at high temperatures. The alloy is readily cold worked in the solution-annealed condition. The strength of the material increases with the amount of cold working without sacrificing ductility or conductivity. After cold working, the material should be aged for 1 hour at 700°F to 800°F to obtain the improved strength and conductivity.

*American Metal Climax, Inc. — Tradename for a zirconium-copper alloy

Room Temperature Properties			
Material	Amzirc		
Condition	Annealed	Quarter Hard	Half Hard
Mechanical Properties			
Tensile Ultimate, MN/m ² (ksi)	241 (35)	338 (49)	344 (50)
Tensile Yield, MN/m ² (ksi) 0.2% Offset	46 (6.7)	296 (43)	317 (46)
Elongation, %	40	20	25
Reduction of Area, %	88	51	81
Modulus of Elasticity, GN/m ² (10 ⁶ psi)	115 (16.7)	115 (16.7)	115 (16.7)
Poisson's Ratio	.34	.34	.34
Physical Properties			
Density, kg/m ³ (lb/in ³)	8885 (.321)		
Specific Heat, J kg ⁻¹ K ⁻¹ (cal/g/K)	385 (.092)		
Thermal Conductivity, W m ⁻¹ K ⁻¹	390		
Coefficient of Thermal Expansion,			
294K to 533K , 10 ⁻⁶ [m/m]K ⁻¹	17.2		
70°F to 500°F , 10 ⁻⁶ (in/in/°F)	(9.5)		

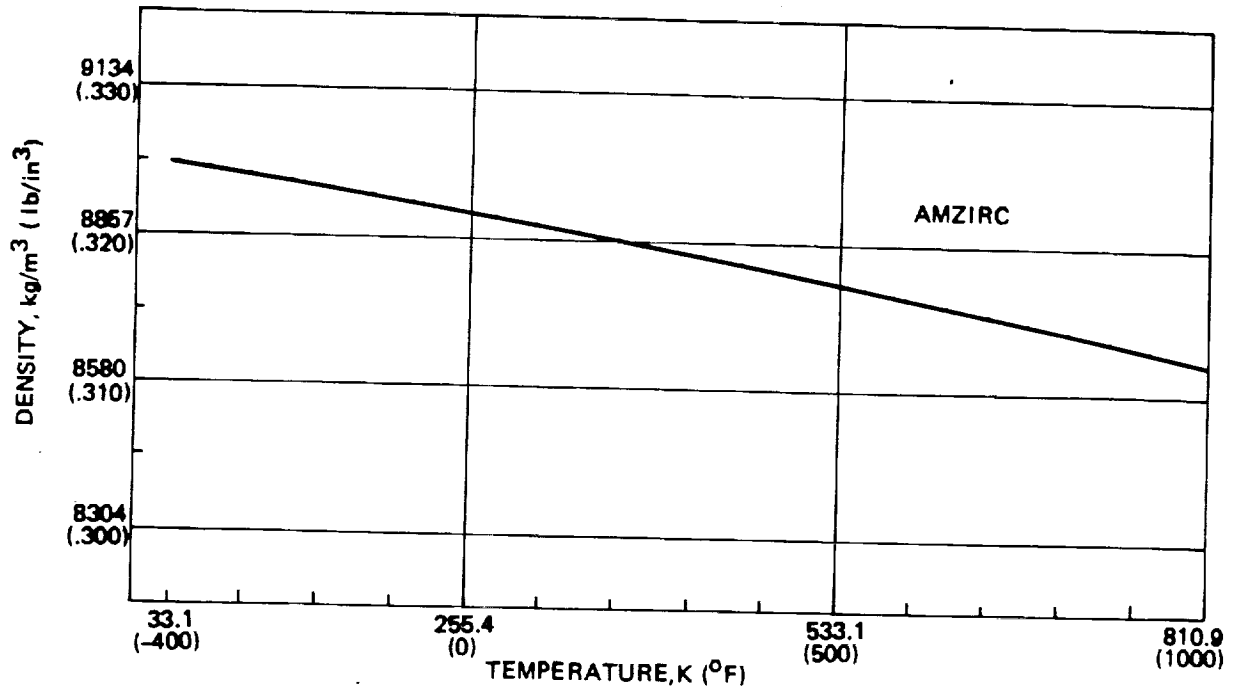


Figure 1 Density vs Temperature for Amzirc

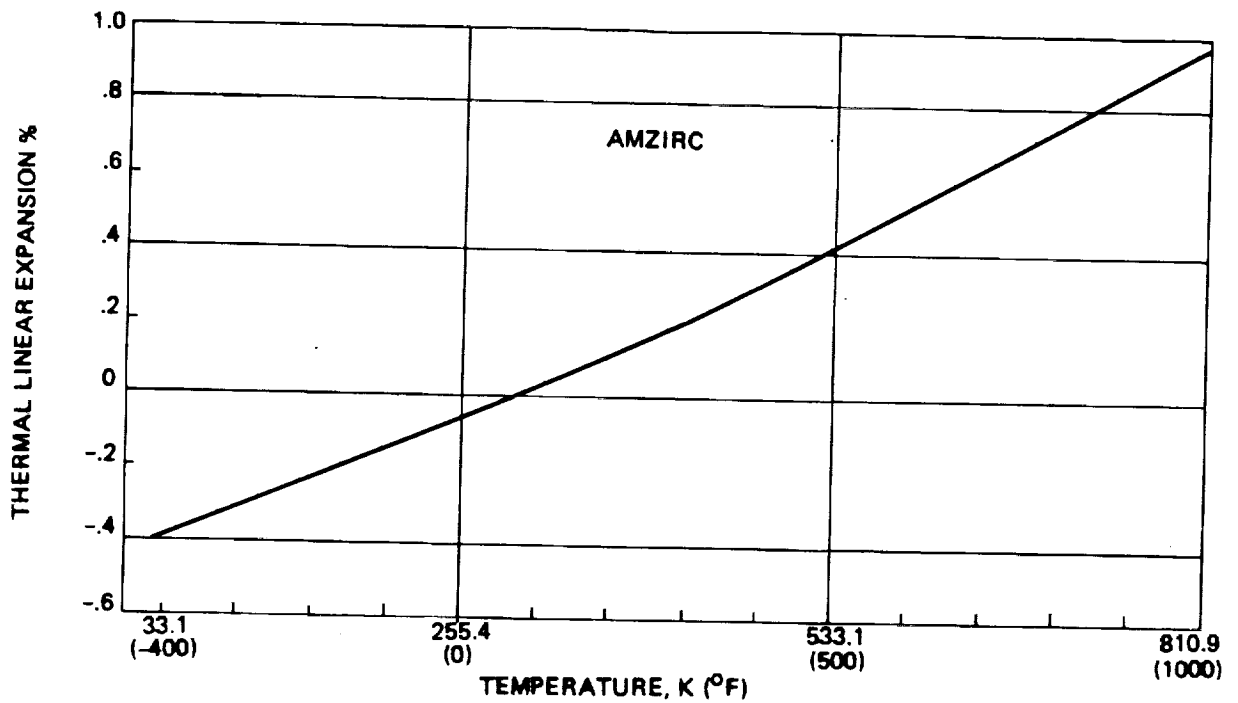


Figure 2 Thermal Linear Expansion vs Temperature for Amzirc

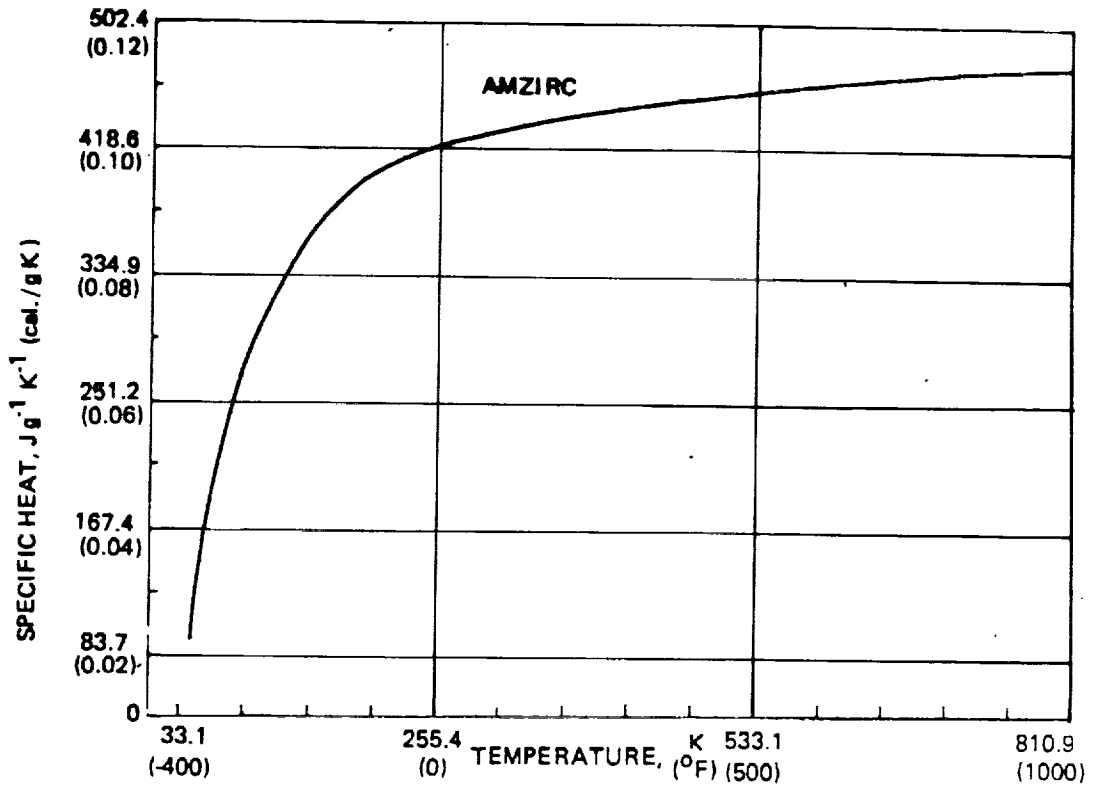


Figure 3 Specific Heat vs Temperature for Amzirc

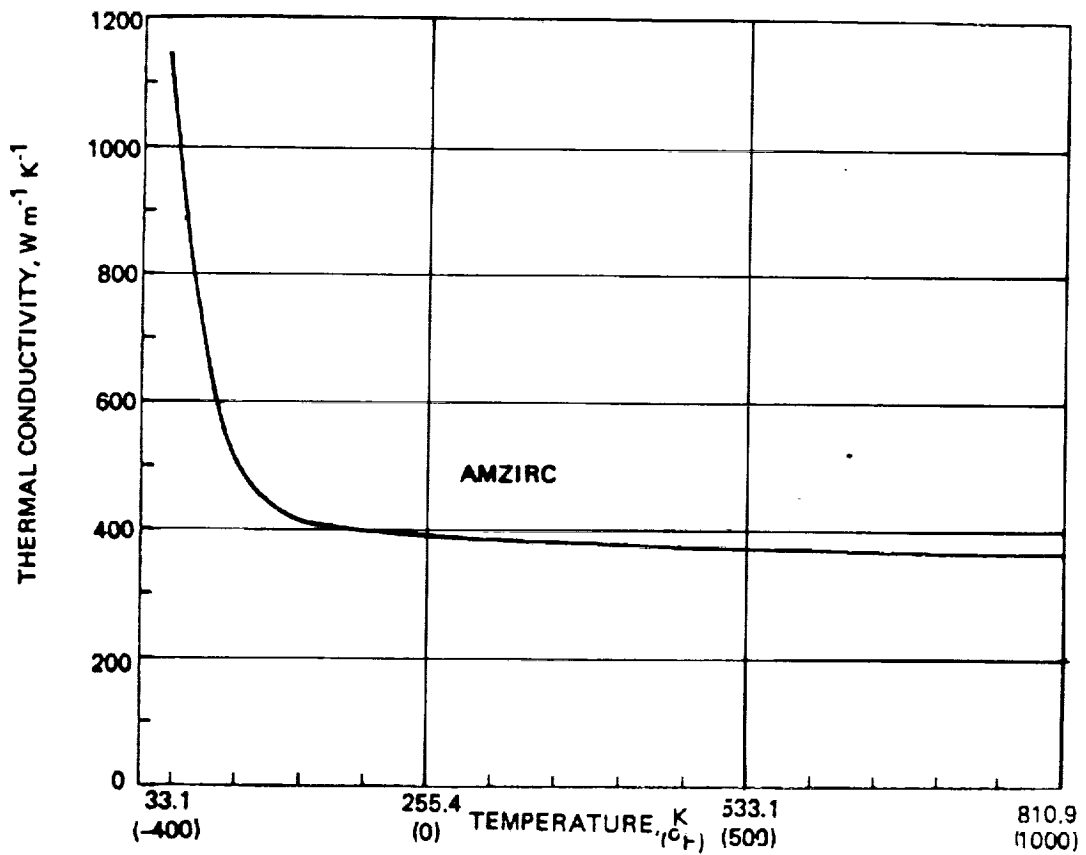


Figure 4 Thermal Conductivity vs Temperature for Amzirc

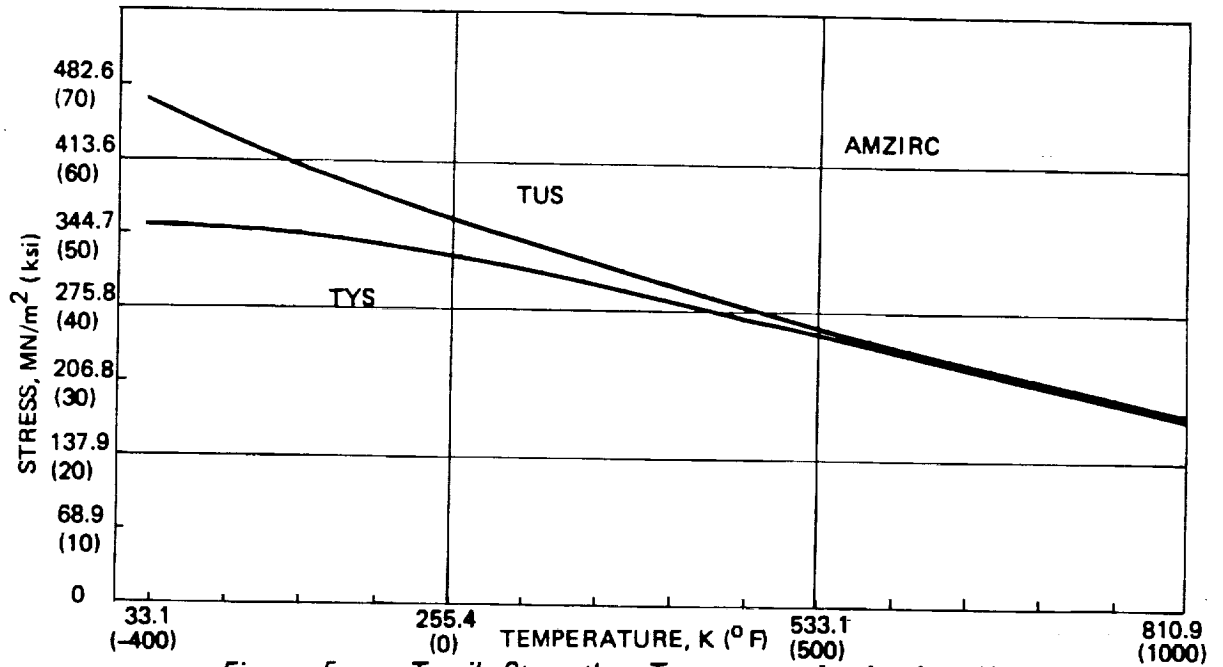


Figure 5 Tensile Strength vs Temperature for Amzirc - Half Hard

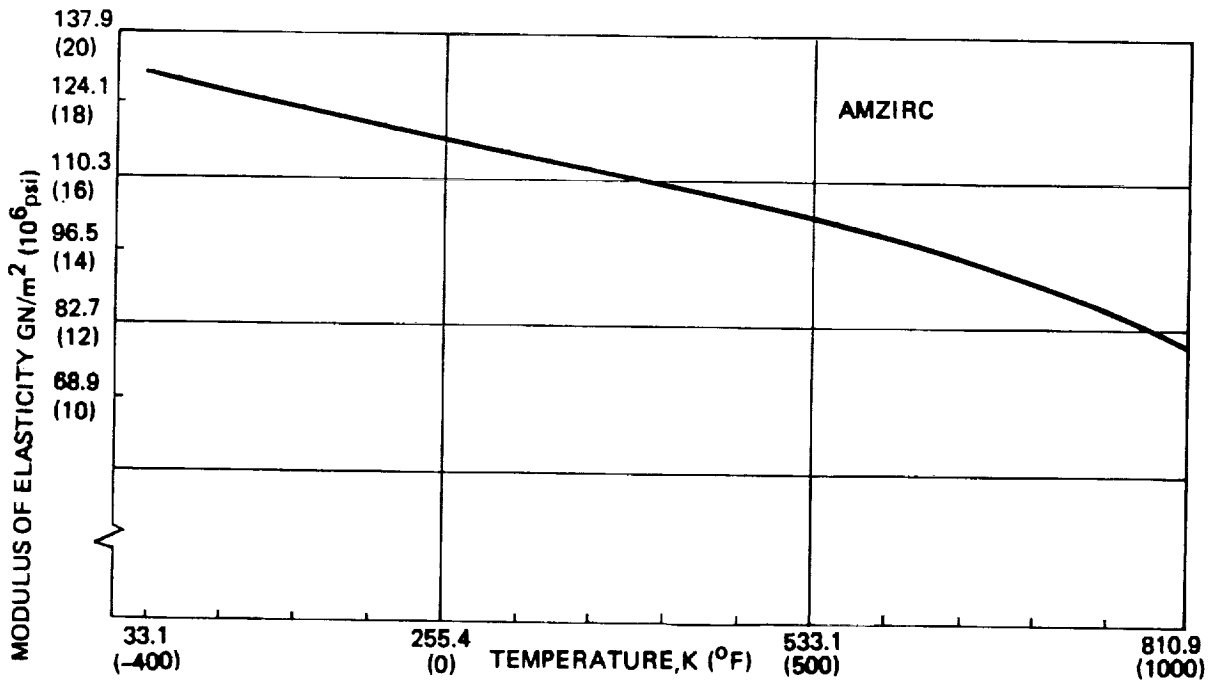


Figure 6 Modulus of Elasticity vs Temperature for Amzirc

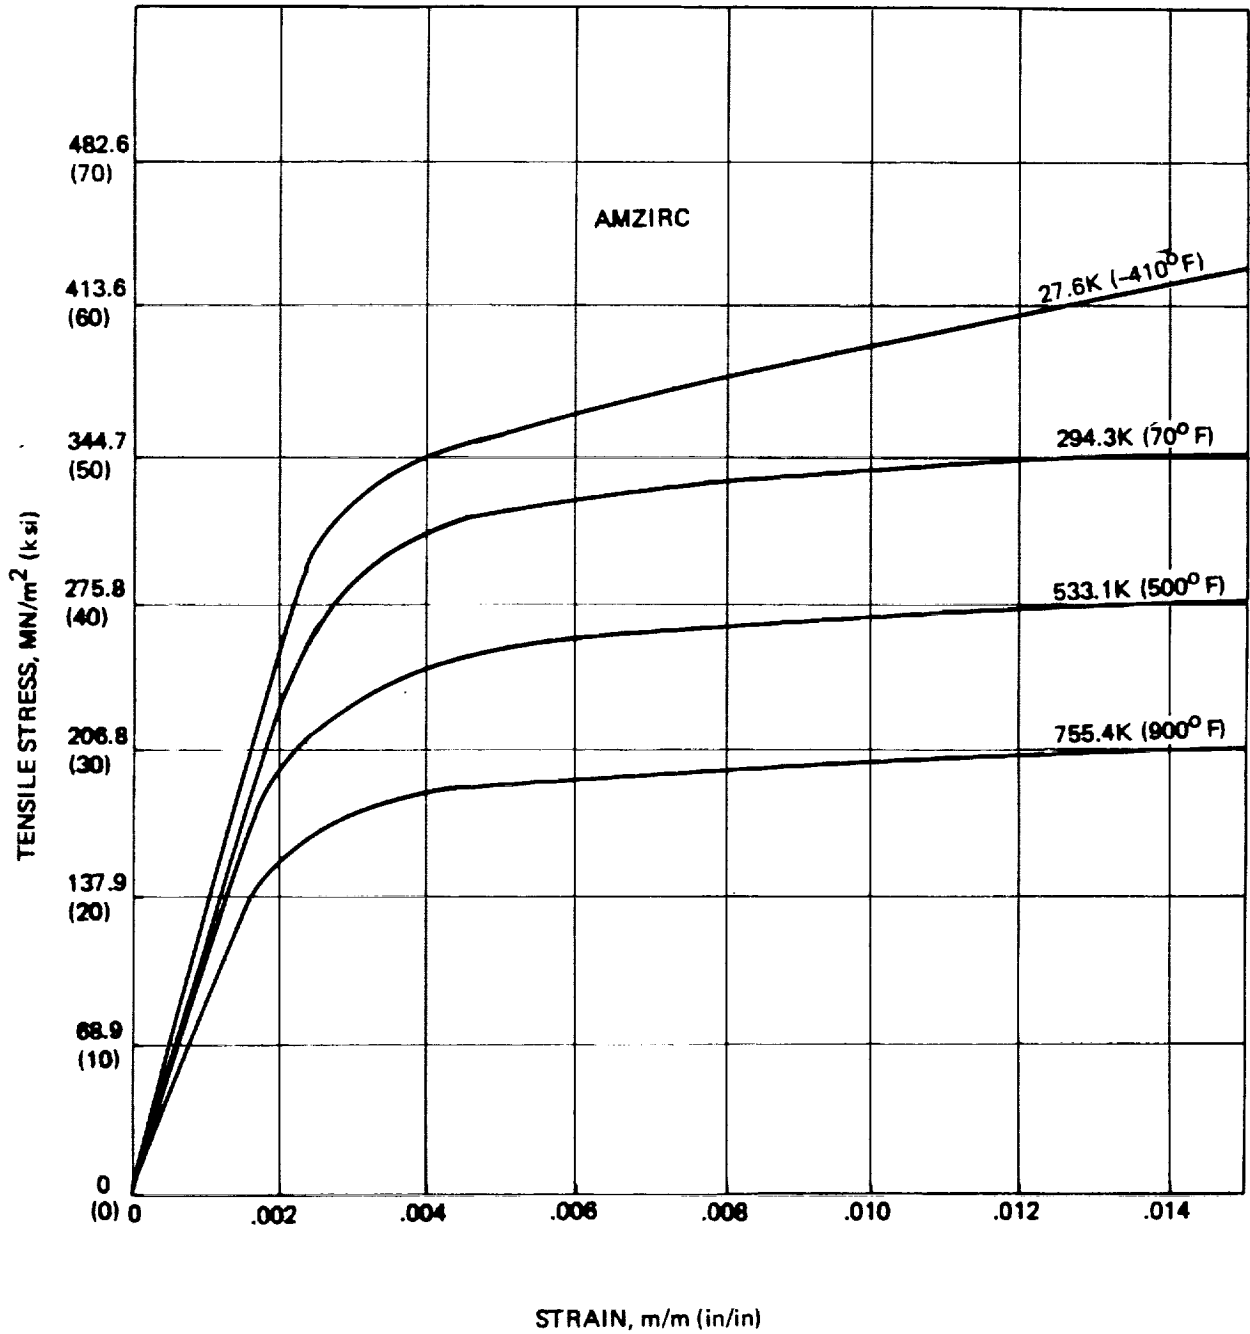


Figure 7 Typical Tensile Stress-Strain Curves for Amzirc-Half Hard Condition

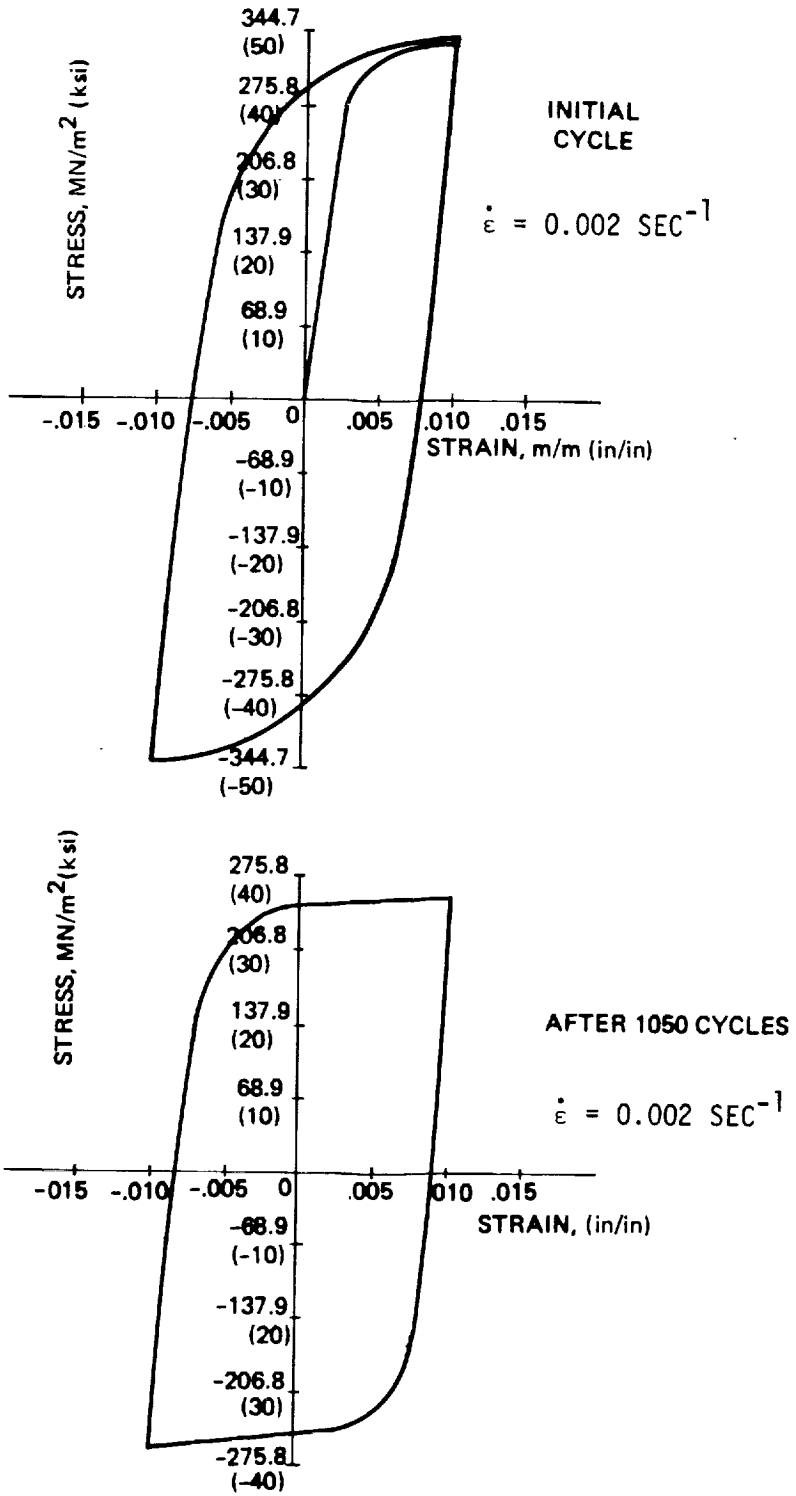


Figure 8 Room Temperature Cyclic Stress-Strain Curves for Amzirc-Half Hard Condition

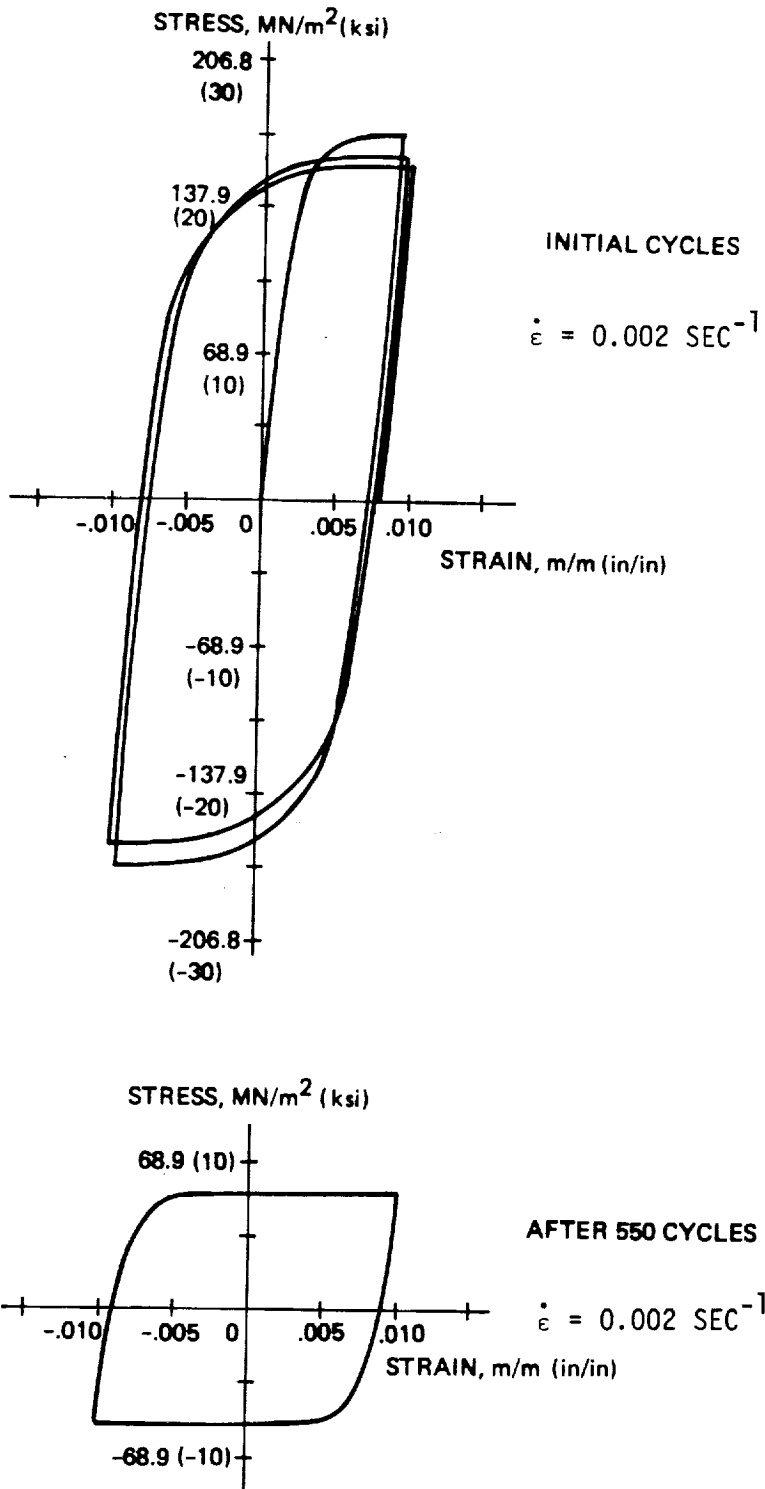


Figure 9 810.9K (1000°F) Cyclic Stress-Strain Curves for Amzirc-Half Hard Condition

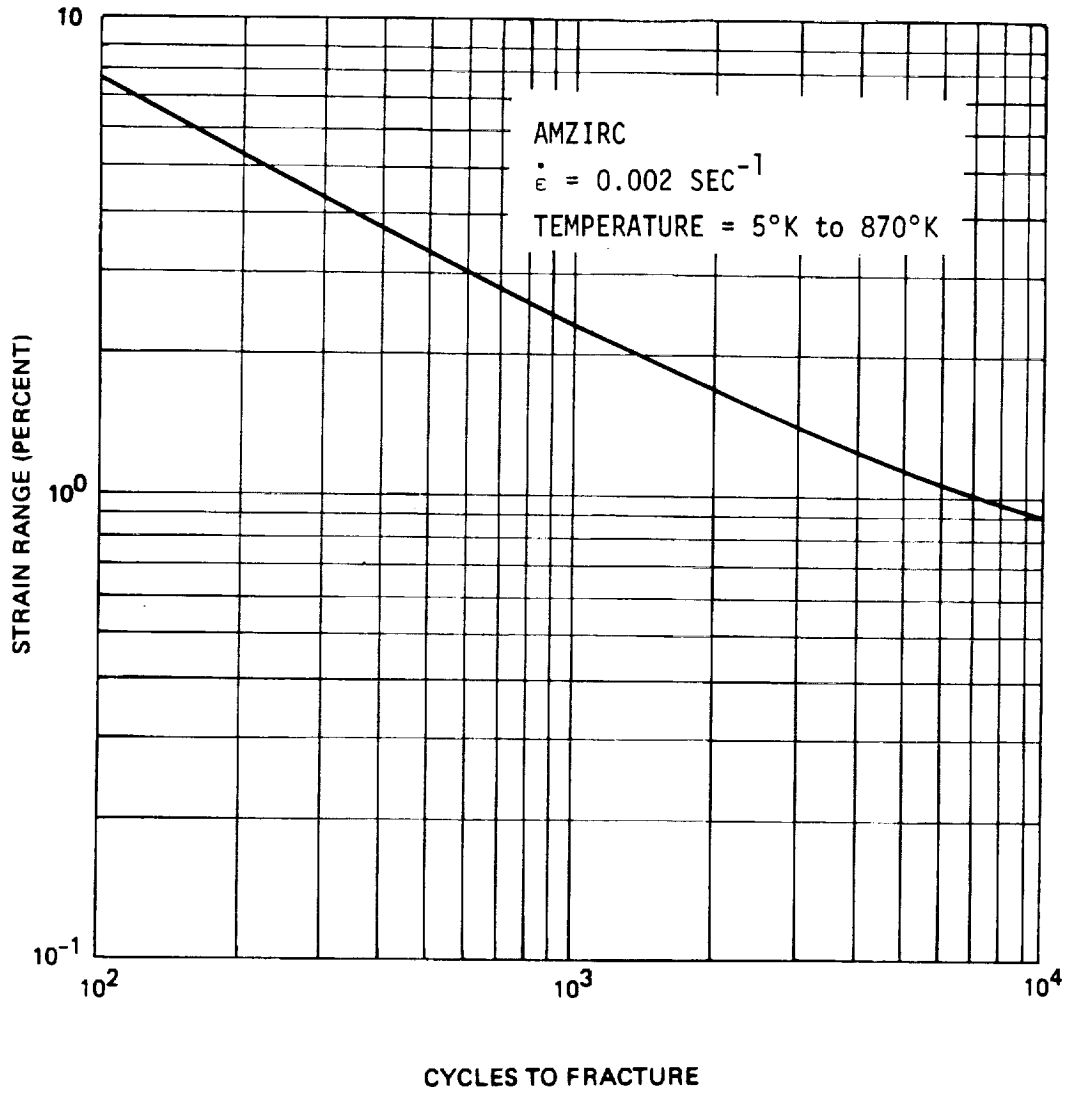


Figure 10 Typical Low-Cycle Fatigue Life of Amzirc - Half Hard Condition

2.2 NARloy - Z*

General Information

NARloy-Z is a copper base alloy containing a nominal 3-percent silver and .5 percent zirconium. The silver-zirconium-copper alloy combines high electrical and thermal conductivity with moderate strength retention at high temperatures. The alloy is strengthened by heat treatment and is normally used in the solution annealed and aged condition.

* Rockwell International' Inc. - Tradename for a silver-zirconium-copper alloy

Room Temperature Properties	
Material	NARloy Z
Condition	Solution Treated and Aged
Mechanical Properties	
Tensile Ultimate, MN/m ² (ksi)	314 (45.6)
Tensile Yield, MN/m ² (ksi) 0.2% Offset	192 (27.9)
Elongation, %	31
Reduction of Area, %	54
Modulus of Elasticity, GN/m ² (10 ⁶ psi)	127 (18.5)
Poisson's Ratio	.34
Physical Properties	
Density, kg/m ³ (lb/in ³)	9134 (.330)
Specific Heat, J kg ⁻¹ K ⁻¹ (cal/g/K)	373 (.089)
Thermal Conductivity, W m ⁻¹ K ⁻¹	295
Coefficient of Thermal Expansion, 294 to 533K , 10 ⁻⁶ [m/m] K ⁻¹ 70°F to 500°F, 10 ⁻⁶ (in/in/°F)	17.2 (9.5)

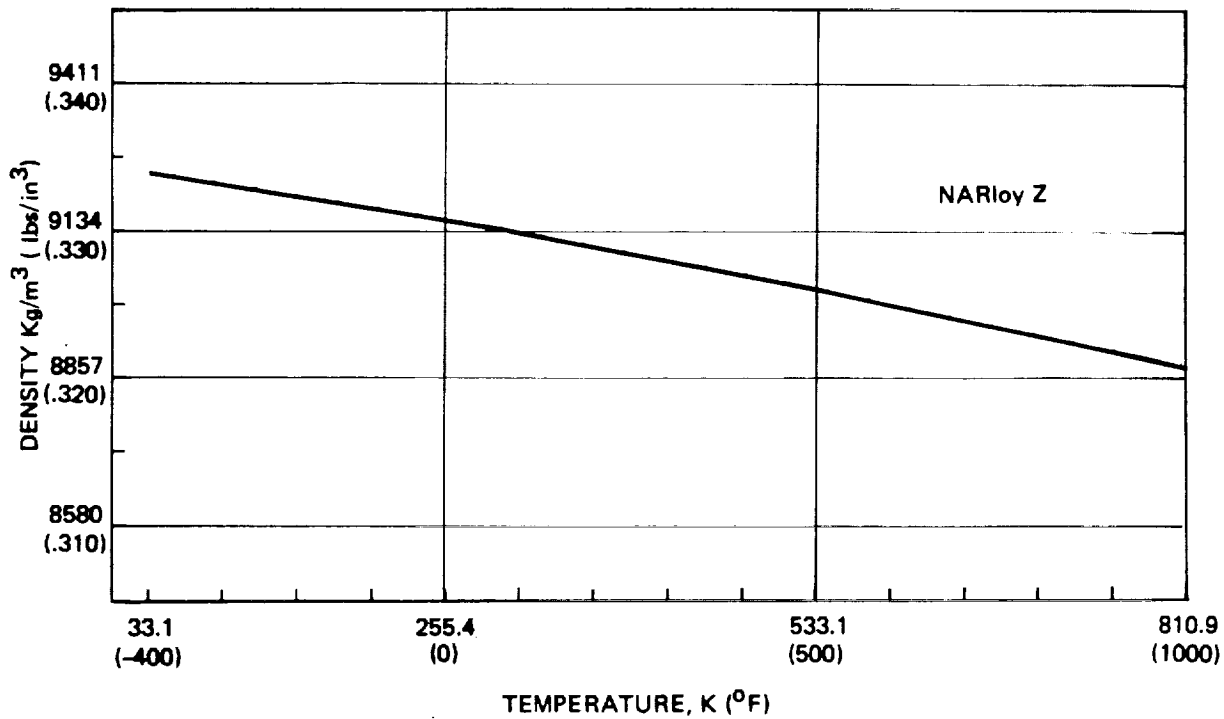


Figure 11 Density vs Temperature for NARloy Z

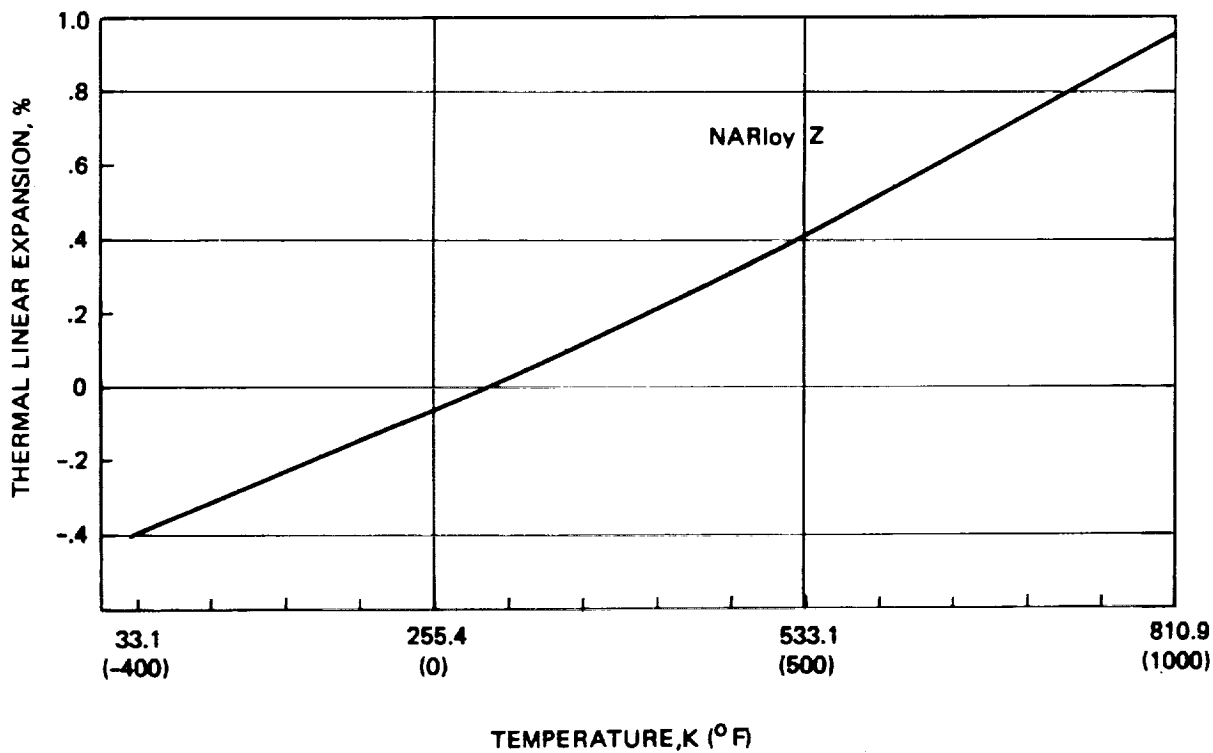


Figure 12 Thermal Linear Expansion vs Temperature for NARloy Z

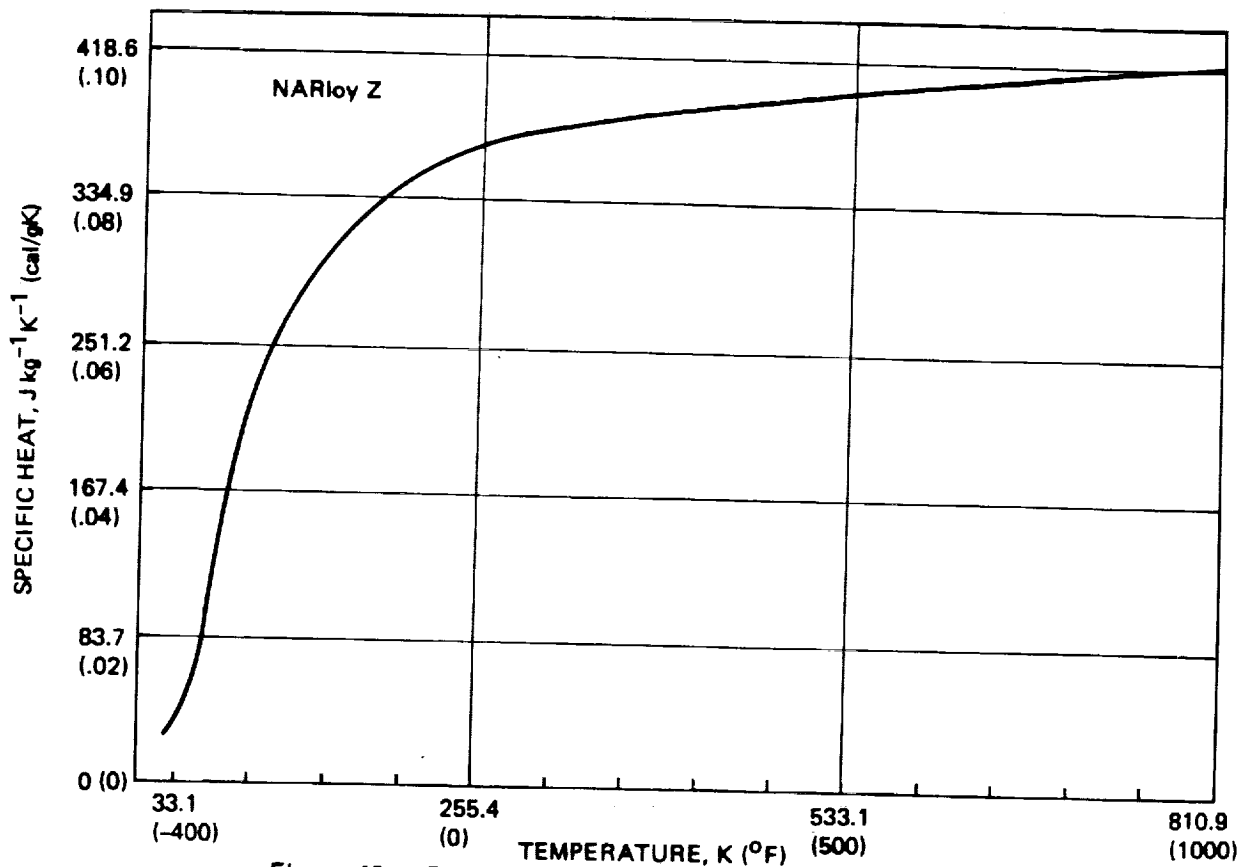


Figure 13 Specific Heat vs Temperature for NARloy Z

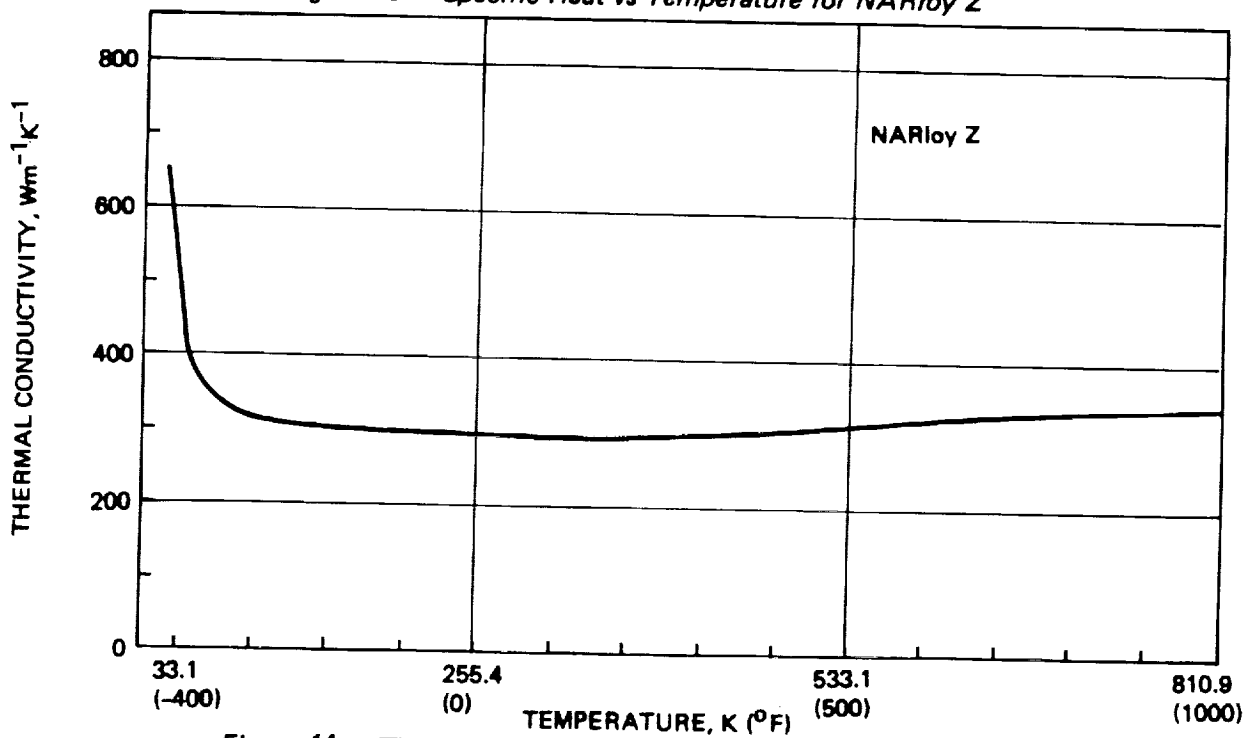


Figure 14 Thermal Conductivity vs Temperature for NARloy Z

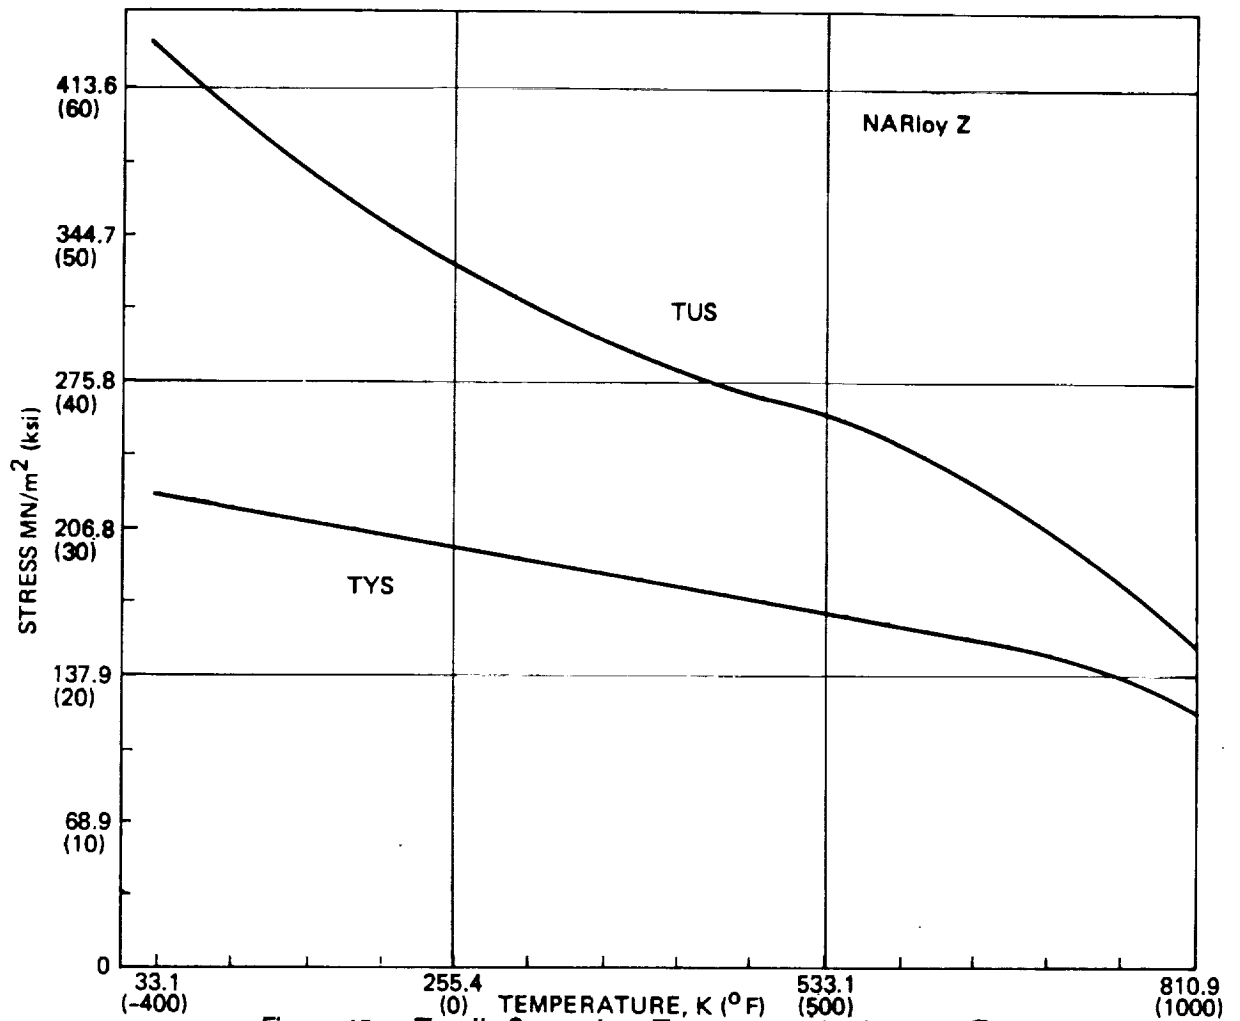


Figure 15 Tensile Strength vs Temperature for NARloy Z

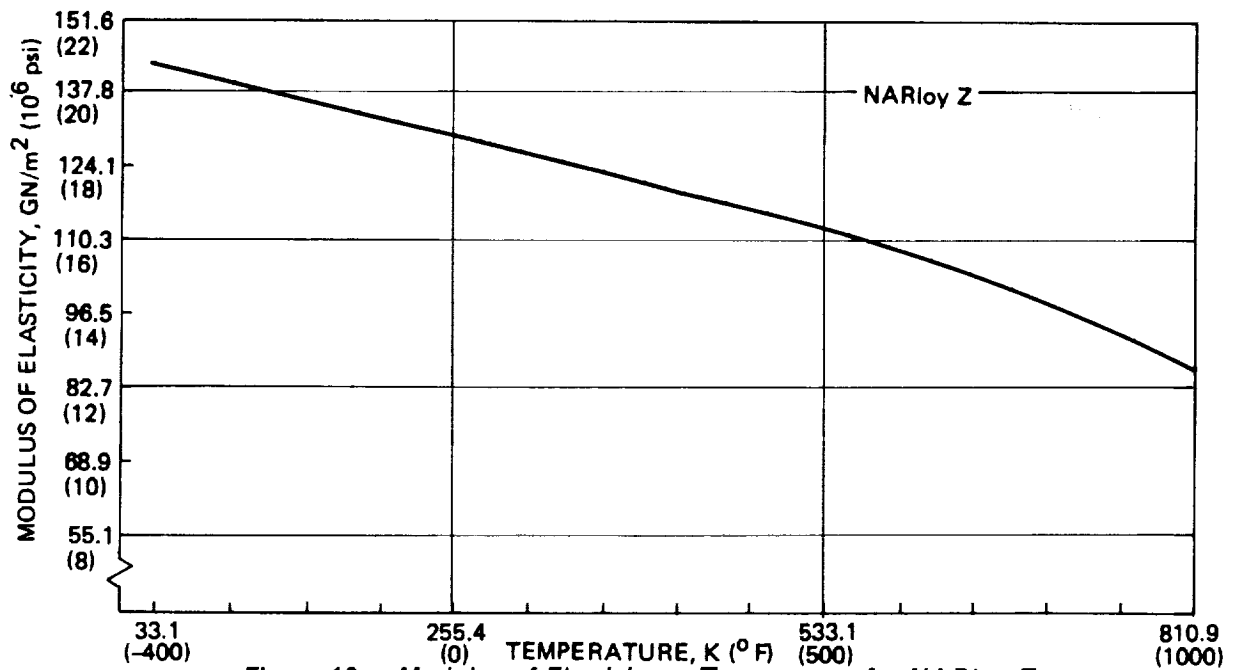


Figure 16 Modulus of Elasticity vs Temperature for NARloy Z

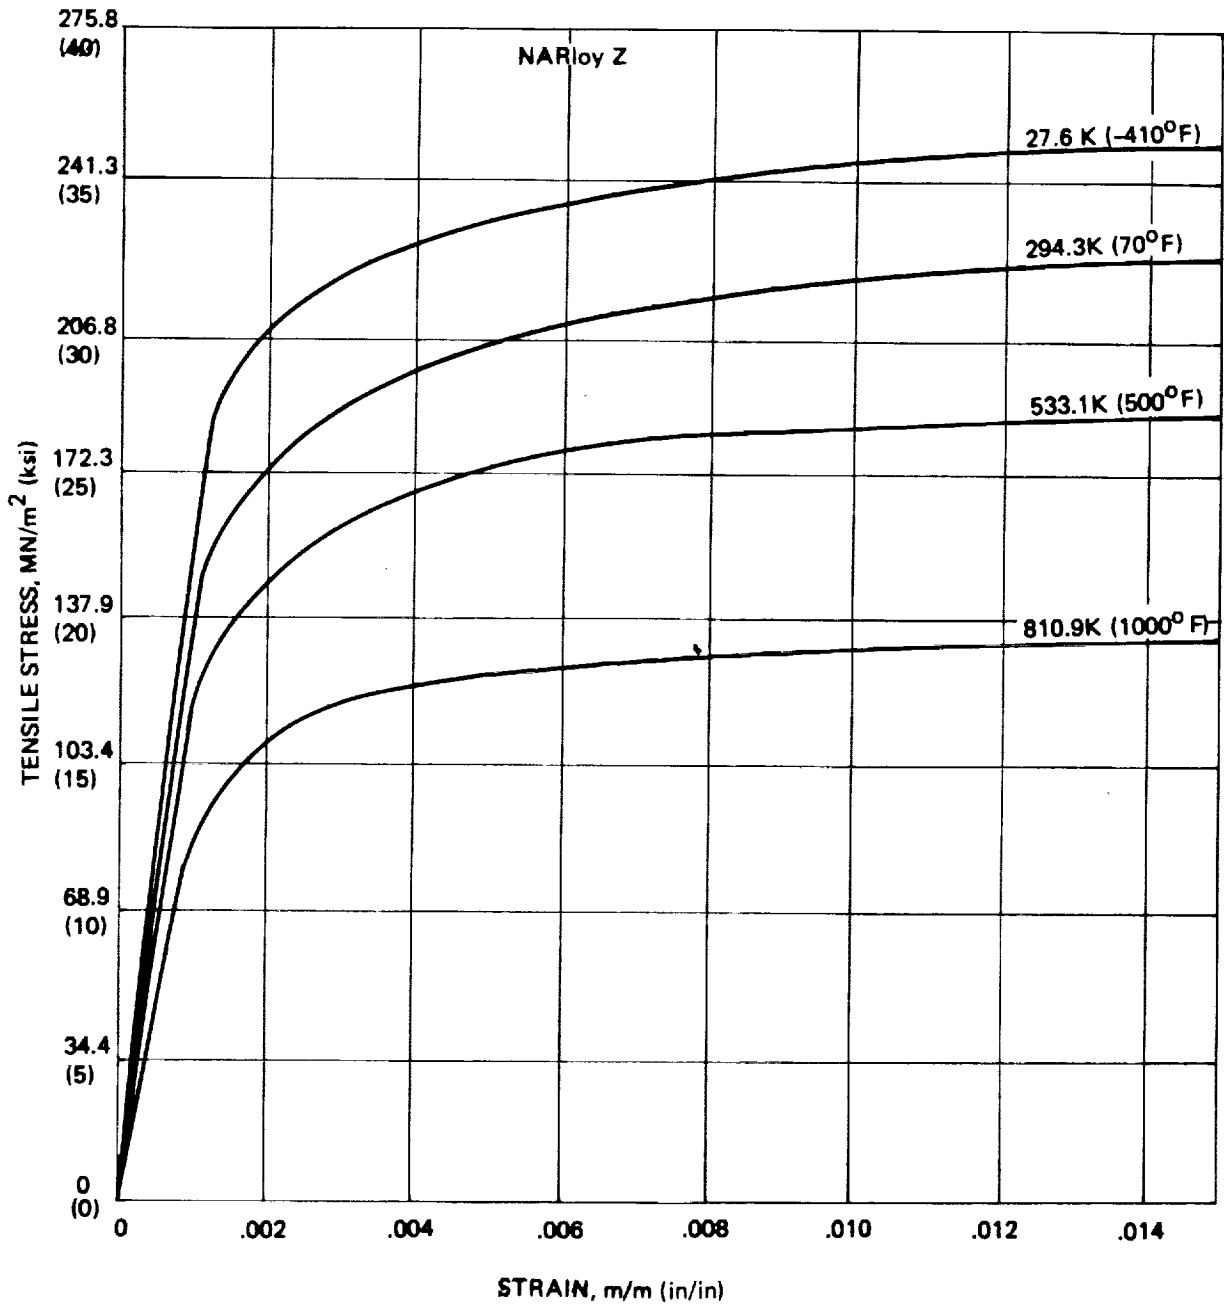


Figure 17 Typical Stress-Strain Curves for NARloy Z

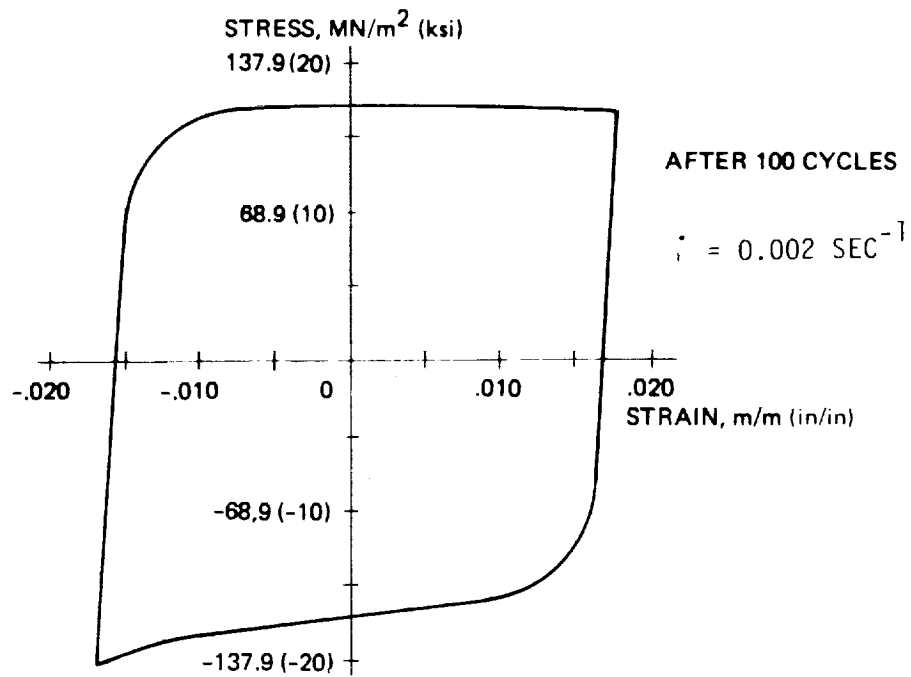
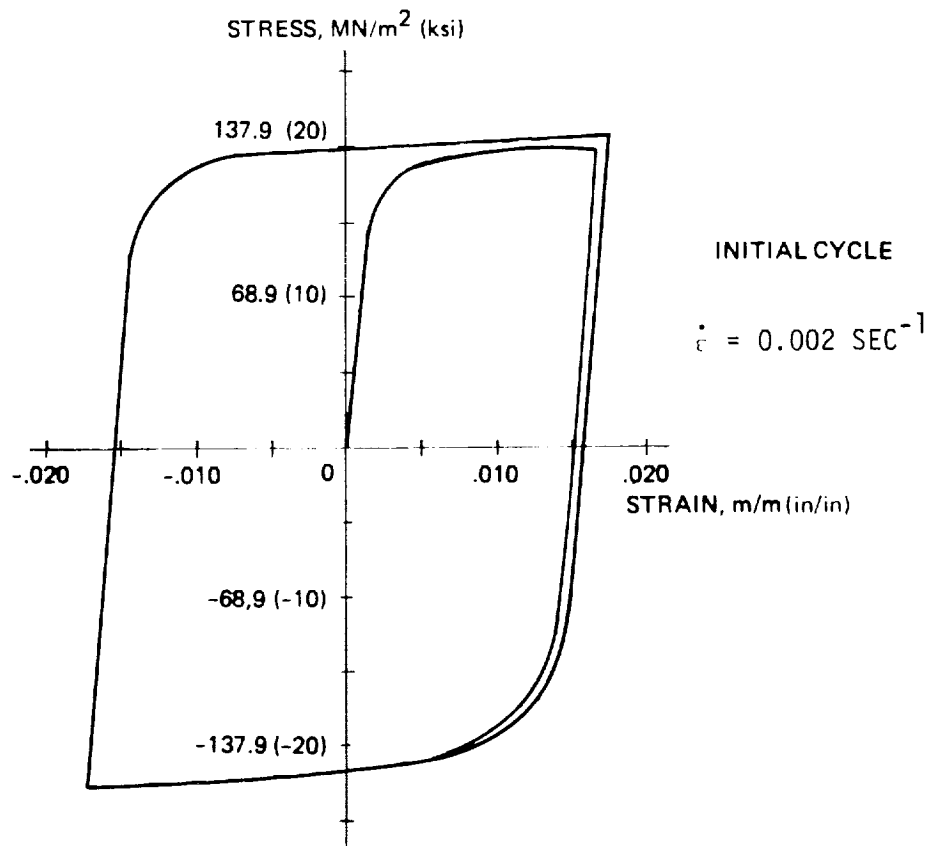


Figure 1^a 810.9K (1000°F) Cyclic Stress Strain Curves for NARloy Z

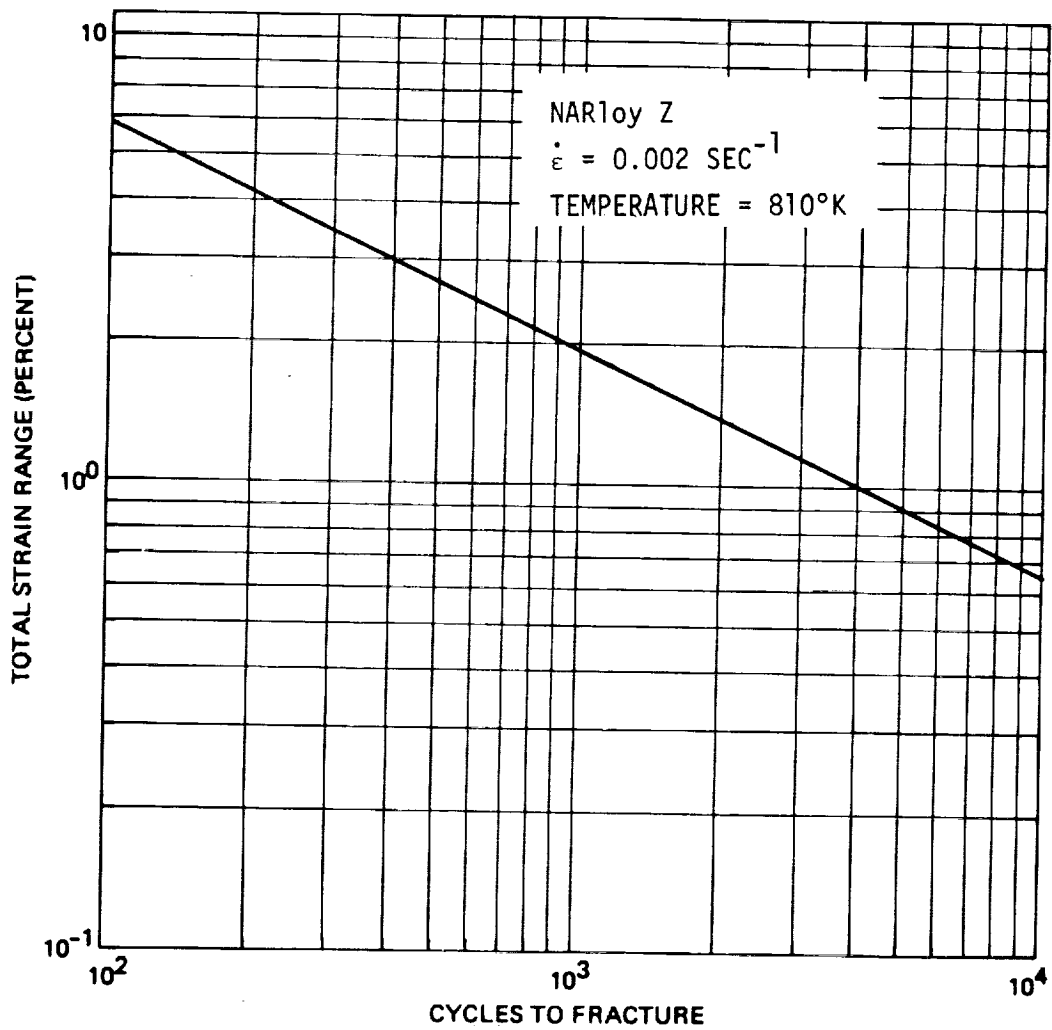


Figure 19 Typical Low-Cycle Fatigue Life of NARloy Z

2.3 *OFHC Copper

General Information

OFHC copper an oxygen free grade of essentially pure copper. The material has very high electrical and thermal conductivity combined with a high melting point.

The material is readily hot or cold worked and the strength of the material increases with the amount of working. In the annealed condition the material has a relatively low strength.

At cryogenic temperatures the material exhibits high ductility.

*American Metal Climax, Inc. – Tradename for an Oxygen-Free High-Conductivity copper.

Room Temperature Properties			
Material	OFHC Copper		
Condition	Annealed	Quarter Hard	Half Hard
Mechanical properties			
Tensile Ultimate, MN/m ² (ksi)	202 (32)	330 (48)	344 (50)
Tensile Yield, MN/m ² (ksi) 0.2% Offset	53 (7.7)	310 (45)	317 (46)
Elongation, %	45	20	25
Reduction of Area, %	80	65	80
Modulus of Elasticity, GN/m ² (psi 10 ⁶)	114 (16.6)	114 (16.6)	114 (16.6)
Poisson's Ratio	.33	.33	.33
Physical Properties			
Density, kg/m ³ (lb/in ³)	8913 (.322)		
Specific Heat, J kg ⁻¹ K ⁻¹ (cal/g/K)	385 (.092)		
Thermal Conductivity, Wm ⁻¹ K ⁻¹	390		
Coefficient of Thermal Expansion,			
294K to 533K , 10 ⁻⁶ [m/m] K ⁻¹	17.2		
70°F to 500°F , 10 ⁻⁶ (in/in/°F)	(9.5)		

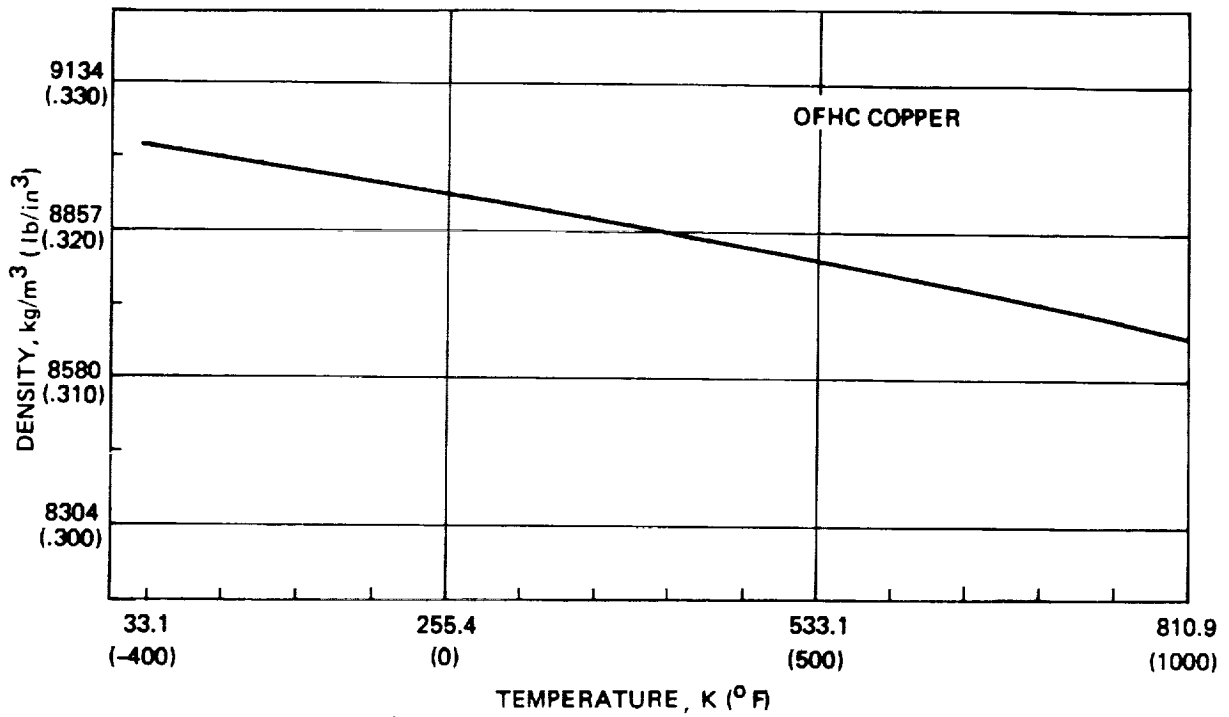


Figure 20 Density vs Temperature for OFHC Copper

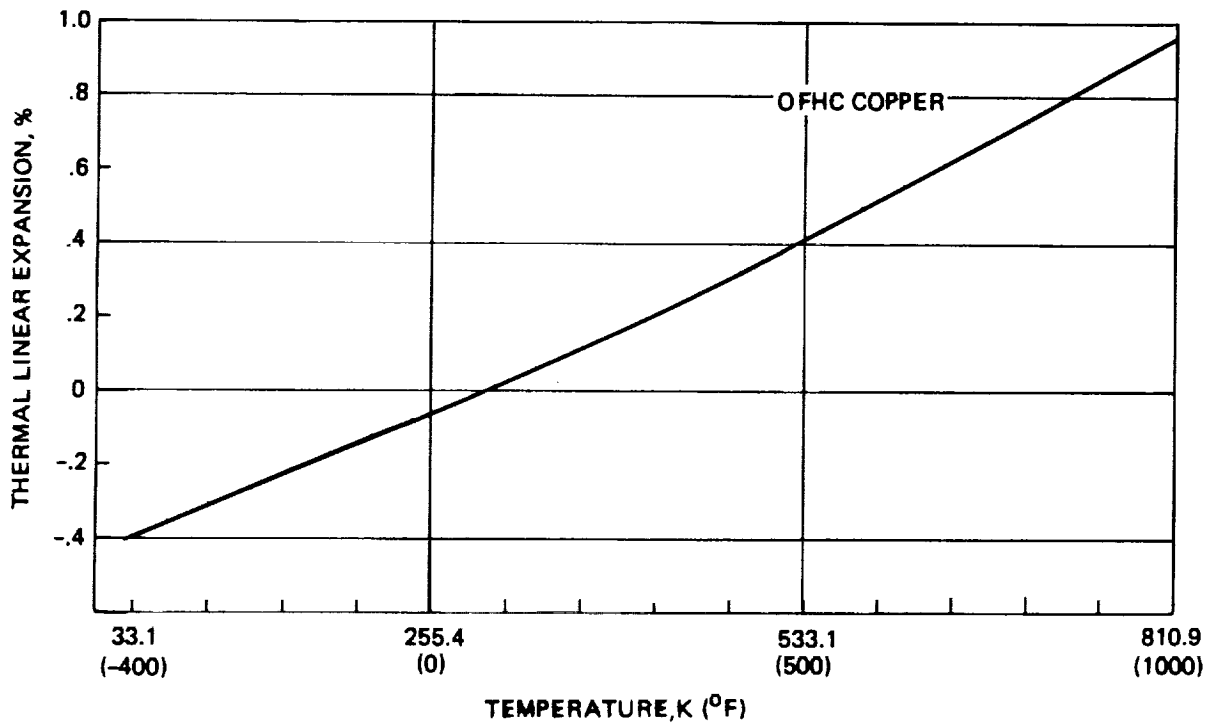


Figure 21 Thermal Linear Expansion vs Temperature for OFHC Copper

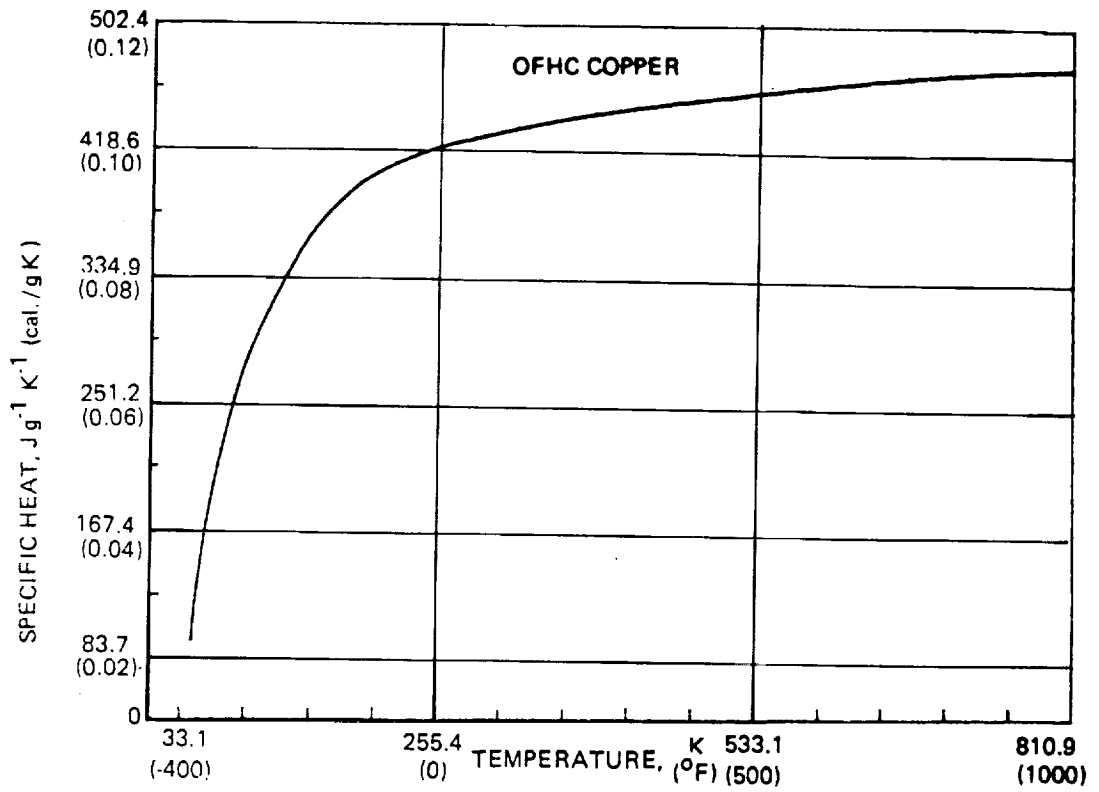


Figure 22. Specific Heat vs. Temperature for OFHC Copper

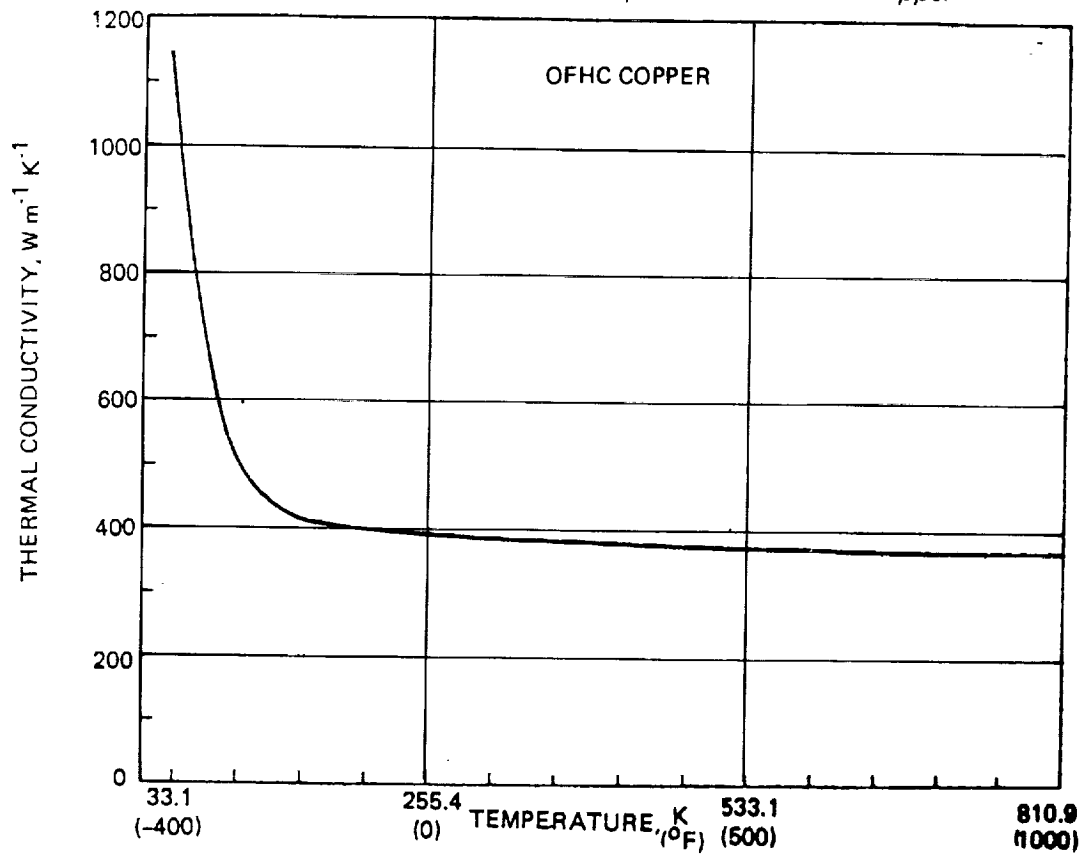


Figure 23 Thermal Conductivity vs Temperature for OFHC Copper

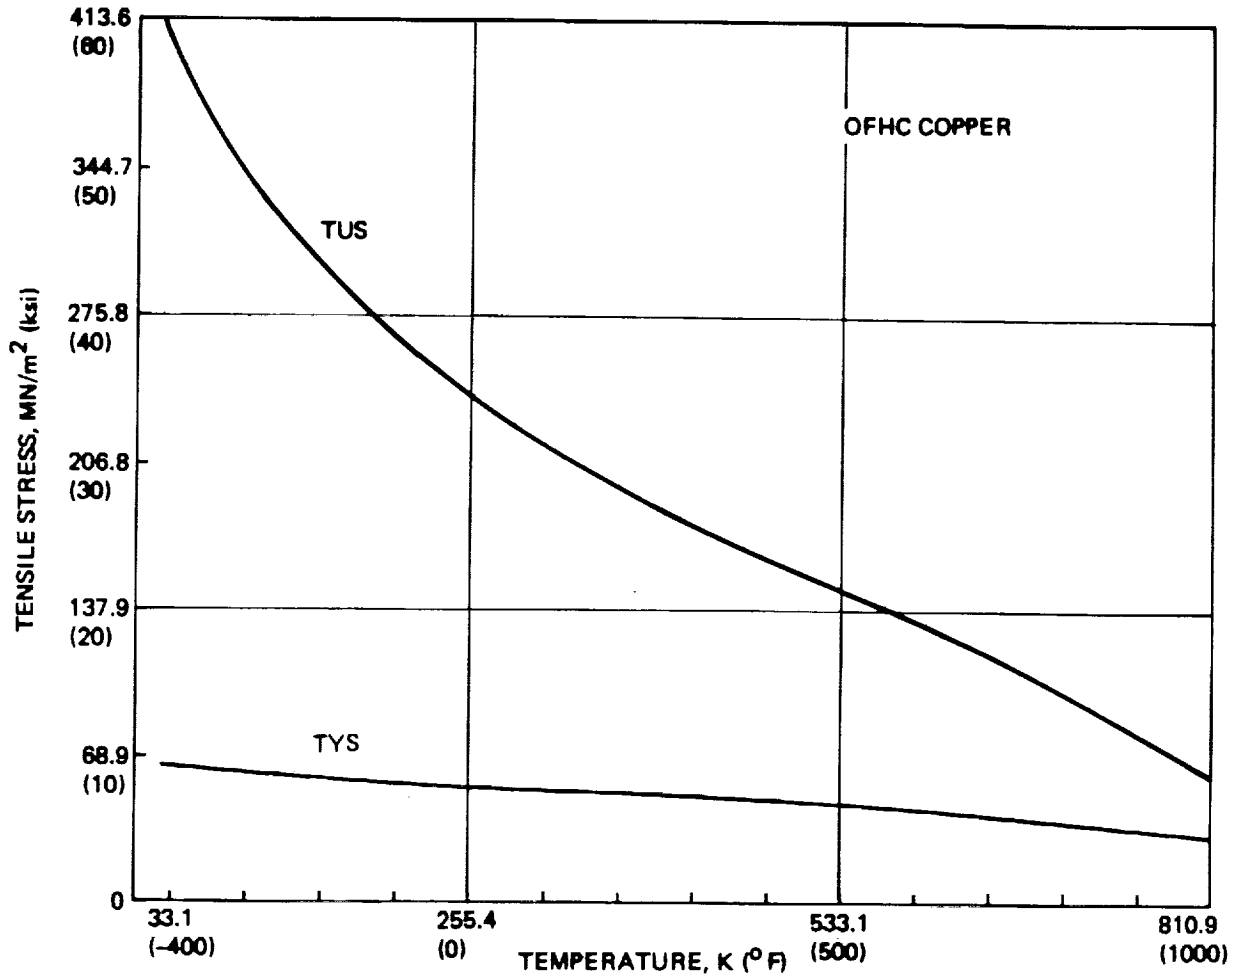


Figure 24 Tensile Strength vs Temperature for OFHC Copper Annealed Condition

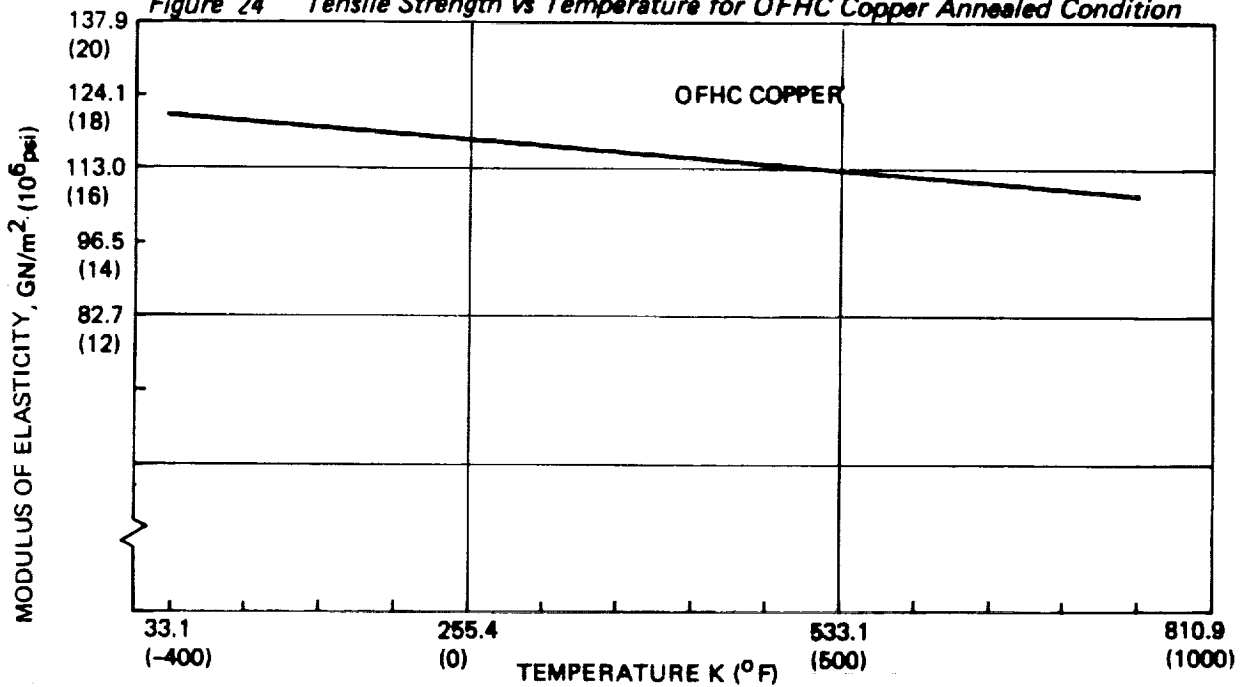


Figure 25 Modulus of Elasticity vs Temperature for OFHC Copper

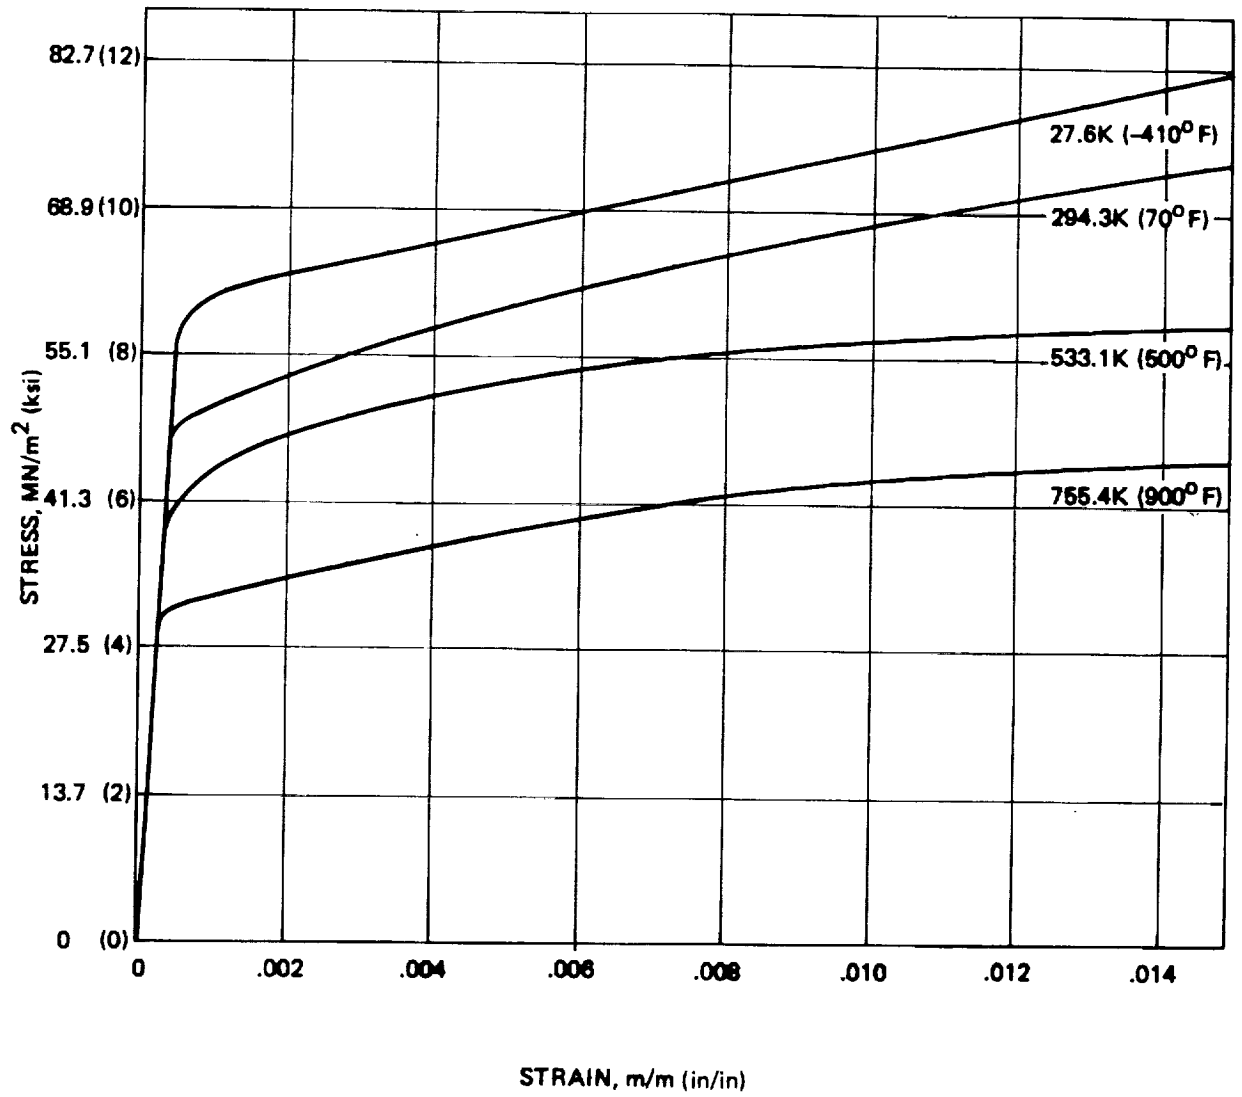


Figure 26 Typical Stress-Strain Curves for OFHC Copper Annealed Condition

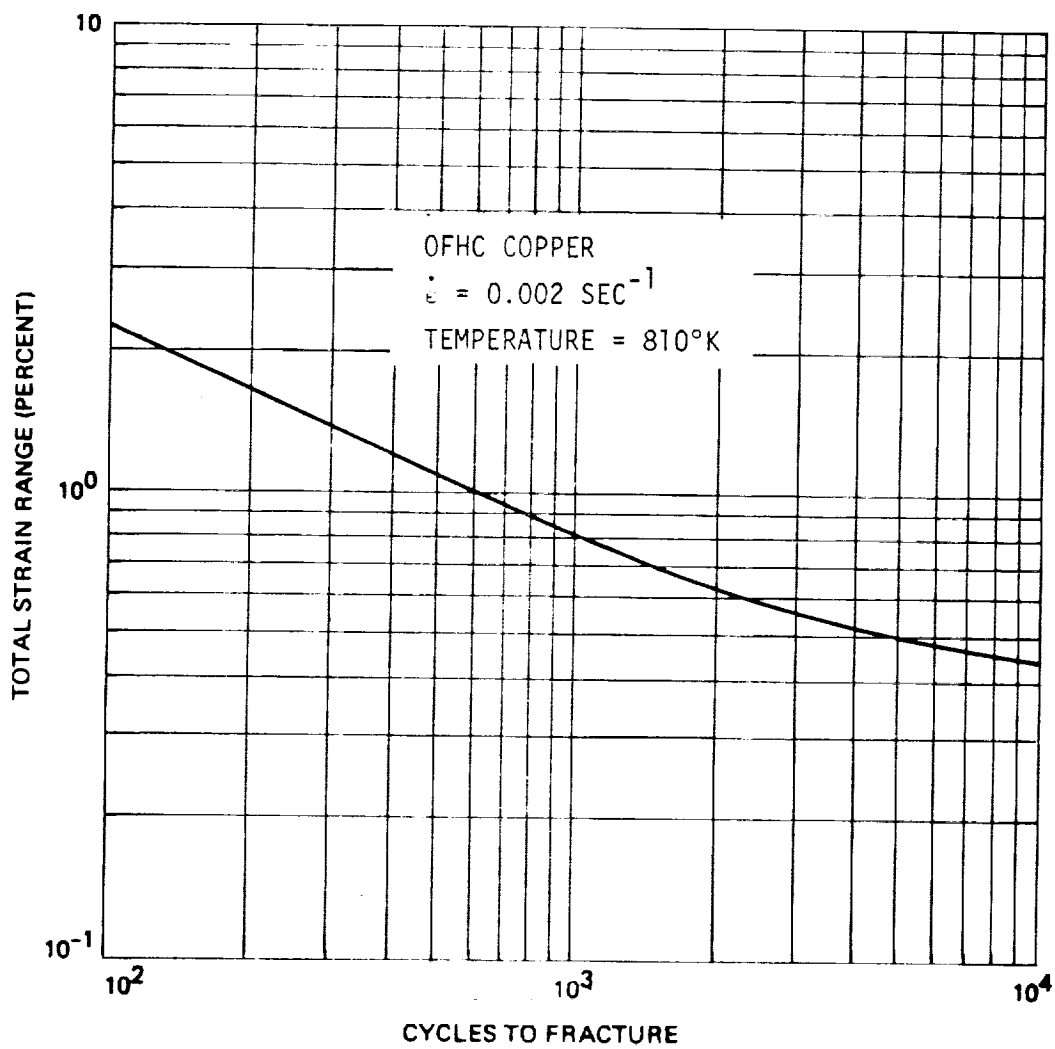


Figure 27 Typical Low-Cycle Fatigue Life of OFHC Copper Annealed Condition

2.4 Electroformed Copper

General Information

Electroformed copper is essentially pure copper obtained from an electro-chemical process. The technique involves the deposition of copper ions from a sulfate electrolyte onto a mandrel. The copper deposits may be bonded to or sandwiched between other deposits to provide integral heat sinks. The material can be joined to other materials using the same methods that would be employed for wrought copper. The electroformed copper has very high electrical and thermal conductivity, relatively low strengths, and is non-magnetic.

Room Temperature Properties	
Material:	Electroformed Copper
Condition:	As Formed
Mechanical Properties	
Tensile Ultimate, MN/m ² (ksi)	227 (33.0)
Tensile Yield, MN/m ² (ksi) 0.2% offset	107 (15.5)
Elongation, %	20
Reduction of Area, %	53
Modulus of Elasticity, GN/m ² (10 ⁶ psi)	114 (16.6)
Poisson's Ratio	.33
Physical Properties	
Density, kg/m ³ (lb/in. ³)	8913 (.322)
Specific Heat, J kg ⁻¹ K ⁻¹ (cal/g/K)	385 (.092)
Thermal Conductivity, W m ⁻¹ K ⁻¹	390
Coefficient of Thermal Expansion, 294K to 533K, 10 ⁻⁶ [m/m] K ⁻¹	17.2
70°F to 500°F, 10 ⁻⁶ (in./in.°F)	(9.5)

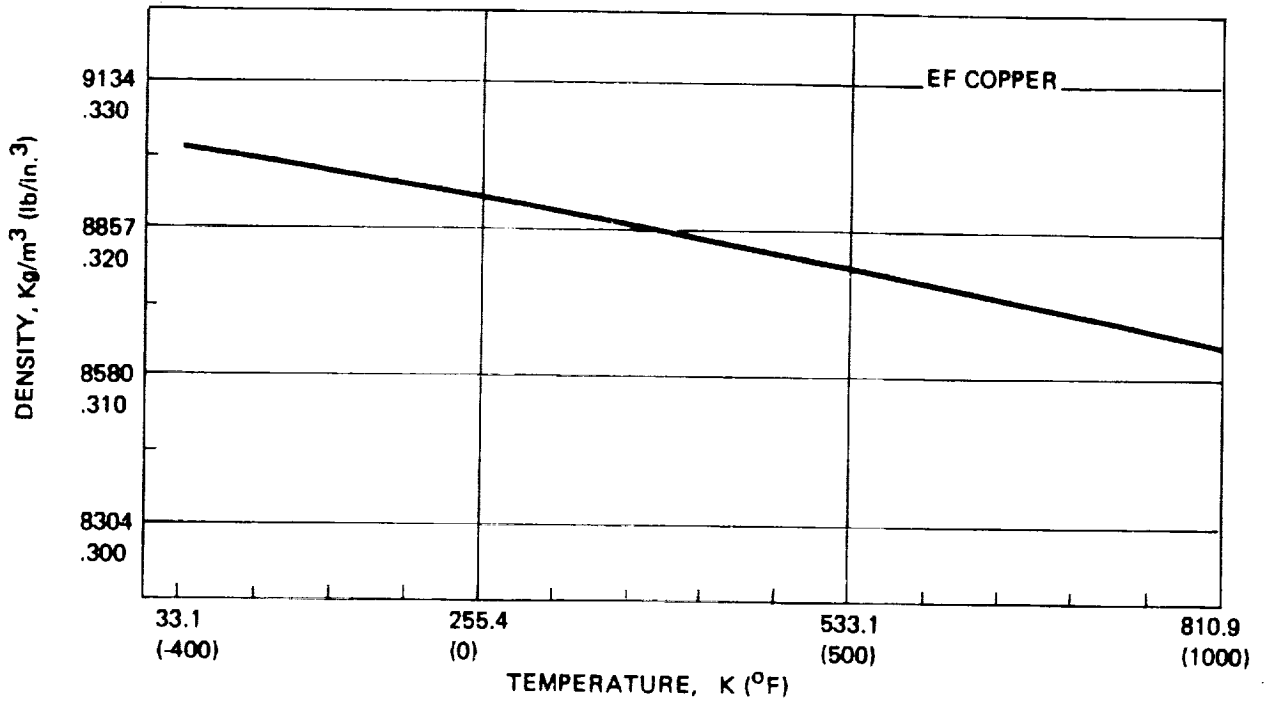


Figure 28 Density vs Temperature for Electroformed Copper

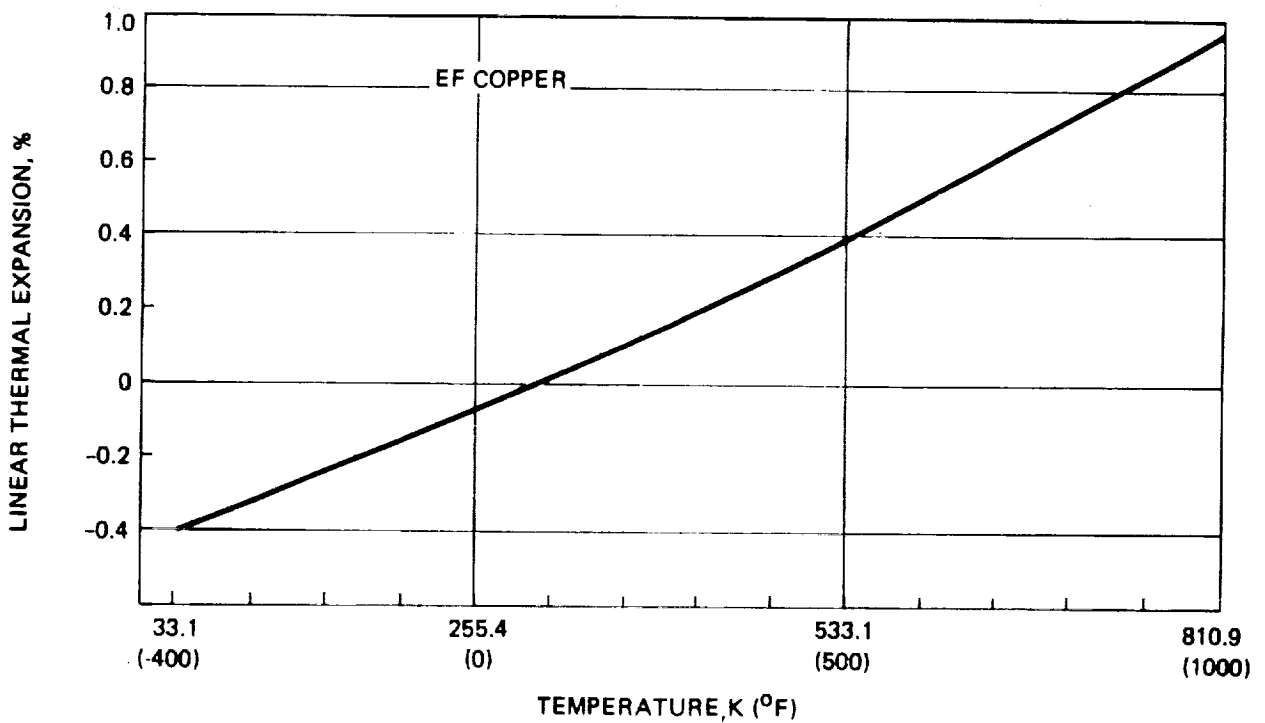


Figure 29 Thermal Linear Expansion vs. Temperature for Electroformed Copper

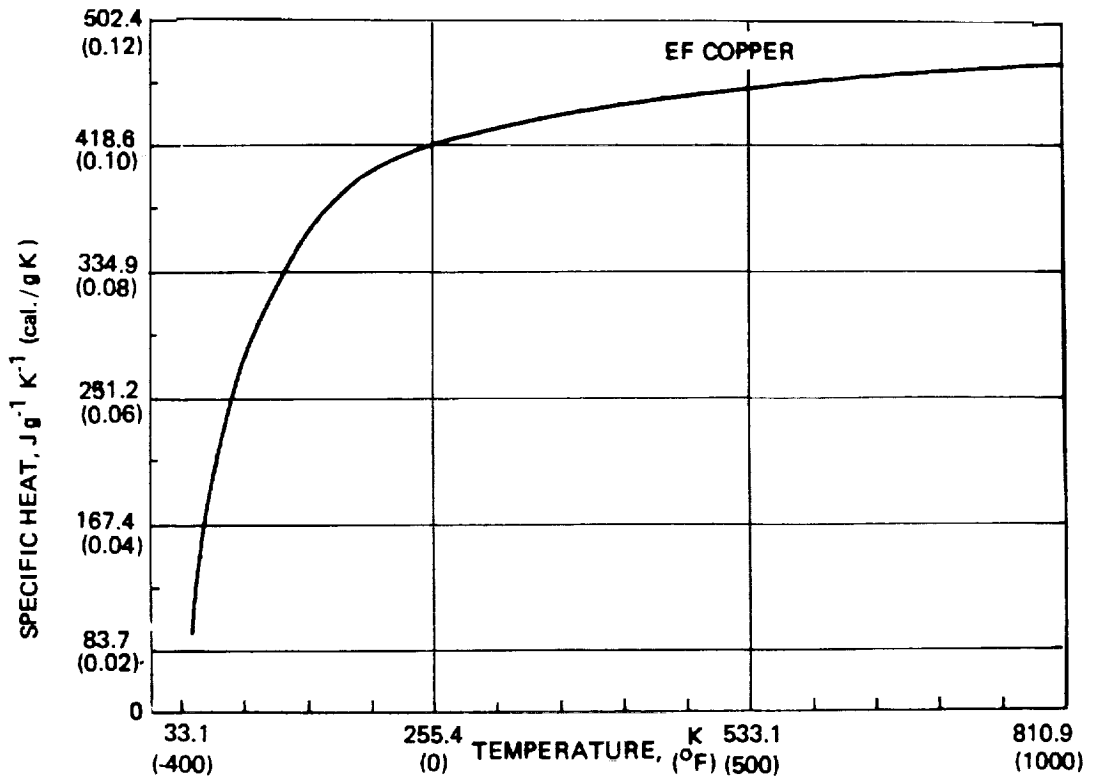


Figure 30 · Specific Heat vs. Temperature for Electroformed Copper

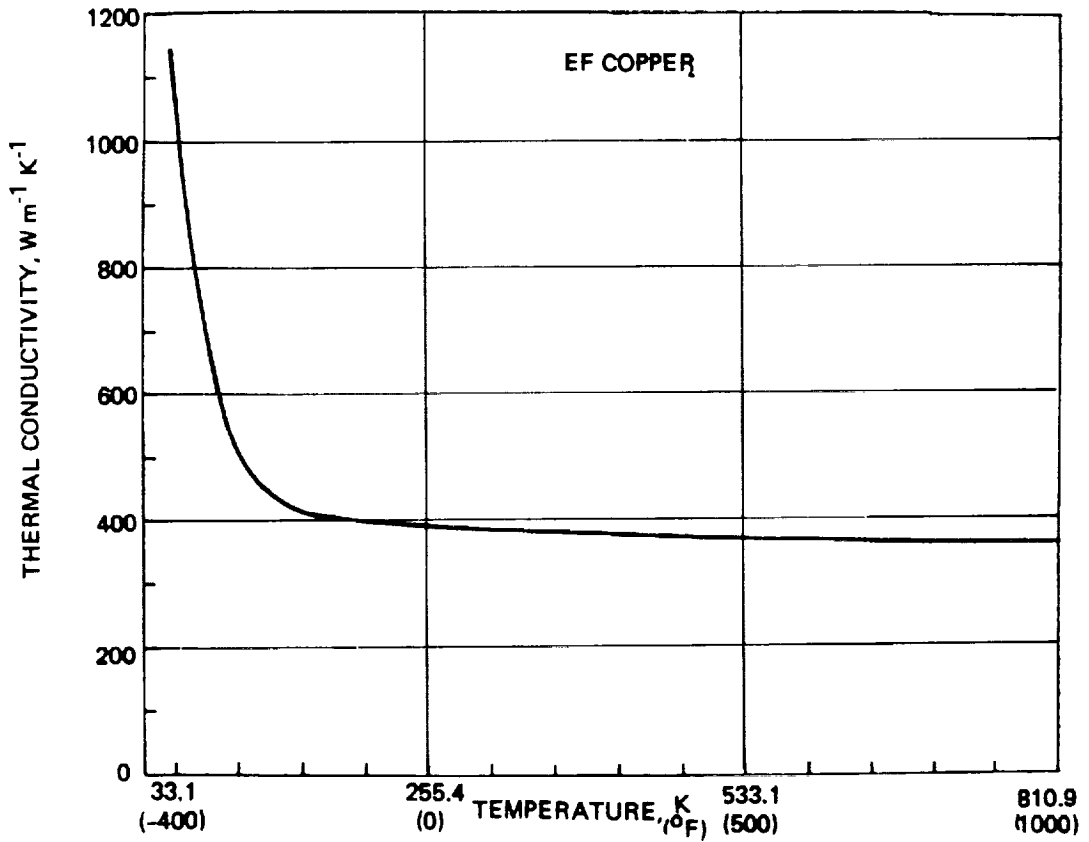


Figure 31 Thermal Conductivity vs. Temperature for Electroformed Copper

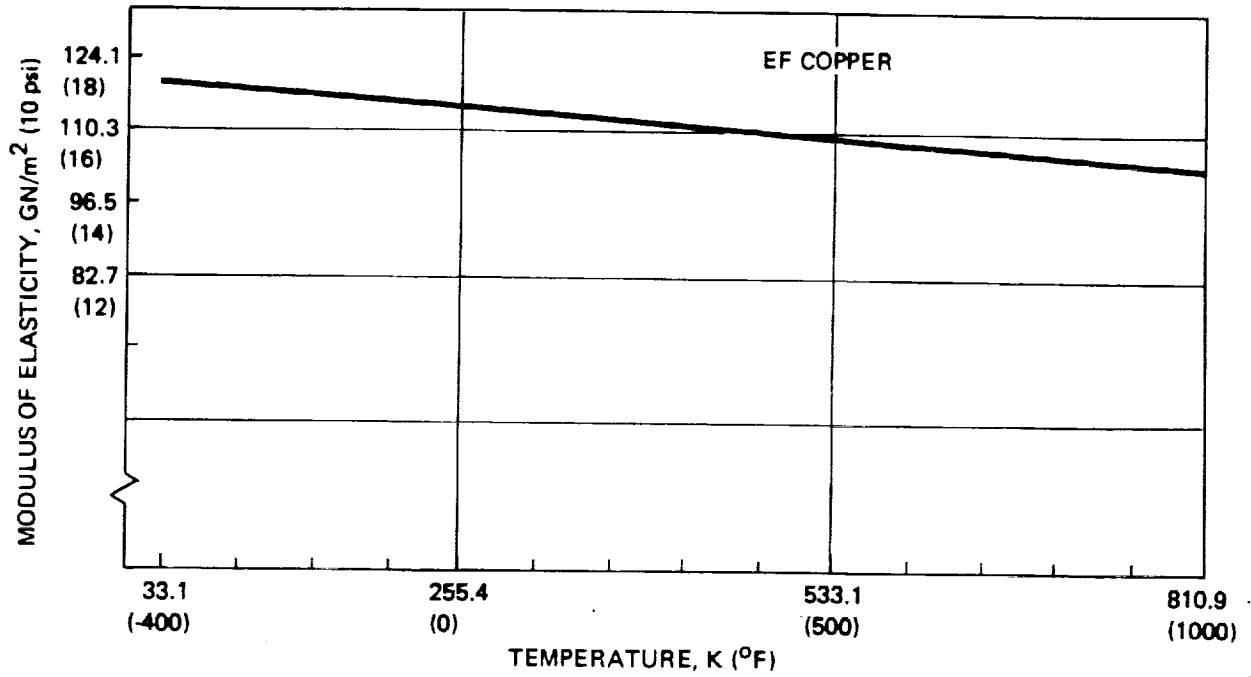


Figure 32 Modulus of Elasticity vs. Temperature for Electroformed Copper

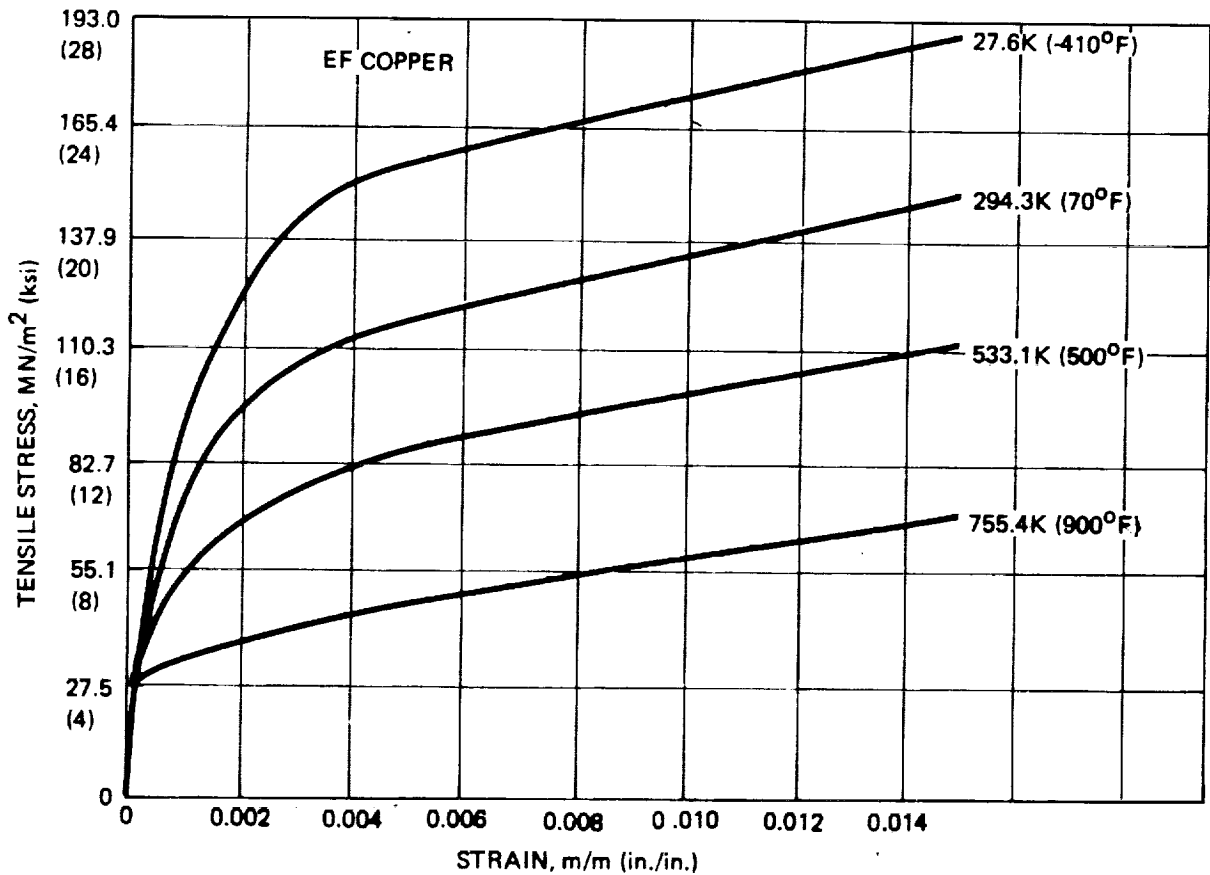


Figure 33 Typical Stress-Strain Curves for Electroformed Copper - As Formed Condition

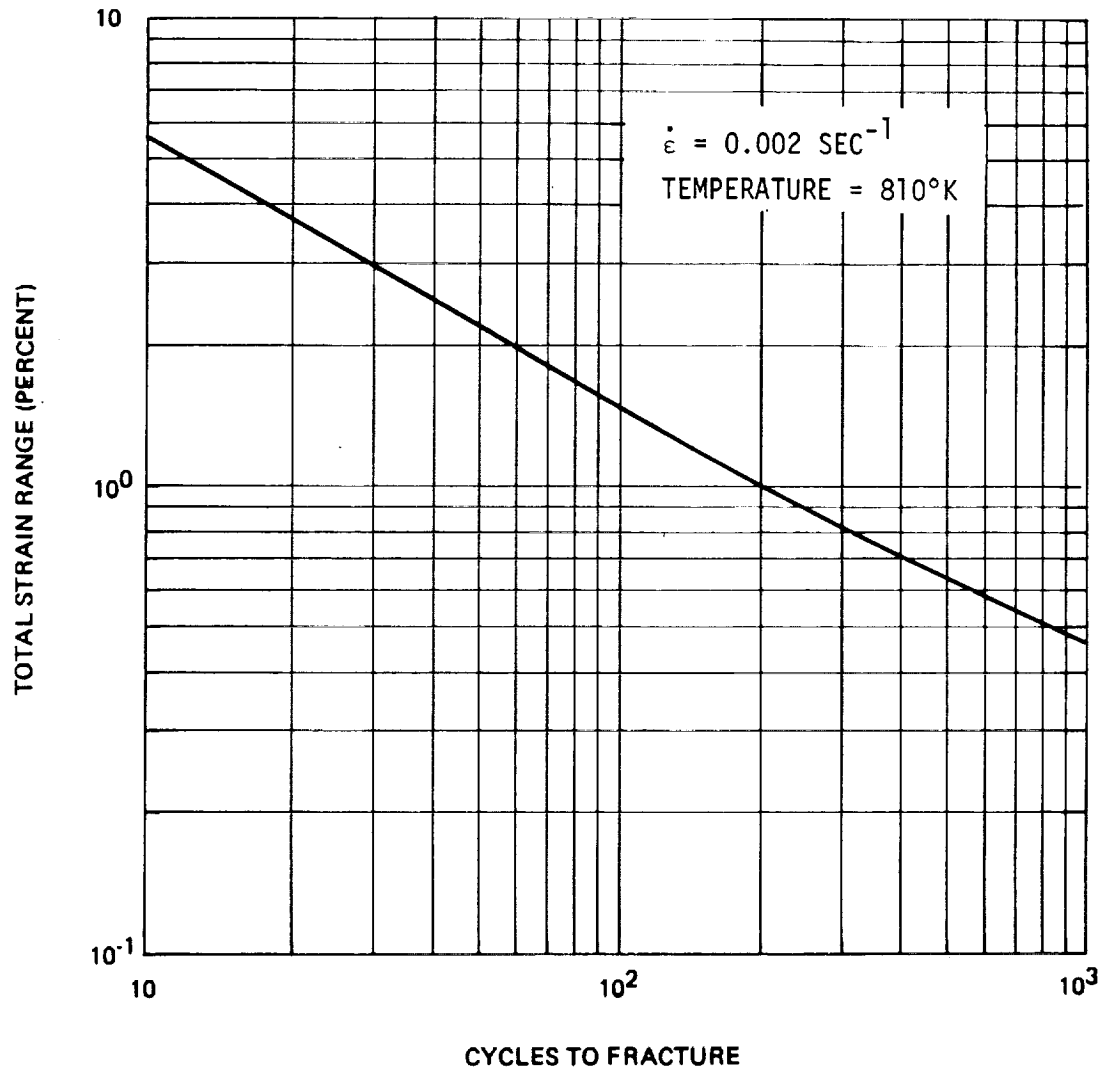


Figure 34 Typical Low-Cycle Fatigue Life of Electroformed Copper
 – As Formed Condition

2.5 Fine Silver

General Information

Fine silver, often called commercial fine silver, has a maximum of 0.10 percent total impurities. Fine silver has the highest electrical and thermal conductivity of all metals and only gold is more ductile and malleable. The metal has rather low strength even after severe cold work and it cannot be hardened by any thermal treatment. Silver can be readily hot or cold worked and is relatively difficult to machine, particularly in the annealed condition. The material can be annealed at low temperatures. Therefore, if the maximum hardening effect of cold work is desired, care must be taken to avoid an appreciable rise in temperature due to working the material too rapidly.

Room Temperature Properties	
Material	Fine Silver
Condition	As Drawn
Mechanical Properties	
Tensile Ultimate, MN/m ² (ksi)	289 (42)
Tensile Yield, MN/m ² (ksi) 0.2% Offset	283 (41)
Elongation, %	5
Reduction of Area, %	85
Modulus of Elasticity, GN/m ² (10 ⁶ psi)	71 (10.3)
Poisson's Ratio	.37
Physical Properties	
Density, kg/m ³ (lb/in ³)	10,490 (.379)
Specific Heat, J kg ⁻¹ K ⁻¹ (cal/g/K)	237 (.0565)
Thermal Conductivity, Wm ⁻¹ K ⁻¹	400
Coefficient of Thermal Expansion, 294K to 533K , 10 ⁻⁶ (m/m) K ⁻¹ 70°F to 500°F , 10 ⁻⁶ (in/in/°F)	19.5 (10.3)

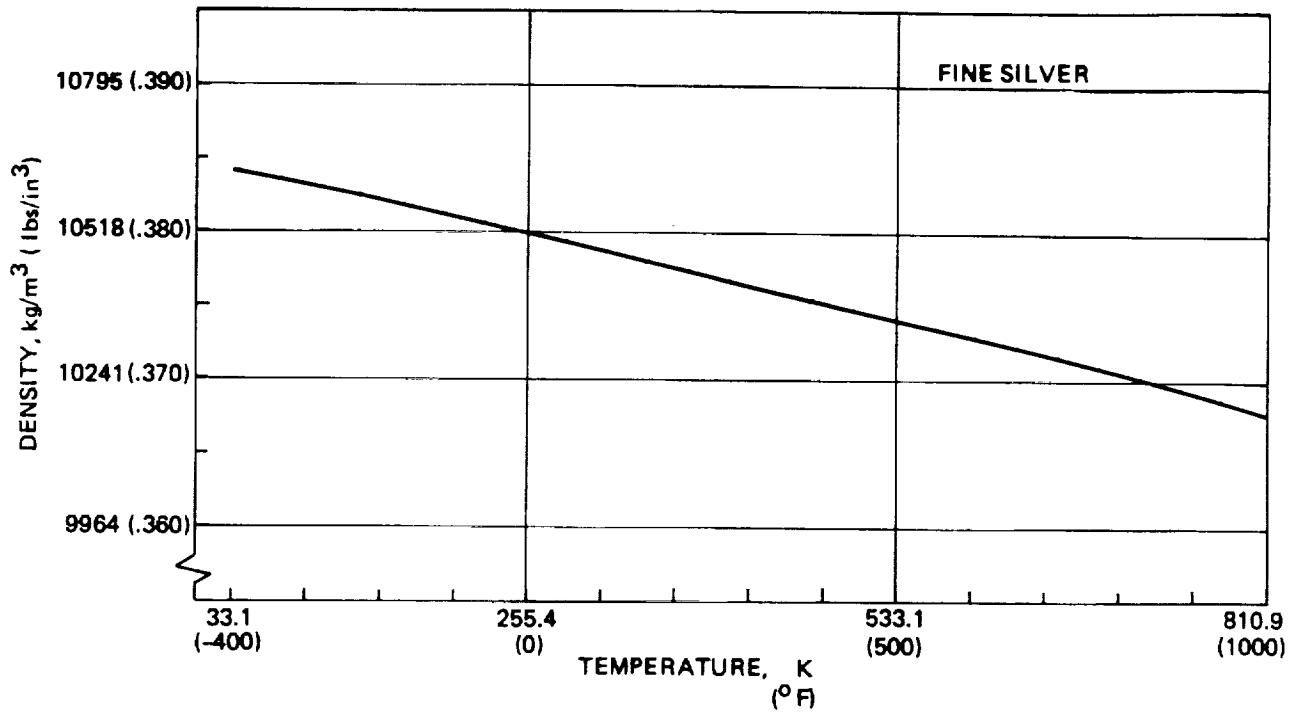


Figure 35 Density vs Temperature for Fine Silver

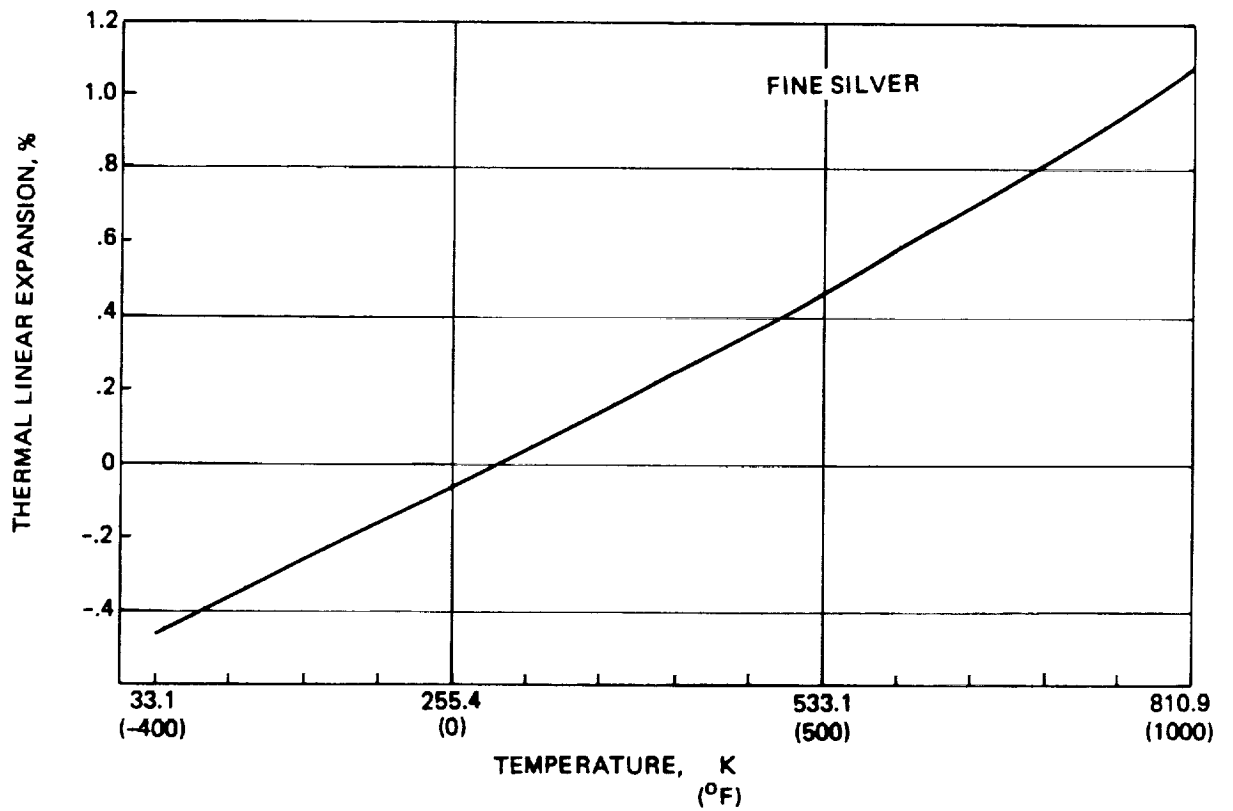


Figure 36 Thermal Linear Expansion vs Temperature for Fine Silver

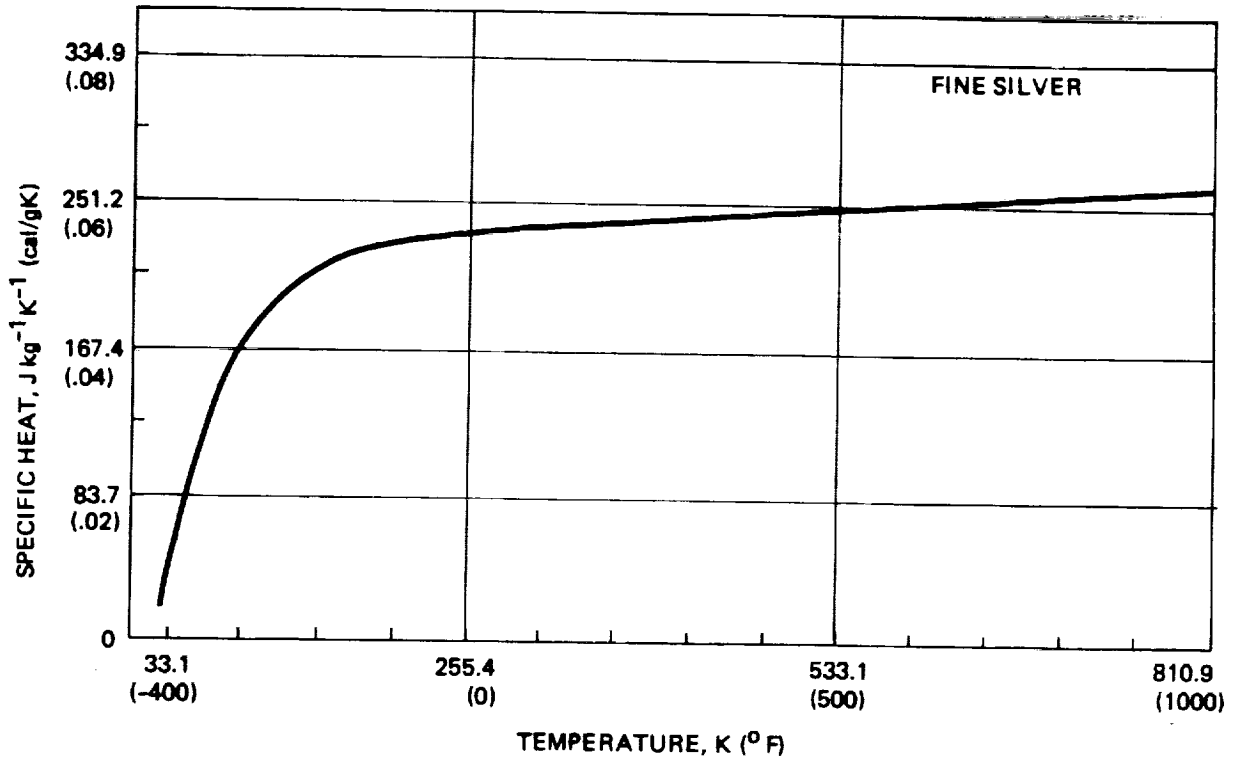


Figure 37 Specific Heat vs Temperature for Fine Silver - As Drawn Condition

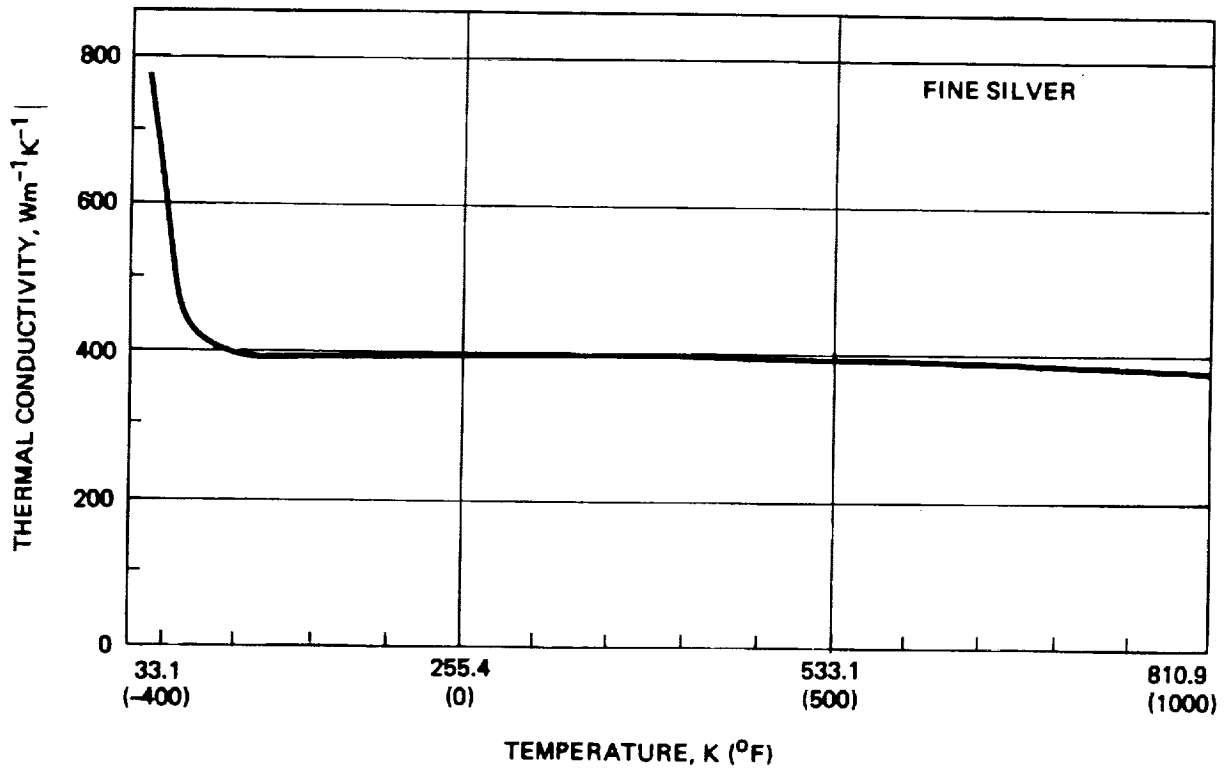


Figure 38 Thermal Conductivity vs Temperature for Fine Silver - As Drawn Condition

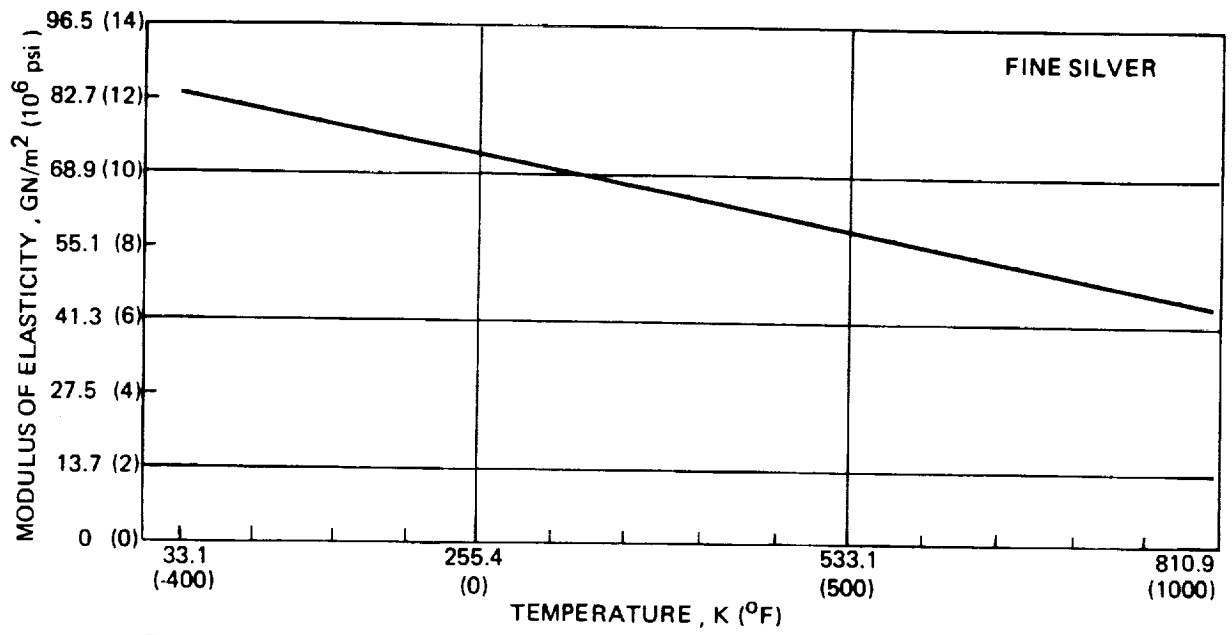


Figure 39 Modulus of Elasticity vs Temperature for Fine Silver—As Drawn Condition

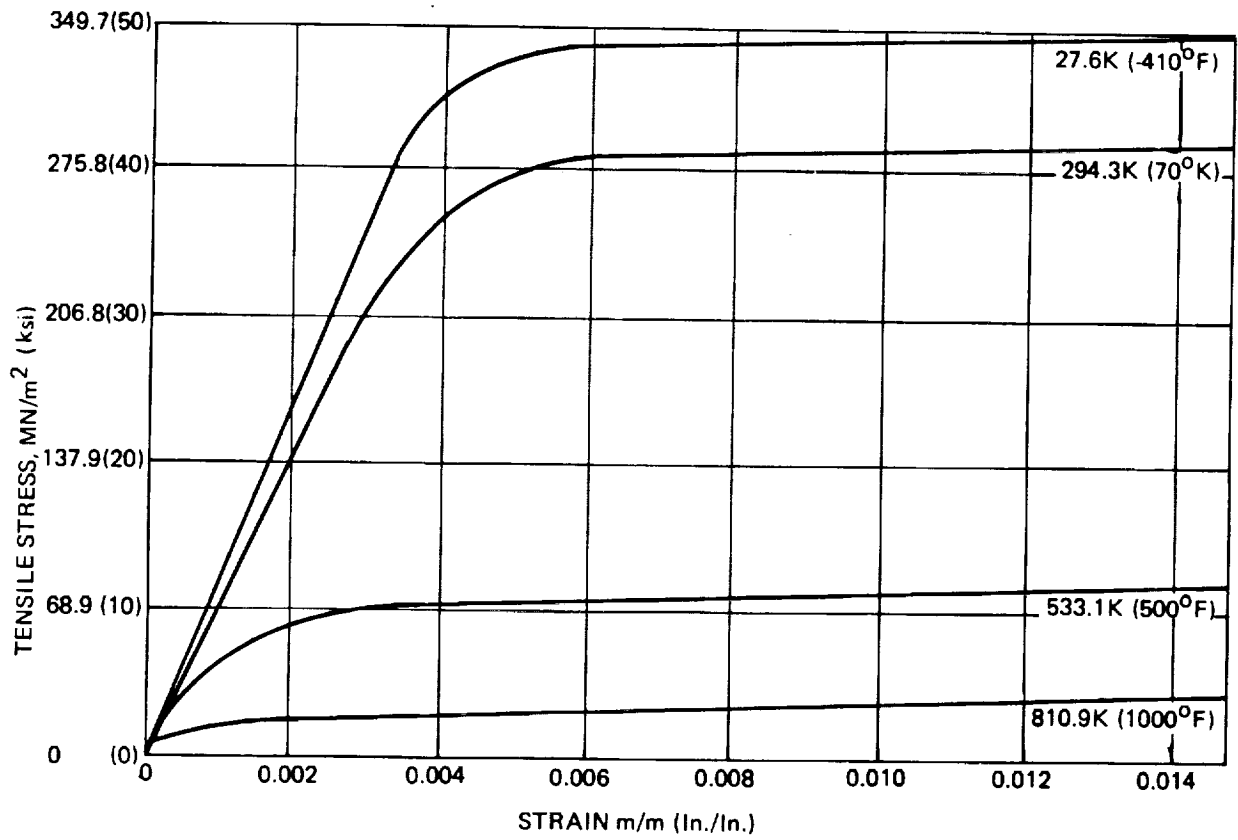


Figure 40 Typical Stress-Strain Curves for Fine Silver—As Drawn Condition

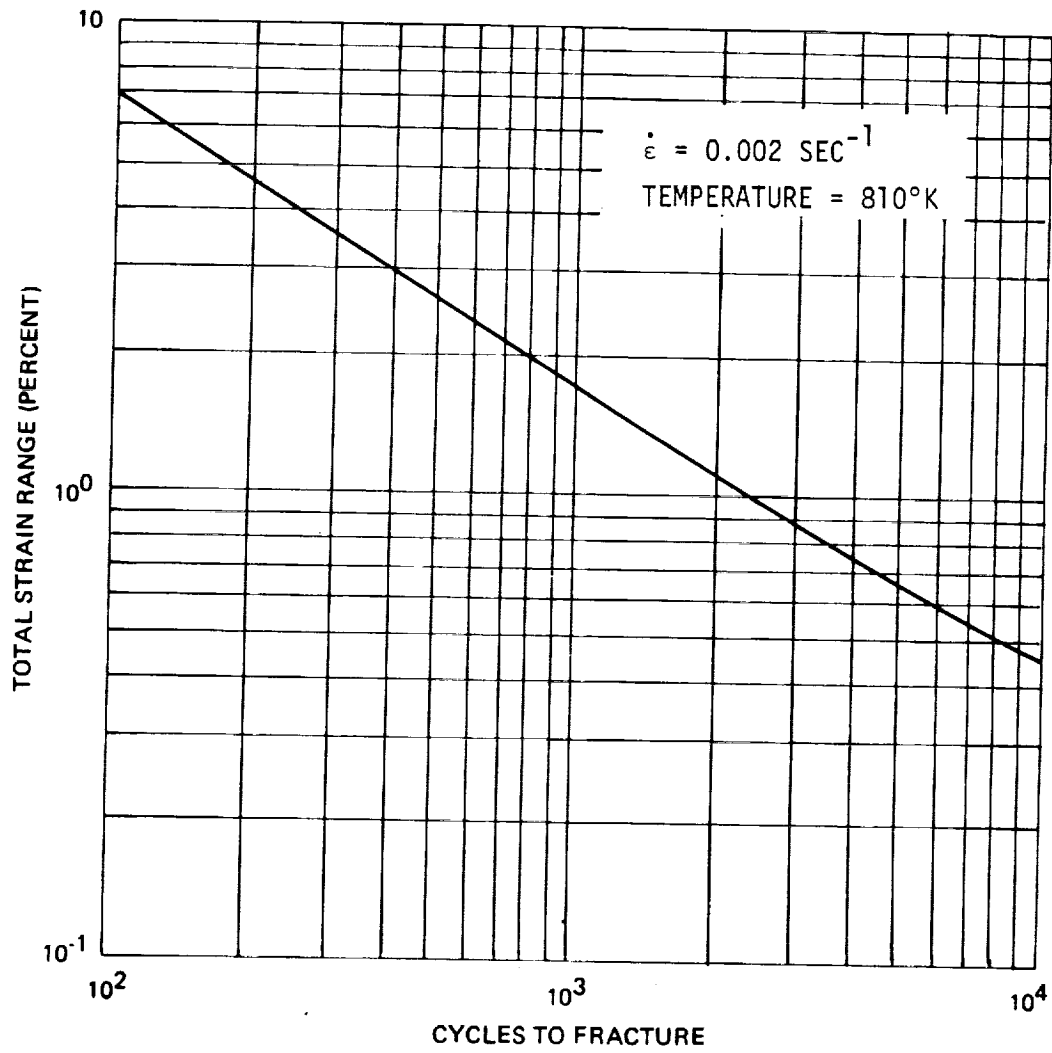


Figure 41 Typical Low-Cycle Fatigue Life of Fine Silver – As Drawn Condition

2.6 Electroformed Nickel

General Information

Electroformed nickel is obtained from an electro-chemical process involving the deposition of nickel ions from an electrolyte onto a mandrel. A sulfamate bath is used to obtain nickel deposits with low internal stresses. The nickel deposits can be bonded to or sandwiched between other material deposits to provide integral heat sinks in an almost unlimited range of regular and irregular configurations. The electroformed nickel is easily joined to other metals by welding, brazing, or soldering with the use of common materials and methods. Mechanical properties of electroformed nickel can be varied over a wide range by the methods of deposition and by the composition of the plating bath. The metallurgical structure is characterized by high-purity, needle-like crystals aligned perpendicular to the mandrel.

Room Temperature Properties	
Material:	Electroformed Nickel (Sulfamate)
Condition:	As Formed
Mechanical Properties: Tensile Ultimate, MN/m ² (ksi) Tensile Yield, MN/m ² (ksi) 0.2% offset Elongation, % Reduction of Area, % Modulus of Elasticity, GN/m ² (10 ⁶ psi) Poisson's Ratio	551 (80) 344 (50) 20 193 (28) .34
Physical Properties Density, kg/m ³ (lb/in. ³) Specific Heat, J kg ⁻¹ K ⁻¹ (cal/g/K) Thermal Conductivity, W m ⁻¹ K ⁻¹ Coefficient of Thermal Expansion, 294K to 533K, 10 ⁻⁶ [m-m] K ⁻¹ 70°F to 500°F, 10 ⁻⁶ (in./in./°F)	8913 (.322) 444 (.106) 90 12.2 (6.8)

3.0 REFERENCES

1. J. B. Conway, R. H. Stentz and J. T. Berling, High Temperature, Low Cycle Fatigue of Copper-Base Alloys in Argon; Part I, Mar-Test Inc. Report MTI-R003-2-1, NASA Lewis Research Center Contract NAS3-16753, 1973.
2. J. B. Conway, R. H. Stentz and J. T. Berling, High Temperature, Low Cycle Fatigue of Copper-Base Alloys in Argon; Part II - Zirconium-Copper at 482, 538 and 593°C, Mar-Test Inc. Report MTI-R993-2-2, NASA Lewis Research Center Contract NAS3-16753, August 1973.
3. J. B. Conway, R. H. Stentz and J. T. Berling, High Temperature, Low Cycle Fatigue of Copper-Base Alloys in Argon; Part III - Thermal Mechanical Strain Cycling, Hold-Time and Notch Fatigue Results, Mar-Test Inc. Report MTI-R003-2-3, NASA Lewis Research Center Contract NAS3-16753, December 1973.
4. J. B. Conway, R. H. Stentz and J. T. Berling, High Temperature, Low Cycle Fatigue of Advanced Copper-Base Alloys for Rocket Nozzles; Part I - NARloy Z, Mar-Test Inc. Report MTI-R003-3-1, NASA Lewis Res. Center Contract.
5. Unpublished static and cyclic stress-strain curves from NASA Lewis Research Center Contract NAS3-16753, High Temperature, Low Cycle Fatigue of Copper-Base Alloys; Mar-Test Inc. 1973.
6. Unpublished cyclic stress-strain curves from NASA Lewis Research Center Contract NAS3-17777; High Temperature Low Cycle Fatigue of Advanced Copper-Base Alloys for Rocket Nozzles; Part I-NARloy Z; Mar-Test Inc. 1974.
7. Unpublished Amzirc Material Properties Data, Enclosure to NASA Lewis Research Center letter 5312, R. J. Quentmeyer to Val Derlugin, November 1974.

REFERENCES (Cont'd)

8. Unpublished Rocketdyne NARloy Z low cycle fatigue data from NASA Marshall Space Flight Center, Table I of Boeing Coordination Sheet No. 2-5020-5560-HGB-CS-006, K. H. Dickenson to Joe Masters, February 1974.
9. Richard P. Reed and Ritchie P. Mikesell, Low Temperature Mechanical Properties of Copper and Selected Copper Alloys, A compilation from the literature, National Bureau of Standards Monograph 101, 1967.
10. R. Michael McClintock and Hugh P. Gibbons, Mechanical Properties of Structural Materials at Low Temperatures, A compilation from the literature, National Bureau of Standards Monograph 13, 1960.
11. D. L. Harrod, E. Vandergrift and L. France, Mechanical Property Determination of High Conductivity Metals and Alloys WANL-M-FR-72-005, Westinghouse Astronuclear Laboratory, NAS7-725, February 1973.
12. Technical Survey OFHC Brand Copper, High Conductivity Oxygen Free, The American Metal Company, Limited, 1957.
13. Dennis D. Horn and Henry F. Lewis, Property Investigation of Copper-Base Alloys at Ambient and Elevated Temperatures, Arnold Engineering Development Center, AEDC-TR-65-72, July 1965.
14. Taylor Lyman, Editor, Metals Handbook Properties and Selection of Metals, American Society for Metals, 1961
15. Vernon A. Lamb and Donald R. Valentine, Physical and Mechanical Properties of Electrodeposited Copper, Literature Survey, American Electroplater's Society Research Project No. 21, December 1965.
16. Alloy Digest, Data on World Wide Metals and Alloys, Fine Silver, Filing Code Ag-6, Engineering Alloys Digest, Inc. June 1971.
17. Alloy Digest, Data on World Wide Metals and Alloys, OFHC Copper, Filing Code Cu-144, Engineering Alloys Digest, Inc. August 1964.

REFERENCES (Cont'd)

18. Alloy Digest, Data on World Wide Metals and Alloys, AMZIRC, Filing Code Cu-99, Engineering Alloys Digest, Inc. April 1961.
19. E. F. Green, Rocketdyne Materials Bulletin, Zirconium-Copper (AMZIRC), Rocketdyne, California, 1972.
20. E. F. Green, Rocketdyne Materials Bulletin, MARloy-Z, Rocketdyne, California, 1974.
21. E. F. Green, Rocketdyne Materials Bulletin, OFHC Copper, Rocketdyne, California, 1972.
22. L. C. McCandles, Development of Improved Electroforming Technique (NASA CR 134480) General Technologies Corp. November 1973.
23. J. Robert Kattus and Clifford L. Dotson, Tensile, Fracture and Short-Time Creep Properties of Aircraft-Structural Materials at Very High Temperatures after Rapid Heating, Wright Air Development Center, WADC Technical Report 55-391, December 1955.
24. J. B. Preston, W. P. Roe and J. R. Kattus, Determination of the Mechanical Properties of Aircraft-Structural Materials at Very High Temperatures after Rapid Heating, Wright Air Development Center, WADC Technical Report 57-649, January 1958.
25. W. H. Safranek, A. Survey of Electroforming for Fabricating Structures, N66-23152 (AD-461826) Battelle Memorial Inst., October 1964.
26. D. C. Jerome and W. H. Armstrong, NARloy Z Creep Test Report, Boeing Saturn/Apollo/Skylab Division, Memorandum 5-9430-H-1357, July 1973.
27. Heli-Coil Electroforming Literature, Electroforming Division/Heli-Coil Corporation, Danbury, Connecticut, Eugene N. Castellano, General Manager.
28. Physical and Mechanical Properties of Chemcast Materials, Chemical Casting Company, Redondo Beach, California.

REFERENCES (Cont'd)

29. Electroforming With Nickel, The International Nickel Company, Inc. New York, New York.
30. Y. S. Touloukian, Editor, Thermophysical Properties of Matter, The TPRC Data Series, Thermophysical Properties Research Center, Purdue University, 1970.
31. Y. S. Touloukian, Editor, Thermophysical Properties of High Temperature Solid Materials, Thermophysical Properties Research Center, Purdue University, 1967.
32. Theta Technical Services Data, Thermal Expansion Tests Conducted for NASA Lewis Research, Theta Industries, Inc., Test runs #428, 429, 431, 438, 439, 441, 443, 492, 564, and 565, February 1973 - January 1974.
33. M. C. I. Siu, W. L. Carroll and T. W. Watson, Thermal Conductivity and Electrical Resistivity of Six Dilute Copper Alloys and Comparison with the Smith-Palmer Equation, National Bureau of Standards, 1974.
34. J. Kazaroff and G. Halford, High-Temperature, Low-Cycle Fatigue of Copper-Base Alloys for Rocket Nozzle Liner Application, Equation of Universal Slpes (Manson and Hirschberg), NASA Lewis Research Center.



DISTRIBUTION LIST FOR FINAL REPORT - CR-134806

<u>Name</u>	<u>No. Of Copies</u>
National Aeronautics & Space Administration Lewis Research Center 21000 Brookpark Road Cleveland, Ohio 44135	
Attn: J. R. Danicic, MS 500-313	1
E. A. Bourke, MS 500-205	5
Technical Utilization Office, MS 3-19	1
Technical Report Control Office, MS 5-5	1
AFSC Liaison Office, MS 501-3	2
Library, MS 60-3	2
Office of Reliability & Quality Assurance, MS 500-211	1
R. J. Quentmeyer, Project Manager, MS 500-204	20
National Aeronautics & Space Administration Headquarters Washington, DC 20546	
Attn: Office of Aeronautics & Space Technology	
RS/Director, Manned Space Technology	1
RP/Director, Space Propulsion & Power	1
RW/Director, Materials & Structures	1
RPI/F. W. Stephenson	1
Attn: Office of Manned Space Flight	
MT/Director, Advanced Manned Mission	1
Attn: Office of Space Science	
SG/Director, Physics & Astronomy Programs	1
SL/Director, Planetary Programs	1
SV/Director, Launch Vehicles & Propulsion	1
Attn: Office of Technology Utilization Division	
KT/Director, Technology Utilization	1
National Aeronautics & Space Administration Ames Research Center Moffett Field, California 94035	
Attn: Library	1

No. of Copies

National Aeronautics & Space Administration Flight Research Center P. O. Box 273 Edwards, CA 93523	1
National Aeronautics & Space Administration George C. Marshall Space Flight Center Huntsville, AL 35912 Attn: Library	1
R. L. Hurford	1
W. B. McPherson	1
N. Schlemmer	1
J. Thomson	1
National Aeronautics & Space Administration Goddard Space Flight Center Greenbelt, MD 20771 Attn: Library	1
National Aeronautics & Space Administration John F. Kennedy Space Center Cocoa Beach, FL 32931 Attn: Library	1
K. H. Debus, CD	1
National Aeronautics & Space Administration Lyndon B. Johnson Space Center Houston, TX 77001 Attn: Library	1
National Aeronautics & Space Administration Langley Research Center Langley Station Hampton, VA 23365 Attn: Library	1
NASA Scientific & Technical Information Facility P. O. Box 33 College Park, MD 20740 Attn: NASA Representative	10
Office of the Director of Defense Research & Engineering Washington, DC 20301 Attn: Office of Ass't Director (Chemical Technology)	1

No. of Copies

Jet Propulsion Laboratory 4800 Oak Grove Drive Pasadena, CA 91103 Attn: Library D. Dipprey H. Burlage, Jr.	1 1 1
Defense Documentation Center Cameron Station Building 5 5010 Duke Street Alexandria, VA 22314 Attn: TISIA	1
Advanced Research Projects Agency Washington, DC 20525 Attn: Library	1
Aeronautical Systems Division Air Force Systems Command Wright-Patterson Air Force Base Dayton, Ohio Attn: Library	1
Air Force Rocket Propulsion Laboratory (RPM) Edwards, CA 93523 Attn: Library	1
Air Force FTC (FTAT-2) Edwards Air Force Base, CA 93523 Attn: Library	1
Air Force Office of Scientific Research Washington, DC 20333 Attn: Library Dr. J. F. Masi	1 1
U.S. Air Force Washington, DC 20333 Attn: Library	1

No. of Copies

Air Force Aero Propulsion Laboratory Research & Technology Division Air Force Systems Command U.S. Air Force Wright Patterson AFB, OH 45433 Attn: Library (APRP)	1
Arnold Engineering Development Center Air Force Systems Command Tullahoma, TN Attn: Library	1
Bureau of Naval Weapons Department of the Navy Washington, DC Attn: Library	1
U.S. Naval Research Laboratory Washington, DC 20390 Attn: Library	1
U.S. Army Research Office (Durham) Box CM, Duke Station Durham, NC 27706 Attn: Library	1
U.S. Army Missile Command Redstone Scientific Information Center Redstone Arsenal, AL 35808 Attn: Document Section	1
U.S. Naval Missile Center Point Mugu, CA 93041 Attn: Technical Library	1
U.S. Naval Weapons Center China Lake, CA 93557 Attn: Library	1

No. of Copies

Aerojet Liquid Rocket Company P. O. Box 15847 Sacramento, CA 95813 Attn: Technical Library 2484-2015A J. Sims	1 1
Aro Incorporated Arnold Engineering Development Center Arnold AF Station, TN 37389 Attn: Library	1
Battelle Memorial Institute 505 King Avenue Columbus, OH 43201 Attn: Library	1
Bell Aerosystems Inc Box 1 Buffalo, NY 14240 Attn: Library J. M. Senneff J. Flanagan	1 1 1
Boeing Company Space Division P. O. Box 868 Seattle, WA 98124 Attn: Library D. H. Zimmerman	1 1
Boeing Company P. O. Box 1680 Huntsville, AL 35801	1
Chemical Propulsion Information Agency Applied Physics Laboratory 8621 Georgia Avenue Silver Spring, MD 20910	1

No. of Copies

Chrysler Corporation
 Space Division
 P. O. Box 29200
 New Orleans, LA 70129
 Attn: Library 1

General Dynamics/Convair
 P. O. Box 1128
 San Diego, CA 92112
 Attn: Library 1
 R. Tatro 1
 R. Nau 1
 C. F. Peters 1

General Electric Company
 Missiles & Space Systems Center
 Valley Forge Space Tech. Center
 P. O. Box 8555
 Philadelphia, PA 19101
 Attn: Library 1

Grumman Aircraft Engineering Corporation
 Bethpage, L.I., NY
 Attn: Library 1

Ling-Temco-Vought Corporation
 P. O. Box 5907
 Dallas, TX 75222
 Attn: Library 1

Lockheed Missiles & Space Company
 P. O., Box 504
 Sunnyvale, CA 94087
 Attn: Library 1
 R. T. Parmley 1

Marquardt Corporation
 16555 Saticoy Street
 Box 2013 South Annex
 Van Nuys, CA 91409
 Attn: Library 1
 L. R. Bell, Jr. 1

No. of Copies

Martin-Marietta Corporation	
P. O. Box 179	
Denver, CO 80201	
Attn: Library	1
G. C. Skartvedt	1
McDonnell Douglas Astronautics	
5301 Bolsa Avenue	
Huntington Beach, CA 92647	
Attn: Library	1
L. Q. Westmoreland	1
P. Klevatt	1
Philco-Ford Corporation	
Aeronautics Div.	
Ford Rd.	
Newport Beach, CA 92663	
Attn: Library	1
Purdue University	
Lafayette, IN 47907	
Attn: Library	1
Rocketdyne	
A Div. of Rockwell International	
6633 Canoga Avenue	
Canoga Park, CA 91304	
Attn: Library	1
R. J. Burick	1
R. R. Cooper	1
A. Y. Falk	1
R. Campbell	1
N. Bergstresser	1
J. Somerville	1
Rocket Research Corporation	
Willow Road at 116th Street	
Redmond, WA 98052	
Attn: Library	1
Thiokol Chemical Corporation	
Redstone Division	
Huntsville, AL	
Attn: Library	1

No. of Copies

TRW Systems, Inc.
1 Space Park
Redondo Beach, CA 90278
Attn: Library 1
 A. H. Zimmerman 1
 W. A. Carter 1
 H. Burge 1

United Aircraft Corporation
Pratt & Whitney Division
Florida Research & Development Center
P. O. Box 2691
West Palm Beach, FL 33402
Attn: Library 1
 G. B. Cox 1

Amax Copper, Inc.
1270 Ave. of the Americas
New York, NY 10020
Attn: N. Kehl 1
 G. C. Van Tilburg 1

Glidden-Durkee
Metals Group
900 Union Commerce Bldg
Cleveland, Ohio
Attn: M. F. Marchitto 1