

# Surface Fatigue Life of Carburized and Hardened M50NiL and AISI 9310 Spur Gears and Rolling-Contact Test Bars

Dennis P. Townsend  
*Lewis Research Center  
Cleveland, Ohio*

and

Eric N. Bamberger  
*General Electric Company  
Cincinnati, Ohio*

(NASA-TM-101979) SURFACE FATIGUE LIFE OF  
CARBURIZED AND HARDENED M50NiL AND AISI 9310  
SPUR GEARS AND ROLLING-CONTACT TEST BARS  
(NASA. Lewis Research Center) 18 pCSCL 13I

N89-22111

Unclas  
G3/37 0204402

Prepared for the  
25th Joint Propulsion Conference  
cosponsored by the AIAA, ASME, SAE, and ASEE  
Monterey, California, July 10-12, 1989



SURFACE FATIGUE LIFE OF CARBURIZED AND HARDENED M50NiL AND  
AISI 9310 SPUR GEARS AND ROLLING-CONTACT TEST BARS

ORIGINAL PAGE IS  
OF POOR QUALITY

Dennis P. Townsend  
National Aeronautics and Space Administration  
Lewis Research Center  
Cleveland, Ohio

and

Eric N. Bamberger  
General Electric Company  
Cincinnati, Ohio

### Abstract

E-4678

Spur gear endurance tests and rolling-element surface fatigue tests were conducted to investigate vacuum-induction-melted, vacuum-arc-melted (VIM-VAR) M50NiL steel for use as a gear steel in advanced aircraft applications, to determine its endurance characteristics, and to compare the results with those for standard VAR and VIM-VAR AISI 9310 gear material. Tests were conducted with spur gears and rolling-contact bars manufactured from VIM-VAR M50NiL and VAR and VIM-VAR AISI 9310. The gear pitch diameter was 8.9 cm (3.5 in.). Gear test conditions were an inlet oil temperature of 320 K (116 °F), an outlet oil temperature of 350 K (170 °F), a maximum Hertz stress of 1.71 GPa (248 ksi), and a speed of 10 000 rpm. Bench rolling-element fatigue tests were conducted at ambient temperatures with a bar speed of 12 500 rpm and a maximum Hertz stress of 4.83 GPa (700 ksi). The VIM-VAR M50NiL gears had a surface fatigue life that was 4.5 and 11.5 times that for VIM-VAR and VAR AISI 9310 gears, respectively. The surface fatigue life of the VIM-VAR M50NiL rolling-contact bars was 13.2 and 21.6 times that for the VIM-VAR and VAR AISI 9310, respectively. The VIM-VAR M50NiL material was shown to have good resistance to fracture through a fatigue spall and to have fatigue life far superior to that of both VIM-VAR and VAR AISI 9310 gears and rolling-contact bars.

### Introduction

Recent developments by aircraft turbine engine groups and others have required the use of fracture-resistant bearing materials for integral rolling-element bearing races. Higher speed bearings require races with good fracture toughness to prevent serious failures after a race fatigue failure (i.e., spall) occurs. The use of advanced high-hot-hardness steels for aircraft engine bearings and aircraft transmissions for helicopters, VSTOL, and geared fans or turboprops has been shown<sup>1,2</sup> to extend the operating life at higher operating temperatures. In addition the use of high-hot-hardness materials can considerably lengthen operating times if the lubrication and cooling system fails and the operating temperature increases.

Several high-hot-hardness carburizing grade gear steels have been developed in recent years, and tests with these materials have shown longer surface fatigue lives than standard AISI 9310 gear steel.<sup>3-5</sup> A more recent high-hot-hardness steel, M50NiL, was developed originally as a carburizing-grade race material for rolling-element bearings. It improved fracture toughness while retaining hot hardness and long bearing fatigue life.<sup>6</sup> This material was developed from the

standard AISI M50 bearing material by reducing the carbon content to improve the fracture toughness and by adding a small amount of nickel to stabilize the austenite and to prevent the formation of excessive amounts of ferrite and retained austenite.<sup>6</sup> With its reduced carbon content the M50NiL material can be case carburized to give a hard bearing surface while retaining a tough core. Rolling-contact (RC) fatigue tests with M50NiL<sup>6</sup> have shown it to have excellent surface fatigue life.

The objectives of the research reported herein were (1) to investigate M50NiL for use as a gear material, (2) to determine the surface endurance characteristics of M50NiL, and (3) to compare the results with those for standard VAR and VIM-VAR AISI 9310 aircraft gear materials. To accomplish these objectives, tests were conducted with spur gears and RC test bars manufactured from M50NiL. For comparison purposes spur gears and RC test bars manufactured from VAR and VIM-VAR AISI 9310 were also tested for fatigue life. The gear pitch diameter was 8.9 cm (3.5 in.). Test conditions for the gears included an inlet oil temperature of 320 K (116 °F) that resulted in an outlet oil temperature of 350 K (170 °F), a maximum Hertz stress of 1.71 GPa (248 ksi), and a speed of 10 000 rpm. The rolling-element fatigue tests<sup>6,7</sup> were conducted with 0.952-cm (0.375-in.) diameter test bars. The RC tests were conducted at ambient temperature with a bar speed of 12 500 rpm and a maximum Hertz stress of 4.83 GPa (700 ksi).

### Apparatus and Procedures

#### Gear Test Apparatus

The gear fatigue tests were performed in the NASA Lewis Research Center's gear fatigue test apparatus (Fig. 1). This test rig uses the four-square principle of applying the test gear load so that the input drive only needs to overcome the frictional losses in the system. Oil pressure and leakage flow are supplied to the load vanes through a shaft seal. As the oil pressure on the load vanes inside the slave gear is increased, torque is applied to the shaft. This torque is transmitted through the test gears back to the slave gear, where an equal but opposite torque is maintained by the oil pressure. This torque on the test gears, which depends on the hydraulic pressure applied to the load vanes, loads the gear teeth to the desired stress level. The two identical test gears can be started under no load, and the load can be applied gradually without changing the running track on the gear teeth.

Separate lubrication systems are provided for the test gears and the main gearbox. The two

lubrication systems are separated at the gearbox shafts by pressurized labyrinth seals. Nitrogen is the seal gas. The test gear lubricant is filtered through a 5- $\mu$ m nominal fiberglass filter. The test lubricant can be heated electrically with an immersion heater. The skin temperature of the heater is controlled to prevent overheating the test lubricant.

A vibration transducer mounted on the gearbox is used to automatically shut off the test rig when gear surface fatigue occurs. The gearbox is also automatically shut off if there is a loss of oil flow to either the main gearbox or the test gears, if the test gear oil overheats, or if there is a loss of seal gas pressurization.

The belt-driven test rig can be operated at several fixed speeds by changing pulleys. The operating speed for the tests reported herein was 10 000 rpm.

#### Rolling-Contact Fatigue Tester

The RC fatigue tester is shown in Fig. 2. A cylindrical test bar is mounted in the precision chuck. The drive motor attached to the chuck drives the bar, which in turn drives two idler rollers. Load is applied by closing the rollers against the test bar with a micrometer-threaded turnbuckle and a calibrated load cell. Lubrication is supplied by a drop feed system; a needle valve controls the flow rate. Several test runs can be made on one test bar by moving the bar position in the axial direction relative to roller contacts. The test bar rotates at 12 500 rpm and receives 25 000 stress cycles per minute. The maximum Hertz stress was 4.83 GPa (700 ksi).

#### Test Gears

The test gears are shown in Fig. 3. The dimensions of the gears are given in Table I. All the gears had a nominal surface finish on the tooth face of 0.41  $\mu$ m (16  $\mu$ in.) rms. All the gears had a standard 20° involute profile with tip relief. The tip relief was 0.0013 cm (0.0005 in.) starting at the highest point of single-tooth contact.

#### Rolling-Contact Test Bar Specimens

The test specimens for the RC fatigue tester were cylindrical bars 7.6 cm (3.0 in.) long with a 0.952-cm (0.375-in.) diameter. The surface finish was 0.13 to 0.20  $\mu$ m (5 to 8  $\mu$ in.) rms.

The large mating rollers had a diameter of 19 cm (7.5 in.) and a crown radius of 0.635 cm (0.250 in.). The surface finish of the rollers was the same as that of the test bars.

#### Test Material

The 9310 test gears and RC bars were manufactured from either vacuum-arc-remelted (VAR), consumable-electrode vacuum-melted (CVM), or vacuum-induction-melted, vacuum-arc-remelted (VIM-VAR) AISI 9310.

The M50NiL test gears and RC bars were manufactured from VIM-VAR material. This M50NiL material was developed from a standard AISI M50 by reducing the carbon content from 0.85 to 0.13 to provide improved fracture toughness and adding a

small amount of nickel (3.4 percent) to stabilize the austenite and to prevent the formation of excessive amounts of ferrite and retained austenite.

The chemical composition of the test gears and RC bars is given in Table II. The heat treatment procedure for the gears and RC bars is given in Table III. The gears and RC bars were case carburized and hardened to the case and core properties shown in Table IV. A cross section through an AISI 9310 gear tooth is shown in Fig. 4(a), and a cross section of an M50NiL gear tooth is shown in Fig. 4(b). The case and core photomicrographs of the 9310 and M50NiL are shown in Figs. 5(a) and (b), respectively. The retained austenite shown for the M50NiL is much higher than would be expected for the treatment procedure specified in Table III. This high level of retained austenite was apparently the result of missing the deep freeze treatment. This was further verified when the used gear was given a deep freeze at 200 K (-100 °F) and double temper at 797 K (975 °F). The retained austenite was then found to be 5 percent. A cross section through an M50NiL gear tooth after the deep freeze and temper is shown in Fig. 4(c). In addition the hardness increased approximately 2 points Rockwell C, as shown in Fig. 6. It was not expected that the absence of the deep freeze would significantly change the fatigue life of the M50NiL gears.

#### Lubricant

All the gears were lubricated with a single batch of synthetic paraffinic oil, which was the standard test lubricant for the gear tests. The physical properties of this lubricant are summarized in Table V. Five vol % of an extreme-pressure additive designated Lubrizol 5002 (partial chemical analysis given in Table V) was added to the lubricant.

The RC test specimens were lubricated with a standard diester test lubricant that met the MIL-L-7808G specification. The fluid was a mixture of two base stocks, a diester plus a (trimethylol propane) polyester. The additives in this fluid included antioxidants, load-carrying additives, metal passivators, a hydrolytic stability additive, and a silicone antifoam additive. The types and levels of the additives are proprietary. The lubricant properties are given in Table V.

#### Test Procedure

Gears. After the test gears were cleaned to remove their protective coating, they were assembled on the test rig. The test gears ran in an offset condition with a 0.30-cm (0.120-in.) tooth-surface overlap to give a load surface on the gear face of 0.28 cm (0.110 in.), allowing for an edge radius on the gear teeth. Since the offset test method may introduce edge loading effects, the method was originally checked with both crowned and uncrowned gears. There was no difference between the crowned and uncrowned gears; also all fatigue spalls with uncrowned gears originated evenly along the tooth flank and never started at the edge location. This is proof that the offset test condition is an acceptable method for surface fatigue testing.

If both faces of the gears were tested, four fatigue tests could be run for each set of gears. All tests were run-in at a load per unit length of

1230 N/cm (700 lb/in.) for 1 hr. The load was then increased to 5800 N/cm (3300 lb/in.), which resulted in a pitchline maximum Hertz stress of 1.71 GPa (248 ksi). At the pitchline load the tooth bending stress was 0.21 GPa (30 ksi) if plain bending was assumed. However, because there was an offset load, an additional stress was imposed on the tooth bending stress. Combining the bending and torsional moments gave a maximum stress of 0.26 GPa (37 ksi). This bending stress did not include the effects of tip relief, which would also increase the bending stress.

Operating the test gears at 10 000 rpm gave a pitchline velocity of 46.55 m/sec (9163 ft/min). Lubricant was supplied to the inlet mesh at 800 cm<sup>3</sup>/min (49 in.<sup>3</sup>/min) and 320±6 K (116±10 °F). The lubricant outlet temperature was nearly constant at 350±3 K (170±5 °F). The tests ran continuously (24 hr/day) until the rig was automatically shut down by the vibration detection transducer (located on the gearbox adjacent to the test gears) or until 500 hr of operation without failure were completed. The lubricant circulated through a 5-µm fiberglass filter to remove wear particles. For each test 3.8 liters (1 gal) of lubricant were used. At the end of each test, the lubricant and the filter element were discarded. Inlet and outlet oil temperatures were continuously recorded on a strip-chart recorder.

The pitchline elastohydrodynamic (EHD) film thickness was calculated by the method of Dowson.<sup>8</sup> It was assumed, for this film thickness calculation, that the gear temperature at the pitch line was equal to the outlet oil temperature and that the inlet oil temperature to the contact zone was equal to the gear surface temperature, even though the inlet oil temperature was considerably lower. It is possible that the gear surface temperature was even higher than the outlet oil temperature, especially at the end points of sliding contact. The EHD film thickness for these conditions was computed to be 0.33 µm (13 µin.), which gave an initial ratio of film thickness to composite surface roughness  $h/\sigma$  of 0.55 at the 1.71-GPa (248-ksi) pitchline maximum Hertz stress.

Each running surface on a pair of gears was considered as a system and, hence, a single test. Test results were evaluated by using Weibull plots calculated by the method of Johnson.<sup>9</sup> (A Weibull plot is the number of stress cycles versus the statistical percentage of gear systems failed.) Since the gears were run in an offset condition, four tests were obtained from each pair of gears.

**RC tests.** Fatigue testing was also performed in the RC rig. The test bar was installed and the rollers were brought against the bar by using the turnbuckle. The load applied was sufficient to allow the bar to drive the contacting rollers and the bar was accelerated to the 12 500-rpm test speed.

When the rollers and the test bar were in thermal equilibrium at a bar temperature of ~305 K (90 °F), the full load of 1250 N (281 lb) was applied to give the test bar a maximum Hertz stress of 4.83 GPa (700 ksi). When a fatigue failure occurred, the rig and related instrumentation were automatically shut down by a vibration detection system. The axial position of the test bar in the drive chuck was changed to a new running track

before testing was resumed. Test results were also evaluated according to the methods of Johnson.<sup>9</sup>

## Results and Discussion

### Gear Life Results

One lot each of VAR AISI 9310, VIM-VAR AISI 9310, and VIM-VAR M50NiL spur gears were endurance tested. Test conditions were a tangential load of 5.788 N/cm (3305 lb/in.), which produced a maximum Hertz stress of 1.71 GPa (248 ksi), and a speed of 10 000 rpm. The gears failed by classical subsurface pitting fatigue. The pitting fatigue life results of these tests are shown in the Weibull plots of Fig. 7 and are summarized in Table VI. These data were analyzed by the method of Johnson.<sup>9</sup>

The VAR AISI 9310 material exhibited 10- and 50-percent pitting fatigue lives of  $18.8 \times 10^6$  and  $46 \times 10^6$  stress cycles (31 and 77 hr), respectively. The failure index (i.e., the number of fatigue failures out of the number of sets tested) was 18 out of 19. A typical fatigue spall that occurred near the pitch line is shown in Fig. 8(a). This spall is similar to those observed in rolling-element fatigue tests. The pitchline pitting is the result of high subsurface shearing stress, which develops subsurface cracks. These subsurface cracks propagate into a crack network and result in a fatigue spall that is slightly below the pitch line, where the Hertz stress is very high from single-tooth contact and where some sliding conditions exist.

Pitting fatigue life results of the gears made from VIM-VAR AISI 9310 material are also shown in Fig. 7. The 10- and 50-percent surface fatigue lives were  $48 \times 10^6$  and  $200 \times 10^6$  stress cycles (80 and 333 hr), respectively. The failure index was 24 out of 33. Nine suspensions did not fail after completing 500 hr of testing. The 10-percent life of the VIM-VAR AISI 9310 was more than two times, and the 50-percent life more than four times, that of the VAR material. The confidence number for the 10-percent life level was 92.5 percent, which indicates that the difference is statistically significant. (The confidence number indicates the percentage of time the relative lives of the material will occur in the same order). These data indicate that for longer life the use of VIM-VAR AISI 9310 steel is preferred over VAR AISI 9310 steel.

The pitting fatigue life results of the gears made from VIM-VAR M50NiL material are also shown in Fig. 7. The 10- and 50-percent surface fatigue lives were  $217 \times 10^6$  and  $496 \times 10^6$  stress cycles (362 and 827 hr), respectively. The failure index was 2 out of 20. Eighteen suspensions ran 500 hr without failure. A typical fatigue spall for the VIM-VAR M50NiL gear is shown in Fig. 8(b). Some of the M50NiL gears were deliberately run with a surface fatigue spall for up to 12 additional hours without a tooth fracture occurring. This indicated that the M50NiL has a good fracture toughness since no tooth fractures occurred even though gears were run with fatigue spalls and thus increased dynamic loads. The 10-percent surface fatigue life of the VIM-VAR M50NiL was more than 11 times that of the VAR AISI 9310 and more than 4 times that of the VIM-VAR AISI 9310. The confidence numbers for the M50NiL were 99 percent compared with the VAR 9310 and 92.5 percent compared to the VIM-VAR 9310, both of which are statistically significant.



## Rolling-Element Life Results

Test bars of VAR AISI 9310, VIM-VAR AISI 9310, and VIM-VAR M50NiL were tested in the RC fatigue tester shown in Fig. 2. The test data were originally reported in Refs. 6 and 7. One lot of each material was tested. The RC bars were tested at a maximum Hertz stress of 4.83 GPa (700 ksi) and a bar speed of 12 500 rpm. The RC tests were run at ambient temperature (no external heat source) with a MIL-L-7808G lubricant. The results of these tests are shown in the Weibull plots of Fig. 9 and are summarized in Table VI. These data were analyzed by the method of Johnson.<sup>9</sup> A typical surface fatigue spall for an RC test specimen is shown in Fig. 10.

The VAR AISI 9310 RC test bars exhibited 10- and 50-percent pitting fatigue lives of  $4.2 \times 10^6$  and  $9.4 \times 10^6$  stress cycles (2.8 and 6.3 hr), respectively. The failure index was 10 out of 10.

The VIM-VAR AISI 9310 RC test bars had 10- and 50-percent pitting fatigue lives of  $6.84 \times 10^6$  and  $15.74 \times 10^6$  stress cycles (4.6 and 10.5 hr), respectively. The failure index was 10 out of 10. The confidence number for the difference in the 10-percent lives of the VAR and VIM-VAR 9310 test bars was 76 percent. Although this is low, it is still considered statistically significant.

The VIM-VAR M50NiL RC test bars had 10- and 50-percent pitting fatigue lives of  $90.6 \times 10^6$  and  $219 \times 10^6$  stress cycles (60.4 and 146 hr), respectively. The failure index was 5 out of 20. The confidence number for the difference in life between the M50NiL bars and the VAR and VIM-VAR AISI 9310 was 99 percent, a statistically significant difference.

From the results of the data for the gear tests and the RC test bars for VAR AISI 9310, VIM-VAR AISI 9310, and VIM-VAR M50NiL it is concluded that the VIM-VAR 9310 material is superior to the VAR material for surface fatigue life. This conclusion was not unexpected since a cleaner steel would have fewer inclusions, where fatigue spalls tend to originate, and therefore longer fatigue life.

VIM-VAR M50NiL was shown to be far superior in life to either VAR or VIM-VAR AISI 9310, being 4.5 times the VIM-VAR 9310 for gears and 13.2 times the VIM-VAR 9310 for RC bars and 11.5 times the VAR 9310 for gears and 21.6 times the VAR 9310 for RC bars. These life differences are very large and indicate that the VIM-VAR M50NiL offers a significant advantage as a gear material over VIM-VAR AISI 9310. In addition the VIM-VAR M50NiL gear material exhibited good fracture toughness and thus is very attractive as a gear material. The higher temperature capability of the M50NiL 589 K (i.e., 600 °F) also enhances this material for gear applications where this requirement is needed such as high-speed aircraft and aircraft that must operate for up 1 hr after loss of lubricant.

### Summary of Results

Spur gear endurance tests and rolling-element surface tests were conducted to investigate VIM-VAR M50NiL steel for use as a gear steel in advanced aircraft applications, to determine its endurance characteristics, and to compare the results with

those for standard VAR and VIM-VAR AISI 9310 gear materials. Tests were conducted with spur gears and rolling-contact (RC) bars manufactured from VIM-VAR M50NiL and VAR and VIM-VAR AISI 9310. The gear pitch diameter was 8.9 cm (3.5 in.). Gear test conditions were an inlet oil temperature of 320 K (116 °F), an outlet oil temperature of 350 K (170 °F), a maximum Hertz stress of 1.71 GPa (248 ksi), and a speed of 10 000 rpm. Bench rolling-element fatigue tests were conducted at ambient temperature with a bar speed of 12 500 rpm and a maximum Hertz stress of 4.83 GPa (700 ksi).

The following results were obtained:

1. The VIM-VAR M50NiL test gears had a 10-percent surface fatigue life that was 4.5 times that of the VIM-VAR AISI 9310 and 11.5 times that of the VAR AISI 9310 material.

2. The VIM-VAR M50NiL RC test bars had a 10-percent surface fatigue life that was 13.2 times that of the VIM-VAR AISI 9310 and 21.6 times that of the VAR AISI 9310 material.

3. The VIM-VAR M50NiL was shown to have good resistance to fracture through a fatigue spall in a gear tooth and to have fatigue life far superior to that of VAR and VIM-VAR AISI 9310 in both gear and RC bar tests.

### References

1. Parker, R.J., Bamberger, E.N., and Zaretsky, E.V., "Bearing Torque and Fatigue Life Studies With Several Lubricants for Use in Range 500 °F to 700 °F," NASA TN D-3948, 1967.
2. Bamberger, E.N., Zaretsky, E.V., and Anderson, W.J., "Effects of Three Advanced Lubricants on High-Temperature Bearing Life," *Journal of Lubrication Technology*, Vol. 92, No. 1, Jan. 1970, pp. 23-33.
3. Townsend, D.P., Parker, R.J., and Zaretsky, E.V., "Evaluation of CBS 600 Carburized Steel as a Gear Material," NASA TP-1390, 1979.
4. Townsend, D.P., and Zaretsky, E.V., "Endurance and Failure Characteristics of Modified VASCO X-2, CBS 600 and AISI 9310 Spur Gears," *Journal of Mechanical Design*, Vol. 103, No. 2, Apr. 1987, pp. 505-515. (NASA TM-81421).
5. Townsend, D.P., "Surface Fatigue Life and Failure Characteristics of EX-53, CBS 1000 M and AISI 9310 Gear Materials," NASA TP-2513, 1985.
6. Bamberger, E.N., and Kroeger, D.J., "Rolling Element Fatigue Life of a Carburized Modified M50 Bearing Steel," NASA CR-168295, 1984.
7. Nahm, A.H., "Rolling Element Fatigue Testing of Gear Materials," R78AEG476, General Electric, Cincinnati, OH, 1978, NASA CR-135450.
8. Dowson, D., and Higginson, G.R., *Elasto-Hydrodynamic Lubrication*. Pergamon Press, New York, 1966.
9. Johnson, L.G., *The Statistical Treatment of Fatigue Experiments*. Elsevier Publication Co., New York, 1964.

ORIGINAL PAGE IS  
OF POOR QUALITY

TABLE I. - GEAR DATA  
[Gear tolerance per AGMA class 12.]

Number of teeth . . . . .	28
Diametral pitch . . . . .	8
Circular pitch, cm (in.) . . . . .	0.9975 (0.3927)
Whole depth, cm (in.) . . . . .	0.762 (0.300)
Addendum, cm (in.) . . . . .	0.318 (0.125)
Chordal tooth thickness reference, cm (in.) . . . . .	0.485 (0.191)
Pressure angle, deg . . . . .	20
Pitch diameter, cm (in.) . . . . .	8.890 (3.500)
Outside diameter, cm (in.) . . . . .	9.525 (3.750)
Root fillet, cm (in.) . . . . .	0.10 to 0.15 (0.04 to 0.06)
Measurement over pins, cm (in.) . . . . .	9.603 to 9.630 (3.7807 to 3.7915)
Pin diameter, cm (in.) . . . . .	0.549 (0.216)
Backlash reference, cm (in.) . . . . .	0.025 (0.010)
Tip relief, cm (in.) . . . . .	0.0013 (0.0005)
Tooth width, cm (in.) . . . . .	0.64 (0.25)

TABLE II. - CHEMICAL COMPOSITION OF TEST MATERIALS

Element	AISI 9310		M50NiL	
	Gears	RC bars	Gears	RC bars (nominal)
	Composition, wt %			
Carbon:				
Core	0.11	0.11	0.13	0.11 to 0.15
Case	.81	.81	.86	.86
Manganese	.58	.69	.28	-----
Phosphorus	.003	.005	.002	-----
Sulfur	.004	.002	.002	-----
Silicon	.26	.30	.18	-----
Copper	.21	.07	.05	-----
Chromium	1.38	1.24	4.21	4.0 to 4.25
Molybdenum	.13	.11	4.30	4.0 to 4.5
Vanadium	-----	-----	1.19	1.13 to 1.33
Nickel	3.20	3.19	3.44	3.20 to 3.60
Cobalt	-----	-----	.01	-----
Iron	Balance	Balance	Balance	-----

TABLE III. - HEAT TREATMENT PROCEDURE FOR MATERIALS TESTED

Step	Process	AISI 9310						M50NiL					
		Gears			RC bars			Gears			RC bars		
		Temp- erature		Time, hr	Temp- erature		Time, hr	Temp- erature		Time, hr	Temp- erature		Time, hr
		K	°F		K	°F		K	°F		K	°F	
1	Preoxidation	---	---	---	---	---	---	1228	1750	a2	1228	1750	a2
2	Carburizing	1172	1650	8	1242	1775	12	1228	1750	---	1228	1750	b12, c12
3	Tempering	922	1200	10	866	1100	10	922	1200	2	(d)	(d)	---
4	Preheating	---	---	---	---	---	---	1090	1500	---	---	---	---
5	Austenizing or hardening	1088	1500	2.5	1130	1575	.4	1380	2025	.25	1380	2025	15
6	Quenching	---	---	---	---	---	---	866	1100	.2	866	1100	10
7	Tempering	---	---	---	---	---	---	797	975	2	797	975	2
8	Deep freezing	189	-120	---	200	-100	---	200	-100	1	200	-100	1
9	Tempering	450	350	2	455	360	1	797	975	2 + 2	797	975	2

aAir.

bAt 0.7 CP.

cAt 0.6 CP.

dOil quench.

eOmitted by error.

TABLE IV. - METALLURGICAL CASE AND CORE CHARACTERISTICS OF TEST SPECIMENS

Material	Effective case depth at Rockwell C 50		Rockwell C hardness		Case retained austenite, vol %	Grain size		Room temperature	478 K (400 °F)		
	mm	in.	Case	Core		Case	Core		Fracture toughness		
									MPa $\sqrt{m}$	ksi $\sqrt{in.}$	MPa $\sqrt{m}$
AISI 9310: Gears RC bars	0.81 .84	0.032 .033	61 61.4	38 38	10 11.2	--	---	94	85	---	---
M50NiL: Gears RC bars	1.9 2.0	0.075 .080	60.6 64	48 45	46.0 8.0	>7	5-7	53	48	120	108

ORIGINAL PAGE IS  
OF POOR QUALITY

ORIGINAL PAGE IS  
OF POOR QUALITY

TABLE V. - LUBRICANT PROPERTIES


Property	Synthetic paraffinic oil plus additives <sup>a</sup>
Kinematic viscosity, cm <sup>2</sup> /sec (cS) at	
244 K (-20 °F)	2500x10 <sup>-2</sup> (2500)
311 K (100 °F)	31.6x10 <sup>-2</sup> (31.6)
372 K (210 °F)	5.5x10 <sup>-2</sup> (5.5)
477 K (400 °F)	2.0x10 <sup>-2</sup> (2.0)
Flashpoint, K (°F)	508 (455)
Fire point, K (°F)	533 (500)
Pour point, K (°F)	219 (-65)
Specific gravity	0.8285
Vapor pressure at 311 K (100 °F), torr	0.1
Specific heat at 311 K (100 °F), J/kg K (Btu/lb °F)	2190 (0.523)

<sup>a</sup>EP additives: Lubrizol 5002 (5 vol %) containing 0.03 vol % phosphorus and 0.93 vol % sulfur.


TABLE VI. - FATIGUE LIFE RESULTS FOR TEST GEARS AND ROLLING-CONTACT BARS

Material	System life, millions of stress cycles		Weibull slope	Failure index	Confidence number at 10-percent life level, percent <sup>a</sup>
	10 Percent	50 Percent			
Gears:					
VAR AISI 9310	18.8	46	2.1	18 out of 19	----
VIM-VAR AISI 9310	48	200	1.3	24 out of 33	92.5
VIM-VAR M50NiL	217	496	2.3	2 out of 20	99
Rolling-contact bars:					
VAR AISI 9310	4.2	9.4	2.3	10 out of 10	----
VIM-VAR AISI 9310	6.84	15.74	2.26	10 out of 10	76
VIM-VAR M50NiL	90.6	219	2.1	5 out of 20	99

<sup>a</sup>Percentage of time that the 10-percent life obtained with VAR AISI 9310 will have the same relation to the 10-percent life obtained with VIM-VAR AISI 9310 or VIM-VAR M50NiL.

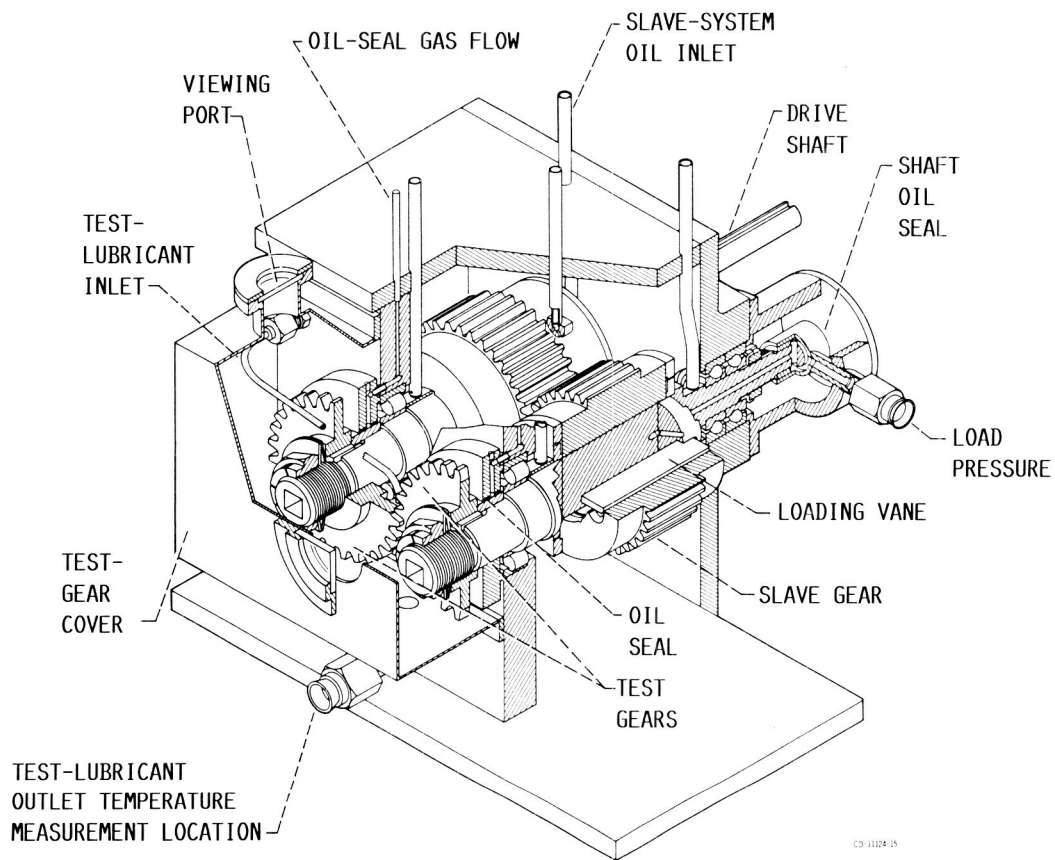

(a) CUTAWAY VIEW.

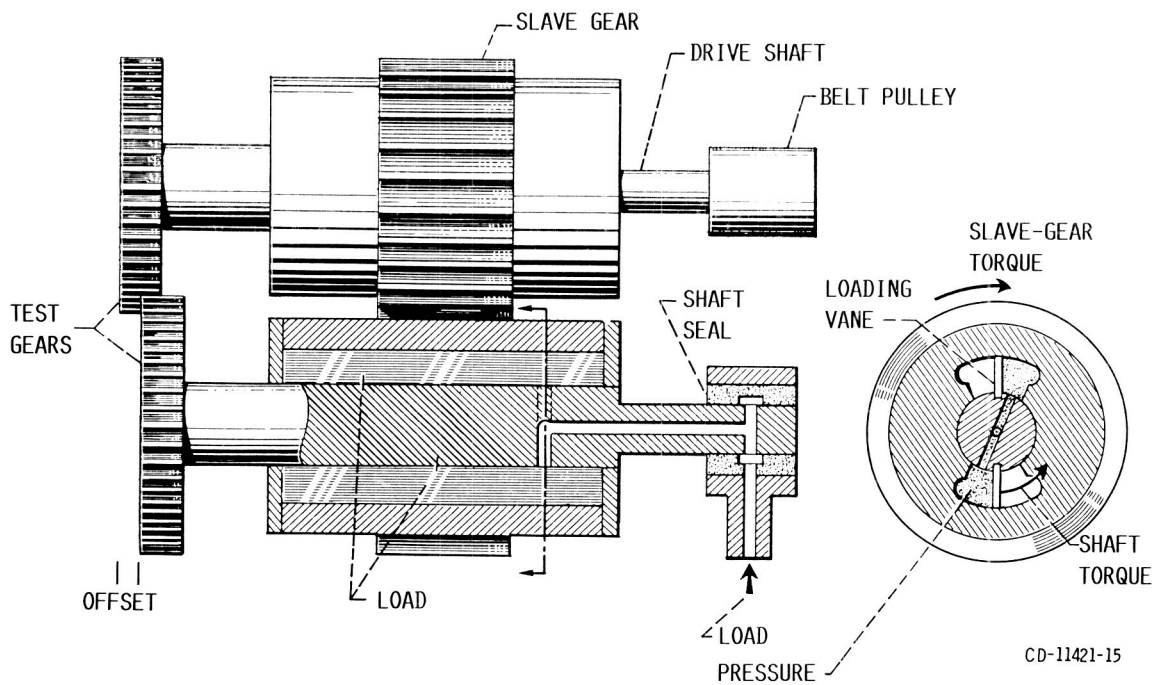

(b) SCHEMATIC DIAGRAM.

FIG. 1. NASA LEWIS RESEARCH CENTER'S GEAR FATIGUE TEST APPARATUS.

ORIGINAL PAGE IS  
OF POOR QUALITY





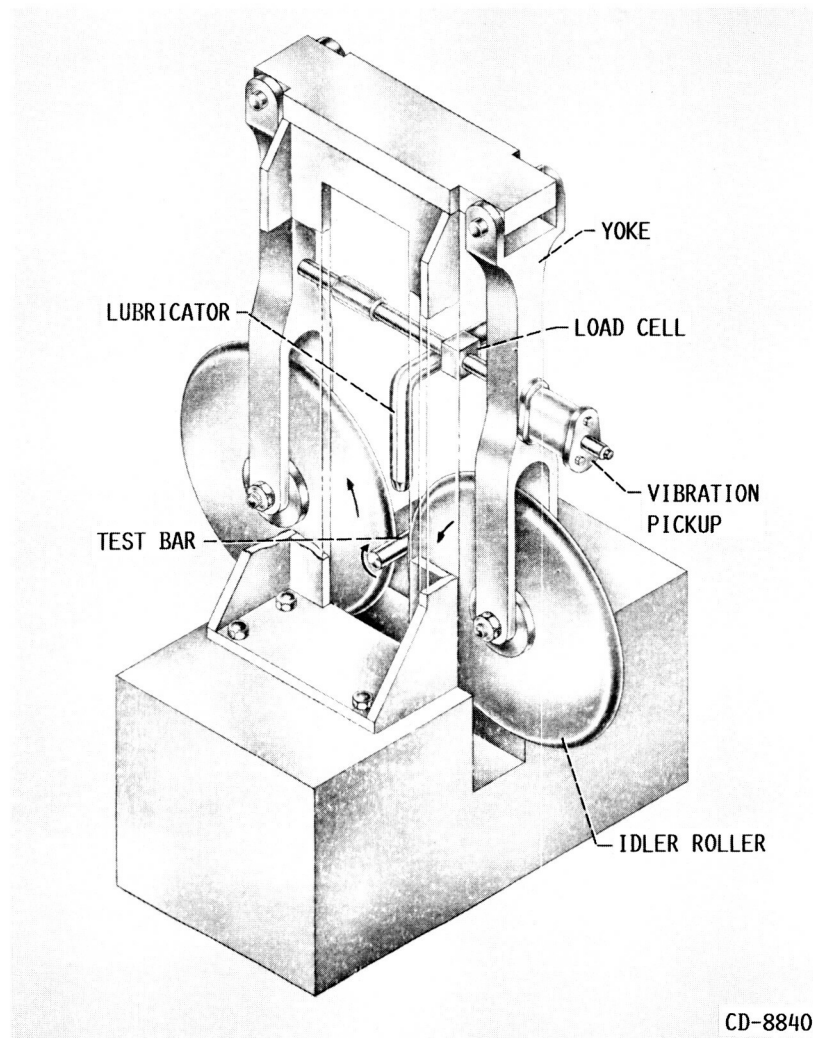


FIG. 2. ROLLING-CONTACT FATIGUE TESTER.

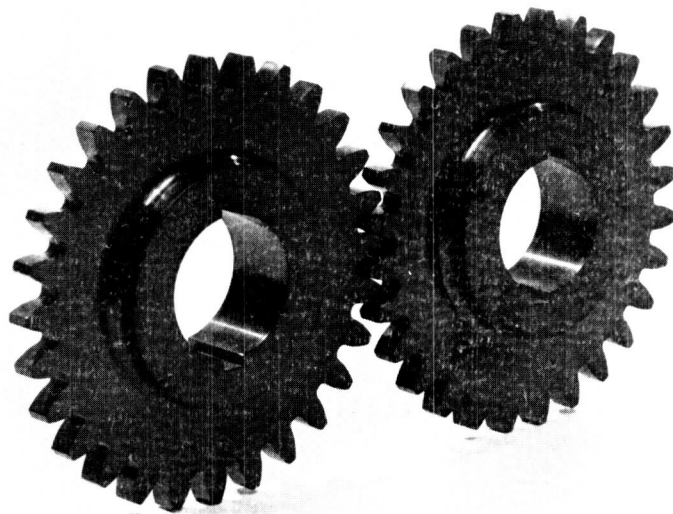

C-72-3230


(a) AISI 9310.

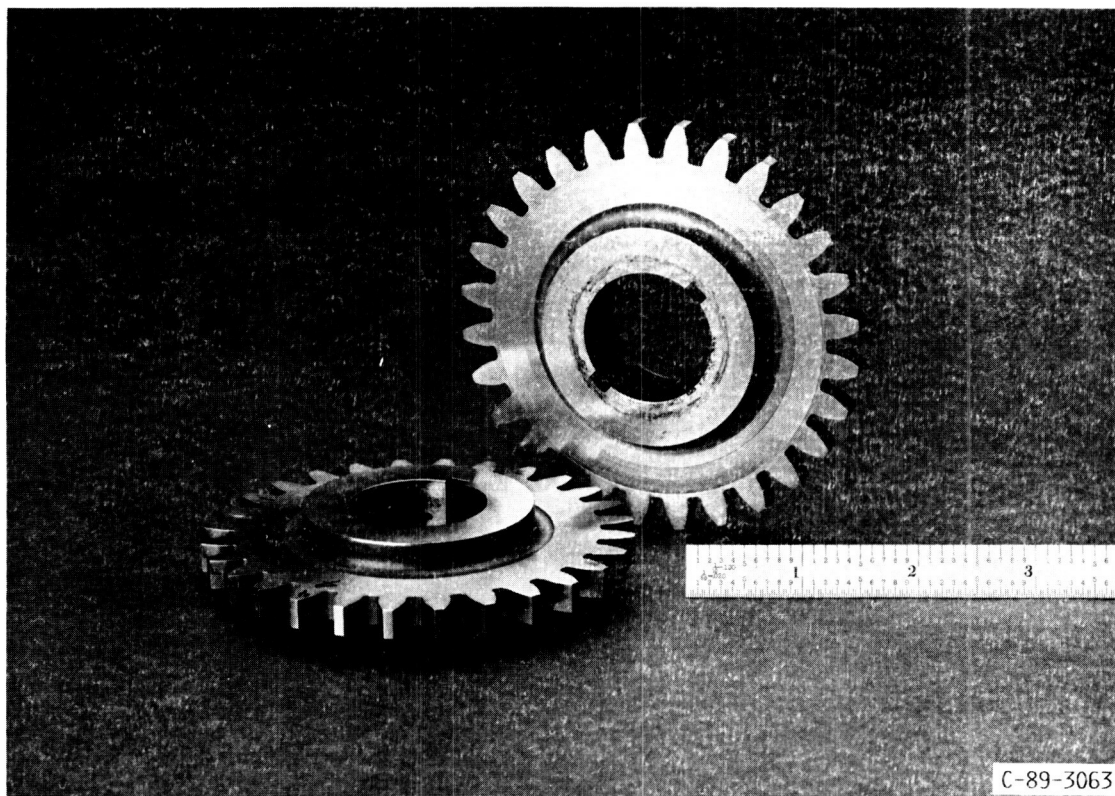


C-89-3063

(b) M50NiL.


FIG. 3. TEST GEARS.

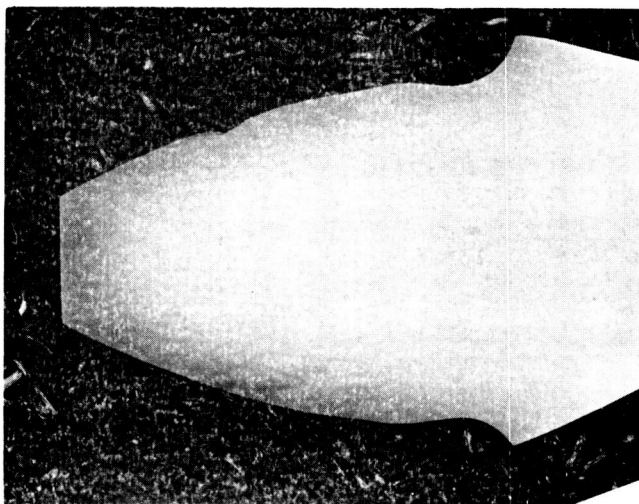

(a) 9310.

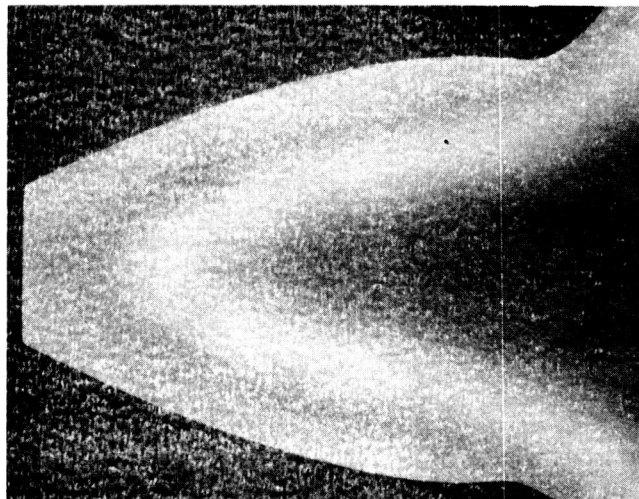


(b) M50NiL WITH NO DEEP FREEZE.

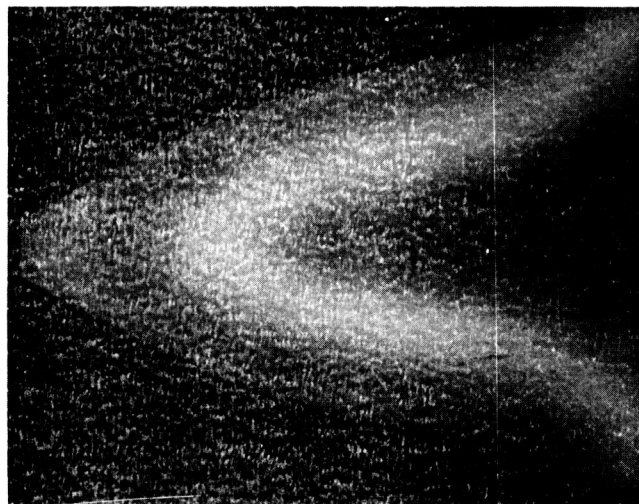


(c) M50NiL WITH DEEP FREEZE.

FIG. 4. CROSS SECTION THROUGH AISI 9310 AND M50NiL WITH AND WITHOUT 200 K ( $-100^{\circ}\text{F}$ ) DEEP FREEZE.




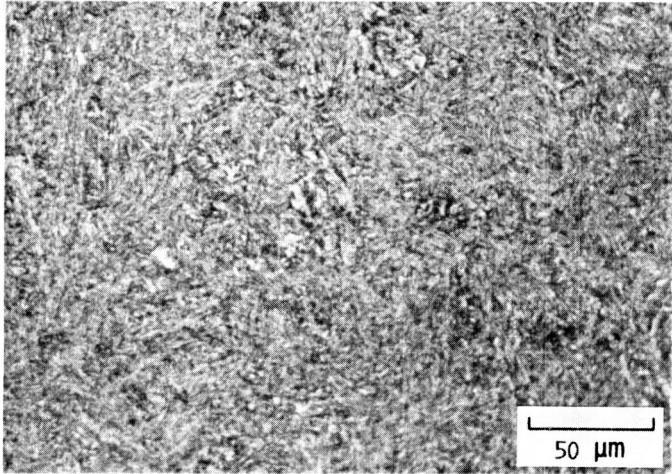


(a) AISI 9310 CASE.

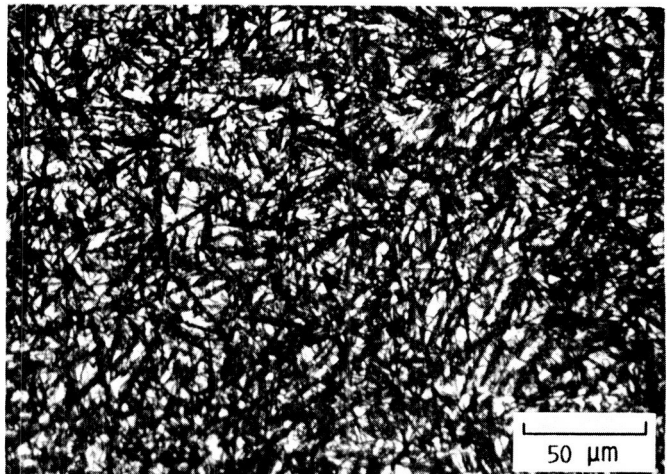

(c) M50NiL CASE.

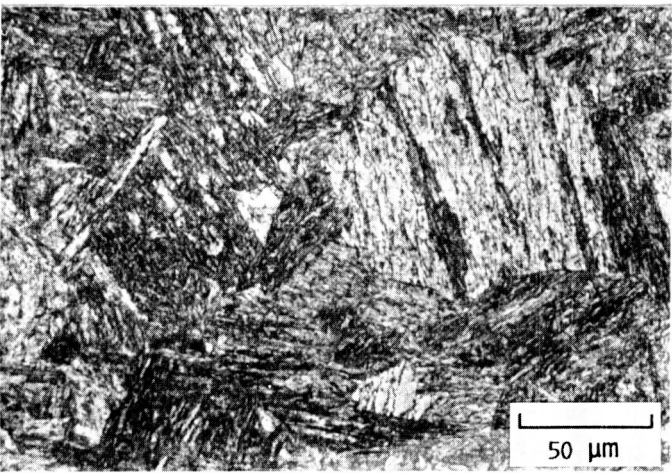

(b) AISI 9310 CORE.

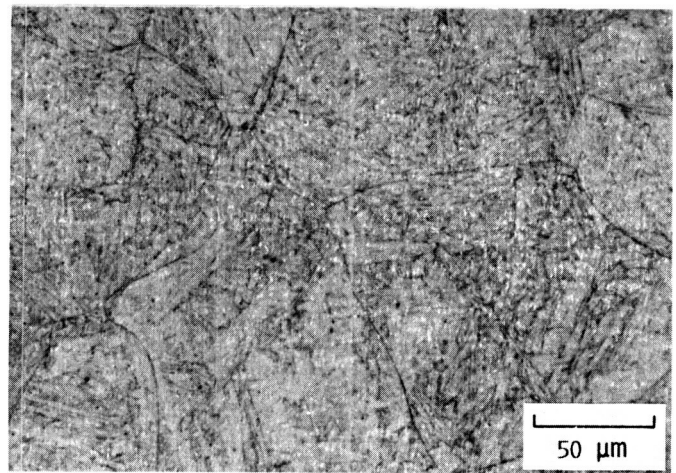

(d) M50NiL CORE.

FIG. 5. CASE AND CORE MICROPHOTOGRAPHS OF AISI 9310 AND M50NiL TEST SAMPLES.

ORIGINAL PAGE IS  
OF POOR QUALITY

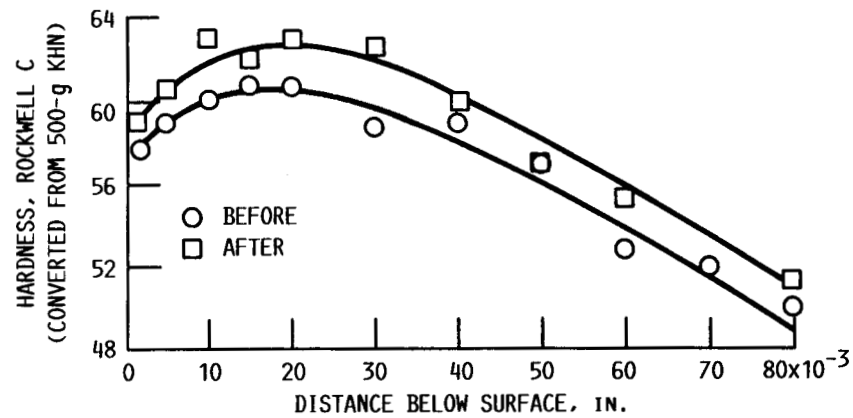


FIG. 6. HARDNESS OF VIM-VAR M50NiL GEAR TOOTH BEFORE AND AFTER ONE DEEP FREEZE AND TEMPER CYCLE.



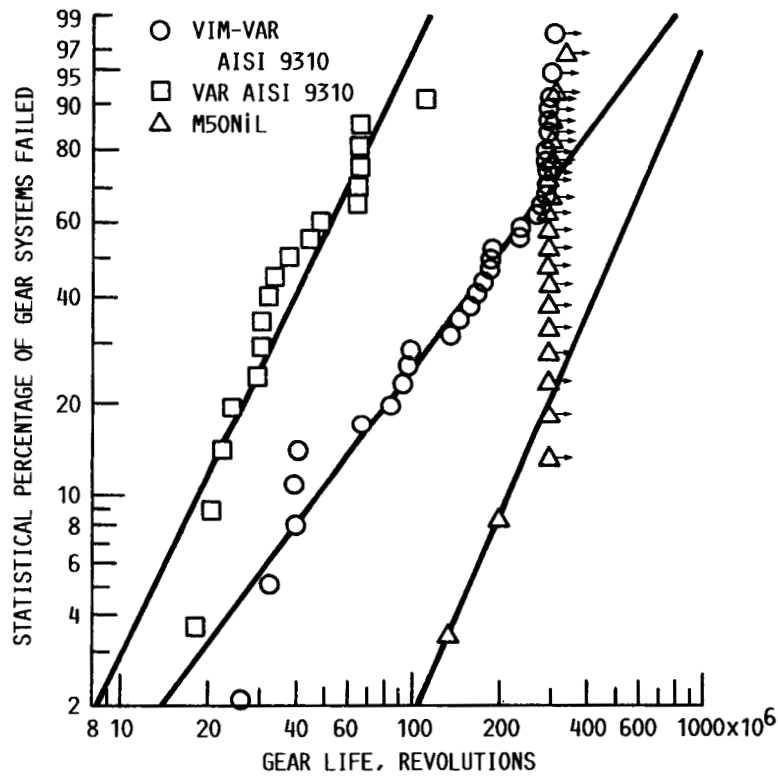


FIG. 7. SURFACE FATIGUE LIFE OF VAR AND VIM-VAR AISI 9310 AND M50NiL TEST GEARS. SPEED, 10 000 rpm; MAXIMUM HERTZ STRESS, 1.71 GPa (248 ksi); TEMPERATURE, 350 K (170 °F); LUBRICANT, SYNTHETIC PARAFFIN WITH 5 VOL % LUBRIZOL 5002 (EP ADDITIVE). ARROWS DENOTE SUSPENSION OF TESTS.

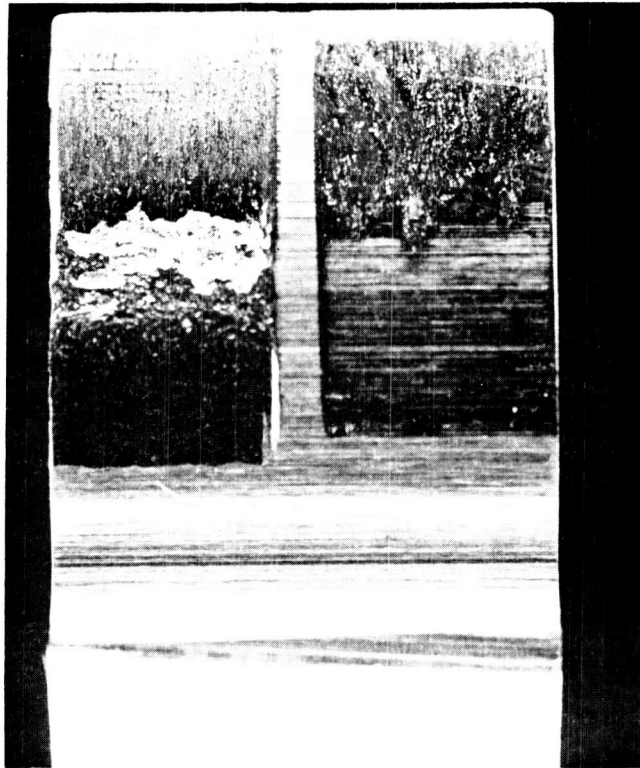

(a) AISI 9310 GEARS.

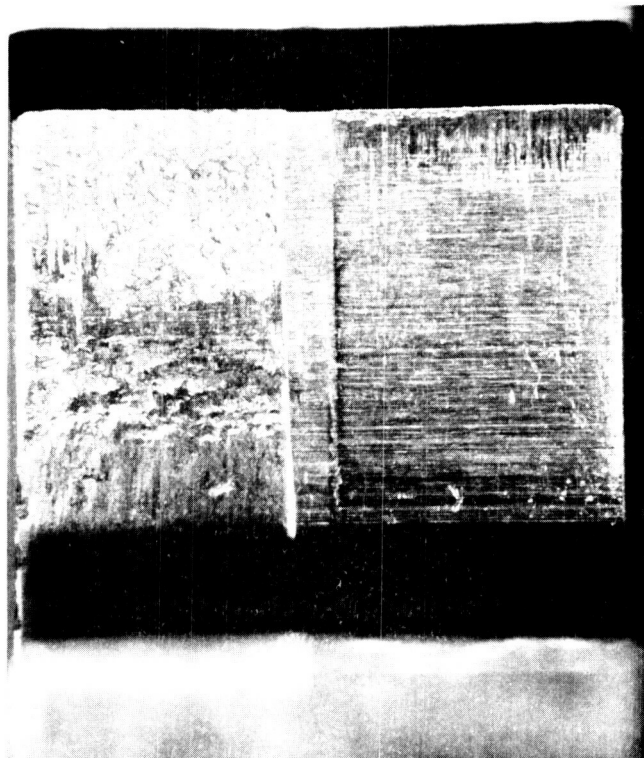

(b) M50NiL GEARS.

FIG. 8. TYPICAL FATIGUE SPALL OF AISI 9310 AND M50NiL TEST GEARS. SPEED, 10 000 rpm; MAXIMUM HERTZ STRESS, 1.71 GPa (248 ksi); TEMPERATURE, 350 K (170 °F); LUBRICANT, SYNTHETIC PARAFFIN WITH 5 VOL % LUBRIZOL 5002 (EP ADDITIVE).

ORIGINAL PAGE IS  
OF POOR QUALITY

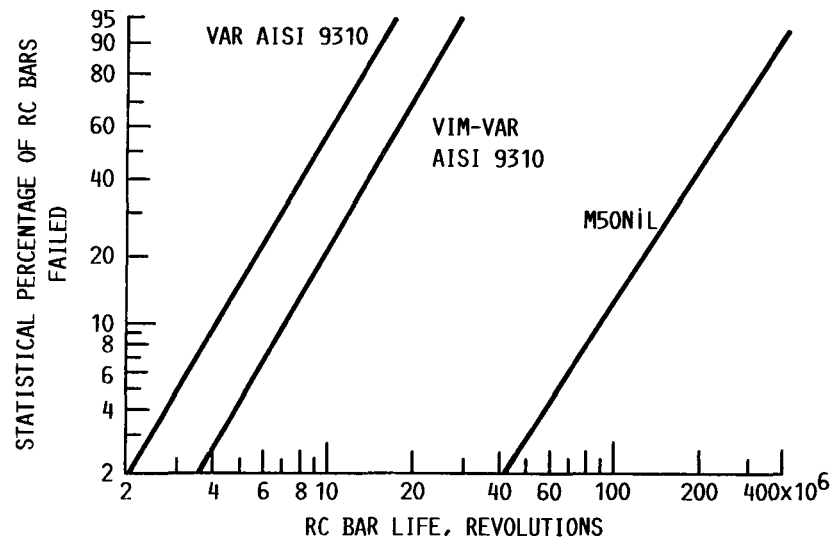


FIG. 9. ROLLING-CONTACT FATIGUE LIFE OF VAR AND VIM-VAR AISI 9310 AND M50NiL IN ROLLING-CONTACT FATIGUE TESTER. MAXIMUM HERTZ STRESS, 4.83 GPa (700 ksi); BAR SPEED, 12 500 rpm; TEMPERATURE, AMBIENT; LUBRICANT, MIL-L-7808G.


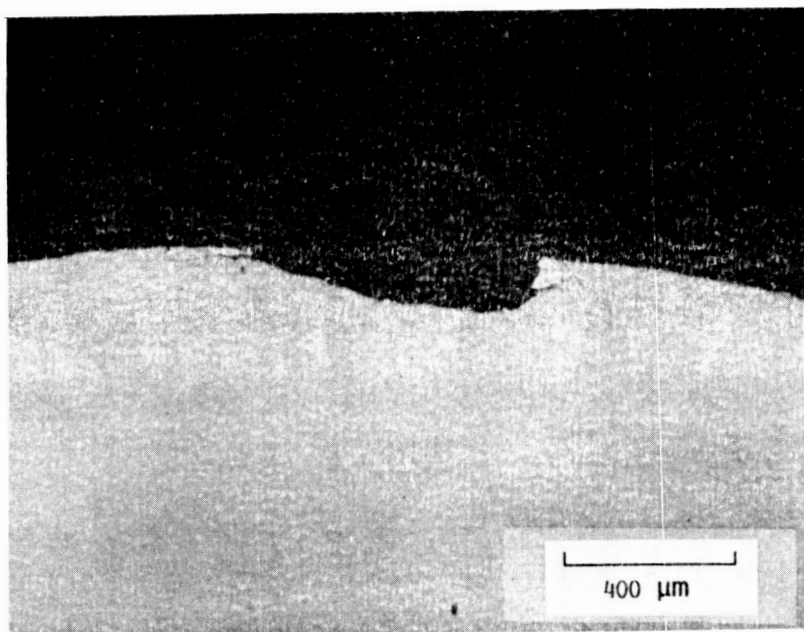


FIG. 10. TYPICAL ROLLING-ELEMENT FATIGUE FAILURE.

ORIGINAL PAGE IS  
OF POOR QUALITY

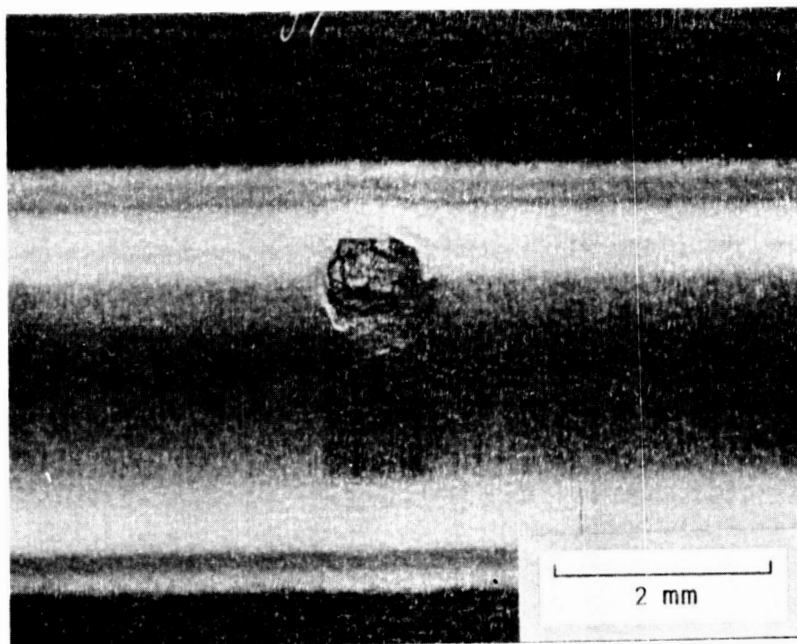

## Report Documentation Page

1. Report No. NASA TM-101979 AVSCOM TR-89-C-011		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle  Surface Fatigue Life of Carburized and Hardened M50NiL and AISI 9310 Spur Gears and Rolling-Contact Test Bars				5. Report Date	
				6. Performing Organization Code	
7. Author(s)  Dennis P. Townsend and Eric N. Bamberger				8. Performing Organization Report No.  E-4678	
9. Performing Organization Name and Address  NASA Lewis Research Center Cleveland, Ohio 44135-3191 and Propulsion Directorate U.S. Army Aviation Research and Technology Activity—AVSCOM Cleveland, Ohio 44135-3127				10. Work Unit No.  505-63-51 1L162209A47A	
				11. Contract or Grant No.	
				13. Type of Report and Period Covered  Technical Memorandum	
12. Sponsoring Agency Name and Address  National Aeronautics and Space Administration Washington, D.C. 20546-0001 and U.S. Army Aviation Systems Command St. Louis, Mo. 63120-1798				14. Sponsoring Agency Code	
15. Supplementary Notes  Prepared for the 25th Joint Propulsion Conference cosponsored by the AIAA, ASME, SAE, and ASEE, Monterey, California, July 10-12, 1989. Dennis P. Townsend, NASA Lewis Research Center; Eric N. Bamberger, General Electric Company, Cincinnati, Ohio.					
16. Abstract  Spur gear endurance tests and rolling-element surface tests were conducted to investigate vacuum-induction-melted, vacuum-arc-melted (VIM-VAR) M50NiL steel for use as a gear steel in advanced aircraft applications, to determine its endurance characteristics, and to compare the results with those for standard VAR and VIM-VAR AISI 9310 gear material. Tests were conducted with spur gears and rolling-contact bars manufactured from VIM-VAR M50NiL and VAR and VIM-VAR AISI 9310. The gear pitch diameter was 8.9 cm (3.5 in.). Gear test conditions were an inlet oil temperature of 320 K (116 °F), and outlet oil temperature of 350 K (170 °F), a maximum Hertz stress of 1.71 GPa (248 ksi), and a speed of 10 000 rpm. Bench rolling-element fatigue tests were conducted at ambient temperatures with a bar speed of 12 500 rpm and a maximum Hertz stress of 4.83 GPa (700 ksi). The VIM-VAR M50NiL gears had a surface fatigue life that was 4.5 and 11.5 times that for VIM-VAR and VAR AISI 9310 gears, respectively. The surface fatigue life of the VIM-VAR M50NiL rolling-contact bars was 13.2 and 21.6 times that for the VIM-VAR and VAR AISI 9310, respectively. The VIM-VAR M50NiL material was shown to have good resistance to fracture through a fatigue spall and to have fatigue life far superior to that of both VIM-VAR and VAR AISI 9310 gears and rolling-contact bars.					
17. Key Words (Suggested by Author(s))  Gears; M50NiL; Fatigue life; AISI 9310; Rolling-contact fatigue			18. Distribution Statement  Unclassified—Unlimited Subject Category 37		
19. Security Classif. (of this report)  Unclassified		20. Security Classif. (of this page)  Unclassified		21. No of pages  18	
				22. Price*  A03	