

Diamondlike Carbon Protective Coatings for Optical Windows

Diane M. Swec and Michael J. Mirtich
Lewis Research Center
Cleveland, Ohio

Prepared for the
1989 Technical Symposia on Aerospace Sensing
sponsored by The International Society for Optical Engineering
Orlando, Florida, March 27-31, 1989



{NASA-TM-102111} DIAMONDLIKE CARBON
PROTECTIVE COATINGS FOR OPTICAL WINDOWS
{NASA. Lewis Research Center} 16 pCSCL 20F

N89-27506

Unclas
G3/74 0224122

DIAMONDLIKE CARBON PROTECTIVE COATINGS FOR OPTICAL WINDOWS

Diane M. Swec and Michael J. Mirtich
National Aeronautics and Space Administration
Lewis Research Center
Cleveland, Ohio 44135

SUMMARY

Diamondlake carbon (DLC) films were deposited on infrared transmitting optical windows and were evaluated as protective coatings for these windows exposed to particle and rain erosion. The DLC films were deposited on zinc selenide (ZnSe) and zinc sulfide (ZnS) by three different ion beam methods: (1) sputter deposition from a carbon target using an 8-cm argon ion source, (2) direct deposition by a 30-cm hollow cathode ion source with hydrocarbon gas in argon, and (3) dual beam direct deposition by the 30-cm hollow cathode ion source and an 8-cm argon ion source. In an attempt to improve the adherence of the DLC films on ZnSe and ZnS, ion beam cleaning, ion implantation with helium and neon ions, or sputter deposition of a thin, ion beam intermediate coating was employed prior to deposition of the DLC film. The protection that the DLC films afforded the windows from particle and rain erosion was evaluated, along with the hydrogen content, adherence, intrinsic stress, and infrared transmittance of the films. Because of elevated stress levels in the ion beam sputtered DLC films and in those ion beam deposited with butane, films thicker than $0.1\text{ }\mu\text{m}$ and with good adherence on ZnS and ZnSe could not be generated. An intermediate coating of germanium successfully allowed the DLC films to remain adherent to the optical windows and caused only a negligible reduction in the specular transmittance of the ZnS and ZnSe at $10\text{ }\mu\text{m}$. These DLC films did not protect the optical windows from simulated particle erosion; however, they did improve the performance of ZnS exposed to rain erosion.

INTRODUCTION

Infrared-transparent materials, such as zinc sulfide (ZnS) and zinc selenide (ZnSe), are those most often used as optical windows. However, these materials are soft and undergo serious degradation when subjected to severe particle-impacting environmental conditions (ref. 1). Therefore, attempts have been made to harden these window surfaces to protect them from sand or rain impact.

Hard thin films may be used to maintain the optical integrity of infrared windows. The desired films must be adherent and durable such that they protect ZnS and ZnSe windows from particle and rain erosion as well as chemical attack. A low film-stress level is also desirable so that a thick layer of these hard films can be deposited for maximum protection of the soft materials. One film with this potential is diamondlake carbon (DLC) (refs. 1 and 2). DLC films are transparent over a broad spectral range, resist chemical attack, and are moisture and abrasion resistant.

Three different ion beam methods were used to deposit DLC films on fused silica (SiO_2), silicon (Si), ZnS, and ZnSe: (1) sputter deposition from a carbon target by an 8-cm argon ion source, (2) direct deposition by a 30-cm

hollow cathode ion source with hydrocarbon gas in argon (Ar), and (3) dual beam direct deposition by the 30-cm hollow cathode and an 8-cm argon ion source. To improve the adherence of the DLC films on ZnS and ZnSe, the following techniques were employed prior to deposition of the film: (1) ion beam cleaning, (2) ion implantation via "knock on" of thin carbon films by 100-keV nitrogen ions, (3) ion implantation with 100-keV neon and helium ions, and (4) thin, ion beam sputter-deposited intermediate coatings of germanium (Ge) or silicon. The DLC films were then evaluated for hydrogen content, adherence, intrinsic stress, infrared transmittance, and protection from particle and rain erosion. An erosion test employing a microsandblaster with 27- μm -diameter aluminum oxide (Al_2O_3) particles was developed to determine quantitative values of the protection that the diamondlike films afforded the window surfaces. After erosion an infrared (IR) spectrophotometer was used to indicate the change in specular transmittance between 2.5 and 50 μm . The DLC-coated windows were also subjected to water droplets at 180 m/sec for exposure times up to 15 min in a rain erosion facility at Wright Patterson Air Force Base. These samples were qualitatively evaluated by optically viewing the pitting, microcracks, and subsurface ring cracks that resulted from the erosion. The results of these studies are presented in this paper.

APPARATUS AND PROCEDURE

Diamondlike carbon films were ion beam sputter deposited from a pyrolytic graphite target by an 8-cm-diameter source (ref. 3). A 1000-eV argon ion beam was produced for sputter cleaning and deposition. The ion beam current density was $\sim 1.0 \text{ mA/cm}^2$ in the vicinity of the sputter target and substrates, which were located 20 cm downstream of the ion source. The ion source was operated with a hot filament neutralizer in a vacuum facility that maintained pressures of 2×10^{-5} torr during operation. In conjunction with this method, hydrogen gas was introduced in the vacuum chamber to evaluate its effect on these films. The introduction of hydrogen gas raised the background pressure to a range of 7×10^{-5} to 10^{-4} torr. Films 0.1 μm thick were deposited on the various substrates.

A 30-cm-diameter ion source with its optics masked to 10 cm in diameter was used to directly deposit the DLC films (ref. 4). The ion source used argon gas in the hollow cathode located in the main discharge chamber, as well as in the neutralizer. Hydrocarbon gas was introduced through a manifold into the discharge chamber at a molar ratio of 0.28 CH_4 or 0.10 C_4H_{10} to argon. Typically, current densities were 1 mA/cm^2 at a distance of 2.5 cm axially downstream of the grids, and argon ion energies ranged from 90 to 250 eV.

It is believed that amorphous carbon films are produced under conditions where growth and sputtering occur simultaneously, therefore increased sputtering may decrease the number of graphite precursors incorporated in the films and hence improve the quality (ref. 4). An 8-cm ion source with a filament cathode was used during the dual beam deposition to direct a beam of 200- to 600-eV argon ions at a current density of $25 \mu\text{A/cm}^2$ on the substrates while the DLC film was being deposited by the 30-cm source.

The intrinsic stress of the DLC films was measured with a stress gauge, and an adherence tester was used to determine the adherence of the DLC films. The transmittance of the DLC films in the visible region was obtained with an integrating sphere, and the IR transmittance was measured with a spectrophotometer.

An erosion test was developed that used a sandblaster to give quantitative values to the protection that the DLC films afforded fused silica (ref. 5). The fused silica surfaces were exposed to 100- μm -diameter SiO_2 particles at 27 m/sec, and then the protective quality of the film was characterized by the resulting change in specular transmittance by a neon-helium ellipsometer. The protection that the DLC films afforded the ZnS and ZnSe surfaces was quantitatively determined from another simulated particle erosion test (ref. 6). The window surfaces were eroded by exposing them to 27- μm -diameter Al_2O_3 particles with an estimated stream velocity of 335 m/sec in a microsandblaster. The protective quality of the film was then characterized by the change in specular transmittance due to the particle erosion with an IR spectrophotometer between wavelengths of 2.5 and 50 μm .

A facility at the Wright Patterson Air Force Base was employed to evaluate the rain erosion performance of the DLC films. The rain erosion facility consisted of a variable-speed rotating arm apparatus with speeds to 210 m/sec and a simulated rainfall of 7×10^{-4} cm/sec. The rotating arm apparatus employed a horizontally mounted, 8-ft double-arm propeller blade powered by a 400-hp motor. A pipe ring containing hypodermic needles was positioned such that controlled water droplets were sprayed on the test specimens, which were mounted in the blade tips.

RESULTS AND DISCUSSION

Hydrogen Content

Nuclear reaction and combustion analysis for hydrogen was performed on the DLC films (ref. 7). This technique showed that DLC films made by the various deposition methods have very similar hydrogen depth profiles. The atomic ratio of hydrogen to carbon (H/C) was low at the film surface and rose to a constant value at a depth of 50 nm. Table I shows the hydrogen-to-carbon ratios measured one-half of the distance through the DLC films for the three different deposition methods. There is a variation in hydrogen content which depends on the method used to deposit the DLC film. DLC films made by single ion-beam deposition with CH_4 had an H/C ratio of 0.91. Adding the energy of the second ion source (dual beam) reduced this ratio to 0.62. Thus, the second source removed some of the hydrogen. DLC films generated by the single source, but with C_4H_{10} , also had an H/C ratio of 0.62. The films generated by ion beam sputter deposition from a graphite target contained the least amount of hydrogen, an H/C ratio of 0.22. The addition of up to 35 percent hydrogen gas into the vacuum facility during sputter deposition doubled the hydrogen content of these films.

Semiquantitative infrared spectroscopy was also performed on these ion beam deposited films. The integrated intensity of the C-H stretching band at about 3.4 μm indicated that the ratio of chemically bonded hydrogen to carbon was between 0.03 and 0.44 (ref. 7). The difference between the two hydrogen analysis techniques indicates the presence of nonbonded hydrogen in the films.

Intrinsic Stress

The DLC films deposited on Si exhibited a compressive stress that varied depending on the deposition method, hydrocarbon gas, and energy of deposition. Figures 1 to 3 show the stress levels of 0.1- μm -thick DLC films made by the different ion beam deposition methods. Figure 1 is a plot of the compressive stress as a function of the H/Ar gas ratio for CH_4 and C_4H_{10} gases deposited at 110 eV by the single ion-beam source. The stress for each type of film was independent of the H/Ar ratio, but was 2.5 times as large for the C_4H_{10} films as it was for the CH_4 films. Figure 2 shows that the stress in the CH_4 single beam films can be reduced to values as low as 4×10^9 dyne/cm² by decreasing the deposition energy to 90 eV. Figure 3 shows the compressive stress for DLC films deposited by ion sputtering a graphite target (including those films made with the addition of hydrogen). The compressive stress was 1.6×10^{10} dyne/cm² for a pure, sputter-deposited film and rose slightly to 2.3×10^{10} dyne/cm² for a film with hydrogen addition. These stress levels are higher than those for films made by direct ion beam deposition, single or dual, with CH_4 . Table I lists the stress levels for the various DLC films. The data indicate that the film stress does not depend on the hydrogen content, but on other parameters such as deposition technique and conditions, and hydrocarbon gas.

Adherence

The adherence of the DLC films on fused silica was measured by following the procedure used by Mirtich (ref. 8). Films up to 1 μm thick, deposited by either single or dual beam systems with CH_4 , were at least as adherent as the maximum measurable adherence of the tester: namely, 2.8×10^6 N/m². These films were so adherent that, for some of the films, portions of the SiO_2 gave way with the film still intact. Films made by the single ion-beam system with C_4H_{10} began to spall once the thickness reached 0.15 μm , and the films that were sputter deposited from the graphite target began to spall at 0.2 μm thick, indicating an upper limit of the allowable thickness of these films. This was expected, since the stress levels of these two types of DLC films were greater than those made with CH_4 in either the single or dual beam.

In an attempt to improve the adherence of DLC films that were ion beam deposited on ZnS and ZnSe, four techniques were used prior to film deposition (ref. 9). Ion beam cleaning of the window materials was the first technique used, but was not sufficient, as it was with the SiO_2 or Si substrates, to allow the DLC films to remain adherent. The films had negligible adherence ($< 1.4 \times 10^4$ N/m²) and spalled almost immediately after deposition on both ZnS and ZnSe. The second technique involved ion implantation via "knock on" of thin carbon films on the surface of ZnS and ZnSe by 50 to 100 keV nitrogen ions. This technique also failed to allow the DLC films to remain adherent. In the third technique, the window surfaces were ion implanted with neon or helium at energies varying between 50 and 100 keV and at doses from 0.5×10^{17} to 2×10^{17} particles/cm². These films spalled after a period of time. The fourth technique, which used a thin intermediate coating of germanium or silicon, successfully allowed the DLC films to remain adherent. Thin films of Ge or Si, 0.1 μm thick, were ion beam sputter deposited onto ZnS and ZnSe prior to deposition of DLC. The interface of Si looked good on deposit, but spalled as a function of time and/or thickness. Germanium films as thick as 0.4 μm

exhibited adherence equal to the strength of the substrate and showed no sign of deterioration even after 6 months. DLC films deposited on ZnS and ZnSe with an intermediate Ge coating of $0.05\text{ }\mu\text{m}$ showed adherence values of 10^6 to $1.4 \times 10^6\text{ N/m}^2$, also equal to the strength of the substrate. It was also possible to obtain the same adherence values of DLC-Ge films deposited on ZnS and ZnSe substrates that were first implanted with 100-keV He ions at doses to 2×10^{17} particles/cm².

A bonus of ion implantation was the improved physical hardness of the substrate, shown in figure 4 for ZnS. The Vickers hardness as a function of the applied load for unimplanted ZnS and ZnSe was compared with that for ZnS and ZnSe that were He ion implanted at 100 keV at a dose equal to 2×10^{17} particles/cm². At the 5-g indenter load, the surface hardness for the implanted ZnS shows a dramatic 70 percent increase over the unimplanted ZnS.

Transmittance

The transmittance of the DLC films on fused silica in the visible region was obtained by using the Bowman technique (ref. 10). The DLC films obtained from the single ion-beam deposition method with CH₄ have a spectral transmittance similar to those generated by the dual beam source, but the single beam films have lower transmittance values when they are greater than $0.12\text{ }\mu\text{m}$ thick. This is evident in figure 5, where the spectral transmittance is shown for DLC films, $0.15\text{ }\mu\text{m}$ thick, generated by both methods. The $0.15\text{-}\mu\text{m}$ -thick dual beam film has greater transmittance at all wavelengths when compared with the single beam film of the same thickness. The increased absorption most likely arises from the presence of systems of conjugated double bonds within the film, although the presence of oxygen could also play a role (ref. 11). Both the graphitic precursors and the oxygen would be expected to be reduced by the increased sputtering from the second source. A $0.05\text{-}\mu\text{m}$ -thick DLC film that was single ion-beam deposited from CH₄ displays spectral transmittance values greater than 90 percent at wavelengths greater than $0.8\text{ }\mu\text{m}$. Figure 5 also shows spectral data for a $0.17\text{-}\mu\text{m}$ -thick DLC film that was ion beam sputter deposited from a graphite target. The transmittance was measured only between 0.4 and $0.8\text{ }\mu\text{m}$ for this film, and it is very low compared with the DLC films that were direct deposited. The low transmittance of the sputtered film may be due to its low hydrogen content.

The DLC films deposited on Si substrates acted as antireflective coatings, enhancing the infrared transmittance that was greatest at shorter wavelengths and that decreased with increasing wavelength. This antireflective property was observed for all of the DLC films deposited on Si, and therefore was independent of deposition method.

A spectrophotometer was used to measure the IR transmittance of the DLC films deposited on the ZnS and ZnSe substrates. The spectral transmittance of the window material did not change in the wavelength region of 2.5 to $25\text{ }\mu\text{m}$ for the ZnS and ZnSe substrates coated with $0.1\text{-}\mu\text{m}$ -thick DLC films. The use of an intermediate Ge film or ion implantation also did not change the IR transmittance of ZnS and ZnSe. Figure 6 shows the specular IR transmittance of ZnS before and after implantation with 100-keV He ions at a dose of 5×10^{16} particles/cm². The two traces fall on top of each other, indicating that there is no variation in the IR specular transmittance of ZnS after exposure to

100-keV He ions. The intermediate coating of Ge, which allows good DLC film adherence to ZnS and ZnSe, shows only small reductions in IR specular transmittance especially at larger wavelengths. This is shown in figure 7, where the IR specular transmittance of a ZnSe substrate coated with an intermediate layer of 0.03 μm Ge and a 0.1- μm DLC film from the single beam with CH_4 is presented along with the transmittance of an uncoated ZnSe substrate. Although the IR specular transmittance is reduced at shorter wavelengths, only a 1 percent loss occurs at 10 μm . This reduction could be eliminated by picking the proper DLC and Ge thicknesses to allow the combination to become an antireflective coating.

Erosion Tests

To determine the protection the DLC films afforded the ZnS and ZnSe, the surfaces were exposed to both 27- μm -diameter Al_2O_3 particles in a micro-sandblaster and water droplets at 180 m/sec for exposure times up to 15 min.

Particle erosion. - The erosion protection that the various DLC films afforded fused silica was first evaluated to determine the best method of coating the optical windows. For this test, 2- by 2-cm SiO_2 samples were one-half coated with the DLC films and then placed in the sandblaster (refs. 5 and 12). Only half of the fused silica and half of the DLC film were then exposed to the SiO_2 particles for various periods of time. The specular transmittance data were normalized to eliminate the uncertainty in the various parameters of the particle erosion test, and are presented in a manner that eliminates the exposure time and highlights the protection afforded by the DLC films. Figure 8 is the normalized specular transmittance after the erosion of uncoated fused silica and of fused silica coated with DLC films, 0.1 and 0.2 μm thick, made by the single ion beam with CH_4 . The unprotected fused silica has a slope of one. It is clear that the DLC films extend the erosion lifetime of the fused silica and that the 0.2- μm DLC film extends the lifetime more than the 0.1- μm DLC film. The protection of the different ion beam deposited DLC 0.1- μm films are presented in figure 9. The DLC films generated by ion beam sputter deposition and by either single or dual ion-beam deposition with CH_4 protected the fused silica, and the protection appears to be independent of the deposition method. The ion beam sputter-deposited DLC films with the addition of hydrogen are also presented. These films eroded at a faster rate than the unprotected fused silica, thus making them less erosion resistant than the other DLC films.

The ZnS and ZnSe substrates were one-half coated with the DLC films that were determined to give the best erosion protection to fused silica and were exposed to the Al_2O_3 particles in the microsandblaster (ref. 6). Figures 10 and 11 indicate the change in specular transmittance at 10 μm due to total erosion time for various surfaces of ZnS and ZnSe, respectively, coated with the DLC films. In both figures there is an envelope that portrays the erosion rate of the uncoated surfaces. This envelope is necessary because each ZnS and ZnSe substrate had a slightly different initial transmittance because the substrate thickness was not the same, although the erosion follows the same curve. The DLC films were 0.1 μm thick, and were either sputter deposited from a graphite target or direct deposited from the single ion-beam source with CH_4 . An intermediate layer of 0.03- μm Ge was used in all cases. Some of the ZnS and ZnSe surfaces were also first He ion implanted at 100 keV at doses of 0.5×10^{17} and 2×10^{17} particles/ cm^2 , and then coated with the DLC film from the

single beam with CH_4 . As both figures indicate, neither the DLC films nor the ion implantation plus the DLC film afforded the ZnS and ZnSe surfaces any extension in particle erosion lifetime after exposure to the Al_2O_3 particles.

Rain erosion. - Only ZnS surfaces were evaluated for rain erosion performance in the facility at Wright Patterson Air Force Base. The ZnS surfaces were first polished to a 20/10 finish, but many small pits remained in the surface which could not be removed by polishing. This was undesirable since these pits could be a source of crack propagation during the rain erosion testing. Zinc sulfide, DLC coated ZnS, and ZnS that was first implanted with 100-keV He ions at a dose to 2×10^{17} particles/cm² and then coated with the DLC film were subjected to rain erosion. Although no quantitative data will be presented herein, it was clear from optically viewing the ZnS surfaces exposed to the water droplets at 400 mph that there was a performance improvement in the ZnS surface that was ion implanted, coated with a 0.04- μm intermediate layer of Ge, and then coated with a 0.1- μm DLC film from the single beam with CH_4 . In comparison with ZnS or even ZnS windows coated with a 0.1- μm -thick DLC film, the ion implantation plus the DLC coating decreased the number of new pits and delayed the start of subsurface ring fractures. This could be expected since the ion implantation improved the physical hardness (fig. 4) at the surface to a depth of $\sim 1.0 \mu\text{m}$ of the ZnS (ref. 9). There also were no changes in the specular transmittance between 2.5 and 25 μm for the ion-implanted and DLC-coated ZnS surface after it was exposed to rain erosion.

Since ion implantation of the ZnS window resulted in improved performance, a ZnS surface was implanted with He^+ at 1 MeV to further increase the depth of surface physical hardness. However, during the rain erosion test of this ZnS surface (which was also coated with 0.1- μm DLC and 0.04- μm Ge), the ion-implanted surface layer delaminated from the ZnS substrate.

CONCLUSIONS

Three different ion beam methods were used to deposit diamondlike carbon (DLC) films on various substrates. The hydrogen content of the ion beam deposited DLC films was nearly one, while the ion beam sputter-deposited films had a relatively low H/C ratio even with the addition of hydrogen gas. The compressive stress exhibited by the DLC films did not depend on the hydrogen content, but on other parameters such as the deposition technique and conditions, and hydrocarbon gas. Elevated stress levels of DLC films that were ion beam deposited with C_4H_{10} or ion beam sputter deposited from a graphite target indicated that thick films with good adherence on ZnS and ZnSe could not be generated.

Even though the DLC films on fused silica exhibited adherence as good as the maximum measurable adherence of the tester, these films were not as adherent on the ZnS and ZnSe substrates. Therefore, four techniques were used prior to the deposition of the DLC films to improve the adherence. Ion beam cleaning and ion implantation did not increase film adherence. Ion implantation did, however, improve the physical hardness of the substrates. An intermediate coating of Ge successfully allowed the DLC films to remain adherent, and exhibited an adherence equal to the strength of the substrate. This intermediate Ge film caused a small reduction in the IR specular transmittance of ZnS and ZnSe at shorter wavelengths, but only a 1 percent loss occurred at 10 μm .

Since the DLC films deposited on Si acted as an antireflective coating, thereby enhancing the IR transmittance, this reduction could be eliminated by picking the proper combination of DLC and Ge thicknesses to produce an antireflective coating.

Although ion implantation plus a DLC film did not protect the ZnS and ZnSe windows exposed to the simulated particle erosion, it did improve the performance of ZnS exposed to rain erosion. The ZnS windows that were He ion implanted and coated with DLC and an intermediate Ge layer had fewer new surface pits and a delayed start of subsurface ring cracks. Hardening the window surface itself by ion implantation, in addition to coating it with a thick stress-free diamondlike carbon film, might increase the lifetime of infrared transmitting windows and protect them from both rain and less severe particle erosion.

REFERENCES

1. Nadler, M.P.; Donovan, T.M.; and Green, A.K.: Thermal Annealing Study of Carbon Films Formed by the Plasma Decomposition of Hydrocarbons. *Thin Solid Films*, vol. 116, no. 1-3, June 22, 1984, pp. 241-247.
2. Holland, L.; and Ojha, S.M.: Infrared Transparent and Amorphous Carbon Grown Under Ion Impact in a Butane Plasma. *Thin Solid Films*, vol. 48, no. 3, Feb. 1, 1978, pp. L21-L23.
3. Banks, B.A.; and Rutledge, S.K.: Ion Beam Sputter Deposited Diamond-Like Films. NASA TM-82873, 1982.
4. Mirtich, M.J.; Swec, D.M.; and Angus, J.C.: Dual Ion Beam Deposition of Carbon Films With Diamondlike Properties. NASA TM-83743, 1984.
5. Nir, D.: Mechanical Protection of DLC Films on Fused Silica Slides. NASA TM-87056, 1985.
6. Swec, D.M.; Mirtich, M.J.; Nir, D.; and Banks, B.A.: Comparison of Protective Coatings for Infrared Transmitting Windows. *J. Vac. Sci. Technol. A*, vol. 4, no. 6, Nov.-Dec. 1986, pp. 3030-3031.
7. Angus, J.C.; Stuitz, J.E.; Shiller, P.J.; McDonald, J.R.; Mirtich, M.J.; and Domitz, S.: Composition and Properties of the So-Called "Diamond-Like" Amorphous Carbon Films. *Thin Solid Films*, vol. 118, no. 3, Aug. 17, 1984, pp. 311-320.
8. Mirtich, M.J.: Adherence of Ion Beam Sputter Deposited Metal Films on H-13 Steel. *J. Vac. Sci. Technol.*, vol. 18, no. 2, Mar. 1981, pp. 186-189.
9. Mirtich, M.J.; Nir, D.; Swec, D.M.; and Banks, B.A.: The Use of Intermediate Layers to Improve the Adherence of Diamondlike Carbon Films on ZnS and ZnSe. *J. Vac. Sci. Technol. A*, vol. 4, 1986, pp. 2680-2681.
10. Bowman, R.L.; Mirtich, M.J.; and Weigand, A.J.: The Changes in Optical Properties of Various Transmitting Materials Due to Simulated Micro-meteoroid Exposure. NASA TM X-52687, 1969.

11. Angus, J.C.; Mirtich, M.J.; and Wintucky, E.G.: Ion Beam Deposition of Amorphous Carbon Films With Diamond Like Properties. Metastable Materials Formation by Ion Implantation, S.T. Picraux and W.J. Choyke, eds., North-Holland, 1982, pp. 433-440.
12. Mirtich, M.J.; Nir, D.; Swec, D.M.; and Banks, B.A.: Diamondlike Carbon Protective Coatings for IR Materials. NASA TM-87083, 1985.

TABLE I. - PROPERTIES OF DIAMONDLIKE CARBON FILMS
DEPOSITED BY DIFFERENT ION BEAM
DEPOSITION METHODS

Deposition method	Stress, dyne/cm ²	Hydrogen content, H/C
Single beam, CH ₄	0.9x10 ¹⁰	0.91
Single beam, C ₄ H ₁₀	2.6	.62
Dual beam, CH ₄	.9	.62
Graphite sputtering	1.6	.22
Graphite sputtering + H ₂ addition	2.3	.53

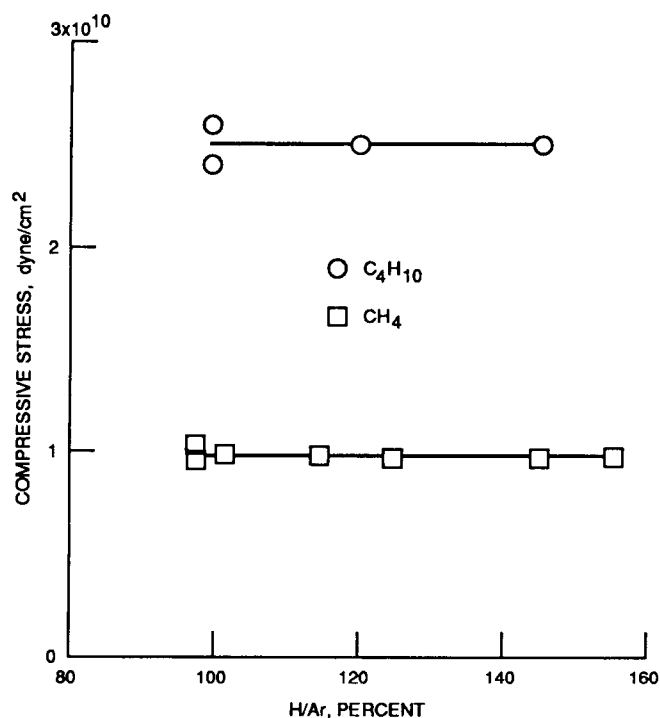


Figure 1. - Compressive stress as function of H/Ar gas ratio for 0.1- μ m-thick DLC films made with CH₄ and C₄H₁₀ in the single ion-beam source at 110 eV.

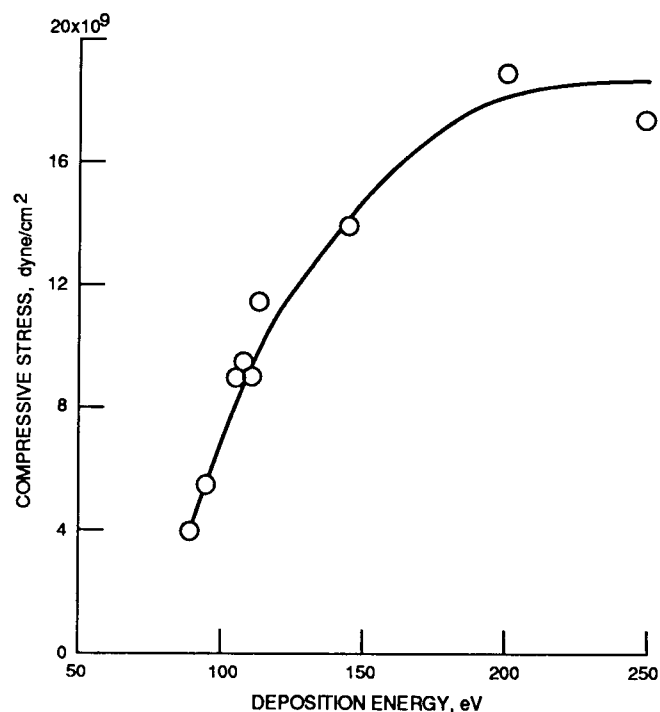


Figure 2. - Compressive stress as function of deposition energy for 0.1- μ m-thick DLC films made with CH₄ in the single ion-beam source.

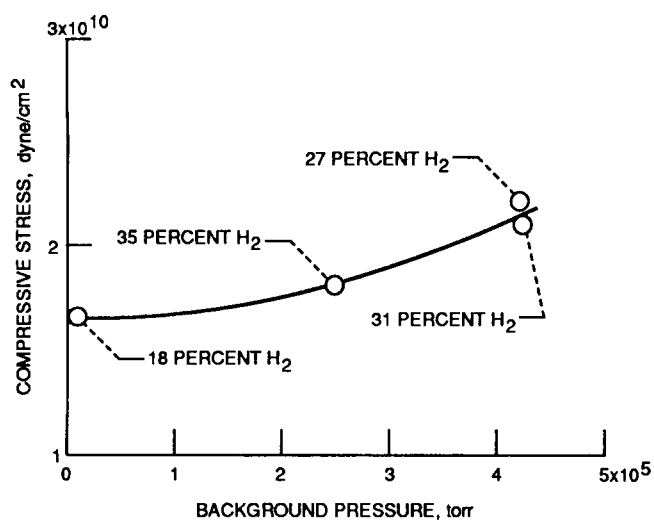


Figure 3. - Compressive stress as function of background pressure for 0.1- μ m-thick DLC films sputter deposited from a graphite target with the addition of H₂ into the vacuum facility.

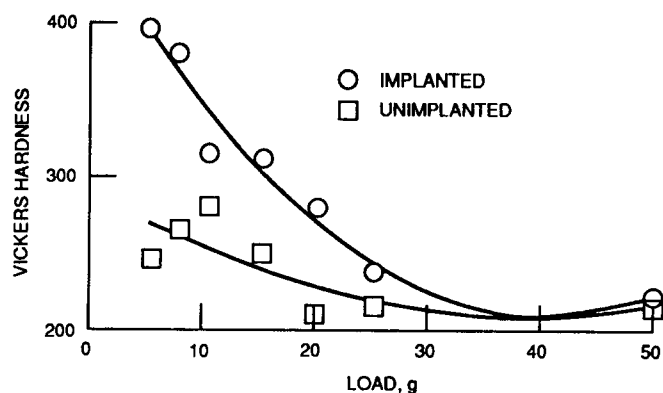


Figure 4. - Vickers hardness as function of applied load for unimplanted ZnS, and for ZnS implanted with He ions, at 100 keV at a dose of 2×10^{17} particles/cm².

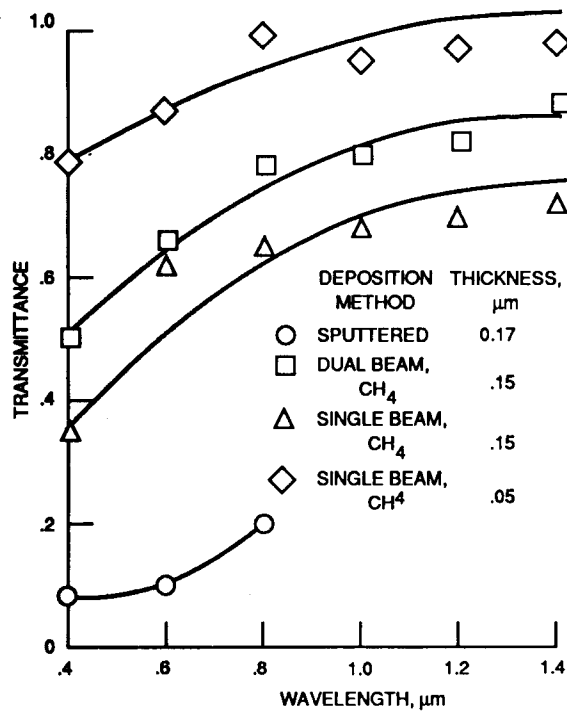


Figure 5. - Transmittance as function of wavelength for DLC films made with CH₄ in the single or dual ion-beam source, and DLC films made by sputter deposition of a graphite target.

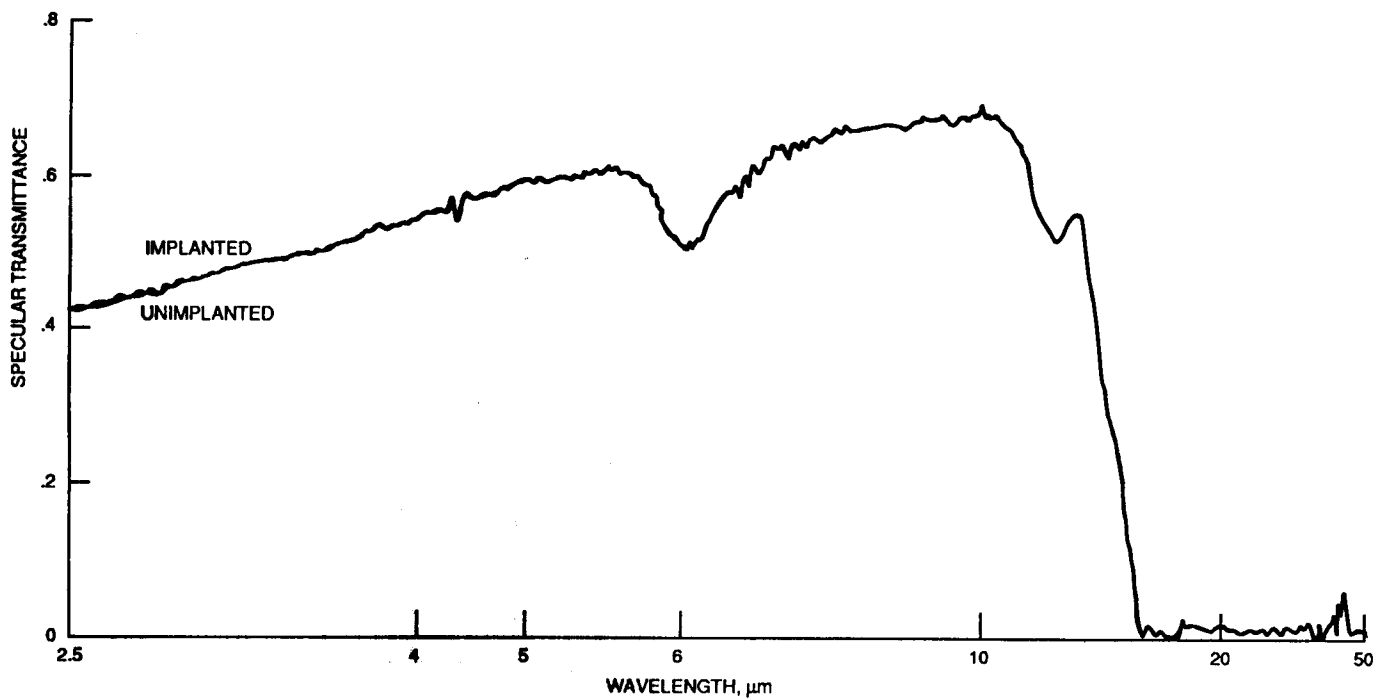


Figure 6. - Specular transmittance of ZnS before and after He ion implantation at 100 keV at a dose of 5×10^{16} particles/cm².

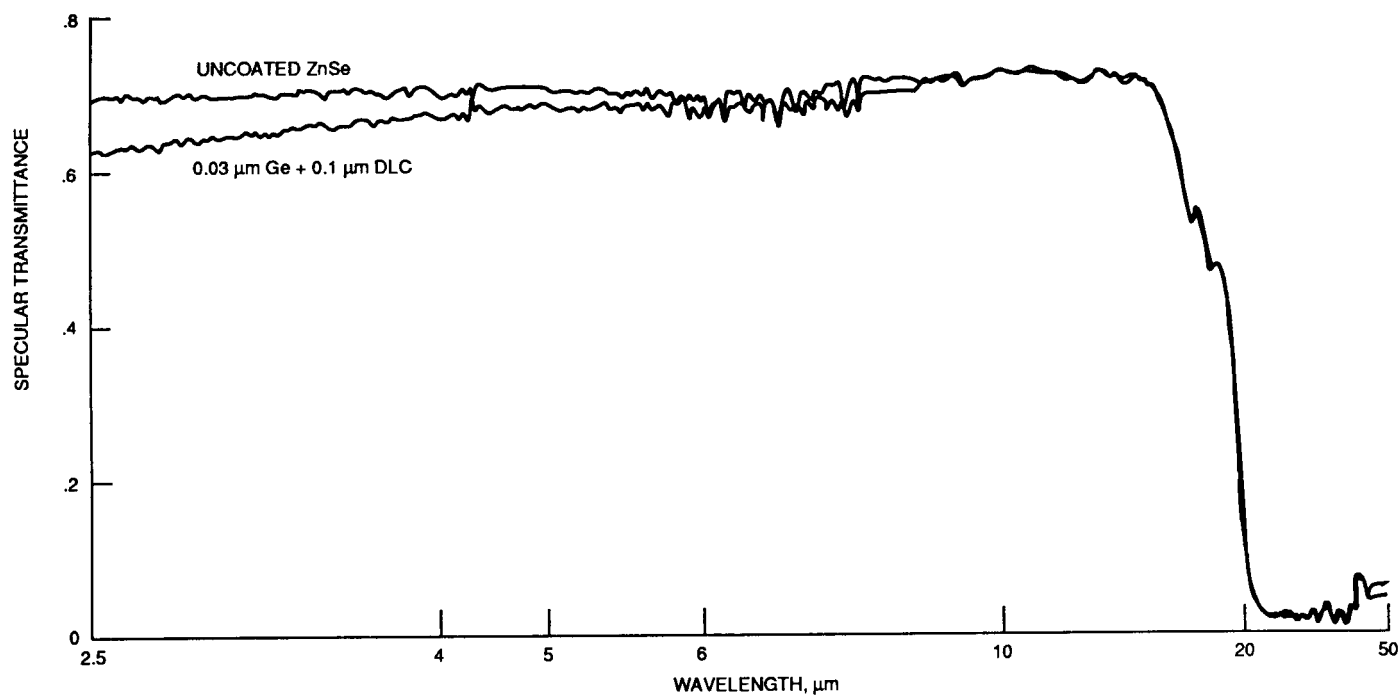


Figure 7. - Specular transmittance of 0.1-μm DLC film made with CH_4 in the single beam with and without an intermediate layer of 0.03-μm Ge on the ZnSe substrate.

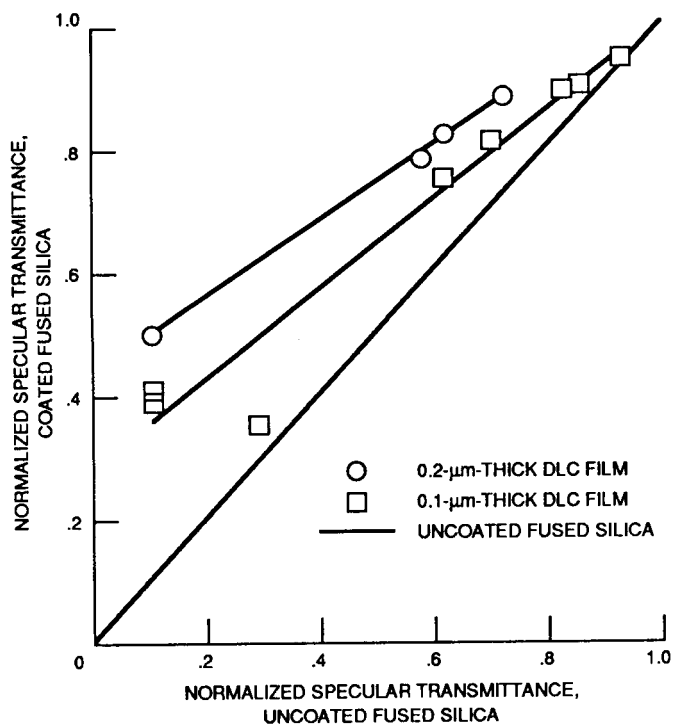


Figure 8. - Normalized specular transmittance of fused silica coated with DLC films, 0.1 and 0.2 μm thick, made with CH_4 in the single ion-beam source, and uncoated fused silica, both after exposure to 100-μm SiO_2 particles at 27 m/sec.

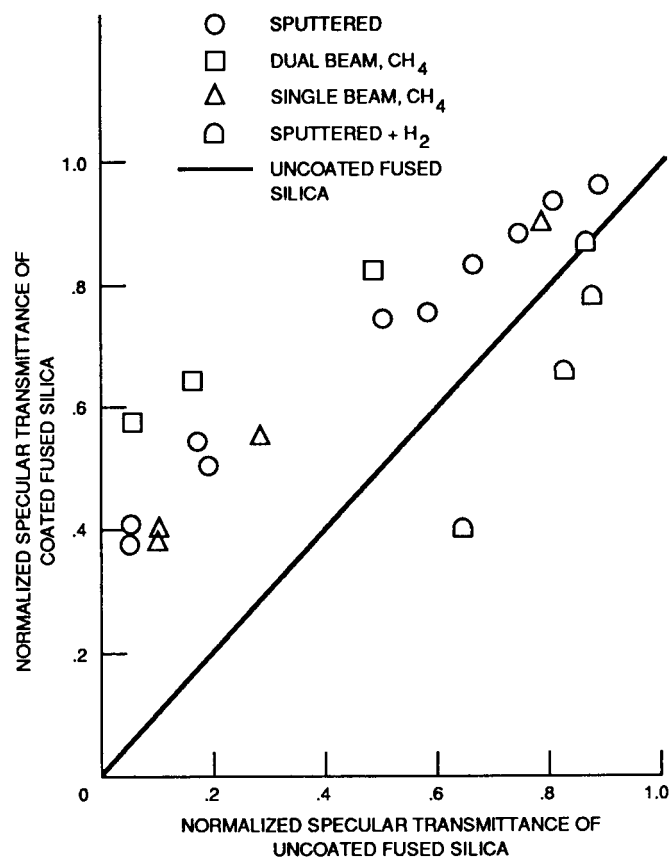


Figure 9. - Protection that 0.1-μm-thick DLC films deposited by various methods afforded fused silica after exposure to 100-μm SiO_2 particles at 27 m/sec.

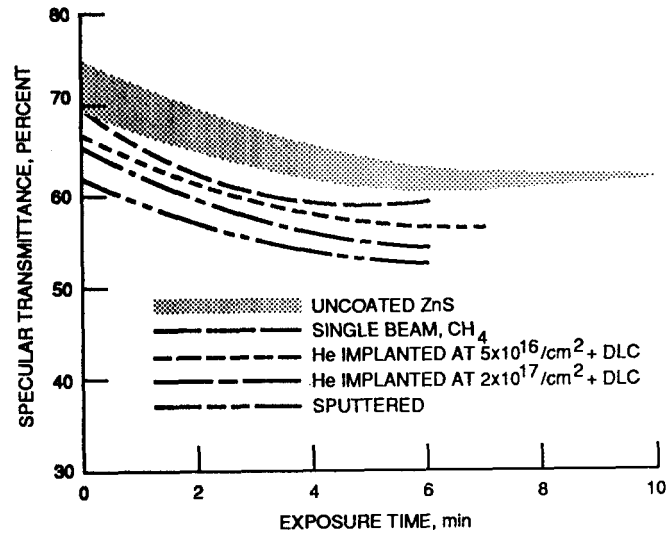


Figure 10. - Change in specular transmittance at 10 μm due to total erosion time for various surfaces of ZnS coated with DLC films.

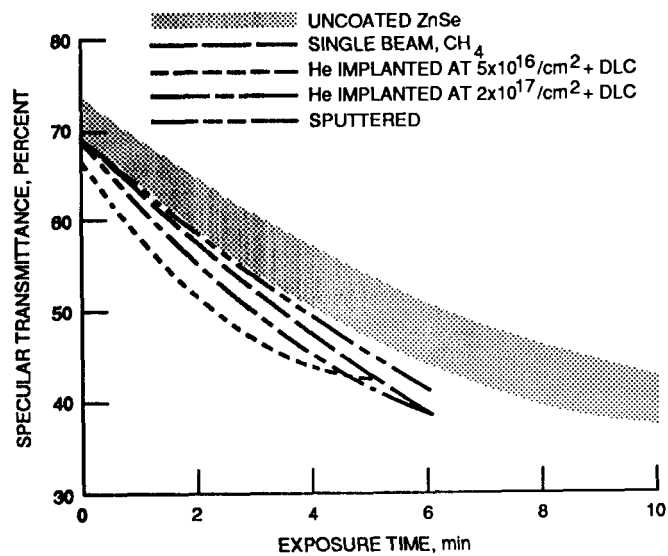


Figure 11. - Change in specular transmittance at 10 μm due to total erosion time for various surfaces of ZnSe coated with DLC films.

1. Report No. NASA TM-102111		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle Diamondlike Carbon Protective Coatings for Optical Windows				5. Report Date	
				6. Performing Organization Code	
7. Author(s) Diane M. Swec and Michael J. Mirtich				8. Performing Organization Report No. E-4881	
				10. Work Unit No. 506-41-41	
9. Performing Organization Name and Address National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135-3191				11. Contract or Grant No.	
				13. Type of Report and Period Covered Technical Memorandum	
12. Sponsoring Agency Name and Address National Aeronautics and Space Administration Washington, D.C. 20546-0001				14. Sponsoring Agency Code	
15. Supplementary Notes Prepared for the 1989 Technical Symposia on Aerospace Sensing sponsored by The International Society for Optical Engineering, Orlando, Florida, March 27-31, 1989.					
16. Abstract <p>Diamondlike carbon (DLC) films were deposited on infrared transmitting optical windows and were evaluated as protective coatings for these windows exposed to particle and rain erosion. The DLC films were deposited on zinc selenide (ZnSe) and zinc sulfide (ZnS) by three different ion beam methods: (1) sputter deposition from a carbon target using an 8-cm argon ion source, (2) direct deposition by a 30-cm hollow cathode ion source with hydrocarbon gas in argon, and (3) dual beam direct deposition by the 30-cm hollow cathode ion source and an 8-cm argon ion source. In an attempt to improve the adherence of the DLC films on ZnSe and ZnS, ion beam cleaning, ion implantation with helium and neon ions, or sputter deposition of a thin, ion beam intermediate coating was employed prior to deposition of the DLC film. The protection that the DLC films afforded the windows from particle and rain erosion was evaluated, along with the hydrogen content, adherence, intrinsic stress, and infrared transmittance of the films. Because of the elevated stress levels in the ion beam sputtered DLC films and in those ion beam deposited with butane, films thicker than 0.1 μm and with good adherence on ZnS and ZnSe could not be generated. An intermediate coating of germanium successfully allowed the DLC films to remain adherent to the optical windows and caused only negligible reduction in the specular transmittance of the ZnS and ZnSe at 10 μm. These DLC films did not protect the optical windows from simulated particle erosion; however, they did improve the performance of ZnS exposed to rain erosion.</p>					
17. Key Words (Suggested by Author(s)) Diamondlike carbon films Ion beam deposition Infrared transmitting windows			18. Distribution Statement Unclassified—Unlimited Subject Category 74		
19. Security Classif. (of this report) Unclassified		20. Security Classif. (of this page) Unclassified		21. No of pages 14	
				22. Price* A03	