

1N-33
79782
P-5

Performance of a Y-Ba-Cu-O Superconducting Filter/GaAs Low Noise Amplifier Hybrid Circuit

K.B. Bhasin and S.S. Toncich
National Aeronautics and Space Administration
Lewis Research Center
Cleveland, Ohio

C.M. Chorey
Sverdrup Technology, Inc.
Lewis Research Center Group
Brook Park, Ohio

and

R.R. Bonetti and A.E. Williams
COMSAT Laboratories
Clarksburg, Maryland

Prepared for the
1992 IEEE MTT-S International Microwave Symposium
Albuquerque, New Mexico, June 2-4, 1992



PERFORMANCE OF A Y-Ba-Cu-O SUPERCONDUCTING FILTER/GaAs

LOW NOISE AMPLIFIER HYBRID CIRCUIT

K.B. Bhasin and S.S. Toncich
National Aeronautics and Space Administration
Lewis Research Center
Cleveland, Ohio 44135

C.M. Chorey
Sverdrup Technology, Inc.
Lewis Research Center Group
Brook Park, Ohio 44142

R.R. Bonetti and A.E. Williams
COMSAT Laboratories
Clarksburg, Maryland 20871

Abstract

A superconducting 7.3 GHz two-pole microstrip bandpass filter and a GaAs low noise amplifier (LNA) were combined into a hybrid circuit and characterized at liquid nitrogen temperatures. This superconducting/semiconducting circuit's performance was compared to a gold filter/GaAs LNA hybrid circuit. The superconducting filter/GaAs LNA hybrid circuit showed higher gain and lower noise figure than its gold counterpart.

Introduction

Before the discovery of high-T_c superconductivity, the integration of low-T_c superconductors with semiconducting devices was not feasible since many semiconducting devices freeze-out below 10 K. The recent demonstration of high-T_c superconducting passive microwave components operating at liquid nitrogen temperatures^{1,2} has enhanced the feasibility of integrating these superconducting components with semiconducting devices to achieve high performance microwave systems. GaAs and heterostructure microwave semiconducting devices make strong candidates for integration since they have shown significantly lower noise figures at liquid nitrogen temperatures.^{3,4}

In deep space communications, radio astronomy and radiometer applications, low noise and low loss requirements are frequently met by cooling the microwave components. For the first time we have combined in a hybrid circuit a superconducting microstrip bandpass filter and a GaAs low noise amplifier (LNA), which is a basic building block in these applications. We compared its performance to a hybrid gold filter/LNA circuit operating at the same temperature. The circuit design, fabrication, and experimental results are presented below.

Circuit Design and Fabrication

A two-pole microstrip bandpass filter was designed with a 2.5 percent bandwidth, 0.5 dB passband ripple, and 7.5 GHz center frequency on lanthanum aluminate substrate. The layout of the two-pole filter is shown in Fig. 1. The filter was fabricated using laser ablated YBCO superconducting films (~5000 Å) on a 10 mil lanthanum aluminate substrate. A gold film deposited by E-beam evaporation on the opposite side of lanthanum aluminate substrate

was used as a ground plane. An identical filter using gold film for the microstrip and the ground was also fabricated.

The LNA selected was an Avantek Inc. PGM 11421 with a specified frequency response from 4 to 11 GHz, a minimum gain of 8.0 dB, and a typical noise figure of 2.5 dB. The bandpass filter/GaAs LNA hybrid was mounted in a brass test fixture as shown in Fig. 2. The devices were connected by 10 mil gold bond wires to 50 Ω input/output microstrip lines that were fabricated on 10 mil thick Duroid ($\epsilon_r = 2.3$) substrate. The length of the microstrip lines were chosen so as to minimize the interaction between the launcher pins and the devices.

The coax to microstrip transition was implemented using SMA female flange connectors. Silver paint was used to improve the contact between the center conductor of the launcher and the microstrip line.

Cryogenic Measurements and Results

The LNA and bandpass filters were tested individually to verify their performance at T = 300 and 77 K. An HP 8510B automatic network analyzer (ANA) was used to measure insertion gain or loss, and a HP 8970A noise figure meter was used to determine the noise figure of the LNA. Table 1 presents a summary of the pertinent results that apply for this work. The data for the gold filter shows a reduction in the insertion loss of 1.4 dB between T = 300 and 77 K. This is due to lower ohmic loss in the gold conductor and to a reduction of loss in the dielectric substrate at T = 77 versus 300 K. The HTS filter shows a significantly smaller insertion loss than the gold filter at 77 K. This is due to the near elimination of conductor loss in the YBCO film compared to the loss in the gold conductor. Most of the loss present of the HTS filter is due to the use of a gold ground plane.

The primary advantage in using an HTS filter over a gold filter is that the HTS filter offers a much smaller insertion loss. If the HTS filter's gold ground plane were replaced with HTS material, a further reduction in insertion loss could be achieved.

For the LNA/bandpass filter hybrid measurements, a full two port calibration was performed inside the cryostat so as to move the ANA reference planes to the ends of the semi-rigid cables

inside the cryostat. Since this experiment is concerned only with the relative difference in gain of the hybrid circuit and not with the absolute gain, a two port calibration was selected over a TRL or LRL calibration, which could move the reference planes of the ANA onto the test fixture, thereby removing its effect as well. In all measurements performed, only the filters were changed in the test fixture.

To calibrate the noise figure meter, the LNA/bandpass filter was replaced in the test fixture by a 50 Ω thru line supplied by Avantek Inc. An ANA measurement was made to determine the total insertion loss of the test fixture and semi-rigid cables over the frequency range of 7.0 to 8.0 GHz. This loss was found to be 2.6 dB in this frequency range. One half of this loss (1.3 dB), representing the loss of that portion of the test fixture that appears at the input of the hybrid, was subtracted away from the noise figure measurements that were made on the hybrid at the appropriate frequency points, leaving only the actual noise figure of the hybrid.

Figure 3 shows the difference in the hybrid's gain when gold and HTS filters, respectively, are used, while Fig. 4 shows the difference in the noise figures. Since the HTS filter becomes functional only after the system reaches cryogenic temperatures, there is no room temperature data provided for it. This particular filter was fabricated on a high quality substrate, it began to conduct at $T = 89$ K, and reached its minimum insertion loss at $T = 85$ K.

At 77 K the gold filter/LNA hybrid shows a noise figure improvement of nearly 3.5 dB as compared to 300 K, while the HTS filter/LNA hybrid shows a 5.5 dB improvement in noise figure compared to gold at 300 K. As expected, the overall gain of the HTS filter/LNA hybrid is greater than that of the gold hybrid due to a lower insertion loss of the HTS filter.

As a check on the accuracy of these results, the data obtained for the LNA and filters individually is inserted in the expression for the noise figure of a cascade, $F_t = F_1 + (F_2 - 1)/G_1$. Here, F_1 and F_2 are the noise figures of the filter and LNA respectively, and G_1 is the loss of the filter. Table 2 shows the results for the minimum noise figure of the hybrid. There is good agreement between the calculated and measured noise figures for the hybrid.

Conclusions

A low loss two-pole Y-Ba-Cu-O superconducting bandpass filter on lanthanum aluminate substrate was connected in series with a packaged GaAs low noise amplifier and fully characterized at 77 K. The noise figure characteristics of the superconducting filter/LNA hybrid circuit when compared to the gold filter/LNA hybrid circuit showed an improvement of 2.1 dB at 77 K. The gain characteristics showed an improvement of 0.5 dB for the HTS filter hybrid over the gold hybrid at 77 K.

This first demonstration of superconducting filter/GaAs LNA hybrid circuit shows potential for applications in radio astronomy, radiometers and deep space communications systems where high performance is desired in spite of the cooling requirements.

Acknowledgment

The authors wish to acknowledge the assistance of Mr. Ed Rylander, Sr. Test Engineer at Avantek Inc., Folsom, CA for his useful discussions on noise figure measurement and for supplying us with Avantek thru lines for calibration purposes.

References

1. IEEE Trans. Microwave Theory Tech., vol. 39, no. 9, 1991 (entire issue).
2. D.C. Webb and M. Nisenoff, "The high temperature superconductivity space experiment," Microwave J., vol. 34, pp. 85-91, 1991.
3. M.W. Pospieszalski, S. Weinreb, R.D. Norrod, and R. Harris, "FET's and HEMT's at cryogenic temperatures—their properties and use in low-noise amplifiers," IEEE Trans. Microwave Theory Tech., vol. 36, pp. 552-560, 1988.
4. S. Weinreb, "Low-noise, cooled GASFET amplifiers," IEEE Trans. Microwave Theory Tech., vol. 28, pp. 1041-1054, 1980.

TABLE 1.—DATA ON THE LNA AND BANDPASS FILTERS
USED IN THIS EXPERIMENT

[The frequency range is 7.0 to 8.0 GHz. The gain/loss values shown are average values over this frequency band. For the filters, noise figure values were taken to be the magnitude of the respective insertion loss.]

		Gain/loss, dB	Noise figure, dB
LNA (PGM 11421)	T = 300 K	8.9	2.5
	T = 77 K	9.5	0.9
Gold filter	T = 300 K	-4.2	4.2
	T = 77 K	-2.8	2.8
HTS filter	T = 77 K	-0.5	0.5

TABLE 2.—CALCULATED AND MEASURED VALUES FOR THE NOISE FIGURE
OF THE HYBRID CIRCUIT

	Calculated noise figure, dB	Measured noise figure, dB
Gold filter/LNA, T = 300 K	6.7	7.0
Gold filter/LNA, T = 77 K	3.7	3.6
HTS filter/LNA, T = 77 K	1.4	1.5

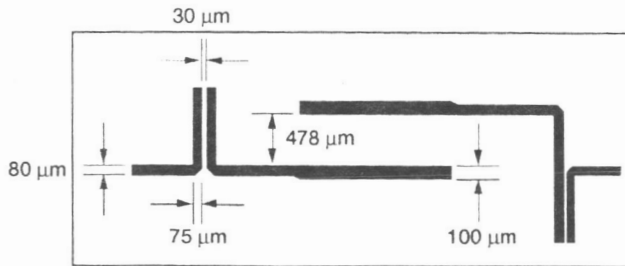


Figure 1.—Layout of the C-band, two pole bandpass filter.

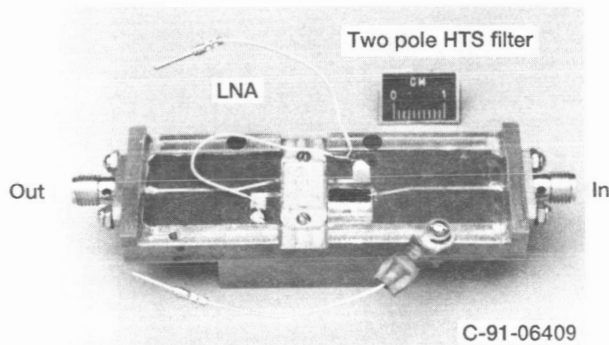


Figure 2.—Test fixture used for measurements on bandpass filter/LNA hybrid.

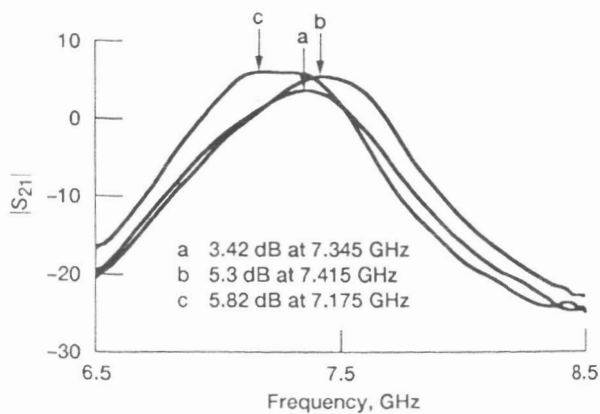


Figure 3.—Forward transmission (gain) of the gold filter/LNA hybrid (a) at T = 300 K, (b) at T = 77 K, and (c) the HTS filter/LNA hybrid at T = 77 K.

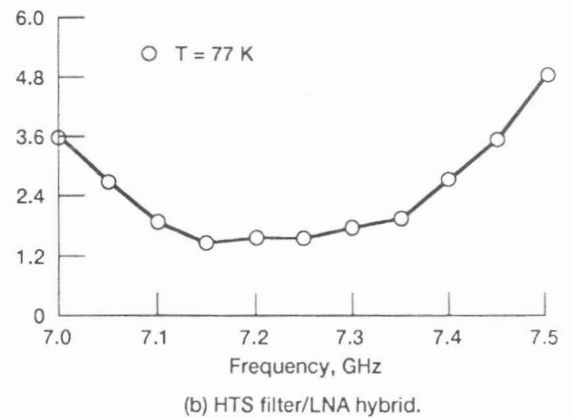
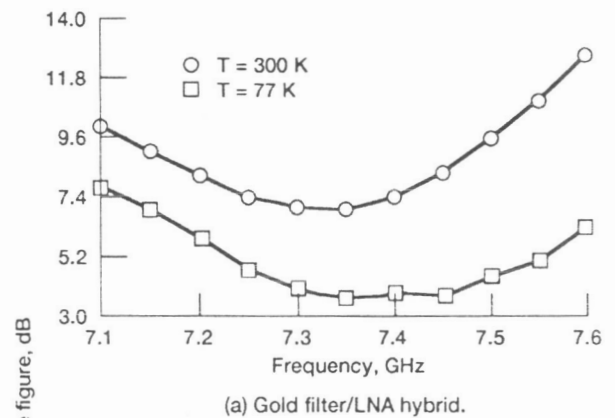


Figure 4.—Noise figure measurement as a function of temperature.

ORIGINAL PAGE
BLACK AND WHITE PHOTOGRAPH

REPORT DOCUMENTATION PAGEForm Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE 1992	3. REPORT TYPE AND DATES COVERED Technical Memorandum	
4. TITLE AND SUBTITLE Performance of a Y-Ba-Cu-O Superconducting Filter/GaAs Low Noise Amplifier Hybrid Circuit			5. FUNDING NUMBERS WU-506-72-1B	
6. AUTHOR(S) K.B. Bhasin, S.S. Toncich, C.M. Chorey, R.R. Bonetti, and A.E. Williams				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135-3191			8. PERFORMING ORGANIZATION REPORT NUMBER E-6869	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, D.C. 20546-0001			10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA TM-105546	
11. SUPPLEMENTARY NOTES Prepared for the 1992 IEEE MTT-S International Microwave Symposium, Albuquerque, New Mexico, June 2-4, 1992. K.B. Bhasin and S.S. Toncich, NASA Lewis Research Center. C.M. Chorey, Sverdrup Technology, Inc., Lewis Research Center Group, 2001 Aerospace Parkway, Brook Park, Ohio 44142 (work funded by NASA Contract NAS3-25266); and R.R. Bonetti and A.E. Williams, COMSAT Laboratories, Clarksburg, Maryland 20871.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category 33			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A superconducting 7.3 GHz two-pole microstrip bandpass filter and a GaAs low noise amplifier (LNA) were combined into a hybrid circuit and characterized at liquid nitrogen temperatures. This superconducting/semiconducting circuit's performance was compared to a gold filter/GaAs LNA hybrid circuit. The superconducting filter/GaAs LNA hybrid circuit showed higher gain and lower noise figure than its gold counterpart.				
14. SUBJECT TERMS GaAs circuit; Cryogenic electronics; HTS			15. NUMBER OF PAGES 4	
			16. PRICE CODE A02	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT	