

1N-37
136512
P-22

Development of Braided Rope Seals for Hypersonic Engine Applications: Flow Modeling

Rajakkannu Mutharasan
Drexel University
Philadelphia, Pennsylvania

Bruce M. Steinetz
NASA Lewis Research Center
Cleveland, Ohio

and

Xiaoming Tao, Guang-Wu Du, and Frank Ko
Drexel University
Philadelphia, Pennsylvania

December 1992

(NASA-TM-105942) DEVELOPMENT OF
BRAIDED ROPE SEALS FOR HYPERSONIC
ENGINE APPLICATIONS: FLOW MODELING
(NASA) 22 p

893-14473

Unclass

NASA

464739

03/37 0136512

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE December 1992	3. REPORT TYPE AND DATES COVERED Technical Memorandum		
4. TITLE AND SUBTITLE Development of Braided Rope Seals for Hypersonic Engine Applications: Flow Modeling		5. FUNDING NUMBERS WU-505-63-5B		
6. AUTHOR(S) Rajakkannu Mutharasan, Bruce M. Steinetz, Xiaoming Tao, Guang-Wu Du, and Frank Ko				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135-3191		8. PERFORMING ORGANIZATION REPORT NUMBER E-6166-1		
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, D.C. 20546-0001		10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA TM-105942		
11. SUPPLEMENTARY NOTES Rajakkannu Mutharasan, Xiaoming Tao, Guang-Wu Du, and Frank Ko, Drexel University, Philadelphia, Pennsylvania, 19104 and Bruce M. Steinetz, NASA Lewis Research Center. Responsible person, Bruce M. Steinetz, (216) 433-3302.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category 37			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A new type of engine seal is being developed to meet the needs of advanced hypersonic engines. A seal braided of emerging high temperature ceramic fibers comprised of a sheath-core construction has been selected for study based on its low leakage rates. Flexible, low-leakage, high temperature seals are required to seal the movable engine panels of advanced ramjet-scrumjet engines either preventing potentially dangerous leakage into backside engine cavities or limiting the purge coolant flow rates through the seals. To predict the leakage through these flexible, porous seal structures new analytical flow models are required. Two such models based on Kozeny-Carman equations are developed herein and are compared to experimental leakage measurements for simulated pressure and seal gap conditions. The models developed allow prediction of the gas leakage rate as a function of fiber diameter, fiber packing density, gas properties, and pressure drop across the seal. The first model treats the seal as a homogeneous fiber bed. The second model divides the seal into two homogeneous fiber beds identified as the core and the sheath of the seal. Flow resistances of each of the main seal elements are combined to determine the total flow resistance. Comparisons between measured leakage rates and model predictions for seal structures covering a wide range of braid architectures show good agreement. Within the experimental range, the second model provides a prediction within 6 to 13 percent of the flow for many of the cases examined. Areas where future model refinements are required are identified.				
14. SUBJECT TERMS			15. NUMBER OF PAGES 20	
			16. PRICE CODE A03	
17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT	20. LIMITATION OF ABSTRACT	

1N-37
136512
P- 22

Development of Braided Rope Seals for Hypersonic Engine Applications: Flow Modeling

Rajakkannu Mutharasan
Drexel University
Philadelphia, Pennsylvania

Bruce M. Steinetz
NASA Lewis Research Center
Cleveland, Ohio

and

Xiaoming Tao, Guang-Wu Du, and Frank Ko
Drexel University
Philadelphia, Pennsylvania

December 1992

(NASA-TM-105942) DEVELOPMENT OF
BRAIDED ROPE SEALS FOR HYPERSONIC
ENGINE APPLICATIONS: FLOW MODELING
(NASA) 22 p

N73-14478

Unclass

NASA

484739

03/31 0136512

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE December 1992	3. REPORT TYPE AND DATES COVERED Technical Memorandum		
4. TITLE AND SUBTITLE Development of Braided Rope Seals for Hypersonic Engine Applications: Flow Modeling		5. FUNDING NUMBERS WU-505-63-5B		
6. AUTHOR(S) Rajakkannu Mutharasan, Bruce M. Steinetz, Xiaoming Tao, Guang-Wu Du, and Frank Ko				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135-3191		8. PERFORMING ORGANIZATION REPORT NUMBER E-6166-1		
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, D.C. 20546-0001		10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA TM-105942		
11. SUPPLEMENTARY NOTES Rajakkannu Mutharasan, Xiaoming Tao, Guang-Wu Du, and Frank Ko, Drexel University, Philadelphia, Pennsylvania, 19104 and Bruce M. Steinetz, NASA Lewis Research Center. Responsible person, Bruce M. Steinetz, (216) 433-3302.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category 37			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A new type of engine seal is being developed to meet the needs of advanced hypersonic engines. A seal braided of emerging high temperature ceramic fibers comprised of a sheath-core construction has been selected for study based on its low leakage rates. Flexible, low-leakage, high temperature seals are required to seal the movable engine panels of advanced ramjet-scamjet engines either preventing potentially dangerous leakage into backside engine cavities or limiting the purge coolant flow rates through the seals. To predict the leakage through these flexible, porous seal structures new analytical flow models are required. Two such models based on Kozeny-Carman equations are developed herein and are compared to experimental leakage measurements for simulated pressure and seal gap conditions. The models developed allow prediction of the gas leakage rate as a function of fiber diameter, fiber packing density, gas properties, and pressure drop across the seal. The first model treats the seal as a homogeneous fiber bed. The second model divides the seal into two homogeneous fiber beds identified as the core and the sheath of the seal. Flow resistances of each of the main seal elements are combined to determine the total flow resistance. Comparisons between measured leakage rates and model predictions for seal structures covering a wide range of braid architectures show good agreement. Within the experimental range, the second model provides a prediction within 6 to 13 percent of the flow for many of the cases examined. Areas where future model refinements are required are identified.				
14. SUBJECT TERMS			15. NUMBER OF PAGES 20	
			16. PRICE CODE A03	
17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT	20. LIMITATION OF ABSTRACT	

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION

PROPOSED JOURNAL ARTICLE

DEVELOPMENT OF BRAIDED ROPE SEALS FOR HYPERSONIC
ENGINE APPLICATIONS: FLOW MODELING

Rajakkannu Mutharasan
Drexel University
Philadelphia, Pennsylvania 19104

Bruce M. Steinetz
National Aeronautics and Space Administration
Lewis Research Center
Cleveland, Ohio 44135

Xiaoming Tao, Guang-Wu Du, and Frank Ko
Drexel University
Philadelphia, Pennsylvania 19104

Prepared for

AIAA Journal

October 1992

DEVELOPMENT OF BRAIDED ROPE SEALS FOR HYPERSONIC
ENGINE APPLICATIONS: FLOW MODELING

Rajakkannu Mutharasan^{*}
Drexel University
Philadelphia, Pennsylvania 19104

Bruce M. Steinetz[†]
National Aeronautics and Space Administration
Lewis Research Center
Cleveland, Ohio 44135

Xiaoming Tao,[‡] Guang-Wu Du,[§] and Frank Ko[¶]
Drexel University
Philadelphia, Pennsylvania 19104

ABSTRACT

A new type of engine seal is being developed to meet the needs of advanced hypersonic engines. A seal braided of emerging high temperature ceramic fibers comprised of a sheath-core construction has been selected for study based on its low leakage rates. Flexible, low-leakage, high temperature seals are required to seal the movable engine panels of advanced ramjet-scamjet engines either preventing potentially dangerous leakage into backside engine cavities or limiting the purge coolant flow rates through the seals. To predict the leakage through these flexible, porous seal structures new analytical flow models are required. Two such models based on Kozeny-Carman equations are developed herein and are compared to experimental leakage measurements for simulated pressure and seal gap conditions. The models developed allow prediction of the gas leakage rate as a function of fiber diameter, fiber packing density, gas

^{*}Professor of Chemical Engineering.

[†]Research Engineer, Structural Dynamics Branch, Member AIAA.

[‡]Research Associate, Fibrous Materials Research Center (FMRC).

[§]Research Associate (FMRC).

[¶]Professor of Materials Engineering.

properties, and pressure drop across the seal. The first model treats the seal as a homogeneous fiber bed. The second model divides the seal into two homogeneous fiber beds identified as the core and the sheath of the seal. Flow resistances of each of the main seal elements are combined to determine the total flow resistance. Comparisons between measured leakage rates and model predictions for seal structures covering a wide range of braid architectures show good agreement. Within the experimental range, the second model provides a prediction within 6 to 13 percent of the flow for many of the cases examined. Areas where future model refinements are required are identified.

NOMENCLATURE

A_c	cross-area of seal
A_y	yarn cross-sectional area
D_f	fiber diameter
g_c	gravitational constant
\dot{M}	mass flow rate of gas
M_w	molecular weight of gas
N_c	number of core yarns
N_s	number of sheath yarns
P_o	pressure downstream of seal
P_i	pressure upstream of seal
R	flow resistance of the seal
Re	Reynolds number
R_g	universal gas constant
T	absolute temperature
t, t_1, t_2	seal dimensions (see Fig. 4)
u	superficial gas velocity

y_o	half the clearance between the seal and its housing
ϵ	porosity (see Eqs. (27) to (29))
ϕ	shape factor, defined in Eq. (4)
θ	braid angle (see Fig. 1)
ρ_f	mass density of fiber
μ	gas viscosity
ρ	gas density

Subscripts:

c	core
e	edge
sl	seal
s	sheath
1,2...7	flow paths (see Fig. 4)

INTRODUCTION

Ramjet-scamjet engines require sliding panel seals to prevent combustion gases from leaking past the articulating engine panels, similar to articulating panel seals of turbojet two-dimensional converging-diverging nozzles.¹ However, new seals are required for advanced hypersonic engines because of higher thermal loads and the need to seal larger engine sidewall distortions. As a point of comparison, turbojet nozzle seals developed under the Augmented Deflector Exhaust Nozzle Program² used superalloy seals that sealed pressure differentials up to 30 psi, sealed sidewall distortions up to 0.030 in., and were cooled to 1200 °F. Hypersonic engine seals, however, are required to operate at higher temperatures (1800 to 2000 °F), seal higher pressure differentials (up to 100 psi) and seal larger sidewall distortions (up to 0.150 in.), as described in Ref. 3.

A seal concept that shows promise of meeting these challenging demands is the braided ceramic rope seal being developed at NASA Lewis Research Center. The braided ceramic rope seal structure consists of a high density uniaxial core structure overbraided with an outer sheath for structural integrity, as shown in Fig. 1. Braided of emerging high temperature ceramic fibers this seal shows promise of operating hot and remaining flexible at temperatures up to 2000 °F. Early design studies⁴ identified important seal design parameters including: fiber diameter; yarn bundle size, fiber packing density, and percent core structure for low leakage.

Accompanying the development of these engine seals, NASA is also developing engine seal flow models to predict the seal leakage through these porous seal structures. These seal flow models can be used during the design process in one of two ways: to predict performance losses associated with parasitic leakage through the seals; and to predict purge coolant flow rates through these seals where ambient engine flow temperatures exceed the seal's operating temperature limit. The purpose of this paper is to provide an analytic means of predicting the gas flow through these braided structures and to determine quantitatively the relationship between gas leakage rate and the pore structure of the seal.

THEORETICAL

Definition of Flow Path

As shown in Fig. 1, the flow path across a seal system can be divided into two categories: (1) flow through the seal and (2) flow around seal. The flow in the first path is related to the packing architecture of the seal itself and the flow via the second path is dependent on the surface properties of the seal and housing.

Flow through seal.— Based on data from a large amount of experimental data obtained using a variety of packing materials, both spherical and granular in shape, Ergun⁵ derived the following equation:

$$\frac{-(P_o - P_i)g_c}{\rho u^2} \frac{(\phi D)}{t} \frac{\epsilon^3}{1 - \epsilon} = \frac{150(1 - \epsilon)}{(\phi D) \rho u / \mu} + 1.75 \quad (1)$$

where P denotes pressure, subscripts i the inlet and o the outlet. In the above equation, if the Reynolds number $Re = (\phi D) \rho u / \mu (1 - \epsilon)$, is small (less than 10), then the constant 1.75 on the right side of the equation can be ignored. In the case of an engine seal, the flow is expected to be laminar as the gas leakage rate and the fiber diameter are small. This implies that the viscous term dominates in the above equation and the inertial term is negligible. Under such a condition, the pressure drop is proportional to flow velocity, u .

In earlier studies the tortuous pore structure of the bed was modeled as a solid bed consisting of an assembly of capillaries with circular cross section.⁶ The capillary model focused on the spaces or the pores in the porous solid. The best known equation proposed based on this approach is the Kozeny-Carman equation,⁷ which includes permeability coefficient as a function of porosity. One form of this equation is given below as:

$$u = \frac{-(P_o - P_i)g_c}{150 \frac{\mu t}{(\phi D)^2} \frac{(1 - \epsilon)^2}{\epsilon^3}} \quad (2)$$

The shape factor, ϕ is defined as:

$$\phi = \frac{\text{area of sphere equivalent to particle volume}}{\text{actual surface area of particle}}$$

The shape factor, ϕ is unity for a sphere and 0.87 for a cylinder with its diameter equal to its length. The equivalent diameter of a particle is defined as the diameter of a sphere having the same volume as the particle. For a fiber with a diameter D_f and length L , the equivalent diameter is:

$$D = \left(1.5 D_f^2 L\right)^{1/3} \quad (3)$$

and the shape factor is:

$$\phi = (1.5)^{2/3} \frac{(L/D_f)^{2/3}}{L/D_f + 0.5} \quad (4)$$

Hence, (ϕD) can be expressed as:

$$(\phi D) = 1.5 D_f \frac{L/D_f}{L/D_f + 0.5} \quad (5)$$

If the ratio L/D_f is very large the term (ϕD) will approach the value of $1.5D_f$. If direction of flow is across the axis of fiber, a situation that occurs in a seal containing substantial amount of longitudinal fibers, the length scale, L , in the above equation should be expected to be of the same order of magnitude as the diameter of the fiber. The parameter (ϕD) can be thought of as characteristic dimension intrinsic to flow through the fibrous seal.

The Kozeny-Carman equation predicts successfully the pressure drop in packed beds with porosity ranging from 0.3 to 0.6. For porous media with higher porosity such as most fiber beds and textile fabrics, a number of authors (e.g., see Ref. 8) have shown that predicted pressure drop is much greater than measured values. In the current application, for determining leakage rate of a gas through a seal having low porosity, Kozeny-Carman equation is a good starting point. Taking cross sectional area for gas flow as A_c and the seal length as L , Eq. (2) can be rearranged as

$$\frac{\dot{M}}{L} = \frac{-(P_o^2 - P_i^2)}{300 \frac{\mu R_g T}{M_w g_c} \frac{t L}{A_c} \frac{(1 - \epsilon)^2}{\epsilon^3 (\phi D)^2}} \quad (6)$$

where ideal behavior of gas is assumed, and the density of gas ρ is based on an average value evaluated at the two end-point pressures as:

$$\rho = \frac{(P_o + P_i) M_w}{2 R_g T} \quad (7)$$

Flow Around Seal.– Edge flow can be treated as a flow between parallel nonporous surfaces separated by a small gap. Assuming that the gap between the surfaces can be considered constant and equal to $2y_o$, one can relate the pressure difference across the seal to the gas leakage velocity as:⁹

$$P_o - P_i = \frac{3\mu ut}{g_c y_o^2} \quad (8)$$

Rearranging the above in the form of Eq. (6) gives:

$$\frac{\dot{M}}{L} = \frac{-(P_o^2 - P_i^2)}{\frac{3\mu R_g T}{M_w g_c} \frac{t}{y_o^3}} \quad (9)$$

Flow Resistance.– Examination of Eq. (6) for flow through the seal and Eq. (9) for flow around the seal suggests the definition of flow resistance R as:

$$R = \frac{-(P_o^2 - P_i^2)}{\dot{M}/L} \quad (10)$$

The flow resistance R is a function of properties of both fluid and seal architecture and, for this analysis, is assumed to be independent of the pressure difference across it and any compressive pressure the seal may be subjected to.

Flow Modeling

In a previous paper,⁴ critical design parameters such as fiber packing density and fiber bundle size were identified through a combination of theoretical and experimental studies. Since the seal consists of both braids in the sheath and longitudinal fibers in the core, one expects different porosity values to be applicable in the two regions. In this investigation, two models are proposed to quantitatively evaluate the flow resistances.

Model I.– As shown in Fig. 2, the seal is assumed to be a homogeneous fiber bed having a uniform constant porosity regardless of the core and sheath structures. Thus, only one value of

porosity is used to calculate the flow resistance. The gas leakage rate can be expressed as the sum of the leakages through the seal and around the seal, and is given by:

$$\frac{\dot{M}}{L} = \frac{\dot{M}_e}{L} + \frac{\dot{M}_{sl}}{L} = \frac{(P_i^2 - P_o^2)}{R} \quad (11)$$

where subscripts, sl and e refer to the seal and edge, respectively. The individual leakages are given by:

$$\frac{\dot{M}_e}{L} = \frac{(P_i^2 - P_o^2)}{R_e} \quad (12)$$

$$\frac{\dot{M}_{sl}}{L} = \frac{(P_i^2 - P_o^2)}{R_{sl}} \quad (13)$$

The flow resistances encountered in the flow path through the seal is determined from Eq. (6) and is given as:

$$R_{sl} = 300 \frac{\mu R_g T t L (1 - \epsilon)^2}{M_w g_c A_c \epsilon^3 (\phi D)^2} \quad (14)$$

The edge flow consists of two parallel paths as shown in Fig. 2 and the flow resistance of each of these two paths may be summed in parallel as:

$$R_e = \frac{R_{e1} R_{e2}}{R_{e1} + R_{e2}} \quad (15)$$

with:

$$R_{e1} = 9 \frac{\mu R_g T}{M_w g_c} \frac{t}{y_o^3} \quad \text{and} \quad R_{e2} = 3 \frac{\mu R_g T}{M_w g_c} \frac{t}{y_o^3}$$

where R_{e1} is three times R_{e2} because of the longer path length, see Fig. 2. Since the edge flow and flow through the seal occur in parallel, the overall flow resistance of the seal system is therefore given by:

$$R = \frac{R_e R_{sl}}{R_e + R_{sl}} \quad (16)$$

Model II.– The second model, illustrated in Fig. 3, deals with a composite seal in which the sheath and core are allowed to have independent porosity values. The seal has a sheath and a core with porosities ϵ_s and ϵ_c , respectively. Flow resistances along the various flow paths illustrated in Fig. 4, are given as:

$$R_1 = 9K \frac{t}{y_o^3} \quad (17)$$

$$R_2 = R_6 = 300 K \frac{t}{t_2} \frac{(1 - \epsilon_s)^2}{\epsilon_s^3 (\phi D)^2} \quad (18)$$

$$R_3 = R_5 = 300 K \frac{t_2}{t} \frac{(1 - \epsilon_s)^2}{\epsilon_s^3 (\phi D)^2} \quad (19)$$

$$R_4 = 300 K \frac{(1 - \epsilon_c)^2}{\epsilon_c^3 (\phi D)^2} \quad (20)$$

$$R_{345} = R_3 + R_4 + R_5 \quad (21)$$

$$R_7 = 3K \frac{t}{y_o^3}$$

where $K = \frac{\mu R_g T}{M_w g_c}$. The flow resistance of the seal can be determined by summing the flow resistances in parallel, given as:

$$\frac{1}{R_s} = \frac{1}{R_2} + \frac{1}{R_{345}} + \frac{1}{R_6} \quad (23)$$

Flow resistance of edge flow is:

$$R_e = \frac{R_1 R_7}{R_1 + R_7} \quad (24)$$

The total flow resistance of the seal for substitution into Eq. (11) is then given by:

$$R = \frac{R_e R_s}{R_e + R_s} \quad (25)$$

Calculation Basis

Two important parameters in determining flow resistance through the seal are porosity and the characteristic dimension, D . The actual porosity of the seal in the application condition is expected to be lower than in the initial installed position. The porosity (method of determination discussed below) was assumed to be a constant for any given seal. With regard to D , since the bulk of the seal is made up of longitudinal fibers and that the number of fiber-fiber interfaces is significantly larger than the number of yarn-yarn interfaces, the characteristic dimension was taken as the fiber diameter, D_f . The characteristic dimension (ϕD) , takes on values between $1.5D_f$ and $0.75D_f$ when the ratio L/D_f is taken to be large or 0.5, respectively. The latter value gives better fit with experimental data under a variety of situations investigated. Therefore, all calculations presented in this paper are based on $(\phi D) = 0.75D_f$.

Another characteristic dimension is the distance, y_o in calculating seal edge leakage. In the present calculation, the clearance was assumed to be proportional to fiber diameter. Specifically y_o is assumed to be $0.1 (\phi D)$.

The cross section area of a yarn A_y (in.²) can be determined from its denier and fiber density ρ_f (g/cm³) as:

$$A_y = \frac{\text{yarn denier}}{5.8 \times 10^6 \rho_f} \quad (26)$$

where denier is a yarn density term used in the textile industry and is the yarn mass in grams per 9000 m of length.

The following are the parameters used for calculation of various results reported:

$\rho_f = 2.54 \text{ g/cm}^3$ $R_g = 1.545 \times 10^3 \text{ lb-ft/}^\circ\text{R}$ $T = 528 \text{ }^\circ\text{R}$ $g_c = 32.1 \text{ lb}_m \text{ ft/lb}_f \text{ sec}^2$	$D_f = 10 \text{ } \mu\text{m}$ denier = 812 g per 9000 m $(\phi D) = 0.75D_f$ $y_o = 0.1 (\phi D)$	$M_w (\text{air}) = 29 \text{ lb}_m/\text{lb mole}$ $M_w (\text{He}) = 4 \text{ lb}_m/\text{lb mole}$ $\mu \text{ of air} = 0.0175 \text{ cP}$ $\mu \text{ of helium} = 0.019 \text{ cP}$
---	--	--

EXPERIMENTAL

Braided Seal Specimens

Eight seal specimens were made using 812 denier E-glass fibers (Owens Corning Glass, Granville, Ohio). The specimens were labeled A1 through H1 and their architectural parameters, braiding angle, number of longitudinal yarns and number of braiding yarns, are summarized in Table 1. Specimens G1 and H1 have the highest number of longitudinal yarns while A1, B1, and C1 have the lowest number of longitudinal yarns.

Flow Measurement

The experimental details of the flow measurement were described in an earlier paper by the authors.⁴ Seal specimens 1 ft in length were mounted in a specially developed test fixture and were leak tested under room temperature at various inlet pressure conditions in the range of 5 to 80 psig. The pressure upstream of the seal was varied and the resulting leakage of gas (either air or helium) was measured. Lateral preloads were applied uniformly to the back of the seal with an inflatable rubber diaphragm at either 80 or 130 psig. The flow resistance of the seal was computed from the ratio of the difference of squares of absolute pressures over the mass leakage rate.

Porosity

An ultra-low viscosity embedding media (purchased from Polysciences Inc., Warrington, PA) was used as a rigidizing medium to infiltrate the specimen. Polymerization was accomplished at 70 °C for 12 hr. The specimen then was cut and polished. Scanning electron micrographs were taken to determine the dimension of the seal cross section and packing geometry of fibers. The thickness of the braid sheath, t_2 , was measured using the electron photomicrographs.

Porosity of the seal for calculating flow resistances described earlier was obtained from the geometry of fiber layout and is given by:

$$\epsilon = 1 - \frac{A_y(N_c + N_s/\cos \theta)}{t^2} \quad (27)$$

where N_c and N_s are the number of core and sheath yarns and t^2 is the cross sectional area of the installed seal. Note that the seal is treated as a homogeneous fiber bed having a single average porosity value for Model I.

The porosity of sheath and core sections of the specimens for Model II were determined from the following two equations:

$$\epsilon_c = 1 - \frac{A_y N_c}{t_1^2} \quad (28)$$

$$\epsilon_s = 1 - \frac{A_y N_s / \cos \theta}{t^2 - t_1^2} \quad (29)$$

where t and t_1 are the overall width of the installed seal, and the width of the core region, respectively (see Fig. 4).

RESULTS AND DISCUSSION

Pressure Drop Correlations

In Fig. 5, typical measured air leakage rates are plotted as a function of the difference of the squares of the pressure across the seal for specimens A1 and G1 at preload pressures of 80 and 130 psig. The linear relationship between the two variables is indicative of the validity of the pressure dependency presented earlier in Eq. (10). Although only two sample results are shown in Fig. 5, all eight specimens examined in this investigation showed excellent correlation with correlation coefficient lying in the range of 0.990 to 0.999. The slope of the line in Fig. 5 is equal to the inverse of flow resistance, $1/R$.

Flow Resistances for Different Gases

Because of the many environments the seals are expected to operate in, it is important to be able to predict the flow resistance to various potential coolants or leakage gases. Shown in Fig. 6 is the measured resistance of helium plotted against the resistance of air for a wide range of seal architectures (specimens A1, B1, C1, D1, G1, and H1), pressure drop conditions (between 5 to 80 psig), preload conditions (80 and 130 psig) investigated. If the seal's pore structure is constant, flow resistance is directly proportional to viscosity and inversely proportional to density of the flowing gas (e.g., Eq. (6)). Hence, when we compare the flow resistance of helium to that of air in Fig. 6, we expect the slope of the straight line to be:

$$\text{SLOPE} = \frac{(\mu/M_w)_{\text{Helium}}}{(\mu/M_w)_{\text{Air}}} \quad (30)$$

The straight line indicated in Fig. 6 is the theoretical line with a slope of 7.9 obtained using Eq. (30). Experimental data given in Fig. 6 when fitted with a straight line yielded a slope of 6.2, which compares favorably with the theoretical value of 7.9.

Comparison of Measured and Predicted Leakage Rates

The measured and predicted leakage rates for A1 and G1 seals with widely different seal architectures are shown in Figs. 7 and 8 for applied pressure differentials up to 80 psi for both air and helium test gases. Also shown in the figure are the effects of lateral preload on seal leakage. Lateral preloads of 80 and 130 psig were applied to the back of the seal with a diaphragm compressing the seal against the adjacent sidewall. Key braiding and geometry parameters of these two seal structures denoted A1 and G1 are listed in Table 1.

Comparing the overall leakage rates between specimen A1 and G1 one finds that the leakage rates for G1 are considerably less than A1. Specimen G1 meets the tentative leakage limit of 0.004 lb/sec/ft (e.g., Ref. 3) for air pressure differentials up to 40 psi with a preload of 80 psig. Specimen A1 meets the leakage limit for pressure differentials only up to 30 psi.

In general, both models predict the leakage rates reasonably well with the measured data over the full pressure range for both air and helium test gases. Model II gives values closer to those measured at a preload of 80 psig, and Model I predicts values closer to those measured at 130 psig.

In examining Figs. 7(a) and 8(a), the versatility of Model II in predicting actual leakage rates is demonstrated. At a pressure differential of 40 psi and preload of 80 psig, the discrepancy between the measured and predicted leakage rates were only between 6 to 13 percent even though the overall leakage rates differed by a factor of 1.7.

In all the cases, the fiber diameter was used as the basis of calculation. However, if yarn diameter is used as the equivalent diameter, the prediction of the gas leakage rate is very poor as it differs from experimental observation by more than four orders of magnitudes.

Potential Sources of Modeling Discrepancy

A potential source of the discrepancy between the measured and predicted leakage rates is the porosity dependence on preload. As the preload pressure is increased the fibers are urged closer to one another and closer to the adjacent surface making it more difficult for the air to flow around the fibers, thus increasing flow resistance. Neither of the models considered in this paper account for this porosity-load dependence and is presently under development.

The choice of shape factor ϕ has a considerable effect on the predicted leakage rates. For example, since in Eq. (6) the term containing (ϕD) is squared, increasing it from $0.75D_f$ to $0.80D_f$ increases the predicted leakage by 14 percent. Selection of the shape factor ϕ is based on the quality of the model fit to experimental observations and the seal porosity value used. As improved measured values of porosity become available, it is expected that the shape factor could change and approach the theoretical upper limit of 1.5.

SUMMARY AND CONCLUSIONS

Two analytical models have been developed for predicting leakage rates of braided rope seals being developed for panels of advanced hypersonic engines. Both models are based on the Kozeny-Carman relations for flow through porous media, where the characteristic size dimension is a scaled fiber diameter (e.g., $0.75D_f$) based on experimental observations.

The first model treats the seal as a homogeneous fiber bed having a single average value for its porosity. The second model treats the two-dimensional braided seal structures as a system of flow resistances analogous to a series of resistors in an electrical network.

Based on the findings from the comparison between measured and predicted leakage rates, the following results were obtained:

1. Leakage rates predicted using Model II agree favorably to the measured leakage rates for modest preloads (80 psig) for a wide range of braided seal architectures. Agreement within 6 to 13 percent was observed at a pressure differential of 40 psi for seal specimens A1 and G1 whose overall leakage rates differed by a factor of 1.7.

2. Theoretical predictions compared to experimental observations for air and helium indicate that relative resistance to leakage flow depends on the ratio of the quotients of each gas's viscosity and molecular weight.

ACKNOWLEDGMENT

The authors wish to thank Ms. Susan Marr for making most of the specimens. The financial sponsorship of this project from NASA grant NAG3-1059 is gratefully acknowledged.

REFERENCES

1. Kuchar, A.D., "Variable Convergent-Divergent Exhaust Nozzle Aerodynamics," Aircraft Propulsion Systems Technology and Design, edited by G.C. Oates, American Institute of Aeronautics and Astronautics, Inc., Washington, D.C., 1989, pp. 301-338.

2. "Advanced V/STOL Propulsion Component Development. Vol. 1: Nozzle/Deflector. Final Report," R77AEG441-VOL. 1, Aircraft Engine Group, General Electric Co., Cincinnati, OH, Aug. 1977.
3. Steinetz, B.M., "Evaluation of an Innovative High Temperature Ceramic Wafer Seal for Hypersonic Engine Applications," NASA TM-105556, Feb., 1992.
4. Ko, F., Steinetz, B.M., and Mutharasan, R., "Development of Braided Rope Engine Seals." NASA TM-105902.
5. Ergun, S.: "Fluid Flow Through Packed Columns," Chemical Engineering Progress, Vol. 48, No. 2, Feb. 1952, pp. 89-94.
6. White, F.M.: Viscous Fluid Flow, McGraw Hill Book Company, New York, 1974.
7. Scheidegger, A.E., The Physics of Flow Through Porous Media, Rev. ed., University of Toronto Press, Toronto, Canada, 1960.
8. Van Den Brekel, L.D.M. and De Jong, E.J., "Hydrodynamics in Packed Textile Beds," Textile Research Journal, Vol. 59, No. 8, Aug. 1989, pp. 433-440.
9. Bennett, C.O., and Myers, J.E., Momentum, Heat and Mass Transfer, Third edition, McGraw-Hill Book Company, New York, 1982.

TABLE 1.—SEAL CONSTRUCTION DETAILS AND POROSITY DATA

Sample number	Braiding angle, θ , °	Core fiber, percent	Average porosity ^a	Thickness t_2 , ^d	Core porosity ^b	Sheath porosity ^c
A1	45	39.6	0.48	0.11	0.34±0.04	0.54±0.02
B1	30	39.4	0.48	0.12	0.24±0.06	0.56±0.01
C1	10	41.1	0.50	0.09	0.50±0.03	0.50±0.02
D1	45	57.2	0.42	0.09	0.19±0.05	0.58±0.02
E1 ^e	30	60.7	0.46	n/a	n/a	n/a
F1 ^e	10	55.0	0.40	n/a	n/a	n/a
G1	45	82.2	0.45	0.02	0.47±0.02	0.37±0.16
H1	30	81.3	0.45	0.02	0.47±0.02	0.32±0.18

^aCalculated from Eq. (27).

^bCalculated from Eq. (28).

^cCalculated from Eq. (29).

^dThe accuracy of t_2 measurement was in the range of ±0.005.

^eE1 and F1 were damaged during use.

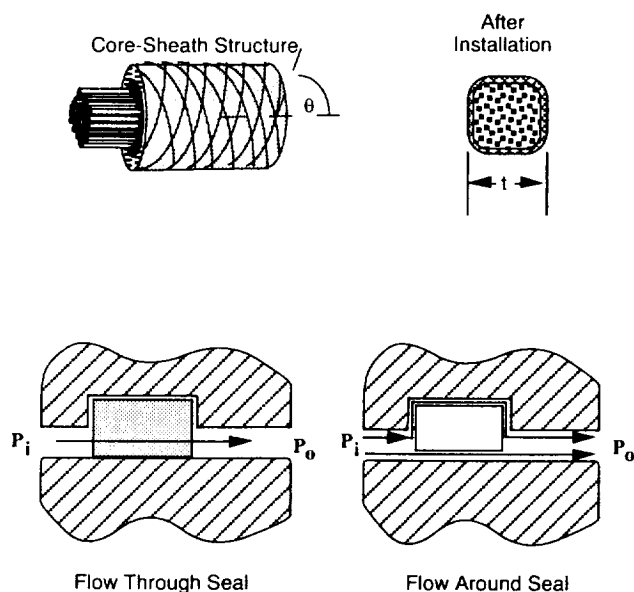


Figure 1.—Definitions of seal leakage flow paths.

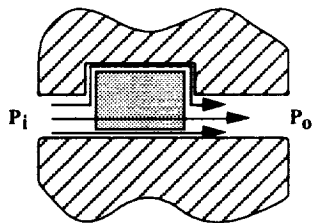


Figure 2.—Schematic diagram for flow Model I: uniform seal porosity.

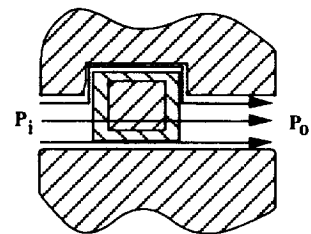


Figure 3.—Schematic diagram for flow Model II: independent sheath and core porosities.

Flow Path	Leakage Rate
	$\frac{\dot{M}_1}{L}$
	$\frac{\dot{M}_2}{L}$
	$\frac{\dot{M}_{345}}{L}$
	$\frac{\dot{M}_6}{L}$
	$\frac{\dot{M}_7}{L}$

Figure 4.—Flow paths used in calculating total flow resistance for Model II.

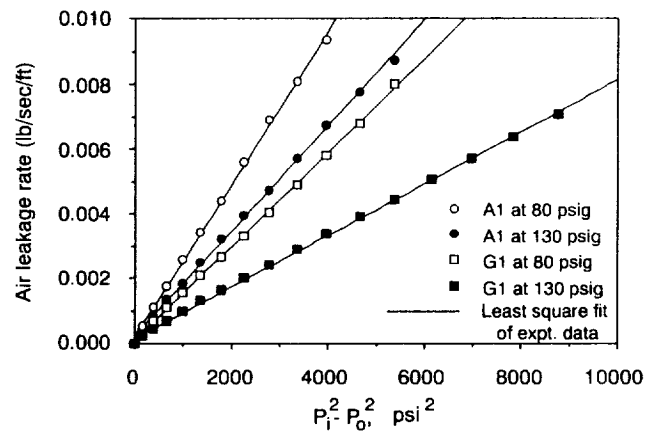


Figure 5.—Measured seal leakage data validating seal leakage pressure dependence.



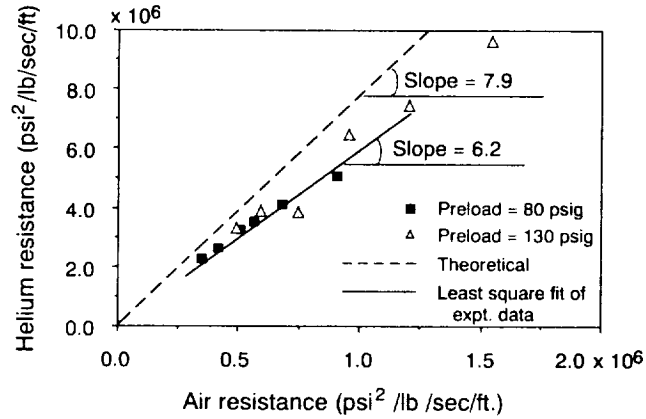



Figure 6.—Measured seal flow resistances of air and helium compared to theoretical expectations.

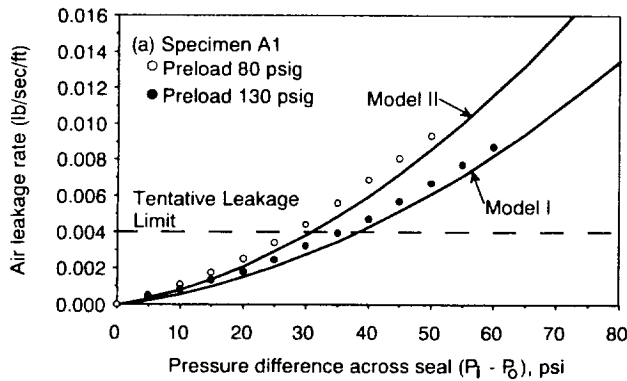


(a) Air.

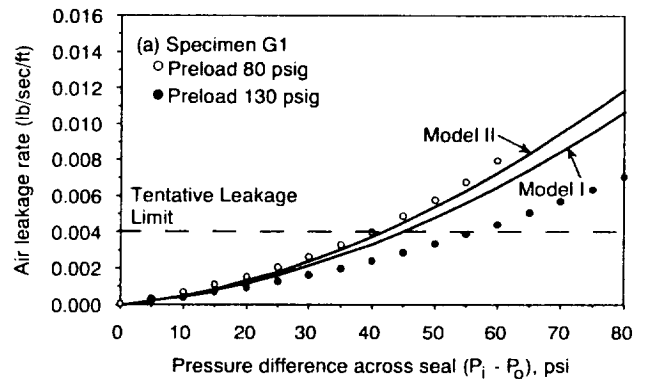

(a) Air.

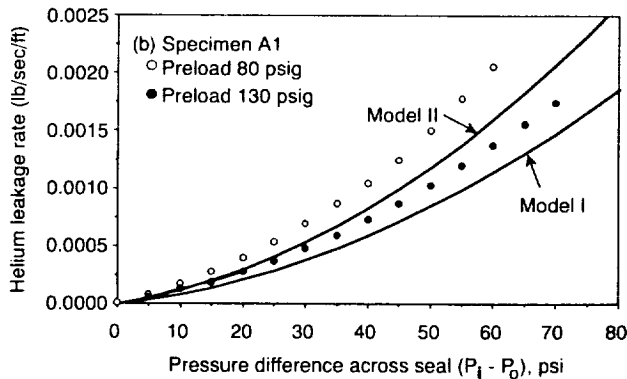

(b) Helium.

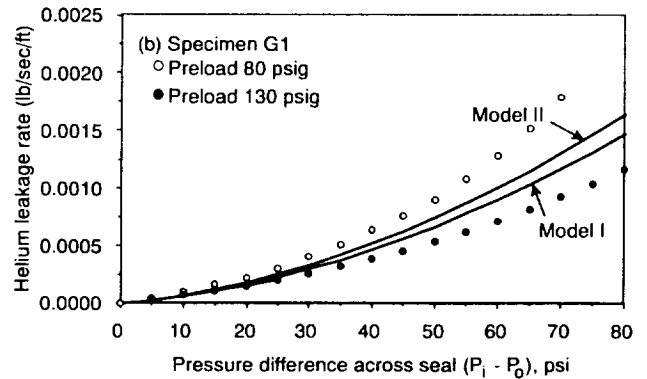

(b) Helium.

Figure 7.—Seal A1: measured leakage rates versus pressure drop (symbols) compared to predictions (lines).

Figure 8.—Seal G1: measured leakage rates versus pressure drop (symbols) compared to predictions (lines).

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE December 1992		3. REPORT TYPE AND DATES COVERED Technical Memorandum
4. TITLE AND SUBTITLE Development of Braided Rope Seals for Hypersonic Engine Applications: Flow Modeling			5. FUNDING NUMBERS WU-505-63-5B	
6. AUTHOR(S) Rajakkannu Mutharasan, Bruce M. Steinetz, Xiaoming Tao, Guang-Wu Du, and Frank Ko				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135-3191			8. PERFORMING ORGANIZATION REPORT NUMBER E-6166-1	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, D.C. 20546-0001			10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA TM-105942	
11. SUPPLEMENTARY NOTES Rajakkannu Mutharasan, Xiaoming Tao, Guang-Wu Du, and Frank Ko, Drexel University, Philadelphia, Pennsylvania, 19104 and Bruce M. Steinetz, NASA Lewis Research Center. Responsible person, Bruce M. Steinetz, (216) 433-3302.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category 37			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A new type of engine seal is being developed to meet the needs of advanced hypersonic engines. A seal braided of emerging high temperature ceramic fibers comprised of a sheath-core construction has been selected for study based on its low leakage rates. Flexible, low-leakage, high temperature seals are required to seal the movable engine panels of advanced ramjet-scamjet engines either preventing potentially dangerous leakage into backside engine cavities or limiting the purge coolant flow rates through the seals. To predict the leakage through these flexible, porous seal structures new analytical flow models are required. Two such models based on Kozeny-Carman equations are developed herein and are compared to experimental leakage measurements for simulated pressure and seal gap conditions. The models developed allow prediction of the gas leakage rate as a function of fiber diameter, fiber packing density, gas properties, and pressure drop across the seal. The first model treats the seal as a homogeneous fiber bed. The second model divides the seal into two homogeneous fiber beds identified as the core and the sheath of the seal. Flow resistances of each of the main seal elements are combined to determine the total flow resistance. Comparisons between measured leakage rates and model predictions for seal structures covering a wide range of braid architectures show good agreement. Within the experimental range, the second model provides a prediction within 6 to 13 percent of the flow for many of the cases examined. Areas where future model refinements are required are identified.				
14. SUBJECT TERMS			15. NUMBER OF PAGES 20	
			16. PRICE CODE A03	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT	