

X 3. N 21/5 : 6/1502

GOVT. DOC.

NACA TN No. 1502

NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

TECHNICAL NOTE

No. 1502

BEARING TESTS OF 14S SHEET AND PLATE

By R. L. Moore

Aluminum Company of America



Washington

August 1948

~~CONN. STATE LIBRARY~~

AUG 16 1948

BUSINESS, SCIENCE
& TECHNOLOGY DEPT.

NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

TECHNICAL NOTE NO. 1502

BEARING TESTS OF 14S SHEET AND PLATE

By R. L. Moore

SUMMARY

Tests were made to determine bearing yield and ultimate strengths of bare and Alclad 14S-W¹ and 14S-T¹ sheet and plate in thicknesses of 0.064 inch, 0.250 inch, and 0.750 inch. From the results of these tests it was concluded that the ratios of bearing to tensile properties for the with-grain direction were essentially the same as proposed in NACA TN Nos. 901, 920, 974, and 981 for other high-strength aluminum-alloy sheet and plate.

INTRODUCTION

Previous investigations of bearing strength made in the Aluminum Research Laboratories in connection with the design of riveted, bolted, or pin-connected joints have covered most of the aluminum alloys used in sheet or plate form in aircraft structural design (references 1 to 4). Although bearing-strength data have been given in reference 5 for 14S sheet, the only tests of this alloy appear to be those made on 1/4-inch-thick forged bars and reported in reference 1. In view of the importance being attached to 14S as a high-strength, general-purpose, aluminum alloy, some additional investigation of bearing properties was believed to be warranted.

The object of these tests was to determine bearing yield and ultimate strengths of several thicknesses of 14S-W and 14S-T sheet and plate and to establish approximate ratios of bearing to tensile properties.

MATERIAL

Table I gives essential data on the tempers, thicknesses, and tensile properties of the materials used for these bearing tests. It will be noted that both yield and ultimate strengths, as well as elongation values, were consistently higher for the with-grain than for the cross-grain direction. The greatest differences were observed for the yield strengths of the W temper and ranged, as shown in table II, from 10 to 20 percent. It should also be noted from table II that the cross-grain tensile properties were in every case slightly higher than

¹New Alcoa temper designations: 14S-W now 14S-T3 in case of 0.064-in. sheet; 14S-T4 in case of 0.250- and 0.750-in. plate. 14S-T now 14S-T6 in all cases.

published as typical for these alloys and tempers in reference 6. The maximum differences were about 10 percent. From these comparisons it was concluded that the material selected for this investigation of bearing strengths was typical of commercial 14S sheet and plate.

PROCEDURE

All the bearing tests were made on 2-inch-wide specimens cut in duplicate from both the with- and cross-grain directions. Those from the $\frac{3}{4}$ -inch-thick plate were machined to a thickness of 0.250 inch from the center, whereas the specimens from the 0.064-inch and 0.250-inch Alclad samples were tested in full thickness. The 0.064-inch-thick specimens were loaded in bearing on a $\frac{1}{4}$ -inch-diameter steel pin; those of 0.250-inch thickness were loaded on a $\frac{1}{2}$ -inch-diameter steel pin.

Edge distances, measured in the direction of stressing from the center of the hole to the edge of the specimen, were limited in these tests to 1.5 and 2 times the pin diameter since these distances are the only ones for which bearing design values are commonly given (reference 5)

Figure 1 shows the general arrangement for making bearing tests in a 40,000-pound-capacity Amsler hydraulic testing machine. Hole elongations, from which values of bearing yield strength were determined, were obtained by measuring the relative movement of the pin and the specimen by means of a filar micrometer microscope which could be read directly to 0.01 millimeter. The projecting portion of the pin on the microscope side was flattened slightly on the under side to provide a shoulder on which the reference mark for pin movement was located. A small scratch on the specimen under the pin provided a reference mark for specimen movement.

RESULTS AND DISCUSSION

Table III gives values of bearing yield and ultimate strength and types of failure for all the bearing tests. The yield-strength values indicated were selected from the bearing stress-hole elongation curves shown in figures 2 to 7 as the stresses corresponding to an offset of 2 percent of the pin diameter.

The general behavior of the 14S specimens in bearing was the same as previously observed for the other high-strength, wrought-aluminum alloys tested in the form of sheet and plate. Failures occurred either by shearing out the portion of the specimen above the pin or by a combination of shear and tensile fracture through the pin hole. Shear

failures predominated in the 0.064-inch-thick specimens, for which the ratio of specimen width to pin diameter was 8, whereas combined shear and tensile failures were obtained in the majority of the 0.250-inch-thick specimens, for which the ratio of width to pin diameter was 4. It should be emphasized, however, that these differences in specimen proportions were not in a range where they had any significant effect on the bearing properties determined.

Previous tests have indicated no marked difference in with- and cross-grain bearing properties and the values shown in table III are in generally good agreement with this observation. The maximum difference indicated in table II was only about 7 percent and the average differences for all tests under any one set of conditions did not exceed 4 percent.

Table IV gives the ratios obtained between average bearing and tensile strengths. It is quite evident from these data and those given in table V that the 14S sheet and plate samples exhibited about the same bearing-strength characteristics as previously observed for other high-strength aluminum alloys in the same form. The following nominal ratios of bearing to tensile properties, which were proposed on the basis of previous tests (references 1 to 4), appear applicable, therefore, to alloy 14S.

Ratios for with-grain tests	Edge distances	
	1.5 × pin diam.	2 × pin diam.
<u>Bearing ultimate</u> Tensile ultimate	1.5	1.9
<u>Bearing yield</u> Tensile yield	1.4	1.6

In three cases in table IV the with-grain ratios of bearing to tensile strengths for different thicknesses of 14S-T were as much as 8 percent less than the foregoing nominal ratios. Since these differences occurred in isolated cases, however, involving different properties or edge distances, they were not considered as significant as if uniformly low ratios had been observed for all tests of any one thickness or temper. In all other cases in table IV the deficiencies in bearing-to-tensile strength ratios for the 14S samples, when they did exist, were less than 6 percent. It should be pointed out that table V shows only two other with-grain ratios (one for 0.250-inch- and one for 2.00-inch-thick 24S-T plate) that are more than 5 percent less than the nominal ratios proposed for sheet and plate.

Emphasis has been placed thus far upon ratios of with-grain bearing to tensile properties because many of the earlier tests of sheet were limited to this direction. The only real need for differentiation with

respect to direction occurs in the case of materials exhibiting a marked difference in tensile yield strength in the with- and cross-grain directions, resulting from a stretcher-levelling or flattening operation. Since bearing properties show no marked directional characteristics, the same ratios of bearing to tensile properties are not applicable to with- or cross-grain tensile yield strengths. The present practice of listing with-grain tensile properties in reference 5 greatly simplifies the use of with-grain ratios in obtaining bearing strengths. It is of interest to point out in this connection that the ratios of cross-grain bearing to tensile yield strength proposed in reference 4 for 24S-T plate reduce to approximately the same ratios as listed herein for the with-grain direction, if the cross-grain values are multiplied by the ratio of the typical cross-grain to with-grain tensile yield strength.

The allowable bearing yield stresses listed in reference 5 for 14S-W sheet are somewhat lower, in proportion to the tensile yield strength, than given for 14S-T sheet. This difference is just opposite to that observed in these tests for which the yield ratios were consistently higher for the 14S-W. The most important observation perhaps is that in only two cases do the design stresses in reference 5 correspond to a higher ratio of bearing to tensile strength than obtained in these tests and that the maximum difference for these cases was only about 7 percent.

CONCLUSION

It was concluded from tests of bare and Alclad 14S-W and 14S-T sheet and plate, in thicknesses of 0.064 inch, 0.250 inch, and 0.750 inch, that the ratios of bearing to tensile properties for the with-grain direction were essentially the same as previously proposed in NACA TN Nos. 901, 920, 974, and 981 for other high-strength, aluminum-alloy sheet and plate, namely:

Ratios for with-grain tests	Edge distances	
	1.5 × pin diam.	2 × pin diam.
<u>Bearing ultimate</u> <u>Tensile ultimate</u>	1.5	1.9
<u>Bearing yield</u> <u>Tensile yield</u>	1.4	1.6

Aluminum Research Laboratories

Aluminum Company of America

New Kensington, Pa., January 20, 1947

REFERENCES

1. Moore, R. L., and Wescoat, C.: Bearing Strengths of Some Wrought-Aluminum Alloys. NACA TN No. 901, 1943.
2. Moore, R. L., and Wescoat, C.: Bearing Strengths of Bare and Alclad XA75S-T and 24S-T81 Aluminum Alloy Sheet. NACA TN No. 920, 1943.
3. Wescoat, C., and Moore, R. L.: Bearing Strengths of 75S-T Aluminum-Alloy Sheet and Extruded Angle. NACA TN No. 974, 1945.
4. Moore, R. L., and Wescoat, C.: Bearing Strengths of 24S-T Aluminum Alloy Plate. NACA TN No. 981, 1945.
5. Anon.: Strength of Metal Aircraft Elements. ANC-5, Amendment No. 2, Aug. 1946.
6. Anon.: Alcoa Aluminum and Its Alloys. Aluminum Co. of Am., 1946, table 12.

TABLE I

TENSILE PROPERTIES OF 14S SHEET AND PLATE USED IN BEARING TESTS

[All values are average of two tests made in accordance with A.S.T.M. Standards (E8-42). W indicates with grain; X indicates across grain]

Alloy and temper	Sample	Nominal thickness (in.)	Direction of test	Tensile strength (psi)	Yield strength (offset = 0.2 percent) (psi)	Elongation in 2 in. (percent)
Alclad 14S-W	74466	0.064	X	64,800	40,400	20.5
			W	65,800	47,400	21.2
Alclad 14S-T	74467	.064	X	68,200	60,700	9.5
			W	68,800	62,000	11.0
Alclad 14S-W	74474	.250	X	64,500	39,800	19.0
			W	65,200	47,600	21.0
Alclad 14S-T	74475	.250	X	68,000	59,700	10.2
			W	69,600	63,800	11.5
14S-W	75933	.750	X	66,500	43,900	16.0
			W	69,600	48,300	17.3
14S-T	75958	.750	X	70,600	62,800	8.3
			W	71,600	63,800	9.8

TABLE II

COMPARISONS BETWEEN WITH-GRAIN AND CROSS-GRAIN STRENGTHS IN TENSION AND BEARING

Alloy and temper	Nominal thickness (in.)	Ratios of observed with-grain to cross-grain properties						Ratios of observed cross-grain to typical properties	
		Tensile ultimate	Tensile yield	Bearing ultimate		Bearing yield		Tensile ultimate	Tensile yield
				e = 1.5D ¹	e = 2D	e = 1.5D	e = 2D		
Alclad 14S-W	0.064	1.02	1.17	1.02	1.03	1.02	1.02	1.10	1.06
Alclad 14S-T	.064	1.01	1.02	.99	.93	.97	.93	1.05	1.05
Alclad 14S-W	.250	1.01	1.20	.97	1.02	1.00	1.04	1.09	1.05
Alclad 14S-T	.250	1.02	1.07	.97	.99	.97	.96	1.05	1.03
14S-W	.750	1.05	1.10	1.03	1.00	.97	.95	1.07	1.10
14S-T	.750	<u>1.01</u>	<u>1.02</u>	<u>.96</u>	<u>1.00</u>	<u>.99</u>	<u>1.00</u>	<u>1.01</u>	<u>1.05</u>
Average for W temper		1.03	1.16	1.01	1.02	1.00	1.00	1.09	1.07
Average for T temper		1.01	1.04	.97	.97	.98	.96	1.04	1.04

¹e, edge distance; D, pin diameter.

TABLE III

BEARING STRENGTHS OF 14S SHEET AND PLATE

Alloy and temper	Specimen thickness (in.) (1)	Direction of test	Test	Bearing strengths (psi)					
				Edge distance = 1.5 × pin diameter			Edge distance = 2 × pin diameter		
				Ultimate	Yield (2)	Type of failure (3)	Ultimate	Yield	Type of failure
Alclad 14S-W (74466)	0.064	X	1 2 Av.	104,100 103,500 103,800	66,000 63,500 64,800	S S S	131,300 131,300 131,300	78,000 76,000 77,000	S TS S
Alclad 14S-W	.064	W	1 2 Av.	105,900 105,900 105,900	65,000 66,900 66,000	S S S	142,300 129,400 135,900	78,000 79,000 78,500	S S S
Alclad 14S-T (74467)	.064	X	1 2 Av.	110,300 109,800 110,100	86,000 85,500 85,800	S S S	153,100 141,100 147,100	107,000 102,300 104,700	S S S
Alclad 14S-T	.064	W	1 2 Av.	109,700 109,400 109,600	79,000 80,000 79,500	S S S	134,700 149,700 142,200	97,200 96,500 96,900	S S S
Alclad 14S-W (74474)	.250	X	1 2 Av.	100,800 99,200 100,000	64,500 66,000 65,300	TS TS TS	129,500 129,600 129,600	77,000 77,500 77,300	TS TS TS
Alclad 14S-W	.250	W	1 2 Av.	95,600 98,800 97,200	65,500 68,000 66,800	TS TS TS	130,500 129,500 130,000	79,800 81,000 80,400	TS S S
Alclad 14S-T (74475)	.250	X	1 2 Av.	104,000 104,200 104,100	87,200 87,000 87,100	TS TS TS	140,000 135,600 137,800	100,000 96,000 98,000	TS TS TS
Alclad 14S-T	.250	W	1 2 Av.	100,000 102,000 101,000	86,300 86,200 86,300	TS TS TS	134,900 132,000 133,500	94,000 95,000 94,500	TS TS TS
14S-W (75933)	.250	X	1 2 Av.	98,600 96,000 97,300	69,100 68,200 68,700	TS TS TS	131,600 131,700 131,700	85,000 81,700 83,400	S TS S
14S-W	.250	W	1 2 Av.	100,600 99,000 99,800	71,100 66,800 68,900	TS TS TS	130,000 124,400 127,200	74,500 84,500 79,500	S TS S
14S-T (75958)	.250	X	1 2 Av.	103,200 101,600 102,400	84,000 83,900 84,000	TS TS TS	136,900 145,000 141,000	97,500 103,800 100,700	TS TS TS
14S-T	.250	W	1 2 Av.	98,400 99,400 98,900	82,500 86,200 84,400	TS TS TS	138,000 141,600 139,800	102,100 100,000 101,100	TS TS TS

¹All bearing specimens were 2 in. wide. Those of 0.064-in. thickness were loaded on a $\frac{1}{4}$ -in.-diameter steel pin; those of 0.250-in. thickness were loaded on a $\frac{1}{2}$ -in.-diameter steel pin.

²Bearing yield strength corresponds to offset of 2 percent of pin diameter on bearing stress-hole elongation curves.

³S indicates shear above pin. TS indicates combination of shear above pin and tensile fracture through hole.

TABLE IV

RATIOS OF AVERAGE BEARING TO TENSILE STRENGTHS

[BS, bearing ultimate strength; BYS, bearing yield strength;
TS, tensile ultimate strength; TYS, tensile yield strength]

Alloy and temper	Nominal thickness (in.)	Direction of test	Ratios for edge distances of -			
			1.5 × pin diameter		2 × pin diameter	
			BS/TS	BYS/TYS	BS/TS	BYS/TYS
Alclad 14S-W	0.064	X	1.60	1.60	2.02	1.91
		W	1.61	1.39	2.06	1.66
Alclad 14S-T	.064	X	1.61	1.41	2.16	1.72
		W	1.59	1.28	2.07	1.56
Alclad 14S-W	.250	X	1.55	1.64	2.01	1.94
		W	1.49	1.40	2.00	1.69
Alclad 14S-T	.250	X	1.53	1.46	2.02	1.64
		W	1.45	1.35	1.92	1.48
14S-W	.750	X	1.46	1.57	1.98	1.90
		W	1.44	1.43	1.83	1.65
14S-T	.750	X	1.45	1.34	2.00	1.60
		W	1.38	1.32	1.95	1.58

TABLE V

COMPARISON OF RATIOS OF BEARING TO TENSILE STRENGTHS FOR 14S WITH
RATIOS FOR OTHER HIGH-STRENGTH ALUMINUM-ALLOY SHEET AND PLATE

Alloy and temper	Nominal thickness (in.)	Direction of test	Ratios for edge distances of -			
			1.5 × pin diameter		2.0 × pin diameter	
			BS/TS	BYS/TYS	BS/TS	BYS/TYS
Alclad 14S-W	0.064	X	1.60	1.60	2.02	1.91
Alclad 14S-T	.064	X	1.61	1.41	2.16	1.72
24S-T	.064	X	1.46	1.57	1.90	1.89
75S-T	.064	X	1.62	1.54	2.05	1.74
Alclad 14S-W	.064	W	1.61	1.39	2.06	1.66
Alclad 14S-T	.064	W	1.59	1.28	2.07	1.56
24S-T	.064	W	1.52	1.41	1.98	1.64
Alclad 24S-T	.064	W	1.53	1.37	2.00	1.56
24S-RT	.064	W	1.45	1.40	1.83	1.54
24S-T81	.064	W	1.45	1.42	1.97	1.59
Alclad 24S-T81	.064	W	1.54	1.46	2.06	1.61
75S-T	.064	W	1.63	1.46	2.03	1.66
Alclad 14S-W	.250	X	1.55	1.64	2.01	1.94
Alclad 14S-T	.250	X	1.53	1.46	2.02	1.64
24S-T	.250	X	1.50	1.53	1.90	1.83
Alclad 14S-W	.250	W	1.49	1.40	2.00	1.69
Alclad 14S-T	.250	W	1.45	1.35	1.92	1.48
24S-T	.250	W	1.43	1.23	1.82	1.54
14S-W	.750	X	1.46	1.57	1.98	1.90
14S-T	.750	X	1.45	1.34	2.00	1.60
14S-W	.750	W	1.44	1.43	1.83	1.65
14S-T	.750	W	1.38	1.32	1.95	1.58
24S-T	2.00	X	1.58	1.56	1.97	1.80
24S-T	2.00	W	1.45	1.55	1.76	1.75

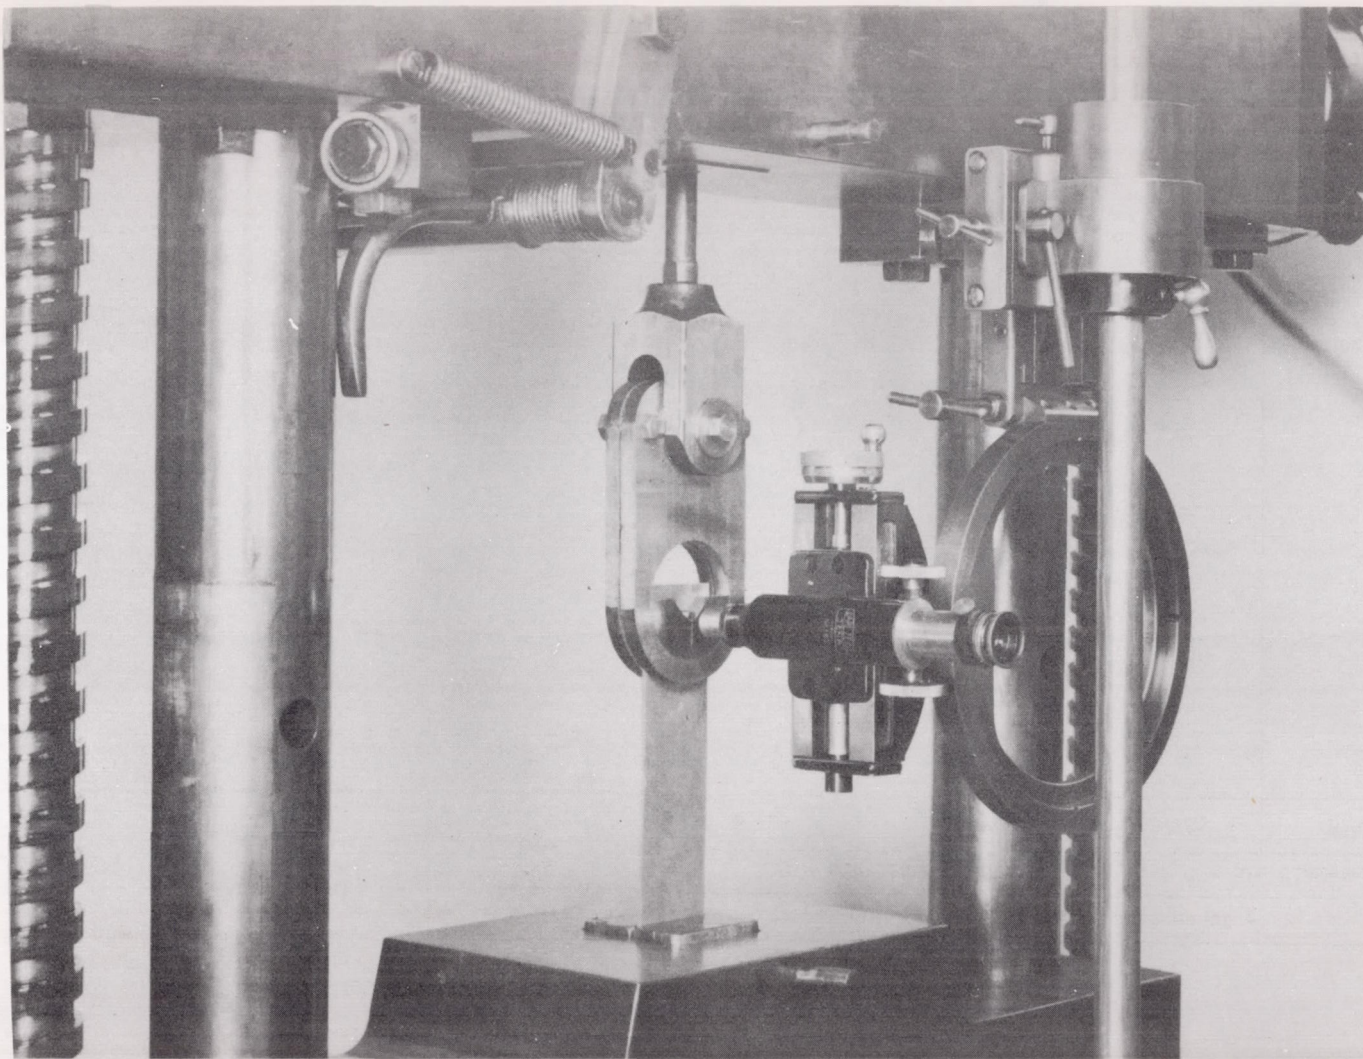


Figure 1.- Arrangement for bearing tests. Microscope used for measurement of hole elongations.

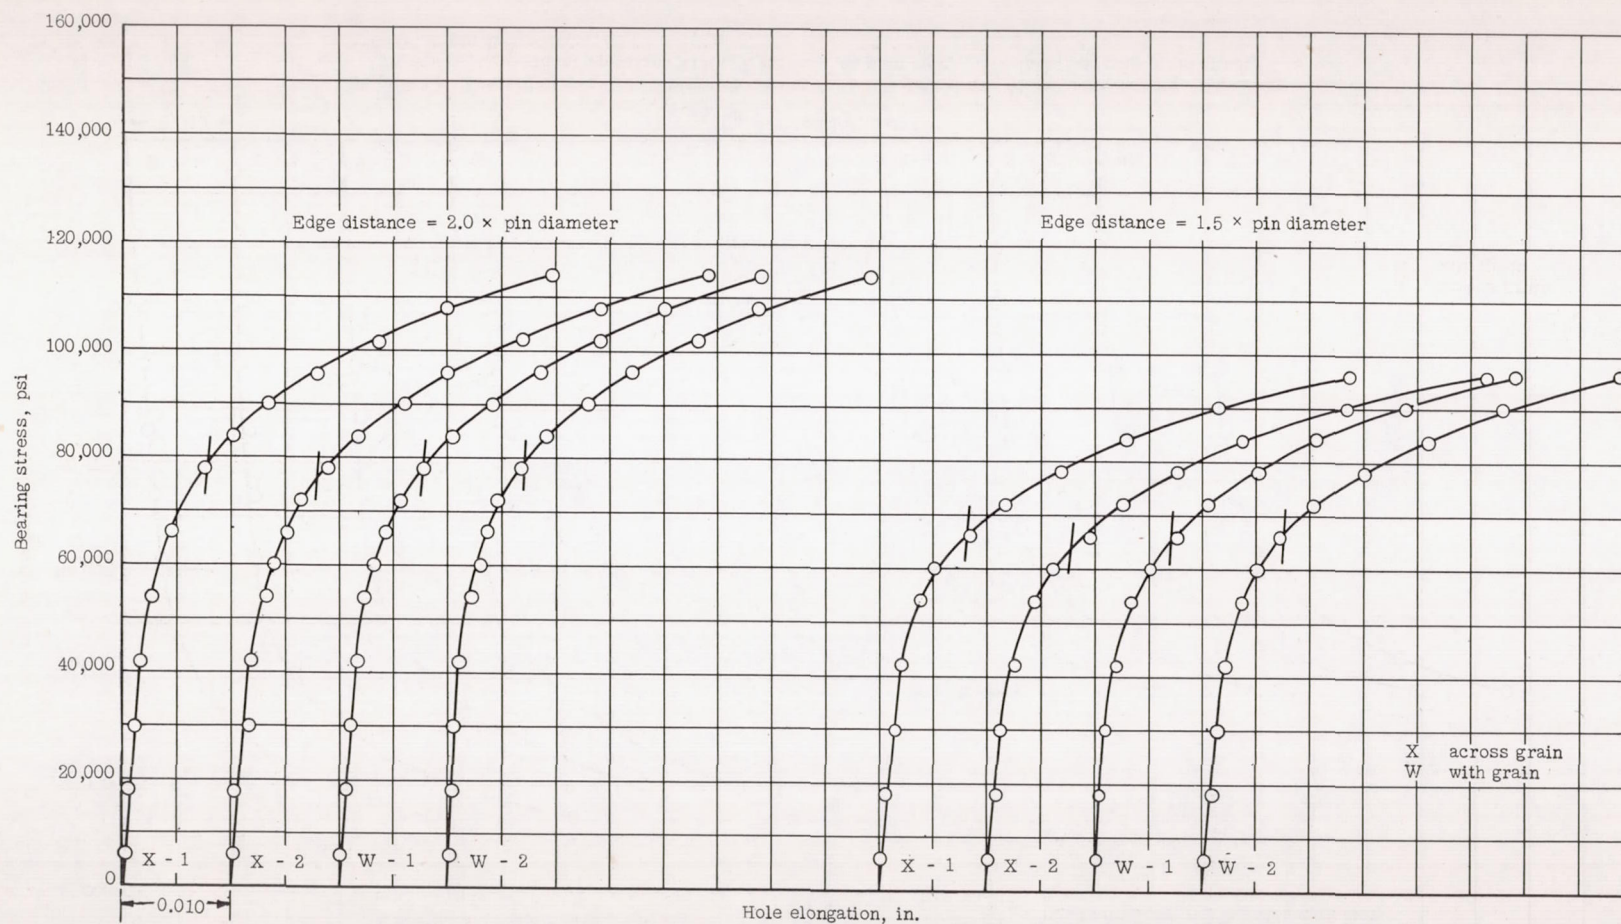


Figure 2.- Bearing stress-hole elongation curves for 0.064-inch-thick Alclad 14S-W sheet. Specimen thickness, 0.064 inch; specimen width, 2 inches; pin diameter, 0.250 inch; bearing-yield offset, $0.02 \times$ pin diameter.

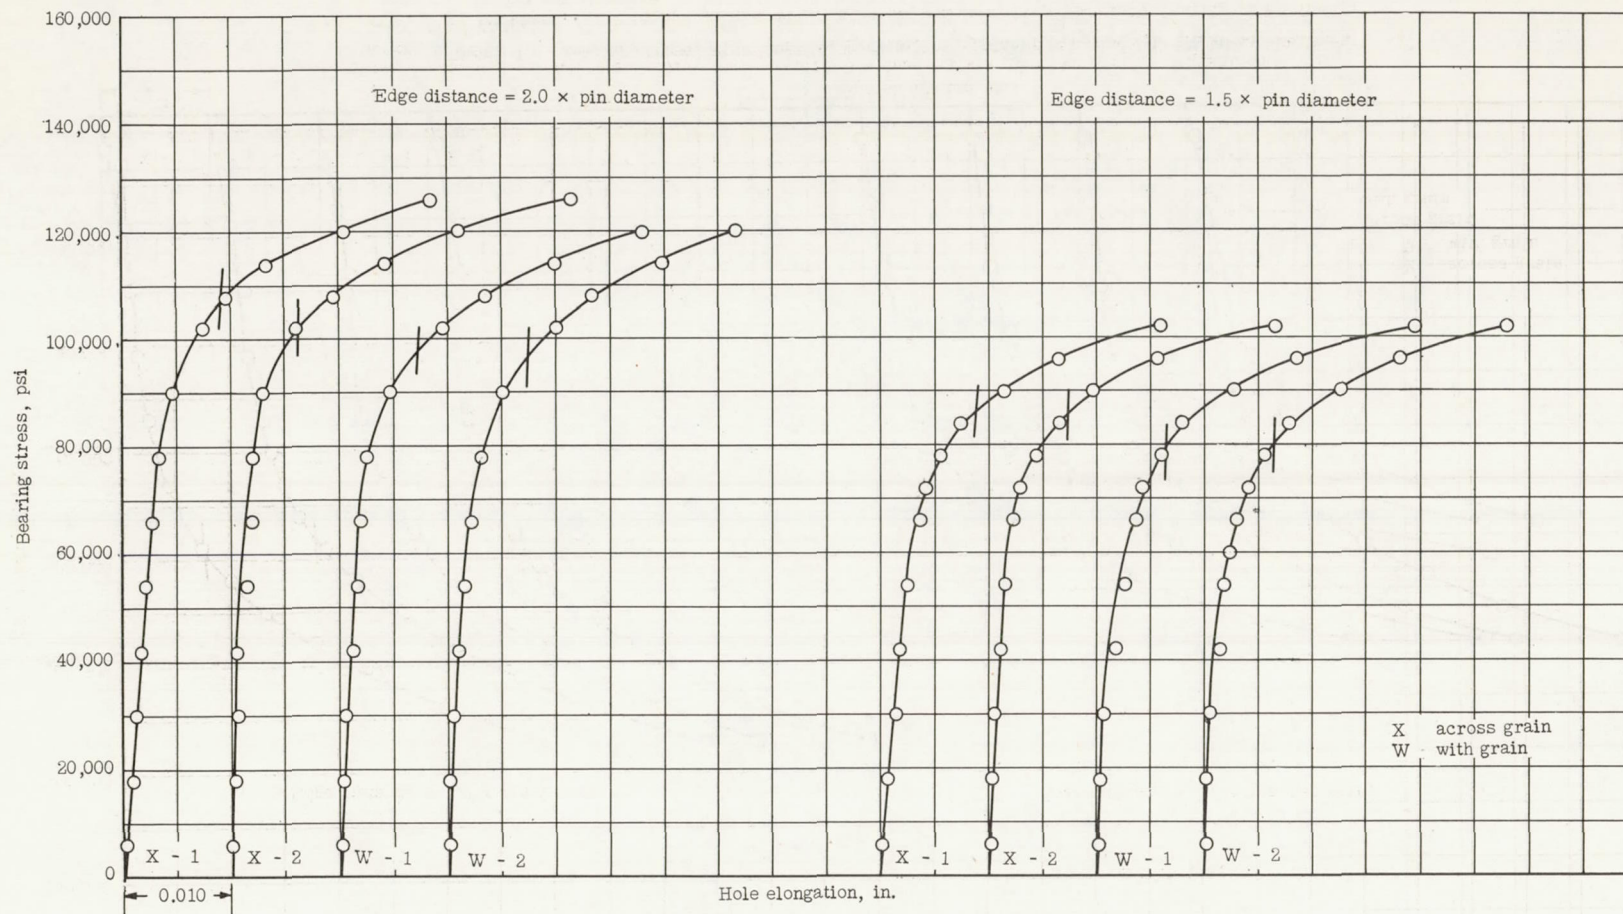


Figure 3.- Bearing stress-hole elongation curves for 0.064-inch-thick Alclad 14S-T sheet. Specimen thickness, 0.064 inch; specimen width, 2 inches; pin diameter, 0.250 inch; bearing-yield offset, $0.02 \times$ pin diameter.

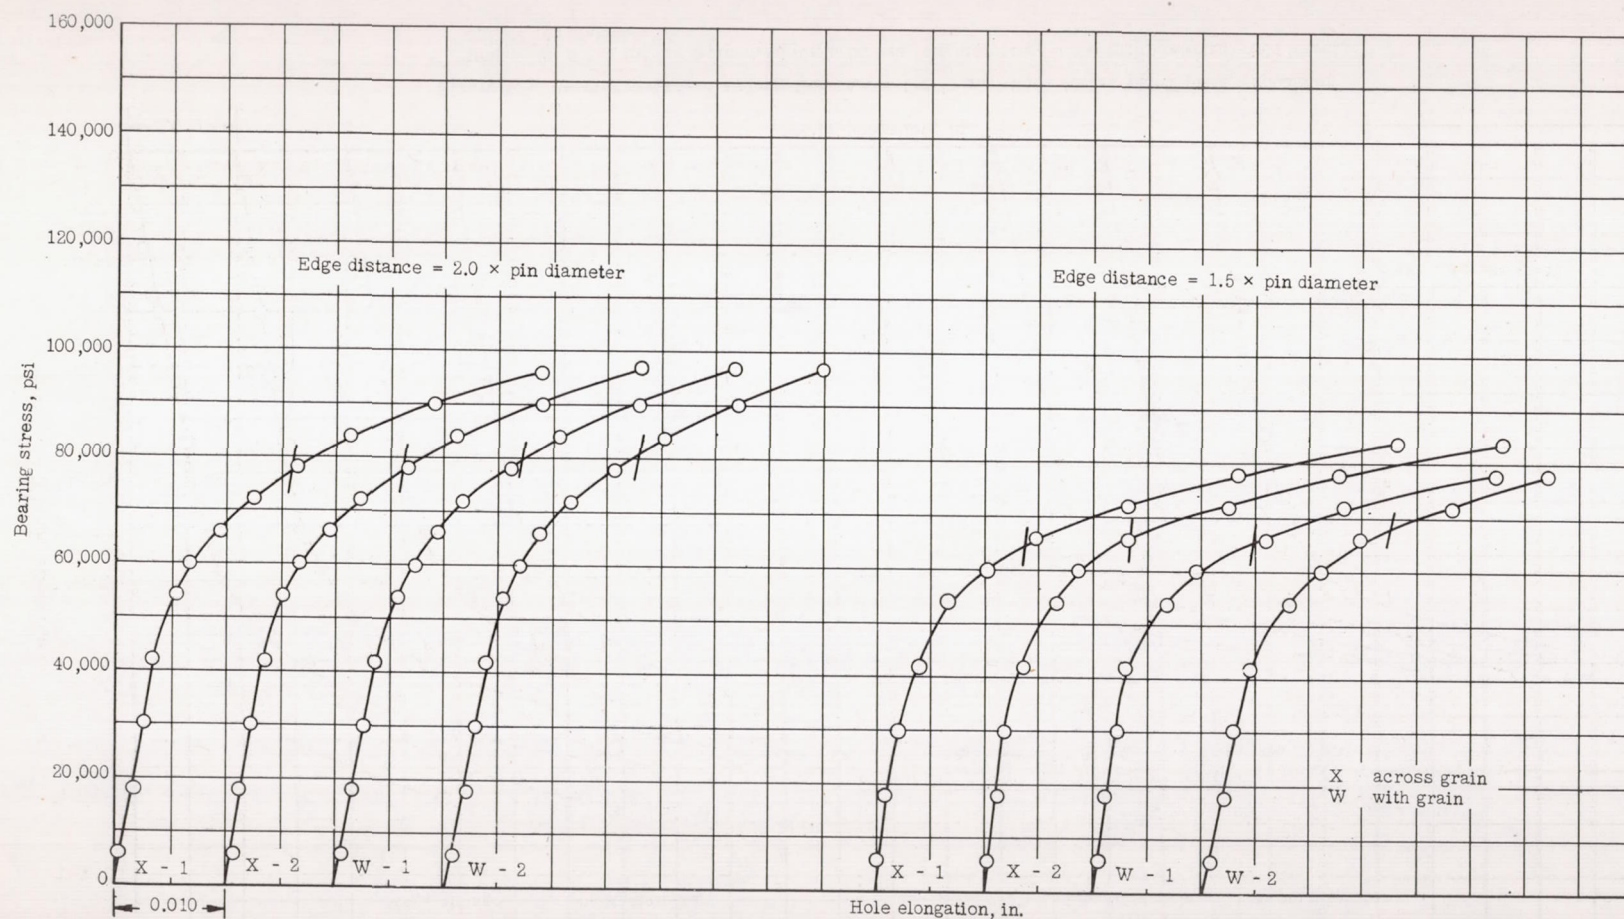


Figure 4.- Bearing stress-hole elongation curves for $\frac{1}{4}$ -inch-thick Alclad 14S-W plate. Specimen thickness, 0.250 inch; specimen width, 2 inches; pin diameter, 0.500 inch; bearing-yield offset, $0.02 \times \text{pin diameter}$.

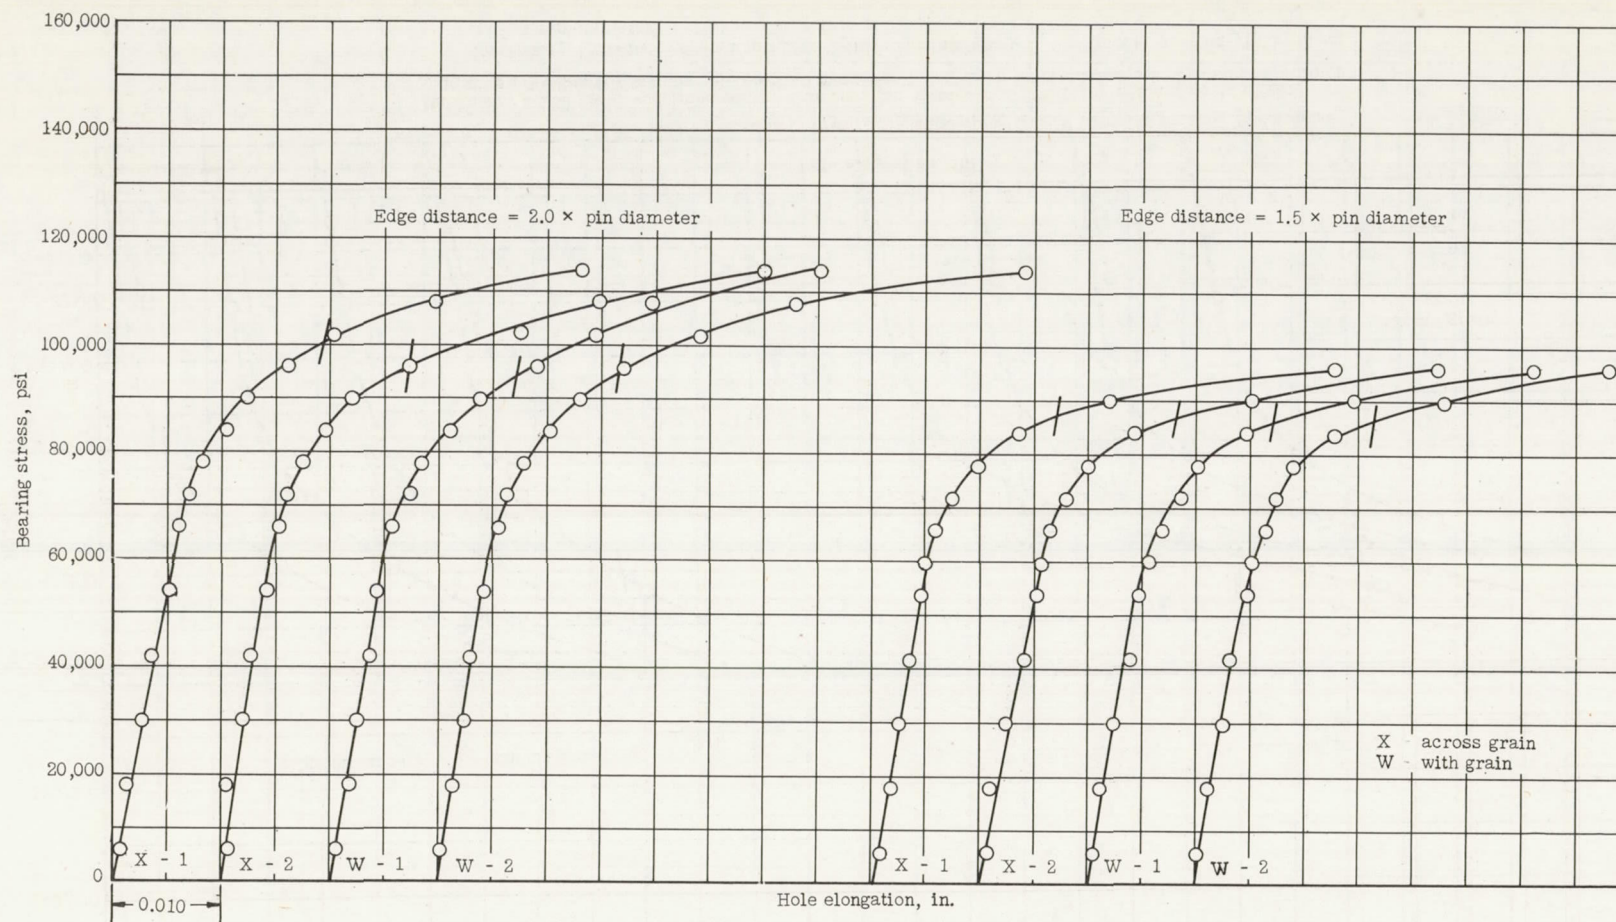


Figure 5.- Bearing stress-hole elongation curves for $\frac{1}{4}$ -inch-thick Alclad 14S-T plate. Specimen thickness, 0.250 inch; specimen width, 2 inches; pin diameter, 0.500 inch; bearing-yield offset, $0.02 \times$ pin diameter.

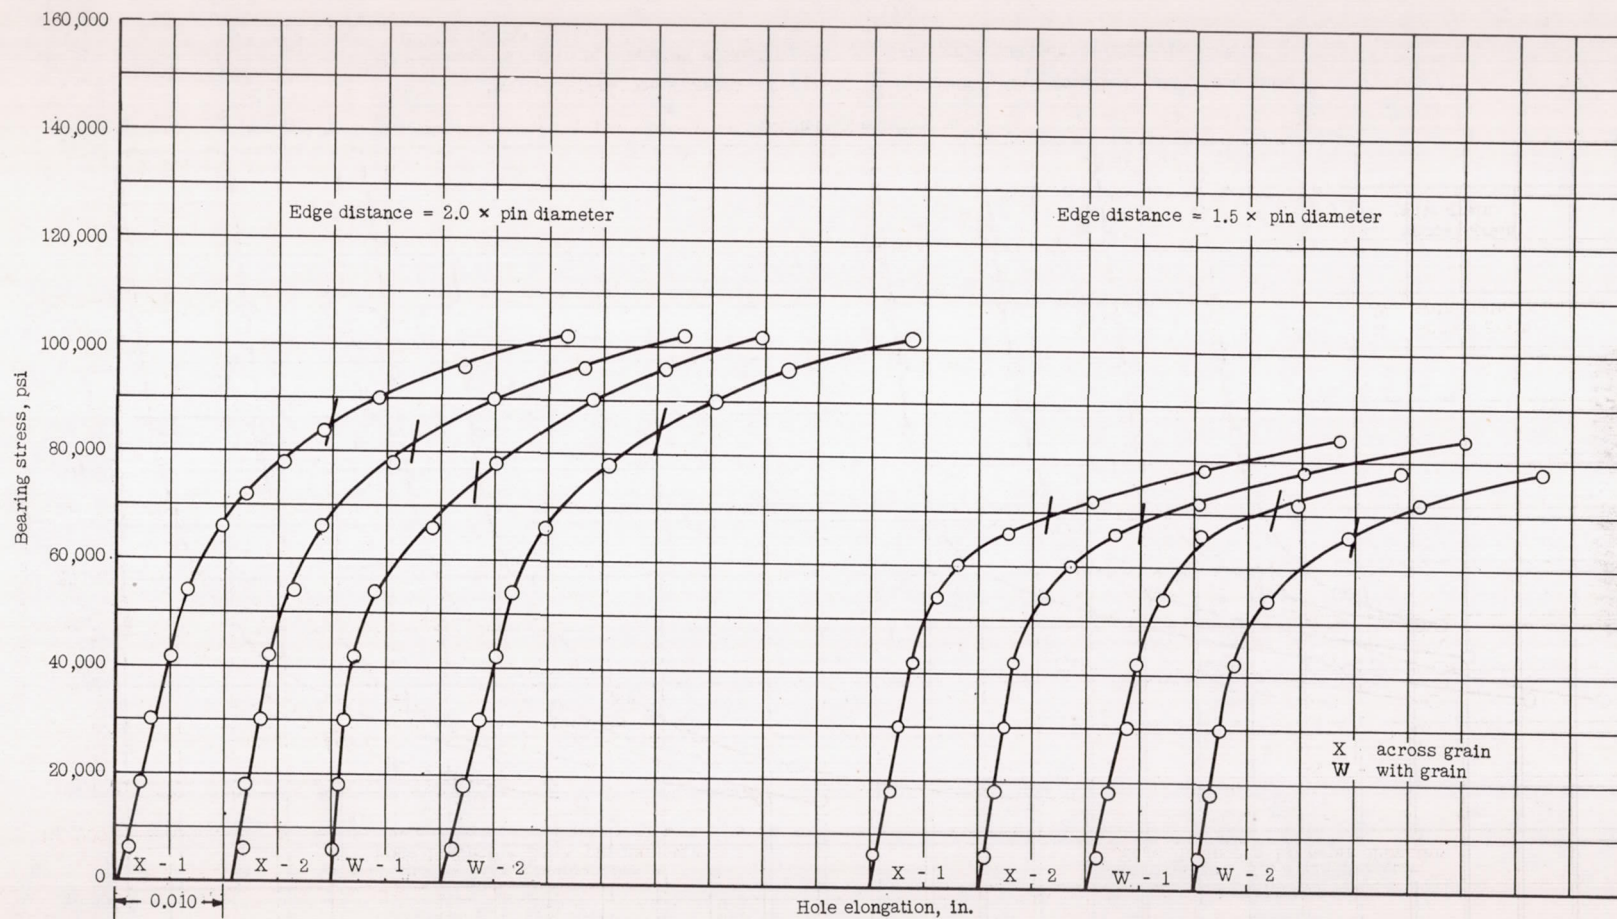


Figure 6.- Bearing stress-hole elongation curves for $\frac{3}{4}$ -inch-thick 14S-W (nonclad) plate. Specimen thickness, 0.250 inch; specimen width, 2 inches; pin diameter, 0.500 inch; bearing-yield offset, $0.02 \times$ pin diameter.

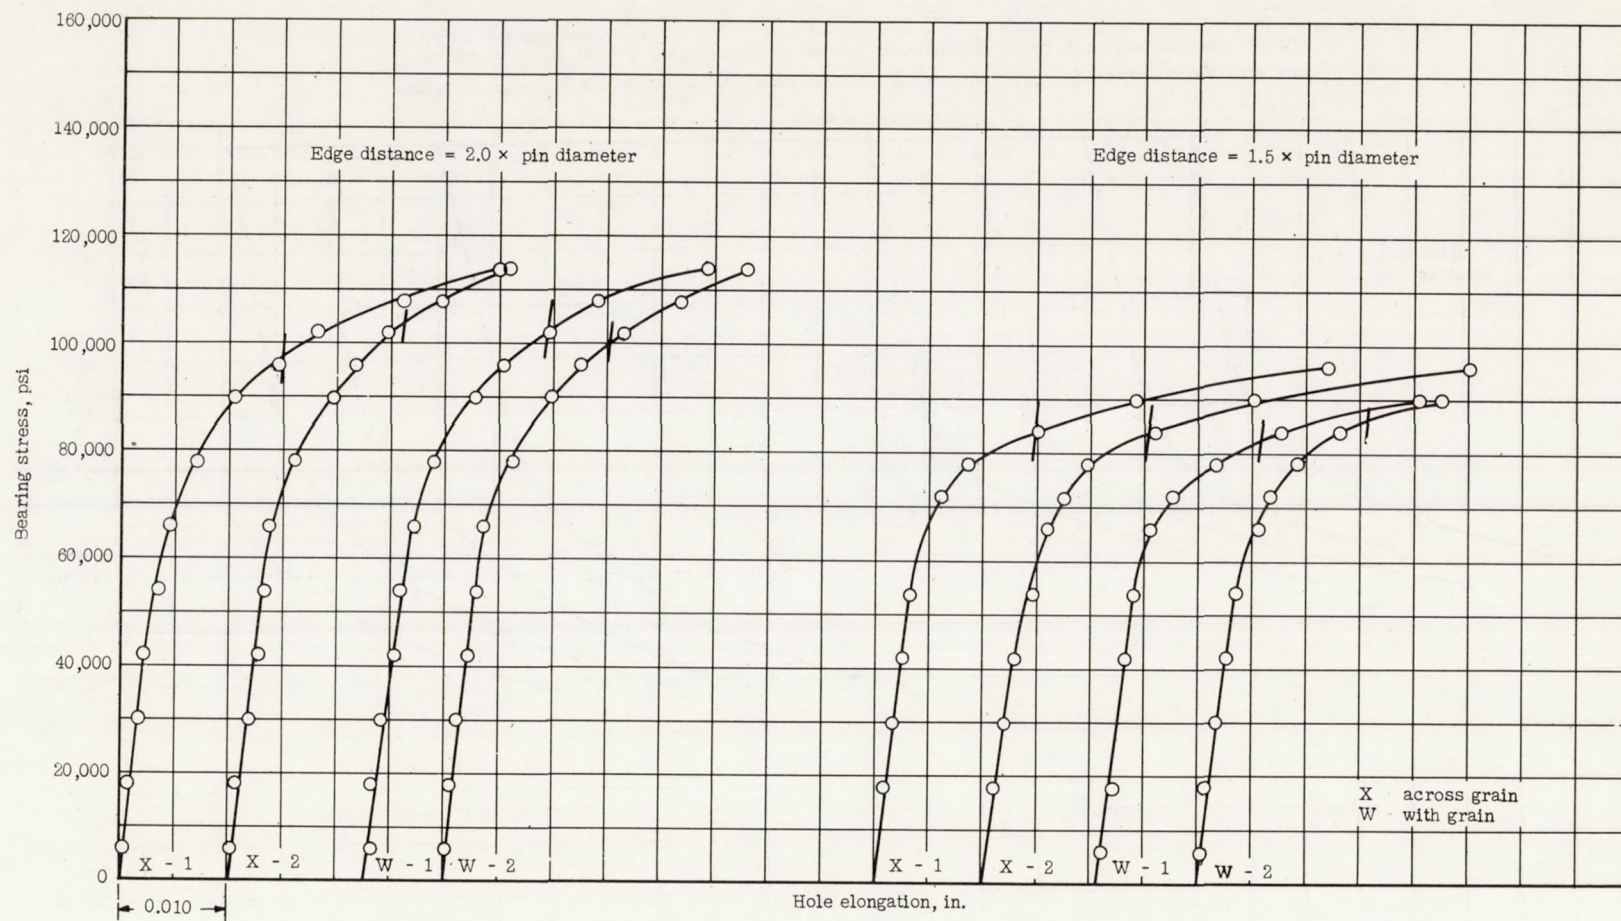


Figure 7.- Bearing stress-hole elongation curves for $\frac{3}{4}$ -inch-thick 14S-T (nonclad) plate. Specimen thickness, 0.250 inch; specimen width, 2 inches; pin diameter, 0.500 inch; bearing-yield offset, $0.02 \times$ pin diameter.