

CLASSIFIED DOCUMENT

This document contains classified information affecting the National Defense of the United States within the meaning of the Espionage Act, USC 50:81 and 82. Its transmission or the revelation of its contents in any manner to an unauthorized person is prohibited by law. Information so classified may be imparted only to persons in the military and naval Services of the United States, appropriate civilian officers and employees of the Federal Government who have a legitimate interest therein, and to United States citizens of known loyalty and discretion who of necessity must be informed thereof.

RESTRICTED

TECHNICAL NOTES

NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

CASE FILE COPY


No. 793

THE COMPRESSIVE YIELD STRENGTH OF EXTRUDED SHAPES OF
24ST ALUMINUM ALLOY

By R. L. Templin, F. M. Howell, and E. C. Hartmann
Aluminum Company of America

PROPERTY FAIRCHILD
ENGINEERING LIBRARY

Washington
January 1941

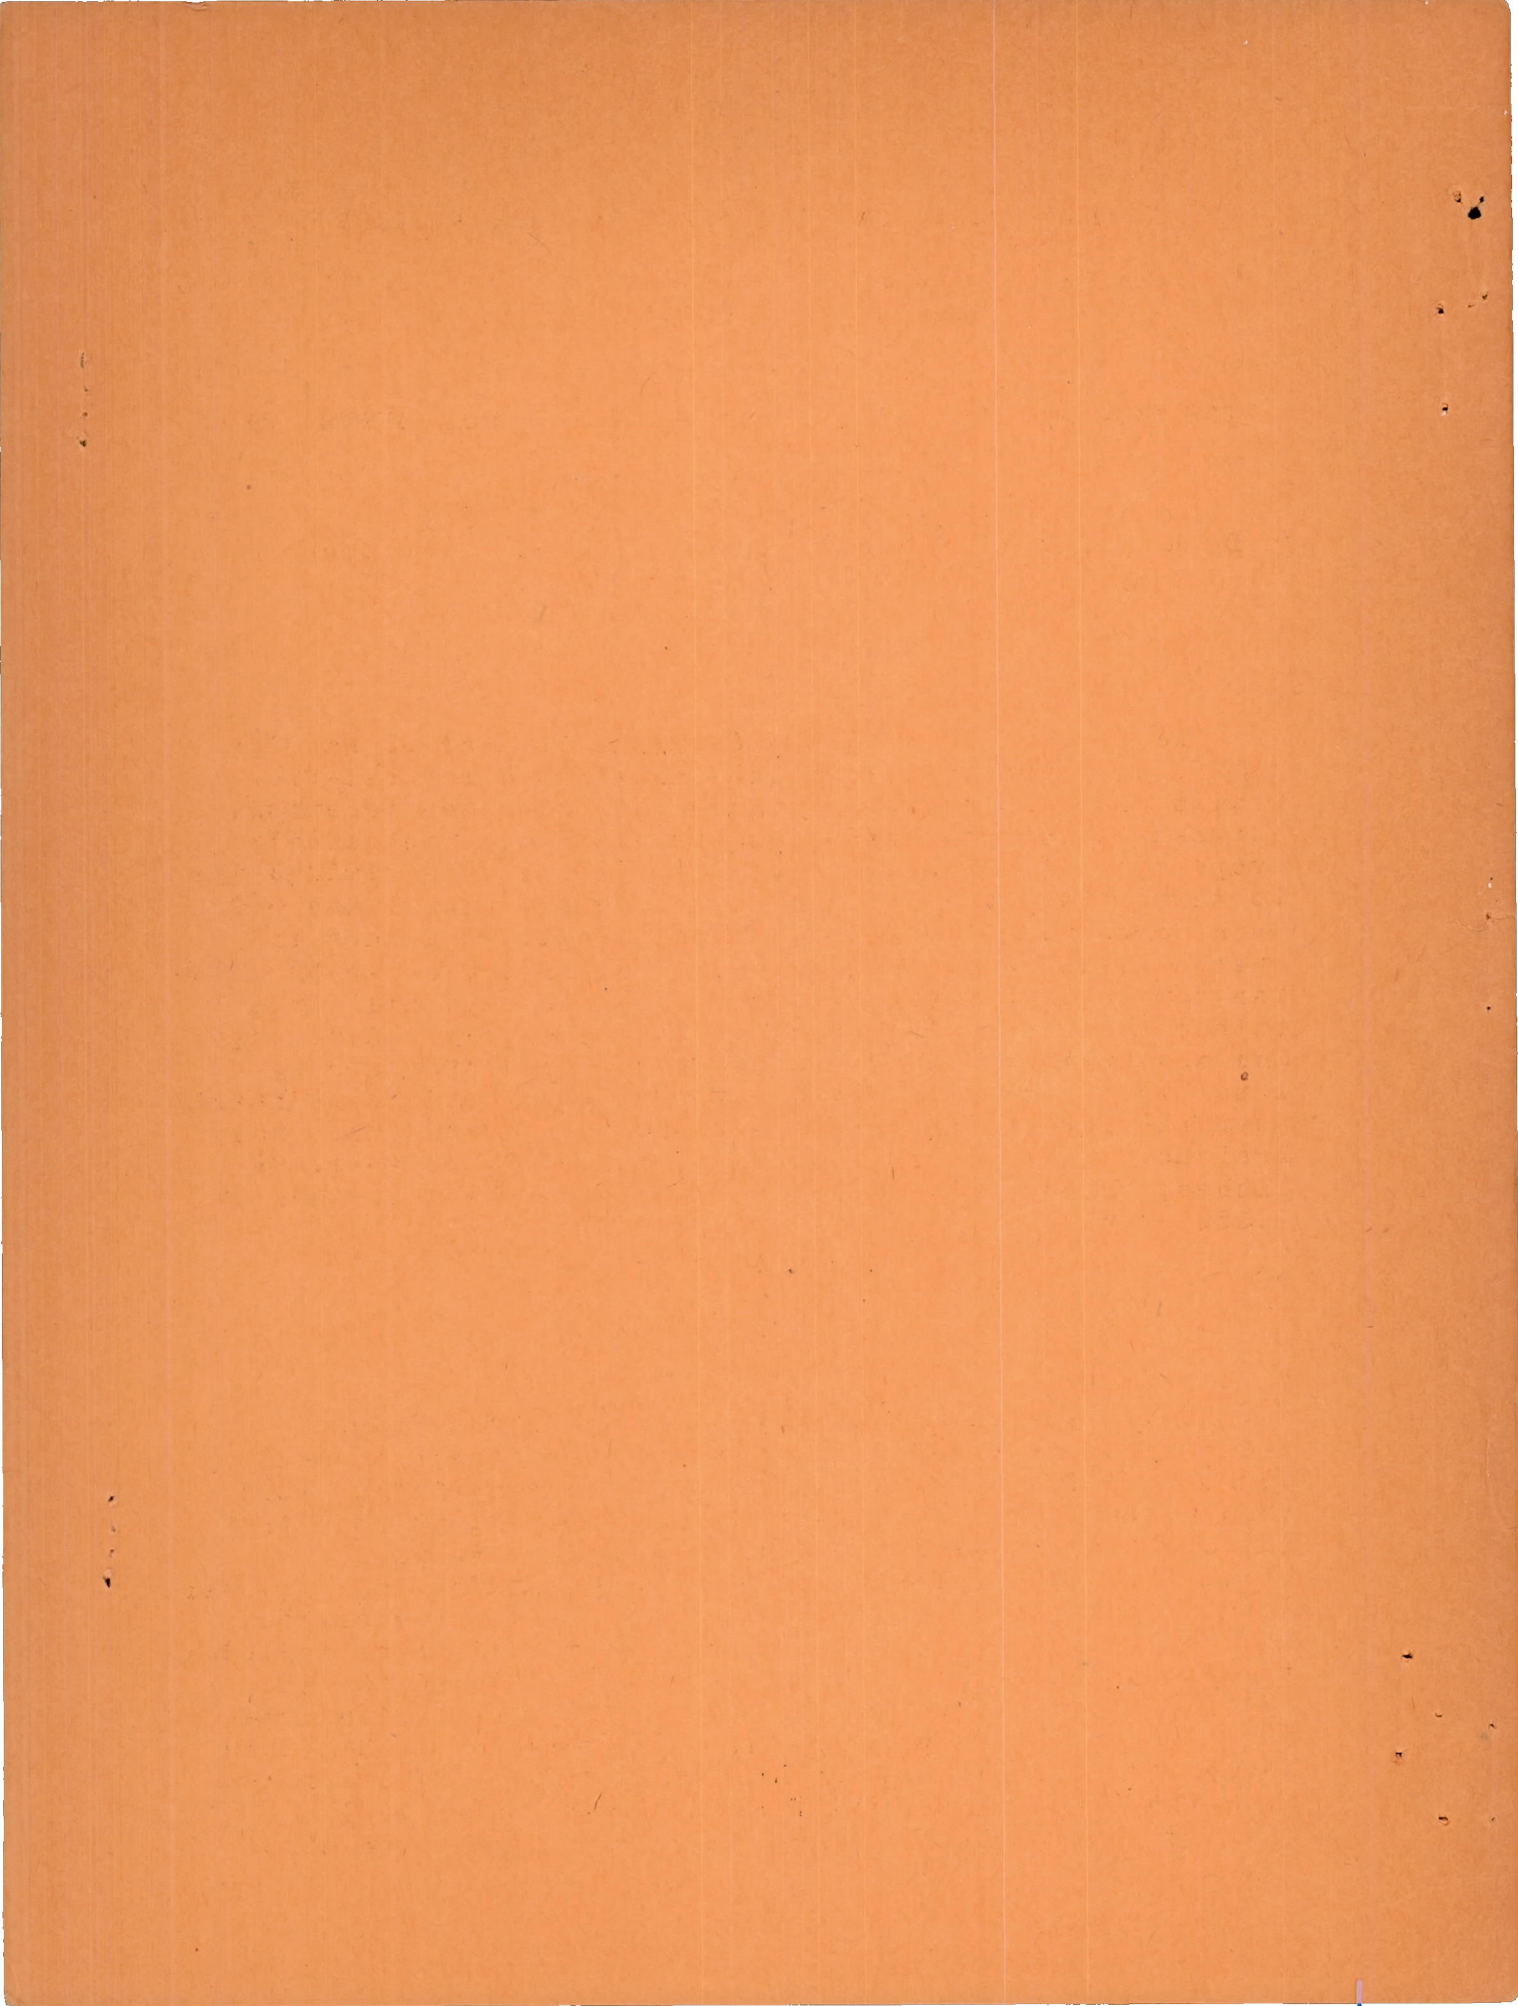

NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

TECHNICAL NOTE NO. 793

THE COMPRESSIVE YIELD STRENGTH OF EXTRUDED SHAPES OF 24ST ALUMINUM ALLOY

By R. L. Templin, F. M. Howell, and E. C. Hartmann

SUMMARY

Tests were made by the Aluminum Company of America on 267 extruded shapes of 24ST aluminum alloy selected at random from plant production to determine the relations between the compressive yield strength and the tensile properties of the material. The samples were divided into three classes according to thickness: less than 0.250 inch, from 0.250 to 1.499 inches; and 1.500 inches and over. Ratios were computed for the three classes by which the compressive yield strength could be estimated from either the tensile strength or the tensile yield strength. The assumption that the compressive yield strength is equal to the tensile yield strength was found to be fairly accurate for the thicknesses 1.500 inches and over, not seriously in error for thicknesses from 0.250 to 1.499 inches, but unsatisfactory for the sections less than 0.250 inch.

INTRODUCTION

Navy Department specification 46A9c and Federal specification QQ-A-354 require extruded shapes of 24ST aluminum alloy to have tensile yield strengths not less than certain minimum values that are dependent upon the thickness of the shape. Minimum compressive yield strengths, although perhaps more important to the engineer than minimum tensile strengths, are not specified because they are too difficult to determine to be included in routine inspection tests and are not needed for the control of quality. In the absence of specific information concerning compressive yield strengths, it has been common practice in the past to assume that the compressive yield strength was equal to the tensile yield strength, even though it was generally understood that

materials which are straightened by stretching usually have compressive yield strengths lower than their tensile yield strengths. Preliminary tests disclosed that the difference between compressive and tensile yield strengths might be large enough to require attention in design, and it was decided to undertake a complete investigation involving a large number of samples selected at random from the general run of commercial production. The timely development of the "pack" method for determining compressive yield strengths of thin sections was an important factor in making this investigation possible. (See reference 1.)

The data upon which this report is based were discussed at a conference with representatives of several government agencies in Washington, D. C., last August. Since that time further study of the data has been made and certain considerations are presented herein that were not included in that discussion.

The object of this investigation was to determine the tensile and the compressive properties of a large number of 24ST extruded shapes selected at random from commercial production in order to investigate the interrelation of these properties. It was believed that through such an investigation a reliable method could be devised by which compressive yield strengths could be accurately estimated from tensile properties, thereby eliminating the need for elaborate expensive routine compression tests.

PROCEDURE

A total of 267 extruded shapes of 24ST aluminum alloy were selected over the period from December 1938 to August 1939. These samples represented a wide variety of shapes and sizes, as indicated in figures 1 to 5. One tensile and one compressive specimen were taken from each shape in the longitudinal direction. The tensile specimens were of the type used for testing sheet (reference 2, fig. 7) when the section thickness was less than 1/2 inch and were of the round type (reference 2, fig. 9) when the section thicknesses were 1/2 inch and greater. The compressive specimens were of the pack type (reference 1) when the section thicknesses were less than 0.243 inch and were 5/8 inch wide solid rectangular blocks when the thicknesses were in the range from 0.243 inch to 0.719 inch. For

thicker sections the compressive specimens were solid rounds. In all cases the tension and the compression specimens were cut from the same part of the section and from adjacent portions of the piece.

The tensile and the compressive tests were made in the usual manner; all pack compression tests and a few of the other tests were made at the Aluminum Research Laboratories while the rest were made at the New Kensington Works laboratory.

RESULTS AND DISCUSSION

All the test data were tabulated and arranged in order of increasing thickness of the portion of the section from which the specimens were cut. There was some duplication of sections and the same die number appeared more than once because pieces made from the same die were selected at different times during the 9 months that the tests were being made.

Table I shows a summary of the tensile and the compressive properties arranged to show minimum, average, and maximum values for each of the three specification ranges of size, as well as for the group as a whole. This table also shows a comparison of the lowest tensile test results with the specified minimum values. It is clear that all the specimens selected for these tests gave results above the specified minimum values.

Figures 6, 7, and 8 show the individual tensile strengths, tensile yield strengths, and compressive yield strengths, respectively, plotted against thickness of section. In all cases there is an upward trend of the data with increasing thickness with a marked leveling off for thicknesses in excess of about 1-1/2 inches. This trend, of course, is consistent with that of the specified minimum tensile properties. In figures 6 and 7 heavy dotted horizontal lines have been drawn to represent the present specified minimum tensile properties for the three ranges of size. The lines drawn in figure 8 will be discussed later.

It is evident from a study of table I and a comparison of figures 7 and 8 that the compressive yield strengths of 24ST extruded shapes are definitely and consistently

lower than the tensile yield strenghts, especially for thicknesses less than 1-1/2 inches. In order to study this relation further, the ratios of compressive yield strength to tensile yield strength were calculated for all cases; the results are plotted on a frequency basis in figure 9. These same ratios are plotted separately for each of the specification ranges of size in figures 10 and 11. These curves show that the most probable values of the ratio of compressive to tensile yield strength are as follows:

Thicknesses less than 0.250 inch 0.88

Thicknesses 0.250 inch to 1.499 inches . . 0.91

Thicknesses 1.500 inches and over 0.96

In a previous investigation based on tests of only 11 24ST shapes ranging in thickness from 0.05 inch to 0.38 inch, the average ratio of compressive to tensile yield strength was found to be 0.85 with a scatter from 0.78 to 1.03. This result agrees fairly well with the results shown in the frequency diagram in figure 10, which covers the most nearly comparable thickness range. The previous investigation also showed that there was less variation in the ratios of compressive yield strength to tensile strength than there was in the ratios of compressive yield strength to tensile yield strength. In other words, tensile strength seemed to be a more satisfactory basis for the ratios than tensile yield strength. With this consideration in mind, table II was prepared to show a comparison of the two sets of ratios summarized from the 267 cases tested. Comparison of the percentage deviation of the minimum and the maximum ratios from the average, given in the last two columns of table II, indicates that tensile strength is slightly better than tensile yield strength as a basis for the ratios, but the advantage is not nearly so pronounced as it appeared to be in the previous investigation.

Thus far in this report the emphasis has been placed on the average values of yield strength rather than on the minimum values. The minimum values, however, may be of considerable importance. The average ratios of compressive yield strength to the tensile properties having been determined, the next step would therefore be to try these ratios out in connection with the specified minimum tensile properties to see whether the resulting computed minimum compressive yield strengths agree with the lowest test results. This comparison has been shown in table III.

It is evident from table III that the general agreement between the computed minimum compressive yield strengths and the lowest test results is good. When the computed minimum compressive yield strength is based on the minimum guaranteed tensile yield strength, only two test results (three-fourths of 1 percent of the total number) are below the computed minimum values. When the computed minimum compressive yield strength is based on the minimum guaranteed tensile strength, the results are somewhat less conservative, three test results (about 1 percent of the total number) being below the minimum.

In order to show graphically how the computed minimum compressive yield strengths in table III compare with the actual test data, the dotted horizontal lines representing the computed minimum compressive yield strengths have been drawn in figure 8. Here again it will be noted that the minimums based on tensile strength are consistently above those based on tensile yield strength. The test results that lie below the computed minimums are all in the thickness range of 0.250 inch to 1.499 inches, and it should be remembered that these two or three values are only about 1 percent of the total number of tests.

It is clear from the data presented in this report that the assumption commonly made that the compressive yield strength is equal to the tensile yield strength is not very satisfactory, as far as the general run of values is concerned. It will be well, however, to investigate this assumption with respect to minimum values. Horizontal lines have been drawn in figure 8 to represent the specified minimum tensile yield strengths. It will be noted that, in the thickness range of 1.500 inches and over, no compressive yield strengths are below the specified minimum tensile yield strength. In the intermediate thickness range only four compressive yield strengths (6 percent of those determined in this range) are below the specified minimum tensile yield strength. In the smallest thickness range, sections thinner than 0.250 inch, 83 compressive yield strengths (47 percent of those determined in this range) are below the specified minimum tensile yield strength. The significance of these relations of the compressive yield strengths and the specified minimum tensile yield strengths is that, except in the thickness range below 0.250 inch, no great error would be involved in the simple assumption that the minimum compressive yield strength is equal to the minimum tensile yield strength. In the range of thickness below 0.250 inch, however, this simple assumption does not seem to be satisfactory.

CONCLUSIONS

From the results of these tests on 267 samples of 24ST extruded shapes selected at random from plant production over a period of 9 months, the following conclusions seem warranted:

1. All the samples tested had tensile strengths and tensile yield strengths greater than the minimum values called for by Federal specification QQ-A-354 and Navy Department specification 46A9c.

2. The compressive yield strength of a 24ST extruded shape can be estimated with a fair degree of accuracy from known tensile yield strength values, as follows:

Thickness	Compressive yield strength (fraction of tensile yield strength)
Less than 0.250 inch	0.88
From 0.250 to 1.499 inches91
1.500 inches and over96

3. Although the foregoing ratios are derived as averages for a large number of samples covering a wide range of properties, when used with the specified minimum tensile yield strength they are reasonably satisfactory for determining representative minimum compressive yield strengths. The following are the minimum compressive yield strengths determined by multiplying the specified minimum tensile yield strengths by the foregoing ratios:

Thickness	Minimum compressive yield strength (lb/sq in.)
Less than 0.250 inch	37,000
From 0.250 to 1.499 inches	40,000
1.500 inches and over	49,900

4. The Aluminum Company of America does not guarantee any minimum compressive yield strengths for its products because the determination of compressive yield strengths is too difficult to permit them to be included in routine

inspection tests and because compressive yield strengths are not needed for control of quality. The computed minimum compressive yield strengths given in conclusion 3 are in good agreement with the lowest test results, except in the range of thicknesses 1.5 inches and over. For this range of thicknesses, no compressive yield strengths were found lower than the specified minimum tensile yield strength, 52,000 pounds per square inch.

5. In the foregoing conclusions it has been shown how the compressive yield strengths can be computed from known tensile yield strengths. Equally satisfactory results can be obtained by computing the compressive yield strengths from known tensile strengths. The relation is as follows:

Thickness	Compressive yield strength (fraction of tensile yield strength)
Less than 0.250 inch	0.66
From 0.250 to 1.499 inches69
1.500 inches and over72

6. The computed minimum compressive yield strengths obtained by the foregoing ratios are as follows:

Thickness	Minimum compressive yield strength (lb/sq in.)
Less than 0.250 inch	37,600
From 0.250 to 1.499 inches	41,400
1.500 inches and over	50,400

7. The assumption commonly made, that the compressive yield strengths of 24ST extruded shapes are equal to the tensile yield strengths, is fairly accurate for either average or minimum values for thicknesses of 1.500 inches and over. It is not seriously in error in the range of thicknesses from 0.250 inch to 1.499 inches. For sections thinner than 0.25 inch, however, this assumption is unsatisfactory because it not only leads to estimated average values of compressive yield strength which are 6000

pounds per square inch too high, but it also overestimates the minimum compressive yield strength of more than 40 percent of material included in this thickness range by amounts up to 4400 pounds per square inch. For thicknesses less than 1.5 inches, either of the two methods given in the foregoing conclusions for estimating compressive yield strengths from tensile properties is more accurate than the commonly made assumption discussed.

Aluminum Research Laboratories,
Aluminum Company of America,
New Kensington, Penna., October 11, 1940.

REFERENCES

1. Aitchison, C. S., and Tuckerman, L. B.: The "Pack" Method for Compressive Tests of Thin Specimens of Materials Used in Thin-Wall Structures. Rep. No. 649, NACA, 1939.
2. Anon.: Tension Testing of Metallic Materials. A.S.T.M., E8-36, 1936.

TABLE I.- Summary of Tensile and Compressive Properties of 24ST Extruded Shapes

(Values in parentheses after the minimum tensile properties are the specified minimums according to Navy Department specification 46A9c and Federal specification QQ-A-354, except the 52,000 lb/sq in. value in the tensile yield strength column. This value is given currently as 51,500 lb/sq in., but soon will be raised to 52,000 lb/sq in. Therefore, the higher value will be used throughout this report.)

Size range		Tensile strength (lb/sq in.)	Tensile yield strength (offset-0.2%) (lb/sq in.)	Compressive yield strength (offset-0.2%) (lb/sq in.)
Less than 0.250 inch	Minimum	58,480 (57,000)	42,600 (42,000)	37,600
	Average	65,380	49,125	43,270
	Maximum	79,350	59,100	54,200
0.250 to 1.499 inches	Minimum	62,190 (60,000)	46,570 (44,000)	37,500
	Average	79,645	59,910	54,830
	Maximum	86,500	69,800	65,500
1.500 inches and over	Minimum	77,460 (70,000)	57,300 (52,000)	54,900
	Average	81,060	61,080	58,700
	Maximum	85,380	65,700	62,800
All sizes	Minimum	58,480	42,600	37,500
	Average	70,425	52,950	47,615
	Maximum	86,500	69,800	65,500

PUBLISHED WEEKLY		PUBLISHED WEEKLY	
1914	1915	1916	1917
1918	1919	1920	1921
1922	1923	1924	1925
1926	1927	1928	1929
1930	1931	1932	1933
1934	1935	1936	1937
1938	1939	1940	1941
1942	1943	1944	1945
1946	1947	1948	1949
1950	1951	1952	1953
1954	1955	1956	1957
1958	1959	1960	1961
1962	1963	1964	1965
1966	1967	1968	1969
1970	1971	1972	1973
1974	1975	1976	1977
1978	1979	1980	1981
1982	1983	1984	1985
1986	1987	1988	1989
1990	1991	1992	1993
1994	1995	1996	1997
1998	1999	2000	2001
2002	2003	2004	2005
2006	2007	2008	2009
2010	2011	2012	2013
2014	2015	2016	2017
2018	2019	2020	2021
2022	2023	2024	2025
2026	2027	2028	2029
2030	2031	2032	2033
2034	2035	2036	2037
2038	2039	2040	2041
2042	2043	2044	2045
2046	2047	2048	2049
2050	2051	2052	2053
2054	2055	2056	2057
2058	2059	2060	2061
2062	2063	2064	2065
2066	2067	2068	2069
2070	2071	2072	2073
2074	2075	2076	2077
2078	2079	2080	2081
2082	2083	2084	2085
2086	2087	2088	2089
2090	2091	2092	2093
2094	2095	2096	2097
2098	2099	2100	2101
2102	2103	2104	2105
2106	2107	2108	2109
2110	2111	2112	2113
2114	2115	2116	2117
2118	2119	2120	2121
2122	2123	2124	2125
2126	2127	2128	2129
2130	2131	2132	2133
2134	2135	2136	2137
2138	2139	2140	2141
2142	2143	2144	2145
2146	2147	2148	2149
2150	2151	2152	2153
2154	2155	2156	2157
2158	2159	2160	2161
2162	2163	2164	2165
2166	2167	2168	2169
2170	2171	2172	2173
2174	2175	2176	2177
2178	2179	2180	2181
2182	2183	2184	2185
2186	2187	2188	2189
2190	2191	2192	2193
2194	2195	2196	2197
2198	2199	2200	2201
2202	2203	2204	2205
2206	2207	2208	2209
2210	2211	2212	2213
2214	2215	2216	2217
2218	2219	2220	2221
2222	2223	2224	2225
2226	2227	2228	2229
2230	2231	2232	2233
2234	2235	2236	2237
2238	2239	2240	2241
2242	2243	2244	2245
2246	2247	2248	2249
2250	2251	2252	2253
2254	2255	2256	2257
2258	2259	2260	2261
2262	2263	2264	2265
2266	2267	2268	2269
2270	2271	2272	2273
2274	2275	2276	2277
2278	2279	2280	2281
2282	2283	2284	2285
2286	2287	2288	2289
2290	2291	2292	2293
2294	2295	2296	2297
2298	2299	2300	2301
2302	2303	2304	2305
2306	2307	2308	2309
2310	2311	2312	2313
2314	2315	2316	2317
2318	2319	2320	2321
2322	2323	2324	2325
2326	2327	2328	2329
2330	2331	2332	2333
2334	2335	2336	2337
2338	2339	2340	2341
2342	2343	2344	2345
2346	2347	2348	2349
2350	2351	2352	2353
2354	2355	2356	2357
2358	2359	2360	2361
2362	2363	2364	2365
2366	2367	2368	2369
2370	2371	2372	2373
2374	2375	2376	2377
2378	2379	2380	2381
2382	2383	2384	2385
2386	2387	2388	2389
2390	2391	2392	2393
2394	2395	2396	2397
2398	2399	2400	2401
2402	2403	2404	2405
2406	2407	2408	2409
2410	2411	2412	2413
2414	2415	2416	2417
2418	2419	2420	2421
2422	2423	2424	2425
2426	2427	2428	2429
2430	2431	2432	2433
2434	2435	2436	2437
2438	2439	2440	2441
2442	2443	2444	2445
2446	2447	2448	2449
2450	2451	2452	2453
2454	2455	2456	2457
2458	2459	2460	2461
2462	2463	2464	2465
2466	2467	2468	2469
2470	2471	2472	2473
2474	2475	2476	2477
2478	2479	2480	2481
2482	2483	2484	2485
2486	2487	2488	2489
2490	2491	2492	2493
2494	2495	2496	2497
2498	2499	2500	2501
2502	2503	2504	2505
2506	2507	2508	2509
2510	2511	2512	2513
2514	2515	2516	2517
2518	2519	2520	2521
2522	2523	2524	2525
2526	2527	2528	2529
2530	2531	2532	2533
2534	2535	2536	2537
2538	2539	2540	2541
2542	2543	2544	2545
2546	2547	2548	2549
2550	2551	2552	2553
2554	2555	2556	2557
2558	2559	2560	2561
2562	2563	2564	2565
2566	2567	2568	2569
2570	2571	2572	2573
2574	2575	2576	2577
2578	2579	2580	2581
2582	2583	2584	2585
2586	2587	2588	2589
2590	2591	2592	2593
2594	2595	2596	2597
2598	2599	2600	2601
2602	2603	2604	2605
2606	2607	2608	2609
2610	2611	2612	2613
2614	2615	2616	2617
2618	2619	2620	2621
2622	2623	2624	2625
2626	2627	2628	2629
2630	2631	2632	2633
2634	2635	2636	2637
2638	2639	2640	2641
2642	2643	2644	2645
2646	2647	2648	2649
2650	2651	2652	2653
2654	2655	2656	2657
2658	2659	2660	2661
2662	2663	2664	2665
2666	2667	2668	2669
2670	2671	2672	2673
2674	2675	2676	2677
2678	2679	2680	2681
2682	2683	2684	2685
2686	2687	2688	2689
2690	2691	2692	2693
2694	2695	2696	2697
2698	2699	2700	2701
2702	2703	2704	2705
2706	2707	2708	2709
2710	2711	2712	2713
2714	2715	2716	2717
2718	2719	2720	2721
2722	2723	2724	2725
2726	2727	2728	2729
2730	2731	2732	2733
2734	2735	2736	2737
2738	2739	2740	2741
2742	2743	2744	2745
2746	2747	2748	2749
2750	2751	2752	2753
2754	2755	2756	2757
2758	2759	2760	2761
2762	2763	2764	2765
2766	2767	2768	2769
2770	2771	2772	2773
2774	2775	2776	2777
2778	2779	2780	2781
2782	2783	2784	2785
2786	2787	2788	2789
2790	2791	2792	2793
2794	2795	2796	2797
2798	2799	2800	2801
2802	2803	2804	2805
2806	2807	2808	2809
2810	2811	2812	2813
2814	2815	2816	2817
2818	2819	2820	2821
2822	2823	2824	2825
2826	2827	2828	2829
2830	2831	2832	2833
2834	2835	2836	2837
2838	2839	2840	2841
2842	2843	2844	2845
2846	2847	2848	2849
2850	2851	2852	2853
2854	2855	2856	2857
2858	2859	2860	2861
2862	2863	2864	2865
2866	2867	2868	2869
2870	2871	2872	2873
2874	2875	2876	2877
2878	2879	2880	2881
2882	2883	2884	2885
2886	2887	2888	2889
2890	2891	2892	2893
2894	2895	2896	2897
2898	2899	2900	2901
2902	2903	2904	2905
2906	2907	2908	2909
2910	2911	2912	2913
2914	2915	2916	2917
2918	2919	2920	2921
2922	2923	2924	2925
2926	2927	2928	2929
2930	2931	2932	2933
2934	2935	2936	2937
2938	2939	2940	2941
2942	2943	2944	2945
2946	2947	2948	2949
2950	2951	2952	2953
2954	2955	2956	2957
2958	2959	2960	2961
2962	2963	2964	2965
2966	2967	2968	2969
2970	2971	2972	2973
2974	2975	2976	2977
2978	2979	2980	2981
2982	2983	2984	2985
2986	2987	2988	2989
2990	2991	2992	2993
2994	2995	2996	2997
2998	2999	3000	3001
3002	3003	3004	3005
3006	3007	3008	3009
3010	3011	3012	3013
3014	3015	3016	3017
3018	3019	3020	3021
3022	3023	3024	3025
3026	3027	3028	3029
3030	3031	3032	3033
3034	3035	3036	3037
3038	3039	3040	3041
3042	3043	3044	3045
3046	3047	3048	3049
3050	3051	3052	3053
3054	3055	3056	3057
3058	3059	3060	3061
3062	3063	3064	3065
3066	3067	3068	3069
3070	3071	3072	3073
3074	3075		

TABLE II.- Summary of Ratios of Compressive Yield Strength to Tensile Yield Strength and to Tensile Strength

Size Range		Ratios		Percentage that minimum ratio is below and maximum ratio is above the average value	
		$\frac{CYS}{TYS}$	$\frac{CYS}{TS}$	$\frac{CYS}{TYS}$	$\frac{CYS}{TS}$
Less than 0.250 inch	Minimum	0.76	0.61	14	8
	Average	.88	.66		
	Maximum	1.04	.78	18	18
0.250 to 1.499 inches	Minimum	.73	.56	20	19
	Average	.91	.69		
	Maximum	1.01	.76	11	10
1.500 inches and over	Minimum	.91	.70	5	3
	Average	.96	.72		
	Maximum	.99	.77	3	7
All thicknesses	Minimum	.73	.56	19	16
	Average	.90	.67		
	Maximum	1.04	.78	16	16

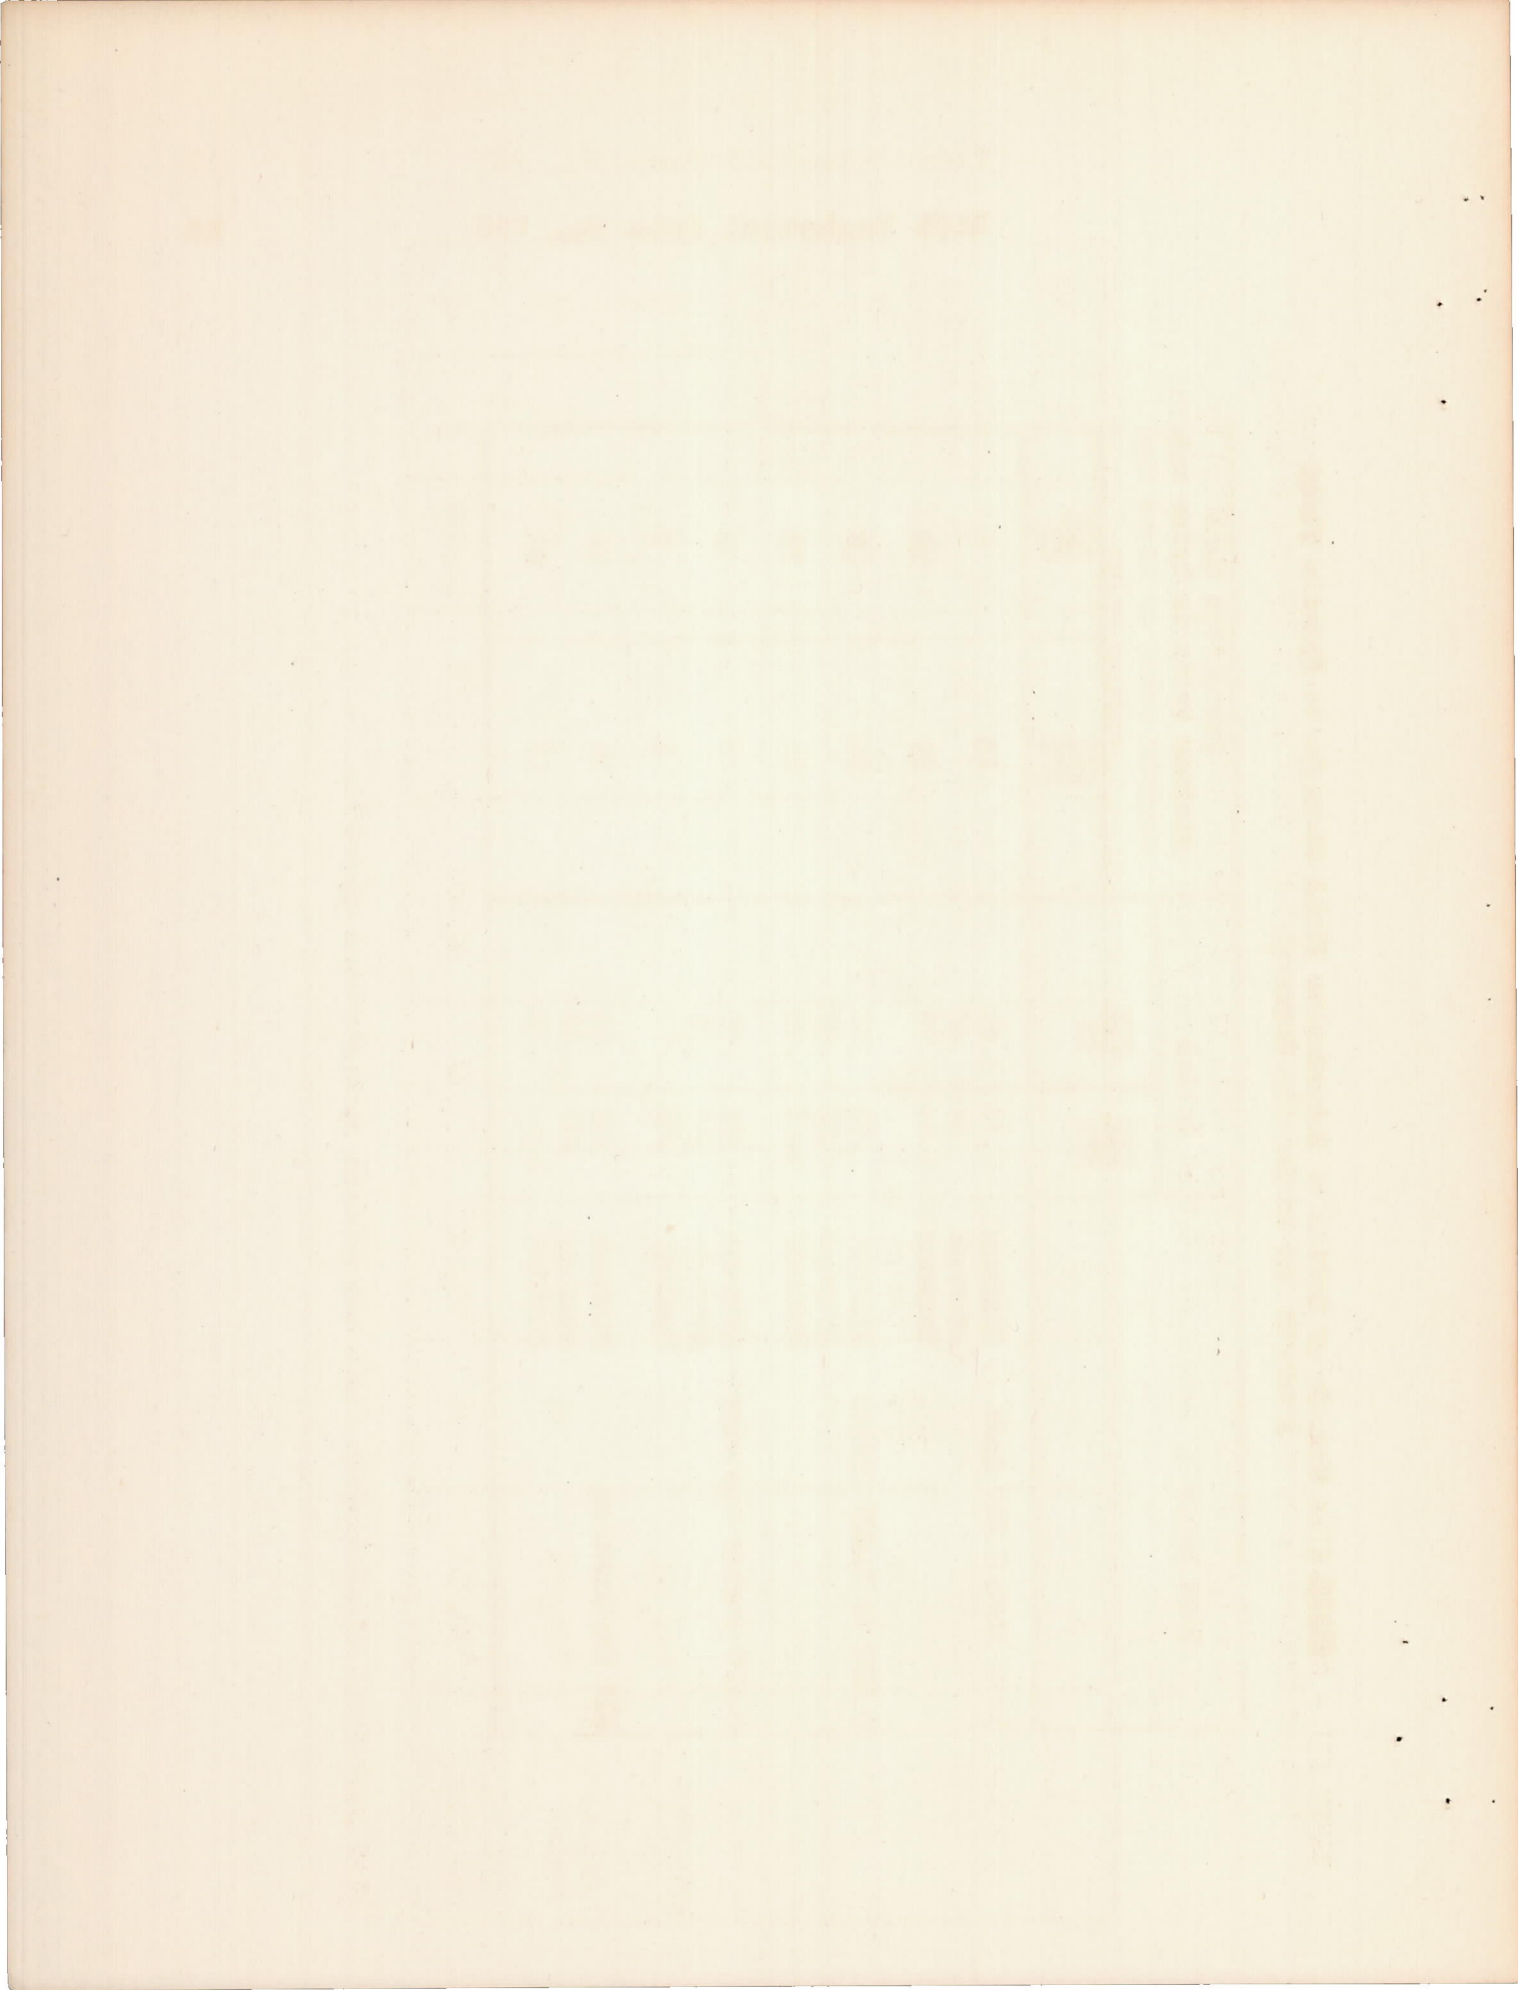
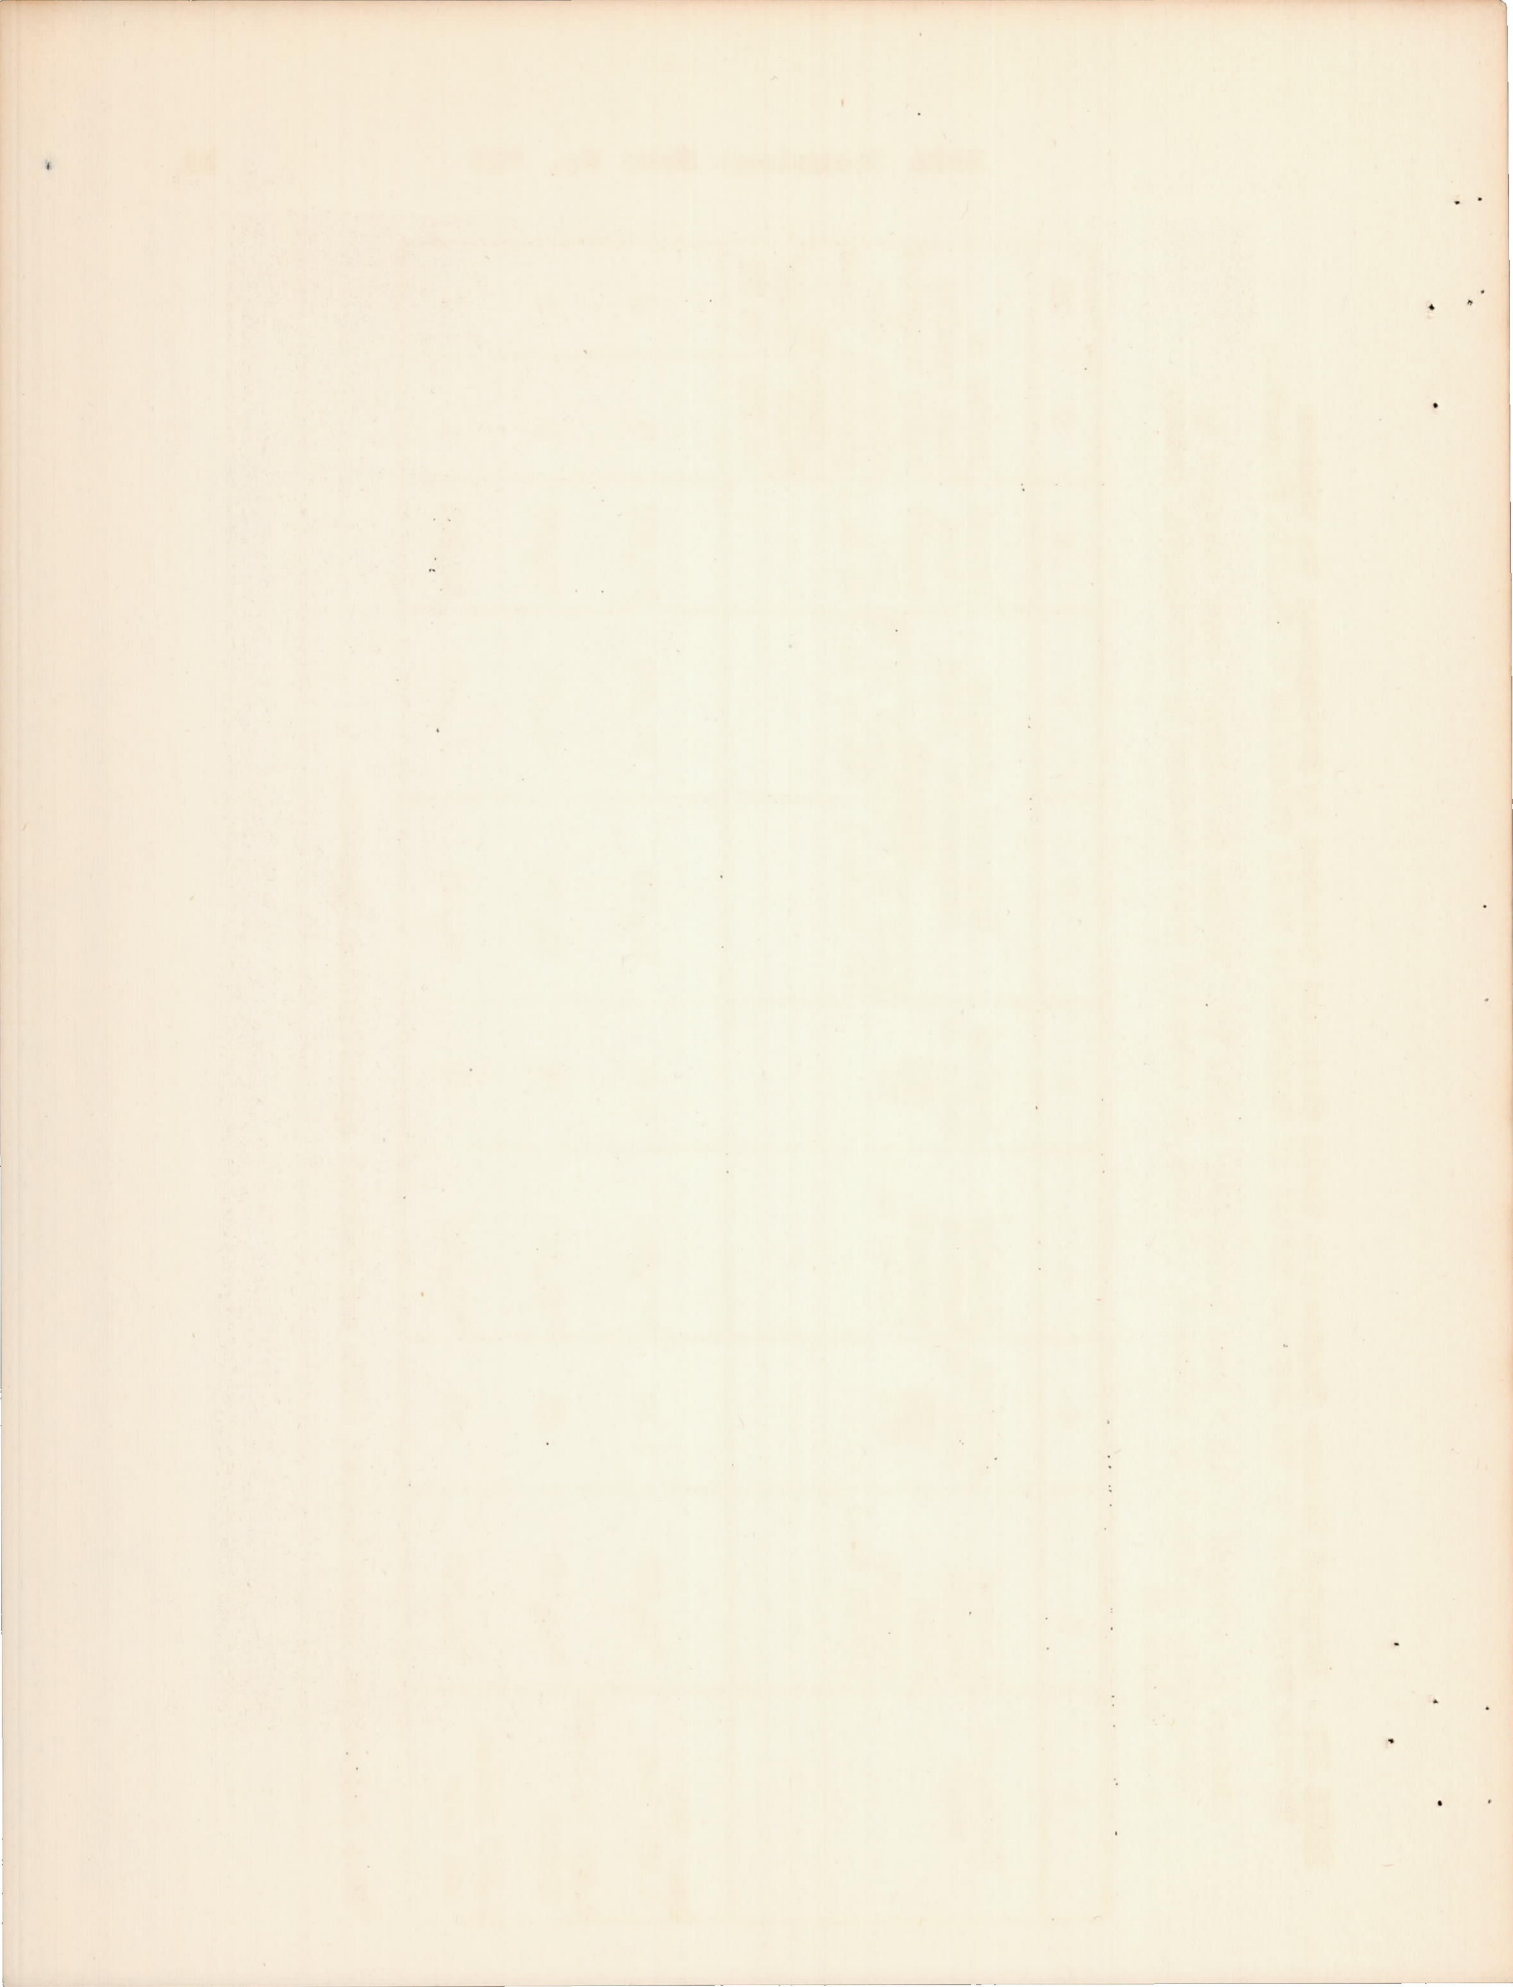


TABLE III.- Computed Minimum Compressive Yield Strengths Obtained by Multiplying the Minimum Tensile Properties by the Average Ratios of Compressive Yield Strengths to Tensile Properties

(Values in columns 3 and 5 were taken from table II. Values in column 6 were obtained by multiplying column 2 by column 3. Values in column 7 were obtained by multiplying column 4 by column 5)

1	2	3	4	5	6	7	8	9	10
Thickness range	Minimum tensile yield strength (lb/sq in.)	Average ratio of <u>CYS</u> <u>TYS</u>	Minimum tensile strength (lb/sq in.)	Average ratio of <u>CYS</u> <u>TS</u>	Computed minimum compressive yield strength		Lowest test result (lb/sq in.)	Number of test results below computed minimum compressive yield strength	
					Based on TYS (lb/sq in.)	Based on TS (lb/sq in.)			
								Based on TYS	Based on TS
Less than 0.250 inch	^a 42,000	0.88	^a 57,000	0.66	37,000	37,600	37,600	0	0
0.250 to 1.499 inches	^a 44,000	.91	^a 60,000	.69	40,000	41,400	37,500	2	3
1.500 inches and over	^a 52,000	.96	^a 70,000	.72	49,900	50,400	54,900	0	0

^aNavy Department specification 46A9c and Federal specification QQ-A-354.



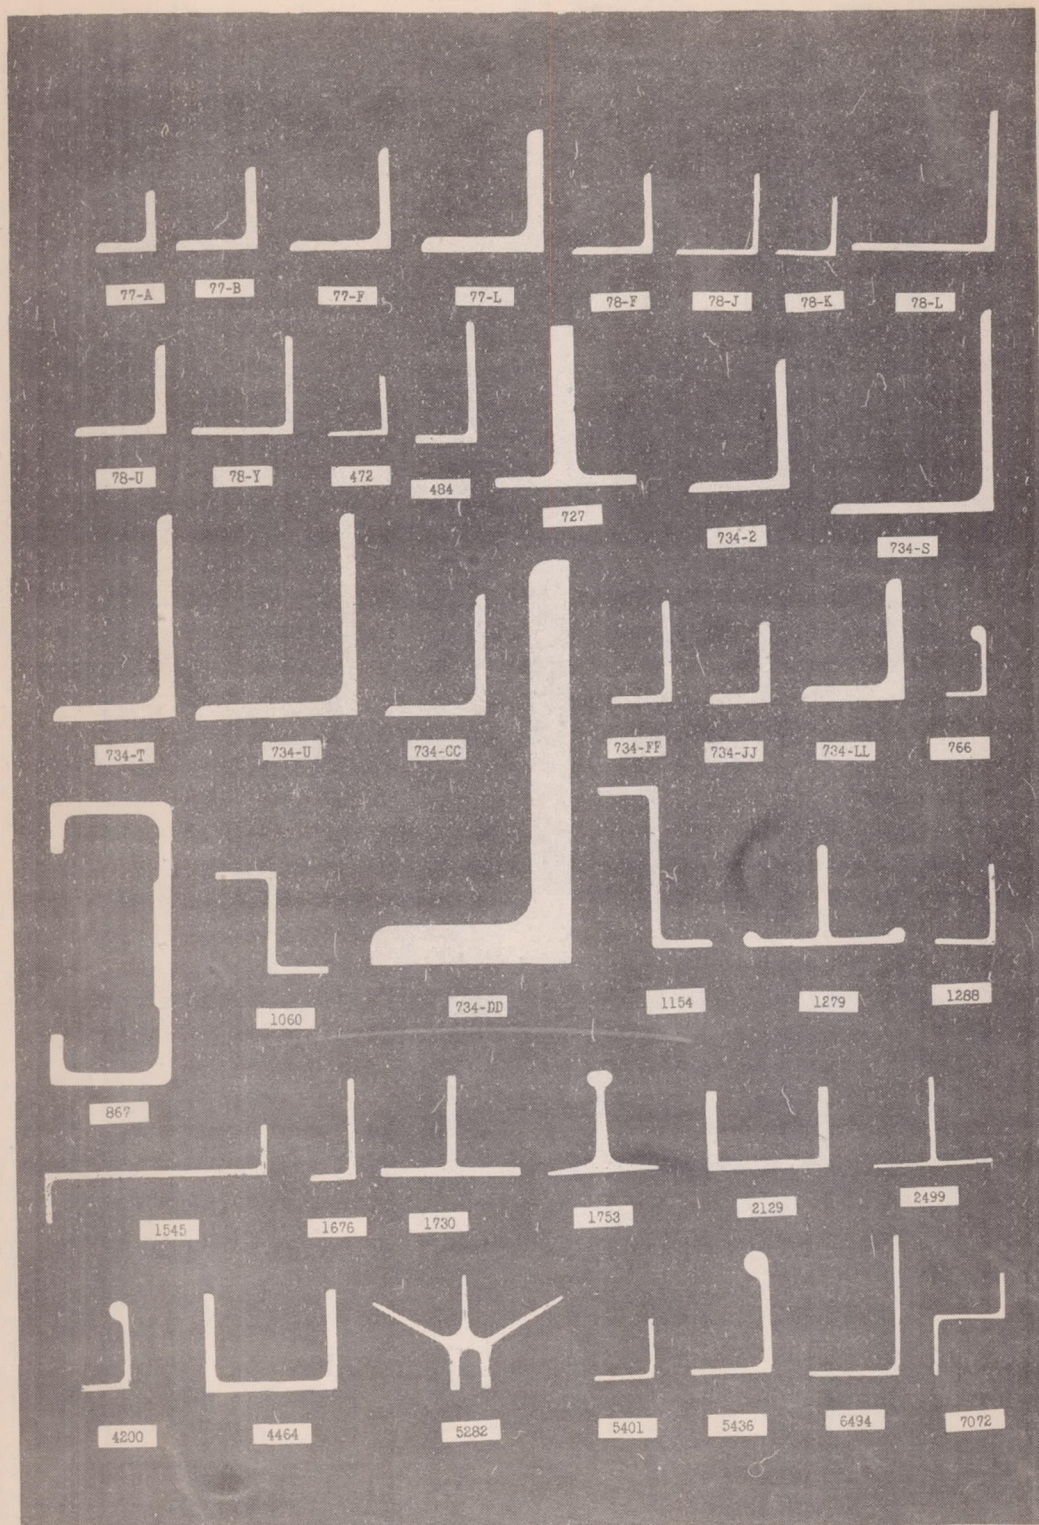
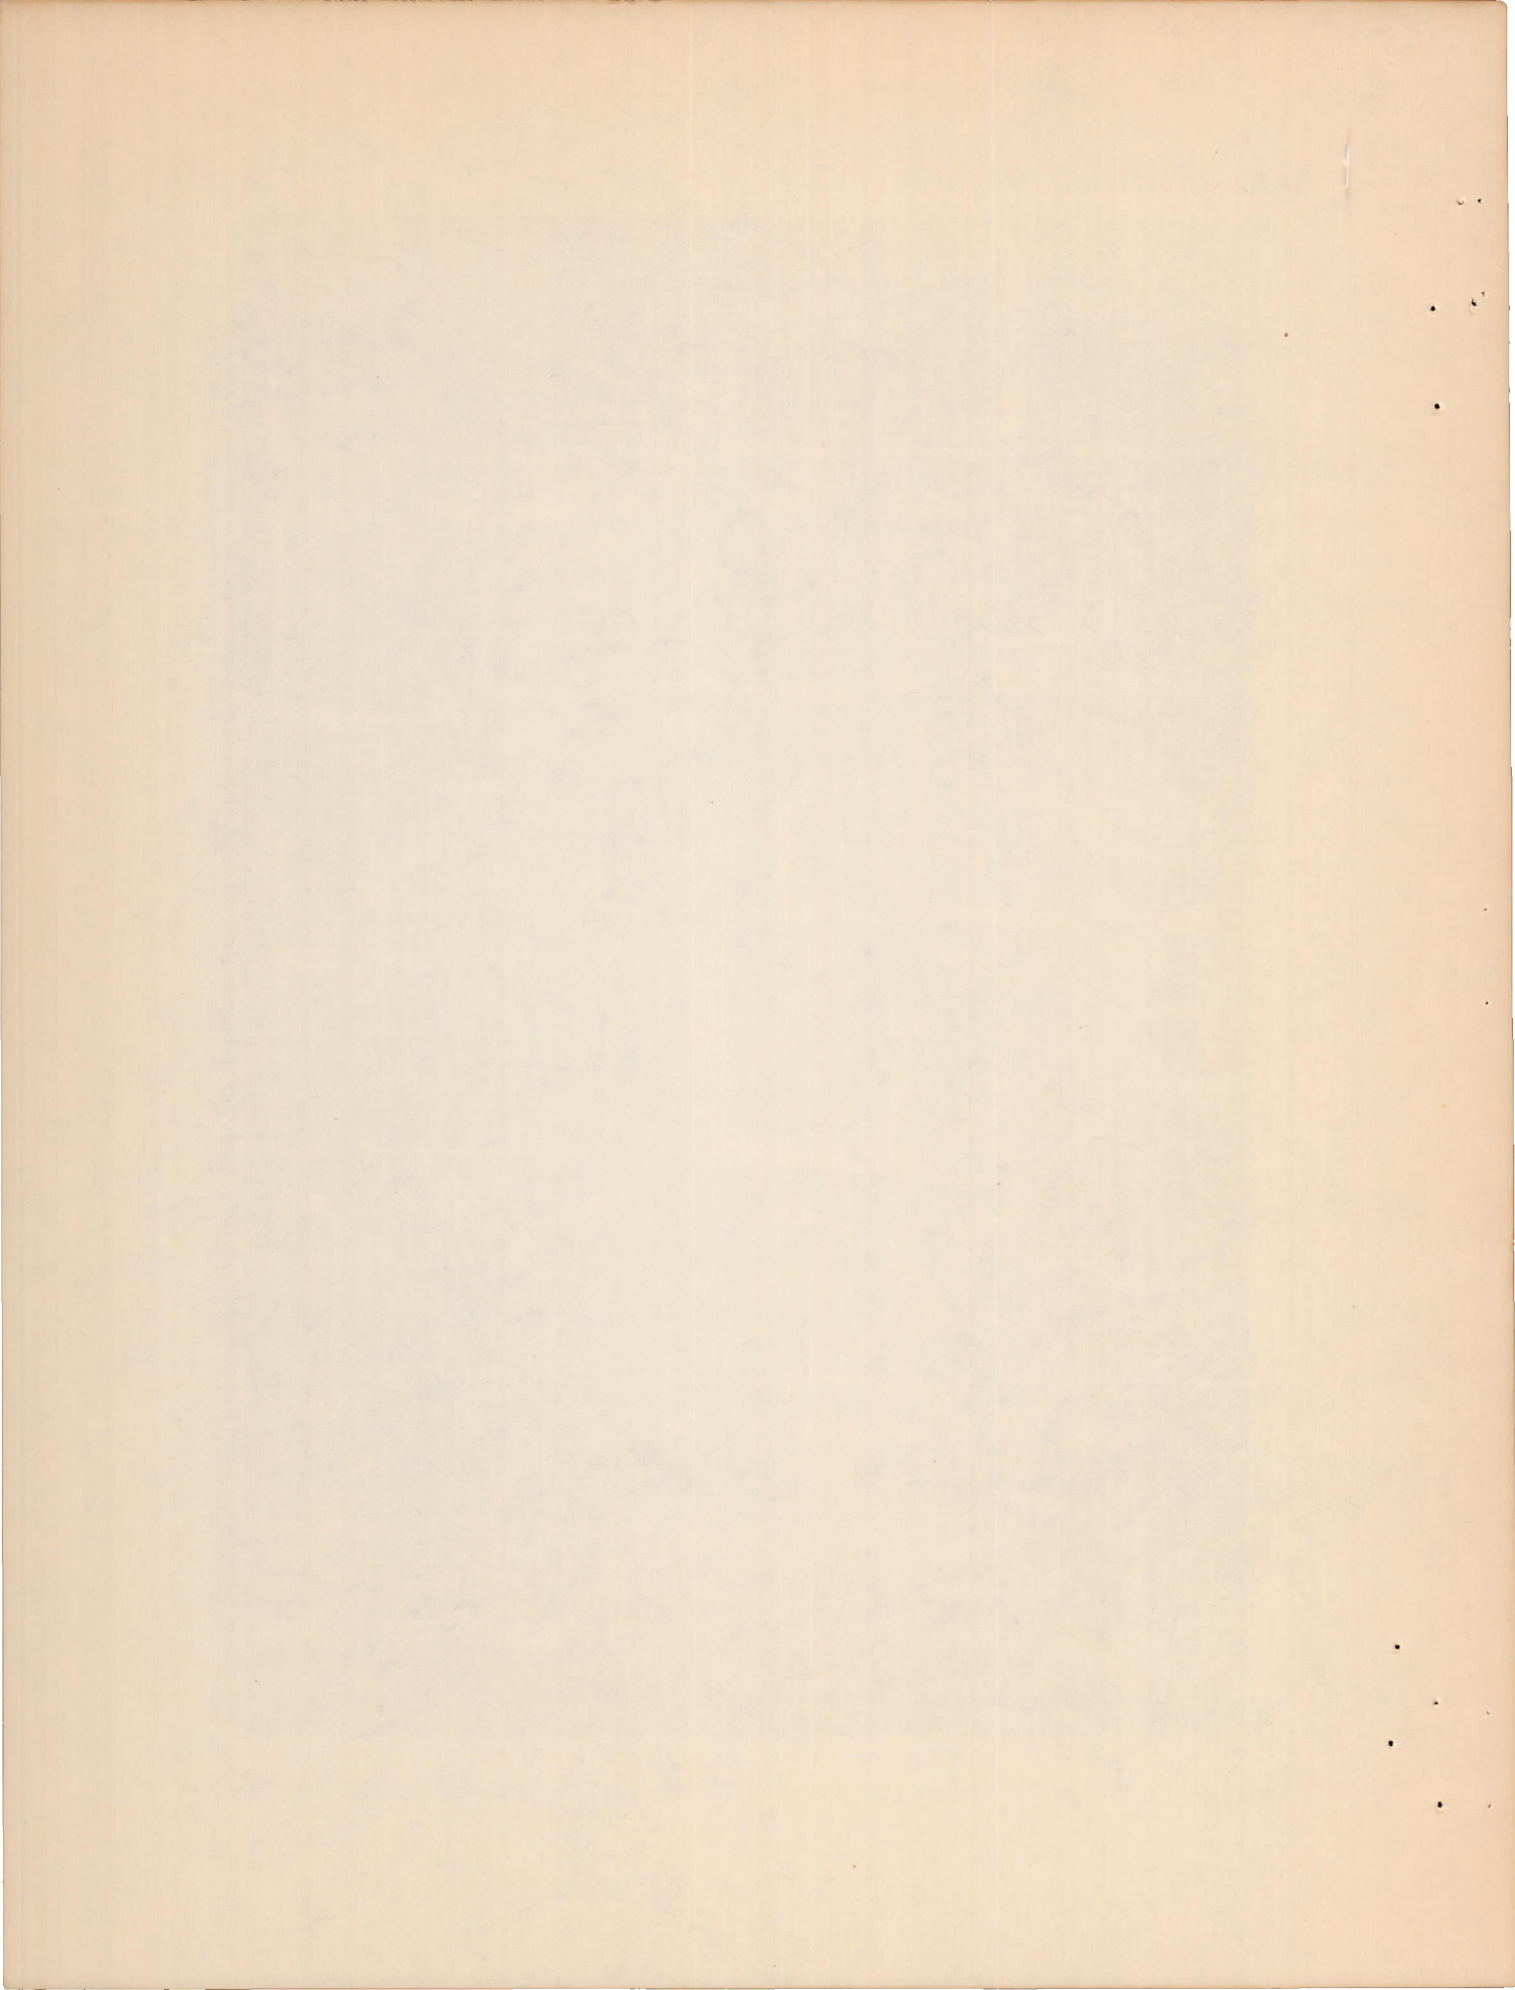


Figure 1a.-Cross sections of 24S-T Extruded Shapes Tested -
Die Nos. 77-A to 7072

(About 1/2 actual size)



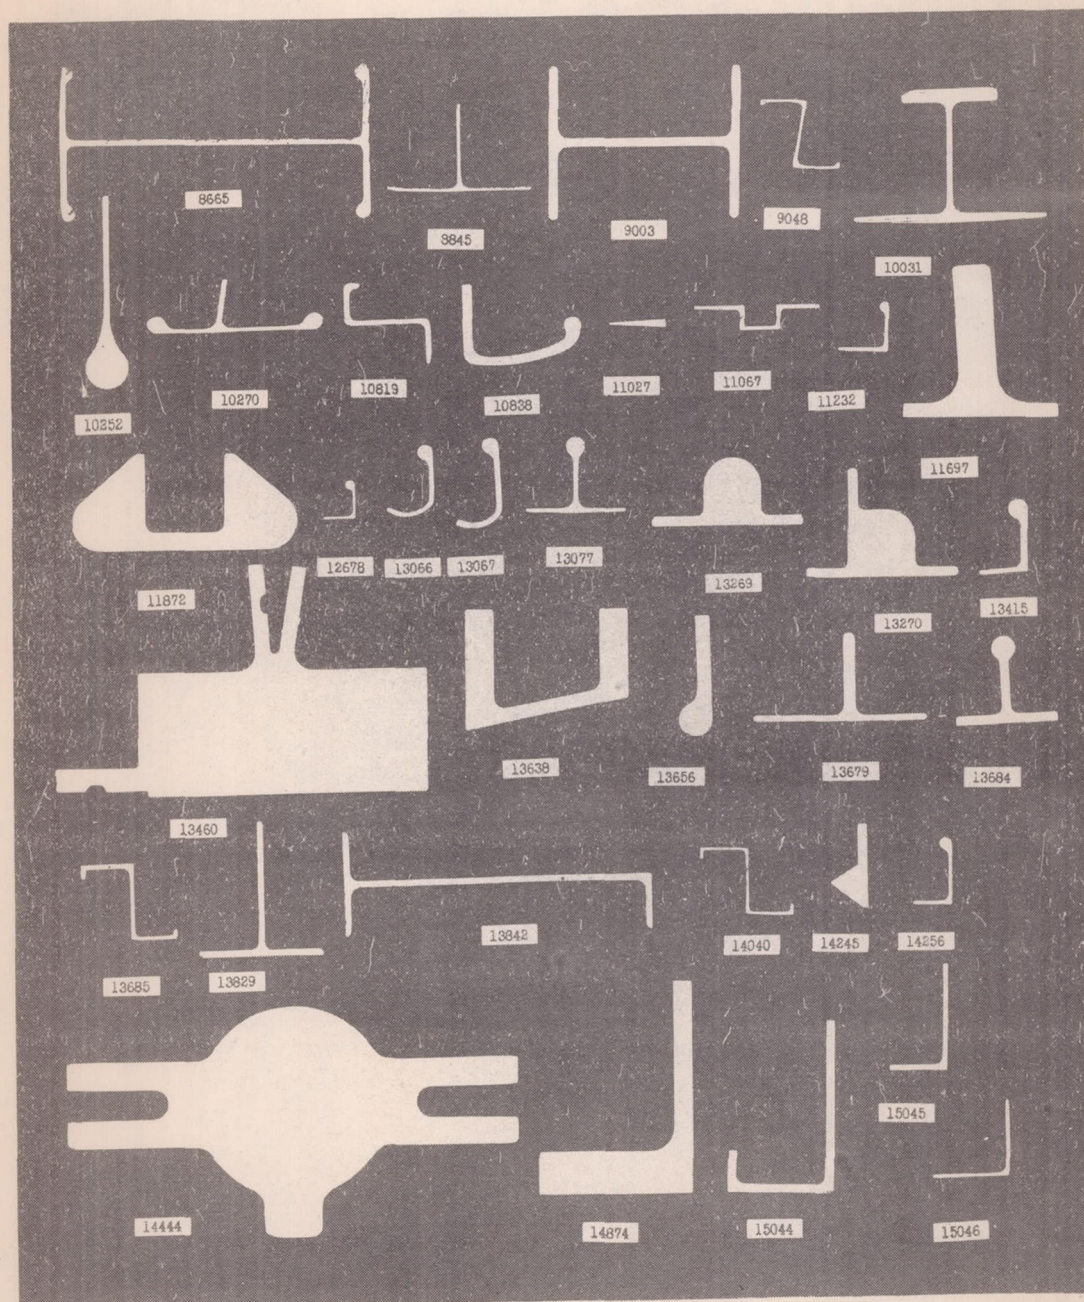
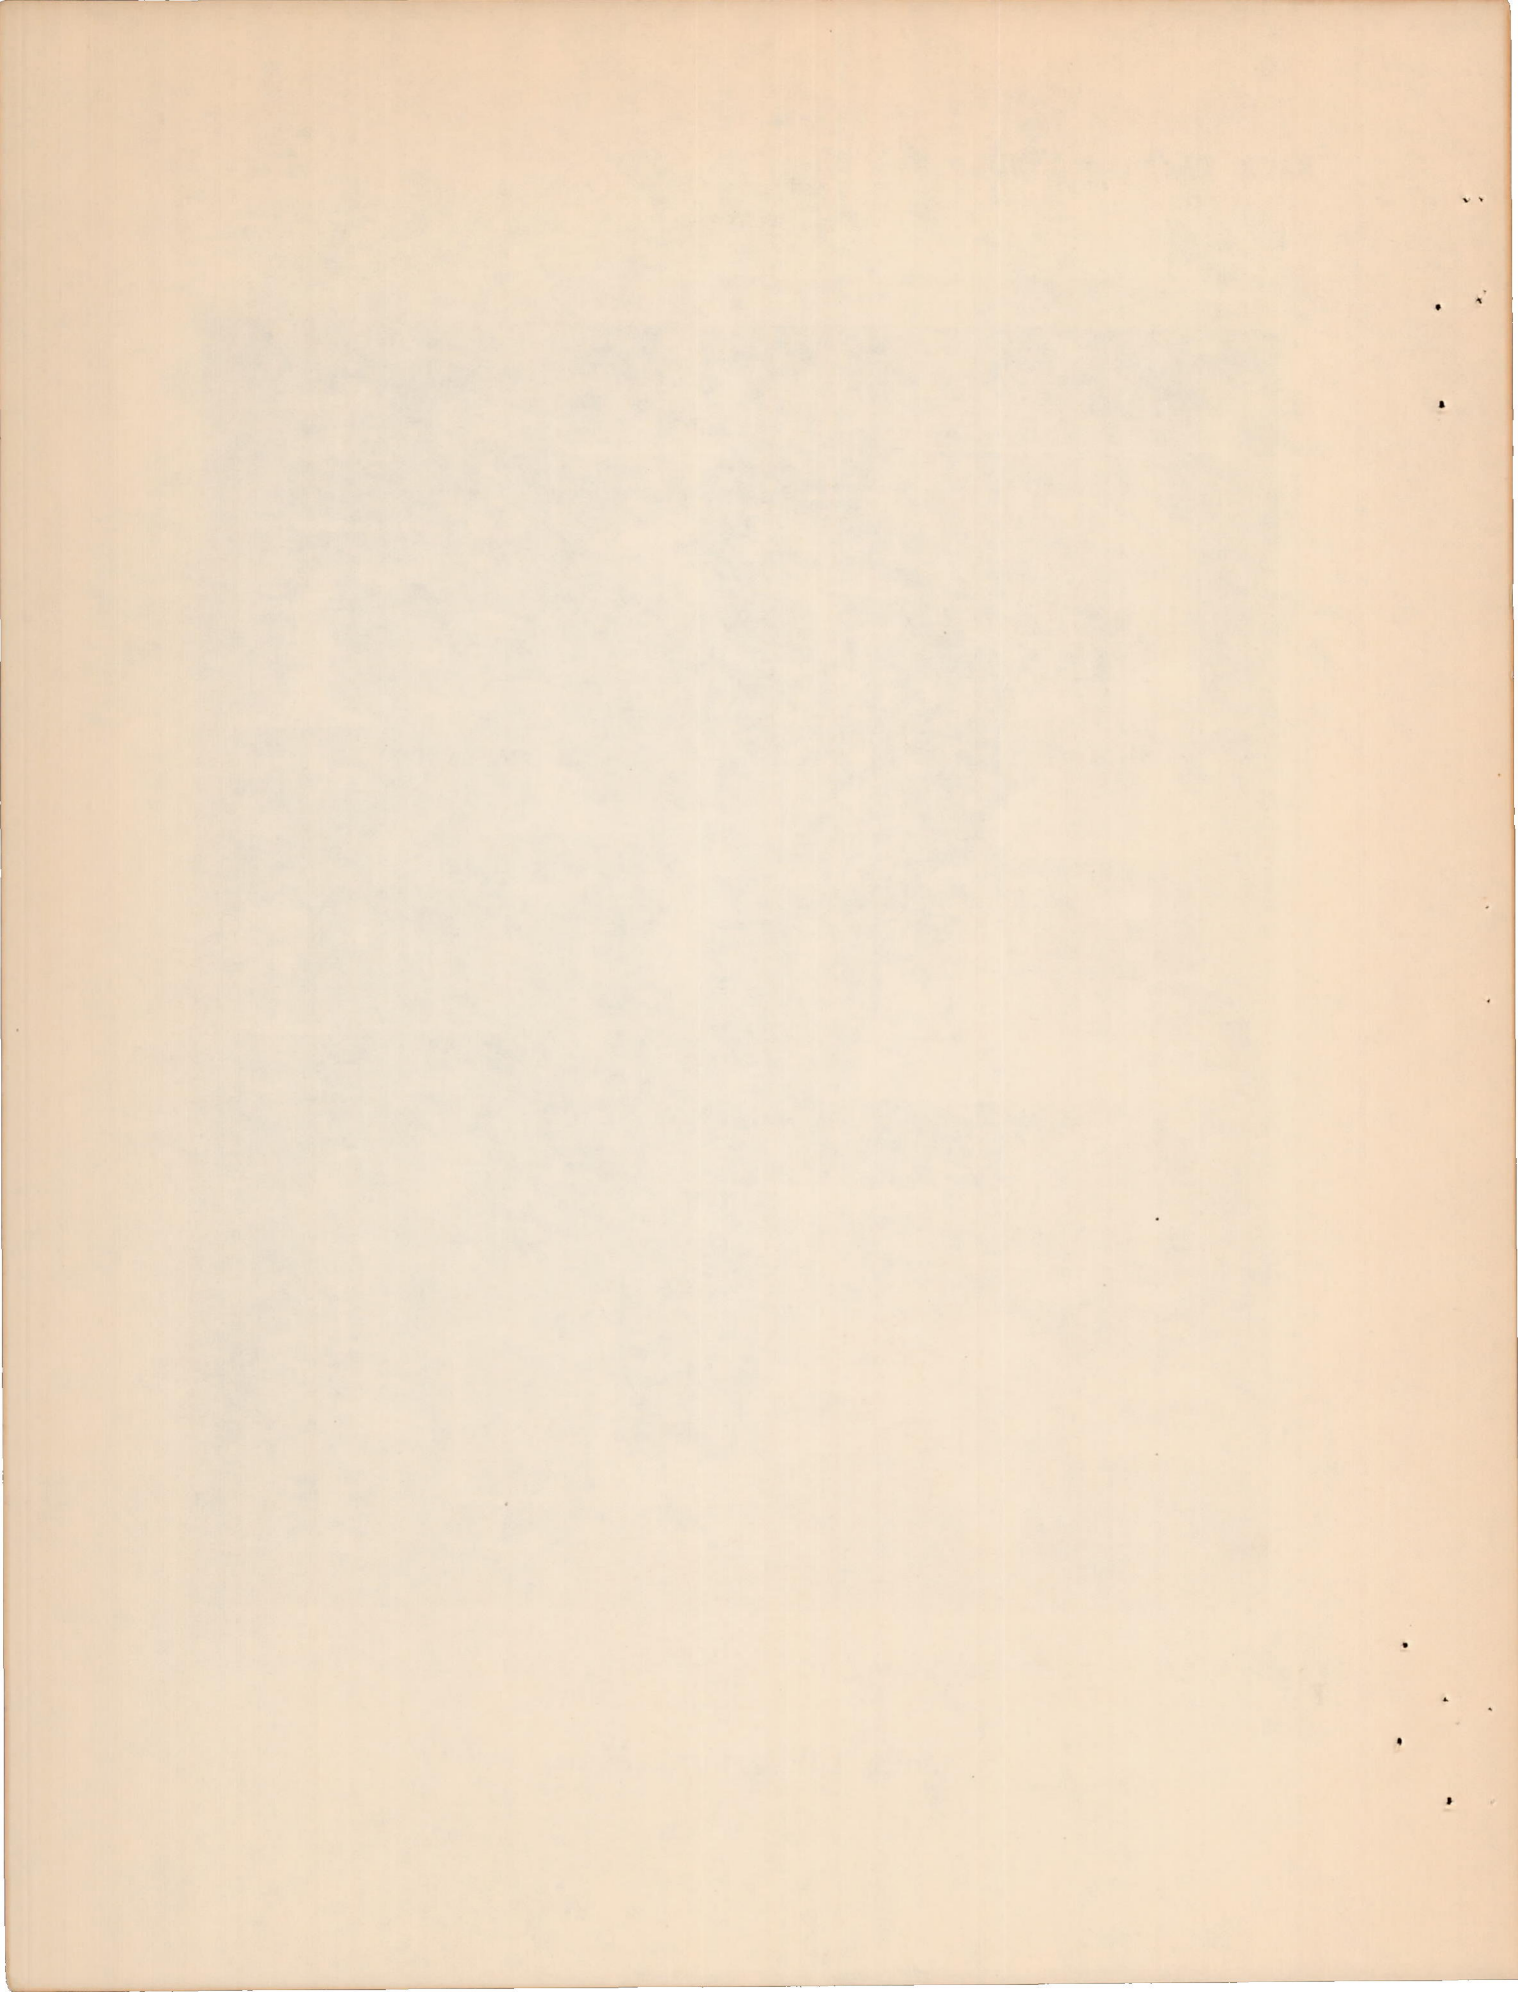


Figure 1b.-Cross sections of 24S-T Extruded Shapes Tested -
Die Nos. 8665 to 15046

(About 1/2 actual size)



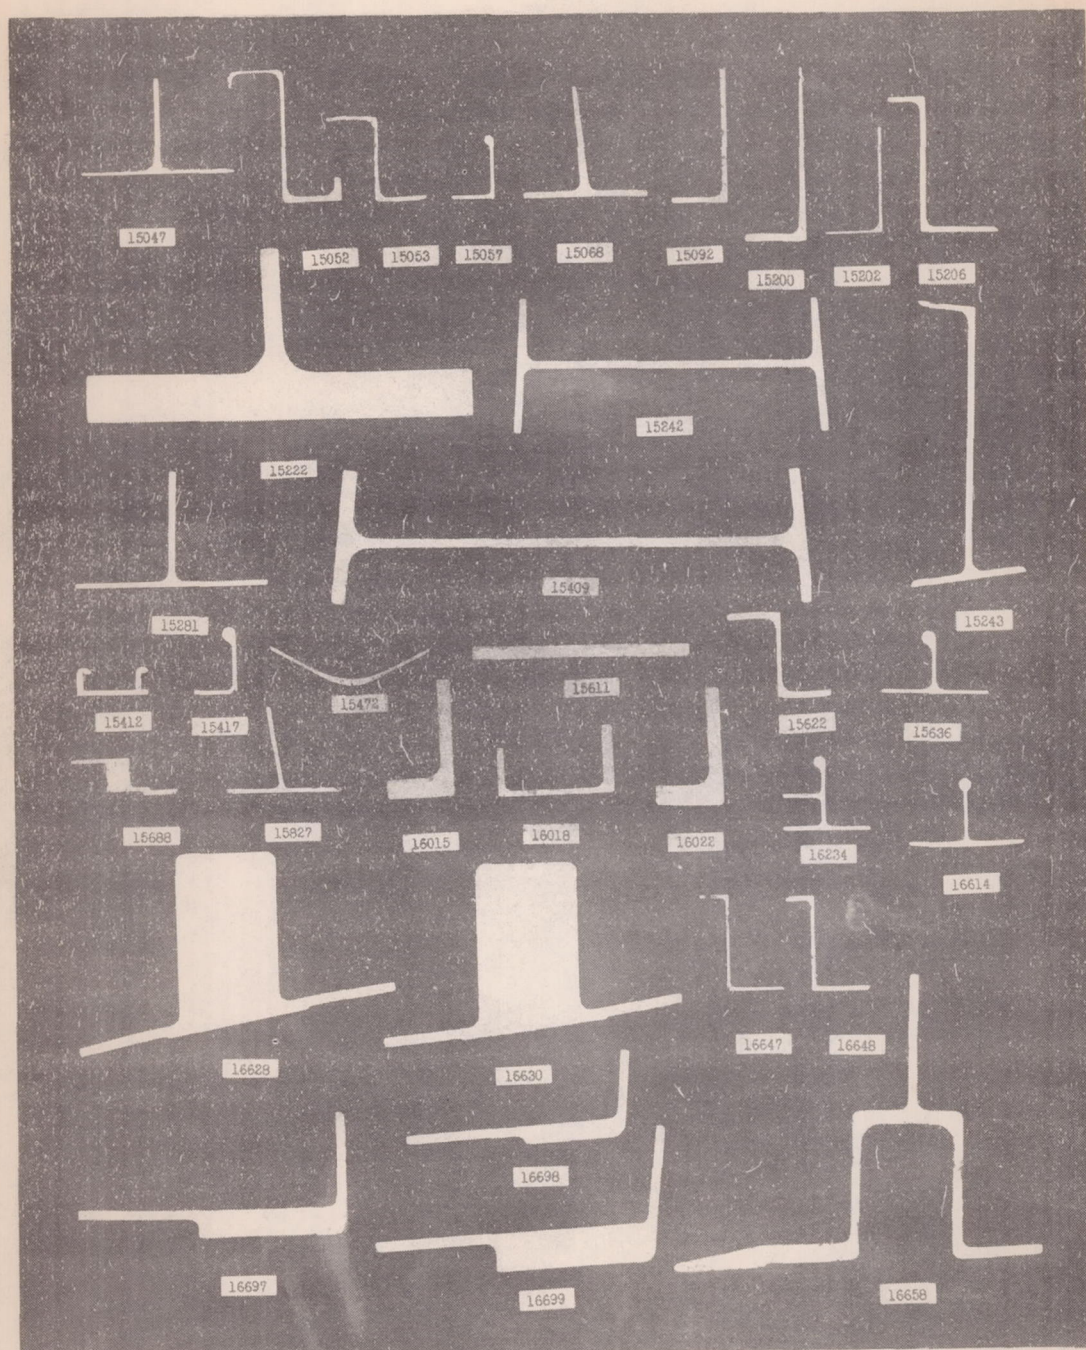
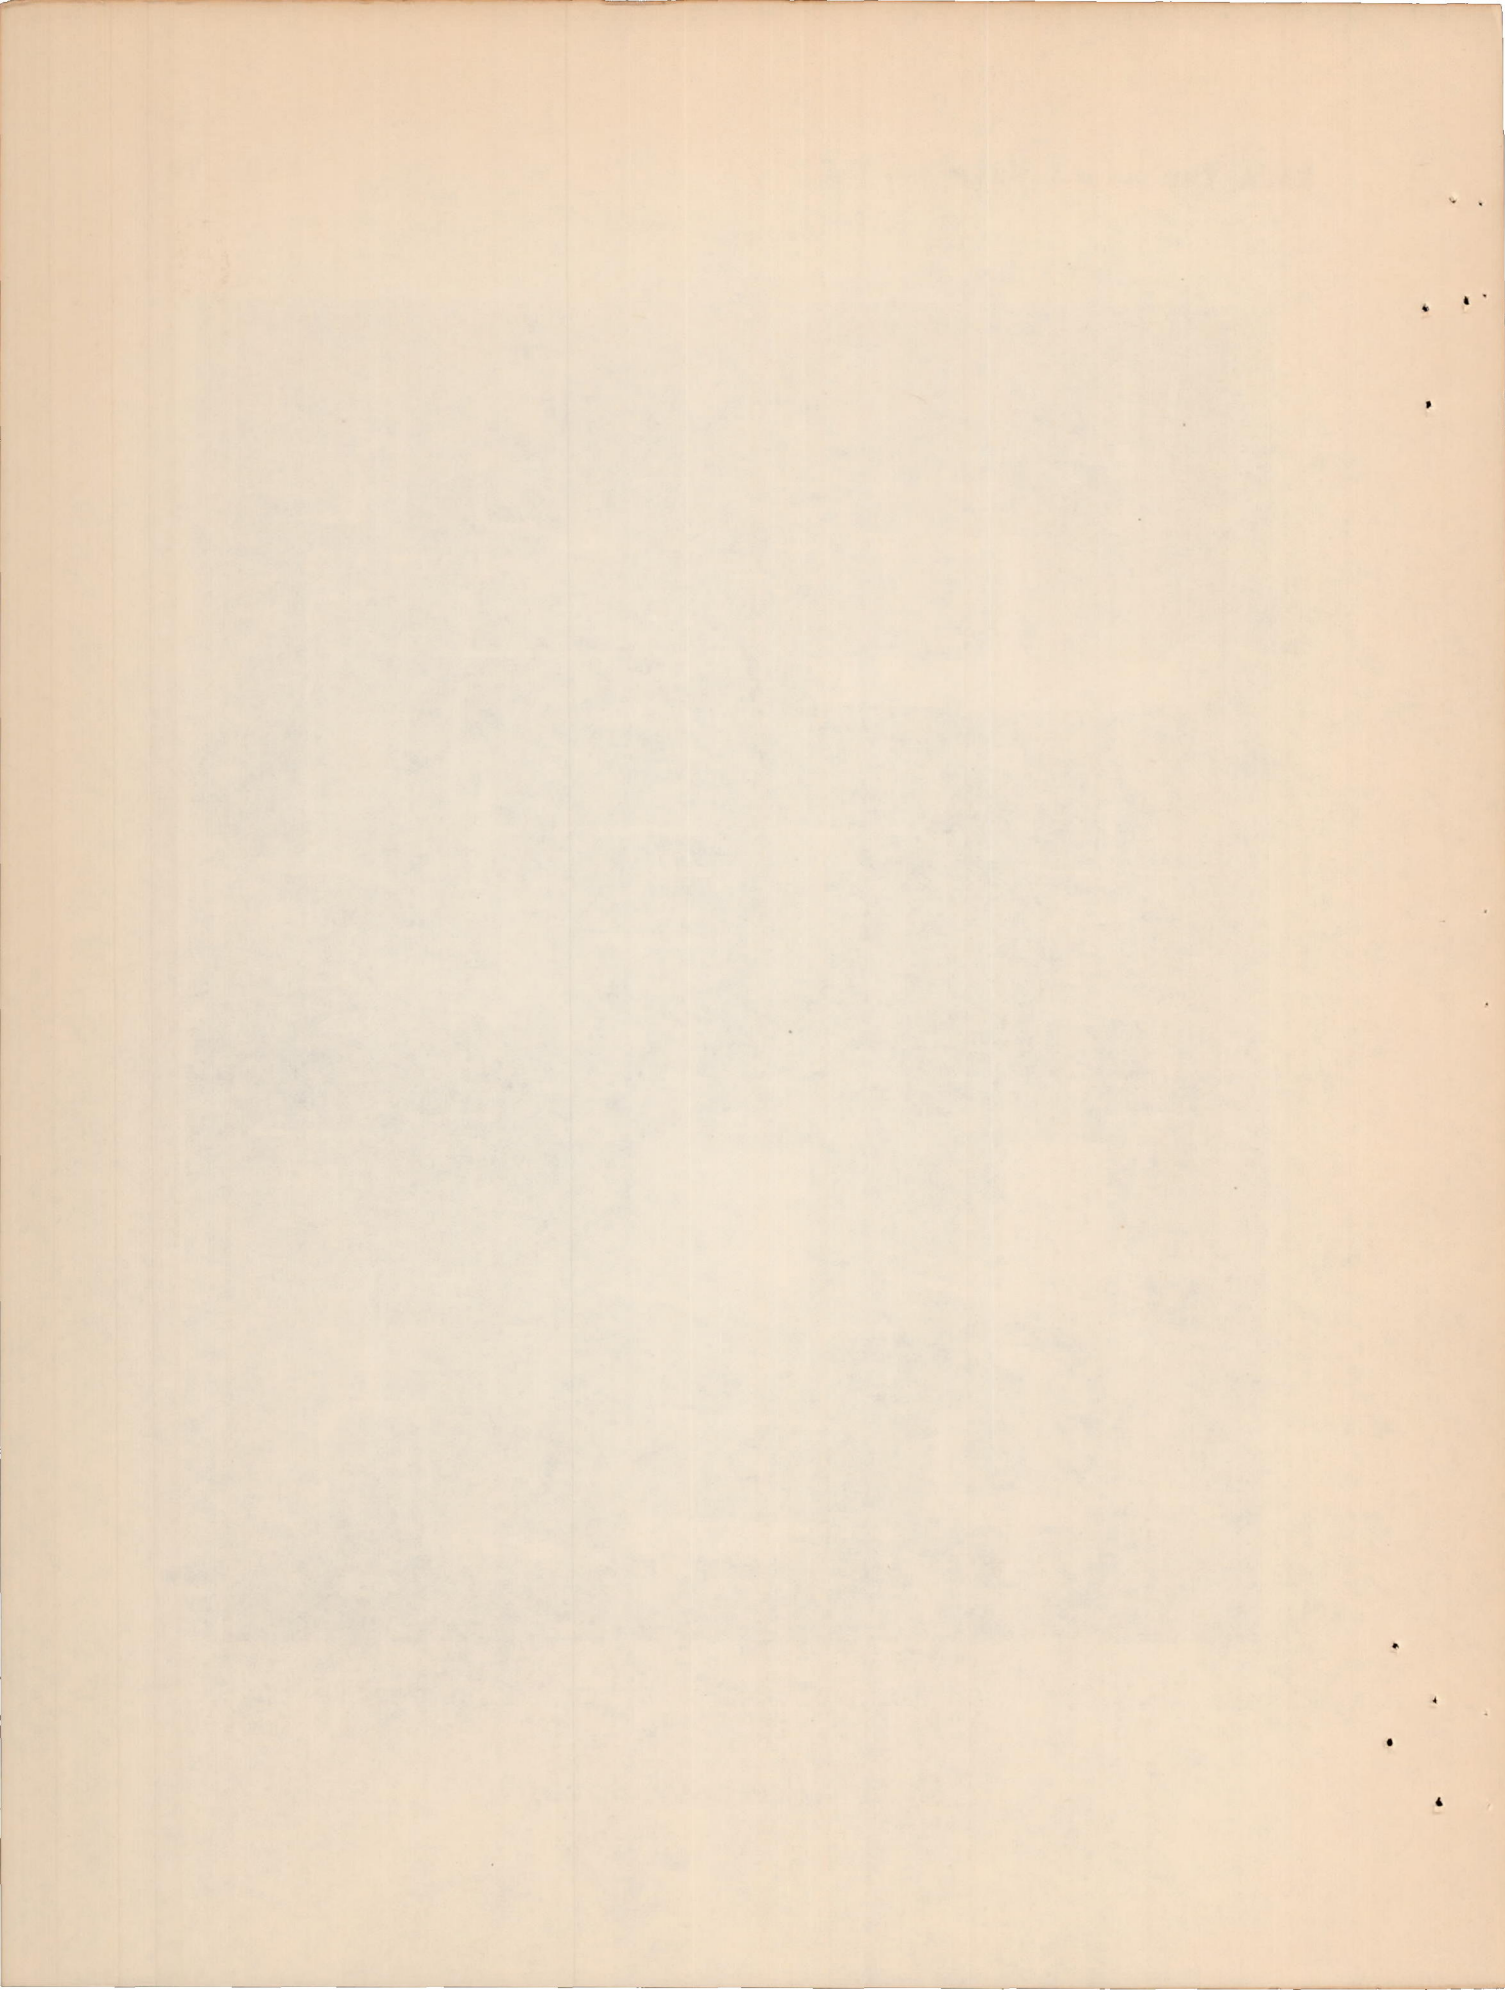


Figure 1c. Cross sections of 24S-T Extruded Shapes Tested -
Die Nos. 15047 to 16658

(About 1/2 actual size)



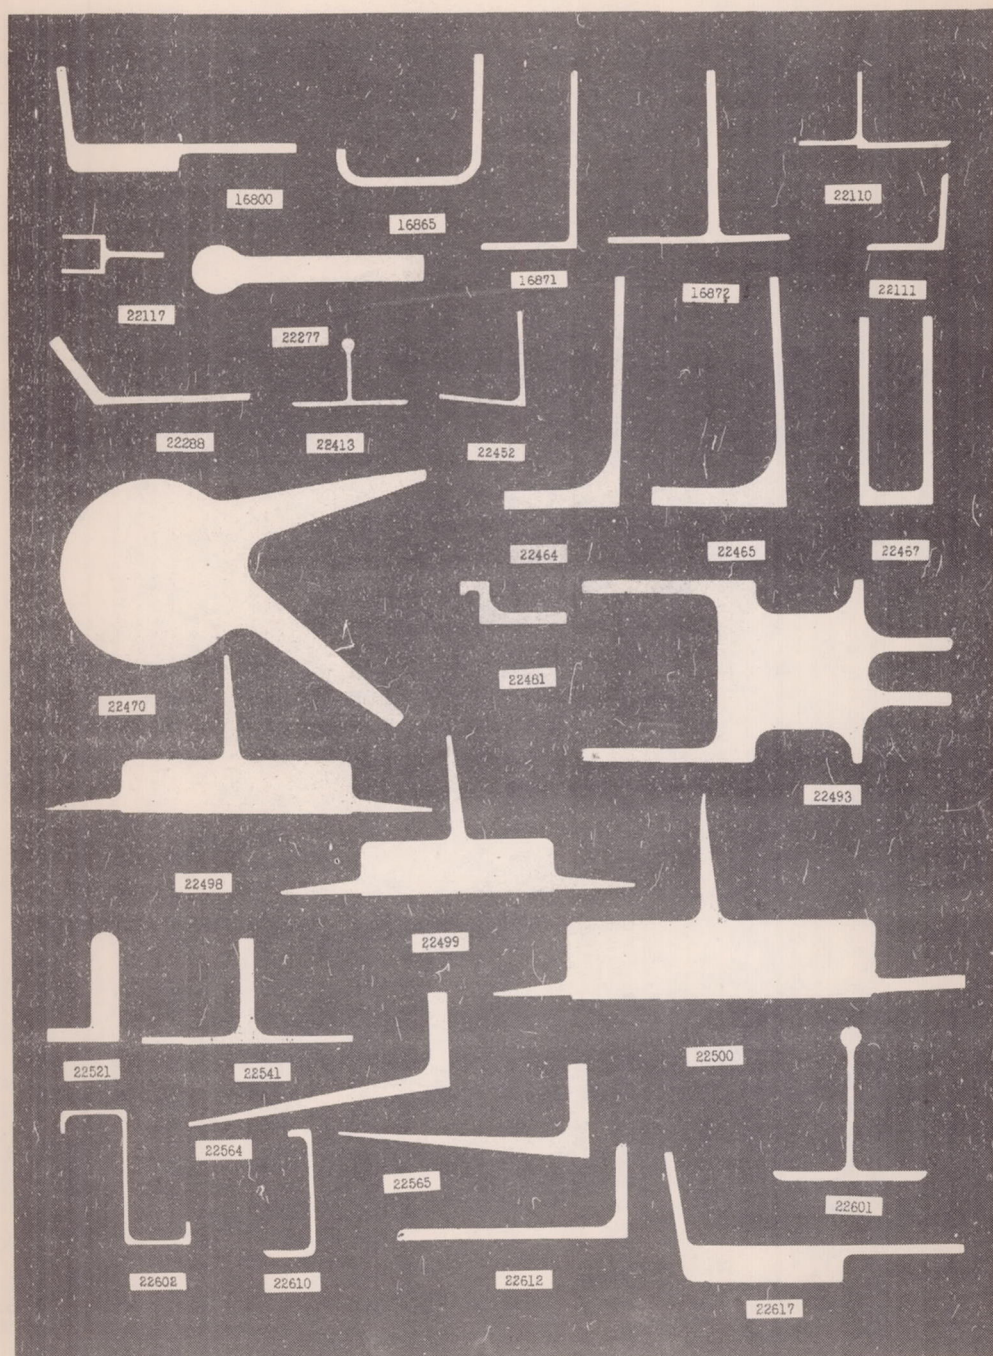
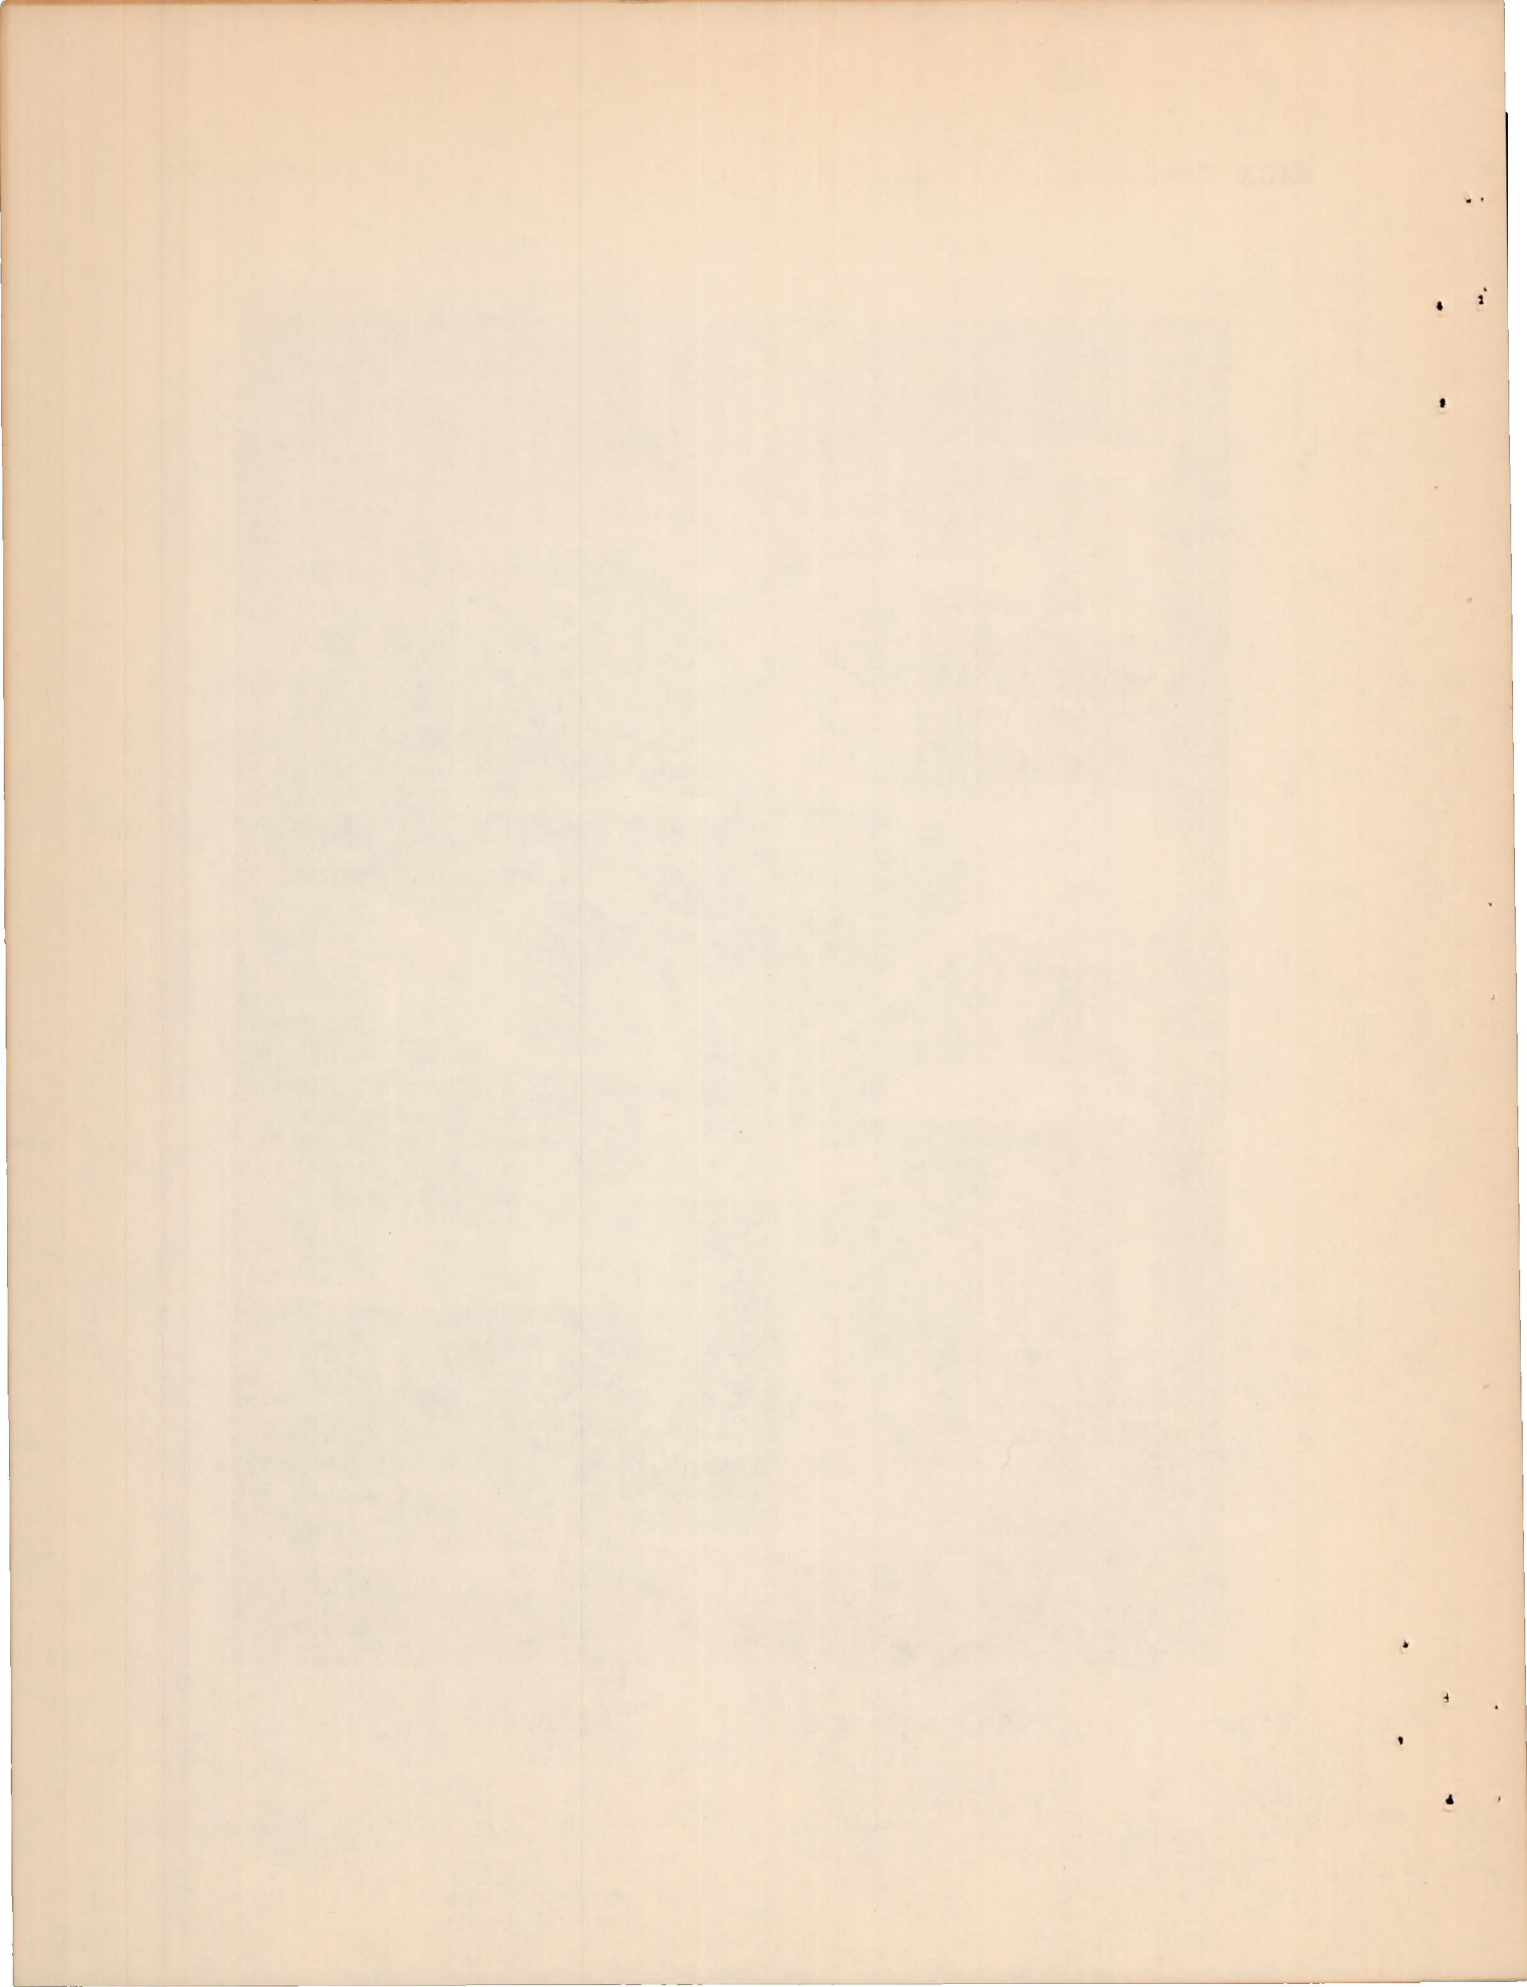


Figure 1d.- Cross sections of 24S-T Extruded Shapes Tested -
Die Nos. 16800 to 22617

(About 1/2 actual size)



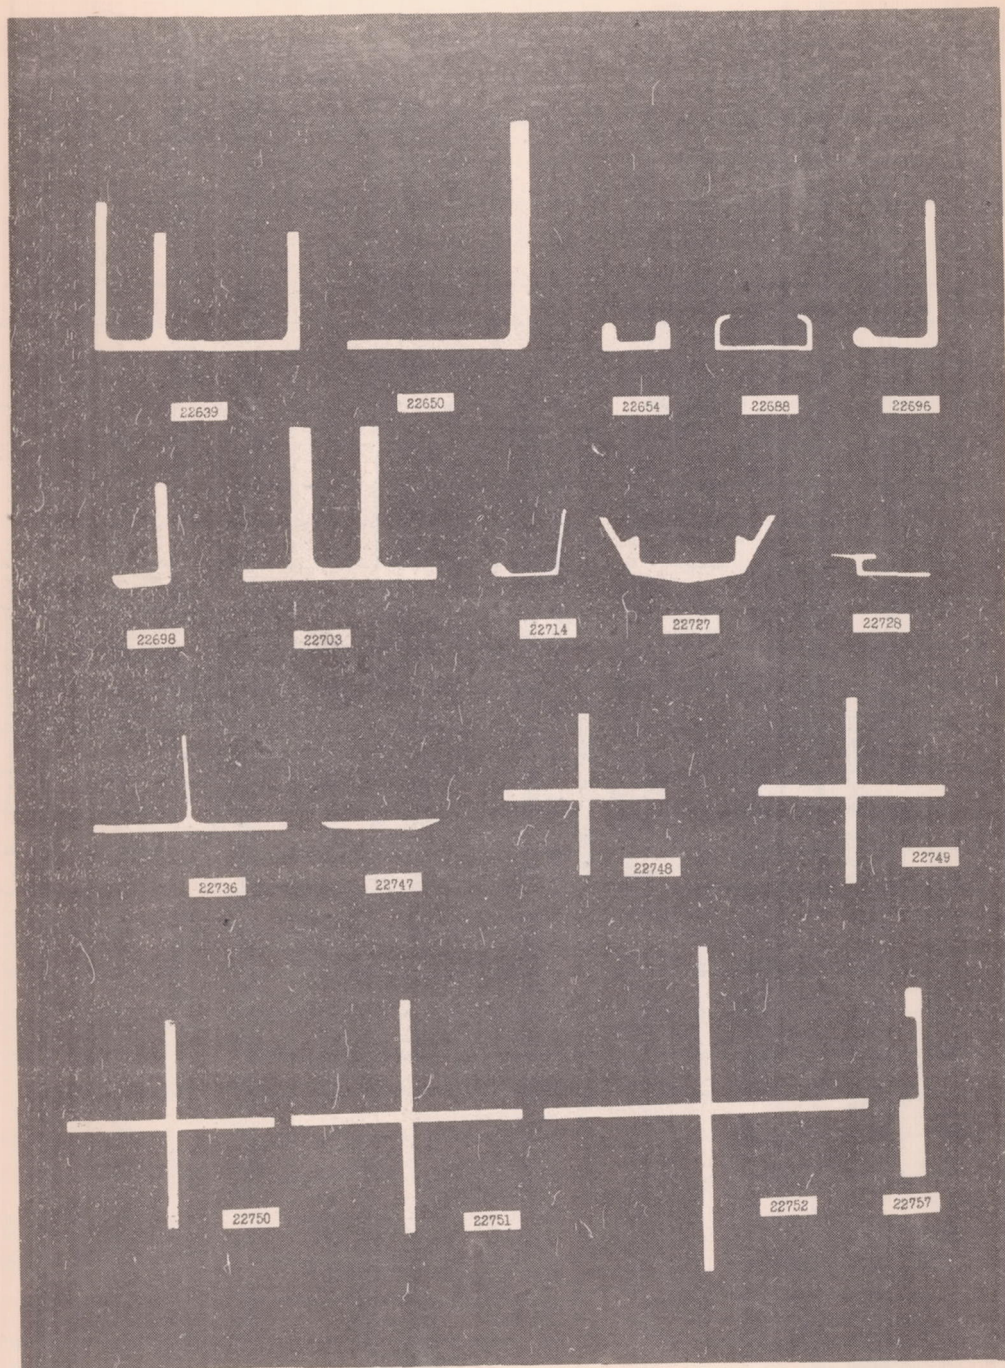


Figure 1e.-Cross sections of 24S-T Extruded Shapes Tested -
Die Nos. 22639 to 22757

(About 1/2 actual size)

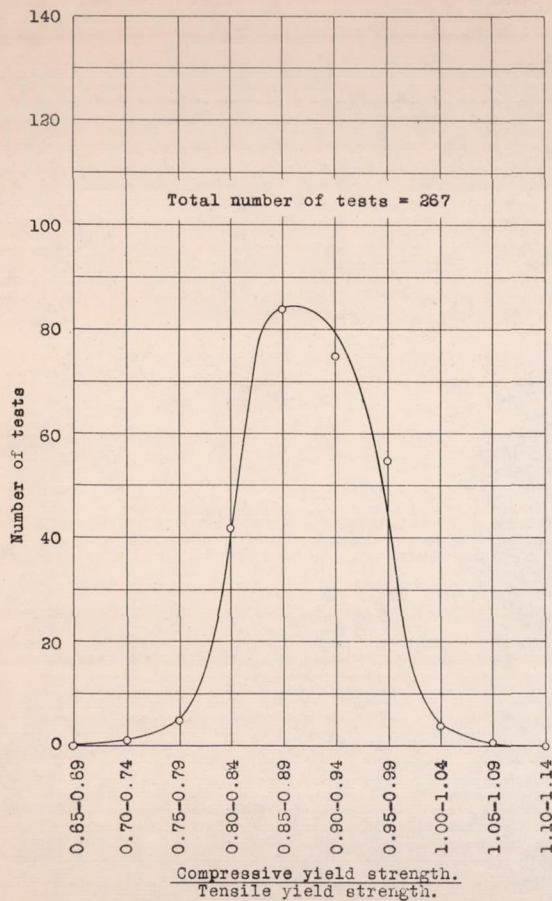


Figure 5.- Frequency curves showing the ratio of compressive yield strength to tensile yield strength for the 267 extruded shapes of 248T aluminum alloy tested.

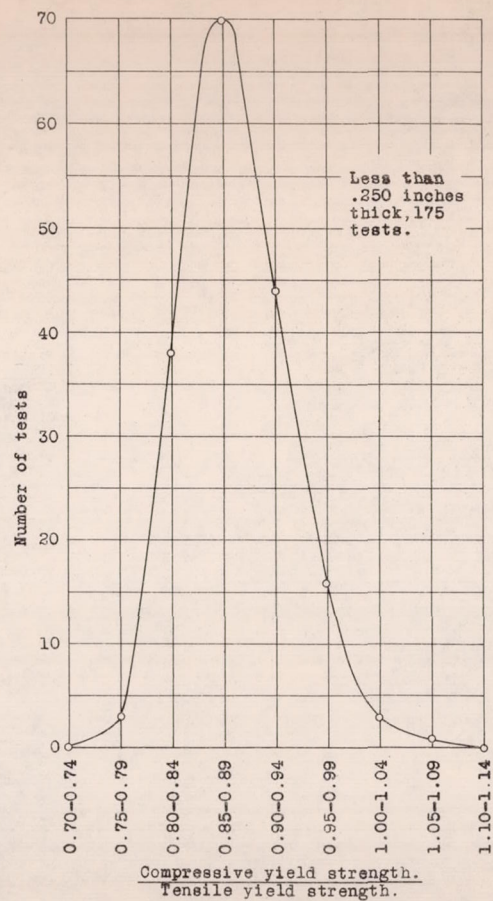


Figure 6.- Frequency curves showing the ratio of compressive yield strength to tensile yield strength for the 175 extruded shapes less than 0.250 inches thick.

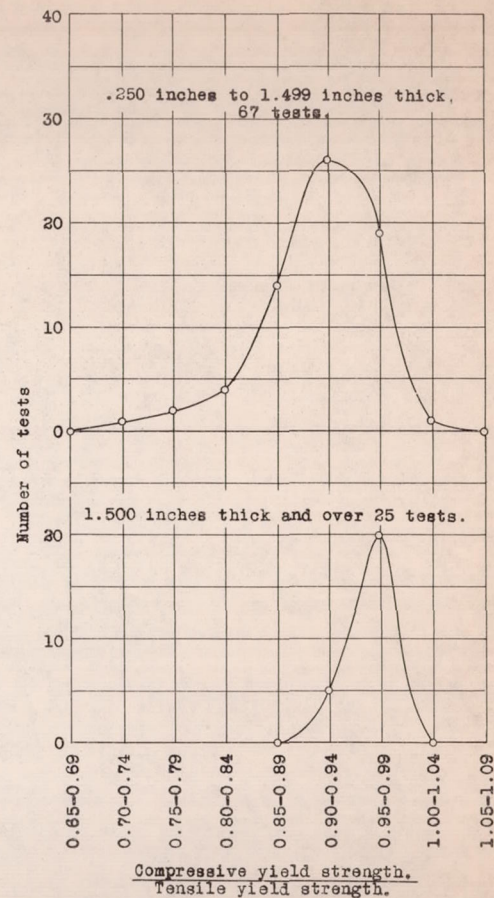


Figure 7.- Frequency curves showing the ratio of compressive yield strength to tensile yield strength for the 67 extruded shapes between 0.250 inches and 1.499 inches thick and the 25 extruded shapes 1.500 inches thick and over.

