

1995-117480

N95-23900

**SURFACE CHARACTERIZATION OF LDEF
CARBON FIBER/POLYMER MATRIX COMPOSITES**

Holly L. Grammer and James P. Wightman
Virginia Polytechnic Institute and State University
Department of Chemistry
Blacksburg, VA 24061
Phone: 703/231-5854, Fax: 703/231-3971

54-24
~~117480~~³
10f

Philip R. Young and Wayne S. Slemp
NASA Langley Research Center
Mail Stop 226
Hampton, VA 23665-5225
Phone: 804/864-4265, Fax: 804/864-8312

SUMMARY

XPS (x-ray photoelectron spectroscopy) and SEM (scanning electron microscopy) analysis of both carbon fiber/epoxy matrix and carbon fiber/polysulfone matrix composites revealed significant changes in the surface composition as a result of exposure to low-Earth orbit. The carbon 1s curve fit XPS analysis in conjunction with the SEM photomicrographs revealed significant erosion of the polymer matrix resins by atomic oxygen to expose the carbon fibers of the composite samples. This erosion effect on the composites was seen after 10 months in orbit and was even more obvious after 69 months.

INTRODUCTION

One of the tasks of the MSIG (Materials Special Investigation Group) is the detailed analysis of LDEF composites. Stein presented a summary of the findings of the LDEF materials studies on polymer-matrix composites and noted that atomic oxygen causes surface degradation of uncoated composites but that thin inorganic coatings prevent atomic oxygen erosion [1]. George and Hill [2] using SEM reported a similar highly eroded topography for both epoxy matrix and polysulfone matrix/carbon fiber composites due to reaction with atomic oxygen. A lack of resin on the exposed (leading edge) surfaces was determined by infrared spectroscopy. Sulfur present in the curing agent of the epoxy resin and sulfur in the polysulfone backbone was presumed to react with atomic oxygen to produce sulfate species on the exposed surfaces of both composites.

Measured decreases in the thickness of epoxy and polysulfone matrix/carbon fiber composites on the leading edge have been reported by Slemp et al. [3] in the range of 75 - 115 mm. Whitaker et al. [4] noted that the measured thickness decrease for the polysulfone matrix (110 mm) was about 50% greater than for the epoxy matrix (70 mm). It was also noted that erosion due to atomic oxygen was much greater for the matrix resin than for the carbon fibers. A detailed XPS study of poly(arylacetylene) matrix/carbon fiber composites on the leading edge has been reported by Mallon et al. [5]. The presence of inorganic silicon at 103.5 eV was noted on the exposed surface.

The objective of the present work was to document changes in the surface chemistry of composite samples taken from LDEF. Surface characterization results obtained using x-ray photoelectron spectroscopy (XPS) and scanning electron microscopy (SEM) are reported. These results

600

are a part of a larger study [6] where surface characterization techniques were used to examine polymer films and aluminum tray clamps taken from LDEF.

EXPERIMENTAL

Materials

An epoxy matrix composite (934/T300) and a polysulfone matrix composite (P1700/C6000) were studied. The epoxy and polysulfone matrix resins were produced by Fiberite and Union Carbide, resp. The T300 and C6000 carbon fibers were produced by Union Carbide and Celanese, resp. A control and two flight samples exposed for 10 and 69 months of each composite were studied. The flight samples were located on Tray B, Row 9 of the LDEF. The flight samples were cut from larger panels processed at the NASA - Langley Research Center using prepreg manufacturer's specifications. Control samples were cut from the same panel as the flight specimens. The control samples remained at the NASA - Langley Research Center in a low humidity environment.

Procedures

Extreme care was used when preparing the composite samples for surface characterization. Lint free nylon white gloves from Fisher Scientific Company were used to prevent sample contamination. The gloves, prior to use, were washed in solvent grade hexane, also obtained from Fisher Scientific, to remove any silicon contamination. The gloves were then subsequently washed with soap and water and allowed to dry. Scotch Magic Tape[®] was used to secure samples for XPS and SEM analysis. Preparation of the composites for XPS and SEM analysis required cutting of the samples using an Exacto-knife. Typical sample dimensions were 13 mm x 13 mm.

Analysis Techniques

XPS (x-ray photoelectron spectroscopy) analysis was performed on a Perkin-Elmer PHI 5400 spectrometer with a magnesium Ka achromatic X-ray source (1253.6 eV) operated at 15 keV and 400 watts with an emission current of 30 mA. The spectrometer was calibrated to the 4f_{7/2} photopeak of gold. Atomic concentrations were determined using PHI software, version 3.0. Curve fitting was carried out by using PHI software, version 3.0. All photopeaks were fitted with Gaussian curves. The peak positions, indicative of the type of chemical functionality present, were assigned using known literature values [7]. The various peak positions were held at a constant value and were referenced to the C1s photopeak characteristic of adventitious carbon-containing organic species taken at 285.0 eV. The full width at half maximum for the C1s photopeaks was held constant at 1.70 eV. Curve fit photopeaks contributing less than 5% to the total carbon content were neglected.

SEM (scanning electron microscopy) photomicrographs were obtained using an International Scientific Instrument ISI SX-40 scanning electron microscope operated at a beam voltage of approximately 20kV. All samples were sputtered for approximately two to three minutes with gold to reduce charging.

RESULTS/DISCUSSION

The surface analysis results for the two composites are discussed separately.

Atomic Composition

The XPS results for the surface composition of the control, 10- and 69-month flight samples are shown in Table I. Elemental photopeaks are listed in the first column followed by the binding energy (in eV) and atomic concentration (in %) for each element. Carbon, oxygen, and nitrogen are expected for an epoxy composite which has a resin-rich surface. For example, the XPS composition of a BASF epoxy composite has been determined [8] to be 67.5% carbon, 14.2% oxygen, and 2.2% nitrogen in reasonable agreement with the present results for the control sample. The organo-fluorine photopeak at 689.3eV present on the composite surface most likely resulted from the transfer of a fluorinated release agent used in the fabrication of the composite. Moyer and Wightman [9] reported a 30% organo-fluorine content on the surface of a carbon fiber/polyimide composite. It is noted that the control sample has a 1.1% silicon characteristic of inorganic silicon at 103.2eV but the source is not identified. The small amounts of sodium (2.0%) and sulfur (1.1%) are not identified although Mallon et al. [5] have reported similar concentrations of minor contaminants on carbon fiber/polymer matrix composites.

As shown in Table I, the surface composition of the 10- and 69-month samples parallels that of the control which might appear at first to be a surprising result. The O/C atomic ratios were essentially the same for the three samples. However, some significant changes were observed. The loss of organo-fluorine was obvious for the two flight samples compared to the control. It is assumed that exposure to atomic oxygen results in the formation of volatile fluorine-containing species. Silicon contamination of LDEF samples is widely reported [1]. It is only noted that the 69-month sample has the highest silicon content (6.3%) with a binding energy characteristic of inorgano-silicon. It is well established that organo-silicon compounds when subjected to atomic oxygen are converted to inorgano-silicon containing materials [5].

Curve Fit Analysis

The results of the curve fit analysis for the three samples are summarized in Table II. Significant differences are observed in the carbon 1s curve fit region for the three samples showing different contributions (percentages) as well as different types of carbon functionality under the carbon 1s envelope. Although the atomic compositions of the three samples were similar (see Table I), the types of carbon functionality for each sample are very different. These results reinforce the necessity of curve-fitting photopeaks obtained in XPS measurements. Information obtained from proper curve fitting procedures is useful and critical in describing the surface chemistry of materials.

The carbon 1s photopeak of the control sample revealed a resin rich surface. The carbon 1s photopeak (C2) corresponding to hydrocarbon functionality accounted for 55.7% of the total carbon. The carbon-oxygen functionality (peaks C3, C4 and C5) accounted for 38.0% of the total carbon.

A dramatic shift in the curve fit analysis is seen for the 10- and 69-month flight samples. In both cases, a new major photopeak (C1) appeared with a binding energy of 283.7 eV assigned to a graphitic type carbon [10]. The appearance of the graphitic type carbon is a direct result of the degradation/erosion of the epoxy matrix to expose the carbon fibers of the composite. The curve fit analysis supports the argument that significant erosion of the epoxy matrix occurred within the first ten months of exposure in low Earth orbit.

The degradation/erosion of polymer matrix composite samples flown on the LDEF, particularly on the leading edge, has been discussed previously [11]. Here, atomic oxygen reaction results in polymer bond breaking and subsequent molecular fragmentation leading to erosion of the materials.

SEM Photomicrographs

The SEM photomicrographs of the control, 10- and 69-month flight samples are shown in Figure 1. Three very different surface topographies are observed in Figure 1 and support the results obtained from the XPS curve fit analysis.

The SEM photomicrograph of the control sample (see Fig. 1A) shows an apparent resin rich surface. The weave pattern seen on this control sample is not the weave pattern of the carbon fibers within the composite but rather the impression left from the scrim cloth used in the consolidation of the composite.

The SEM photomicrograph of the 10-month flight sample (see Fig. 1B) suggests some erosion of the matrix resin. The curve fit analysis of the 10-month flight sample showed carbon functionality that is consistent with the presence of both resin and carbon fiber. Photopeaks C2 - C5 for the 10-month flight sample are attributed to the resin since these photopeaks were also observed in the control sample. However, photopeaks C3-C5 have been reported for carbon fibers [12]. On the other hand, photopeak C1 is uniquely assigned to the carbon fibers. This significant photopeak, accounting for 46% of the total carbon signal, was absent in the control sample.

The SEM photomicrograph of the 69-month flight sample (see Fig. 1C) shows significant continued erosion of the matrix resin. The 69-month flight sample exhibits similar topography as reported previously for composite samples from the LDEF [2]. The carbon 1s curve fit analysis for the 69-month flight sample again suggests that the surface composition results from a combination of both resin and carbon fibers. However, the contribution of the C1 photopeak would suggest the composition is predominantly due to carbon fibers. The SEM photomicrographs are consistent then with the XPS curve fit analysis for the control, 10- and 69-month flight samples.

The SEM photomicrographs and the curve fit analysis support the degradation/erosion of the epoxy matrix within the first 10 months of the mission as well as further degradation for the remaining 59 months. Tennyson [13] reported that an atomic oxygen fluence of 1.33×10^{21} atoms/cm² on Row 12 was sufficient to erode the epoxy layer and a portion of the reinforcing graphite fibers. The epoxy samples discussed in the present study were located on the leading edge (Row 9) of the LDEF where the atomic oxygen fluence was 8.99×10^{21} atoms/cm². Thus, the higher atomic oxygen fluence for Row 9 would facilitate the degradation/erosion of the matrix to expose the carbon fibers as seen in Figure 1.

P1700/C6000 Polysulfone Composite

Atomic Composition

The XPS results for the surface composition of the control, 10- and 69-month flight samples are shown in Table III. Carbon, oxygen, and sulfur are expected for a polysulfone composite which has a resin-rich surface. For example, the XPS composition of a polysulfone film has been determined [14] to be 82% carbon, 15% oxygen, and 3.0% sulfur. Although the concentrations of carbon and sulfur are in good agreement, the sulfur concentration for the composite sample is considerably lower than expected. The organo-fluorine photopeak at 688.9 eV present on the control composite surface most likely resulted from the transfer of a fluorinated release agent used in the fabrication of the composite. This is similar to the concentration of organo-fluorine noted and discussed above for the control epoxy composite.

The control sample has a 1.2 atomic % silicon characteristic of organo-silicon at 102.4 eV but the source is not identified. The sources of the small amounts of aluminum (1.6%) and calcium (1.3%) are

also not identified. George and coworkers [11] have reported similar concentrations of minor contaminants on P1700 polysulfone/T300 composites.

As shown in Table III, the oxygen content of the 10- and 69-month samples differs significantly from that of the control sample. The O/C atomic concentration ratio increases from 0.19 (control) to 0.36 (10 month) to 2.08 (69 months) in sharp contrast to the constancy of the same ratio for the epoxy composite. George et al. [11] have also reported a trend of decreasing carbon content and increasing oxygen content for flight composite samples compared to control composite samples. The loss of organo-fluorine was obvious for the two flight samples compared to the control as was the case for the epoxy composites.

It is noted that the 69-month sample again has the highest silicon content (17.3%) with a binding energy at 103.7 eV characteristic of inorgano-silicon. A similar result was observed on the 69-month epoxy composite. George et al. [11] also reported an increase in silicon content for the flight samples. A possible SiO_x non-volatile contamination layer on the 69-month flight sample is consistent with the observed increase in the oxygen and silicon contents as well as the shift in the binding energy of the silicon 2p photopeak.

Sulfur is noted on the two flight samples at a higher concentration than for the control and closer to the value of 3.0% expected for neat polysulfone. However, the binding energy increased from 167.9 eV (organo-sulfur) for the control to 169.75 eV (inorgano-sulfur) for the two flight samples. The conversion of organo-sulfur to inorgano-sulfur in the presence of atomic oxygen has been documented [2]. The sources of the small amounts of aluminum (1.9%), calcium (0.1%), and sodium (0.8%) are not identified.

The appearance of nitrogen in both the 10-month and 69-month samples and its absence in the control sample may be due to uncovering of the PAN-based carbon fibers following matrix erosion by atomic oxygen. The nitrogen content of PAN-based T300 carbon fibers as determined by XPS has been reported [15] as 2.1% in fair agreement with the value of 1.1% observed in the present work.

Curve Fit Analysis

The carbon 1s curve fit analysis of the control and two flight samples is shown in Table IV. The curve fit analysis of the control sample again revealed a resin rich surface. Hydrocarbon functionality corresponds to 91% of the total photopeak area. The remaining area corresponds primarily to carbon-oxygen functionality.

The curve fit analysis of the 10-month flight sample showed a three-fold decrease in the hydrocarbon functionality and a two-fold increase in the carbon-oxygen functionality. The appearance of the C1 photopeak at 283.5 eV is taken as supporting evidence the carbon fibers were uncovered as the polysulfone matrix resin was eroded by reaction with atomic oxygen. This is the same striking result as was obtained for the epoxy composite.

The curve fit analysis for the 69-month polysulfone composite shows some difference from the epoxy composite. Carbon-oxygen functionality accounted for 50% of the total carbon content for the polysulfone composite compared to only 9% for the epoxy composite. No definitive conclusion is drawn from this result.

ACKNOWLEDGEMENTS

The authors (H. L. G. and J. P. W.) acknowledge the support of this research under NASA Grant NAG-1-1186.

REFERENCES

- [1] Stein, B. A.: LDEF Materials Overview. In LDEF -69 Months in Space, NASA Conference Publication 3194 (Arlene S. Levine, editor), Part 3, 1992, p. 741.
- [2] George, P. E. and Hill, S. G.: Results from Analysis of Boeing Composite Specimens Flown on LDEF Experiment M0003. In LDEF -69 Months in Space, NASA Conference Publication 3134 (Arlene S. Levine, editor), Part 2, 1991, p.1115.
- [3] Slemp, W. S.; Young, P. R.; Witte, jr., W. G. and Shen, J. Y.: Effects of LDEF Flight Exposure on Selected Polymer Matrix Resin Composite Materials. In LDEF -69 Months in Space, NASA Conference Publication 3134 (Arlene S. Levine, editor), Part 2, 1991, p.1149.
- [4] A. F. Whitaker, A. F.; R. R. Kamenetzky, R. R.; M. M. Finckenor, M. M.; and J. K. Norwood, J. K.: Atomic Oxygen Effects on LDEF Experiment A0171. In LDEF -69 Months in Space, NASA Conference Publication 3194 (Arlene S. Levine, editor), Part 3, 1992, p.1125.
- [5] J. J. Mallon, J. J.; J. C. Uht, J. C. and C. S. Hemminger, C. S.: Surface Analysis of Composites Exposed to the Space Environment on LDEF. In LDEF -69 Months in Space, NASA Conference Publication 3194 (Arlene S. Levine, editor), Part 3, 1992, p.963.
- [6] Grammer, H. L.: Surface Characterization of LDEF Materials. M. S. Thesis, Virginia Polytechnic Institute and State University, Blacksburg, VA, 1993.
- [7] High Resolution XPS of Organic Polymers, G. Beamson and D. Briggs, ed., p.277, John Wiley & Sons, Chichester (1992).
- [8] Chin, J. W. and Wightman, J. P.: Surface Pretreatment and Adhesive Bonding of Carbon Fiber-Reinforced Epoxy Composites. In Composition Bonding ASTM STP 1227, D. J. Damico, J. M. Prandy and S. L. F. Nicks, Eds., Am. Soc. Testing & Materials, Philadelphia, PA, in press.
- [9] Moyer, D. J. D. and Wightman, J. P.: Characterization of Surface Pretreatments of Carbon Fiber-Polyimide Matrix Composites. Surface & Interface Analysis, 14, 496-504 (1989).
- [10] Handbook of X-ray Photoelectron Spectroscopy, G. E. Muilenberg, ed., p. 38, Perkin-Elmer Corp., Eden Prarie, MN (1979).
- [11] George, P. E., Dursch, H. W. and Hill, S. G.: Space Environmental Effects on LDEF Composites: A Leading Edge Coated Graphite Epoxy Panel. In LDEF -69 Months in Space, NASA Conference Publication 3194 (Arlene S. Levine, editor), Part 3, 1992, p.923.
- [12] Commercon, P. and Wightman, J. P. : Surface Characterization of Plasma Treated Carbon Fibers and Adhesion to a Thermoplastic Polymer. J. Adhesion, 38, 55 (1992).

[13] Tennyson, R. C.: Additional Results on Space Environmental Effects on Polymer Matrix Composites - Experiment A0180. In LDEF Materials Workshop '91, NASA Conference Publication 3162, (Bland A. Stein and Philip R. Young, compilers), Part 2, 1992, p. 593.

[14] Hollenhead, J. B. and Wightman, J. P.: The Adhesive Bonding of Steel with Polysulfone. J. Adhesion, **37**, 121 (1992).

[15] DeVilbiss, T. A.: Carbon Fiber Surface Treatments for Improved Adhesion to Thermoplastic Polymers. Ph.D. Dissertation, Virginia Polytechnic Institute and State University, Blacksburg, VA, 1987.

(A)



(B)



(C)

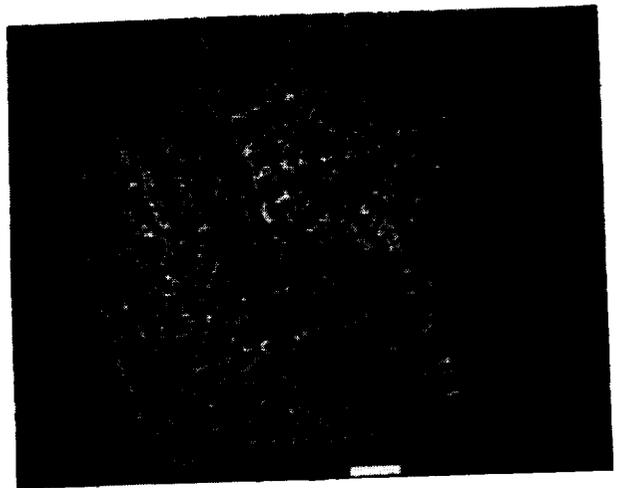


FIGURE 1: SEM PHOTOMICROGRAPHS OF 934/T300 EPOXY COMPOSITE SAMPLES

(A) CONTROL (B) 10 MONTH (C) 69 MONTH.

TABLE I: XPS ANALYSIS OF 934/T300 EPOXY COMPOSITES

CONTROL

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>ATOMIC CONC(%)</u>
C 1s	285.0	68.8
O 1s	532.6	18.1
N 1s	399.9	3.4
F 1s	689.3	5.5
Si 2p	103.2	1.1
Na 1s	1072.2	2.0
S 2p	168.4	1.1

10 MONTH

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>ATOMIC CONC(%)</u>
C 1s	285.0	73.3
O 1s	531.9	18.7
N 1s	399.6	5.5
F 1s	688.2	0.2
Si 2p	103.7	0.8
Na 1s	1071.9	0.5
S 2p	168.4	0.8

69 MONTH

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>ATOMIC CONC(%)</u>
C 1s	285.0	72.0
O 1s	533.3	19.6
N 1s	400.6	0.8
F 1s	nsp*	--
Si 2p	104.0	6.3
Na 1s	nsp	--
S 2p	170.0	0.8

*nsp-no significant peak

TABLE II: CARBON 1s CURVE FIT ANALYSIS OF 934/T300 EPOXY COMPOSITES

CONTROL

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>% AREA</u>	<u>CARBON TYPE</u>
C2	285.0	55.7	<u>C</u> -H
C3	286.3	25.0	<u>C</u> -O
C4	287.8	7.8	<u>C</u> =O
C5	289.4	5.2	O- <u>C</u> =O

10 MONTH

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>% AREA</u>	<u>CARBON TYPE</u>
C1	283.6	46.4	graphitic
C2	285.0	30.8	<u>C</u> -H
C3	286.6	11.8	<u>C</u> -O
C4	288.1	7.3	<u>C</u> =O

69 MONTH

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>% AREA</u>	<u>CARBON TYPE</u>
C1	283.9	49.8	graphitic
C2	285.0	38.9	<u>C</u> -H
C3	286.4	8.6	<u>C</u> -O

TABLE III: XPS ANALYSIS OF P1700/C6000 POLYSULFONE COMPOSITES

CONTROL

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>ATOMIC CONC(%)</u>
C 1s	285.0	76.9
O 1s	532.1	14.5
S 2p	167.9	0.4
F 1s	688.9	4.1
Al 2p	74.7	1.6
Ca 2p	347.6, 351.1	1.3
Si 2p	102.4	1.2

10 MONTH

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>ATOMIC CONC(%)</u>
C 1s	285.0	67.0
O 1s	531.2	24.5
S 2p	168.4	2.4
Si 2p	102.0	2.3
Al 2p	73.8	1.9
Na 1s	1071.3	0.8
N 1s	398.2	1.1

69 MONTH

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>ATOMIC CONC(%)</u>
C 1s	285.0	25.0
O 1s	533.1	51.9
S 2p	169.6	2.9
Si 1s	103.7	17.3
N 1s	400.6	1.2
Ca 2p	348.5, 352.0	0.1

TABLE IV: CARBON 1s CURVE FIT ANALYSIS OF P1700/C6000
POLYSULFONE COMPOSITES

CONTROL

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>% AREA</u>	<u>CARBON TYPE</u>
C 2	285.0	90.8	<u>C</u> -H
C 3	288.9	2.8	O- <u>C</u> =O

10 MONTH

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>% AREA</u>	<u>CARBON TYPE</u>
C 1	283.5	53.3	graphitic
C 2	285.0	27.1	<u>C</u> -H
C 3	286.1	12.2	<u>C</u> -O

69 MONTH

<u>PHOTOPEAK</u>	<u>BINDING ENERGY(eV)</u>	<u>ATOMIC CONC(%)</u>	<u>CARBON TYPE</u>
C 1	283.6	22.4	graphitic
C 2	285.0	18.6	<u>C</u> -H
C 3	286.6	33.3	<u>C</u> -O
C 4	288.0	12.4	<u>C</u> =O
C 5	289.5	4.7	O- <u>C</u> =O