





Space Flight Requirements for Fiber Optic Components; Qualification Testing and Lessons Learned

Melanie N. Ott

NASA Goddard Space Flight Center

USA, melanie.ott@gsfc.nasa.gov


misspiggy.gsfc.nasa.gov/photonics

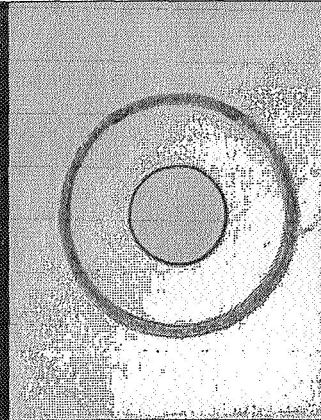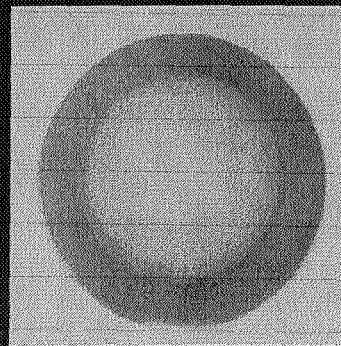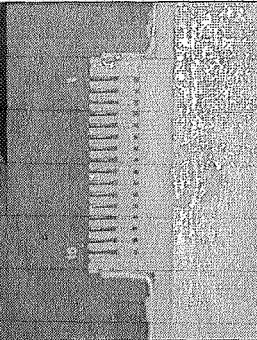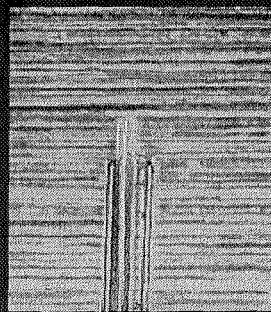

ESA/NASA Workshop 2006

June 22, 2006


NASA Goddard Space Flight Center



Outline



- Introduction
- NASA COTS Photonics Validation Approach
- Typical Environmental Requirements
- Mercury Laser Altimeter Test Results
- LRO – Laser Ranging Requirements
- Laser Ranging Pre qualification Test Data
- Lessons Learned-Manufacturing
- Conclusion



Code 562: Parts, Packaging, & Assembly
Technologies Branch

Contributing Colleagues

The GSFC Code 562 Photonics Group & contributors



Photonics Group pictured left to right--


Dr. Xiaodan "Linda" Jin, Mary Malenab, Frank LaRocca
Patricia Friedberg, Richard Chuska, Shawn Macmurfhy

Other collaborators not pictured:

Adam Matzuseski (Mech Lead LR) & Luis Ramos-Izquierdo (Optics Lead LR)

June 22, 2006

NASA Goddard Space Flight Center



Introduction

Changes in Our GSFC Environment

Short term projects, low budgets

Instruments like GLAS, MLA, VCL, LOLA

Changes to the Mil-Spec system, NASA relied heavily.
Telecommunications products available, state-of-the-art.
Vendors and parts rapidly changing.
Most photonics now COTS.
Qualification not only impossible but far too expensive.
Characterization of COTS for risk mitigation.
Quality by similarity where possible.


June 22, 2006

NASA Goddard Space Flight Center



Issues to Consider

- Schedule, shorter term
- Funds available,
- Identify sensitive or high risk components.
- System design choices for risk reduction.
- Packaging choices for risk reduction.
- Quality by similarity means no changes to part or process.
- Qualify a "lot" by protoflight method—you fly the parts from the lot qualified, not the tested parts.
- Telcordia certification less likely now.
- Pre-qualification for high risk "unknowns"

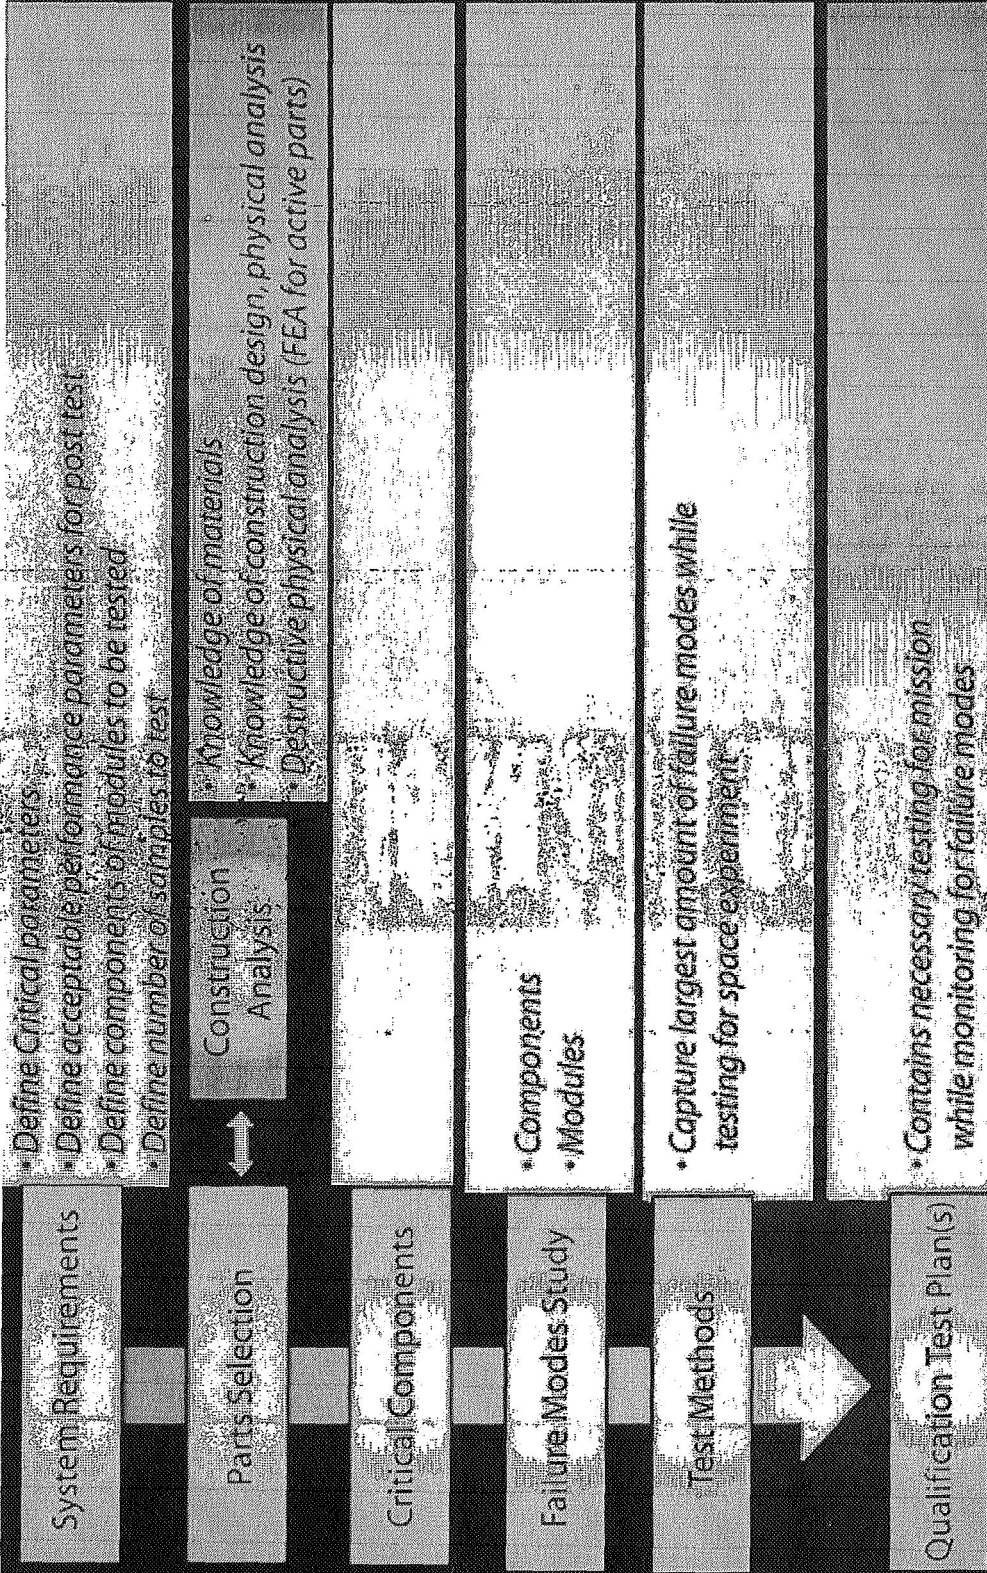

Flow chart courtesy of Suzanne Falvey, Northrup Grumman, based on M Ott reference:

* *Photonic Components for Space Systems*, M. Ott, Presentation for Advanced Microelectronics and Photonics for Satellites Conference, 23 June 2004.

June 22, 2006

NASA Goddard Space Flight Center



COTS Space Flight "Qualification"




Flow chart courtesy of Suzanne Falvey, Northrup Grumman, based on M. Ott reference:

* *Photonic Components for Space Systems*, M. Ott, Presentation for Advanced Microelectronics and Photonics for Satellites Conference, 23 June 2004.

June 22, 2006

NASA Goddard Space Flight Center




Environmental Parameters

- Vacuum requirements
 - (Materials Analysis or Vacuum Test or both)
- Vibration requirements
- Thermal requirements
- Radiation requirements

June 22, 2006

NASA Goddard Space Flight Center



Environmental Parameters: Vacuum

Vacuum outgassing requirements:


- ASTM-E595,
 - 100 to 300 milligrams of material
 - 125°C at 10^{-6} Torr for 24 hours
- Criteria: 1) Total Mass Loss $< 1\%$
 - 2) Collected Volatile Condensable Materials $< 0.1\%$
- Configuration test
- Optics or laser nearby, is ASTM-E595 enough?
 - ask your contamination expert

- 1) Use approved materials
- 2) Preprocess materials, vacuum, thermal
- 3) Decontaminate units: simple oven bake out, or vacuum?
- 4) Vacuum test when materials analysis is not conducted and depending on packaging and device.

Space environment; vacuum is actually 10^{-9} torr, best to test as close as possible for laser systems. Many chambers don't go below 10^{-7} torr.

June 22, 2006


NASA Goddard Space Flight Center



Environmental Parameters: Vibration

Launch vehicle vibration levels for small subsystem
(established for EO-1)


Frequency (Hz)	Protoflight Level
20	0.026 g ² /Hz
20-50	+6 dB/octave
50-800	0.16 g ² /Hz
800-2000	-6 dB/octave
2000	0.026 g ² /Hz
Overall	14.1 grms

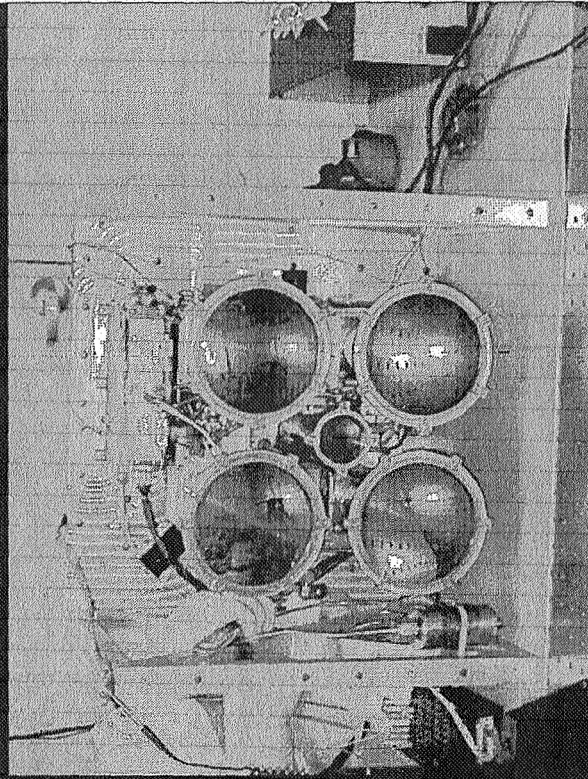

However, this is at the box level, twice the protoflight vibration values establish the correct testing conditions for the small component.

June 22, 2006


NASA Goddard Space Flight Center



Environmental Parameters: Vibration

Launch vehicle vibration levels for small component (based on box level established for EO-1) on the "high" side.


Frequency (Hz)	Protoflight Level
20	0.052 g ² /Hz
20-50	+6 dB/octave
50-800	0.32 g ² /Hz
800-2000	-6 dB/octave
2000	0.052 g ² /Hz
Overall	20.0 grms

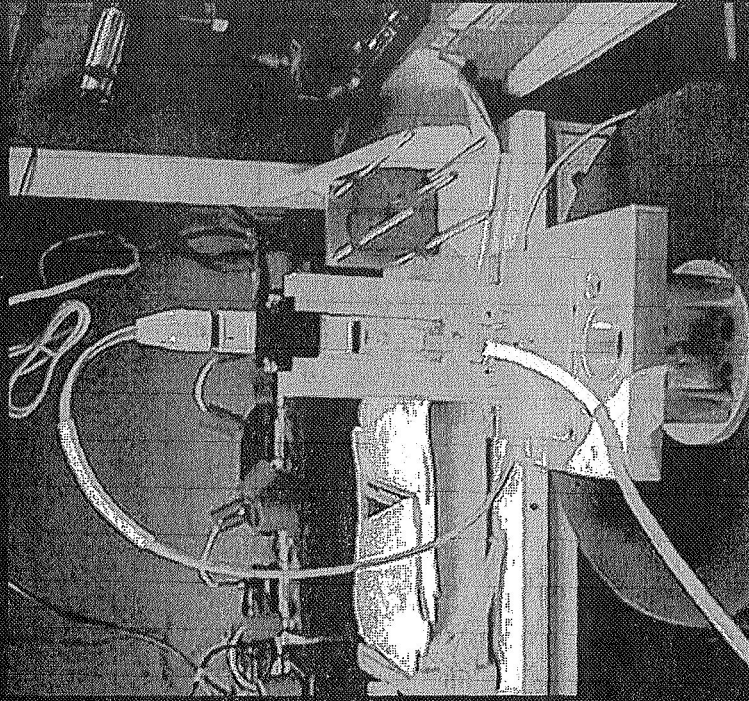

3 minutes per axis, tested in x, y and z

June 22, 2006

NASA Goddard Space Flight Center



Environmental Parameters: Thermal

There is no standard, typical and benign -25 to $+85$ C.
Telcordia is -45°C to $+80^{\circ}\text{C}$.

Depending on the part for testing;

Insitu testing where possible

Add 10°C to each extreme for box level survival

Thermal cycles determined by part type

60 cycles for assemblies for high reliability

30 cycles minimum for assemblies, high risk

100 or more, optoelectronics.

More for high power systems

Knowledge of packaging and failure modes really helps with
determination of necessary thermal cycles

June 22, 2006

NASA Goddard Space Flight Center




Environmental Parameters: Radiation

Assuming 7 year mission,
Shielding from space craft

LEO, 5 – 10 Krads, SAA

MEO, 10 – 100 Krads, Van Allen belts

GEO, 50 Krads, Cosmic Rays

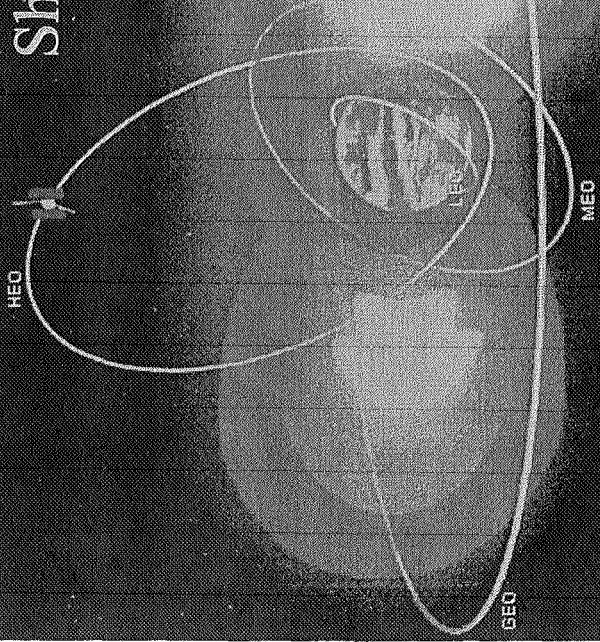

Proton conversion to Total Ionizing Dose (TID)
At 60 MeV, 10^{10} protons/Krad for silicon devices
For systems susceptible to displacement damage

Testing for displacement damage: 3 energies in the range ~ 10 to 200 MeV.
If you have to pick one or two energies stay in the mid range of 65 MeV and lower. Less probability of interaction at high energies.
Ballpark levels: 10^{-12} p/cm² LEO, 10^{-13} p/cm² GEO, 10^{-14} p/cm² for special missions (Jupiter).

June 22, 2006

NASA Goddard Space Flight Center




Environmental Parameters: Radiation

Typical space flight background radiation total dose
30 Krads – 100 Krads over 5 to 10 year mission.

Dose rates for fiber components:

- GLAS, 100 Krads, 5 yr, .04 rads/min
- MLA, 30 Krads, 8 yr, .011 rads/min (five year ave)
- EO-1, 15Krads, 10 yr, .04 rads/min

Any other environmental parameters that need to be considered?
For example, radiation exposure at very cold temp, or prolonged
extreme temperature exposure based on mission demands.



Mercury Laser Altimeter (MLA): Construction Analysis

Optical Fiber Assemblies

Diamond AVIMS connector / W.L. Gore Flexlite

Polymicro Technologies FIA 200/220

Performance: < 0.4 dB loss

Preconditioning of non metallic materials and failure modes knowledge of construction

Hytyl boots: Thermal vacuum precondition: 140°C, 24 hrs, 1 Torr

Flexlite cable: Thermal preconditioning, 8 cycles, -20 to +60°C, 60 min at 60°C

Epotek 353ND: approved for space.


Post processing decontamination of assemblies @ 50°C (To bake out but not to age)

Cure schedule on outgassing database is very high temp.




Best to use close to usage temp cure, with a post cure bake out

June 22, 2006

NASA Goddard Space Flight Center



MLA Assembly Environmental Validation

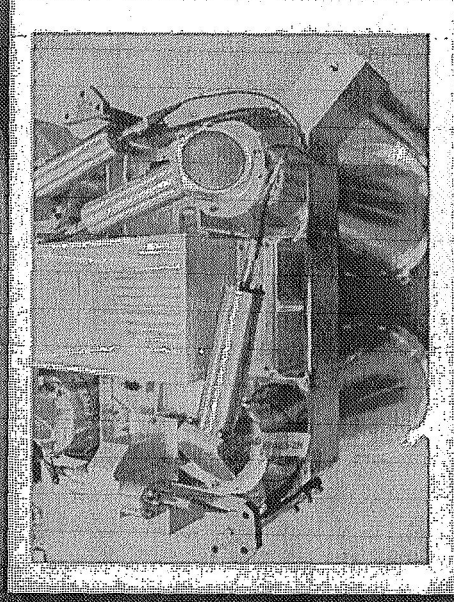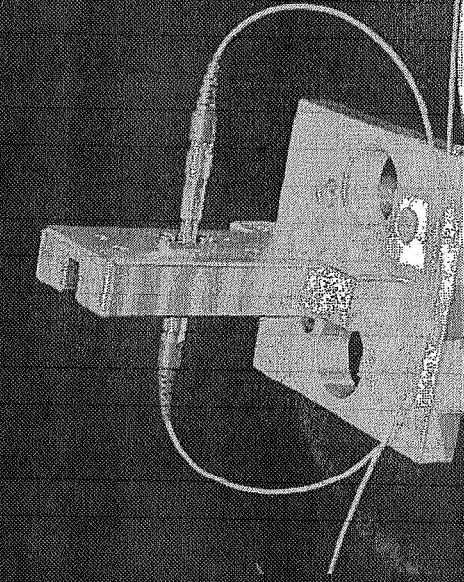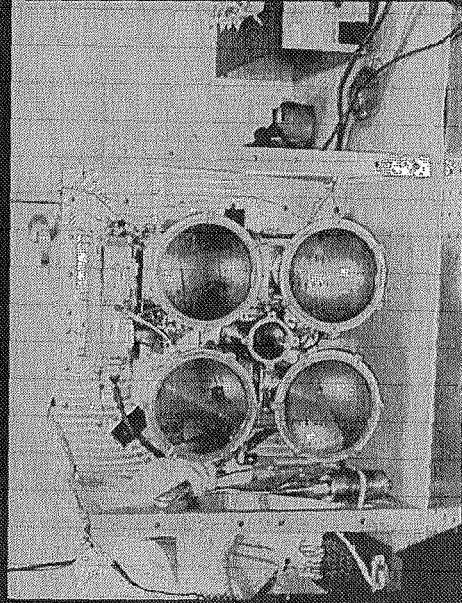

Requirements/Testing: Performance < .4 dB for all, 850 nm
Vibration 14.1 grms, 3 min/axis

Because box level @ 10 grms


Thermal: -30°C to +50 °C, 90 cycles, last 42 monitored
25 minute soak, 2 °C/min ramp rates.

Radiation: two dose rate model, -20°C,
11.2 and 22.7 rads/min to 30 Krads
(Actual dose rate .011 rads/min)

June 22, 2006


NASA Goddard Space Flight Center

SPIE Vol. 5104



MLA Assembly Environmental Validation

High Dose Rate Rad-Induced Attenuation for 200 (red) & 300 (blue) Flexlite Cable

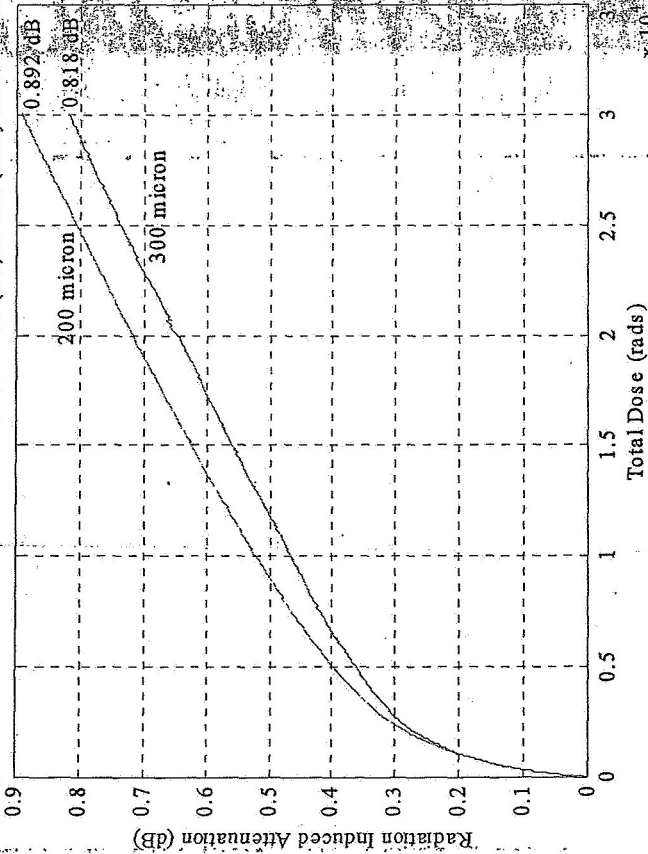


Flexlite Radiation Test, 22.7 rads/min at -18.3°C

Radiation Conclusion: < .07 dB, using 11.2 rads/min, -24.1°C, 26.1 in, "dark"
Results for 10 m, at 30 Krads, -20°C, 850 nm, 23 rads/min ~ 1 dB or 0.10 dB/m

Random Vibration and Thermal Cycling: no registered losses


< / = .04 dB power increase

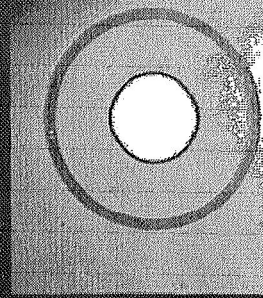


June 22, 2006

NASA Goddard Space Flight Center


Low Dose Rate Rad-Induced Attenuation for 200 (red) & 300 (blue) Flexlite Cable

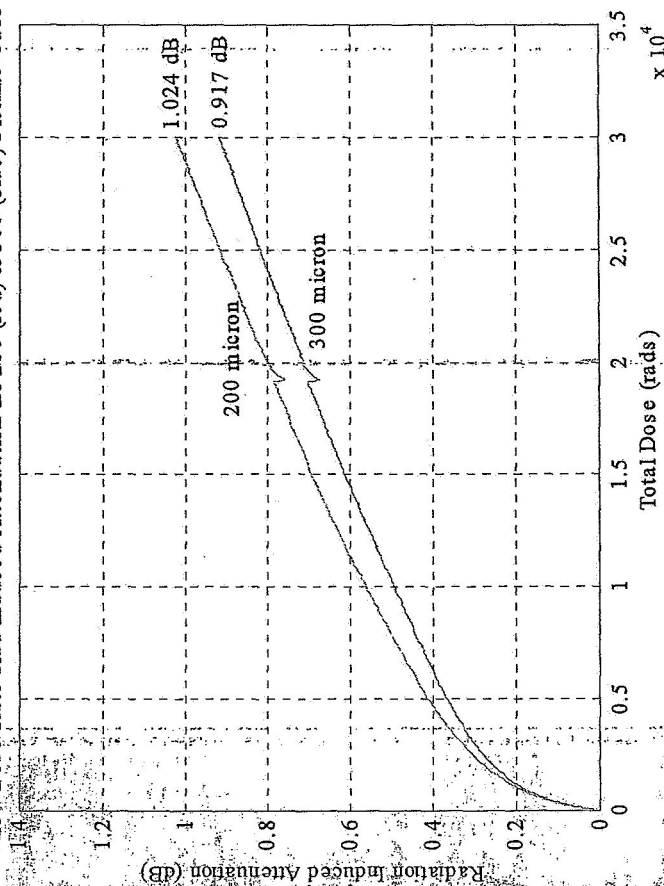

Flexlite Radiation Test, 11.2 rads/min at -24.1°C




Lunar Recon Orbiter : Laser Ranging and Altimetry



HGAS

Receiver Telescope
mounted on HGA
and a fiber array to
route signal from
HGA to LOLA

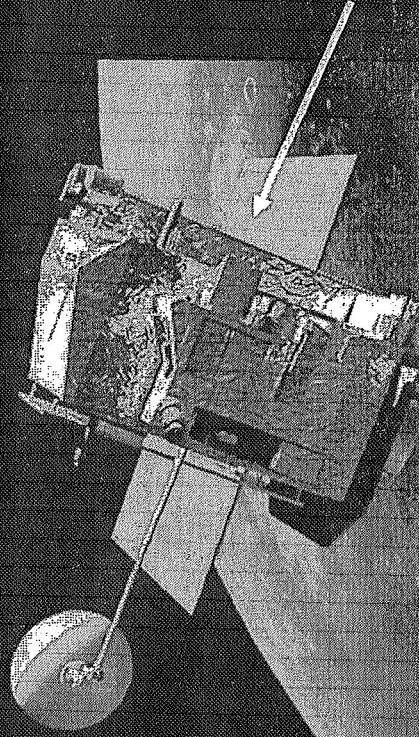


Lunar
Orbiter Laser
Altimeter
LOLA

Deployable HGA will move in x and y via gimbals
Fiber bundle will be routed through gimbals, down boom and to LOLA
Issues: Cold temperature during gimbal movement, low loss requirements

June 22, 2006

NASA Goddard Space Flight Center




Laser Ranging Requirements

- Receiver optics system fiber bundle array
- 10 m max length of assembly
- 7 fiber bundle from receiver telescope to LOLA, single connector
- Some sections will receive nearly 1 Mrad while cold.
- Budget is 2 dB for all losses including environmental and performance.
- Data from MLA not enough for rad performance extrapolation.


June 22, 2006

NASA Goddard Space Flight Center



GSFC Optical Fiber Arrays


AVIM connectors with custom drilling (single hole, not LR design) with 300/330 optical fiber Flexlite cable

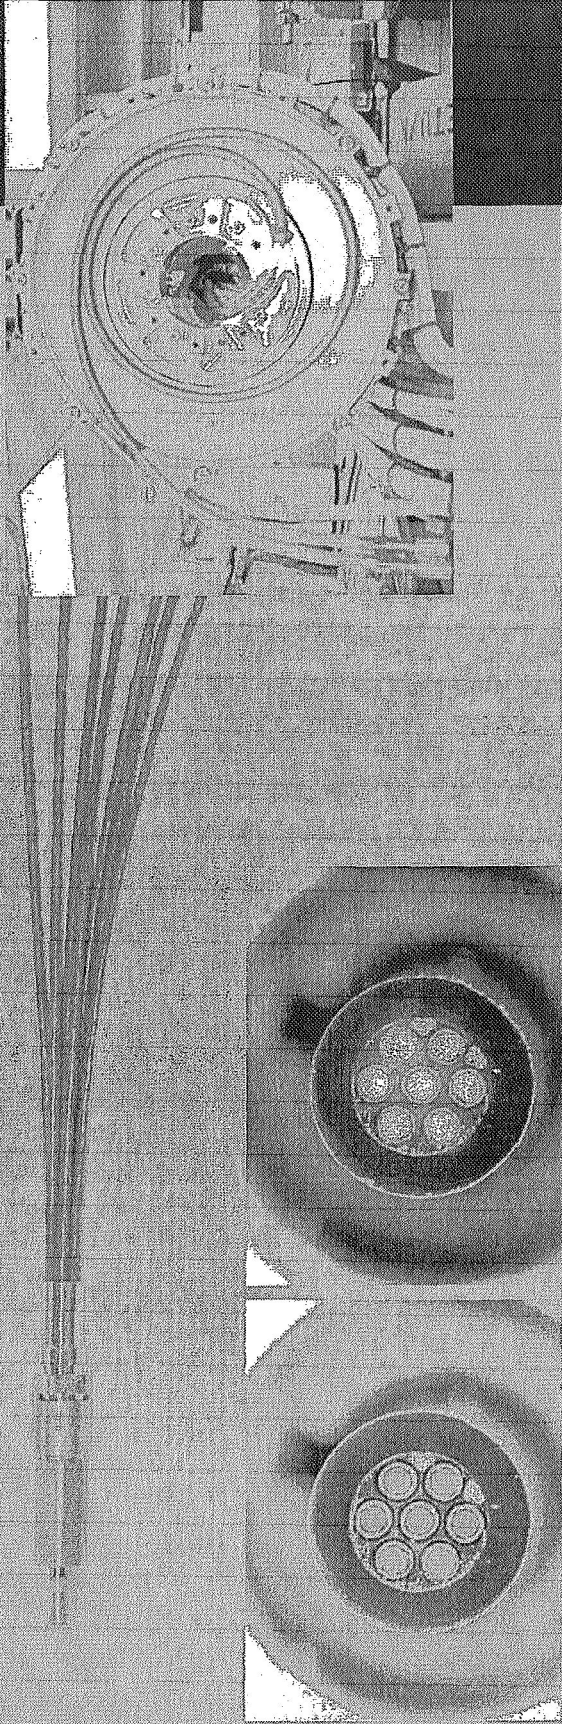


Outgas Testing to ASTM-E595
Diamond AVIMs Right Angle Boot; TML 0.01%, CVCVM 0.00%
W.L. Gore Outer Jacket PFA for over metal braid; TML 0.01%, CVCVM 0.00%

June 22, 2006

NASA Goddard Space Flight Center




LRO Ranging Pre-Qualification Test

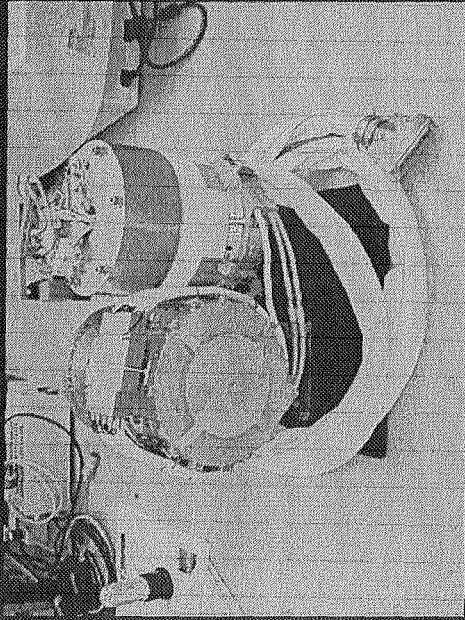


Gimbals

Fiber optic cable (4 m)
gimbal test inside of
thermal chamber
monitored in situ @ 850
nm


Each gimbal cycle up
and back is 4 min 45 sec

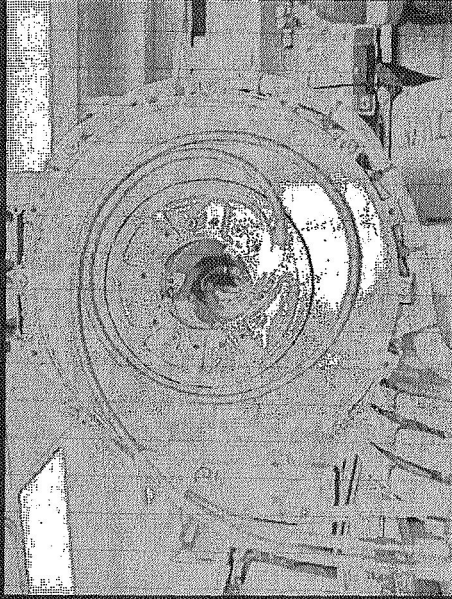

Window inside gimbal; RF cable wrap

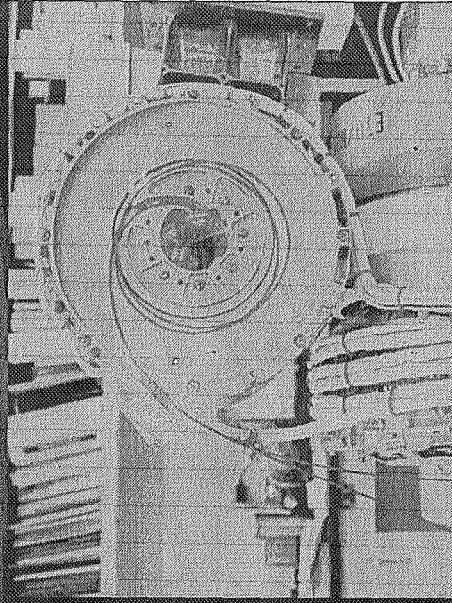


**Window inside gimbal;
Flexlite MLA cable
wrap inside gimbal**

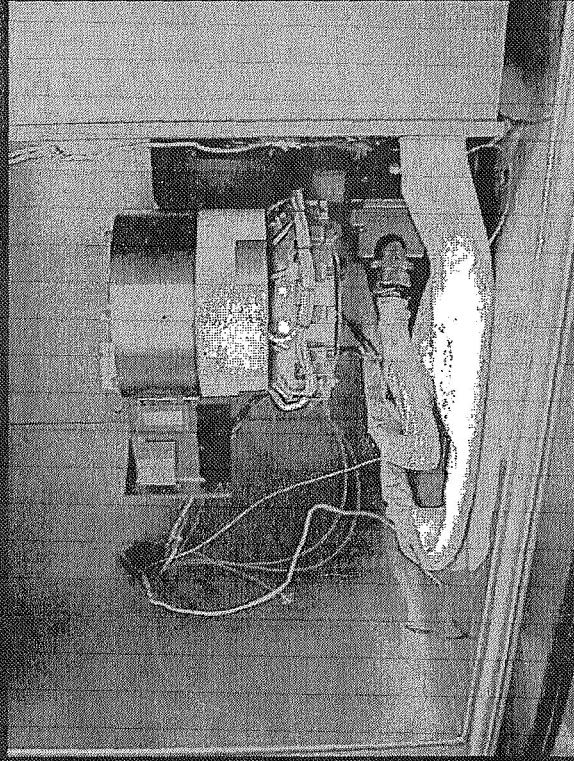

Cable wrapped
through twice,
in constant
motion to 5000
cycles per temp
for 3 temps;
0°C, -10°C and
-20°C

June 22, 2006

NASA Goddard Space Flight Center



LRO Ranging and Altimetry Gimbal Test


Results of Test 1 at 0°C, Last few gimbal cycles, flex losses < 0.010 dB

—◆— Optical Insertion Loss
—■— Gimbal Positions

Gimbal Positions and Optical Insertion Loss


From 5590 to 5596 cycles at 0 degrees C

(Note: The fiber is tight at 0 position and loose at 180)

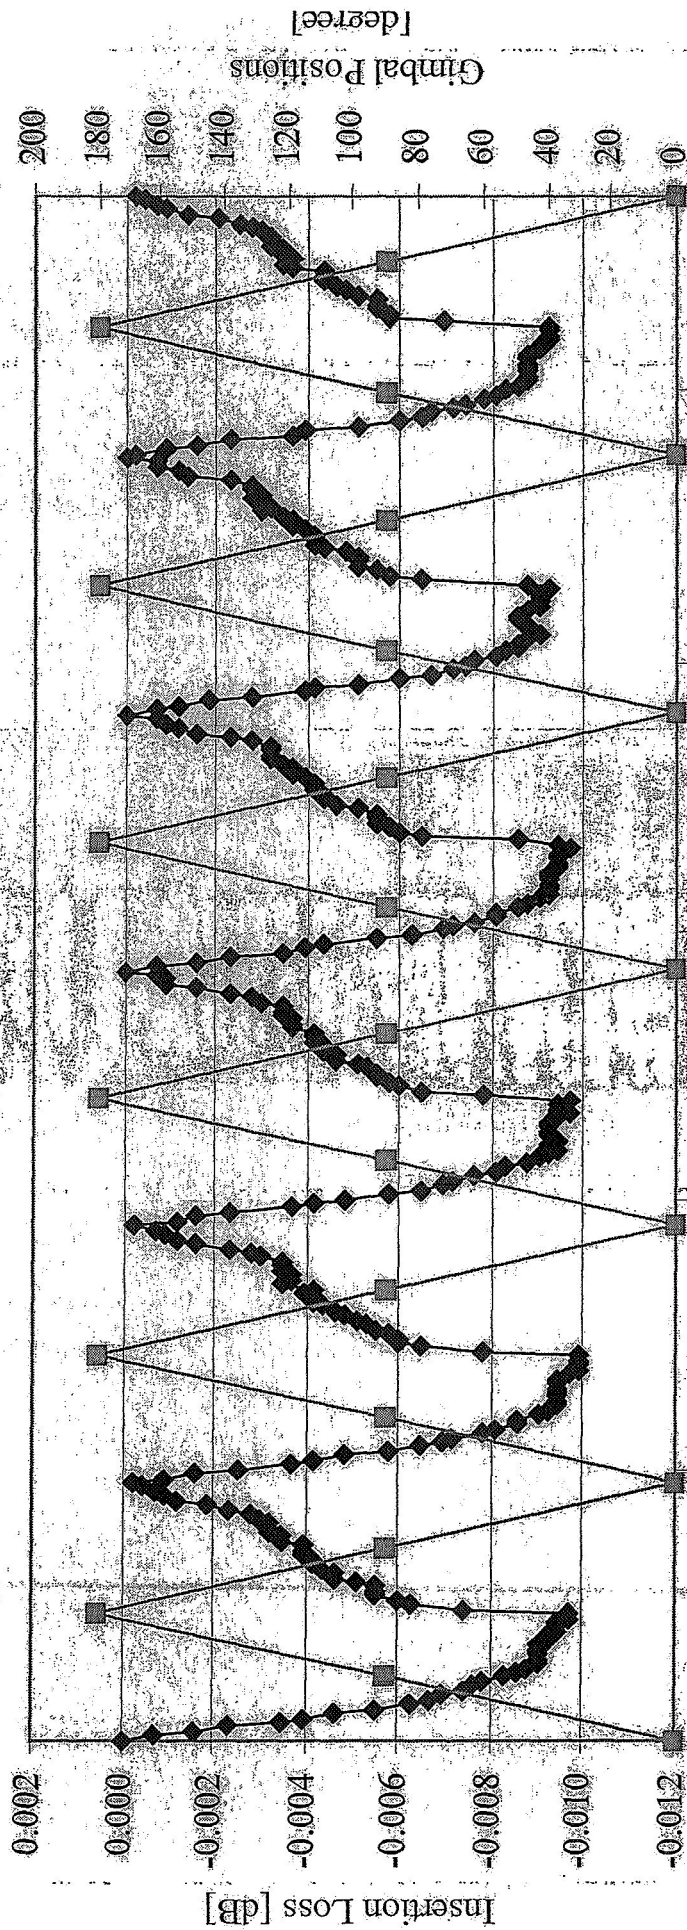

1/9/06 9:02 AM 1/9/06 9:07 AM 1/9/06 9:12 AM 1/9/06 9:17 AM 1/9/06 9:22 AM 1/9/06 9:27 AM

Date & Time




LRO Ranging and Altimetry Test

Results of Test 2 at -10°C, Last few gimbal cycles, flex losses < 0.012 dB

Gimbal Positions and Optical Insertion Loss@-10C
with 5580 to 5586 cycles

(Note: The fiber is tight at 0 degrees position and loose at 180 degrees)

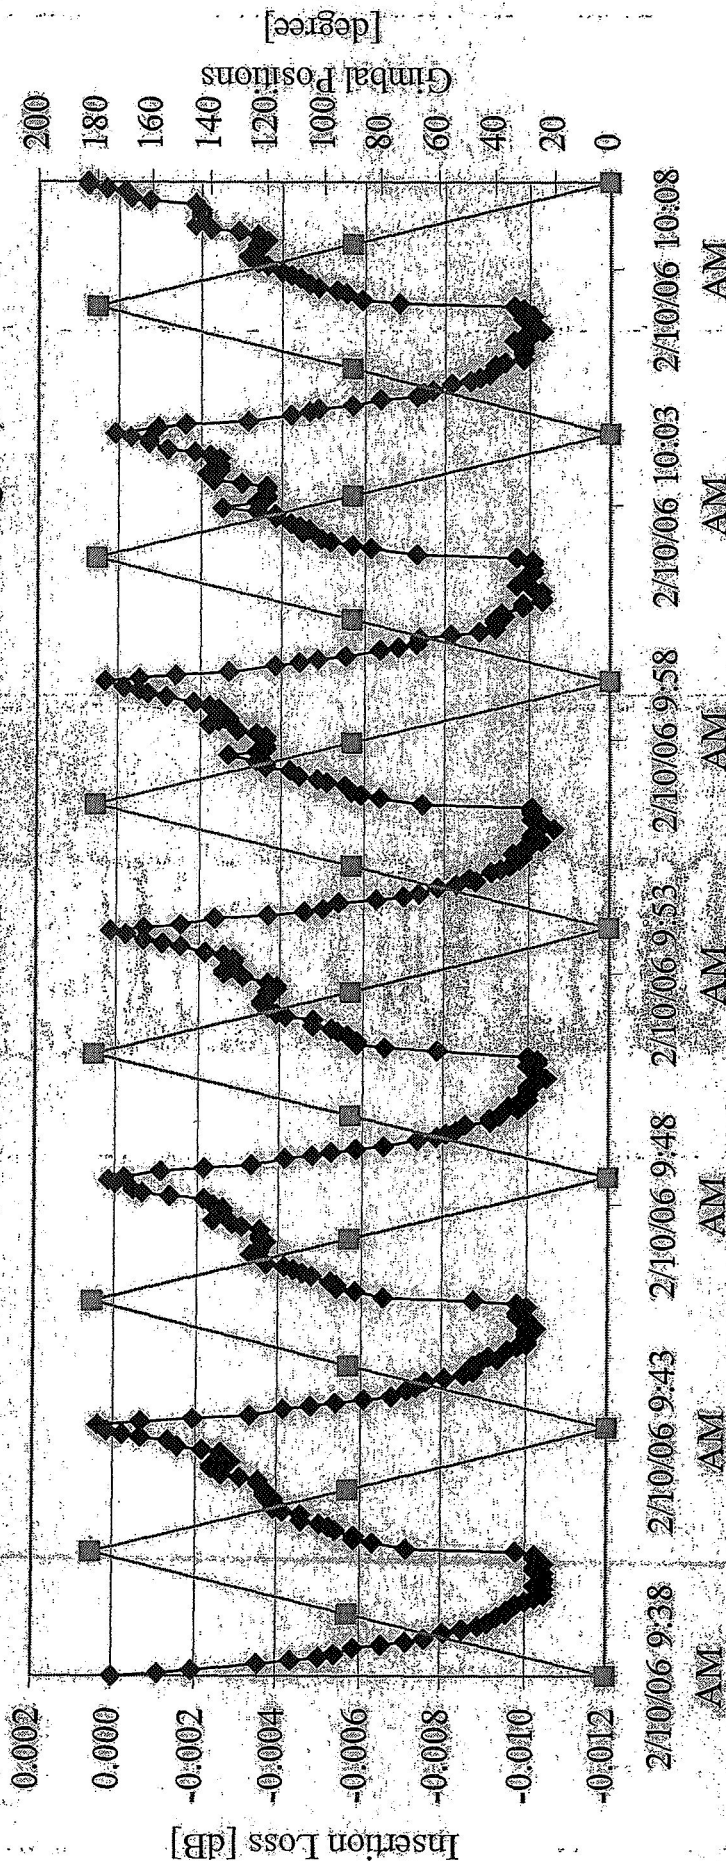




LRO Ranging and Altimetry Test


Results of Test 3 at -20°C, 1580 cycles, flex losses < 0.012 dB

Gimbal Positions and Optical Insertion Loss@-20C
From 1574 to 1580 cycles

(Note: The fiber is tight at 0 position and loose at 180)

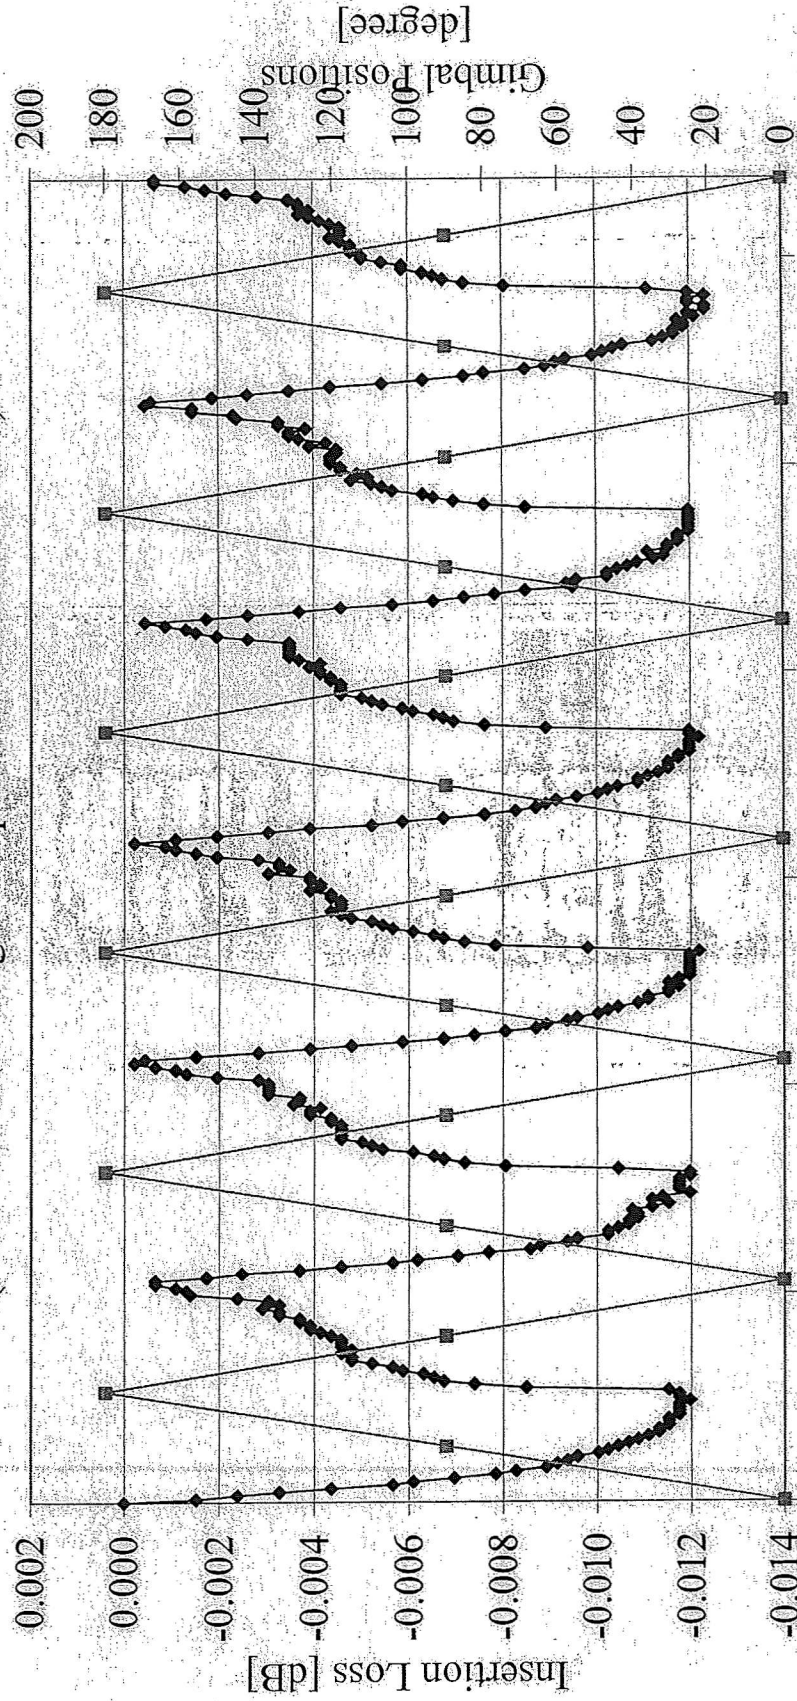

Date & Time




LRO Ranging and Altimetry Test

Results of Test 3 at -20°C, Last few gimbals cycles, flex losses ≤ 0.014 dB

Gimbal Positions and Optical Insertion Loss@-20°C


From 5454 to 5460 cycles

(Note: The fiber is tight at 0 position and loose at 180)

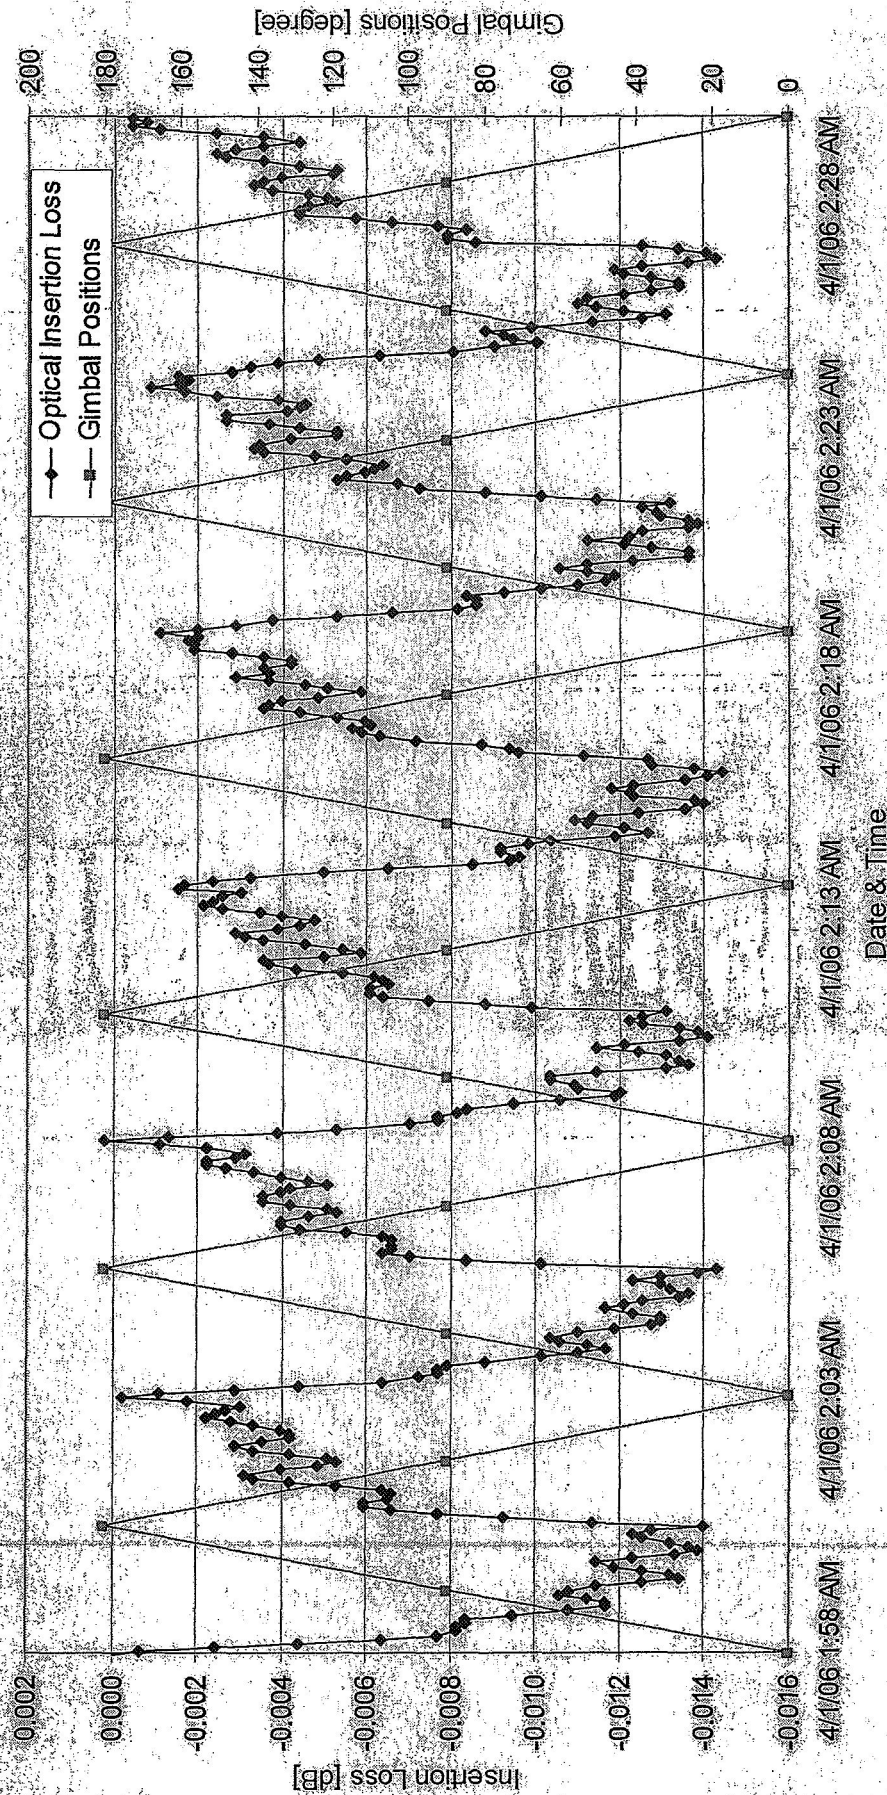


June 22, 2006

NASA Goddard Space Flight Center



Laser Ranging Radiation Prequal Test Results

The radiation test on 10-m long 200/220um fibers

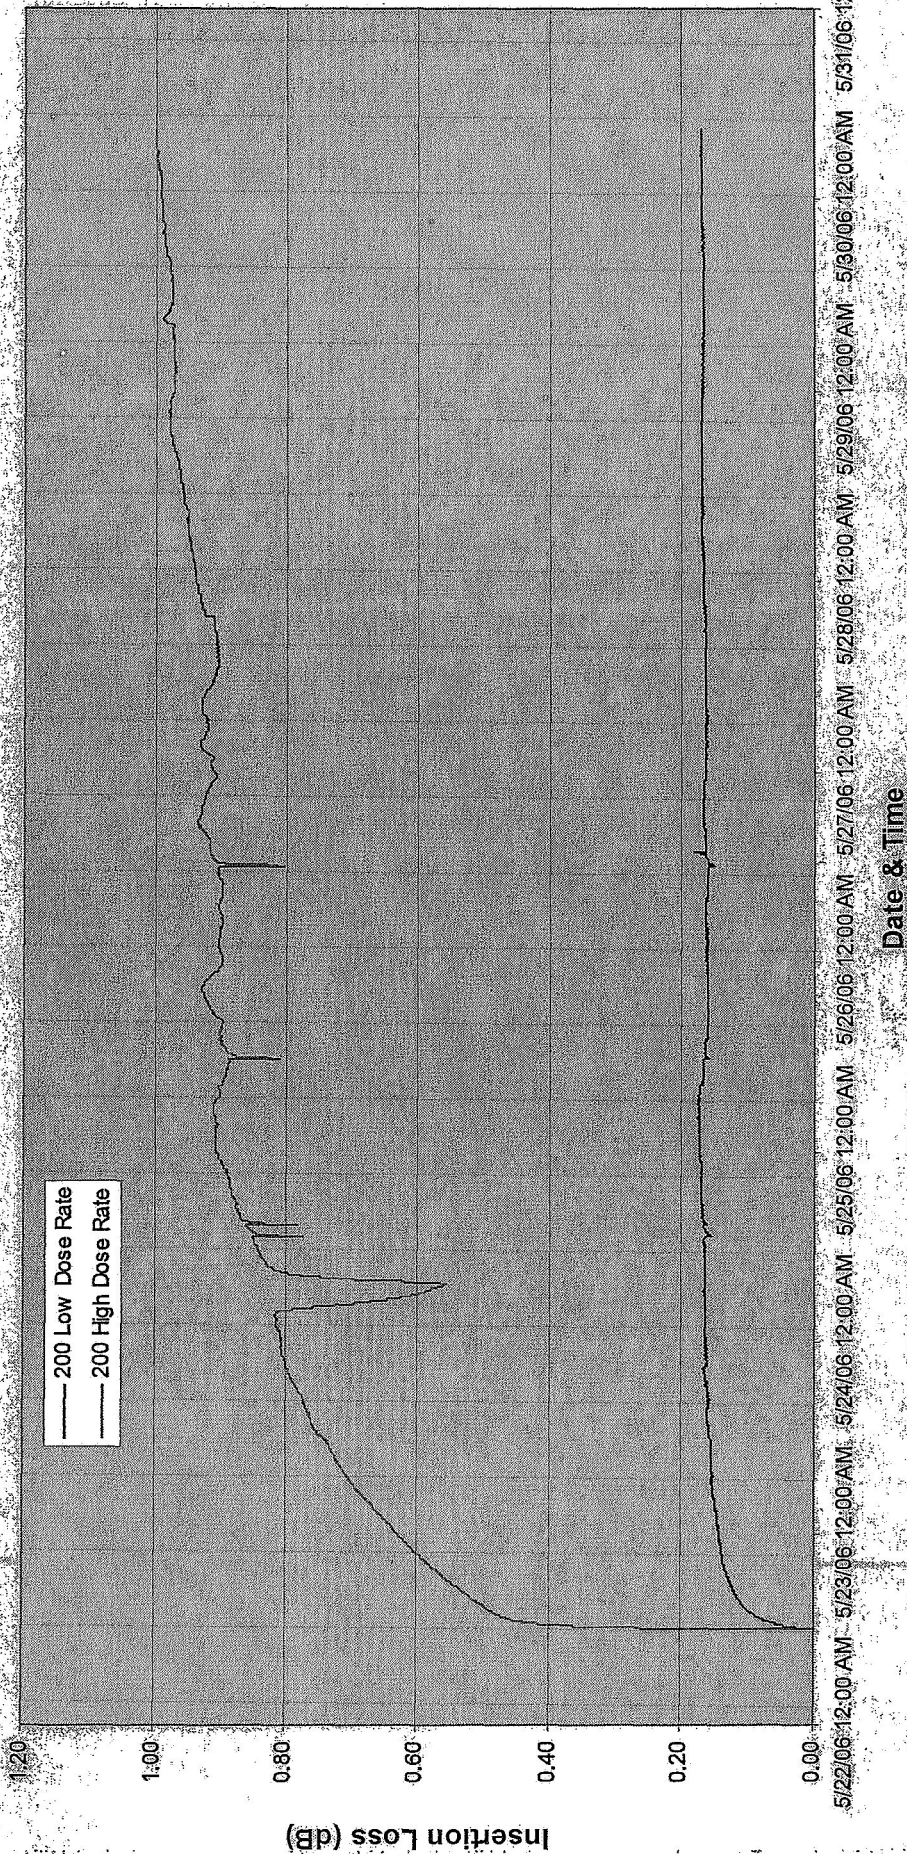

Hytel Diamond AVIMs boots- beyond 1 Mrad no changes visible.

June 22, 2006

NASA Goddard Space Flight Center





Lessons Learned - Terminations

Epoxy curing schedules for space flight applications

If too high a cure temperature is used for terminations Failures can occur if the operation temperature of application is low Germanium doped graded index multimode is very sensitive to stress induced cracking such as CTE.


Germanium doped graded index

- Atomic structure stress
- Concentration higher at core—CTE differences along cross section.
- Micro-cracks exist, internal structure and manufacturing.

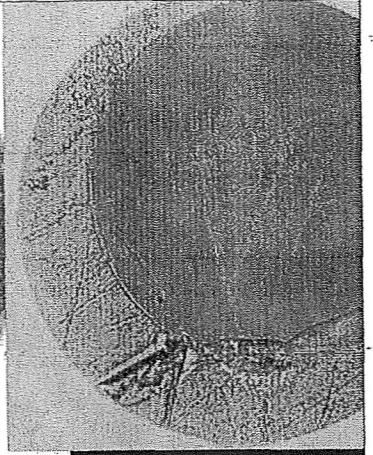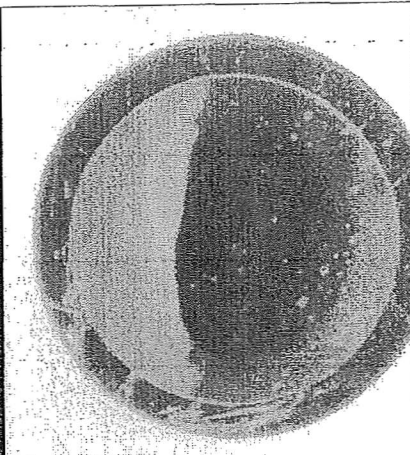

June 22, 2006

NASA Goddard Space Flight Center



Lessons Learned - Terminations

Polishing Processes



GSFC uses nothing larger than 5 micron lapping film.

Using too high of a grit on the lapping film can set up latent cracks.

Inspection and Cleaning

GSFC uses 200 X final inspection.

For especially Ge-doped Graded index fiber, avoid contamination

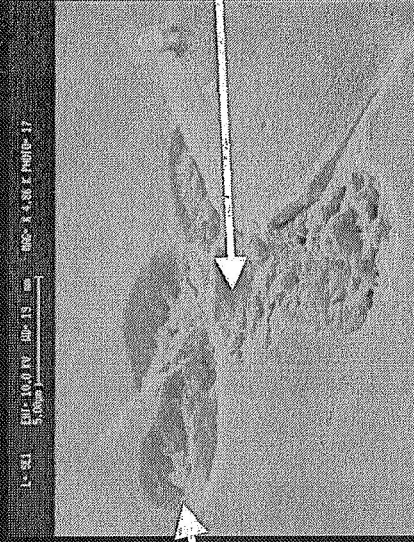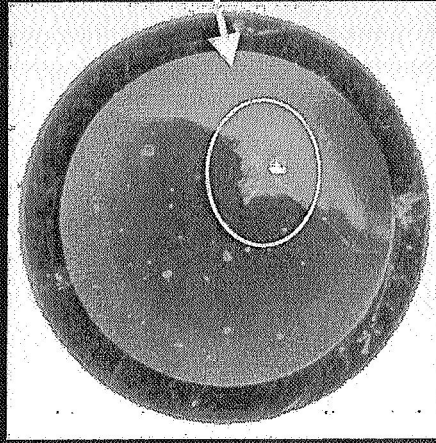

SEM images of contamination – Corrosion on fiber end face

June 22, 2006

NASA Goddard Space Flight Center



Conclusion

"Qualification and Issues with Space Flight Laser Systems and Components" M. Ott, D. B. Coyle, J. Canham, H. Leidecker, Jan 26, 2006 SPIE Photonics West, Vol. 6100.

"Space Flight Requirements for Fiber Optic Components; Qualification Testing and Lessons Learned," Photonics Group, April 2006, SPIE Europe Vol. 6193

SPIE Optics and Photonics session on Photonics for Space Environments XI To be presented in San Diego USA, Aug 2006.

- Current Activities in the Photonics Group
- Qualification of MTP and Ribbon Cable Assemblies for Space

June 22, 2006

NASA Goddard Space Flight Center



Thank you for your attention.

For more information please visit the website:
misspiggy.gsfc.nasa.gov/photronics



NASA GSFC Code 562 Photronics Group

June 22, 2006

NASA Goddard Space Flight Center