

High Temperature VARTM of Phenylethynyl Terminated Imides

Sayata Ghose¹, Roberto J. Cano², Kent A. Watson¹, Sean M. Britton², Brian J. Jensen²,
John W. Connell², Helen M. Herring³ and Quentin J. Linberry⁴

¹National Institute of Aerospace, Hampton, VA 23666-6147

²NASA Langley Research Center, Hampton, VA 23681-2199

³Lockheed Martin Engineering & Sciences Company, Hampton, VA 23666

⁴NASA GSRP at Western Kentucky University, Bowling Green, KY 42101

Abstract

Fabrication of composite structures using vacuum assisted resin transfer molding (VARTM) is generally more affordable than conventional autoclave techniques. Recent efforts have focused on adapting VARTM for the fabrication of high temperature composites. Due to their low melt viscosity and long melt stability, certain phenylethynyl terminated imides (PETI) can be processed into composites using high temperature VARTM (HT-VARTM). However, one of the disadvantages of the current HT-VARTM resin systems has been the high porosity of the resultant composites. For aerospace applications, the desired void fraction of less than 2% has not yet been achieved. In the current study, two PETI resins, LaRC PETI-330 and LaRC PETI-8 have been used to make test specimens using HT-VARTM. The resins were infused into ten layers of IM7-6K carbon fiber 5-harness satin fabric at 260 °C or 280 °C and cured at 371 °C. Initial runs yielded composites with high void content, typically greater than 7% by weight. A thermogravimetric-mass spectroscopic study was conducted to determine the source of volatiles leading to high porosity. It was determined that under the thermal cycle used for laminate fabrication, the phenylethynyl endcap was undergoing degradation leading to volatile evolution. By modifying the thermal cycle used in laminate fabrication, the void content was reduced significantly (typically ~ 3%). Densities of the composites were determined using a density gradient column and the glass transition temperatures of the cured composites were measured by dynamic mechanical analysis. Photomicrographs of the panels were taken and void contents were determined by acid digestion. The results of this work are presented herein.

This paper is work of the U. S. Government and is not subject to copyright protection in the U.S.

Keywords: phenylethynyl terminated imides, VARTM, voids, acid digestion

Corresponding author: Sayata Ghose, sayata.ghose-1@nasa.gov, 1-757-864-2094

1. Introduction

Due to their excellent physical and mechanical properties, aromatic polyimides are finding use in aerospace applications. Polyimide composites are very attractive for applications that require a high strength to weight ratio and excellent thermal stability. Recent work at NASA Langley Research Center (LaRC) has concentrated on developing new polyimide resin systems for advanced aerospace applications that can be processed without the use of an autoclave. Researchers have developed several polyimides from various aromatic diamines and dianhydrides that can be melt processed into coatings, adhesives, composites and films. Controlled molecular weight imide oligomers containing phenylethynyl groups [phenylethynyl terminated imide (PETI), e.g. PETI-8, PETI-330] exhibit exceptional processability during fabrication of neat resin moldings, bonded panels and composites. LaRC PETI-330 is a low molecular weight imide oligomer ($M_n \sim 1250$ g/mole with end caps) with a low, stable melt viscosity and a glass transition temperature (T_g) of around 330°C after curing for 1-2 h at 371°C . It was prepared using 2,3,3',4'-biphenyltetracarboxylic dianhydride, 1,3-bis(4-aminophenoxy)benzene and 1,3-phenylenediamine and endcapped with phenylethynylphthalic anhydride. The resin was designed specifically for resin transfer molding (RTM) and resin infusion (RI) processing and has been used for making composites by RTM and RI. PETI-330 laminates exhibit excellent thermal and mechanical properties [1,2]. PETI-330 laminates have exhibited excellent retention of room temperature open hole compression strength and short beam shear strength after aging 1000 hr at 288°C [3]. LaRC PETI-8 is an aromatic polyimide ($M_n \sim 1125$ g/mole with end caps) based on 3,3',4,4'-biphenyltetracarboxylic dianhydride, a 50:50 molar ratio of 3,4'-oxydianiline and 1,3-bis(3-aminophenoxy) benzene, with 4-phenylethynylphthalic anhydride as the endcapping agent. PETI-8 has a T_g of around 300°C after curing for 1 hour at 371°C and produces excellent tensile shear strengths and flatwise tensile strengths when processed with vacuum bag pressure only [4], eliminating the need for costly autoclave processing. Composites were processed using standard and double-vacuum-bag process and mechanical properties including short beam shear strength, flexural strength and modulus were evaluated at various temperatures [5].

Vacuum assisted resin transfer molding (VARTM) process was developed as a variation of resin transfer molding (RTM) over ten years ago for application in commercial and military, ground-based and marine composite structures [6,7]. The upper tool of the matched metal mold used in RTM is replaced in the VARTM process by a formable vacuum bag material. Both transfer of the matrix resin and compaction of the part are achieved using atmospheric pressure alone. Flow of the resin into the part is improved through the use of a resin distribution medium [8]. The highly-permeable medium induces resin flow through the thickness of the part, reducing filling times. VARTM has shown potential to reduce the manufacturing cost of composite structures. In VARTM, the fibrous preform is infiltrated on a rigid tool surface contained beneath a flexible vacuum bag. Both resin injection and fiber compaction are achieved under pressures of 101.3 KPa or less. Studies have demonstrated the feasibility of the VARTM process for fabrication of void free structures utilizing epoxy resin systems with fiber volume fractions approaching 60% [9]. VARTM using vinyl ester resins have traditionally

yielded composites with low void contents as well and have found applications in the marine industry for making yacht hulls [10] and for rotorline wind turbine blades [11]. However, it should be noted that the focus so far has been on VARTM at room temperature. The Seemans Resin Infusion Molding Process (SCRIMP), patented by TPI Composites [8], is a vacuum infusion process using a high-permeability layer to rapidly distribute the resin on the part surface and then allow through-thickness penetration. The Controlled Atmospheric Resin Infusion Process (CAPRI) patented by The Boeing Company [12], is a SCRIMP variation where vacuum debulking and a reduced pressure difference is used to minimize thickness gradients and resin bleeding.

The CAPRI VARTM process has been extended to the fabrication of composite panels from polyimide systems developed at LaRC. Work has focused on processing various LaRC polyimides (PETI-330, PETI-8) by VARTM at *high temperatures*, hence forth referred to as HT-VARTM. In this case the resins are infused at temperatures above 250 °C, and cured at 371 °C. In HT-VARTM, resin flow lines, tools, sealants and bagging materials must be able to tolerate the high temperature processing cycle. Preliminary evaluation of these resins has shown that they exhibit the necessary melt flow characteristics for HT-VARTM processing, but the laminates typically have void contents greater than 7% by volume [13, 14]. The focus of this study has been to reduce the void content in composite parts and achieve sufficient fiber volume (>58%).

This paper focuses on the HT-VARTM processing trials carried out under several conditions by control of the process variables in an effort to reduce voids. Initial work focused on identifying the source of the volatiles leading to void formation. It was determined that due to the high temperature required for infusion and the low pressure, a small amount of degradation of the phenylethynyl groups was occurring leading to volatile by-products. By adjusting the processing cycle, void content was reduced to routinely achieve 3%. In an attempt to further reduce porosity, optimization of the cure cycle by introducing higher fidelity control of the temperature and pressure is underway.

2. Experimental

2.1 Materials

Two PETI resins were used for the HT-VARTM processing trials. PETI-8 was purchased from Imitec Inc., Schenectady, NY, USA and PETI-330 from Ube Chemicals Ltd, Japan.

2.2 Melt Rheology

Dynamic rheological measurements were obtained using an Advanced Rheometric Expansion System (ARES) Rheometer from Rheometrics, Inc. The measurements were carried out under nitrogen atmosphere in an oscillatory shear mode using parallel plate geometry (30 mm diameter) at a heating rate of 4 °C/min from 100 to 371 °C. The top plate was oscillated at a variable strain and a fixed angular frequency of 10 rad/s while the lower plate was attached to a transducer that recorded the resultant torque. The as-received powders were press molded at room temperature (RT) into 2.54 cm diameter and ~ 1.5 mm thick disks. PETI-8 specimens were heated from 100 to 280 °C at 4 °C/min and held for 2 hours while the PETI-330 was held for 2 hours at both 260 °C and 280 °C.

Storage (G') and loss (G'') moduli were measured as a function of time during the temperature ramp. The minimum viscosity was identified from the measurements.

2.3 High Temperature VARTM

The HT-VARTM set-up utilized in this work is shown in Figure 1. A 1.27 cm thick steel plate was utilized as a tool. Three holes were drilled and tapped into the plate to provide one resin inlet and two vacuum outlets. Aluminum (Al) screen material was utilized as the flow medium. Polyimide bagging material and high temperature sealant was used to seal both an inner bag that contained ten layers of 5-harness IM7-6K carbon fiber perform (unsized), five layers of Al screen flow media, Release Ease™ fabric, a breather material, and an outer bag that provided redundancy should a leak occur in the inner bag after infiltration.

During the initial runs only one oven containing both the resin pot and the tool was used. The tool was placed in an air circulating oven and heated to 280 °C. The resin pot was heated in a separate oven to melt the resin powder and cooled to create a seal for the inlet tube. It was then placed in the air circulating oven once the tool had reached temperature to minimize time-at-temperature effects on the resin. The resin pot was then plumbed to the tool and allowed to heat in the same oven. Vacuum was pulled on both the inner bag (101.6 kPa or 30" of Hg) and the resin pot (101.6 kPa or 30" of Hg) as the resin was heated in order to degas the resin and remove air from the preform. Infiltration began when the resin reached 280 °C, corresponding to its minimum viscosity, by releasing the vacuum on the resin pot to 50.8 kPa (15" of Hg) and allowing the pressure differential to push the resin into the preform. Once the panel was filled, the entire system was then cured at 371 °C for one hour.

To improve the process, two ovens connected to each other by a heated tube were used. The resin pot was placed in the first oven and heated to the injection temperature under full vacuum. The tool was heated separately in the second oven under full vacuum, to the injection temperature. Upon reaching the infusion temperature, the resin was degassed for 5 minutes, vacuum on the pot was released to 50.8 kPa and the connecting valve between the pot and heating tube was opened to allow the resin to flow till infusion was complete. The connecting tube comprised of a 0.64 cm ($\frac{1}{4}$ ") diameter stainless steel tube encased in a 1.27 cm ($\frac{1}{2}$ ") diameter tube around which the heating coil was wrapped. The connecting tube was kept at a temperature 2-5 °C above the infusion temperature. Once infusion was completed, the connecting valve was shut off and the cure cycle was started.

2.4 Density Gradient Column

In order to construct a density gradient column (DGC) of desirable range, two separate solutions of ZnCl/H₂O with densities of ~1.278 g/cc and ~1.376 g/cc, respectively, were mixed. A jacketed glass column was filled with the two miscible solutions to create a linear density gradient, according to ASTM D1505 Method C. Calibrated density beads (American Density Materials Inc.) were then introduced into the column, using a slowly descending basket to prevent turbulence in the column, and were allowed to stabilize in the column overnight. The positions of the calibrated beads were recorded and plotted

versus their known densities to show that a linear gradient of range 1.3000-1.3338 g/cc had been established.

The samples of unknown density were then introduced into the column and allowed to stabilize overnight. Their respective positions were then measured, and their densities calculated, using the following calculation found in ASTM D1505:

$$\text{Density at } x = a + [(x - y)(b - a)/(z - y)]$$

where:

- a and b = densities of the two calibrated beads,
- y and z = distances of the two calibrated beads in cm, respectively, bracketing the sample from an arbitrary level, and
- x = distance of sample above the same arbitrary level.

Densities are reported in grams per cubic centimeter.

2.5 Thermal Characterization

2.5.1 Differential Scanning Calorimetry

Differential scanning calorimetry (DSC) was performed on cured samples in a sealed aluminum pan using a Setaram Instrument DSC 131 thermal analyzer at a heating rate of 20 °C /min with the T_g taken as the mid-point of inflection of the differential heat flow (ΔH) versus temperature curve.

2.5.2 Dynamic Mechanical Analysis

In order to obtain material stiffness as a function of temperature, dynamic mechanical analysis (DMA) was performed on all solid polymer samples where DMA provided a measure of dynamic storage modulus over a range of temperatures [15]. The bar samples were cut to be between 5 and 15 mm in width and 25 and 30 mm in length to conform to the dimensional limits required for the test fixture, using a calibration standard template provided with the DMA apparatus (DMA Q800 by TA Instruments). The average thickness for each bar sample was based on three separate measurements, taken along the length of the specimen with a digital micrometer, not to exceed 5 mm. A sample was mounted across the 3-point bend supports, and the moveable clamp placed in position at the center of the bar. The furnace was then sealed, and the sample allowed to equilibrate at 25 °C. The sample was then heated at 3 °C/min to 400 °C. All samples were tested with an applied preload force of 0.5 N, using a dynamic force with a single frequency oscillation of 1 Hz and amplitude of 20 μm . The storage modulus for each run was calculated as a function of increasing temperature, using thermal analysis software included with the DMA apparatus.

2.5.3 Thermogravimetric Analysis-Mass Spectroscopy, Pyrolysis-Gas Chromatography/Mass Spectroscopy

Thermogravimetric analysis-mass spectroscopy (TGA-MS) experiments were conducted on uncured powder samples using a standard TGA-MS setup with a total purge flow of 100 mL/min of ultra high purity (UHP) nitrogen gas. The TGA portion was ran on a TA Instruments 2950 TGA with an evolved gas furnace and the MS portion was ran on a Pfeiffer ThermoStar mass spectrometer with a mass range of 1-200 amu. The samples were held at room temperature for 30 minutes to evacuate all residual air. The samples were subsequently heated at 20 °C/min to 280 °C with a 45 minute isothermal hold. This

was followed by the experimental segment of interest: 5 °C/min to 371 °C with a 4 hour isothermal hold.

For Pyrolysis-Gas Chromatography/ Mass Spectroscopy (Pyrolysis-GC/MS) uncured powder samples were run in a CDS 5200 Pyrolyzer attached to a Varian GC/MS. The samples were heated according to the same temperature profile used in the TGA-MS experiments. The purge gas was helium. The only chromatogram obtained was for the species evolved during the second heating ramp and isothermal hold at 371 °C. The sample size was 2.5 mg.

In another set of experiments, instead of using a TGA, a horizontal tube furnace was employed to heat the samples. A 2.54 cm stainless steel tube with Swagelok connections on both ends was inserted into the tube furnace. Approximately 3g of uncured powder was loaded into an aluminum boat, which was inserted into the SS tube. UHP nitrogen flowing at 100 mL/min was connected to one side of the SS tube while the MS capillary probe was inserted into the other end. The MS scan range was 1-200 amu. The second heating rate was changed to 10 °C/min for these experiments, and the set points were about 8 °C lower than desired due to temperature variations between TGA and furnace. Therefore, weight loss/species evolution occurred at slightly lower times in the graphs.

2.6 C-Scan

C-scan of the composite panels were carried out using a 3 axis (x, y and z) Ultrasonic Scanner from SONIX Advanced Acoustic Solutions with a WIN IC (C-Scan) Version 4.1.0k software. A Panametrics transducer of 15 MHz/0.635 cm (0.25") diameter and 3.175 cm (1.25") focal length was used. A conventional ultrasonic pulse-echo C-scan method was used for detecting and characterizing delaminations in composites with a gain set to about 54 dB. The C-scan mode, however, has limitations because it provides only planar information and cannot display the depth of flaws in the thickness direction.

2.7 Acid Digestion

Acid digestion of cured composites was carried out following ASTM D3131. Each specimen was weighed to the nearest 0.0001 g and placed into a 100-ml beaker and 30 ml sulfuric acid was added. The beaker was placed on a hot plate and heated until the mixture started to fume; heating was continued for 5 hours. The beaker was then removed from the hot plate and 30 ml of 30% hydrogen peroxide was added down the side of the beaker to oxidize the matrix. The solution was allowed to cool; at this point the fibers floated to the top of the solution and the solution appeared clear. If the matrix is not completely digested, the solution may be filtered and reintroduced into the beaker to repeat the digestion procedure. Otherwise the contents were filtered into preweighed crucibles, washed with ~400 ml distilled water and rinsed with acetone to remove all moisture. The crucibles were dried in an oven at 160 °C for 4 hours, cooled to room temperature in a dessicator and weighed. Equations were used to calculate resin and fiber contents and volume fraction of voids using the obtained weights.

3. Results and Discussion

Figures 2 and 3 show the rheology behavior of the PETI resins used for VARTM runs. The complex viscosity (η^*) was measured as a function of time and temperature with a

temperature hold at possible infusion temperatures. Typically, a viscosity ~ 10 Poise or less is necessary for successful resin infusion during VARTM. But it is also important that the viscosity remains low for at least a couple of hours so as to give sufficient time for degassing and infusion. As evident from Figure 2, η^* for PETI-8 stayed between 1 and 5 Poise for 4 hours at 280 °C, providing a long processing window. However for the PETI-330, at the same temperature, η^* remained around 10 poise for only 20 mins hence reducing the window of operation (Figure 3a). Complex viscosity was then measured at 260 °C (Figure 3b) and it was found that although η^* was slightly above 10 Poise, it remained constant at that value for a much longer period of time. Based on these rheology curves, infusion temperature for PETI-8 was set at 280 °C and for PETI-330 at 262-266 °C.

Small pieces of void free samples obtained by RTM and VARTM were used to determine the densities of the resins using the density gradient column. For both PETI-8 and PETI-330, the resin density was found to be 1.31 g/mL.

For the first set of HT-VARTM runs, infusion was carried out at the chosen infusion temperature with the cure cycle started once infusion was completed. This involved heating the resin from the infusion temperature to 371 °C at 2.77 °C (5 °F)/min and curing at that temperature for 1 hour. The void content of the composite panels obtained were determined by photomicrographs and acid digestion. Figure 4 shows the micrographs of the two PETI resins. Using acid digestion, it was found that PETI-8 had a void content of 6.7 % while that of PETI-330 was 7.5%.

Based on the initial set of data, several approaches to reduce the void content were investigated. TGA/MS experiments were conducted in an attempt to identify volatile species and their source. HT-VARTM processing trials were conducted varying the processing parameters such as vacuum level, degassing time, and the temperature cycle.

To study possible resin degradation, TGA-MS was carried out on PETI-330. Water, carbon dioxide, toluene, benzene and benzaldehyde were evolved during the ramp from infusion temperature to cure temperature and subsequent hold. Pyrolysis-GC/MS data also confirmed the release of benzene and toluene. Also several nitrogen containing compounds were detected. Results from the tube furnace experiments showed that as in the TGA-MS experiments, benzene, toluene, water, and carbon dioxide evolved during the second ramp. They also evolved during the first ramp. With the larger sample size used in this experiment, benzonitrile, benzaldehyde, and styrene were also detected during both ramps. Newly detected species also include diphenylmethane, 1,2-diphenylethylene, and 1-methyl-2-pyrrolidinone (NMP). These species evolved only during the ramp to 371 °C. These chemical species appear to be evolving due to minor degradation of the phenylethynyl endcaps with the exception of NMP which is the solvent used in the synthesis of PETI-330. During these experiments, approximately 0.5-1% of weight was lost, but this leads to a significant volume of gas in a closed system. It appears that this degradation occurs predominately when the pressure is low. In previous studies involving laminate fabrication by RTM, the high pressure (1379 kPa) used during RTM would effectively suppress void formation and void-free panels were made [3].

However, in VARTM, the pressure differential is only 50.8 kPa (15”) which is apparently not enough to fully suppress evolution and volatilization of these low molecular species.

Researchers at the University of Delaware have conducted several experiments on room temperature VARTM of vinyl ester and other similar resins [16,17]. They reached a conclusion that the root cause of void formation was the vaporization of the components of the resin due to the application of the vacuum resulting in the partial pressure drop within the control volume. Their work has shown that effective control of the vacuum on the tool leads to a reduction of voids. Based on this work, for certain VARTM runs, the tool was not kept at full vacuum but at ~60 kPa after the infusion was completed. However, upon acid digestion of the obtained specimen, no reduction in void content was observed. Attempts were also made to increase the degassing time, but this hindered the infusion of the resin by reducing the processing window. Even though degassing times up to 30 minutes were tried, it was found that it made no difference when the degassing time was 5 minutes. Another attempt at process optimization was to wash the neat resins (PETI-8 and PETI-330) with various solvents like methanol, isopropanol or acetone in an attempt to remove low molecular weight components from the resin that may contribute to void formation. Typically about 10% by weight of the resins was removed by these washings. Rheology carried out on these solvent washed samples found that the viscosity was increased by 1-2 orders of magnitude due to the removal of lower molecular weight species. The results show the importance of the contribution of low molecular weight species to melt flow behavior.

The final set of process optimization tests involved modification of the cure cycle. Typically, once infused, the resin is heated directly to the cure temperature of 371 °C and held for 1 hour. Since the TGA-MS data showed that most of the resin degradation occurred during this stage of the process, curing the resins at lower temperatures but for a longer time was studied. Figure 5 shows the images of the resin when cured in a vacuum oven under different cure cycles. In each case, the resin was heated from room temperature to 280 °C, held there for 90 minutes and then ramped to 310 °C and held there for 2, 4 or 6 hours. As seen in Figure 5a, when the resin was cured at 371 °C, numerous voids are present. However, when the cure was carried out at a lower temperature and for a longer time, 4 hours in case of Figure 5b and 6 hours in case of 5c, the porosity decreased. DSC was also carried out on these samples to assess the extent of cure and the cured T_g values are given in Table 1. It is evident from the values that at 4 hours, the resin was not fully cured and had a lower T_g . Based on this data, the resin was cured at 310 °C for 8h instead of the traditional 1h cure at 371 °C. A second approach would be to stage the cure cycle - cure the resin at 310 °C for 8h and then take it to 371 °C and cure for 1h.

VARTM runs on the PETI resins were then carried out based on the modified cure cycles. In order to have better control of the processing parameters, the two-oven set up was used. PETI-8 was infused at 280 °C after degassing at that temperature for 5 minutes. Typically, infusion took about 20 minutes and after 1h the inlet valve connecting the pot to the tool was shut off and the cure cycle started. After an 8 hour cure at 316 °C, the sample was cooled down to room temperature and taken out of the tool. The panel was C-

scanned and then cut into specimens for photomicrography and acid digestion. Figure 6 shows the C-scan of the panel and the photomicrograph of one section. Acid digestion yielded a void content of 3.3% with a fiber volume of 57 %.

For the PETI-330 resin, similar processing conditions were followed. The only difference was the infusion temperature of 260 °C instead of 280 °C and cured at 310 °C instead of 316 °C. A second HT-VARTM run with a staged cure cycle was also carried out. In this cycle the resin was infused at 260 °C and then taken to 310 °C and held for 8 hours. After that it was taken to 371 °C and held for another 1 hour before being cooled down to room temperature. Figure 7 shows the photomicrographs of samples obtained from the two panels. It is apparent from the images that the void content was reduced in Figure 7(b). Acid digestion results further corroborated this observation – the first sample exhibited a void content of 5.5% and a fiber volume of 59% while the second sample had a void content of 3% and a fiber volume of 58%. It should be noted that the samples for acid digestion are typically taken from four corners of the panel as it is likely that the outermost regions of the samples would have the highest voids. For the panel in Figure 7(b), void content was also measured from two samples taken from the center of the panel and the value was 10% lower. Since in the case of PETI-330, staging the cure cycle produced better results, the HT-VARTM run was repeated with the two-stage cure cycle. Figure 8 shows the photomicrograph of this panel and the corresponding C-scan. The panel had a void content of 3.4 % with a fiber volume of 55%. DMA was carried out on the PETI-330 composites and a T_g of ~355 °C was obtained.

4. Summary

One of the toughest challenges faced in HT-VARTM is the reduction of void content to 2% or less required for aerospace applications. To date it has not been possible to fabricate composite panels with less than 2% voids from high temperature polyimide resins by conventional HT-VARTM in spite of the fact that these resins have been successfully fabricated into high quality panels using RI or RTM. The current research has focused on in-depth studies to determine the volatile source and when volatile evolution occurs followed by appropriate modification of the process cycle. Thermal degradation studies demonstrated that the phenylethynyl group in these resins undergoes slight degradation at the processing temperatures and pressures used for HT-VARTM. Process modification involved curing at a lower temperature but for a longer period of time, and staging the cure cycle resulted in composites with void content ~3%, substantially lower than any other reported polyimide composite panels made by HT-VARTM.

Future work will involve implementation of higher fidelity temperature and pressure controls for the HT-VARTM process followed by additional processing trials, as well as evaluation of mechanical properties of the composites.

5. Acknowledgement

The authors would like to thank James M. Baughman of Lockheed Martin for the photomicrographs, Janice Y. Smith and Joseph G. O'Donnell of NASA LaRC for cutting the panels and Alice Chang for acid digestion test. The authors also appreciate the valuable discussions and feedback they received from Dr. Joseph G. Smith Jr. and Dr. Tan H. Hou of NASA LaRC.

6. Figures

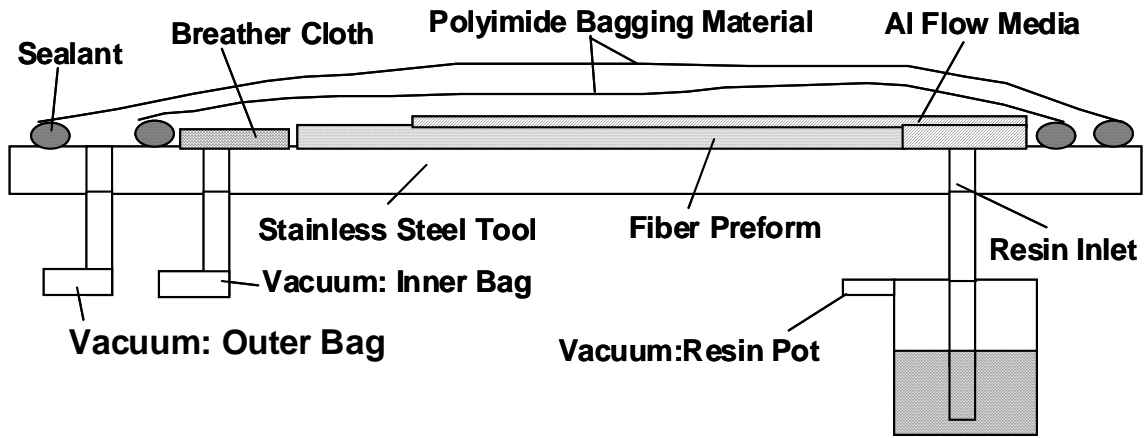


Figure 1: Schematic of HT-VARTM set up

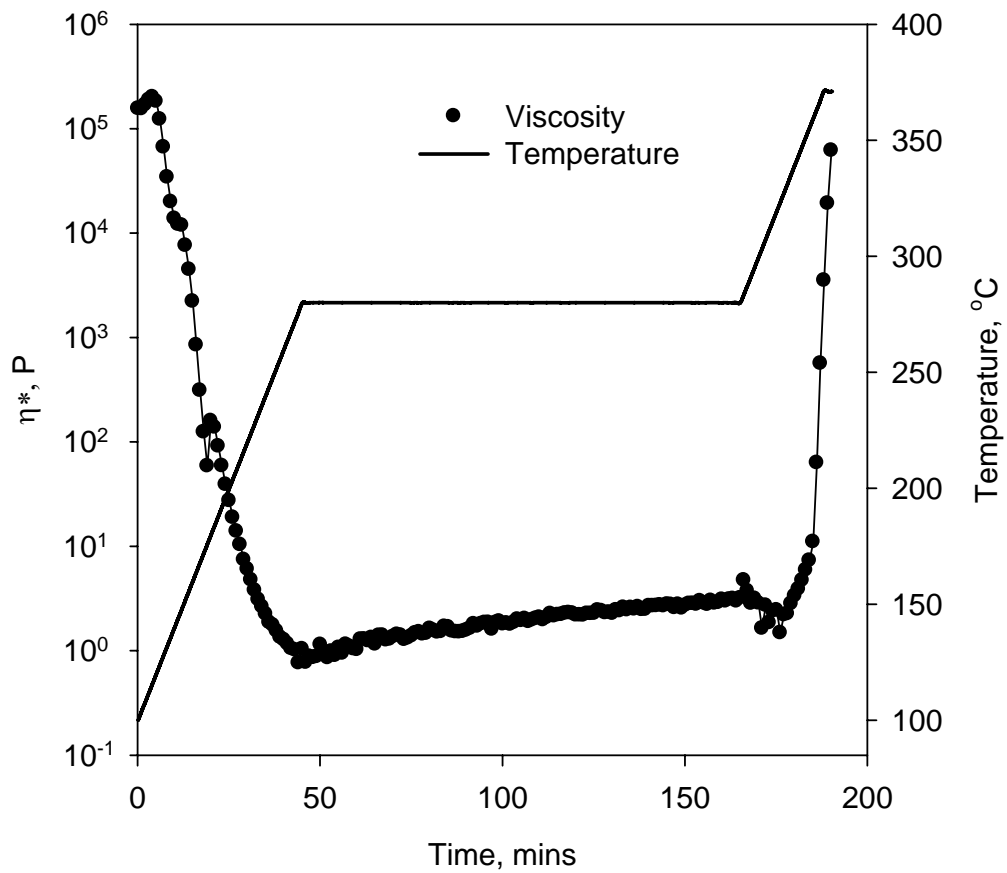


Figure 2: Rheology profile of PETI-8; 2 hour hold at 280 $^{\circ}\text{C}$

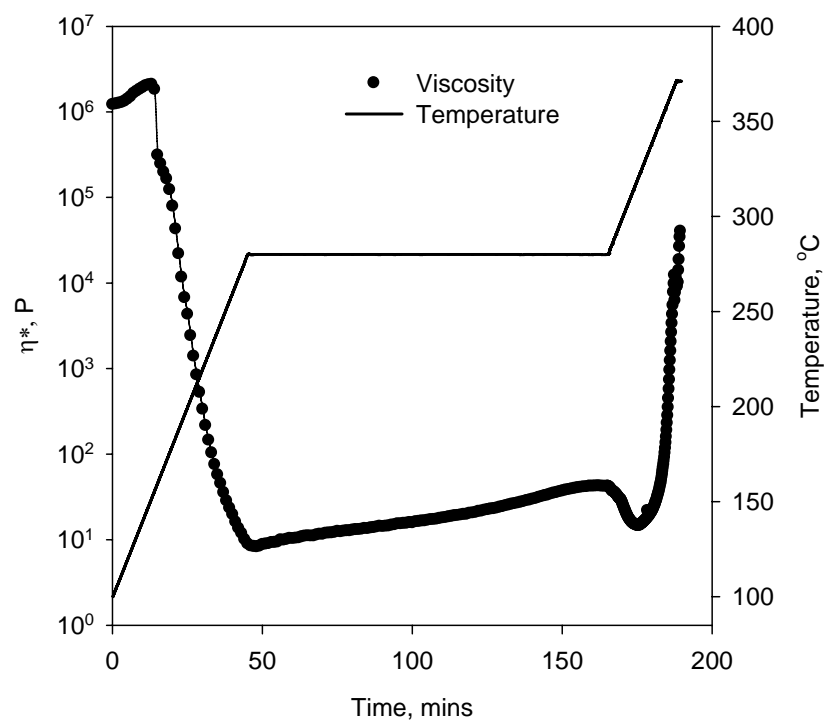


Figure 3a: Rheology profile of PETI-330; 2 hour hold at 280 °C



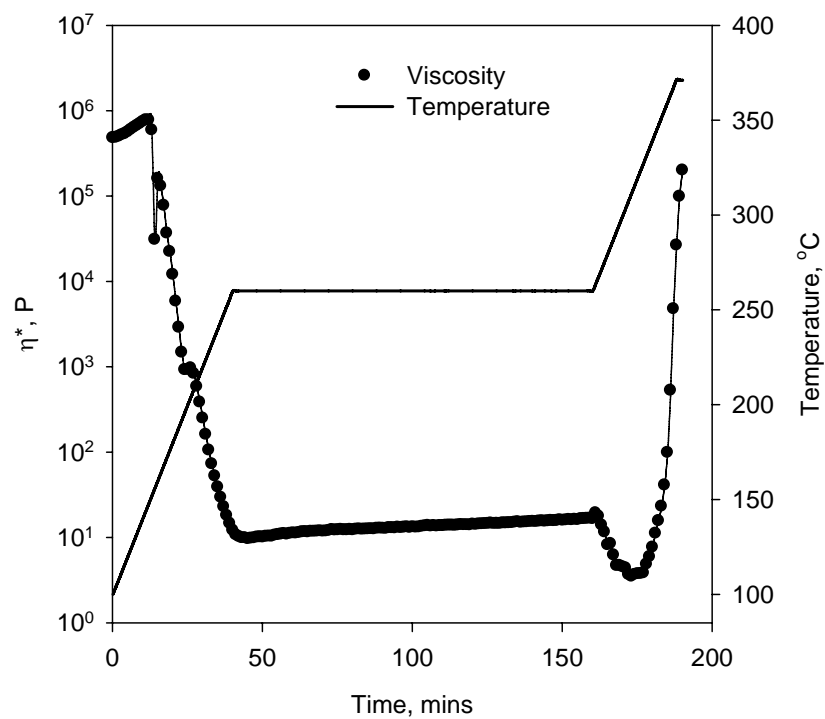


Figure 3b: Rheology profile of PETI-330; 2 hour hold at 260 °C

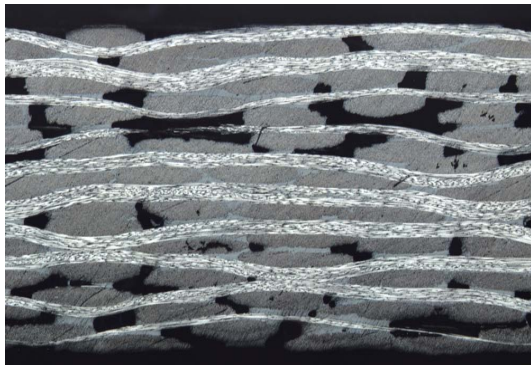


(a)

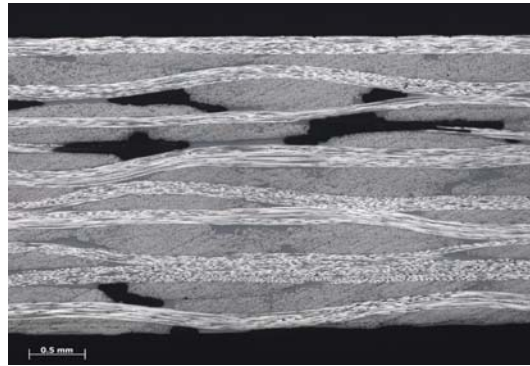

(b)


Figure 4: Photomicrographs of (a) PETI-330 and (b) PETI-8

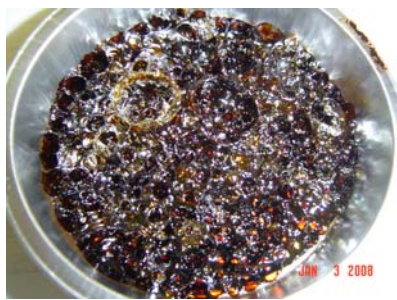

(a)



(b)

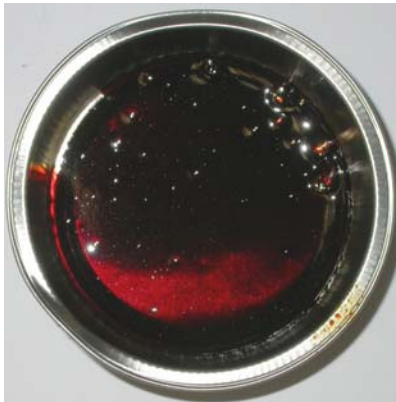

(c)

Figure 5: PETI-330 cure tests under vacuum;
 (a) 280 °C to 371 °C, 1 hour hold at 371 °C
 (b) 280 °C to 310 °C, 4 hour hold at 310 °C
 (c) 280 °C to 310 °C, 6 hour hold at 310 °C

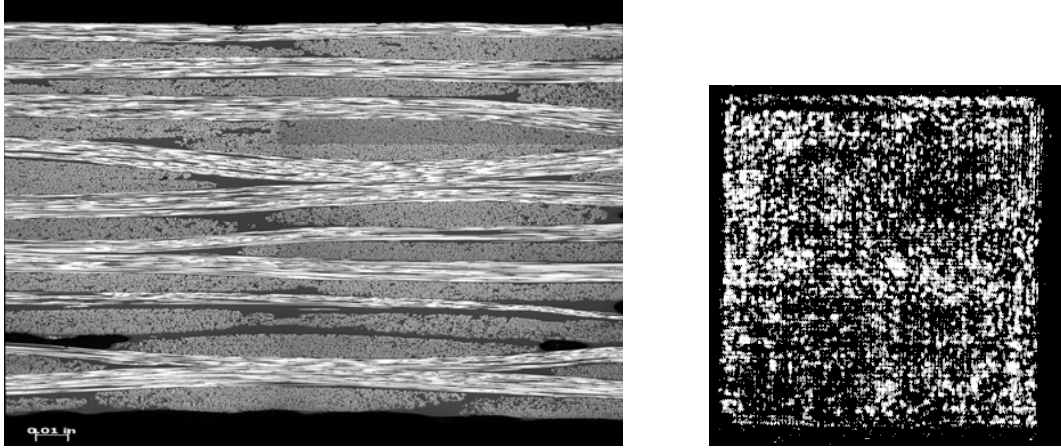


Figure 6: Photomicrograph of PETI-8 composite panel with 3.3% void content and its corresponding C-scan

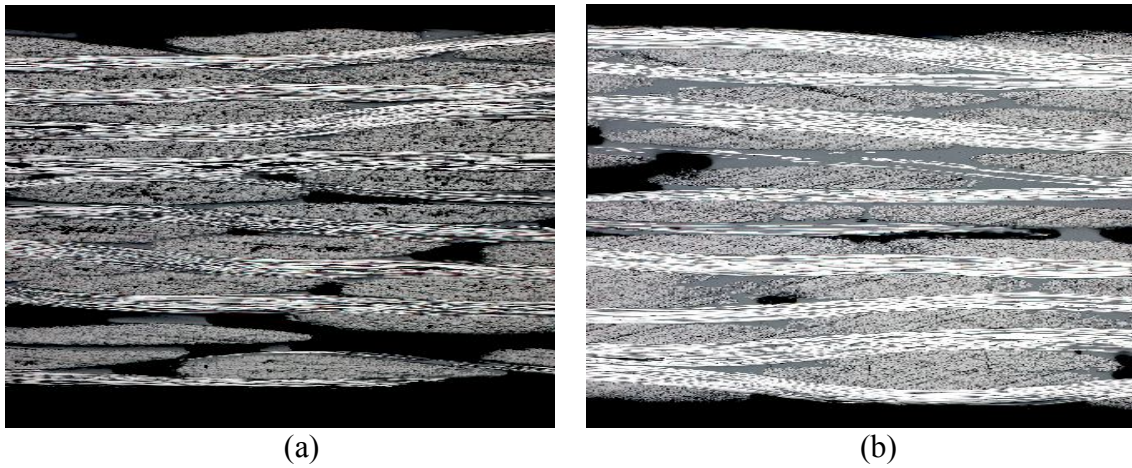


Figure 7: Photomicrograph of PETI-330; 8h at 310 °C (a), 8h at 310 °C followed by 1h at 371 °C (b)

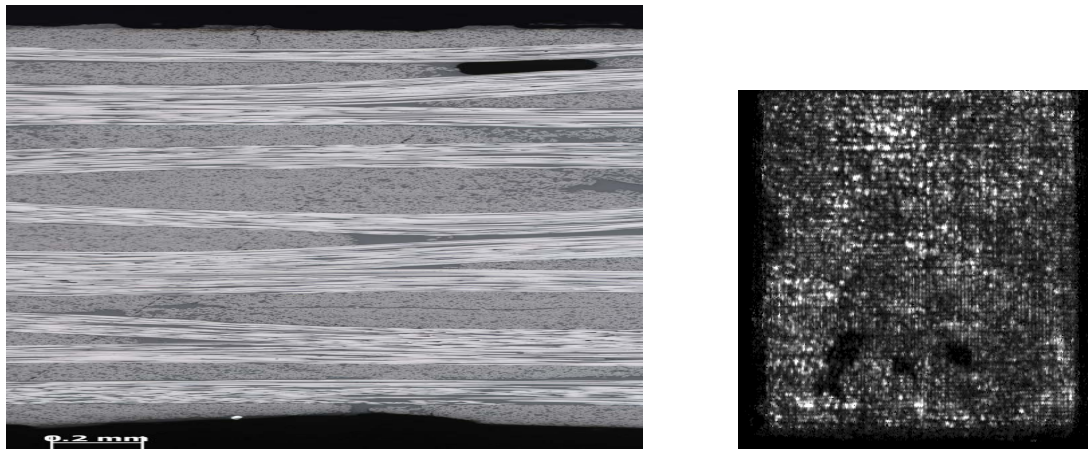


Figure 8: Photomicrograph of PETI-330 composite panel with 3.36 % void content and its corresponding C-scan

Table 1: T_g of PETI-330 samples at different cure cycles

Sample	Cured T _g (°C)
PETI-330, 280 °C to 371 °C, 1h hold at 371 °C	343
PETI-330, 280 °C to 310 °C, 4h hold at 310 °C	318
PETI-330, 280 °C to 310 °C, 6h hold at 310 °C	331

7. References

- 1 Criss JM, Arendt CP, Connell JW, Smith Jr. JG and Hergenrother PM, "Resin transfer molding and resin infusion fabrication of high temperature composites", SAMPE Journal, May/June 2000, 36(3), 32-41.
- 2 Smith Jr. JG, Connell JW, Hergenrother PM, Ford LA and Criss JM, "Transfer molding imide resins based on 2,3,3',4'-biphenyltetracarboxylic dianhydride", Macromol. Symp.2003, 199, 401.
- 3 Connell JW, Smith Jr. JG, Hergenrother PM and Criss JM, "High temperature transfer molding resins: laminate properties of PETI-298 and PETI-330", High Performance Polymers, 2003, 15(4), 375-394.
- 4 Jensen BJ, Lowther SE and Chang AC, "LARC PETI-8: Non-Autoclave Processable Adhesive", Proceedings of the 27th Annual Meeting of the Adhesion Society, February 15-18, 2004.
- 5 Hou TH, Cano RJ, Jensen BJ, Lowther SE, Chang AC and Kellen CB, "Processing and Properties of IM7/LARC PETI-8 Polyimide Composites", Sci. Adv. Matls and Proc. Eng. Ser., 2004, 49.
- 6 Lewit SM and Jakubowski JC, "Low cost VARTM process for commercial and military applications", Proceedings of the 42nd SAMPE International Symposium, 1997, 42, 1173.
- 7 Nguyen LB, Juska T and Mayes SJ, Proceedings of the AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics, and Materials Conference, 1997, 38, 992.
- 8 Seemann WH, 1990. U.S. Patent 4,902,215.
- 9 Thomas LR, Miller AK and Chan AL, "Fabrication of complex high-performance composite structures at low cost using VARTM", Proceedings of the 47th SAMPE International Symposium, 2002, 47, 570-672.
- 10 <http://www.polyworx.com>
- 11 <http://www.lightweight-structures.com>
- 12 Woods JA et.al., 2008, U.S. Patent 7,334,782.
- 13 Criss JM, Koon RW, Hergenrother PM, Connell JW and Smith Jr. JG, "High temperature VARTM of phenylethynyl terminated imide composites", Sci. Adv. Matl's. Proc. Eng. Tech. Con. Ser., 2001, 33, 1009-1021

- 14 Cano RJ, Grimsley BW, Jensen BJ and Kellen CB, "High temperature VARTM with NASA LaRC polyimides", 36th International SAMPE Technical Conference, San Diego, CA, November 15 - 18, 2004
- 15 Menard KP, Dynamic Mechanical Analysis: A Practical Introduction. 1999, Boca Raton: CRC Press LLC
- 16 Niggemann C, Song YS, Gillespie JW and Heider D, "Experimental investigation of the controlled atmospheric pressure resin infusion (CAPRI) process", Journal of Composite Materials, 2008, 42 (11), 1049-1061.
- 17 Saraswat MK, Heider D, Song YS, "A qualitative study of the void formation using ultrasounds during the VARTM process", SAMPE 2007 Technical Conference, Baltimore, MD.