



# Development of Meandering Winding Magnetometer (MWM<sup>®</sup>) Eddy Current Sensors for the Health Monitoring, Modeling and Damage Detection of High Temperature Composite Materials

Rick Russell, NASA KSC

Dr. David Jablonski, Dr. Andy Washabaugh,  
Dr. Yanko Sheiretov, Mr. Christopher Martin  
and Dr. Neil Goldfine, JENTEK Sensors, Inc.

32<sup>nd</sup> HIGH TEMPLE Workshop

February 2, 2012

Palm Springs, CA






# Agenda




- Overview of MWM<sup>®</sup> Technology
- Historical application – Space Shuttle RCC
- Recent Developments for COPVs
  - Health Monitoring
  - NDE
- High Temperature Development

- What is a Meandering Winding Magnetometer (or MWM)?
  - Primary winding is a linear construct that can be aligned with fibers
  - Secondary windings for sensing the response
  - Fabricated on thin flexible substrate creating a conformable sensor
  - Can be manufactured in various array configurations
  - Depth of penetration varies with sensor wavelength (spacing) and frequency
  - Vendor has capability to perform computer simulations

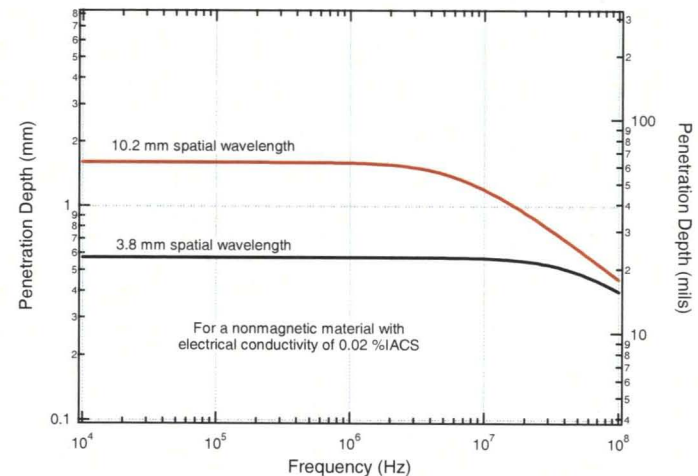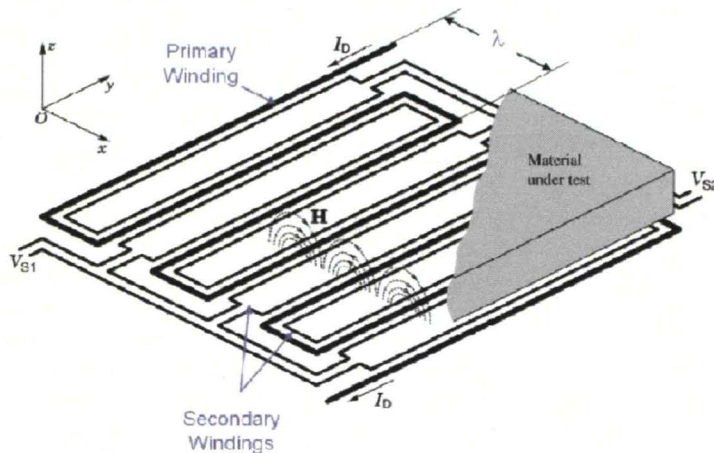


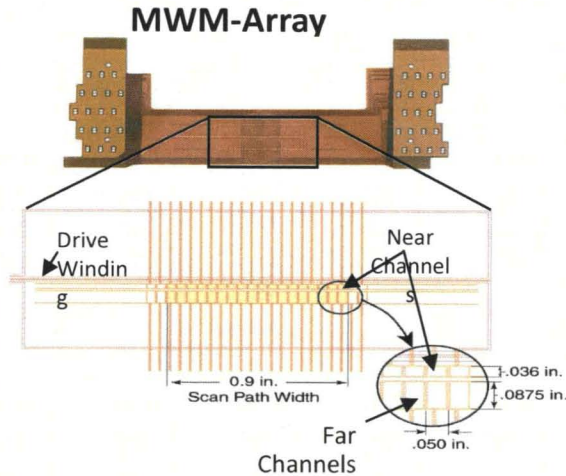

FA41  $\lambda \approx 480/190$

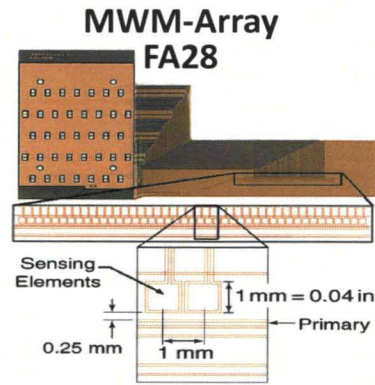


FA28  $\lambda \approx 150$  mils

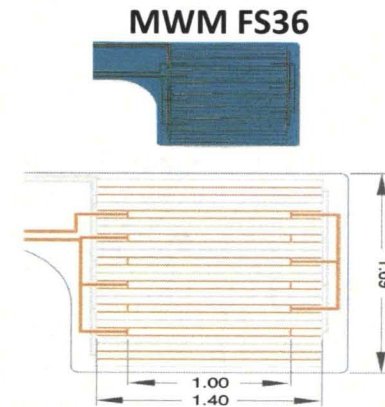


FS36  $\lambda \approx 400.0$

## JENTEK Grid Methods

### MWM and MUT Model

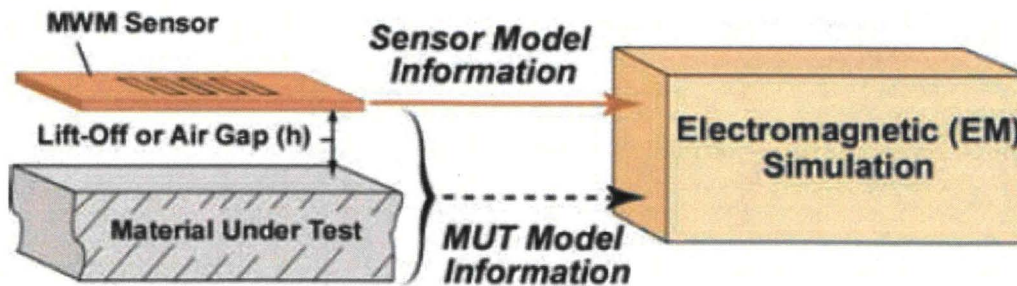


### Measurement Grid

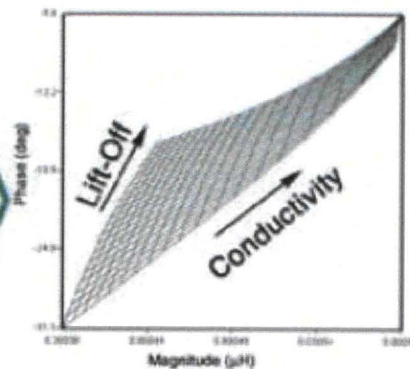





# MWMM Sensor Selection

- Magnetic field Decays exponentially with distance away from the sensor
  - Decay rate determined by skin depth at higher frequencies and sensor dimensions at lower frequencies
- Higher frequencies needed to induce significant eddy currents
- Large dimensions needed for thick composites

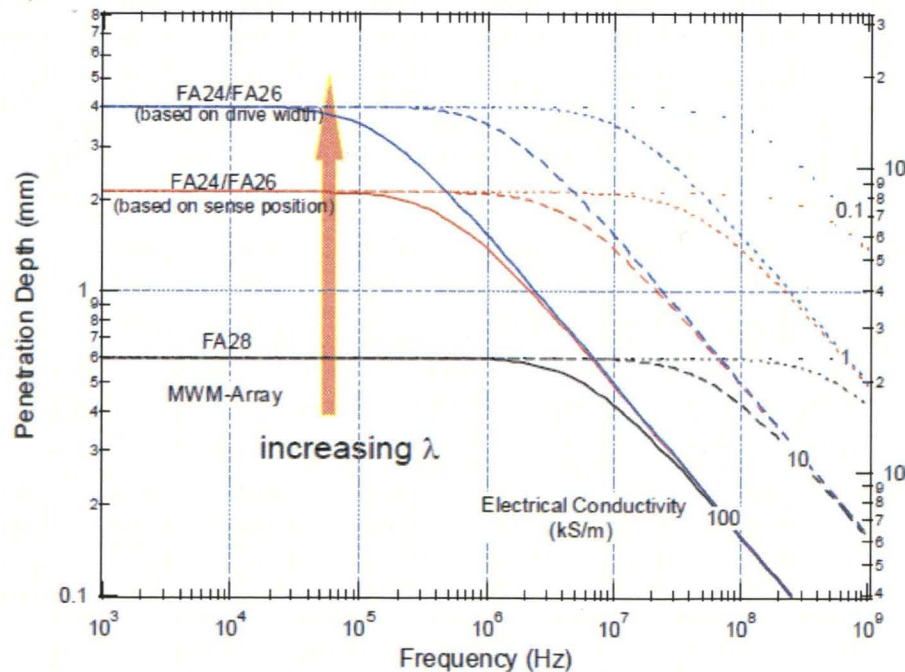



$$\text{Skin depth: } \delta = \sqrt{\frac{1}{\pi f \mu \sigma}}$$

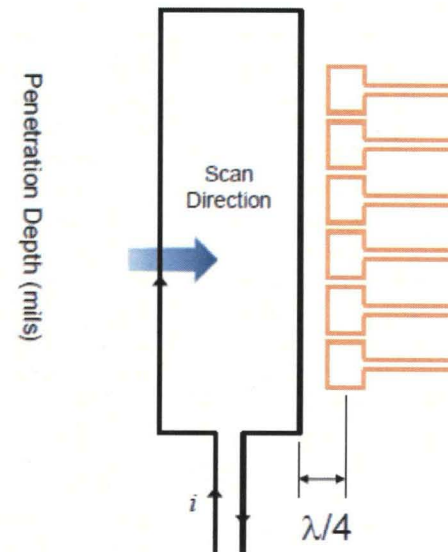

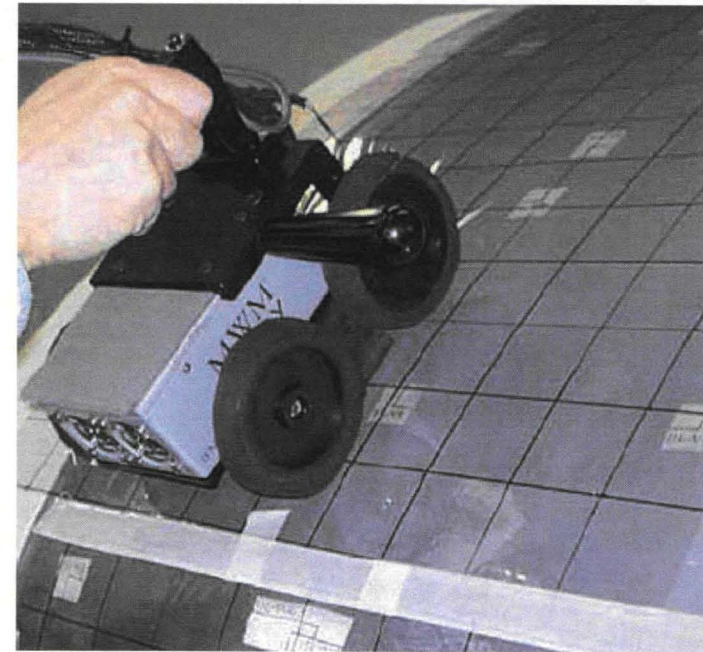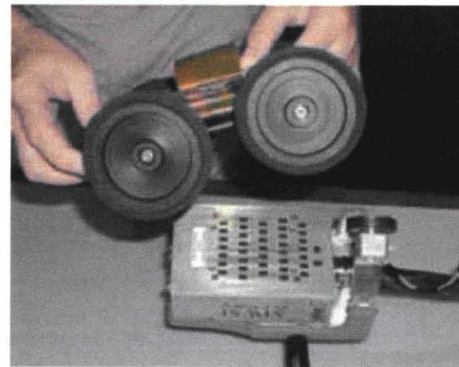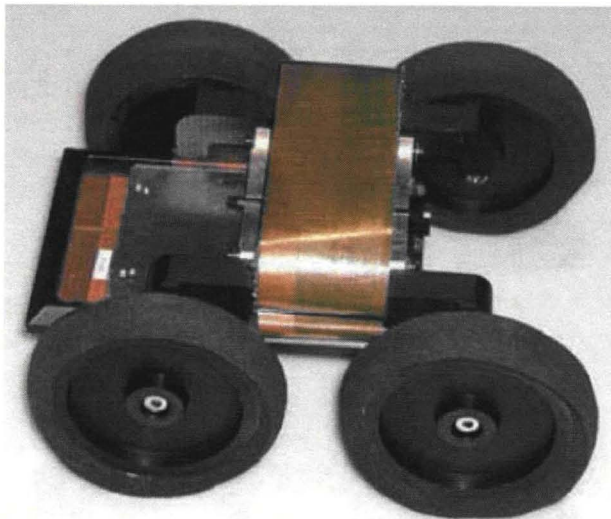

- Foam wheels protect surface
- Manual scanning for complex surfaces
- C-Scan images of wide areas built from multiple passes
- **Adapts automatically to varied curvatures**


# Application: Space Shuttle Orbiter RCC Panels

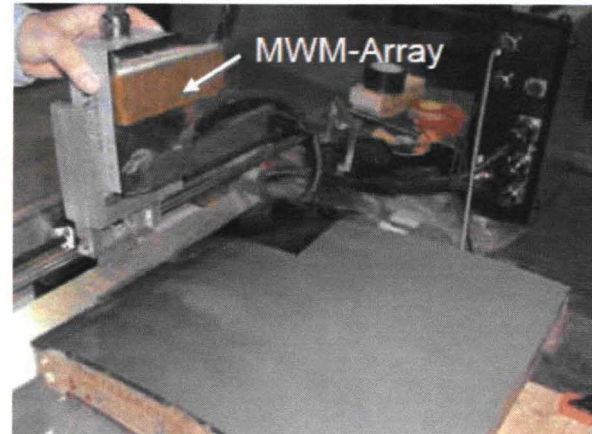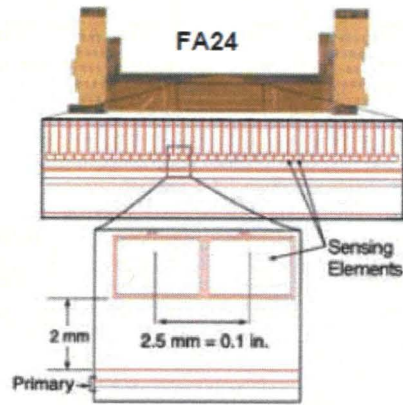


*Blind Test RCC Sample Provided by NASA Langley Research Center*

- Scan width = 37 sensing elements = 3.7 in.
- Scans performed at 1 in./sec.

**Effective Conductivity Image**

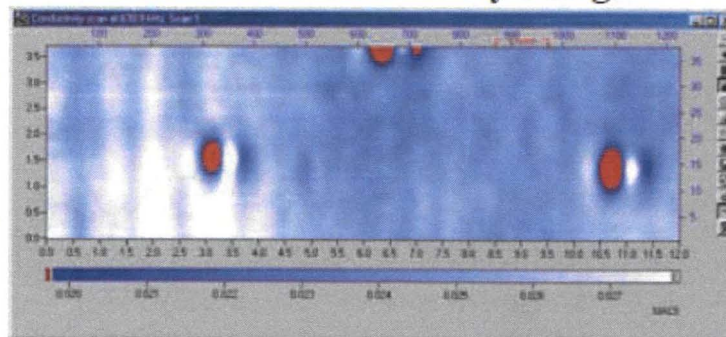





**Lift-Off Image**

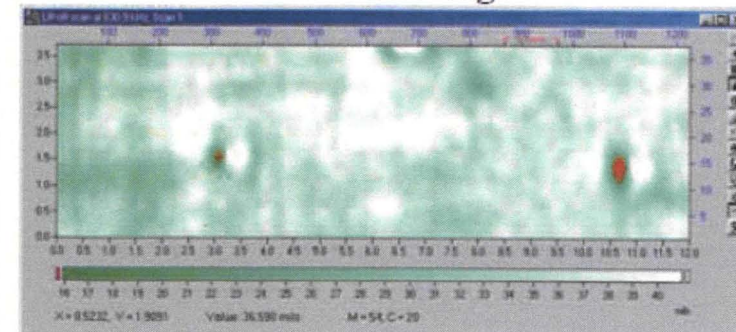

**Throughput: 3.7 in. x 12 in. scan in 12 seconds = 3.7 sq. in./sec**

# COPV Testing – Effect of Fiber Orientation

- Multiple fiber orientations in several different layers
- Orientation measurements with FS33
  - 15.8 MHz data indicated
- Limited penetration depth of MWM so outermost hoop (90°) layer barely visible

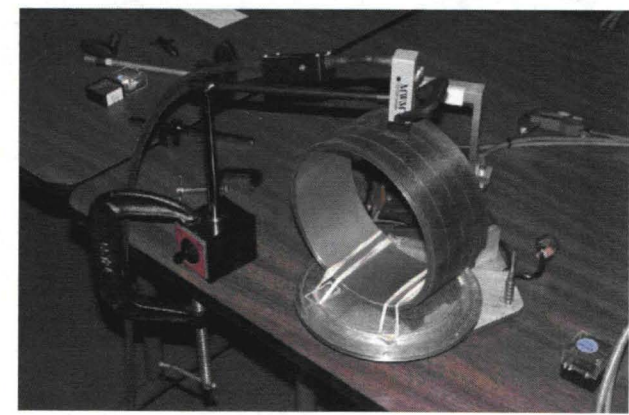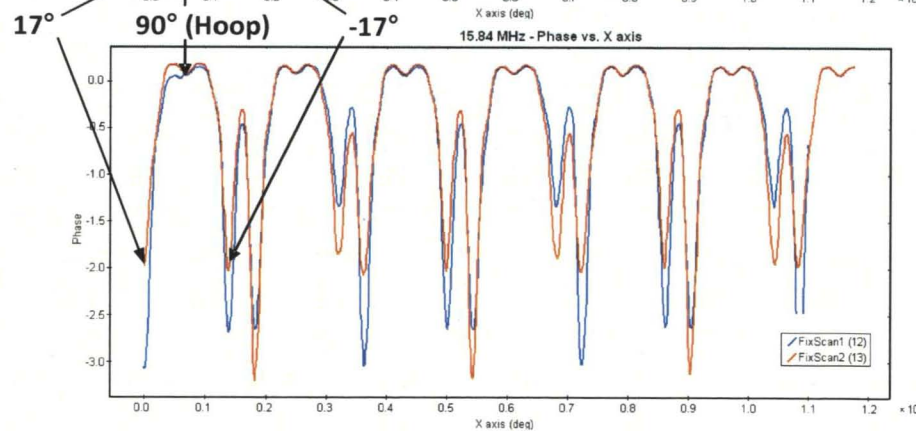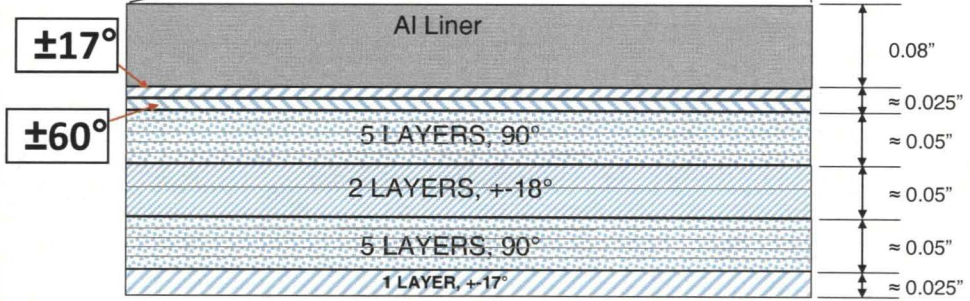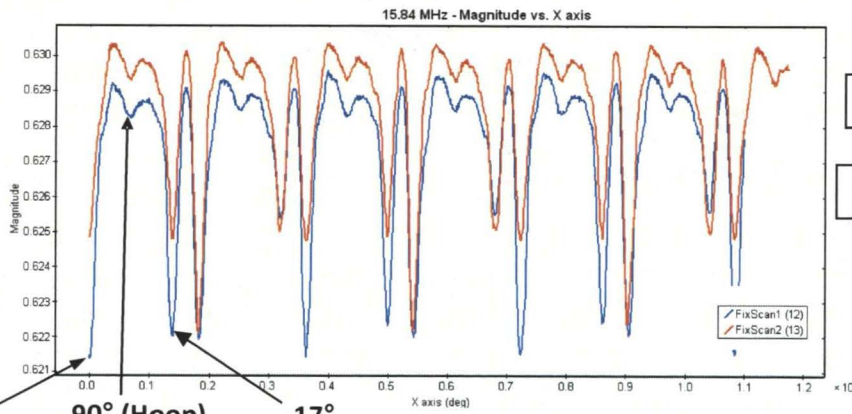




# COPV – Health Monitoring Proof of Concept Coupon Testing




Stresses produced by compressive loading of tapered wedges

- Coupon cut from center section of COPV (~4" wide)
- Two test fixtures designed
- Due to cutting only hoop direction could be measured
- Several different sensor designs and orientations were tested

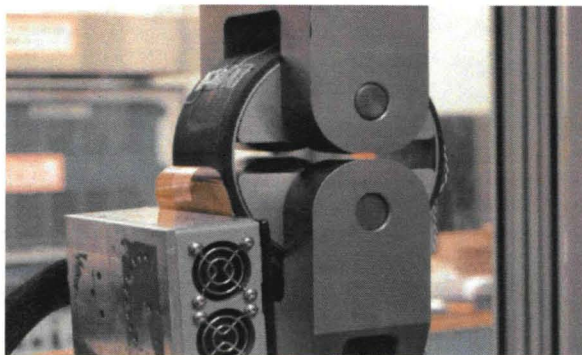

Stresses produced by tensile loading of specially design test fixture

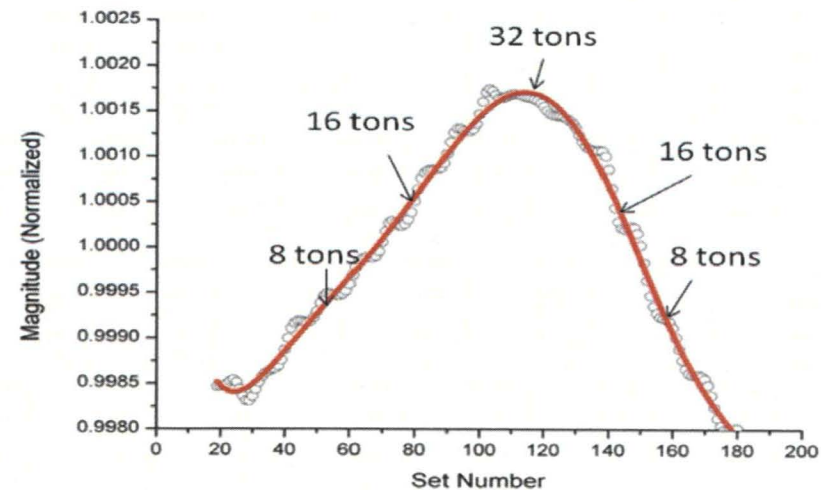




Example of results from compressive loading of tapered wedges test








# COPV – Health Monitoring Proof of Concept Hydrostatic Test



- Full COPV tested hydrostatically at KSC on February 5, 2011
- Vessel cycled to 8,000 psi and back to zero stopping at 2,000 psi increments
  - Pressure chosen to mimic MEOP
  - Estimated design burst pressure of COPV is 16,000 psi
- Based on coupon tests 3 sensor configurations were chosen
  - Different wavelength to obtain various depth of penetration
- Tests were performed with 3 sensor orientations
  - 90°, 60° and 17° to align sensor drive with fiber orientations

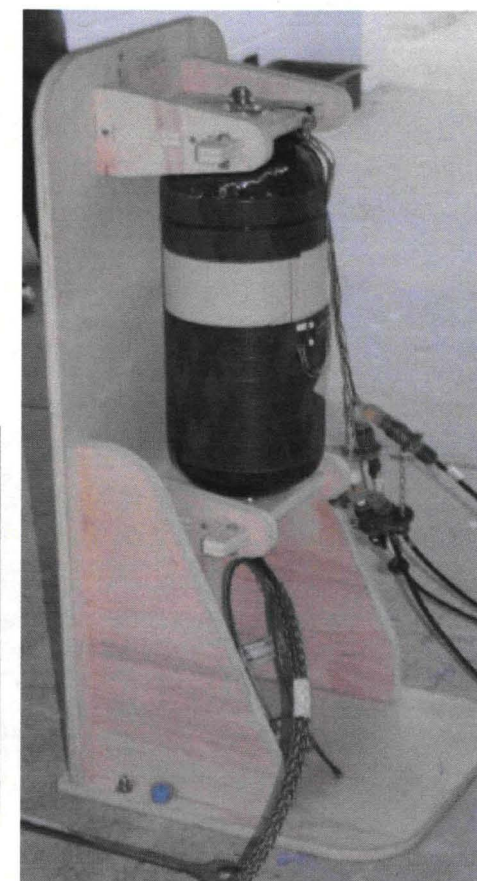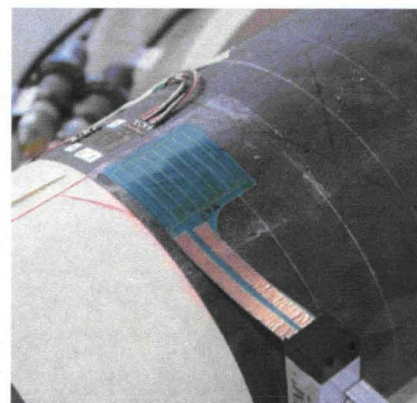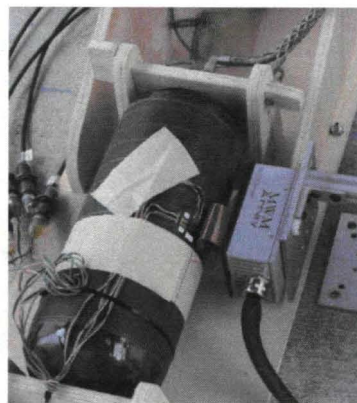


# COPV – Health Monitoring Proof of Concept Hydrostatic Test

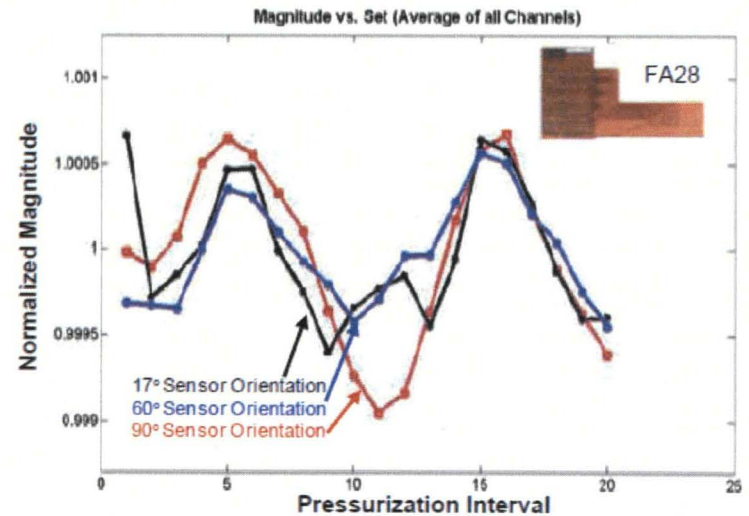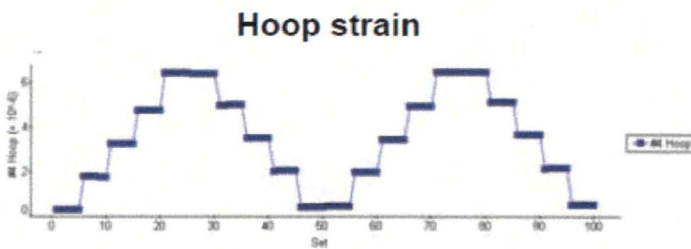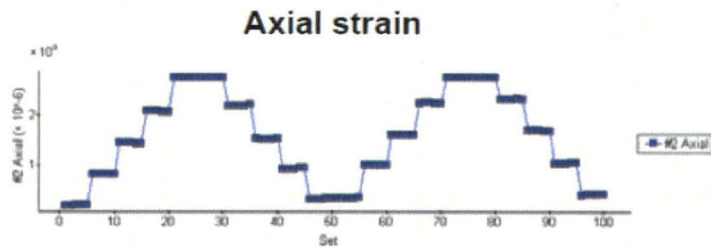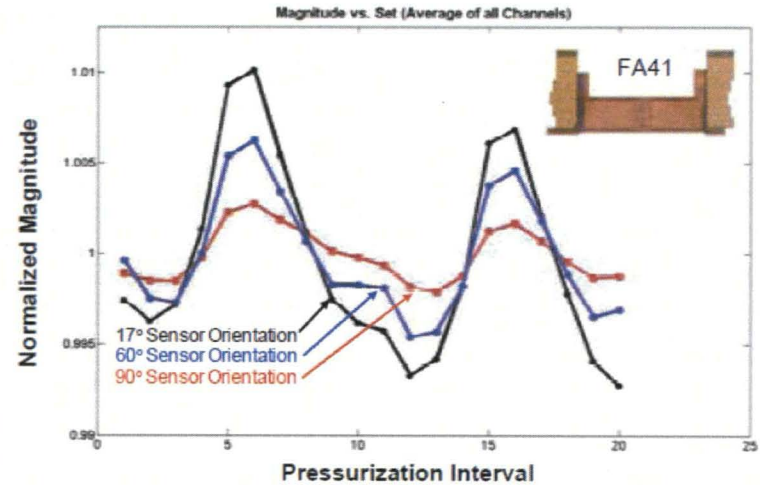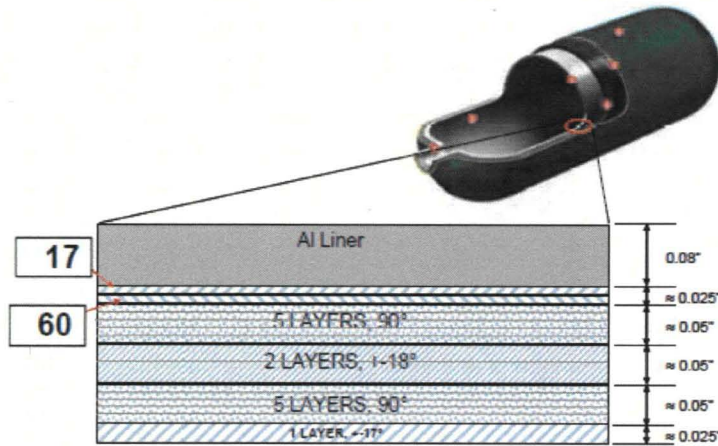


# COPV NDE


- Four COPVs selected from NASA White Sands inventory
- Scanned via MWM before and after impact testing

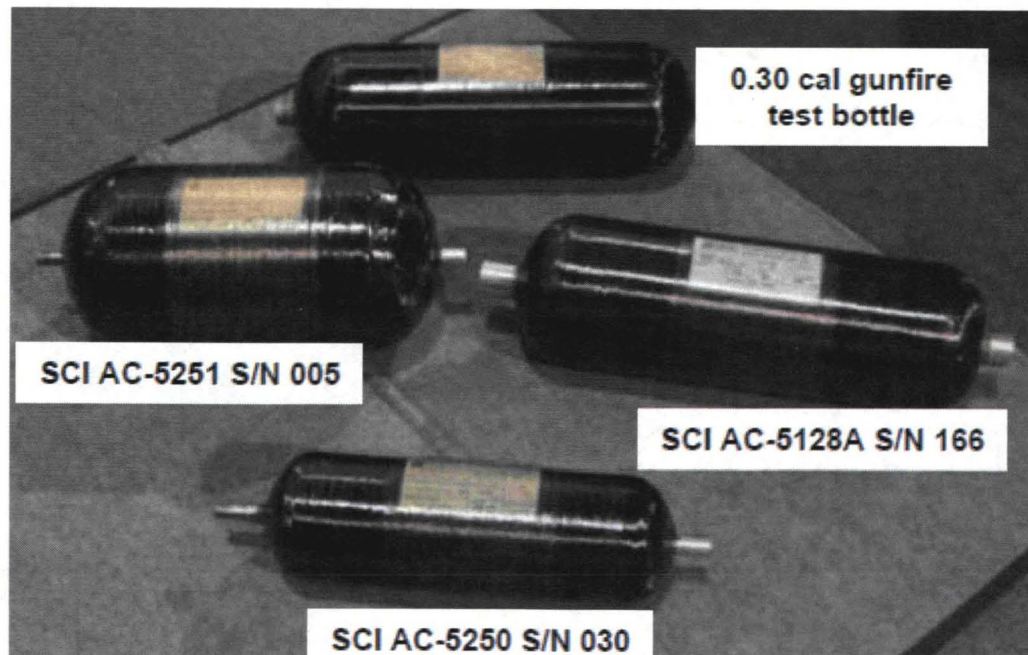

# Rotation Scans

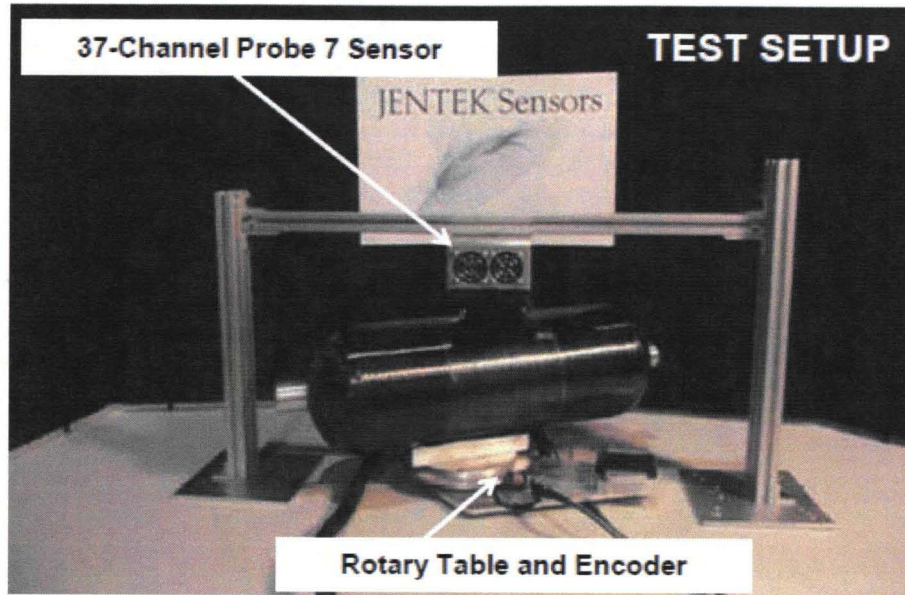




## FA28 MWM-Array Scan

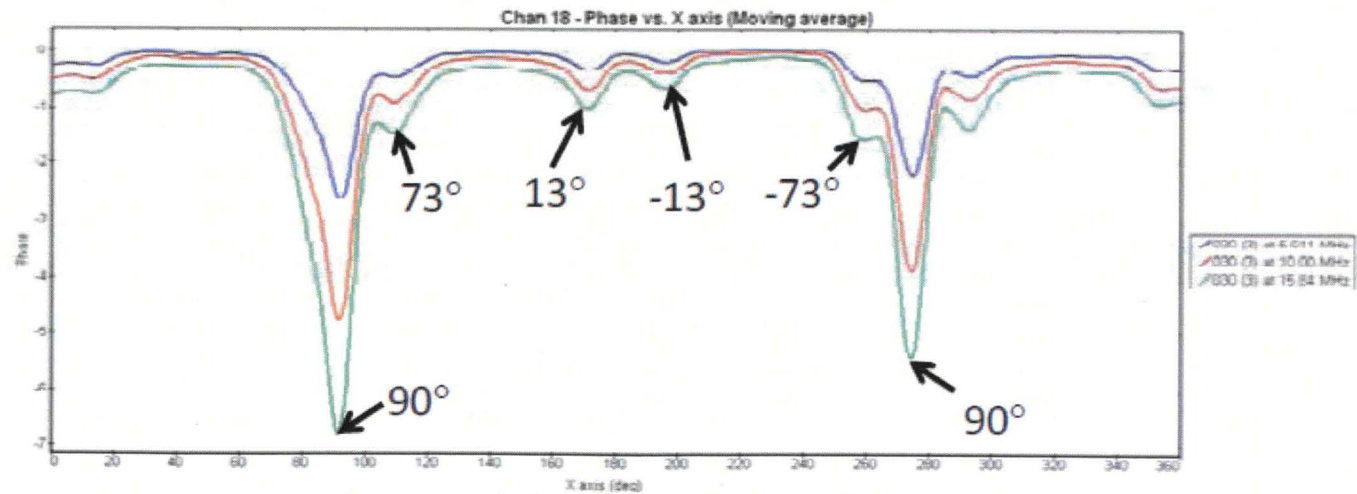





# NE Test setup for hoop oriented fibers

KSC ENGINEERING  
AND TECHNOLOGY

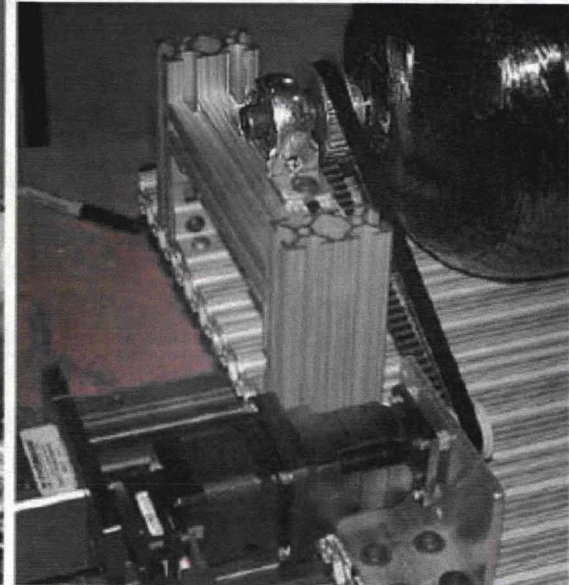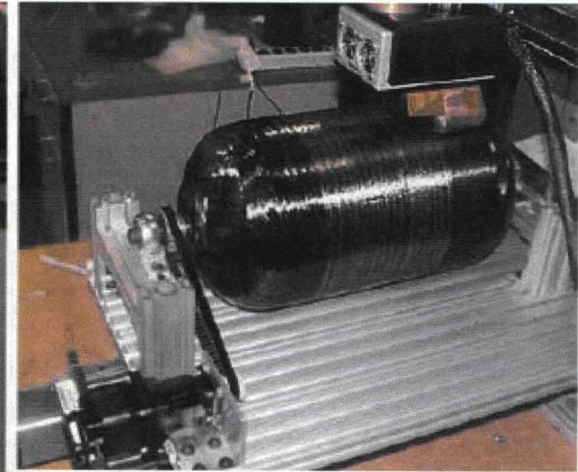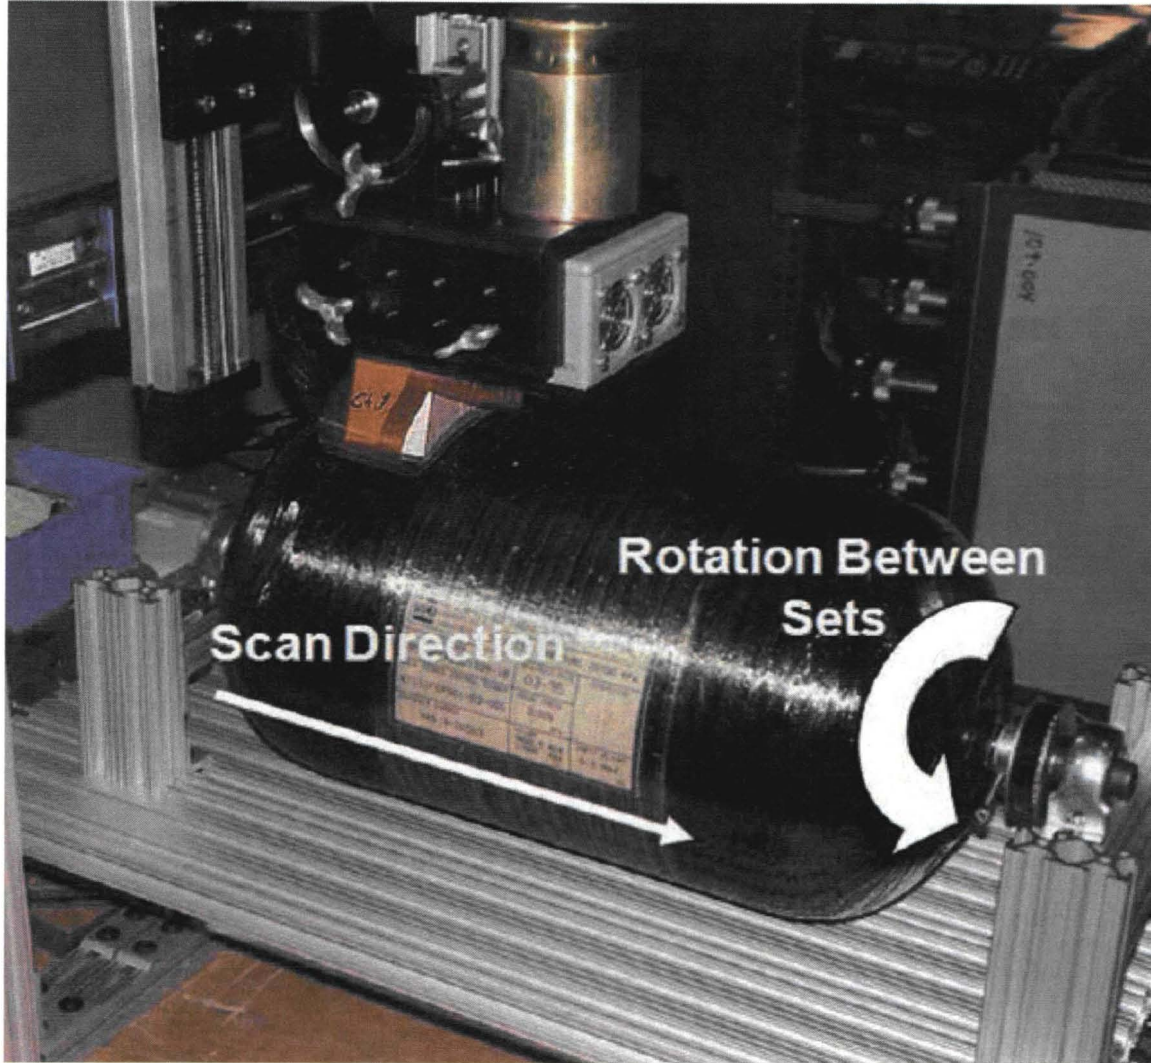

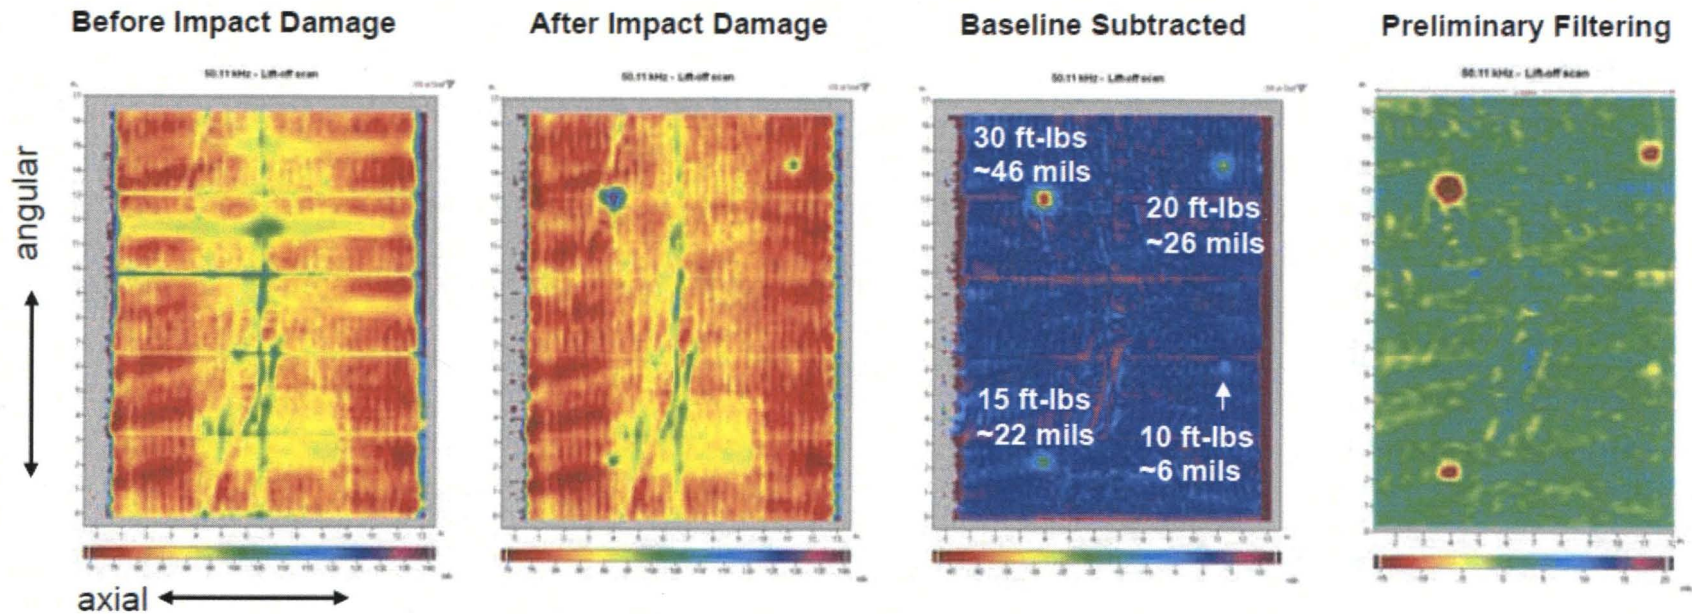

- Sample AC5250-030; 90° Sensor drive orientation
- Higher impact energy results in larger dents in the aluminum liner
- Sensor: MWM-Array FA24
- 50.11 kHz

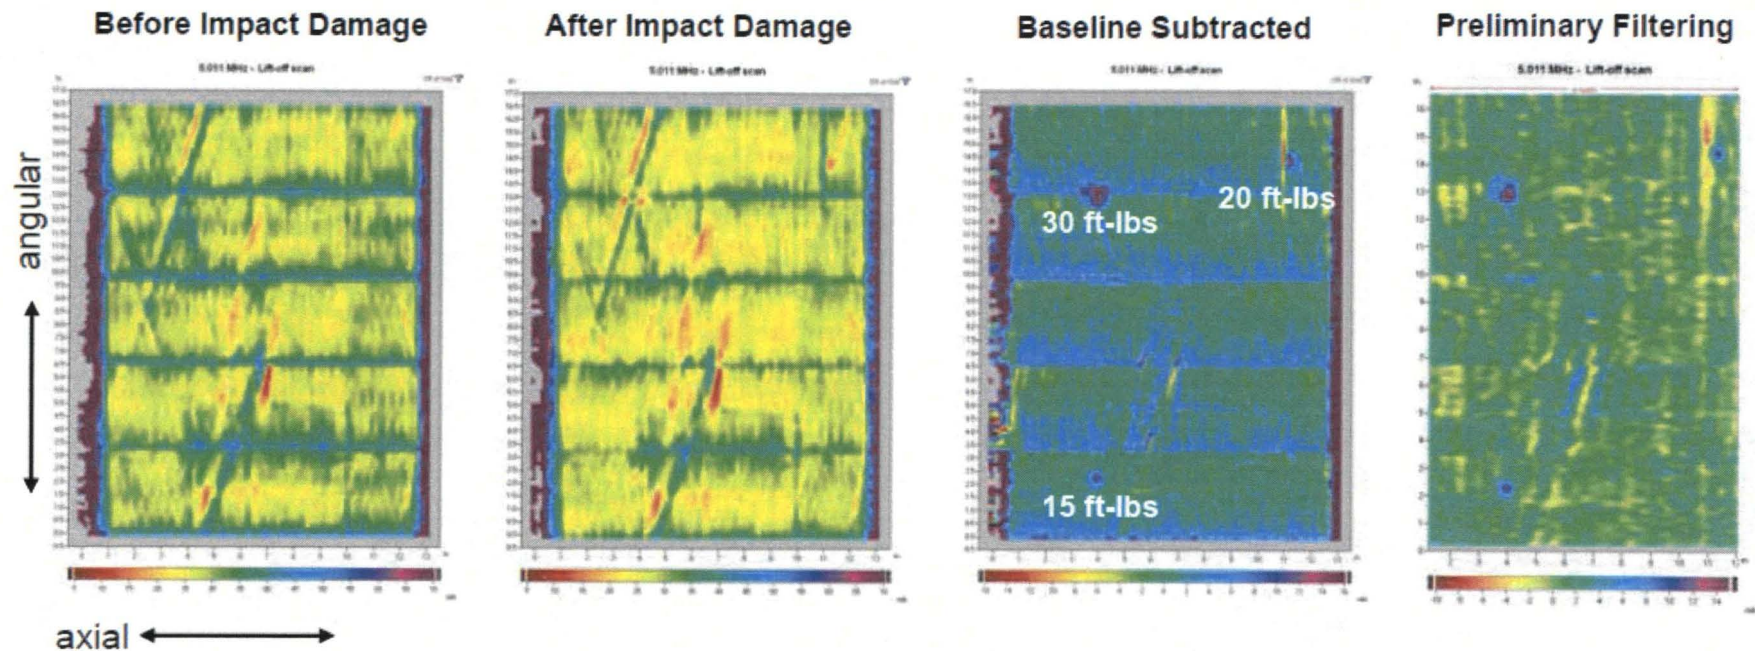


- Sample AC5250-030; 90° Sensor drive orientation
- Sensor: MWM-Array FA24
- 5.011 MHz




# Scan of COPV with Insulation Blanket




Test Setup

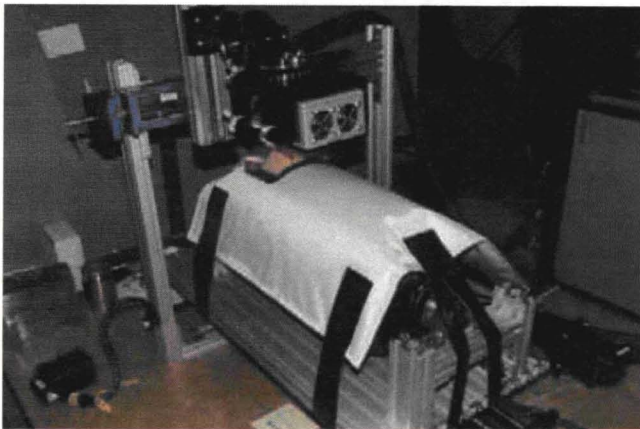

Lift-off C-scan for COPV AC5251-005 without an MLI layer (50 kHz)

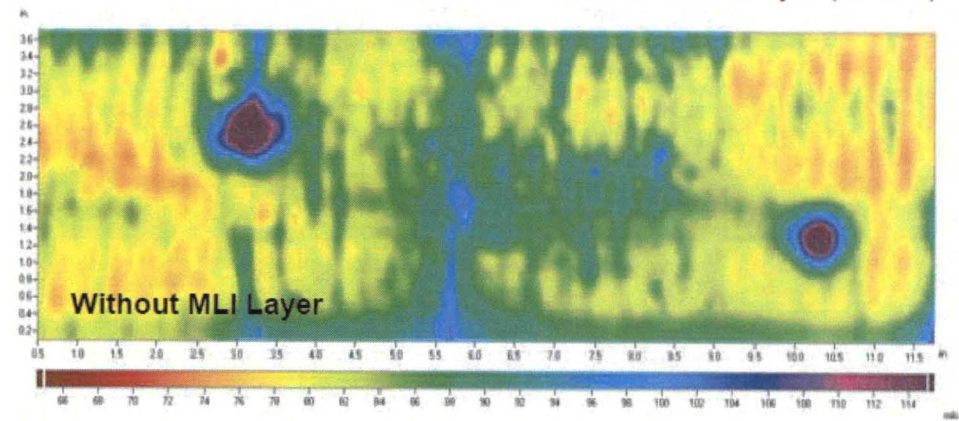


Lift-off C-scan for COPV AC5251-005 with a conductive MLI layer placed over the COPV (50 kHz)

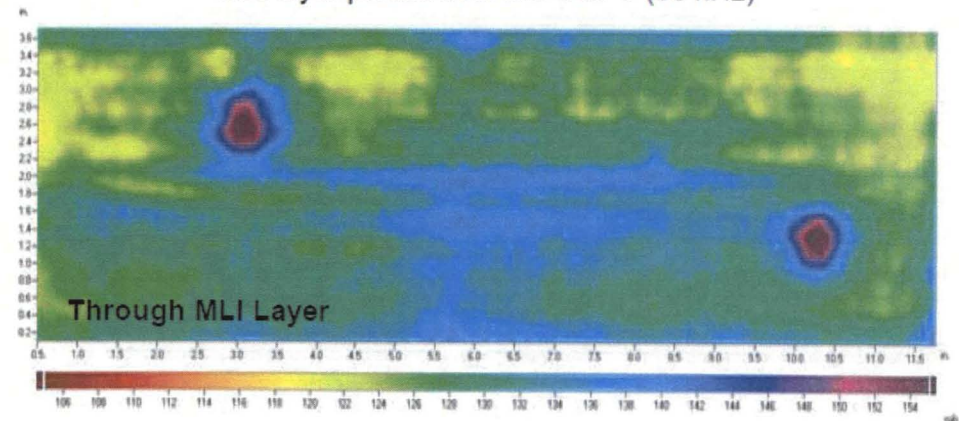


# Composite Structure Impact Damage Detection

Composite Specimen with  
Impact Damage on Scanning Bed

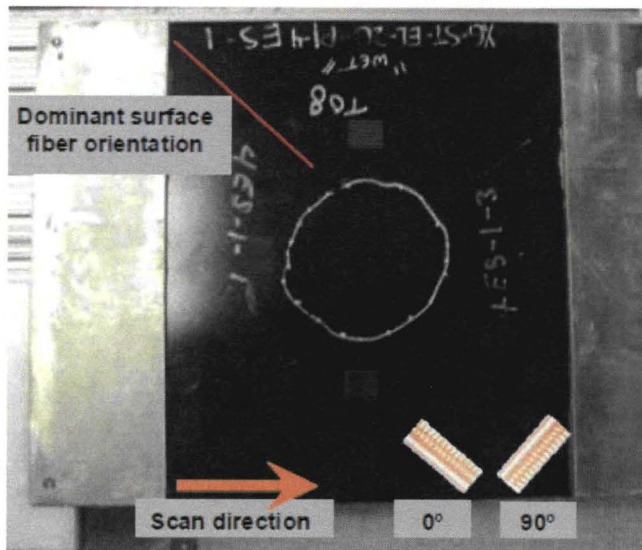


Specimen provided by Lockheed Martin

Sample

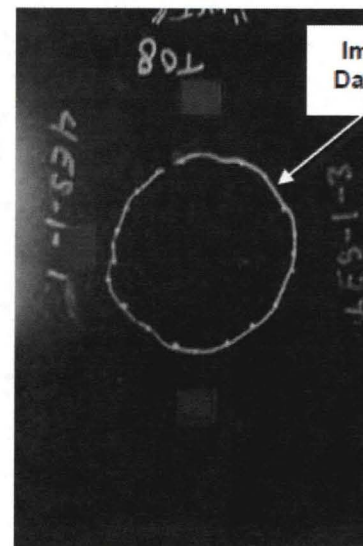


Conductivity

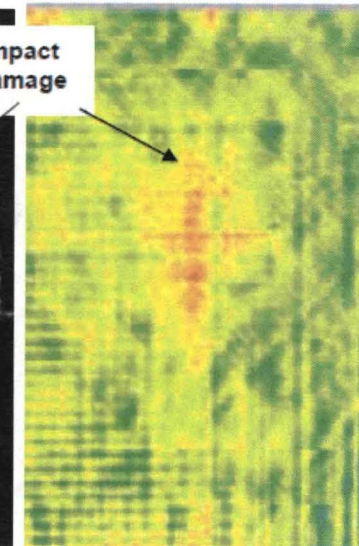



15.84MHz image taken with  
scanning MWM-Array for  
effective conductivity

Proximity

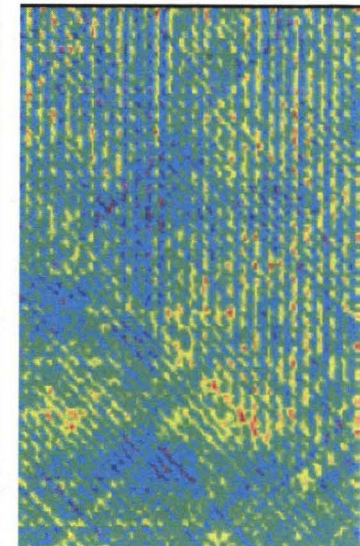

MWM-Array image  
of proximity to first  
fiber layer

# Composite Property Variation with Stress

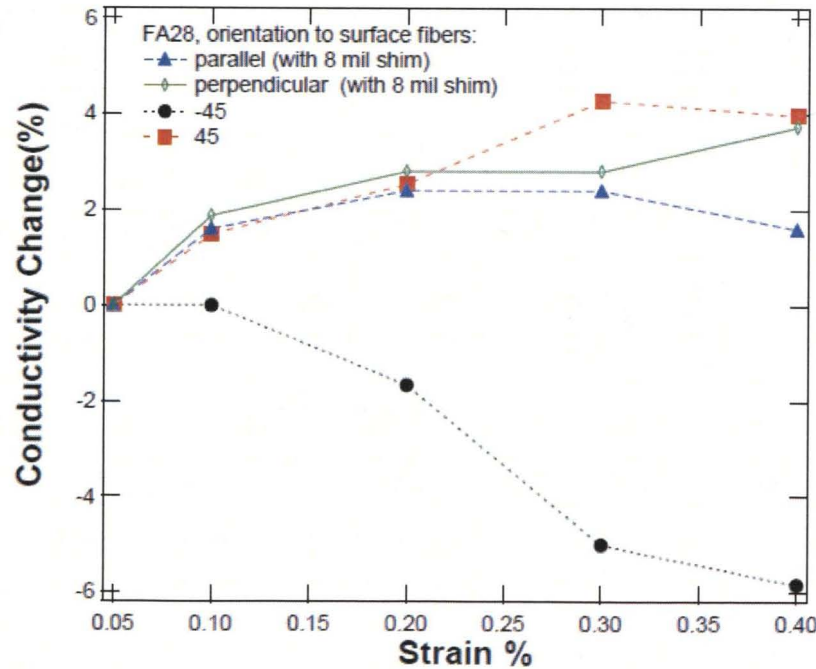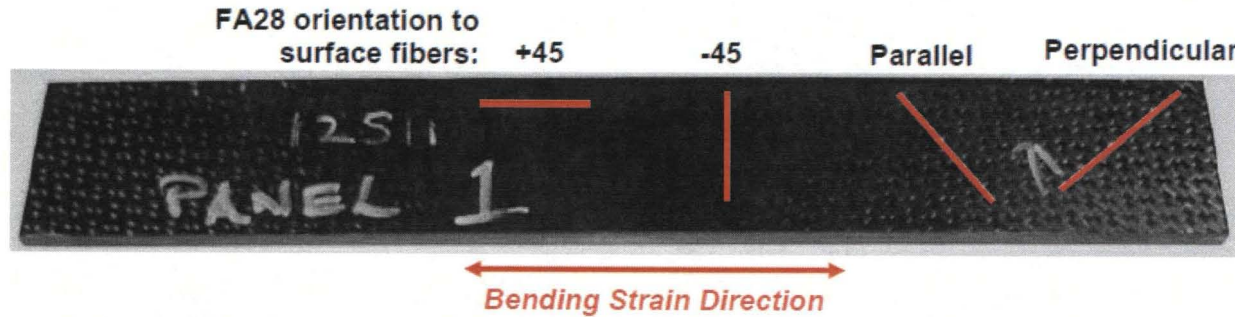


# Development of a High Temperature MWM Array Sensor



- Designed for continuous use at 1000° C by proper selection of high temperature materials.
- Ceramic substrate and high-temperature metal deposited conductive winding constructs.
- Prototype 7-channel MWM-Array sensor built and tested at 850° C with no degradation observed.
- Demonstrated crack detection with prototype high temperature sensor.
- High temperature cabling issues require further development

**Room Temperature  
MWM-Array Sensor**

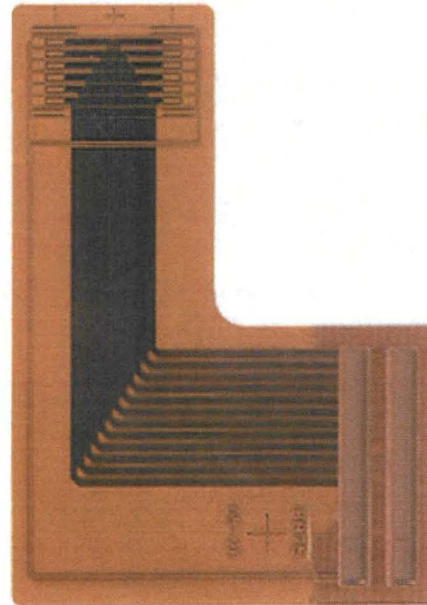

**High Temperature  
MWM-Array Sensor**

