



# Development of an, unstructured, three- dimensional material response model


AIAA SciTech Conference  
Grapevine, TX 2017

Joseph Schulz, Eric Stern, Grant  
Palmer, Suman Muppidi, Olivia  
Schroeder, and Alexandre Martin

# Background




## High-Temperature Gases

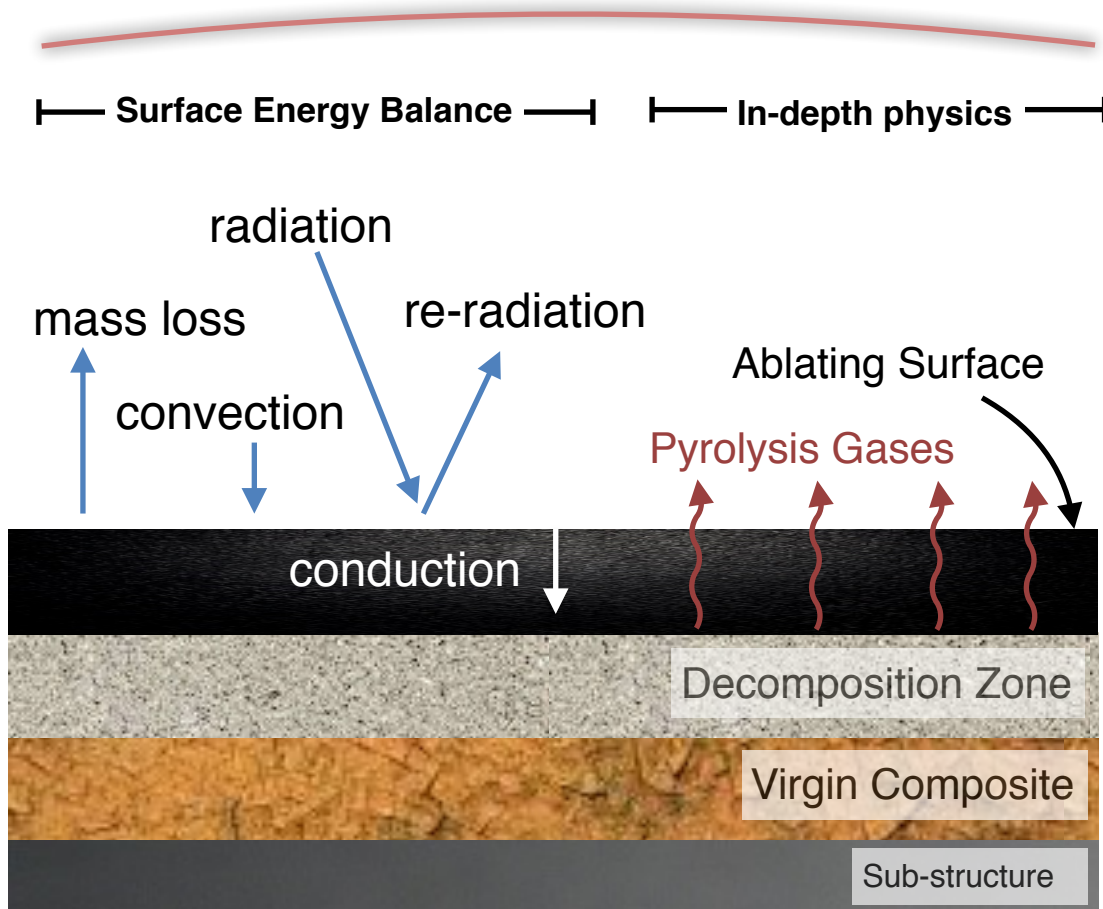

## NASA Material Response Tools

### Engineering Tools

- STAB / CHAR (NASA JSC)
- FIAT / TITAN (NASA ARC)
- **Icarus** (NASA ARC)



*Inform engineering models*

### Research Tools

- PATO (NASA ARC)

### Material Properties


- PuMA (NASA ARC)

\*Not an exhaustive list

- **Why Icarus?**

- Three-dimensional physics modeling and complex geometries
- Coupling to CFD simulation
- Software architecture
  - Easy to add new physics, numerics, and material property models
  - Linking to optimization and inverse parameter estimation methods
- Independent of other NASA material response models
  - Provides verification of predictions

- **Target Applications**

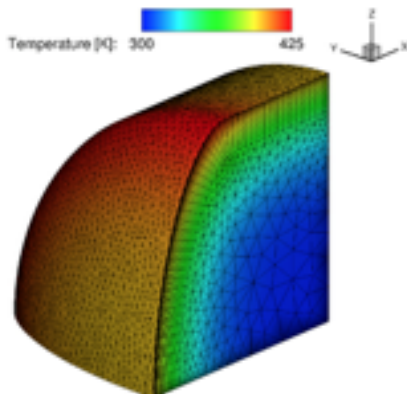

3D ArcJet IsoQ



ADEPT ArcJet Test



Orion Compression Pad






# Icarus



Spring 2017

Winter 2017



## Version 1.0

### **Physics Models**

*Thermal Conduction*  
*+ Decomposition*  
*+ Pyrolysis Gas Continuity*

### **Numerical Methods**

*Time integration*  
*- First-order Backward Euler*  
*- Second-order Runge-Kutta*  
*Spatial integration*  
*- Green-Gauss reconstruction*  
*Mesh Motion*  
*- Radial-basis functions*

### **Verification and Validation**

*Analytical Heat Conduction*  
*Ablation Workshop Test Cases*  
*PICA ArcJet validation*

## Version 2.0

### **Physics Models**

*Thermal Conduction*  
*+ Pyrolysis Gas Momentum*  
*+ Element Conservation*

### **Numerical Methods**

*Implicit Time Integration*  
*- Point relaxation*  
*- Numerical Jacobians*  
*Gradient reconstruction*  
*- Weighted least-squares*

### **Verification and Validation**

*Orion ArcJet validation*  
*HEEET ArcJet validation*  
*MSL Flight data*

## Version 3.0

### **Physics Models**

*Dust erosion / spallation*  
*Linear elasticity model*

### **Numerical Methods**

*AMR*


### **Interface**

*GUI*  
*Design Toolbox*  
*- Shape optimization*  
*- Inverse parameter estimation*  
*- Uncertainty quantification*

ICARUS  
Development Roadmap



# Icarus - Version 1.0 Status

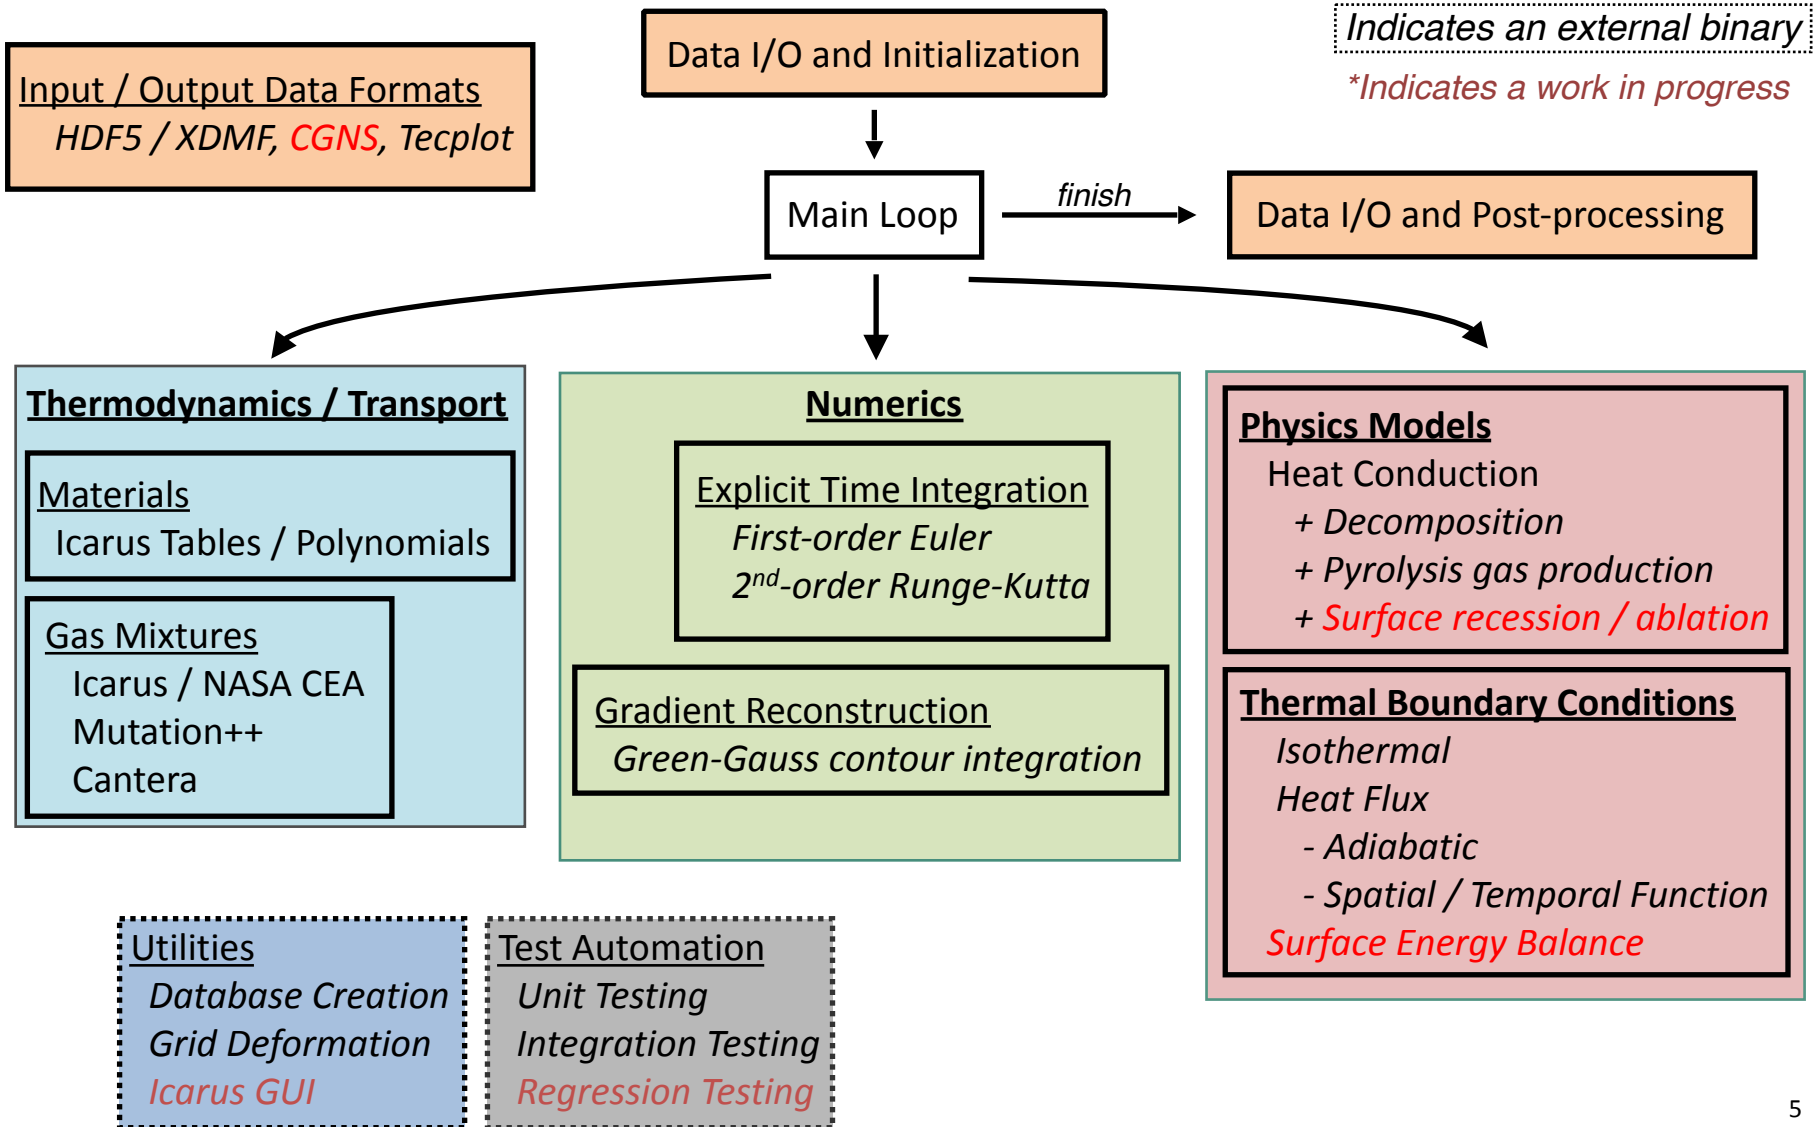


# Icarus - Data Structure



- **Modular data structure partitions physics, numerics, and material or gas models**
  - **Organization is user friendly and extensible**

Processor 1

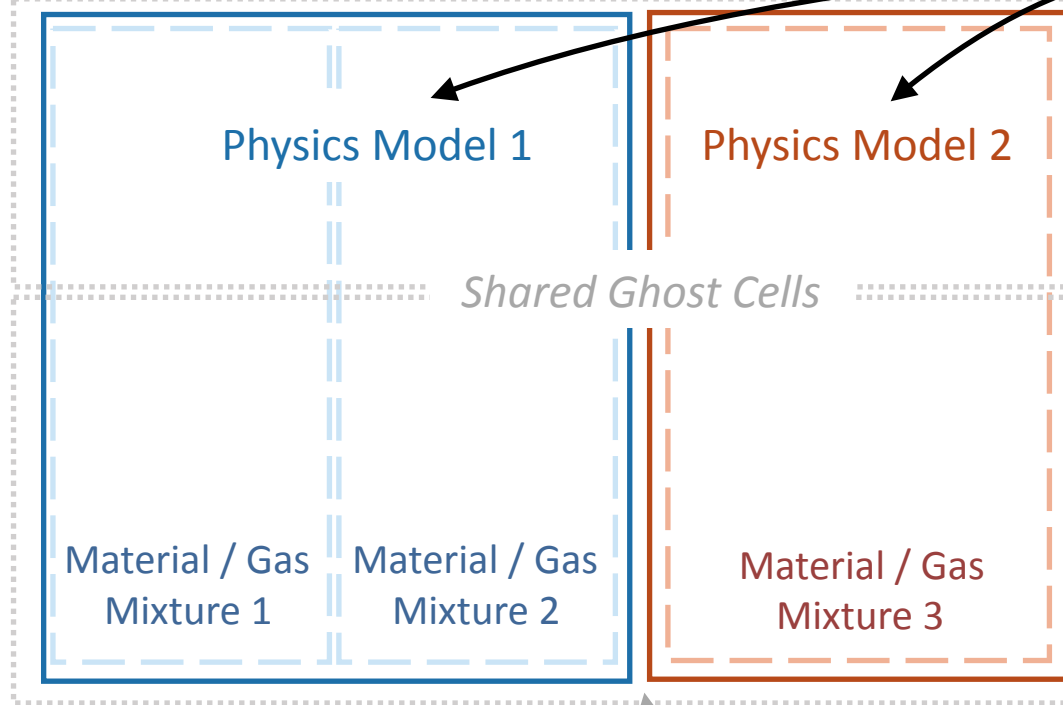

Blocks 1 and 2 are defined for different physics models

Blocks can contain multiple property zones:

- Material / Gas 1
- Material / Gas 2
- Material / Gas 3

Unstructured index ordering

- interior faces / cells
- boundary faces / cells
- processor shared faces / cells

Processor 2

*Model Boundary Condition*




- **Production codes require :**
  1. Sufficient documentation
    - Web-based documentation
    - Uses Sphinx, a Python tool that parses in-source code documentation to create HTML and LaTeX formatted documentation
  2. Verification
    - Automated unit and integration testing (~60% coverage currently)
    - Regression testing
  3. Validation
    - Comparison to Arc Jet data (current focus of PICA validation)
    - Shifting focus this year to AVCOAT modeling
    - MSL flight data
- **Participation in code-to-code comparisons to understand variability in modeling assumptions and prediction uncertainty**
  - Ablation Workshop
  - Relationships with research institutes and university laboratories

- **Icarus Formulation**

- Governing equations
- Numerical formulation

- **Verification Tests**

- Analytical heat conduction
- Multi-dimensional test cases
- **Current On-Going Work**
  - Mesh motion
  - Surface ablation

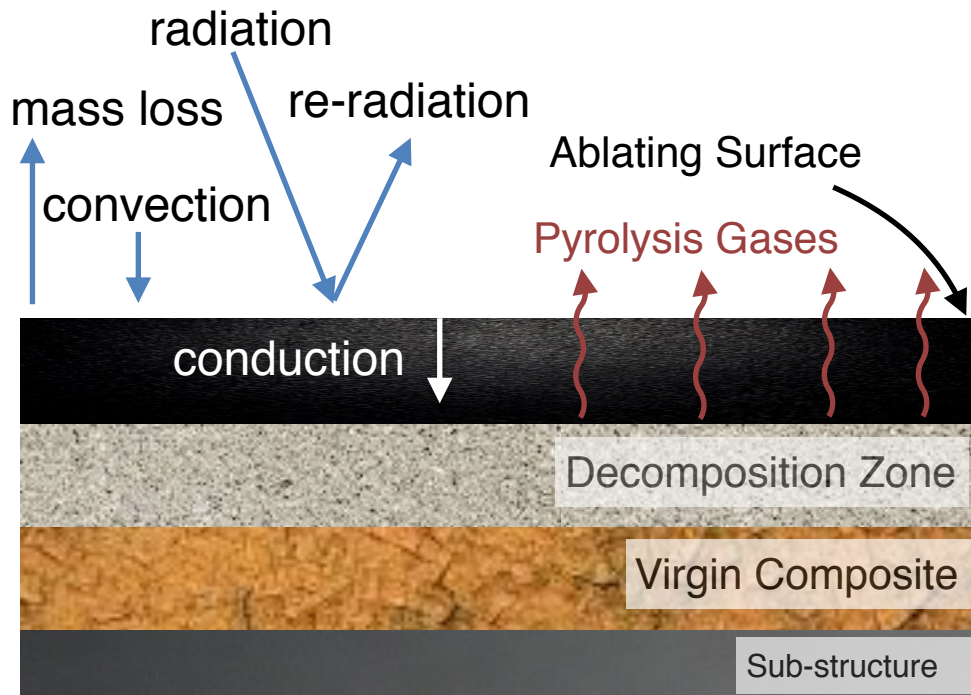

$$\frac{\partial \rho_{s,n}}{\partial t} = -k_n \rho_{v,n} \left( \frac{\rho_k - \rho_{c,n}}{\rho_{v,n}} \right)^{\psi_n} e^{(-T_{a,n}/T)}$$

$$\frac{\partial (\phi \rho_g)}{\partial t} + \frac{\partial}{\partial x_i} (\phi \rho_g u_{g,i}) = \dot{\omega}$$

$$\frac{\partial (\rho e)}{\partial t} + \frac{\partial}{\partial x_i} (\phi \rho_g h_g u_{g,i}) - \frac{\partial}{\partial x_i} \left( \kappa_{ij} \frac{\partial T}{\partial x_j} \right) = 0$$




# Formulation : Pyrolysis



- **Pyrolysis Modeling**

1. Solve the elemental conservation equations
  - Requires a detailed kinetic mechanism and knowledge of material composition
2. Use empirical relationships
  - Measure quantities only at the virgin and fully-charred states
  - Use simplified kinetics

- **Three-component model**

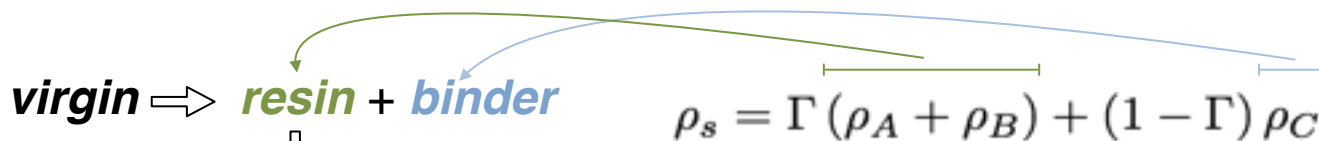


gas

$\Gamma$  : pseudo-volume fraction of pyrolyzing resin  
 $\rho = \phi \rho_g + \rho_s$  ;  $\phi$  is the material porosity

$$\frac{\partial \rho_{s,n}}{\partial t} = -k_n \rho_{v,n} \left( \frac{\rho_{s,n} - \rho_{c,n}}{\rho_{v,n}} \right)^{\psi_n} e^{(-T_{a,n}/T)},$$

$$\omega = \sum_{n=1}^N \Gamma_n \frac{\partial \rho_{s,n}}{\partial t} \quad : \text{total production of pyrolysis gas}$$

Pyrolysis Gases

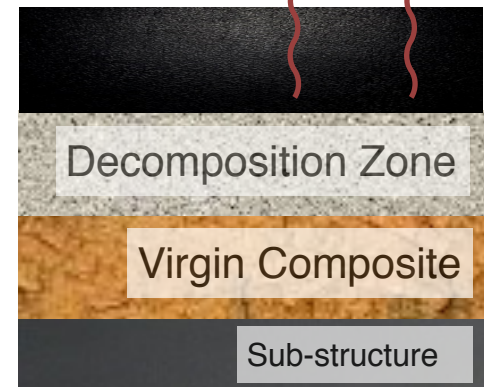

# Formulation : Material Properties



- **Properties are measured for at the virgin and fully-charred states**
  - Requires linearly interpolating between two states

$$\beta = \frac{\rho_v - \rho_s}{\rho_v - \rho_c} \longrightarrow Y_v = \frac{\rho_v}{\rho_v - \rho_c} \left( 1 - \frac{\rho_c}{\rho_s} \right)$$

- Internal energy of the material is evaluated either as a tabular or polynomial curve-fit that is a function of temperature and pressure

$$e_s(p, T) = h_s(p, T) = Y_v e_v(p, T) + (1 - Y_v) e_c(p, T)$$

- **Total mixture quantities are determined by weighted average using the gas mass fraction**

$$e(p, T) = Y_g e_g(T) + (1 - Y_g) e_s(p, T) \quad Y_g = \frac{\phi \rho_g}{\rho} \quad \text{: mass fraction of the gas mixture}$$

- **Thermal equilibrium and gas mixture in chemical equilibrium**

# Formulation : Material Properties




- **Material properties can be orthotropic**
  - Principle axis of the material may not align with the Cartesian frame of reference of the simulation
    - Woven TPS materials : alignment varies continuously
- **Properties defined parallel and orthogonal to the principle axis**

Thermal conductivity tensor in material frame of reference

$$\kappa_{ij} = \begin{bmatrix} \hat{\kappa}_{\parallel} & 0 & 0 \\ 0 & \hat{\kappa}_{\perp} & 0 \\ 0 & 0 & \hat{\kappa}_{\perp} \end{bmatrix}$$

Project tensor onto the surface defined by the normal vector at each grid point

$$\kappa = \mathbf{R}^T \hat{\kappa} \mathbf{R}$$

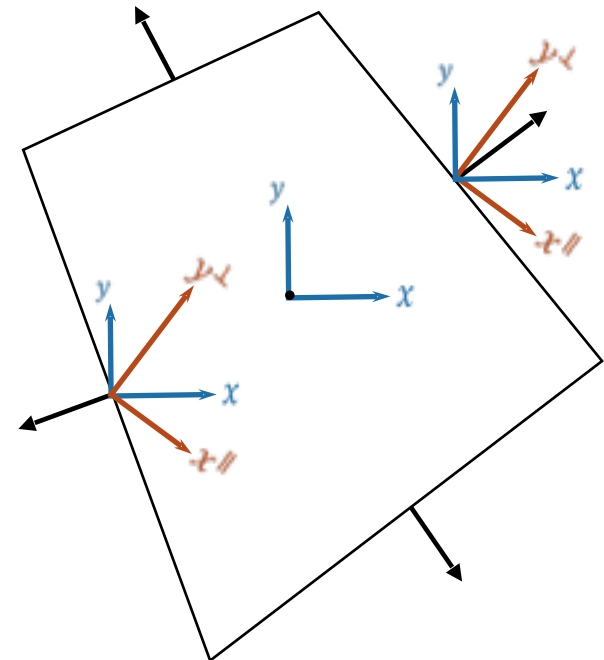

# Formulation : Conservation Equations



## Decomposition of solid material

$$\frac{\partial \rho_{s,n}}{\partial t} = -k_n \rho_{v,n} \left( \frac{\rho_{s,n} - \rho_{c,n}}{\rho_{v,n}} \right)^{\psi_n} e^{(-T_{a,n}/T)}, \quad n = 1, \dots, N$$

## Pyrolysis gas continuity

$$\frac{\partial (\phi \rho_g)}{\partial t} + \frac{\partial}{\partial x_i} (\phi \rho_g u_{g,i}) = \dot{\omega}$$

## Momentum conservation : Darcy's Law

$$u_{g,i} = -\frac{1}{\mu} K_{ij} \frac{\partial p}{\partial x_j}$$

## Total Energy conservation

$$\frac{\partial (\rho e)}{\partial t} + \frac{\partial}{\partial x_i} (\phi \rho_g h_g u_{g,i}) - \frac{\partial}{\partial x_i} \left( \kappa_{ij} \frac{\partial T}{\partial x_j} \right) = 0$$

convection of heat by  
pyrolysis gases



thermal conduction  
by material



- **Time integration**
  - Explicit first-order Euler or second-order Runge-Kutta
- **Gradient Reconstruction**
  - Gauss-Green contour integration

$$\int_{\mathcal{V}} \nabla \phi d\mathcal{V} = \int_{\mathcal{S}} \phi \mathbf{n} \cdot d\mathcal{S}$$

$$\overline{\nabla \phi}_i = -\frac{1}{\mathcal{V}_i} \sum_{j \in J_i} \hat{\phi}_j \mathcal{S}_{i,j}$$

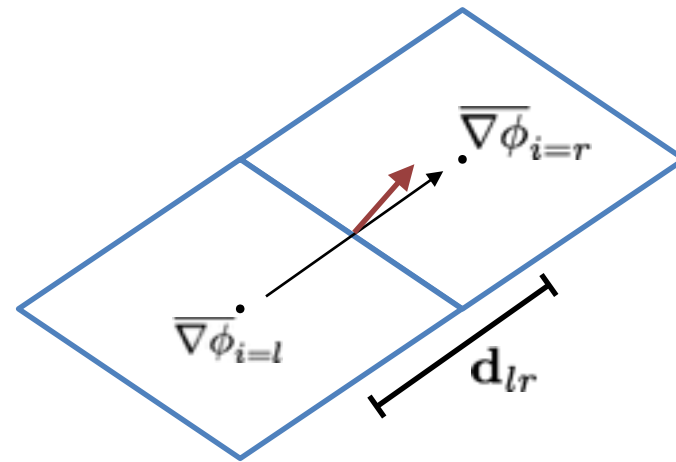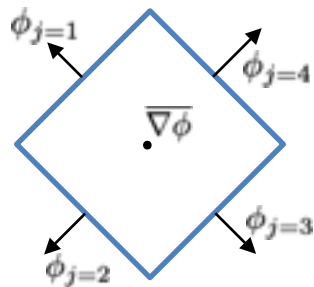

Average the cell-centered gradients neighboring each face

$$\nabla \phi_j = \frac{1}{2} (\overline{\nabla \phi}_{i=l} + \overline{\nabla \phi}_{i=r}) - \hat{\mathbf{d}}_{lr} \left( \frac{1}{2} (\overline{\nabla \phi}_{i=l} + \overline{\nabla \phi}_{i=r}) \cdot \hat{\mathbf{d}}_{lr} \right) + (\phi_{i=l} - \phi_{i=r}) \frac{\hat{\mathbf{d}}_{lr}}{|\mathbf{d}_{lr}|}$$



- **Verification Tests**

- Analytical heat conduction comparisons
- Determine scheme accuracy

- **Multi-dimensional test cases**

- Qualitative verification
- Code-to-code comparisons

- **Current On-Going work**

- Mesh motion
- Surface ablation
- **Conclusions**



- **Analytical solutions exist for the one-dimensional heat conduction equation**
  - Ignored pyrolysis or surface recession (constant density and volume)
  - Scalar material properties (tensors are isotropic)
- **Conservation equations reduce to a single PDE**
  - Assuming linear temperature-dependent properties:

$$\kappa(T) = \kappa_1 + \frac{\kappa_2 - \kappa_1}{T_2 - T_1} (T - T_1) \quad c_v(T) = c_{v,1} + \frac{c_{v,2} - c_{v,1}}{T_2 - T_1} (T - T_1)$$

- Using the variable transformation :

$$\theta = (T - T_1) + \frac{\kappa_2 - \kappa_1}{T_2 - T_1} \frac{1}{2\kappa_1} (T - T_1)^2$$

- Results in:



$$\rho c_v \frac{\partial T}{\partial t} - \kappa \frac{\partial^2 T}{\partial x^2} = 0 \quad \longrightarrow \quad \frac{\partial \theta}{\partial t} = \alpha \frac{\partial^2 \theta}{\partial x^2}$$

# Verification : 1-D Simulation Domain



- **One-dimensional computational domain of 1 m in length**
  - Resolved in the orthogonal directions by 1 grid element
  - Discretization by both triangular prisms and hexahedral elements
- **Estimate the order of accuracy the numerical scheme**
  - Scheme is expected to be second-order accurate
  - Compute the the root-mean-square error (RMS) for an increasing number of grid elements

$$\text{RMS} = \sqrt{\frac{\sum_i^{N_c} (T_{\text{analytical}} - T_{\text{numerical}})_i^2}{N_c}}$$

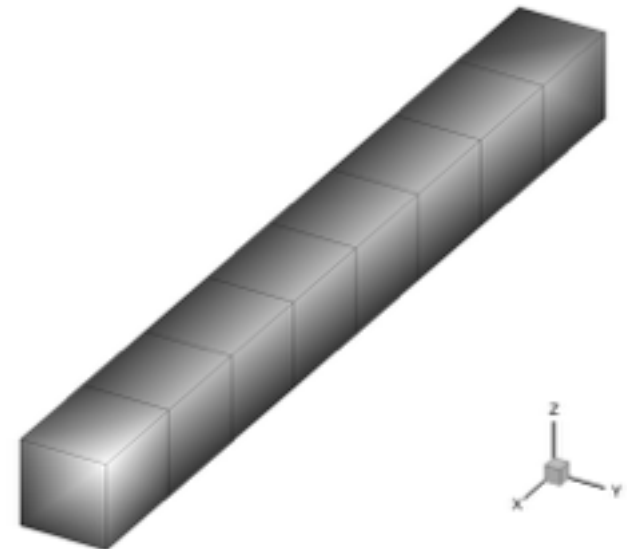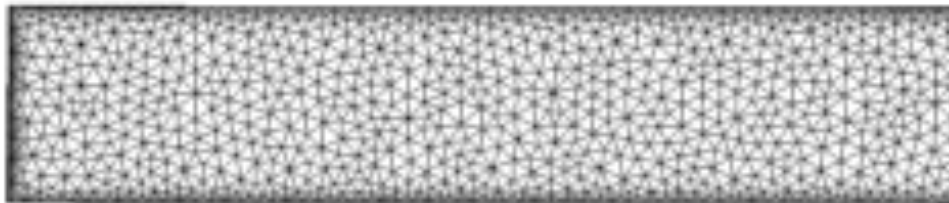





# Verification : Analytical Solution #1



- **Isothermal Boundary with constant material properties**
  - Hexahedral elements : 8, 16, 32, 64, and 128

$$\frac{T_1 - T(x, t)}{T_1 - T_0} = 2 \sum_{i=0}^{\infty} \frac{(-1)^i}{\left(i + \frac{1}{2}\right) \pi} \exp \left[ - \left(i + \frac{1}{2}\right)^2 \pi^2 \frac{\alpha t}{L} \right] \cos \left[ \left(i + \frac{1}{2}\right) \frac{\pi x}{L} \right]$$

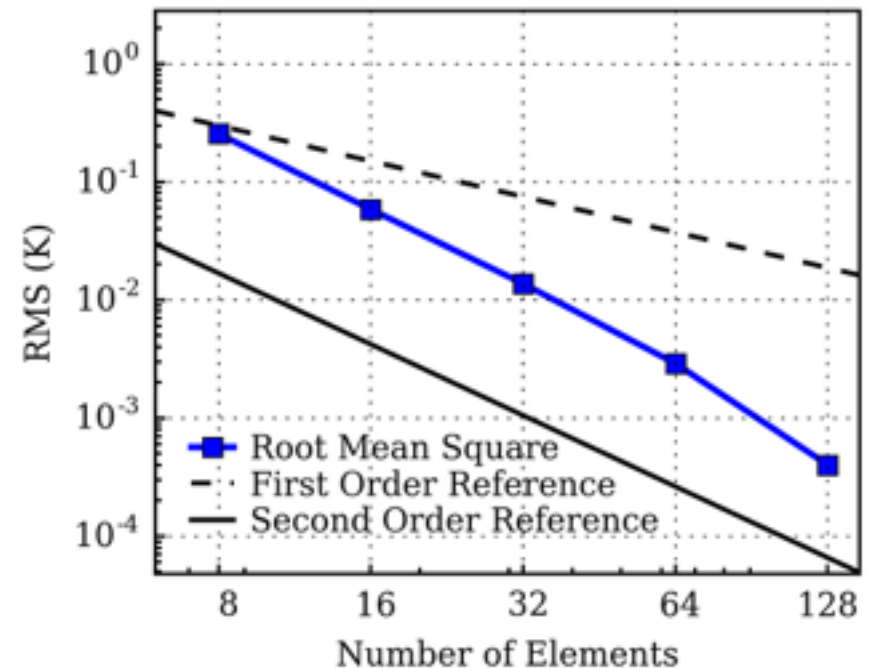
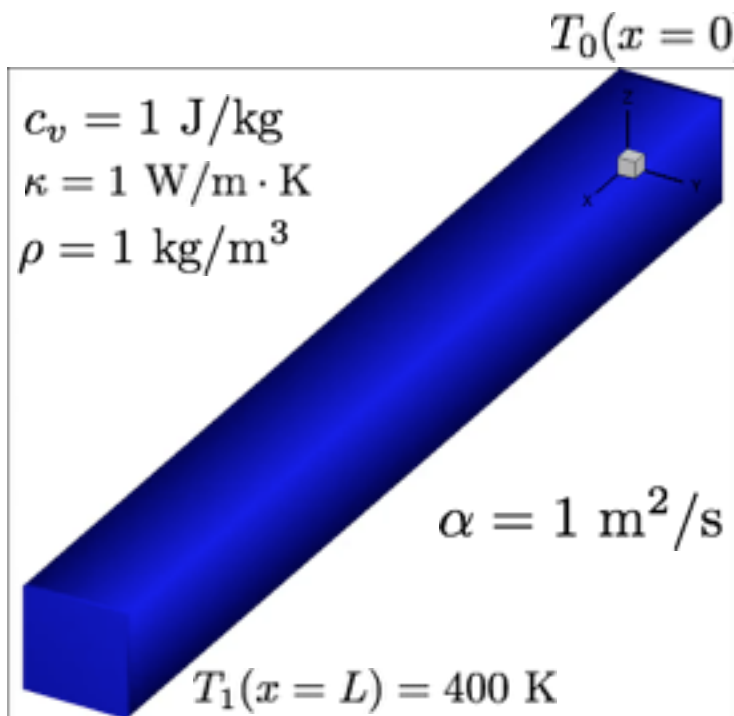


# Verification : Analytical Solution #2



- **Constant heat flux boundary and constant material properties**
  - Hexahedral elements : 8, 16, 32, 64, 128

$$\frac{T(x,t) - T_0}{q_{w,1}L/\kappa} = \frac{\alpha t}{L^2} + \frac{1}{3} - \frac{x}{L} + \frac{1}{2} \left(\frac{x}{L}\right)^2 - 2 \sum_{i=0}^{\infty} \frac{1}{n^2} \exp\left[-n^2\pi^2 \frac{\alpha t}{L^2}\right] \cos\left[\frac{n\pi x}{L}\right]$$

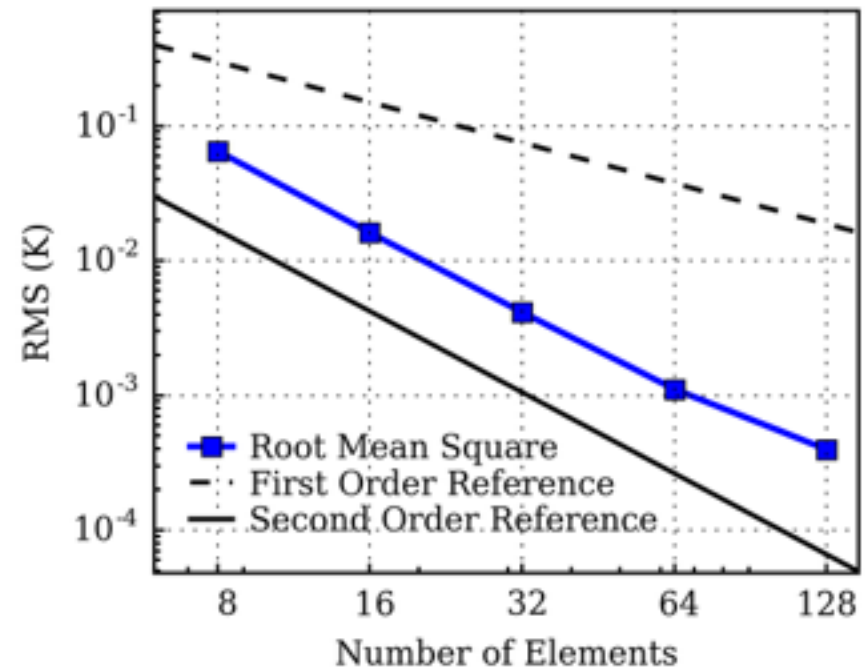
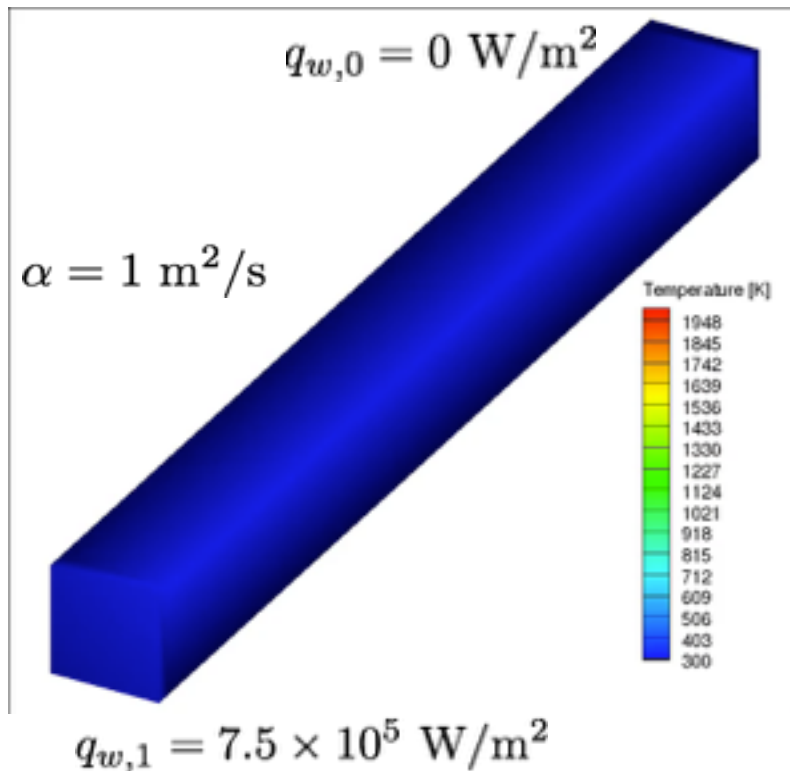


# Verification : Analytical Solution #3



- **Constant heat flux with temperature dependent (linear) material properties**
  - Triangular prisms : 10, 20, 40, 80

$$\frac{T(x, t) - T_1}{T_2 - T_1} = \left( \frac{\kappa_1}{\kappa_2 - \kappa_1} \right) \left[ \sqrt{1 + \frac{2\theta}{T_2 - T_1} \left( \frac{\kappa_2 - \kappa_1}{\kappa_1} \right)} - 1 \right]$$

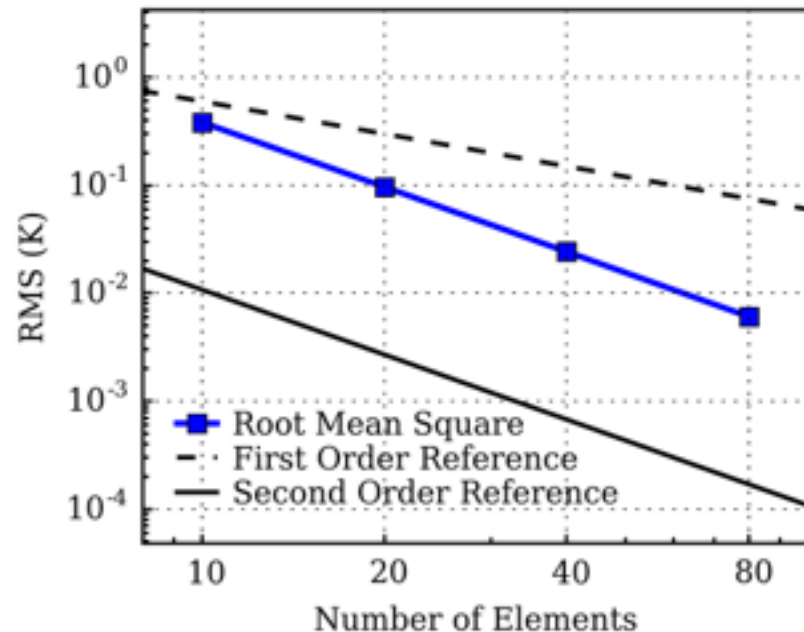
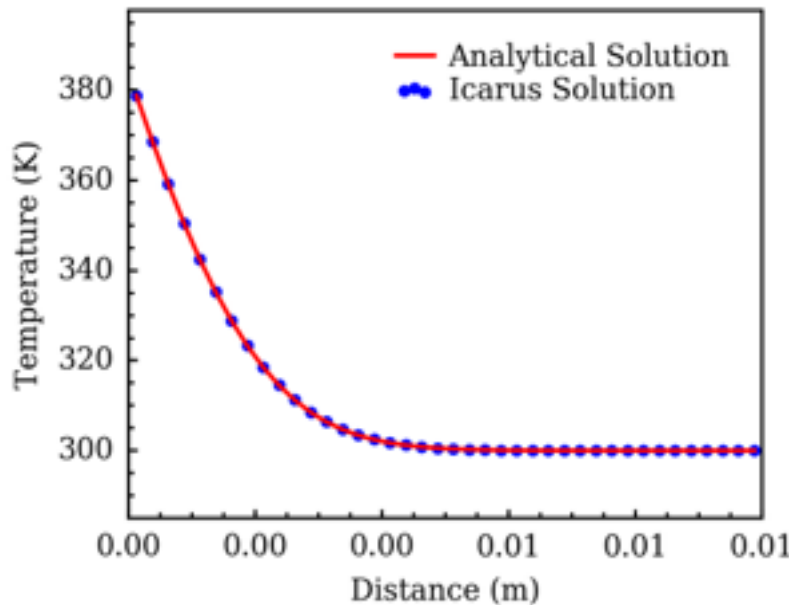


# Verification : Analytical Solution #4



- **Sinusoidal varying heat flux boundary with constant material properties**
  - Solution ill-posed since analytical solution exists for semi-infinite domain

$$T(x, t) - T_0 = \frac{q_{w,0}(t)}{\kappa} \sqrt{\frac{\alpha}{\kappa}} \exp\left[-\frac{\omega}{2\alpha x}\right] \cos\left(\omega t - \sqrt{\frac{\omega}{2\alpha}} x - \frac{\pi}{4}\right)$$

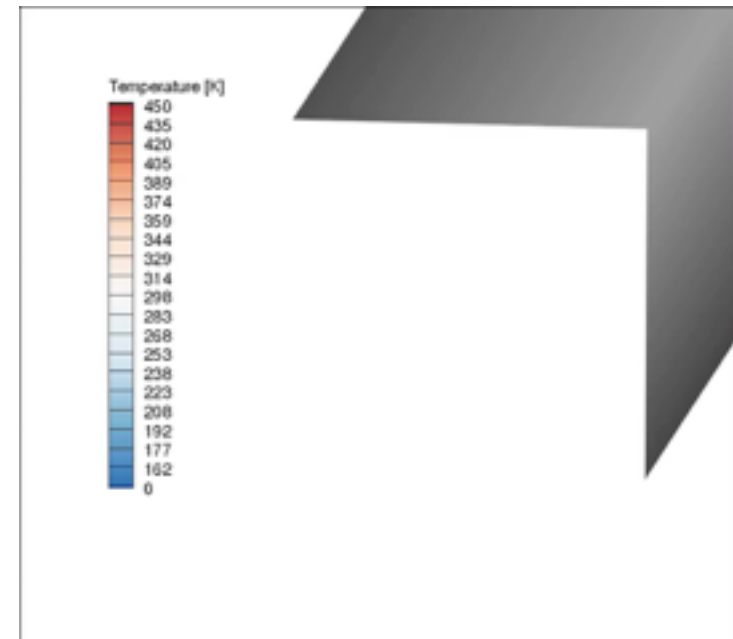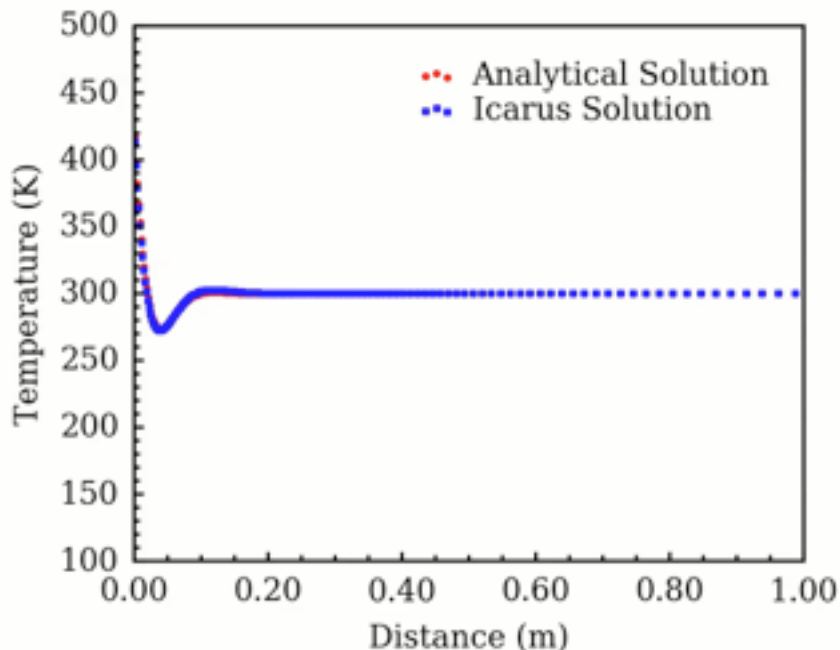



# Ablation Workshop Test Cases



- **One-dimensional domain : L = 5 cm**

- Hexahedral elements : 128

- **Boundary conditions**

- Single isothermal wall

$$T_{x=0} = \begin{cases} 298 \text{ K} : t \leq 0.1 \text{ sec} \\ 1644 \text{ K} : t > 0.1 \text{ sec} \end{cases}$$

- All other boundaries are adiabatic
- Initial pressure : p = 101325 Pa

- **Material : PICA**

- Properties are orthotropic
- Three-component decomposition model

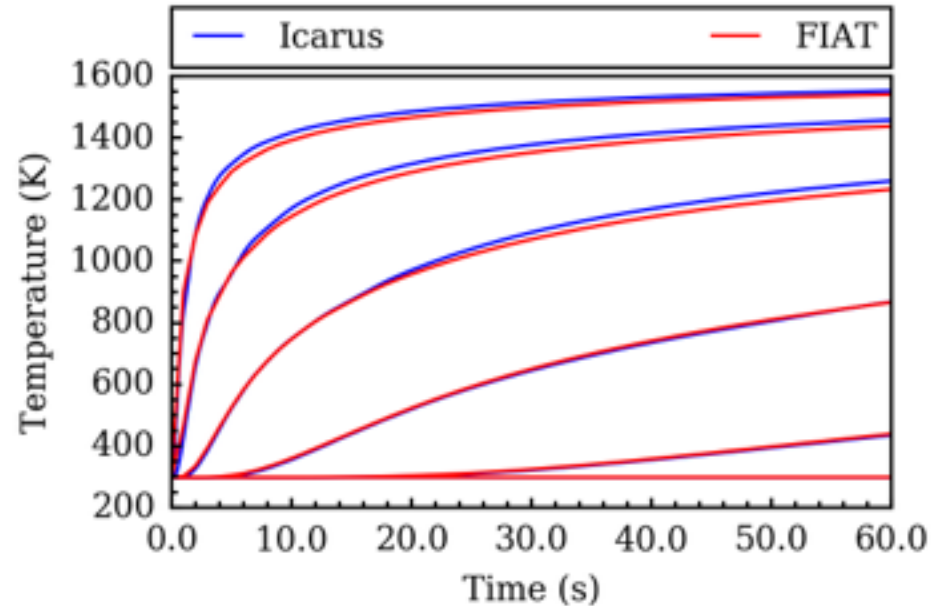


Figure (above) : Code-to-code comparison of Icarus and FIAT for the first ablation workshop test case. Differences are less than 3 percent.

- **Three-dimensional iso-q geometry typical of arc jet test articles**


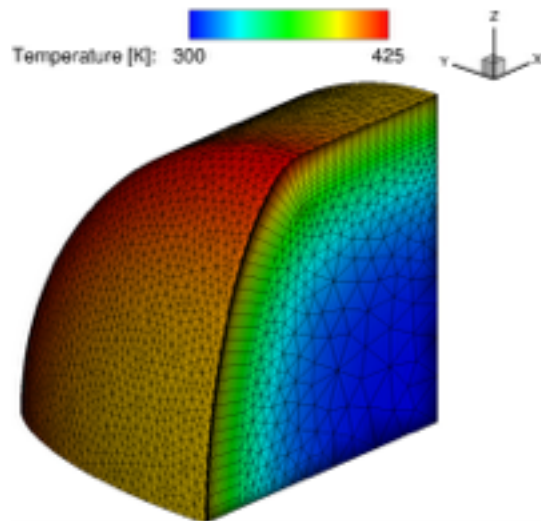


Figure (right) : Temperature contours for Iso-Q geometry heated along the outside radius by a constant heat flux of  $q_w = 7.5 \times 10^5 \text{ W/m}^2$  for TACOT material

Figure (above) : Code-to-code comparison of temperature along the x-axis between Icarus and CHAR

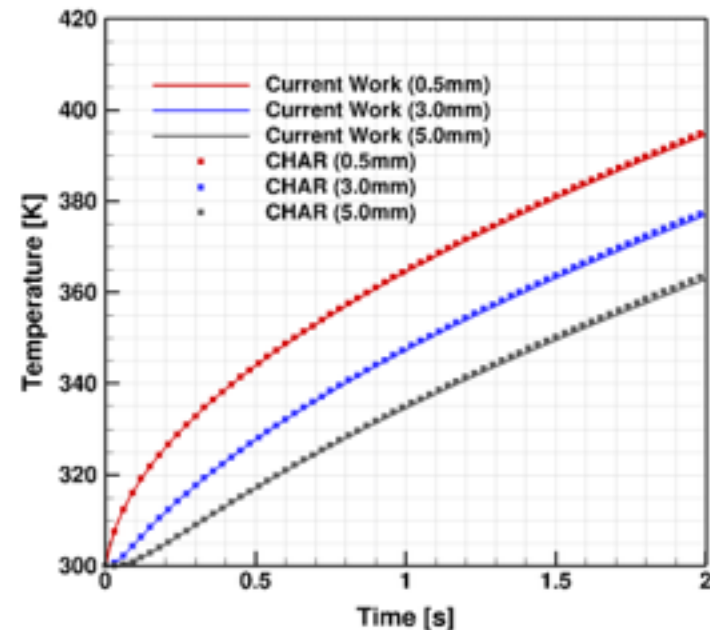

- **Verification Tests**
  - Analytical heat conduction comparisons
  - Determine scheme accuracy
- **Multi-dimensional test cases**
  - Qualitative verification
  - Code-to-code comparisons
- **Work in progress**
  - **Mesh motion / Surface ablation**
  - **Validation**
  - **Release of Icarus v1.0**

- **Ablation results in surface recession**

- Need a robust and efficient method to track the deformation of the computational grid during the simulation

- **Radial Basis Functions**

- A real-valued function whose value depends only on absolute distance
- Often use to approximate functions

$$y(\mathbf{x}) = \sum_{i=1}^N w_i \phi(|\mathbf{x} - \mathbf{x}_i|)$$

- Here N radial basis functions each weighted differently are used to approximate the function







- **Applications to mesh motion**

- Define a radial basis function for each grid point with respect to certain control points
- Compute the weights (requires solving a linear system)





# Mesh Motion

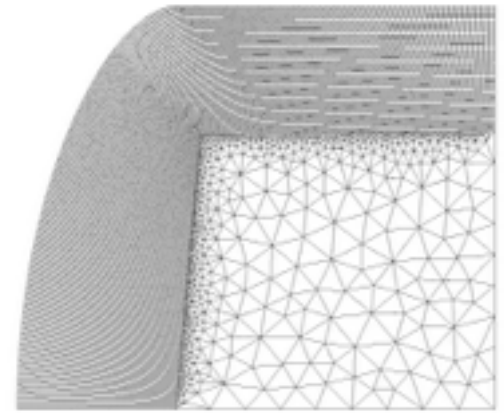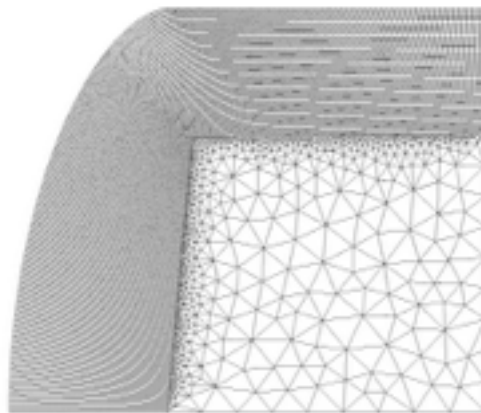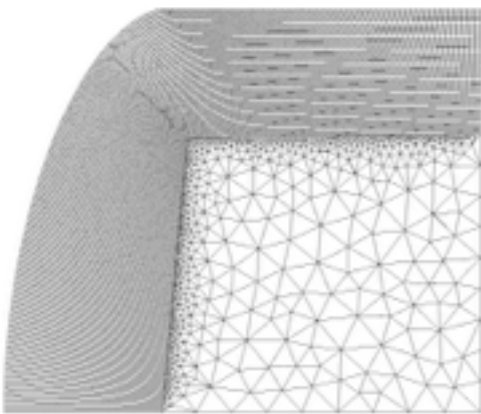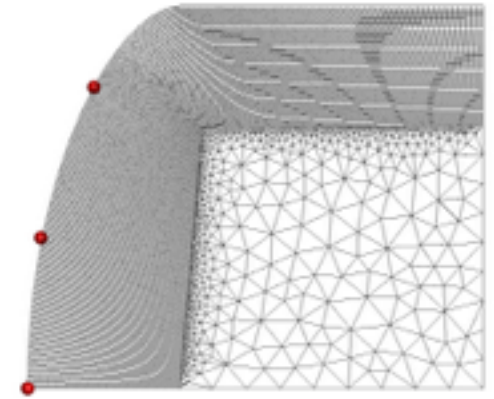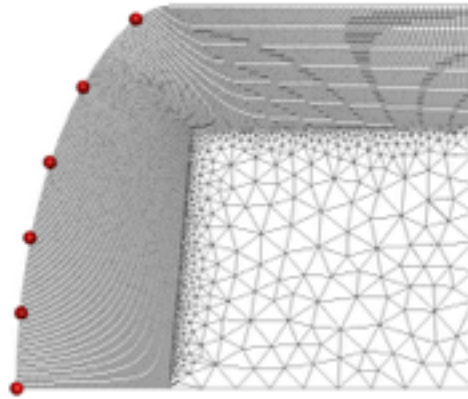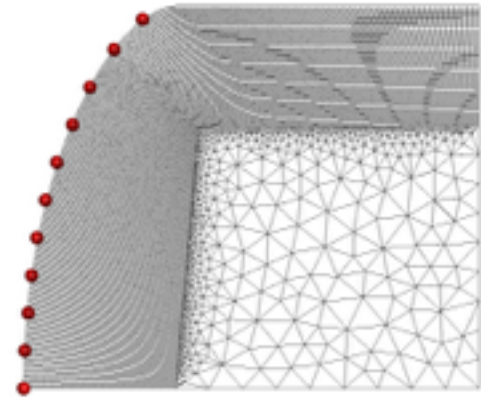

# Future Work and Conclusions



- Focus on the verification of one-dimensional heat conduction and pyrolysis
  - Numerical scheme
  - Thermodynamic / Transport Properties
  - Grid deformation
- Future Work
  - Validation to arc-jet data and continuation of code-to-code comparisons
  - Addition of surface recession / ablation modeling using radial basis function methodology
  - Integration of inverse estimation and Monte-Carlo analysis tools