

Driving Design Factors for Safe, High Power Batteries for Space Applications

By

Eric Darcy/NASA, Houston, TX USA

Jacob Darst/NASA, Houston, TX USA

William Walker/NASA, Houston, TX USA

Donal Finegan/NREL, Golden, CO USA

Paul Shearing/UCL, London, UK

Advanced Automotive Battery Conference

San Diego, CA

June 4-7, 2018

Outline

- Introduction
- Applications and Motivation
- 5 Battery Design Guidelines
- Trading thermal isolation vs heat dissipation
 - Full thermal isolation
 - Drawing heat from cell bottoms
 - Full can length interstitial heat sink approach
- Risk of side wall breaches during thermal runaway
- Insights from cell calorimetry combined with X-ray videography
- Summary




Orion Multi-Purpose Crew Vehicle

- 4-man crew
- Beyond Low Earth Orbit

Command Module Battery System

- 132V, 4 kWh x 4
- $\frac{3}{4}$ C discharge rate

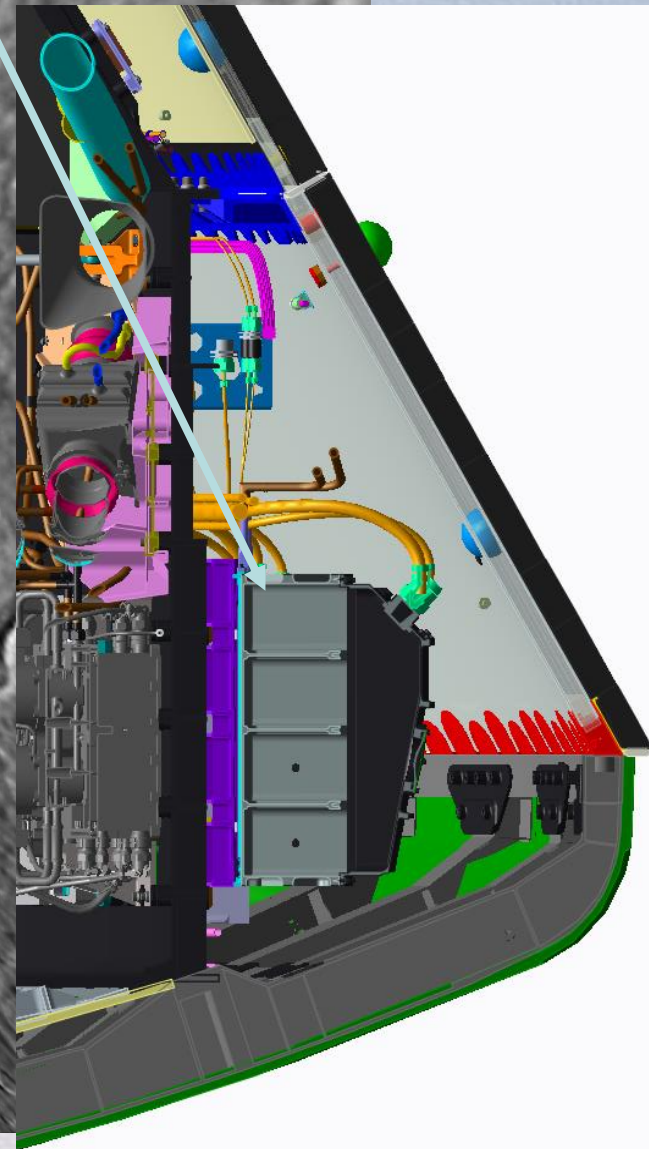

Some of NASA's Future Battery Applications


- **Robonaut 2**

- To enhance and reduce frequency of manned spacewalks
- High energy density and high specific energy battery needed
- 90V, 4 kWh, 7 hour mission



- **Mars Rover Vehicle**

- Terrestrial demonstration vehicle needing high voltage, power battery
- 400V, 4 kWh, 1 hour mission

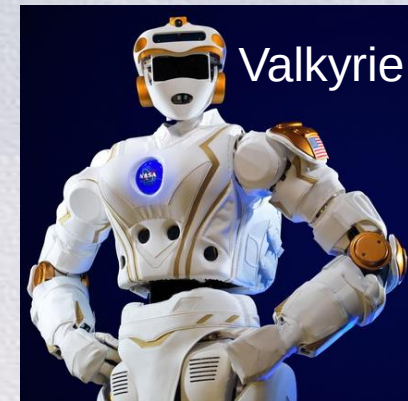

- **Valkyrie, RoboSimian**

- Terrestrial dangerous operations robot
- 90V, 2kWh, 1 hour mission

- **X-57 Electric Plane**

- All electric aircraft demonstrating distributed electric propulsion
- 525V, 50 kWh, 1 hour mission



Achieving Passive TR Propagation Resistant Designs


Pass/fail Criteria

- No TR propagation resulting from the TR of any single cell location at worst case temperature and pressure conditions
- Demonstration required by test
 - Minimum of 3 tests if adjacent cells cycle nominally after the test
 - Minimum of 6 tests if in any one test the adjacent cells are damaged
 - CID opens, cell vents, or leakage
 - Charge retention (soft short)




5 Battery Design Guidelines for Reducing Hazard Severity from a Single Cell TR

- **Reduce risk of cell can side wall breaches**
 - Without structural support most high energy density (>660 Wh/L) designs are very likely to experience side wall breaching during TR
 - Battery should minimize constrictions on cell TR pressure relief
- **Provide adequate cell spacing and heat rejection**
 - Direct contact between cells nearly assures propagation
 - Spacing required is inversely proportional to effectiveness of heat dissipation path
- **Individually fuse parallel cells**
 - TR cell becomes an external short to adjacent parallel cells and heats them up
- **Protect the adjacent cells from the hot TR cell ejecta (solids, liquids, and gases)**
 - TR ejecta is electrically conductive and can cause circulating currents
- **Prevent flames and sparks from exiting the battery enclosure**
 - Provide tortuous path for the TR ejecta before hitting battery vent ports equipped flame arresting screens

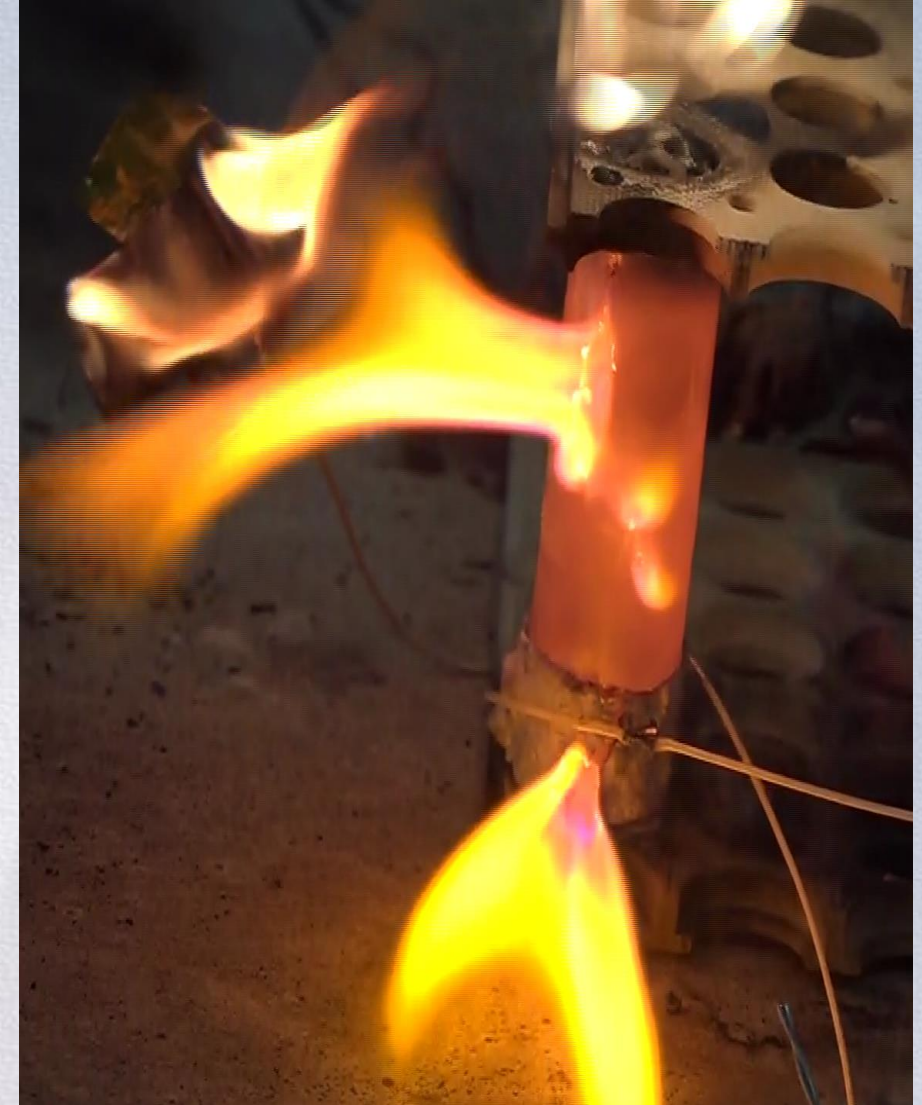


Pre-Test

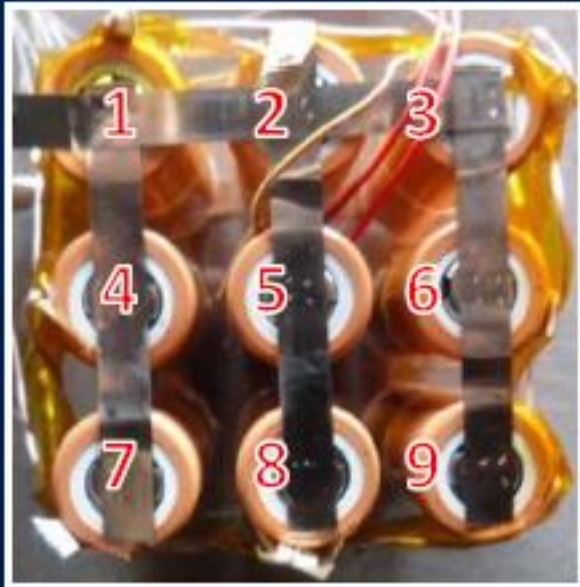


Jeevarajan¹ showed that without any heat dissipation path except through electrical parallel connections, adjacent cells get damaged (shorted) with even 4 mm spacing

9P LGC2 4mm

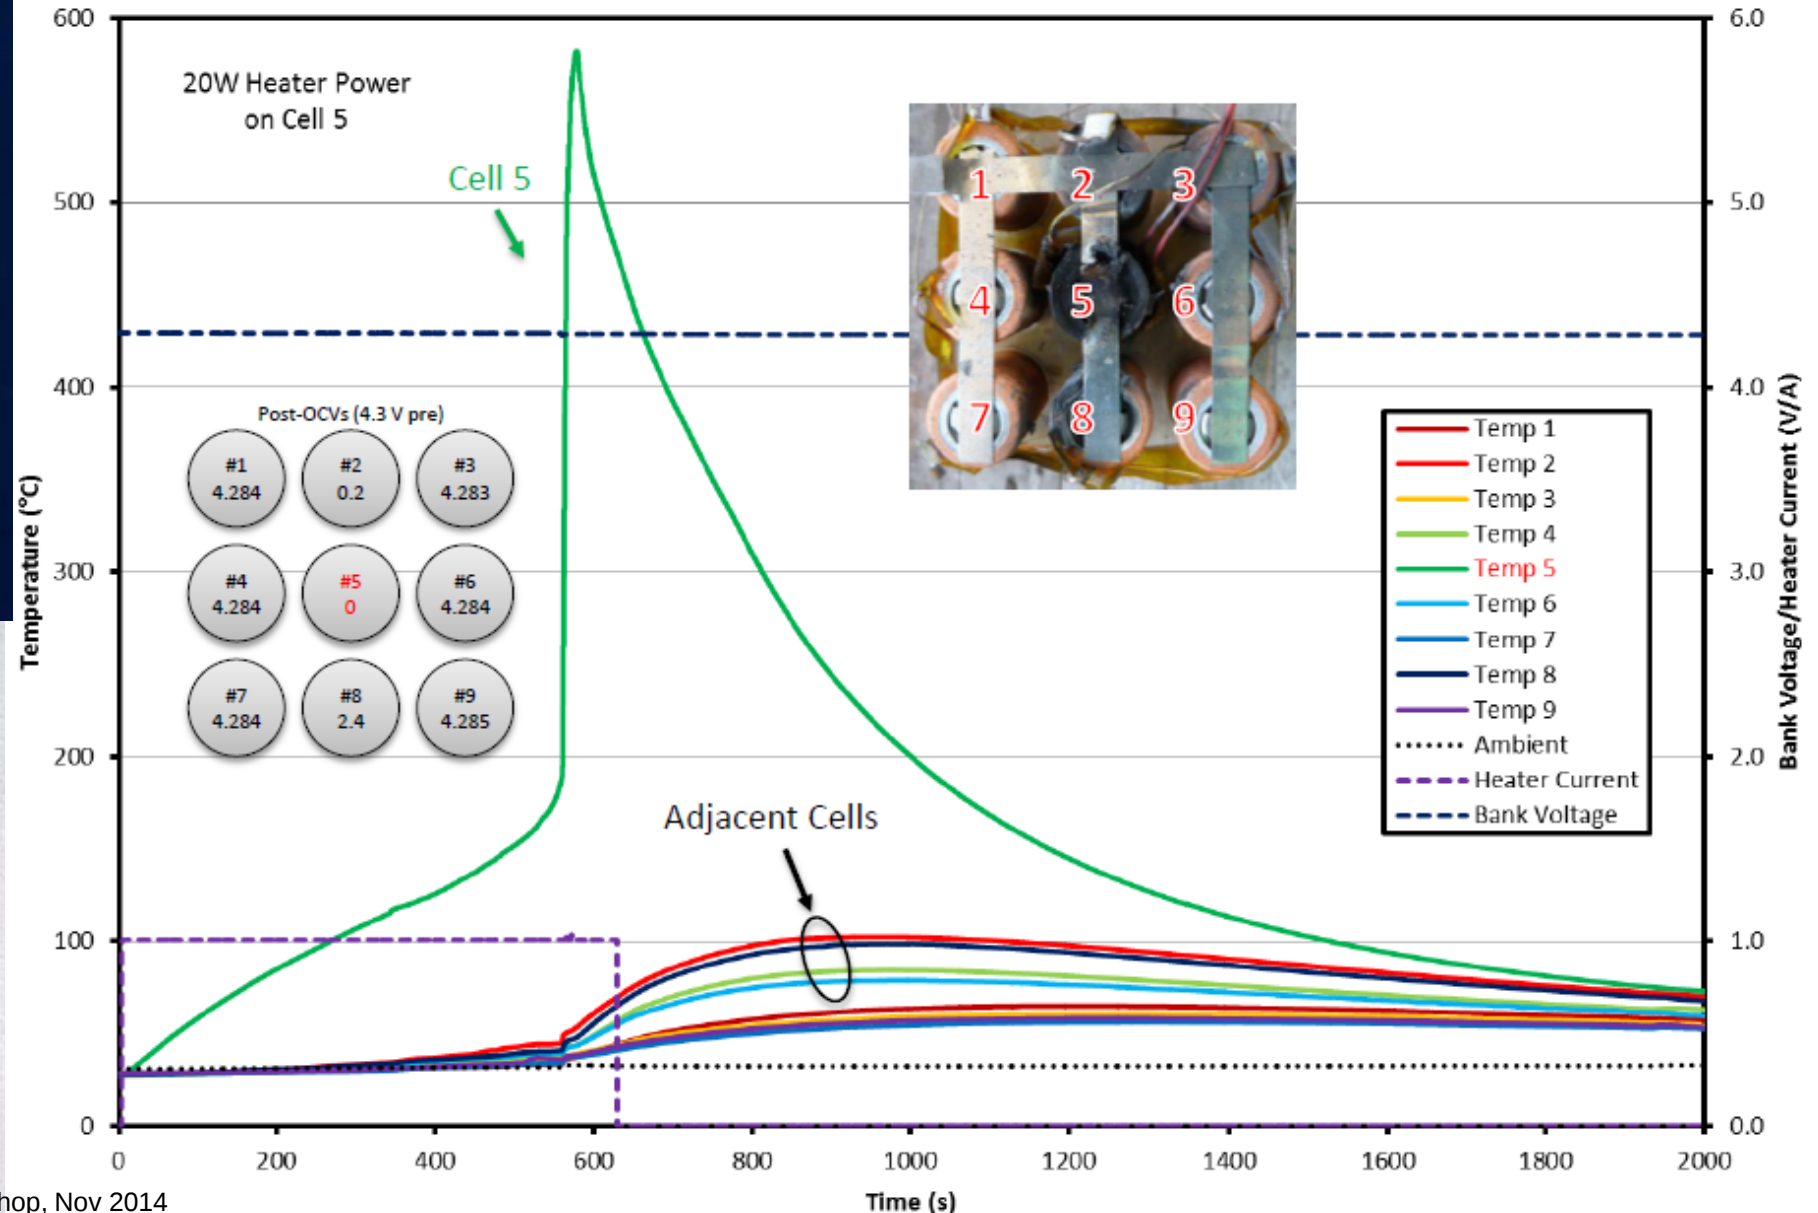

Orion Battery 14-cell Block

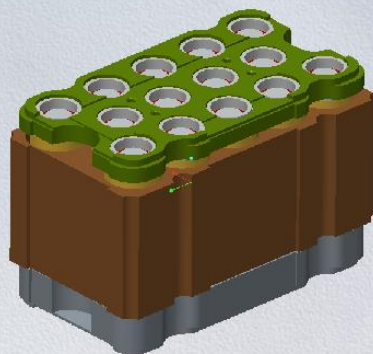

UPPER CAPTURE PLATE
G10 FR4 FIBERGLASS
COMP




MACOR VENT
TUBES



18650 CELL




SYNTACTIC
FOAM LINER

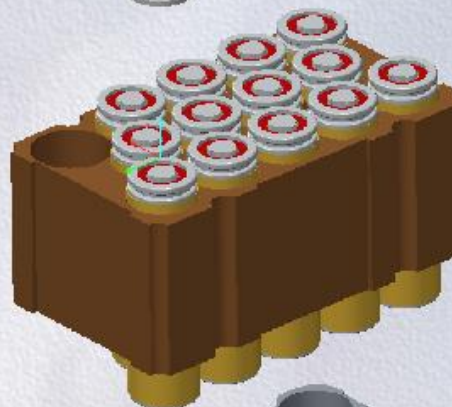


304 Stainless
Steel Sleeve –
9 mil wall
thickness



LOWER HEAT-SINK
CAPTURE PLATE
6061-T651 ALUM

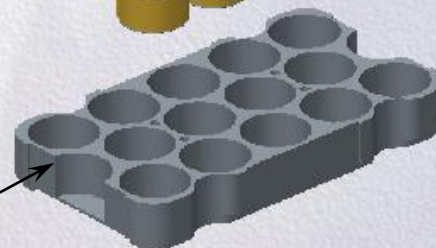



Orion 14P-8S Superbrick

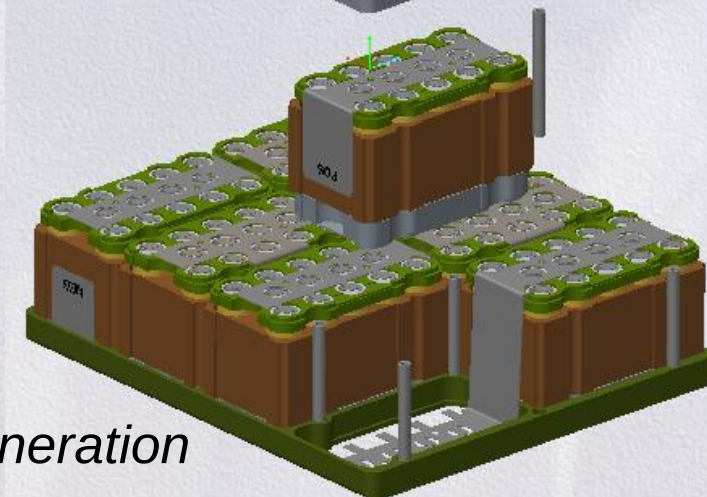

*Draw cell heat generation
through cell bottom*

Isolating vs Providing a heat path

- If you thermally isolate cells (air)
 - Adjacent cell ΔT rise 80-100°C
 - ***Limited to cell designs with little risk of side wall ruptures***
 - Achieves 160-170 Wh/kg
- Orion - Partially conductive (Draw heat from cell bottom)
 - Conduct heat to divider plate
 - Adjacent cell ΔT rise 60-70°C and shorter exposure
 - 14P-8S superbrick with SS sleeves achieves 150-160 Wh/kg

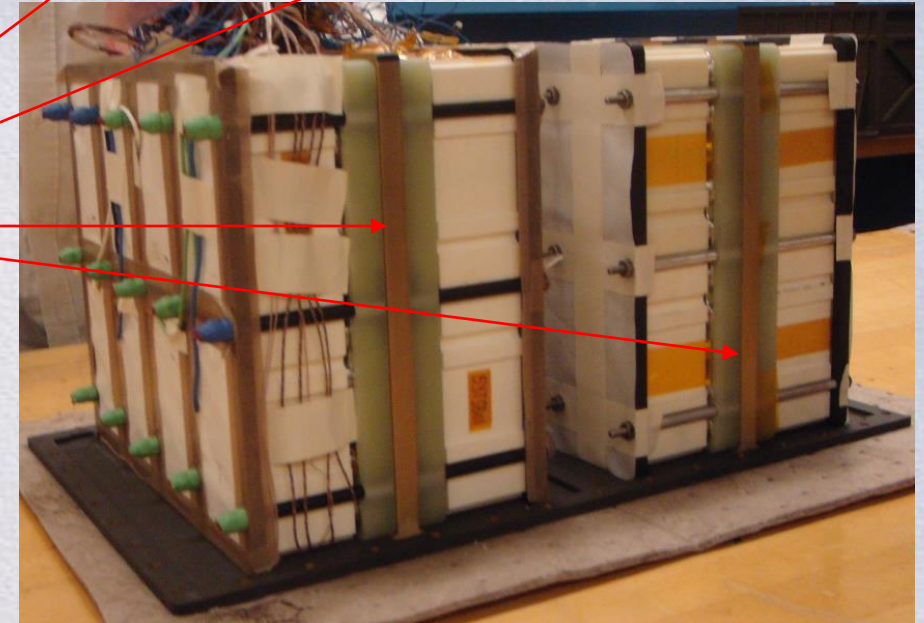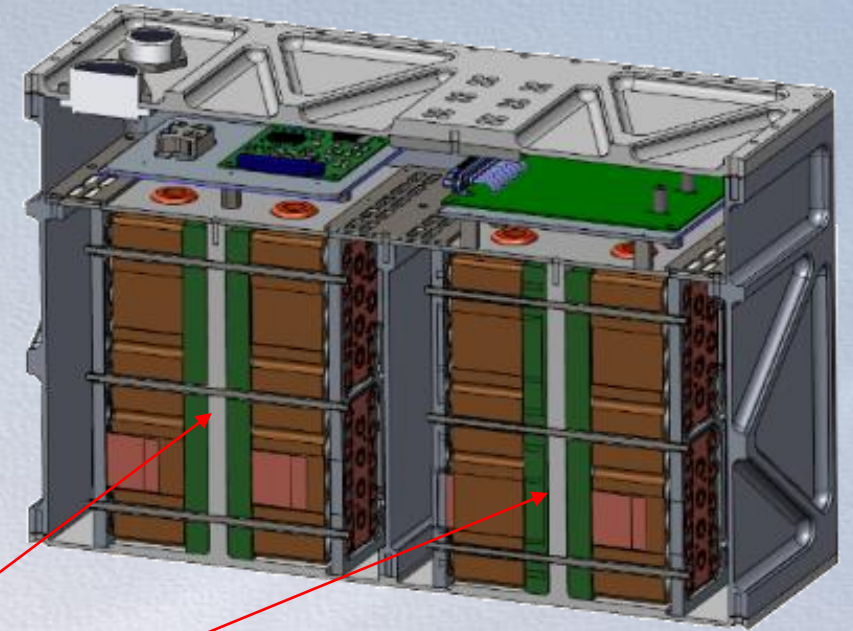



Safer, Higher Performing Battery Design

Compliance with the 5 rules

- **Minimize side wall ruptures** ✓
 - Al interstitial heat sink
- **No direct cell-cell contact** ✓
 - 0.5mm cell spacing, mica paper sleeves on each cell
- **Individually fusing cell in parallel** ✓
 - 12A fusible link
- **Protecting adjacent cells from TR ejecta** ✓
 - Ceramic bushing lining cell vent opening in G10 capture plate
- **Include flame arresting vent ports** ✓
 - Tortious path with flame arresting screens
 - Battery vent ports lined with steel screens

Features


- 65 High Specific Energy Cell Design 3.4Ah (13P-5S)
- 37Ah and 686 Wh at BOL (in 16-20.5V window)
- Cell design likely to side wall rupture, but supported

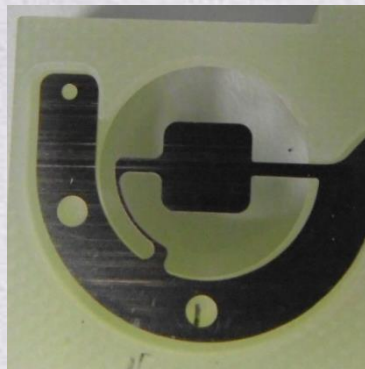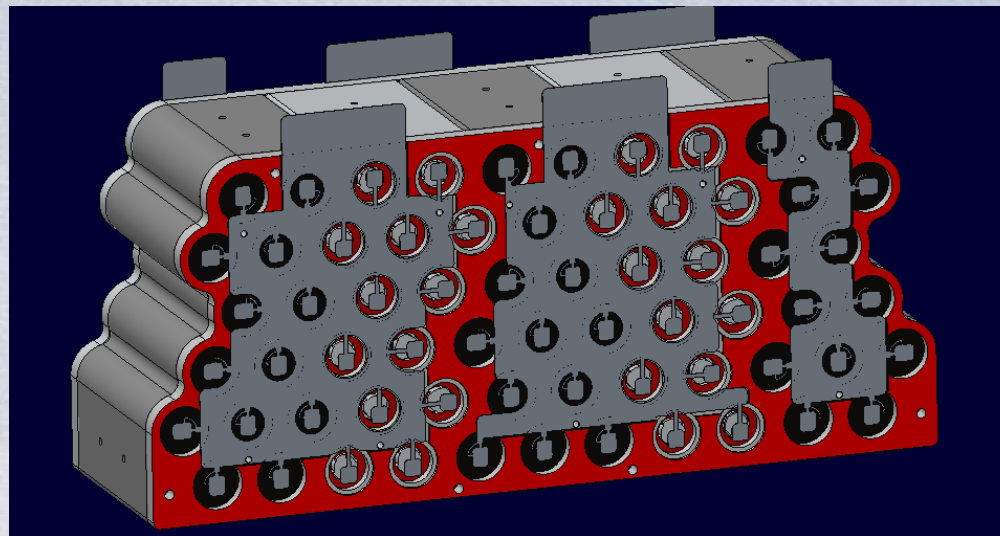

65-Battery Brick

Al Interstitial Heat Sinks


No corner cells - Every cell has at least 3 adjacent cells

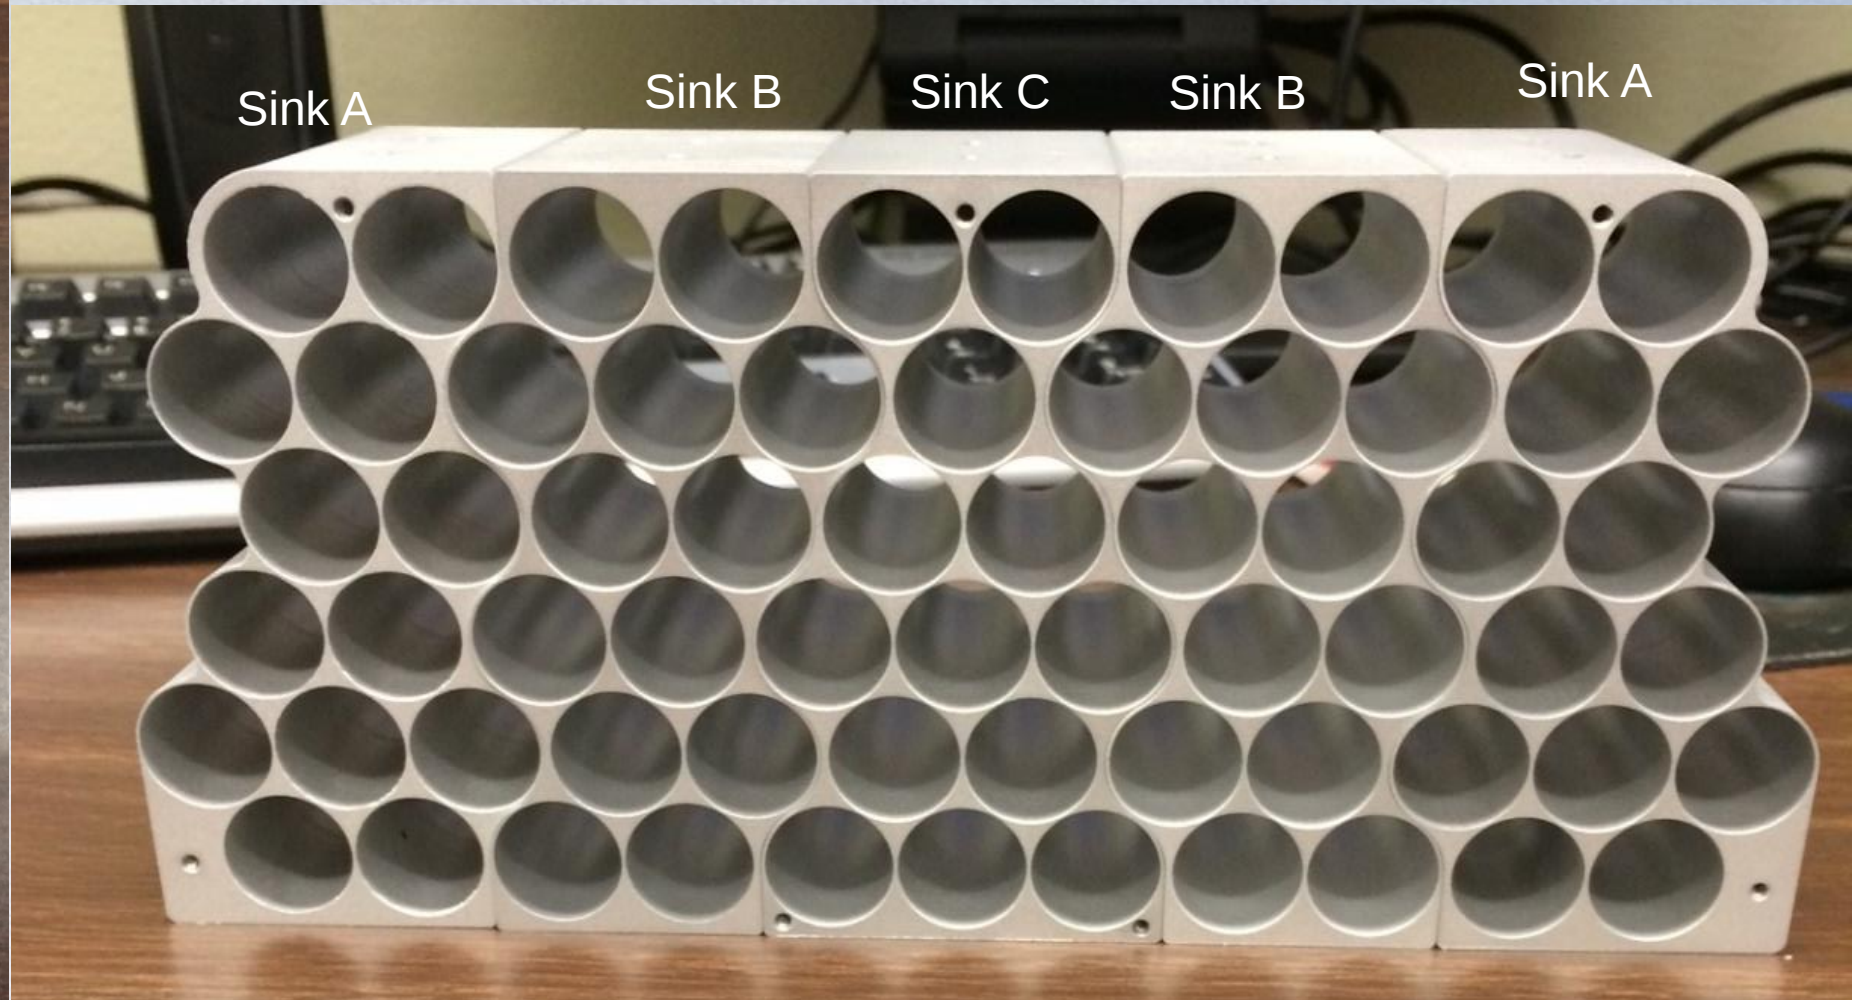

0.5mm cell spacing, Al 6061T6


Cell Brick Assembly > 180 Wh/kg

Mass Categories	g	%
3.4Ah 18650 Cells	3012.75	71.3%
Heat sinks	824.95	19.5%
Mica sleeves	182.31	4.3%
Capture plates	115.81	2.7%
Ceramic bushings	60.15	1.4%
Ni-201 bussing	29.71	0.7%
Total	4225.7	

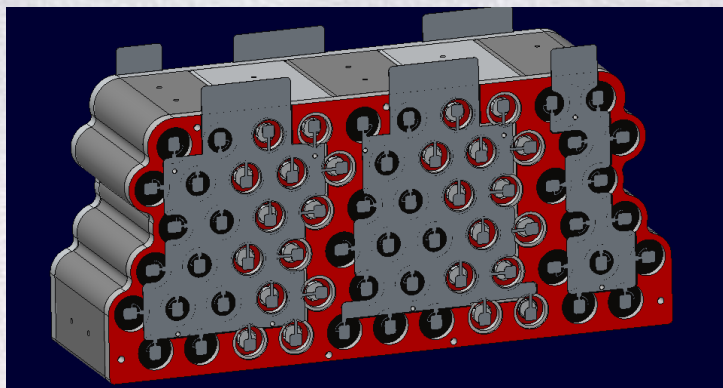

- With 12.41 Wh/cell, cell brick assembly achieves **191 Wh/kg**
 - Assuming 12.41Wh per cell
- Design has 1.4 parasitic mass factor
 - Cell mass x 1.4 = Brick mass



Mass Distribution

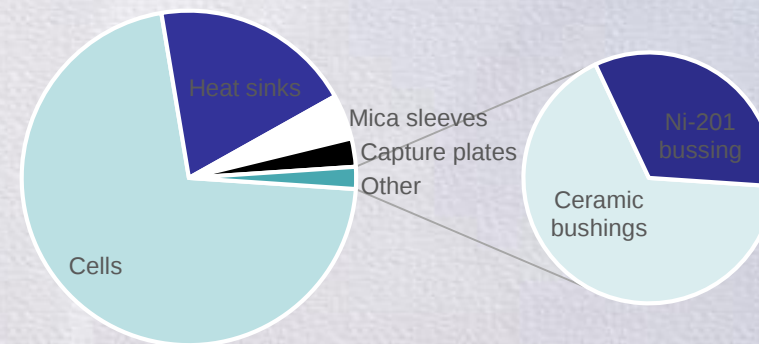

■ Cells
 ■ Heat sinks
 ■ Mica sleeves
 ■ Capture plates
 ■ Ceramic bushings
 ■ Ni-201 bussing

NREL/NASA Cell Internal Short Circuit Device

13

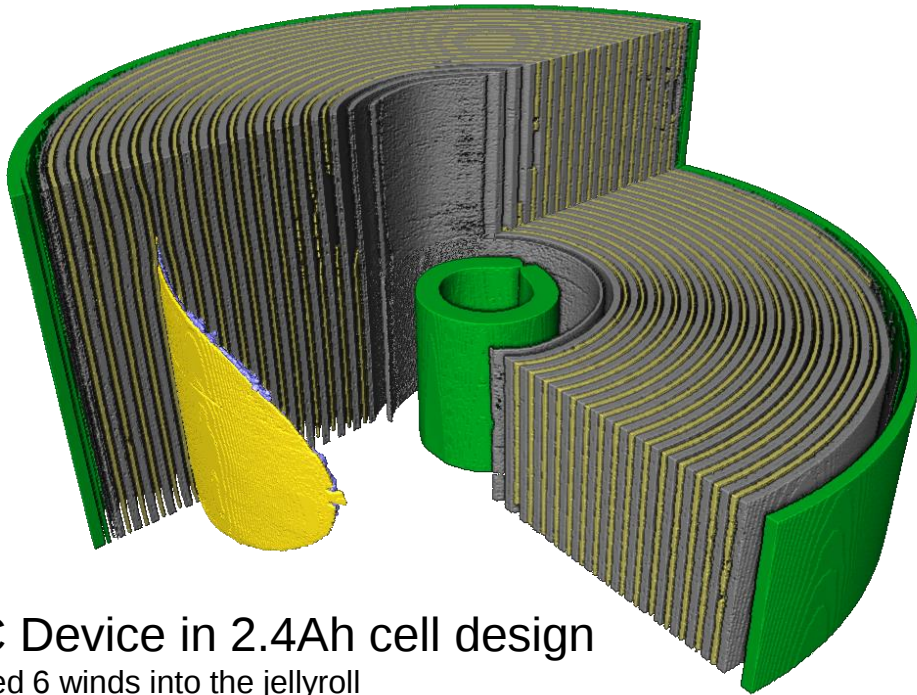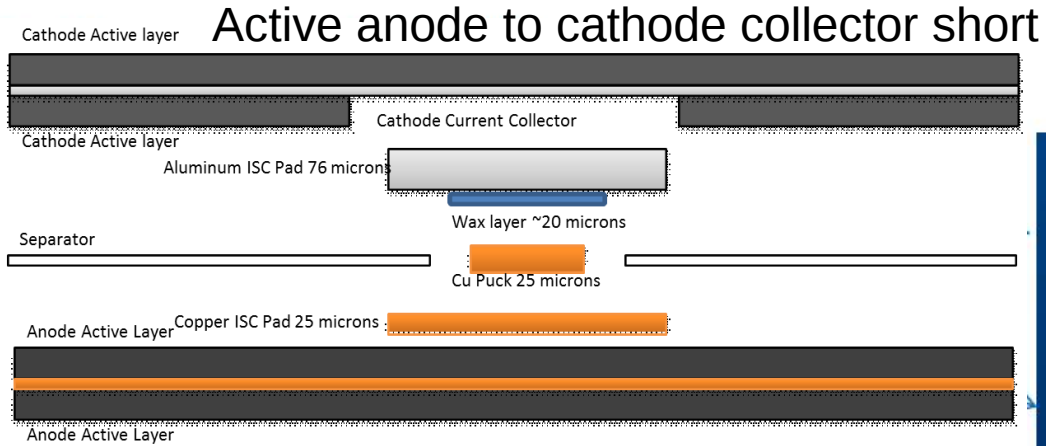


ISC Device in 2.4Ah cell design

Placed 6 winds into the jellyroll

5 mm

Tomography credits: University College of London

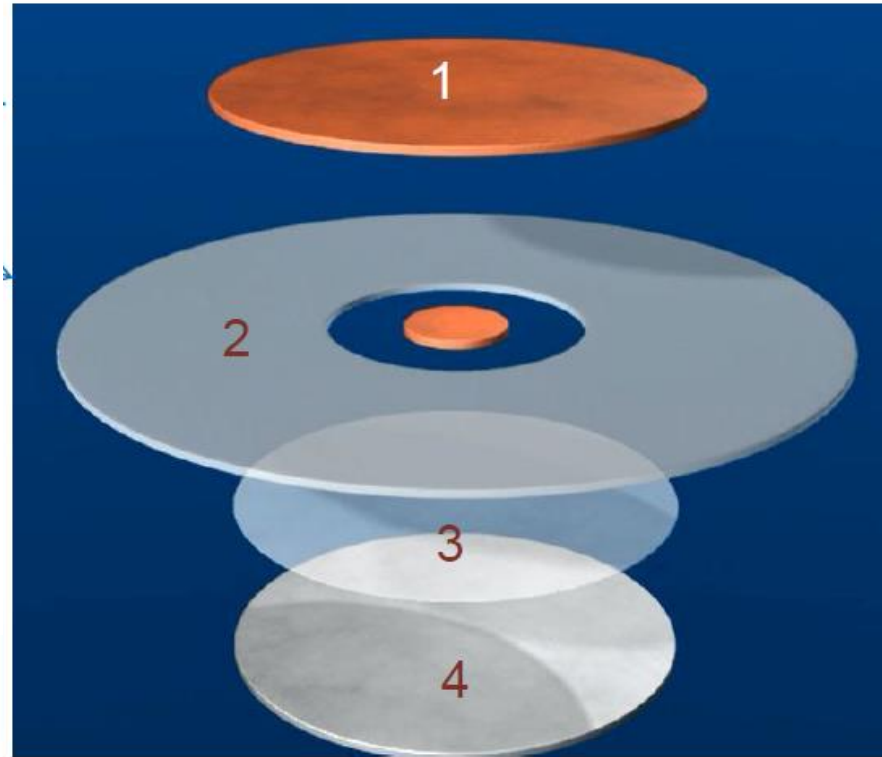

Graphic credits: NREL

Top to Bottom:

1. Copper Pad
2. Battery Separator with Copper Puck
3. Wax – Phase Change Material
4. Aluminum Pad

2010 Inventors:

- Matthew Keyser, Dirk Long, and Ahmad Pesaran at NREL
- Eric Darcy at NASA

US Patent # 9,142,829
issued in 2015

Thin (10-20 μm) wax
layer is spin coated
on Al foil pad



Wax formulation used
melts $\sim 57^\circ\text{C}$

Runner-up NASA
Invention of 2017




2016 Award Winner


No TR Propagation, Only Smoke Exits Battery

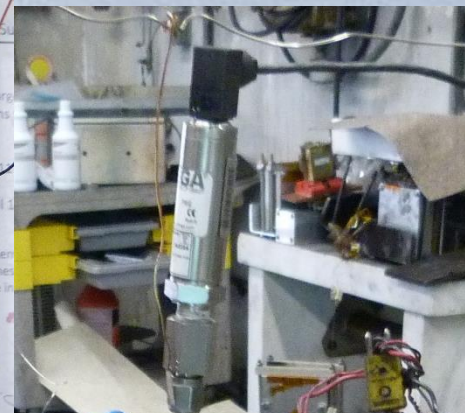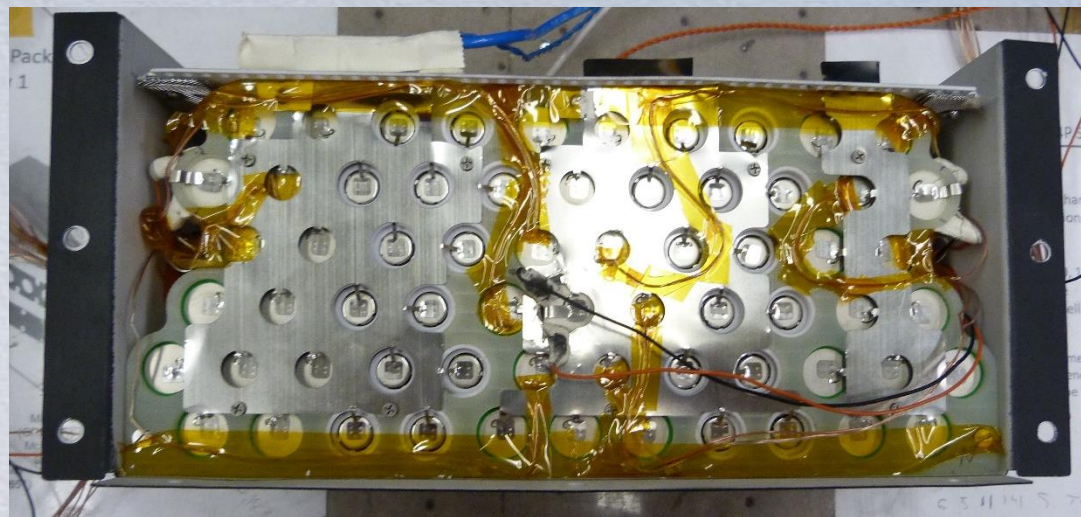


Mesh 40 & 30 steel screens arrest flames and sparks

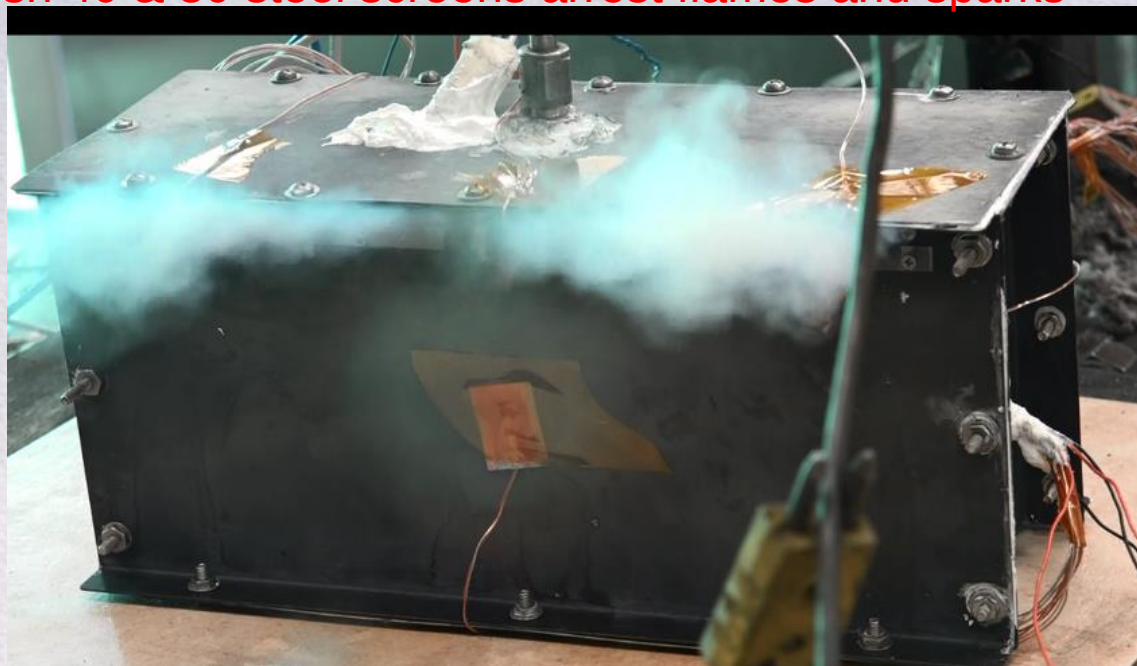

However, trigger cell was only 2.4Ah cell

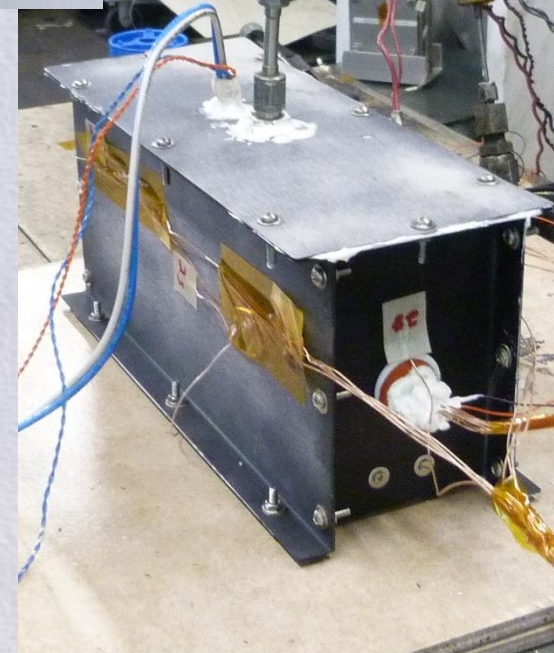

1st Test with 3.5Ah ISC Device Trigger Cell


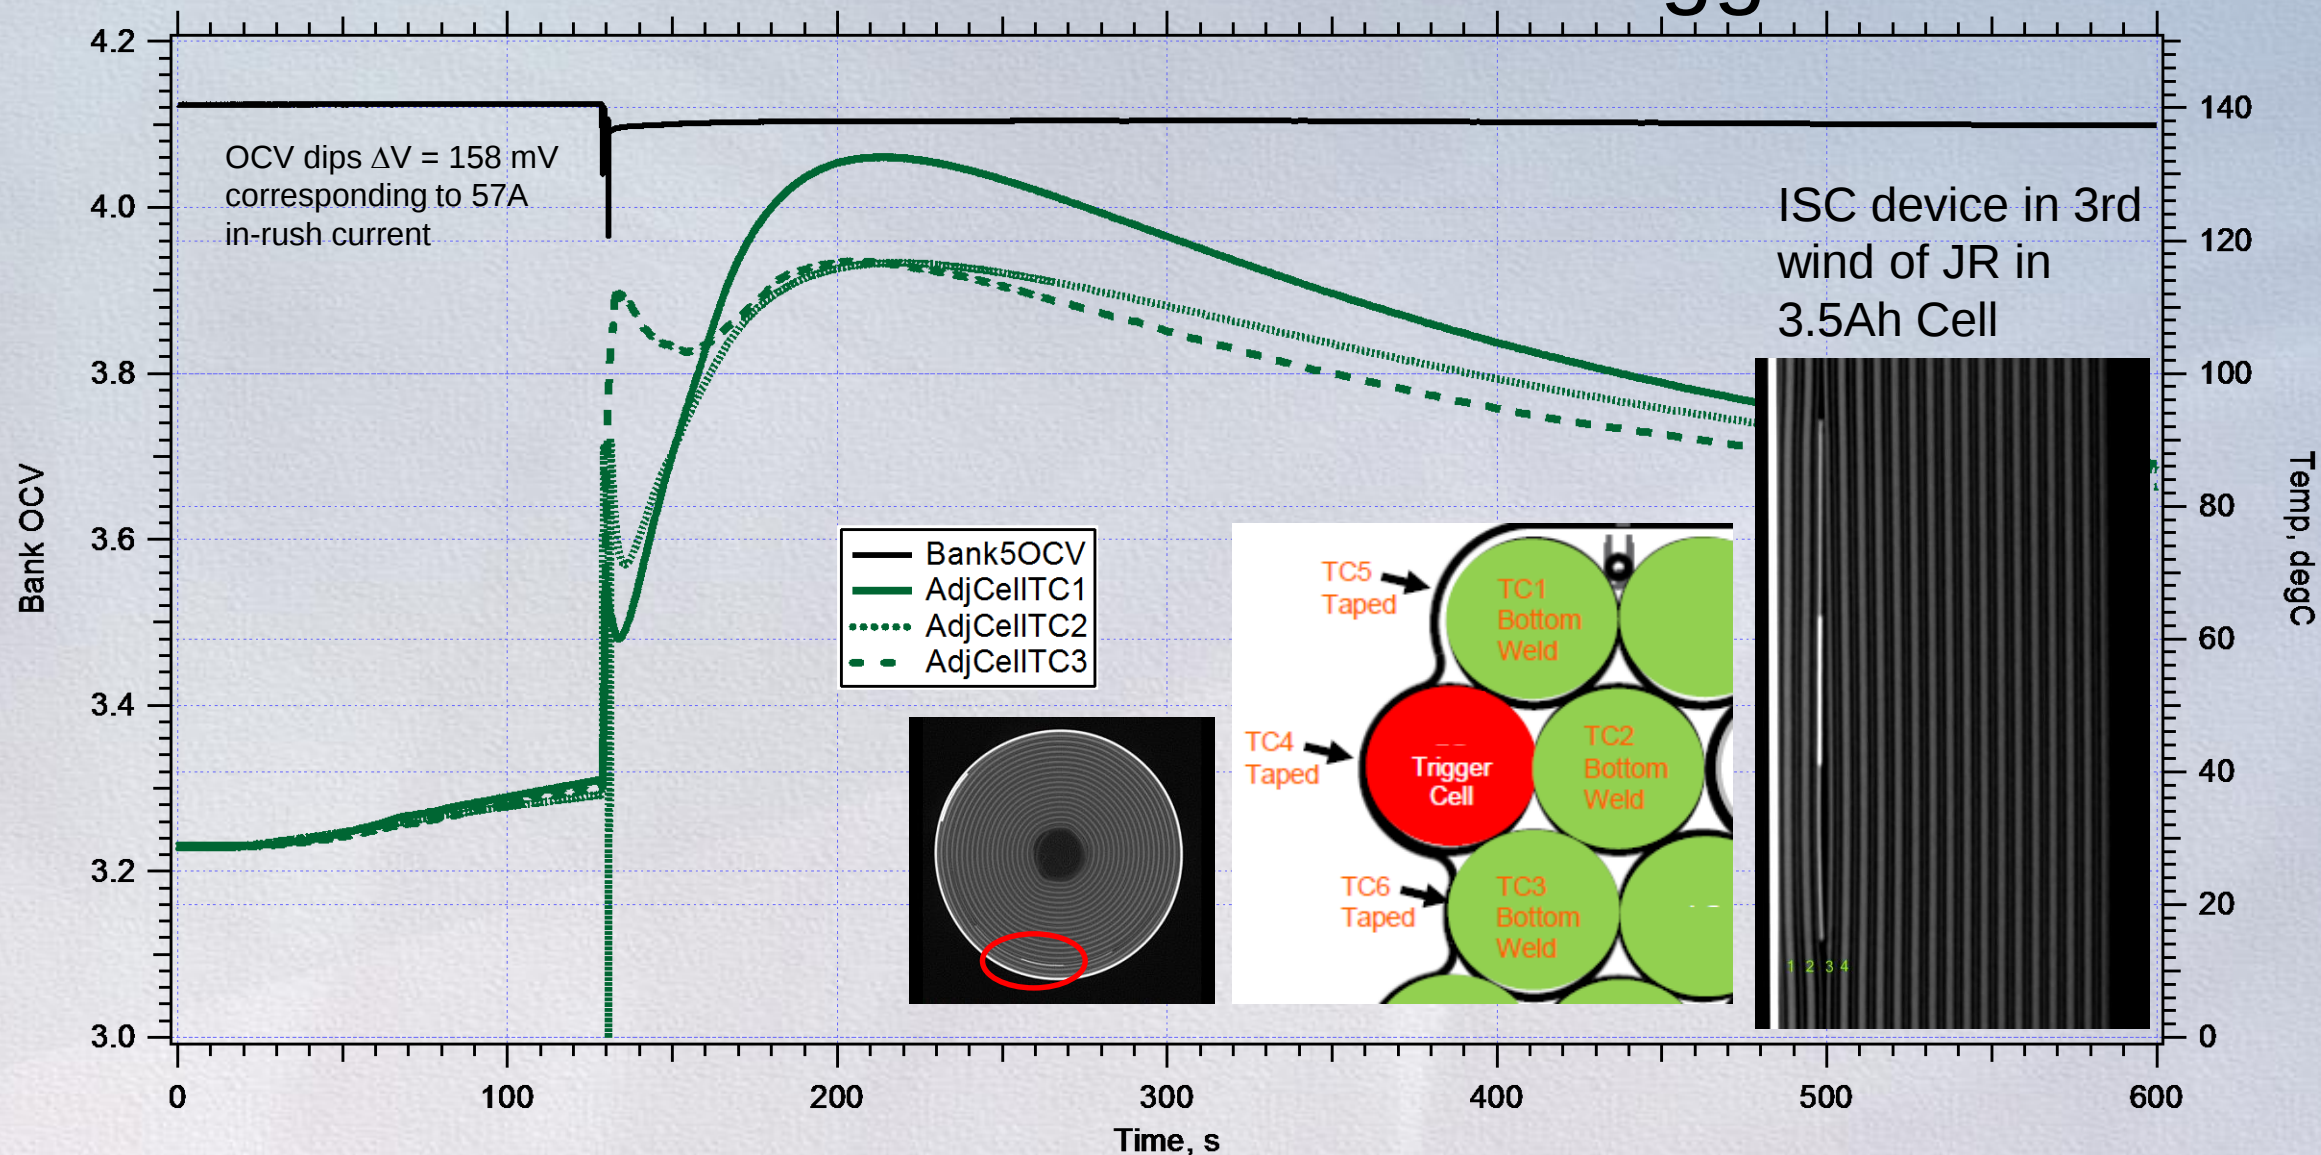


Adjacent cell temperatures TC1, TC2, and TC3 peak at **133°C**, 117°C, and 117°C in 77-87s from onset temperatures of 39°C, 37°C, and 38°C for $\Delta T =$ **94°C**, 77°C, and 78°C, respectively.

No TR Propagation – Only Clean Smoke Exits Gore Vent

Flame arresting steel screens

3.5Ah Cell with ISC device trigger location

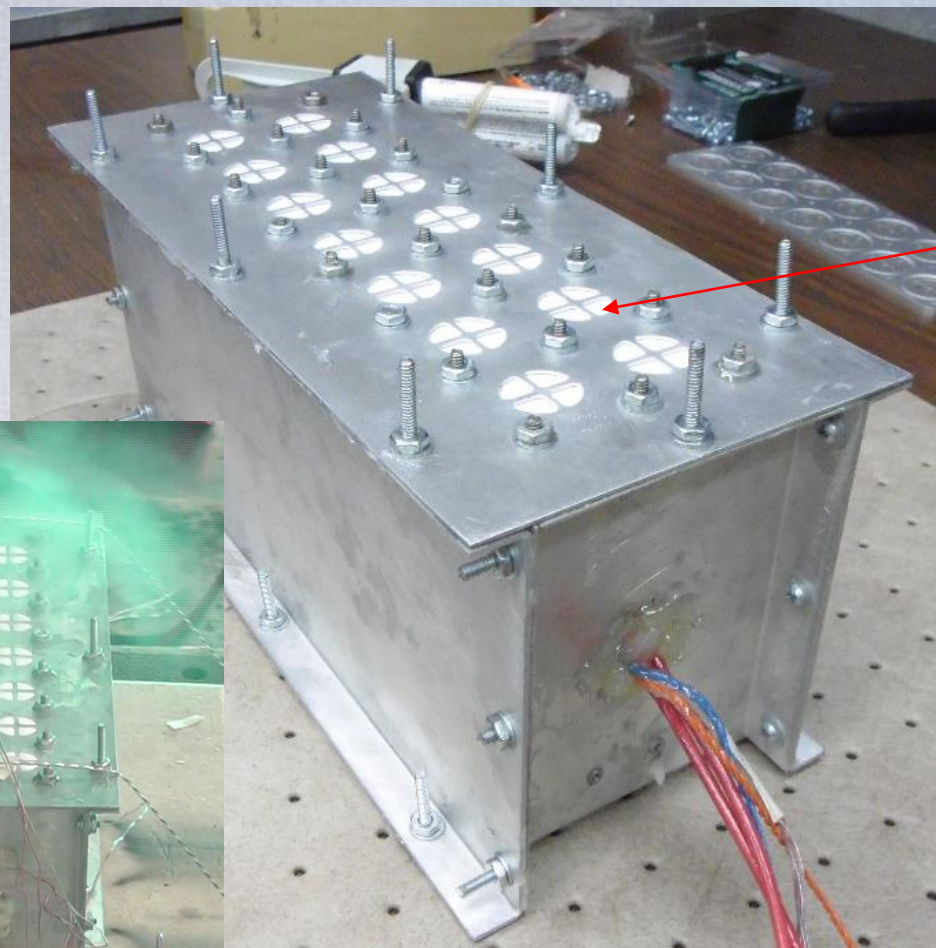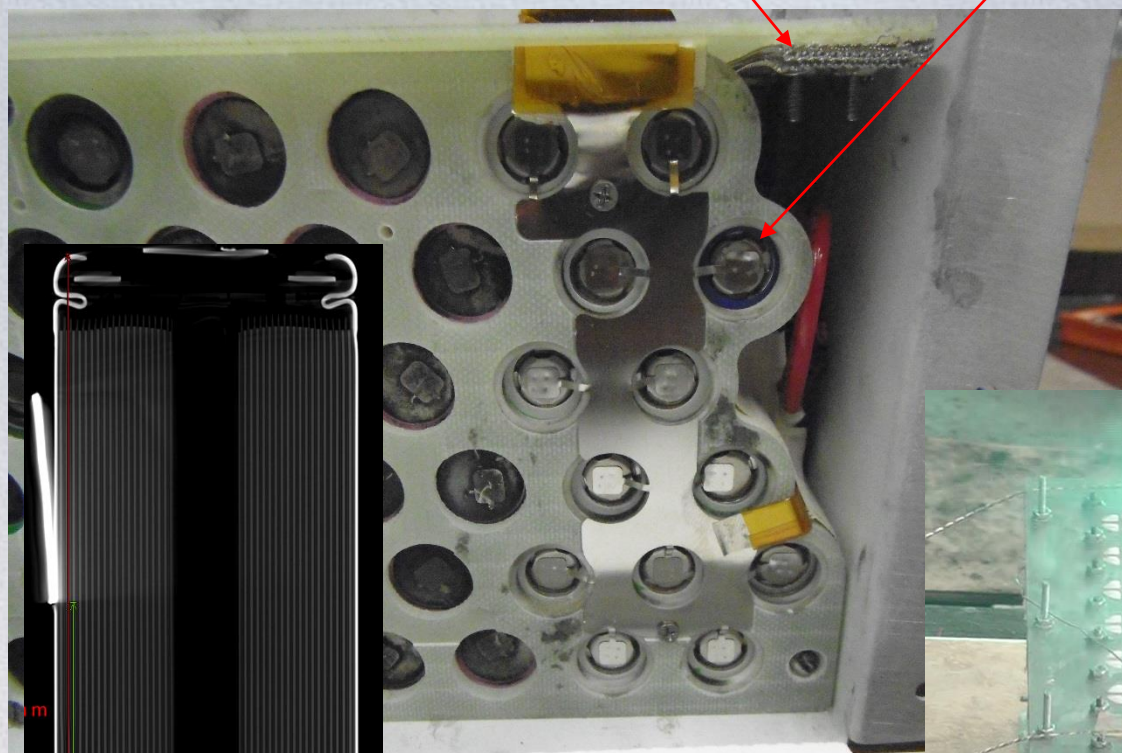

Gore fabric
Vent design

3.5Ah cell with
ISC device in 3rd
JR wind


Battery bottom edge seal fails and relieves
internal pressure at ~11.4 psig (0.77 bar)

3.5 Ah Trigger Cell Experienced a Side Wall Breach

Trigger cell was a struggle to extract from heat sink.

The mica insulation was severely damaged adjacent to rupture

Cell	OCV (V)	Mass (g)
Trigger	0	17.161
1	3.474	46.801
2	0.336	46.691
3	0	46.671

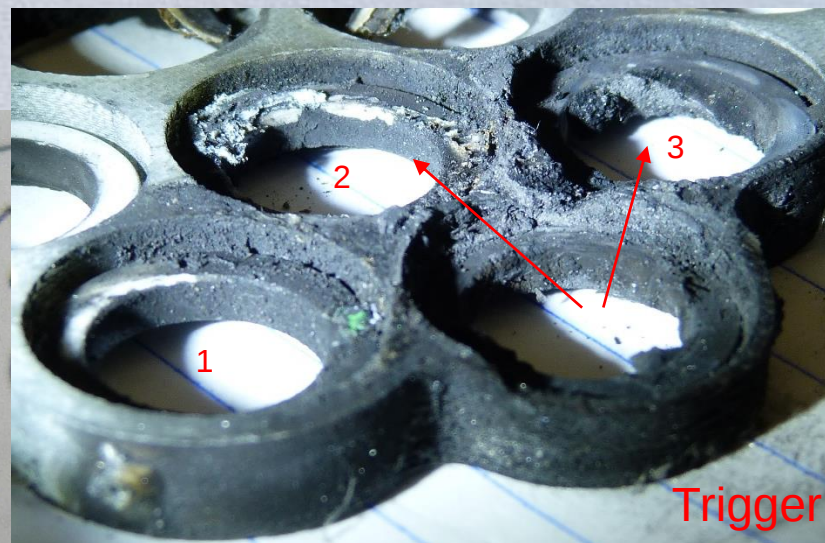

Side-wall Breach of MJ1 Cell


ISC device 3 winds in

Side-wall breach


Hotspot clocked with ISC device followed by side-wall breach (SWB)

First capture of side wall breach using high speed X-ray imaging.

Bulging around the point of initiation occurs and the propagation front makes early contact with the cell casing. The direction of flow shifts towards the widening SWB.

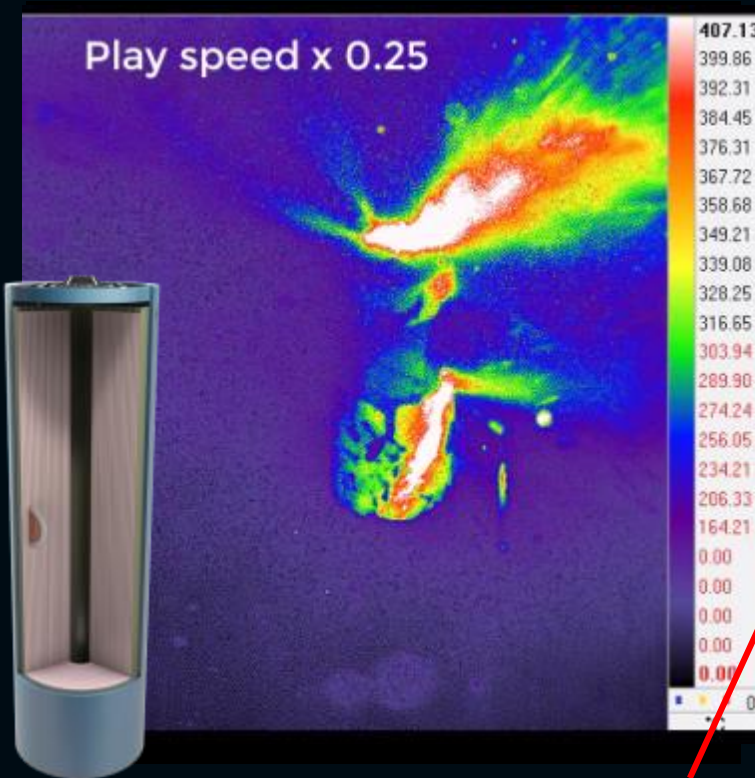


ISC device

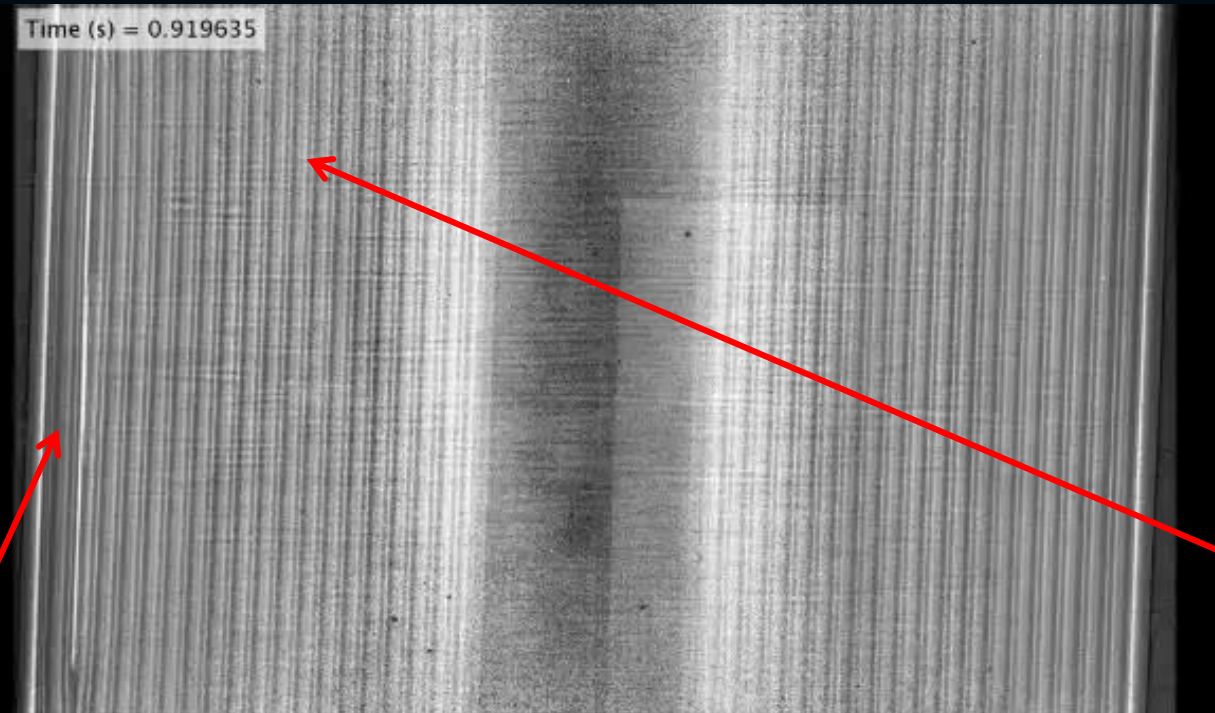

2nd Test 3.5Ah ISC Trigger Cell – OCV, Heaters, & Interior Temps

19

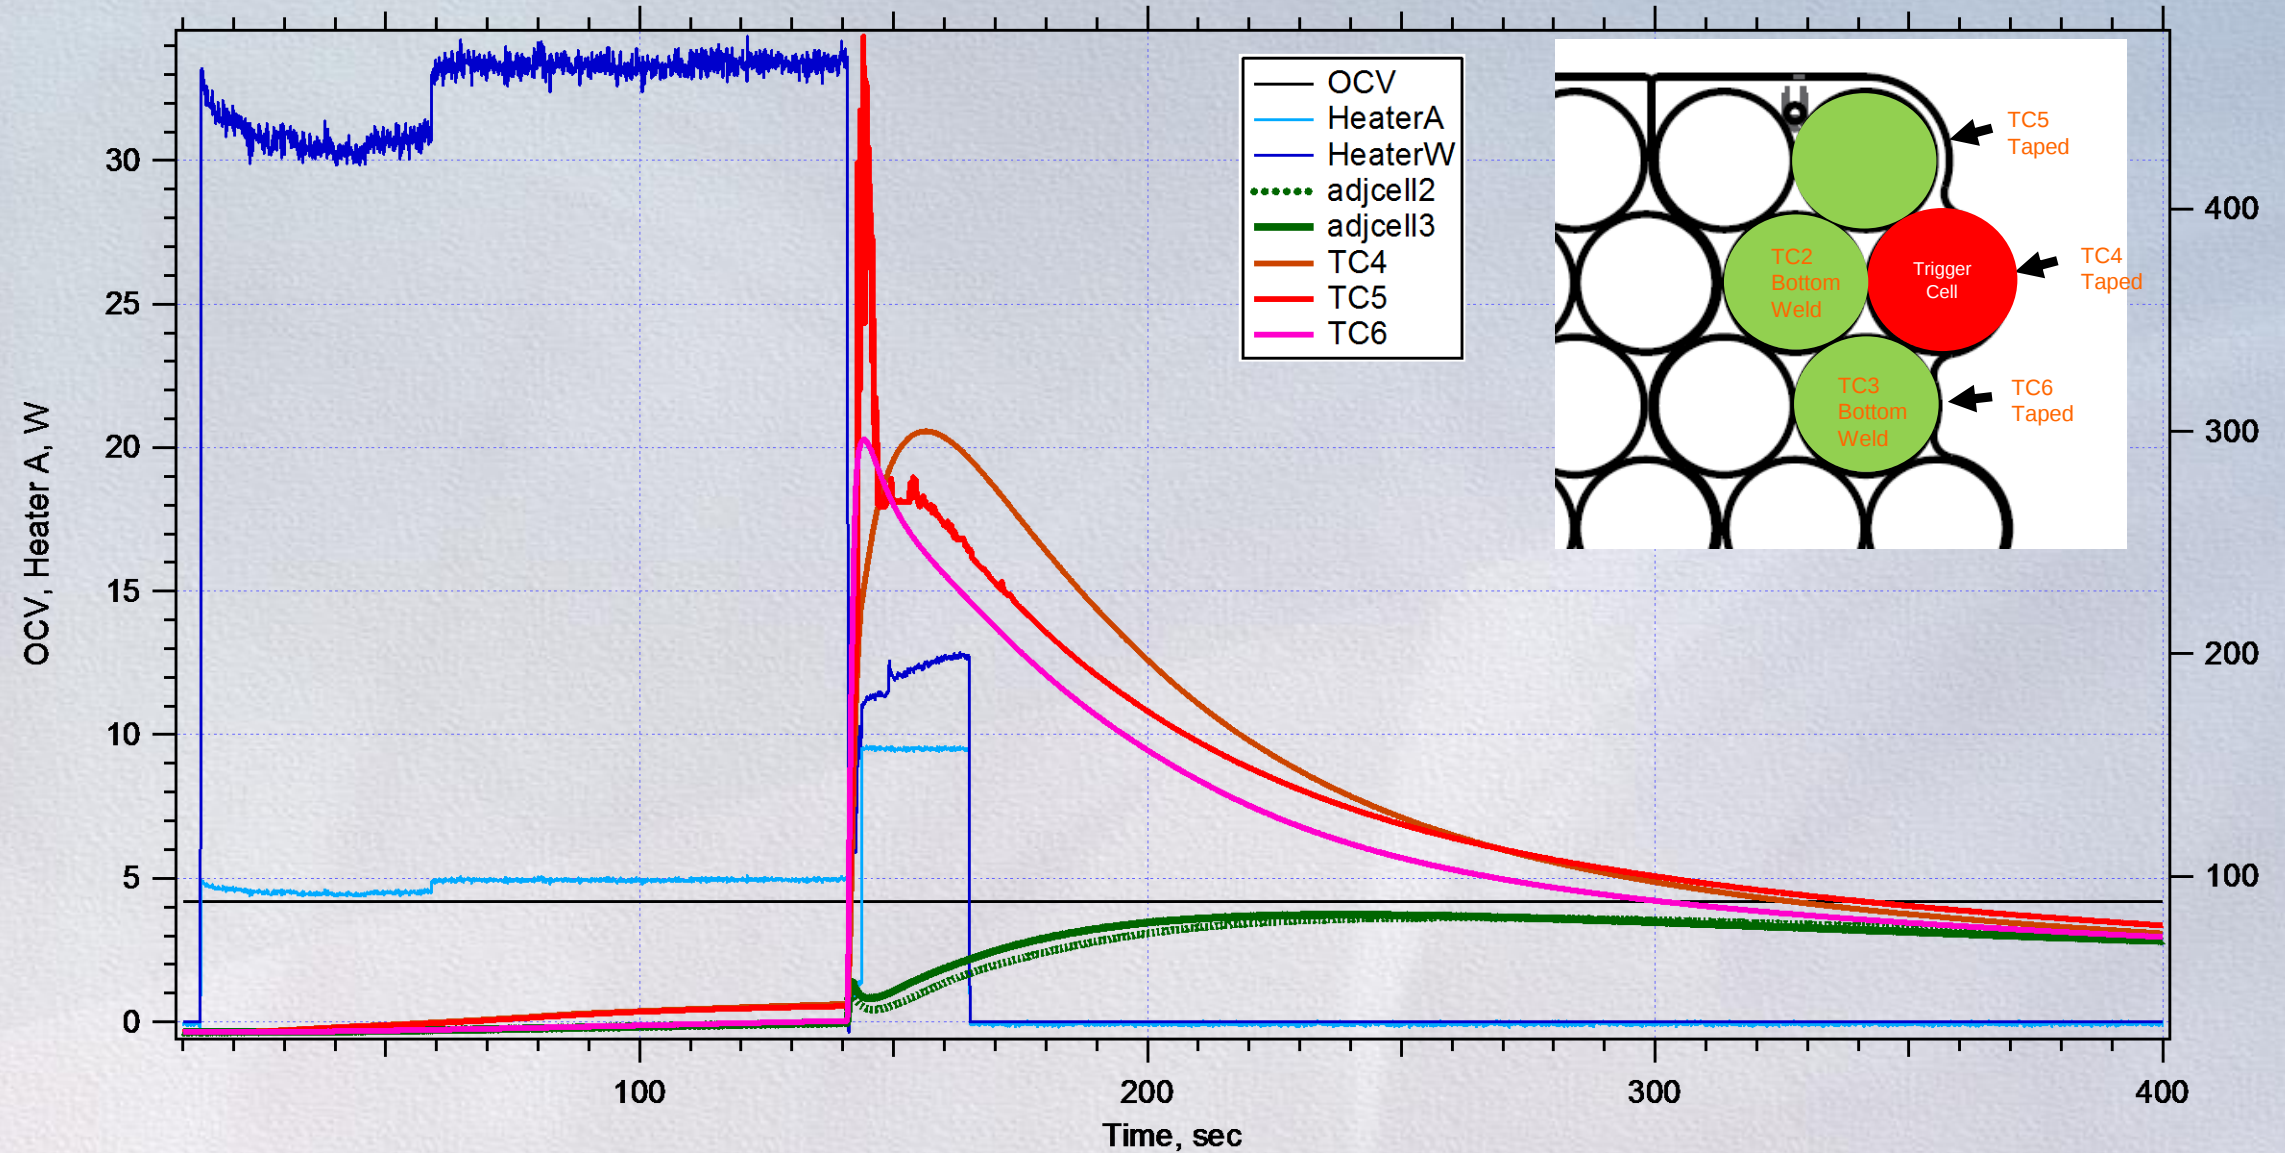

Adjacent cell max temperatures < 83°C

Post-Test Photos – Trigger Cell



Post-Test Mass: 25.3g

Bottom breach

Spin groove is stretched

Findings from 2nd Test with 3.5Ah ISC Trigger Cell


- ISC device in 3.5Ah 18650 cell triggered in 127 seconds with bottom heater at 32W average
 - Very similar initiation time (1st run was in 119s)
 - Very similar biasing of adjacent cells (34-35°C) at onset of TR (1st run at 37-39°C)
- No propagation of TR
 - Despite bottom breach of trigger cell, which damaged the G10/FR4 negative capture plate
 - Reusing the same heat sinks from the first test – undamaged after both tests
- Max adjacent cell temperatures < 83°C
 - Adjacent cell temperature rise was 46-47°C, significantly lower than 1st run (77-94°C)
 - Bottom breach yields a much less severe impact than side wall breach

LG 3.35Ah Cell Design with Bottom Vent



	3.50Ah vs 3.35Ah	
Diameter	max. 18.65	max. 18.45
Height	max. 65.3	max. 65.6
Wall thickness	0.15	0.22
Mass	47.0 g	47.5 g
Capacity	3.5Ah	3.4 Ah
Energy	12.7wh	12.3 Wh
Voltage	2.5~4.2	2.5~4.2
Max current	10A	10A
AC Resistance	30	23

3.35Ah cell design, a bit more power capable than 3.5Ah design

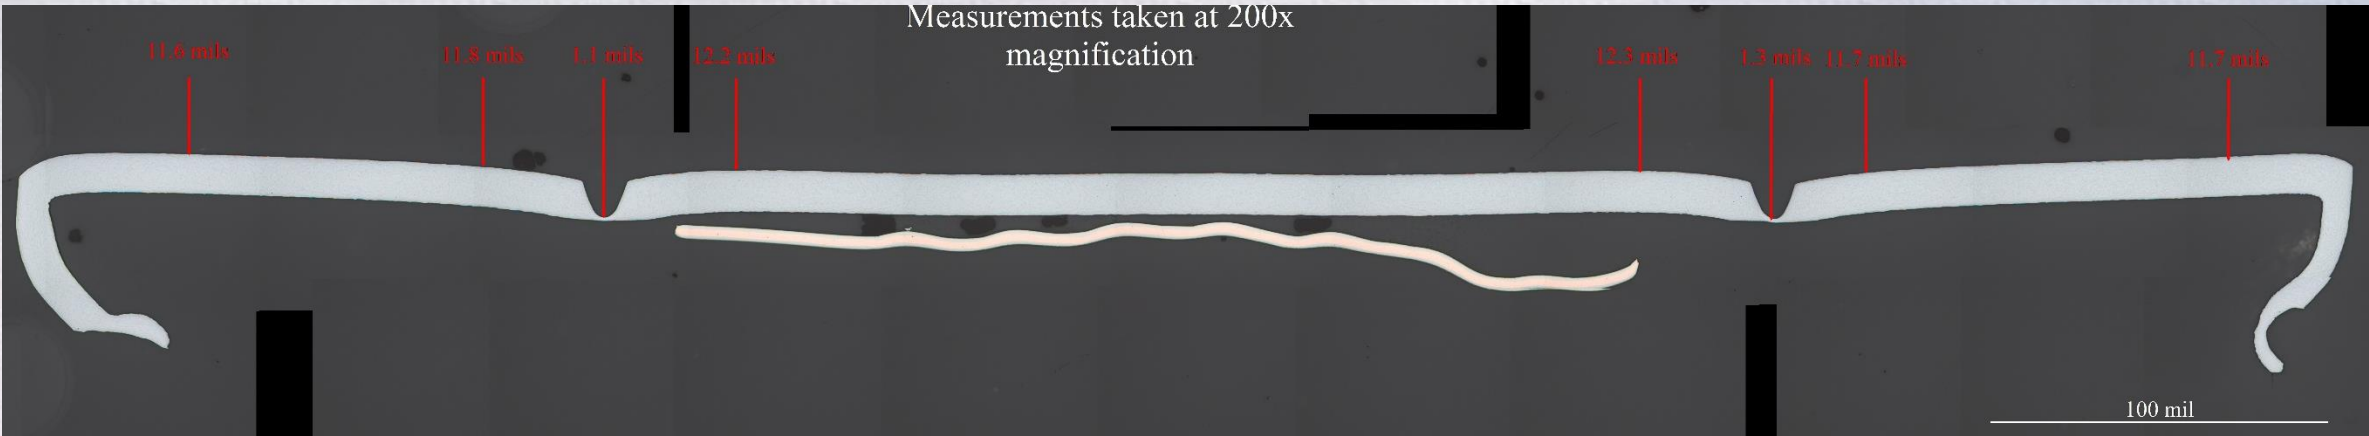


Heat Distribution Calorimeter

Characterising the difference between failure types

Highlight risks associated with the spread of heat sources when cells rupture and compare to when they remain intact

Heat Distribution Calorimeter

- Measure heat output from single cylindrical cells
- **Decouple heat generated within the cylindrical casing and heat generated by ejected material**
- X-ray transparent for in-situ high-speed X-ray imaging
- Scalable to fit any cylindrical cell design
- Ambidextrous design for bottom vent cells

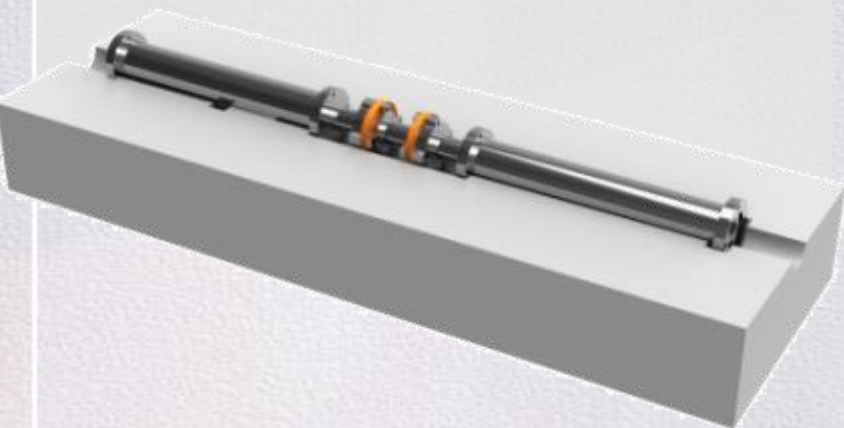

Bore Chamber



- Slows down and extracts heat from escaping flames and gas

Ejecta Mating

- Captures ejected solids such as the electrode assembly
- Thermally isolated from the cell chamber

Cell Chamber

- Contains the cylindrical cell
- Includes heating system for thermally induces failure

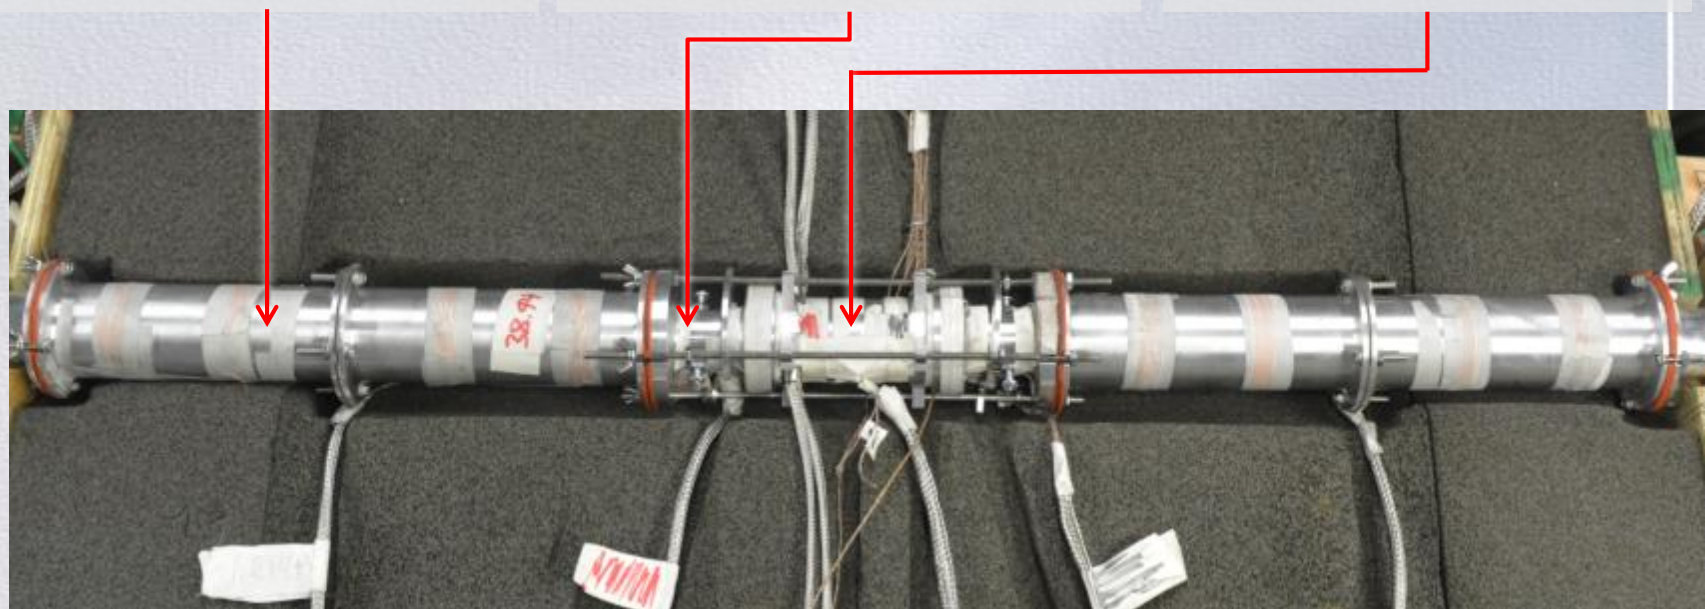

Heat Distribution Calorimeter

Calorimetry experiments have been conducted at the NASA JSC Energy Systems Test Area (ESTA) and at the European Synchrotron Radiation Facility (ESRF) and Diamond Light Source (DSL):

- 38 sets of data processed for successful tests processed to date
- 27 runs at the ESRF and 62 very recently performed with the new calorimeter at the DSL

Key Findings

- Higher energy density cells released more heat
- 3.5Ah MJ1 cells generated 22 % more heat than 3.35Ah cells that have 3 % more capacity
- The distribution of heat released from ejected material and from the cylindrical body of the cell was measured
- A combination of 3.35Ah cells with bottom vents (BV) and without bottom vents (NBV) were tested

Item	Unit	LG 18650-MJ1	3.35 Ah LG 18650	Samsung 18650-30Q	Molicel 18650-J
Capacity at 100% SOC	Ah	3.43	3.35	3.0	2.3
Nominal Voltage	V	3.67	3.7	3.6	3.78
Stored Electrochemical Energy	kJ	45.3	44.6	38.9	31.3
Cell Mass	g	47	47	48	47
Special Features Tested	-	-	BV / ISC/ TCW	-	Separator
Number of Successful Tests	-	9	22	3	5
Test Facility	-	ESTA	ESRF	ESTA	ESRF



BV: Bottom Vent Cells

NBV: Non-Bottom Vent Cells

ISC: Internal Short Circuit Device

TCW: Thin Can Wall

S1 & S2: Two proprietary separators

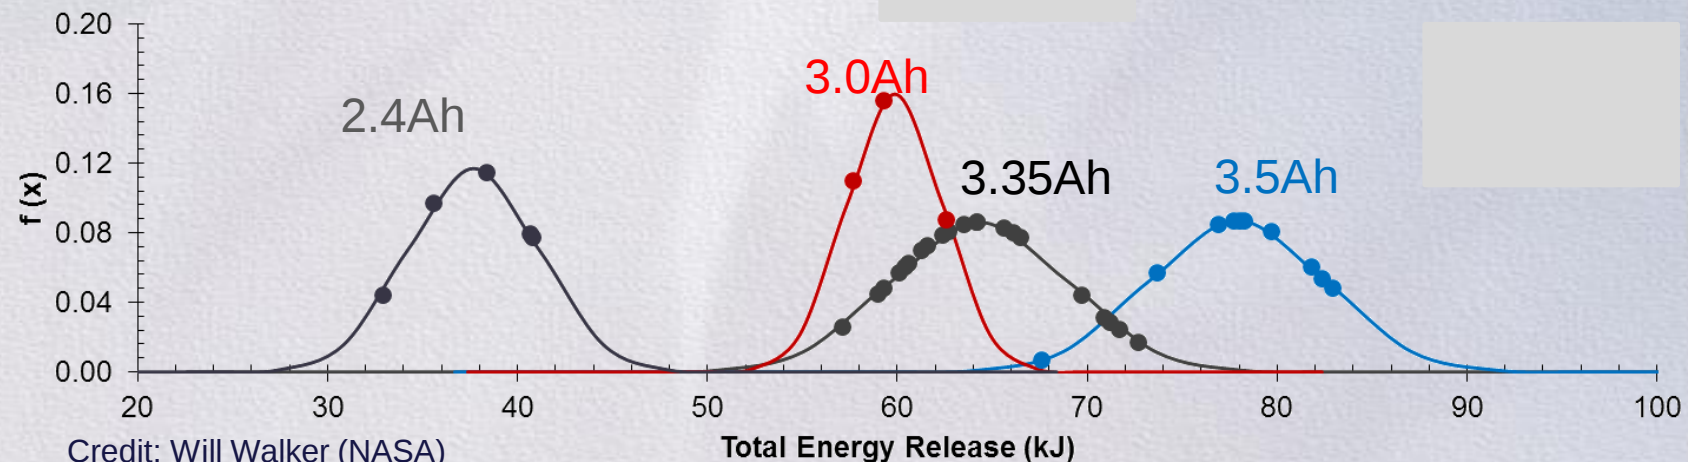

Heat Distribution Calorimeter – 3.35Ah cells

Comparison between the heat distribution of cells with and without bottom vents

Key Findings

- Bottom vent cells produce around 12 % less heat than non-bottom vent cells.


- May be due to bottom-vent cells ejecting less material and thermal runaway reactions being oxygen limited.

- A higher proportion of heat is generated within the cylindrical casing in cells with bottom vents.

- This may be due to a decreased risk of the cell bursting and ejecting the electrode assembly

- A higher proportion of heat is generated from ejected material in cells without bottom vents.


- For both cells, over 60 % of the heat generated during thermal runaway stems from ejected material.

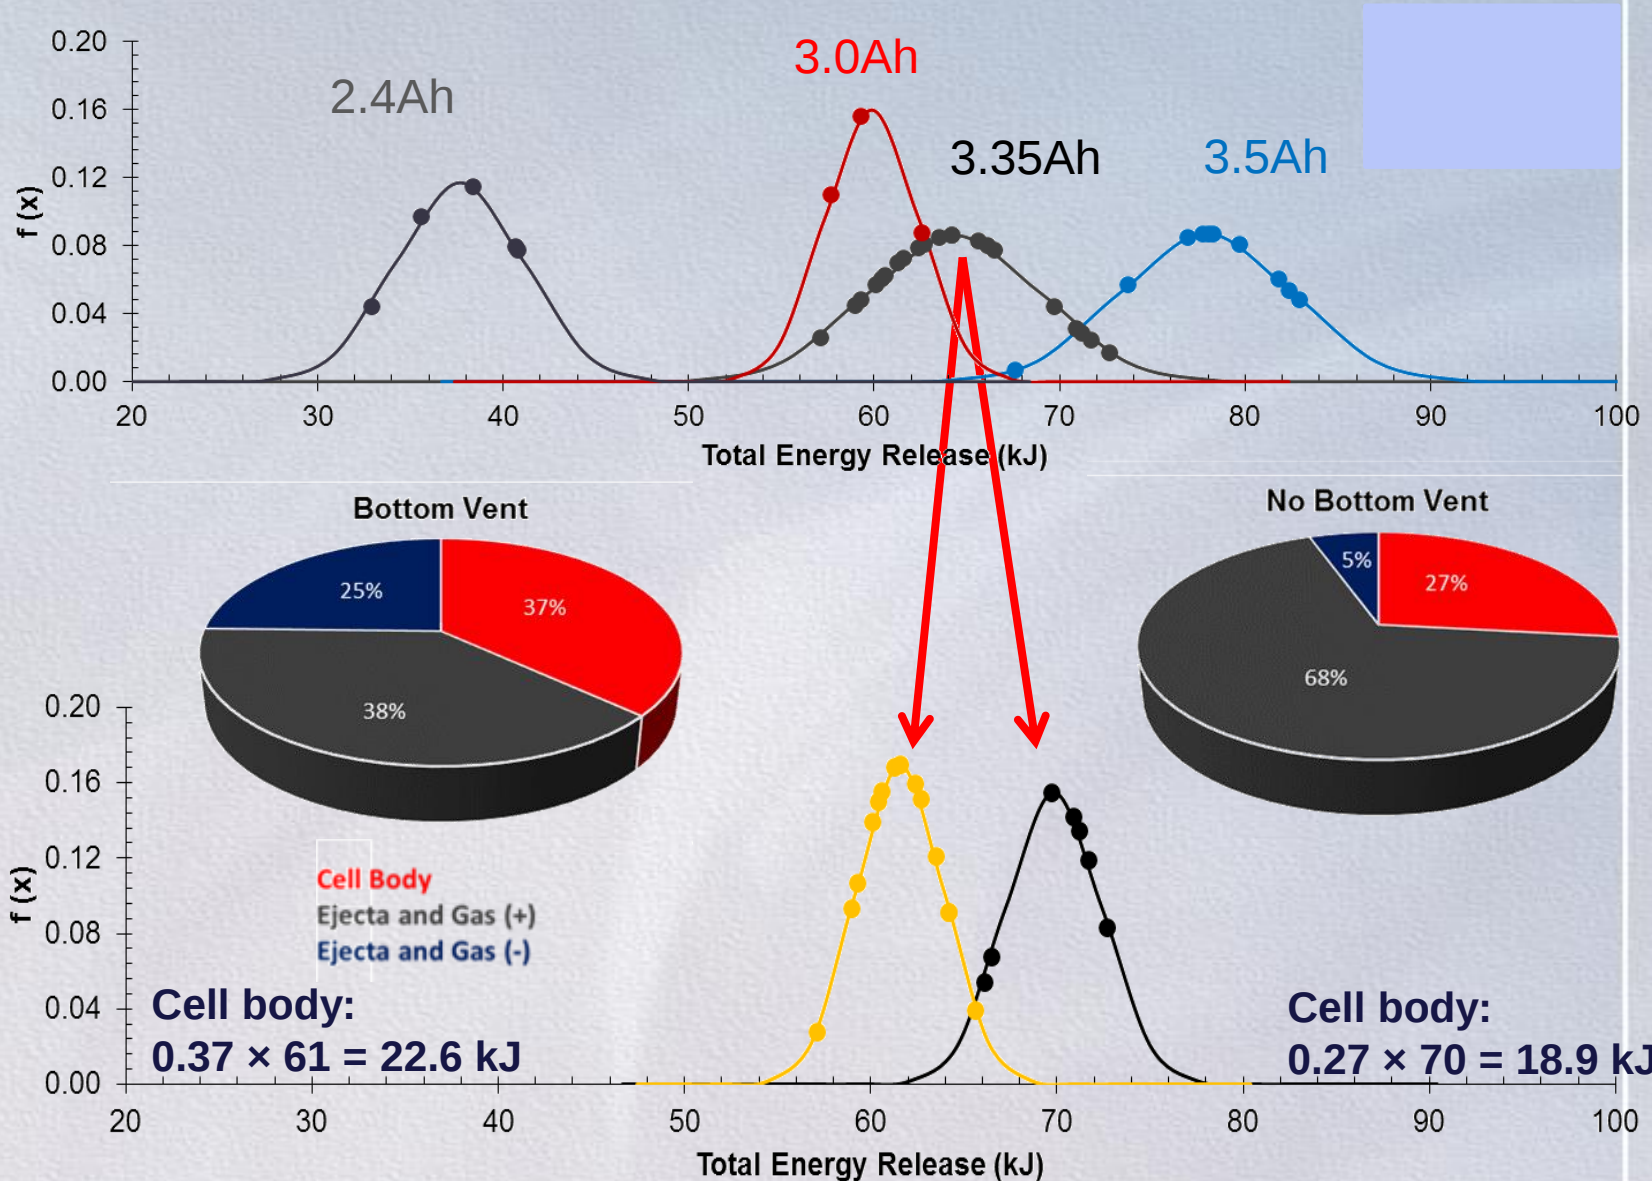

Linking internal dynamics to external risks

High-speed X-ray Imaging

- Oct 2017: Experiment at **The European Synchrotron (ESRF)**, France.
- **29 x 18650 cells** with ISC devices placed at different locations were brought to thermal runaway
- Cell design features varied; with two different wall thicknesses and w/ or w/o bottom vents
- Simultaneous high-speed X-ray imaging and single cell calorimetry
- **Aim:**
 - To link internal phenomenon with external risks and uncover conditions that lead to worst-case failure scenarios
 - Clarify the merits of bottom vents and thicker casing walls

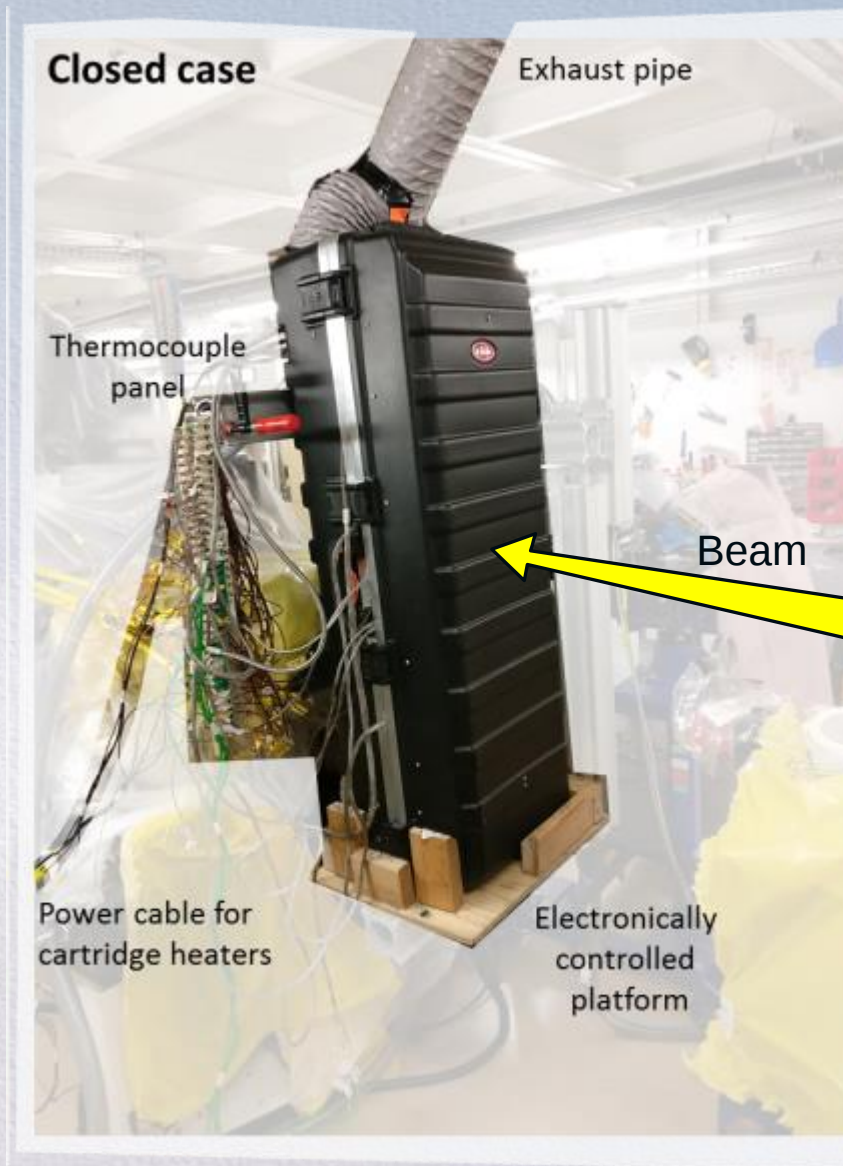


Bottom Vents: Determining Merits

No Bottom Vent (NBV)

Key findings

- Base-plate domes outwards as the gases and debris deflect and take a U-turn through the vacant core of the electrode assembly
- The inner winds of the electrode assembly shear and eject

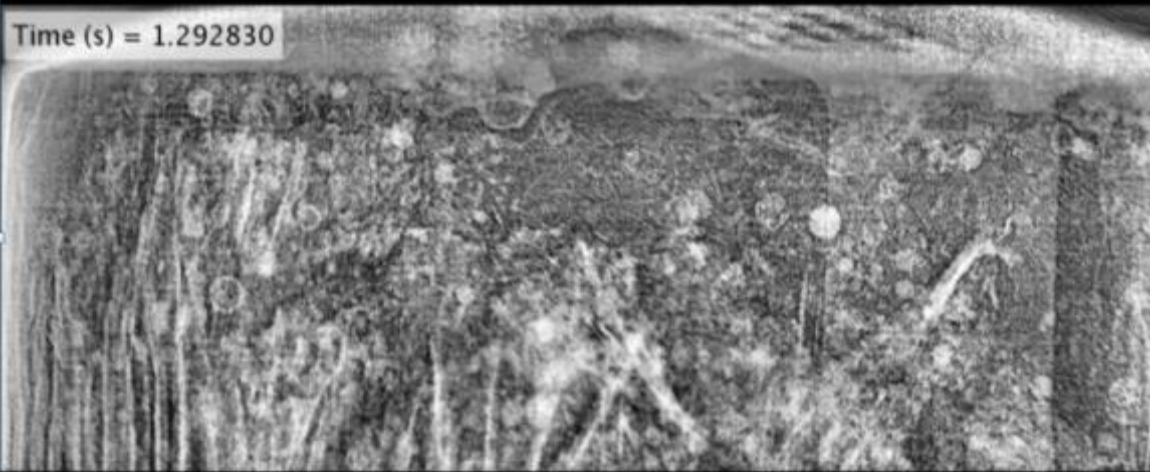


Run 51

Bottom Vent (BV)

Key findings

- Gases and debris does not take a U-turn. The residence time of reacting material is therefore less.
- The thermal mass of the base plate is reduced which may increase the risk of breach due to deflecting material
- The electrode assembly shifts towards the base-vent rather than the top-vent

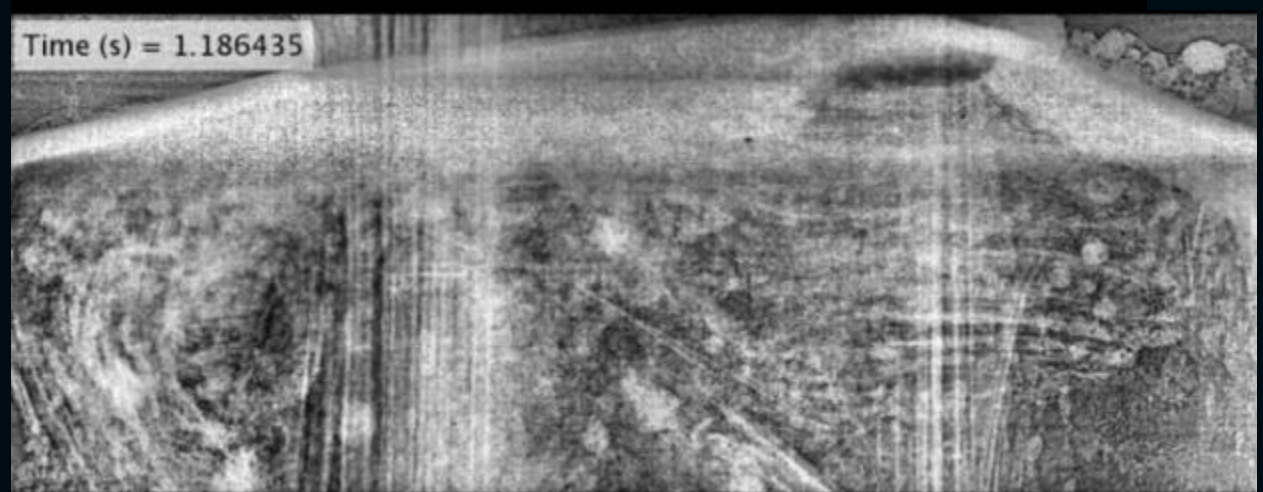

Run 56

Bottom Vent vs No Bottom Vent (only 3.35Ah Cells)

- Inside Calorimeter
 - Bottom vent cells retain 54% of their mass post TR
 - While cells without BV retain only 40%
- Outside Calorimeter with circumferential heater
 - Bottom vent cells retain 50% of their mass post TR
 - While cells without BV retain only 42%
- Counting all tests
 - BV cells retain 52% vs 41% of their pre-test mass
 - Similar results inside or outside calorimeter
 - *Pictures of cell can walls, occurrence of side wall ruptures, and post test mass all suggest BV feature produces less violent TR events*

Calorimeter Runs	3.35Ah w BV		3.35Ah w/o BV	
Average (g)	25.7	54.4%	19.2	39.9%
Sdev (g)	2.7		3.1	
Count	12		8	

% of pre-test mass

Heater Runs	3.35Ah w BV		3.35Ah w/o BV	
Average (g)	23.6	49.9%	20.2	42.0%
Sdev (g)	4.1		4.0	
Count	18		9	

All Valid Runs	3.35Ah w BV		3.35Ah w/o BV	
Average (g)	24.5	51.7%	19.7	41.0%
Sdev (g)	3.7		3.5	
Count	30		17	

Heat output

- 3.5Ah MJ1 cells produce the most heat (1.72 kJ/kJ stored) whereas 3.35Ah cells produce 1.44 kJ/kJ stored.
- > 70 % of the heat output is from ejected material in the 2 cell designs cells.
- *Cells that undergo bottom breach, on average, produce less heat.*

Rupture/Breaching of 18650 cell enclosure

- Side wall, spin groove, bottom, and top cap breaching is melt-through thermal breach, not a pressure induced rupture
- 18650 cells extend by 2-3 mm during header rupture. Allowances need to be made for this extension to avoid unwanted pressure build-up and side-wall breaches.

Merits of bottom vent

- Bottom vent reduces residence time of reacting species.
- The bottom vent leads to less ejected material due to decreased flow rate, and less overall heat generation **but** more heat generated within the casing of the cell. This suggests that the reactions are oxygen starved.

Safe, High Performing Battery Design Guidelines

- Must address risk of side wall breaches: bottom vent, thicker can wall, & protect vulnerable spin groove area
- Provide adequate heat dissipation: conductive interstitial heat sinks along cylindrical wall (also protect against side wall breaches) are best
- Fuse parallel cells to electrically isolate internally shorted cells
- Allow hot ejected materials to disperse their energy quickly while protecting the adjacent cells
- Equip battery vent port with flame arresting features