

# Electrostatic Levitation of ZBLAN and Chalcogenide Glasses

Dennis S. Tucker, PhD

Michael SanSoucie

National Aeronautics and  
Space Administration



**MARSHALL**  
SPACE FLIGHT CENTER



# Background



- Heavy Metal Fluoride Glasses have been studied for ~ 35 years
- $\text{ZrF}_4\text{-BaF}_2\text{-LaF}_3\text{-AlF}_3\text{-NaF}$  (ZBLAN) showed the most promise as optical fiber
- Transmits IR out to ~ 5 microns
- Applications: fiber amplifiers, fiber lasers and nuclear radiation resistant links
- Intrinsic and Extrinsic processes limit light propagation
- Intrinsic: band gap absorption, Rayleigh scatter and multiphonon absorption
- Extrinsic: impurities such as rare-earth ions and crystallite formation
- Theoretical loss coefficient is 0.001 dB/km
- This loss has not been achieved to date due to intrinsic and extrinsic processes




# Background

- ZBLAN fibers obtained from Infrared Focal Systems, Inc. and Bell Laboratories
- Fibers were stripped of coating and placed in evacuated quartz ampoules
- These fibers were first flown on NASA's KC135 Reduced Gravity Aircraft
- KC135 produces ~ 25 sec. of reduced gravity per parabola
- One week of flights led to ~ 200 total parabolas
- Fibers were heated to the crystallization temp. during reduced gravity and compared to unit gravity for same amount of time
- Fibers were also flown on board Conquest sub-orbital rocket
- This flight gave ~ 6.5 minutes of reduced gravity


# Background

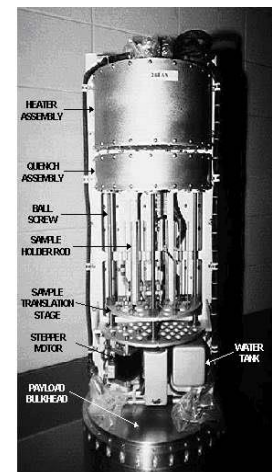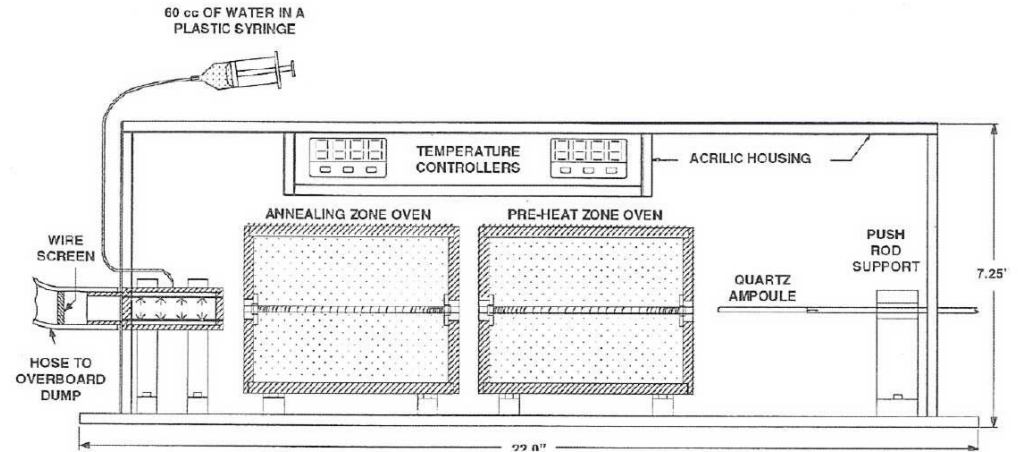

# Background

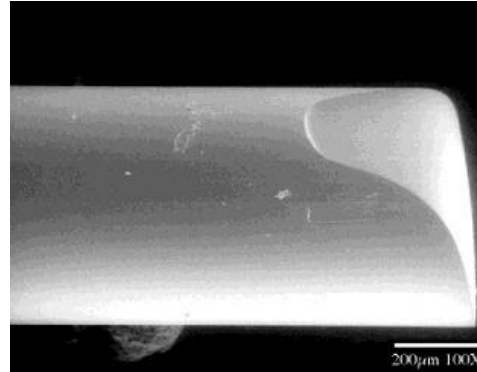


Zero-g

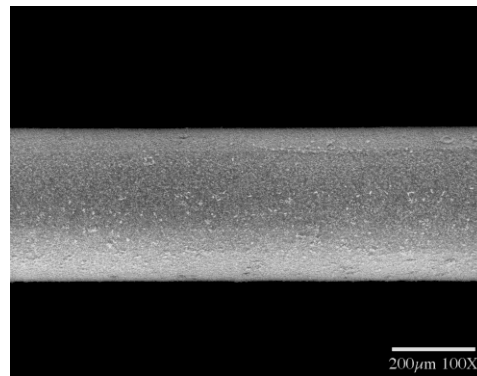


Unit-g

# Background

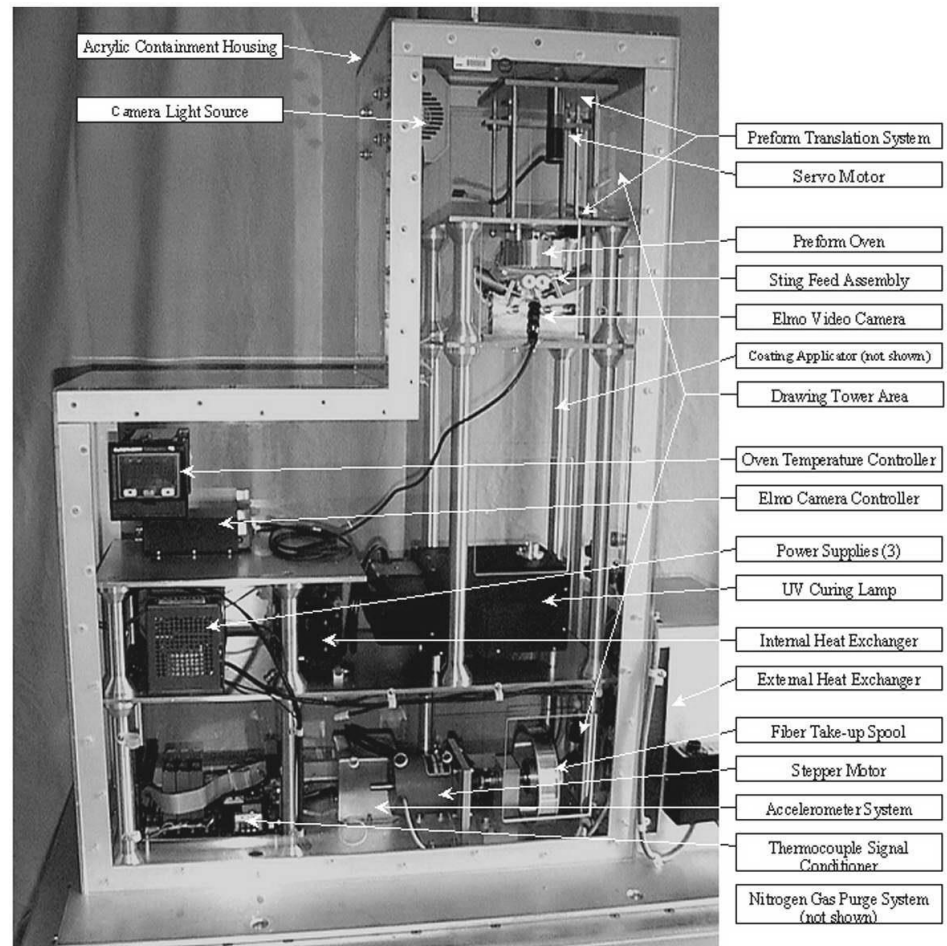

# Background

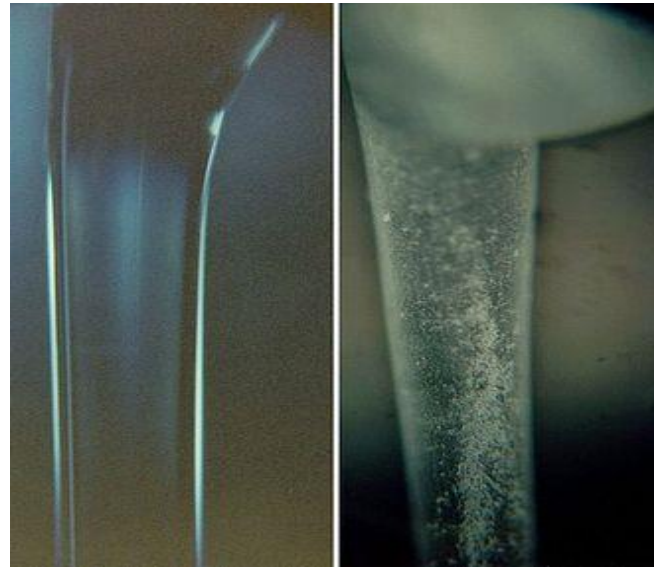

Zero-g

High-g


# Background

- What causes the suppression of crystallization in zero-g?
- Nucleation and Growth Rates are inversely proportional to viscosity
  - $I \sim 1/\eta$  and  $U \sim 1/\eta$
- Ethridge proposed shear thinning present in unit gravity is absent in reduced gravity
- This has been observed for some polymer melts
- Under conditions of shear thinning, effective viscosity decreases with increasing shear rate, thus,
  - $\eta = \eta(\dot{\epsilon})$ , and
  - $I(\dot{\epsilon})$  and  $U(\dot{\epsilon}) \sim 1/\eta(\dot{\epsilon})$
- Low gravity processing is known to reduce convection, which reduces shear
- Thus, crystallization will be reduced in low gravity




# Background

- May be more subtle – Lateral diffusion of barium ion a few nm will induce crystallization – so any perturbation could cause crystallization.

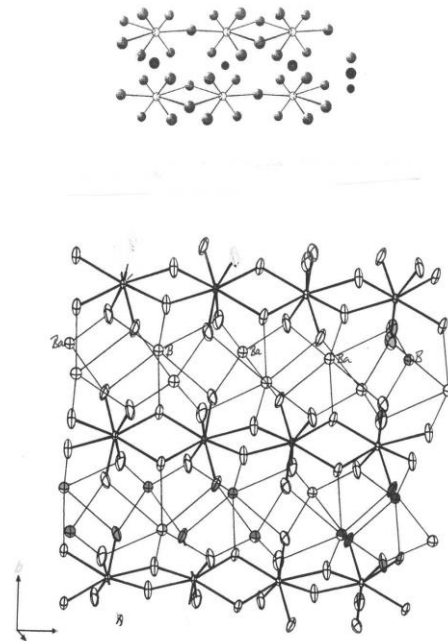

# Background-log viscosity vs. $1/T$

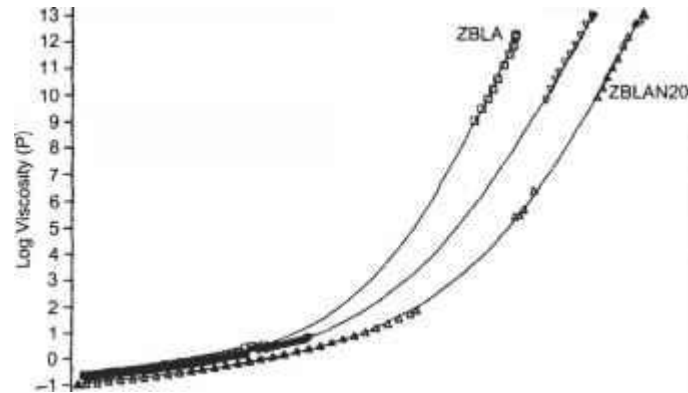

Viscosity of ZBLAN is highly non-linear  
Proposed that processing in zero-g flattens  
viscosity curve




# Experimental

- **It is proposed to use electrostatic levitation (ESL) to perform viscosity and crystallization studies of pure ZBLAN and selected chalcogenide glasses.**
- Viscosity is inversely proportional to nucleation and growth and is the only measurable quantity in these equations, all others being thermodynamic.


## Experimental – Chalcogenide Samples

- Sample 1 : **As<sub>39</sub>Se<sub>61</sub>**
- Sample 2 : **As<sub>38</sub>Se<sub>60</sub>I<sub>2</sub>**
- Sample 3 : **As<sub>38</sub>Se<sub>58</sub>I<sub>4</sub>**
- Sample 4: **As<sub>38</sub>Se<sub>56</sub>I<sub>6</sub>**
- Sample 5 : **As<sub>38</sub>Se<sub>60</sub>I<sub>2</sub>  
doped Pr<sup>3+</sup>.**
- Using Arsenic, Selenium and Iodine: have seen crystals during fiber draw

# ESL of ZBLAN

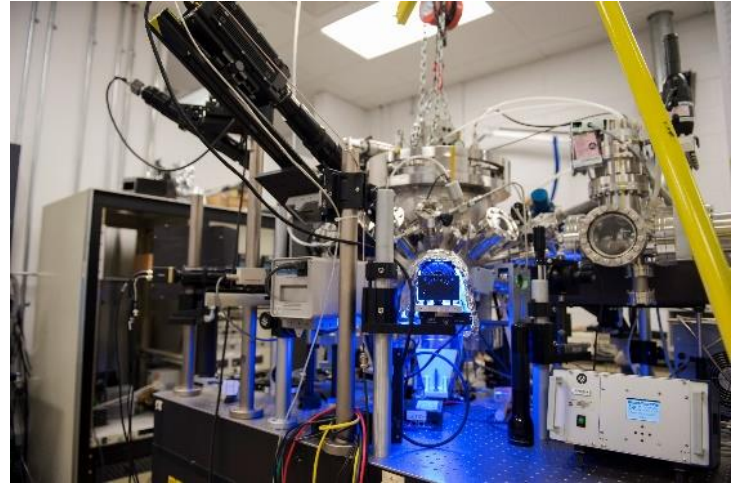

MSFC ESL Facility

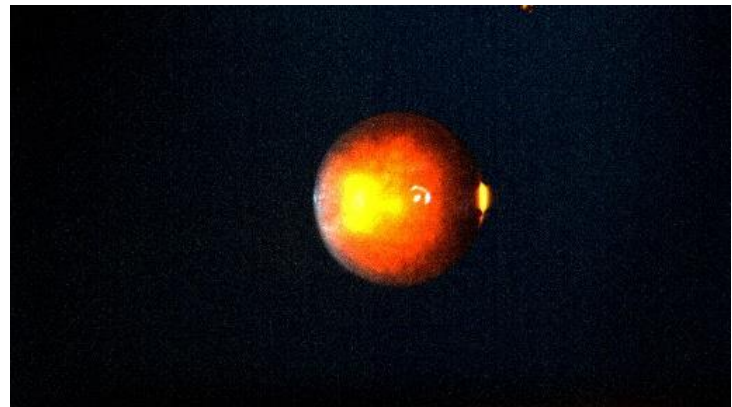


ZBLAN levitated ~ 500C

# Electrostatic Levitation

- ESL uses an electrostatic field to levitate charged specimens
  - Typically 2-3mm spheres
- The field is created between 6 electrodes
  - 3 are grounded
  - 3 are connected to high-voltage DC amplifiers
- Charge is maintained by irradiating the sample with UV light
  - Deuterium arc lamp
  - As samples are heated volatile components tend to evaporate as positively charged ions
    - Surface ionization
- Samples are heated and melted with a laser
  - The ESL lab has Nd:YAG, fiber optic, and CO<sub>2</sub> lasers available
- Temperature is measured with a pyrometer
  - InGaS (~1.5um) typically

# Electrostatic Levitation

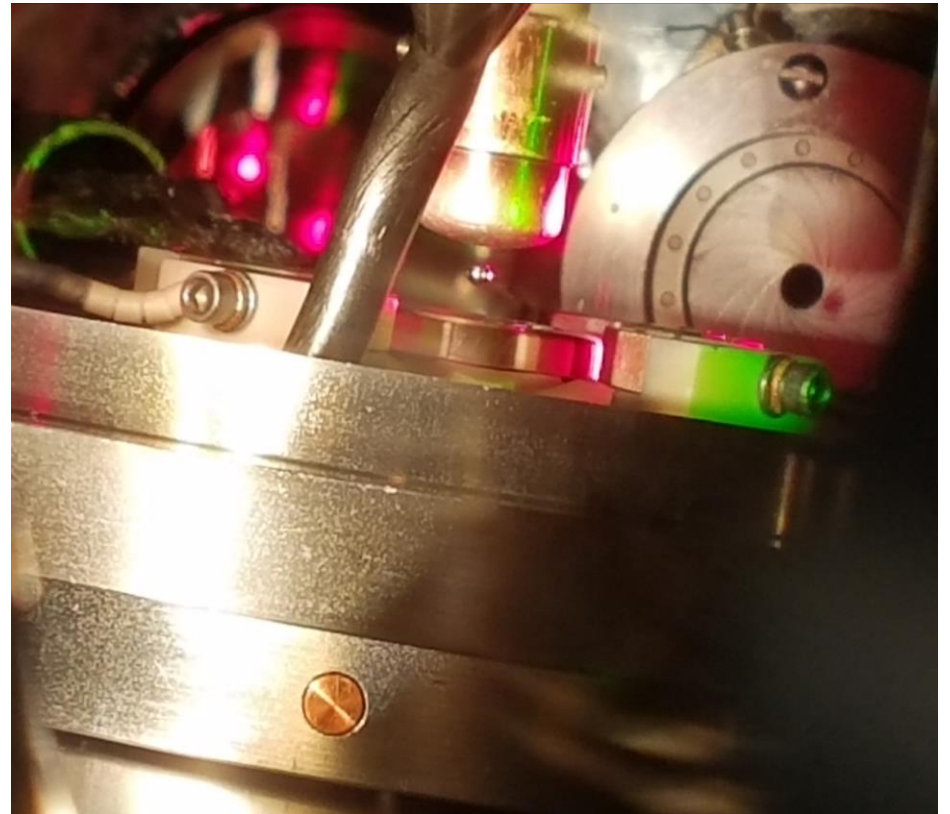




# Viscosity Measurements

- Oscillating drop method
- Surface oscillations are induced in the molten sample by modulating the electrostatic field near the resonant frequency
- Once stable mode 2 oscillations have developed
  - Modulation is turned off
  - Natural frequency of the resulting oscillations and the damping are recorded with high-speed video
    - Typically 1000fps
- Surface tension calculated from natural frequency
- Viscosity calculated from damping coefficient



# Viscosity Measurements

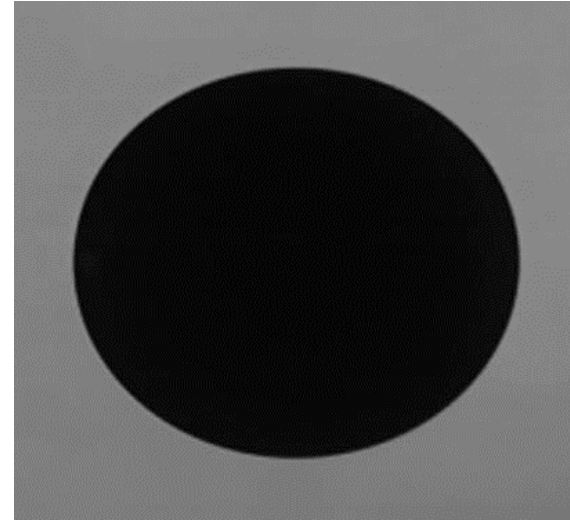

Example of an oscillating sample at its resonant frequency.

$$\omega_l = \sqrt{\frac{l(l-1)(l+2)\gamma}{\rho R_o^3}}$$

Rayleigh  
(1879)

$$\tau_l = \frac{\rho R_o^2}{(l-1)(2l+1)\mu}$$

Lamb  
(1881)



# ESL Experiments with ZBLAN To Date

- The MSFC ESL lab has made several attempts to process ZBLAN samples
- The lab has been able to melt samples and oscillate a couple of samples
- ZBLAN has proven to be a difficult material to work with
  - But not impossible
- More time perfecting the techniques for ZBLAN is required
- Thermal gradients have been an issue
  - Heating from 2 directions, with 2 CO2 lasers should help
    - The lab is currently in the procurement process for two 100W CO2 lasers