

COUPLING FRACTIONAL THERMAL RUNAWAY CALORIMETRY (FTRC) RESULTS WITH STATISTICAL ANALYSIS METHODS

William Walker, Ph.D. ^{1,2}

william.walker@nasa.gov

Additional Contributors

John Darst ^{1,2}

Donal Finegan, Ph.D. ⁴

Gary Bayles, Ph.D. ⁵

Kenneth Johnson ^{1,3,6}

Eric Darcy, Ph.D. ^{1,2}

Steven Rickman ^{1,2,6}

¹National Aeronautics and Space Administration (NASA)


²Johnson Space Center (JSC)

³Marshall Space Flight Center (MSFC)

⁴National Renewable Energy Laboratory (NREL)

⁵Science Applications International Corporation (SAIC)

⁶NASA Engineering and Safety Center (NESC)




NASA STRATEGY TO PROTECT AGAINST THERMAL RUNAWAY



- **Following the 2013 Boeing 787 Dreamliner incident, NASA teams developed new definitions for battery design success criteria:**
 - Always assume thermal runaway (TR) will eventually happen
 - Design should ensure that TR event is not catastrophic
 - Demonstrate that propagation to surrounding cells will not occur

- **Thermal management systems designed to mitigate the effects of thermal runaway and prevent cell-to-cell propagation should consider the following:**
 - No runaway event is the same; even for the same manufacturer and state-of-charge; there is a range of possible outcomes
 - Onset temperature, acceleration temperature, trigger temperature, trigger cell peak temperature and neighbor cell peak temperature
 - Total energy released through sides and top of the cell body
 - Cell failure type (e.g. side wall vs. top), system pressure increase, gases released and ejecta material


- **Optimization of Li-ion battery assemblies that satisfy the aforementioned strategies requires knowledge of the following:**
 - Total energy output range during TR for a single Li-ion cell
 - Fraction of TR energy transferred through the cell casing
 - Fraction of TR energy ejected through cell vent/burst paths




FRACTIONAL THERMAL RUNAWAY CALORIMETRY

➤ **As an NESC assessment, NASA developed a new fractional TR calorimetry (FTRC) method for 18650-format Li-ion cells:**

- Collaborators included NESC, NASA JSC, and SAIC
- Allows discernment between (1) total heat output and (2) fraction of heat released through the cell casing vs. ejecta material
- The energy distributions are determined by post processing temperature vs. time for each calorimeter sub-assembly (i.e. $\sum m_i C_{p_i} dT_i$)
- Ambidextrous configuration accommodates cell designs with bottom vents (BVs)
- Uses high flux heaters or nail penetration to initiate TR quickly
- Simple operation enables multiple experiments per day
- Compatible with high speed X-ray videography⁹
- Optional interface for measuring the gas exhaust heat

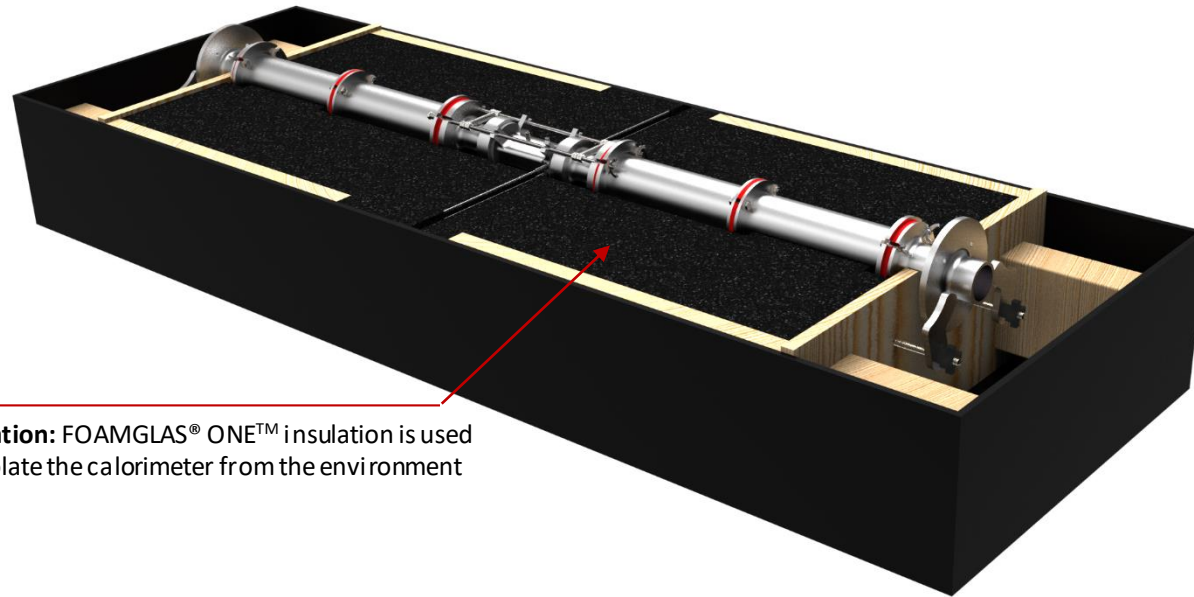

Insulation: FOAMGLAS® ONE™ i insulation is used to isolate the calorimeter from the environment

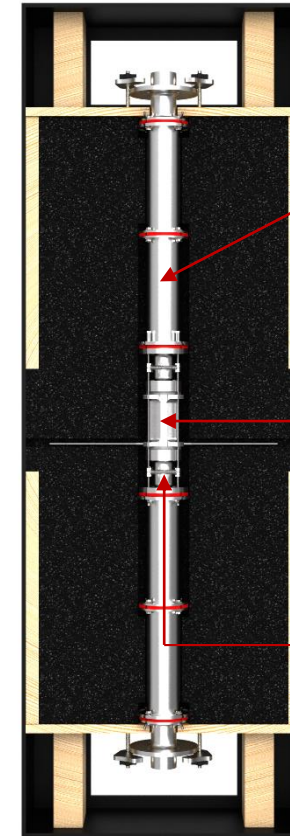

Ejecta Bore Assemblies: Slow down and extract heat from escaping flames and gas


Cell Chamber Assembly: Includes heating system for thermally induced failure and mounting point for nail penetration system

Ejecta Mating Assemblies: Captures ejected solids such as the electrode winding



FRACTIONAL THERMAL RUNAWAY CALORIMETRY

- **Images below outline the primary external components of the FTRC and depict the corresponding internal components:**
 - The design is ambidextrous to accommodate top and bottom vents (and ruptures)
 - An 18650 cell is shown for scaled reference
 - Note that this image depicts the 8th generation of the device; a new 9th generation with improved design features is currently being used

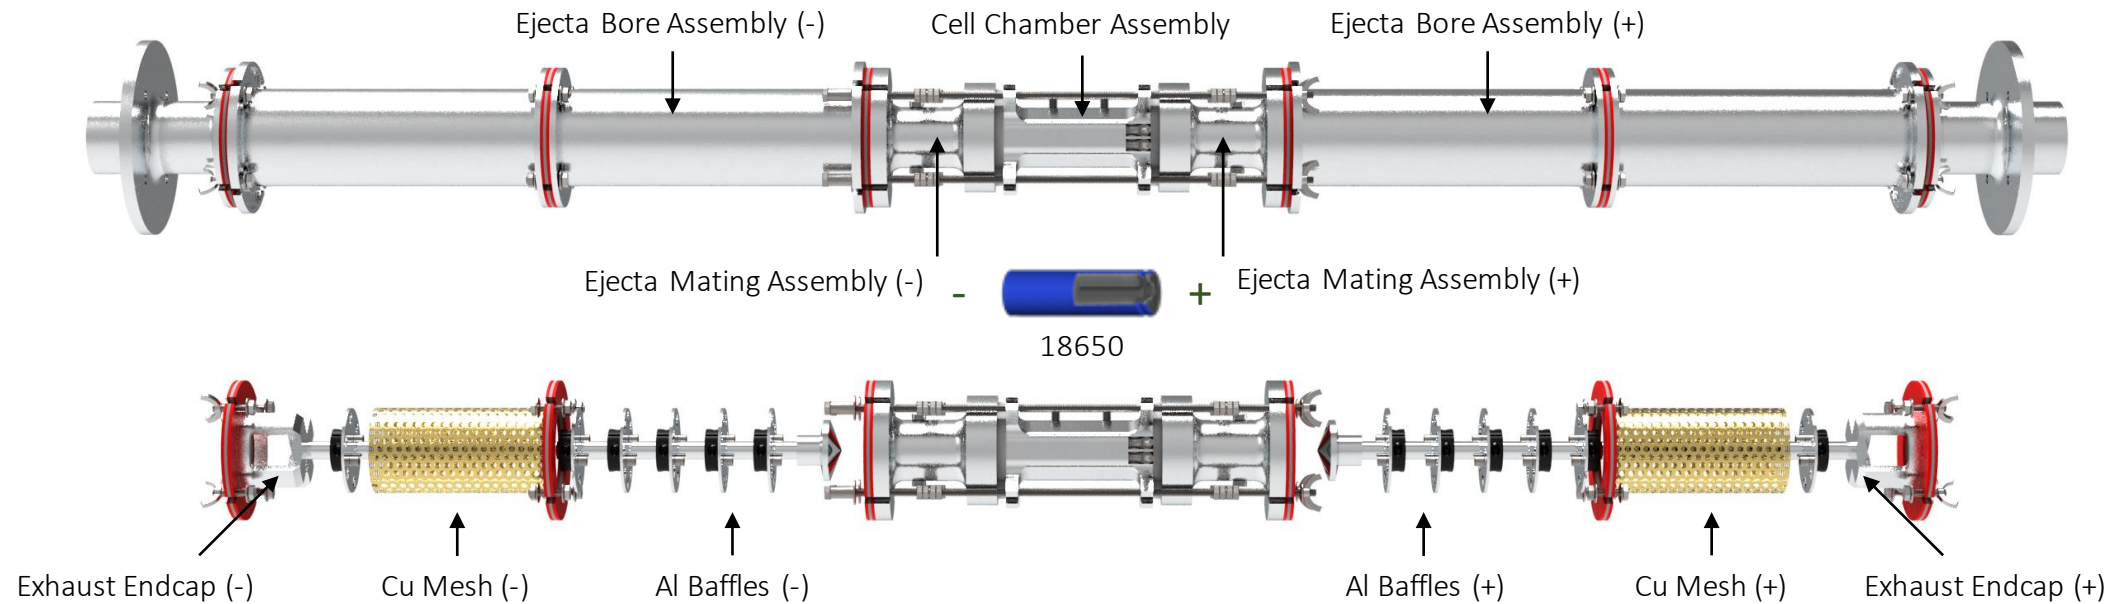


FRACTIONAL THERMAL RUNAWAY CALORIMETRY


➤ **Images below outline the cell chamber, the ejecta mating segment and ceramic bushing, and the baffle and mesh system:**

- The 18650 cell is placed inside the cell chamber (highlighted red) and cartridge heaters in the four slots along the perimeter of the cell chamber (highlighted yellow); the set screws used to press thermocouples against the cell casing are also depicted; the nail penetration mounting interface is not depicted
- The positive and negative side ceramic bushings create the only interface between the cell chamber and ejecta mating segment
- The positive and negative side baffles and meshes create tortuous paths that reduce flow velocity, capture ejected particulates, and arrest any flames generated from thermal runaway


(a)

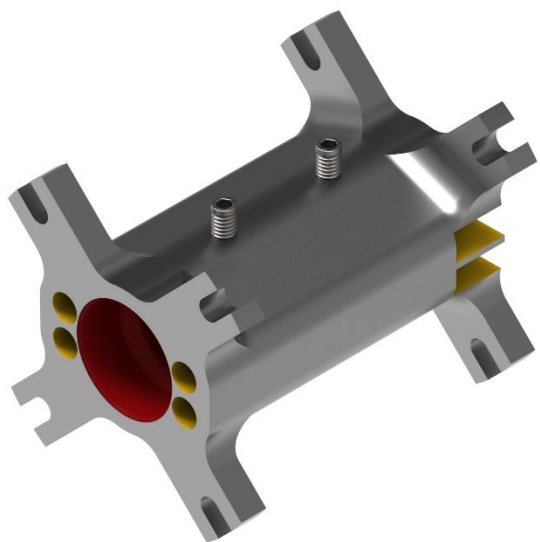

(b)

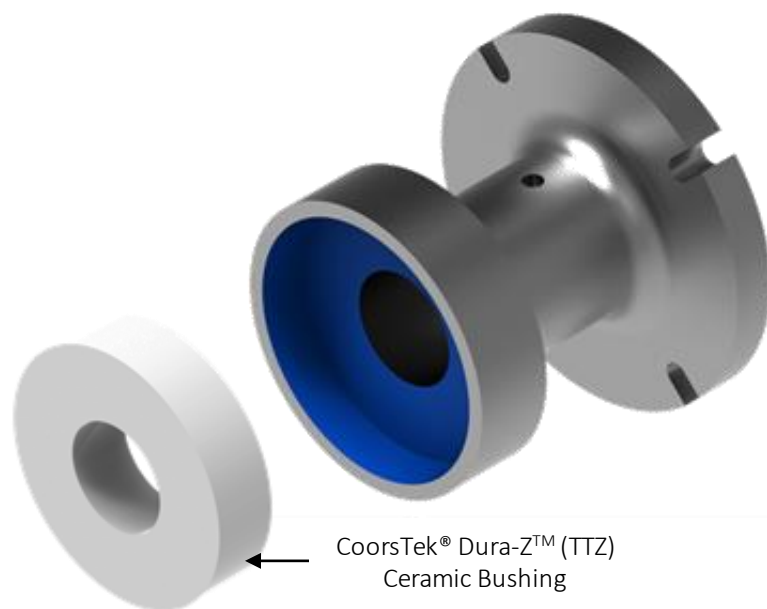


(c)

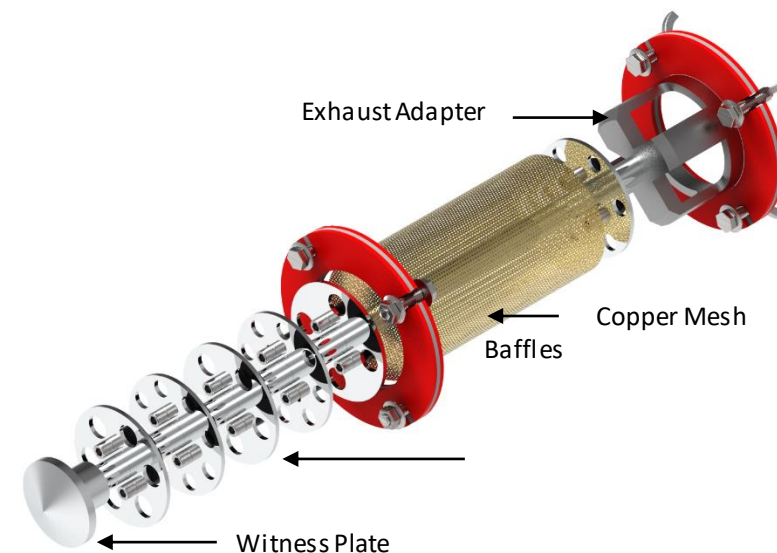




FRACTIONAL THERMAL RUNAWAY CALORIMETRY

- The calculated energy fractions are traceable to every calorimeter assembly, sub-assembly, and individual component
- The primary assemblies used for fractional calculations are the following:
 - Cell Chamber Assembly (Red)
 - Positive Ejecta Mating Assembly (Indigo)
 - Positive Ejecta Bore Assembly (Indigo)
 - Negative Ejecta Mating Assembly (Black)
 - Negative Ejecta Bore Assembly (Black)

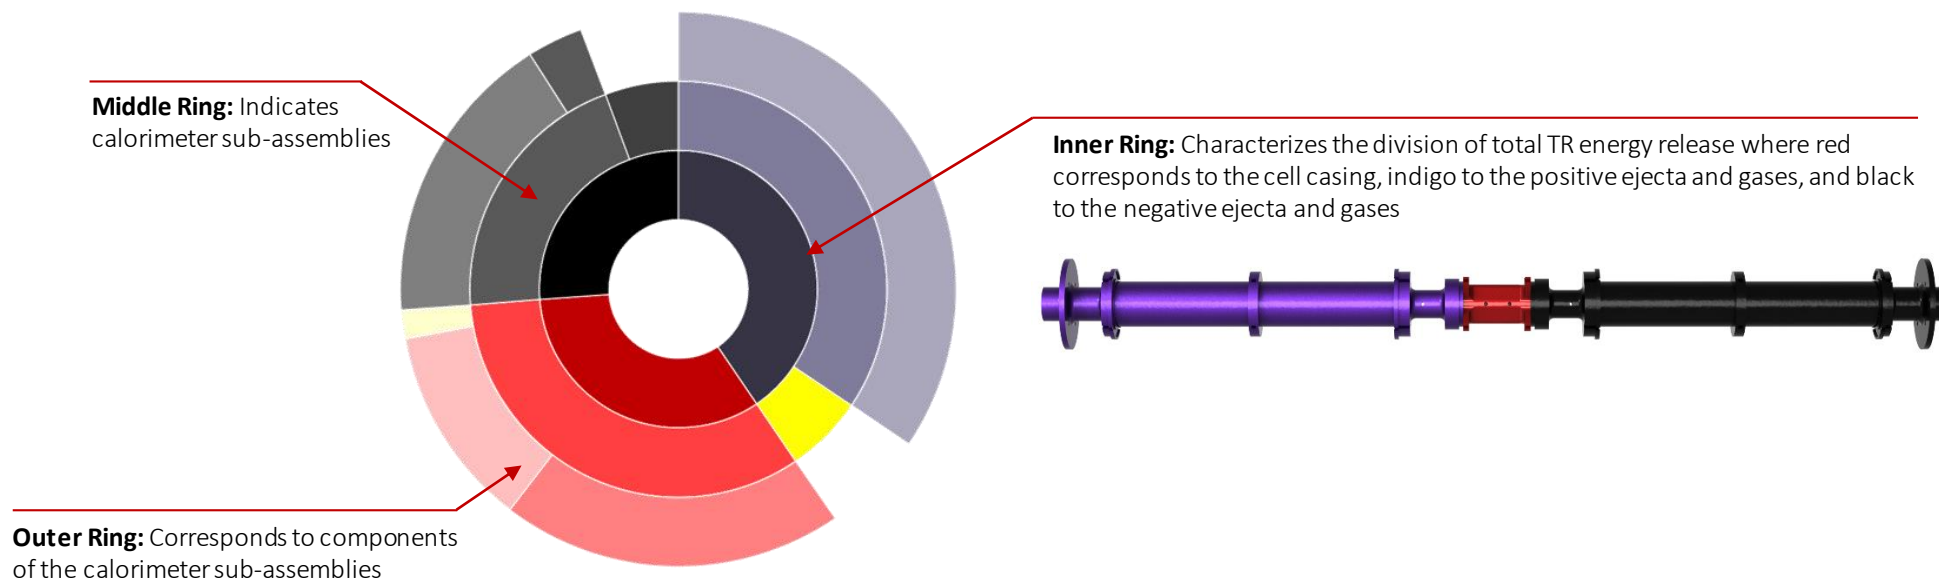



FRACTIONAL THERMAL RUNAWAY CALORIMETRY

➤ **Images below depict the global testing capability of the device:**

- FTRC testing at the NASA JSC Energy Systems Test Area (Red Dot)
- FTRC testing at the European Synchrotron Radiation Facility (ESRF) for in-situ high speed tomography (Green Dot)
- FTRC testing at the Diamond Light Source (DLS) Facility for in-situ high speed tomography (Yellow Dot)


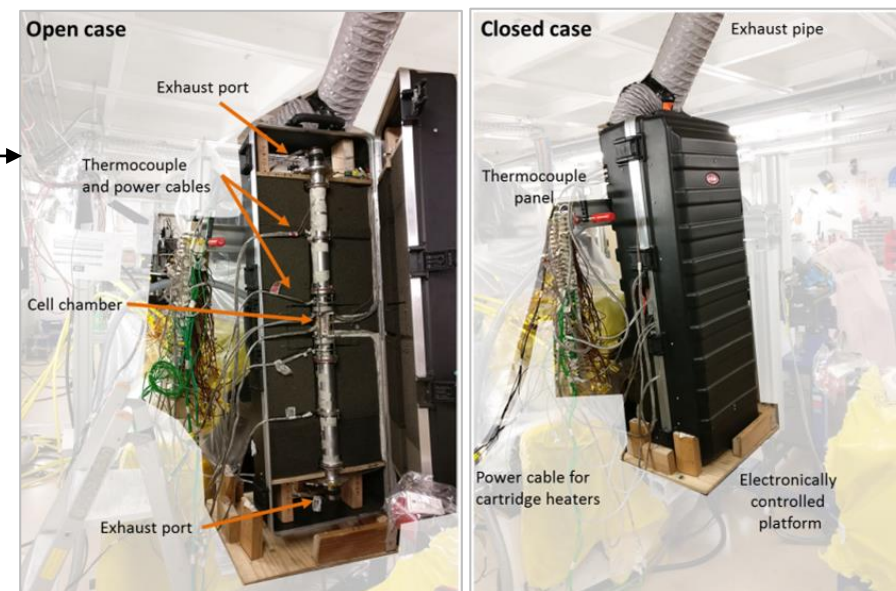


Image courtesy of Dr. Donal Finegan and ESRF

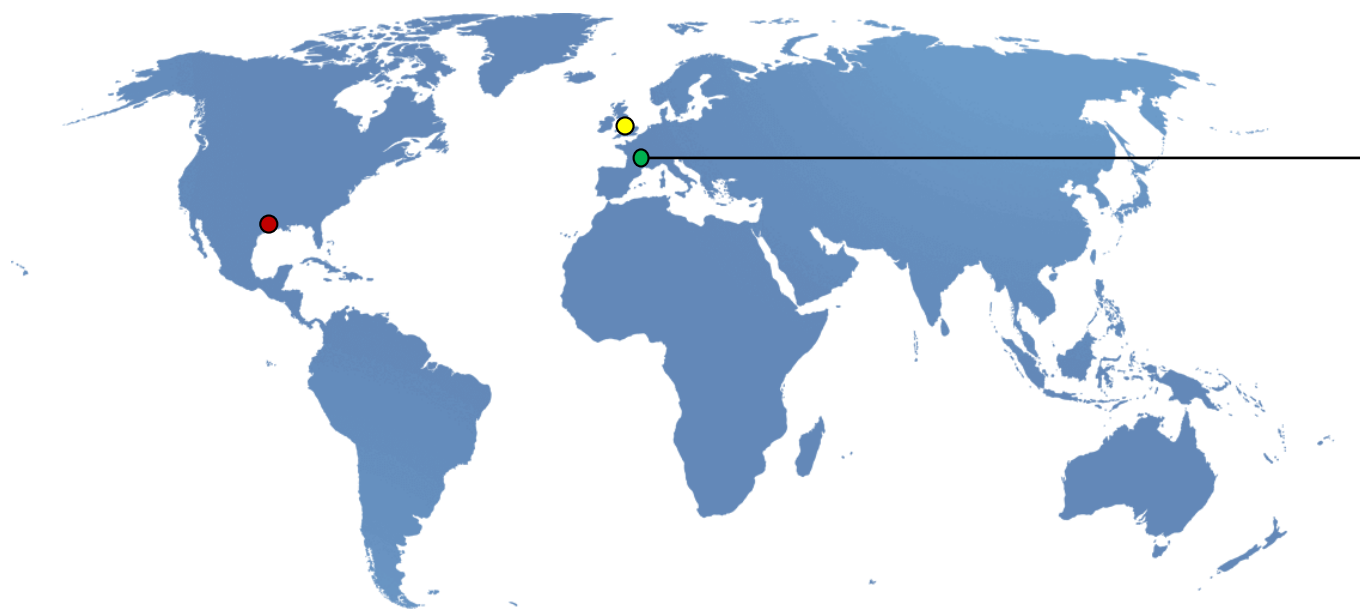

FRACTIONAL THERMAL RUNAWAY CALORIMETRY

Cell type: Li-ion 18650

Capacity: 3.5 Ah

State of Charge: 100 % (4.2 V)

Bottom vent: No

Wall thickness: Not known

Separator: Polymer

Orientation of cell: Positive end up

Location of ISCD radially: N/A

Location of ISCD longitudinally: N/A

Side of ISCD in image: N/A

Location of FOV longitudinally: Top

Frame rate: 2000 Hz

Frame dimension (Hor x Ver): 1280 x 800 pixels

Pixel size: 17.8 μm



DESCRIPTION OF CELL TYPES AND VARIABLES TESTED

- **The TR behavior of a variety of cell types, with varying chemistries and safety features, has been characterized:**
 - 3.35 Ah LG 18650 control groups consider the effects of bottom vent mechanisms (BV) vs. non-bottom vent (non-BV) mechanisms and the cell casing thickness (220 vs. 250 μm);
 - Molicel 18650-J control groups consider standard polymer separators and Dreamweaver gold and silver separators
 - Some of the 3.35 Ah LG 18650 cells and Molicel 18650-J cells had the NASA/NREL developed internal short circuiting (ISC) devices installed to examine TR behavior at lower temperatures (i.e. closer to field failure conditions); image below depicts the device
 - All cells were tested at 100% state of charge

- **Most experiments are conducted with high flux heaters for a trigger mechanism:**
 - For select cells, some of the FTRC experiments were conducted with nail penetration as well (nail results not discussed here)

Variable	Unit	LG 18650	Sony 18650	LG 18650	Panasonic 18650	LG 18650	Samsung 18650	LG 18650	Molicel 18650
Model	-	MJ1	VC7	Test Cell	BE	HG2	30Q	HE2	J
Capacity at 100% SOC	Ah	3.5	3.5	3.35	3.2	3.0	3.0	2.5	2.3
Nominal Voltage	V	3.6	3.6	3.67	3.6	3.6	3.6	3.6	3.78
Nom. Energy	Wh	12.7	12.7	12.4	11.5	10.8	10.8	10.8	8.7
Venting Mechanism	-	Non-BV	BV	BV and Non-BV	BV	Non-BV	Non-BV	Non-BV	Non-BV
Casing Thickness	μm	150	-	220 and 250	125	150	170	-	203
Internal Short Circuit ¹	-	No	No	Yes	No	No	No	No	Yes
Trigger Mechanism	-	Heat/Nail	Heat	Heat/Nail	Heat	Heat	Heat	Heat	Heat/Nail
Separator Material	-	-	-	-	-	-	-	-	Poly, Ag, Au
Count ²	-	15	9	40	2	10	5	3	15

¹ The ISC device was only installed in some of the cells

² The count refers to the total number of cells tested per cell type



DESCRIPTION OF CELL TYPES AND VARIABLES TESTED

- **The TR behavior of a variety of cell types, with varying chemistries and safety features, has been characterized:**
 - 3.35 Ah LG 18650 control groups consider the effects of bottom vent mechanisms (BV) vs. non-bottom vent (non-BV) mechanisms and the cell casing thickness (220 vs. 250 μm);
 - Molice1 18650-J control groups consider standard polymer separators and Dreamweaver gold and silver separators
 - Some of the 3.35 Ah LG 18650 cells and Molice1 18650-J cells had the NASA/NREL developed internal short circuiting (ISC) devices installed to examine TR behavior at lower temperatures (i.e. closer to field failure conditions); image below depicts the device
 - All cells were tested at 100% state of charge

- **Most experiments are conducted with high flux heaters for a trigger mechanism:**
 - For select cells, some of the FTRC experiments were conducted with nail penetration as well (nail results not discussed here)

Variable	Unit	LG 18650	Sony 18650	LG 18650	Panasonic 18650	LG 18650	Samsung 18650	LG 18650	Molice1 18650
Model	-	MJ1	VC7	Test Cell	BE	HG2	30Q	HE2	J
Capacity at 100% SOC	Ah	3.5	3.5	3.35	3.2	3.0	3.0	2.5	2.3
Nominal Voltage	V	3.6	3.6	3.67	3.6	3.6	3.6	3.6	3.78
Nom. Energy	Wh	12.7	12.7	12.4	11.5	10.8	10.8	10.8	8.7
Venting Mechanism	-	Non-BV	BV	BV and Non-BV	BV	Non-BV	Non-BV	Non-BV	Non-BV
Casing Thickness	μm	150	-	220 and 250	125	150	170	-	203
Internal Short Circuit ¹	-	No	No	Yes	No	No	No	No	Yes
Trigger Mechanism	-	Heat/Nail	Heat	Heat/Nail	Heat	Heat	Heat	Heat	Heat/Nail
Separator Material	-	-	-	-	-	-	-	-	Poly, Ag, Au
Count ²	-	15	9	40	2	10	5	3	15


¹ The ISC device was only installed in some of the cells

² The count refers to the total number of cells tested per cell type



DIRECT COMPARISON OF TOTAL ENERGY RELEASE

- **Higher energy cells (e.g. the LG 18650-MJ1) release more TR energy, have more violent ejections, and lower remaining cell mass when compared to lower energy cells (e.g. the Molicel 18650-J):**
 - Note that the normal distributions (left image) shown below are created from the raw data and are generated to give an initial glance at the data
 - These plots do not break down the impacts of the aforementioned design variables on the thermal runaway behavior; hence the significant differences in standard deviations seen in the plot below
 - Although direct interpretation of the raw data is insightful, we recommend referring to the regression model results (next few slides) for final assessment of thermal runaway behavior


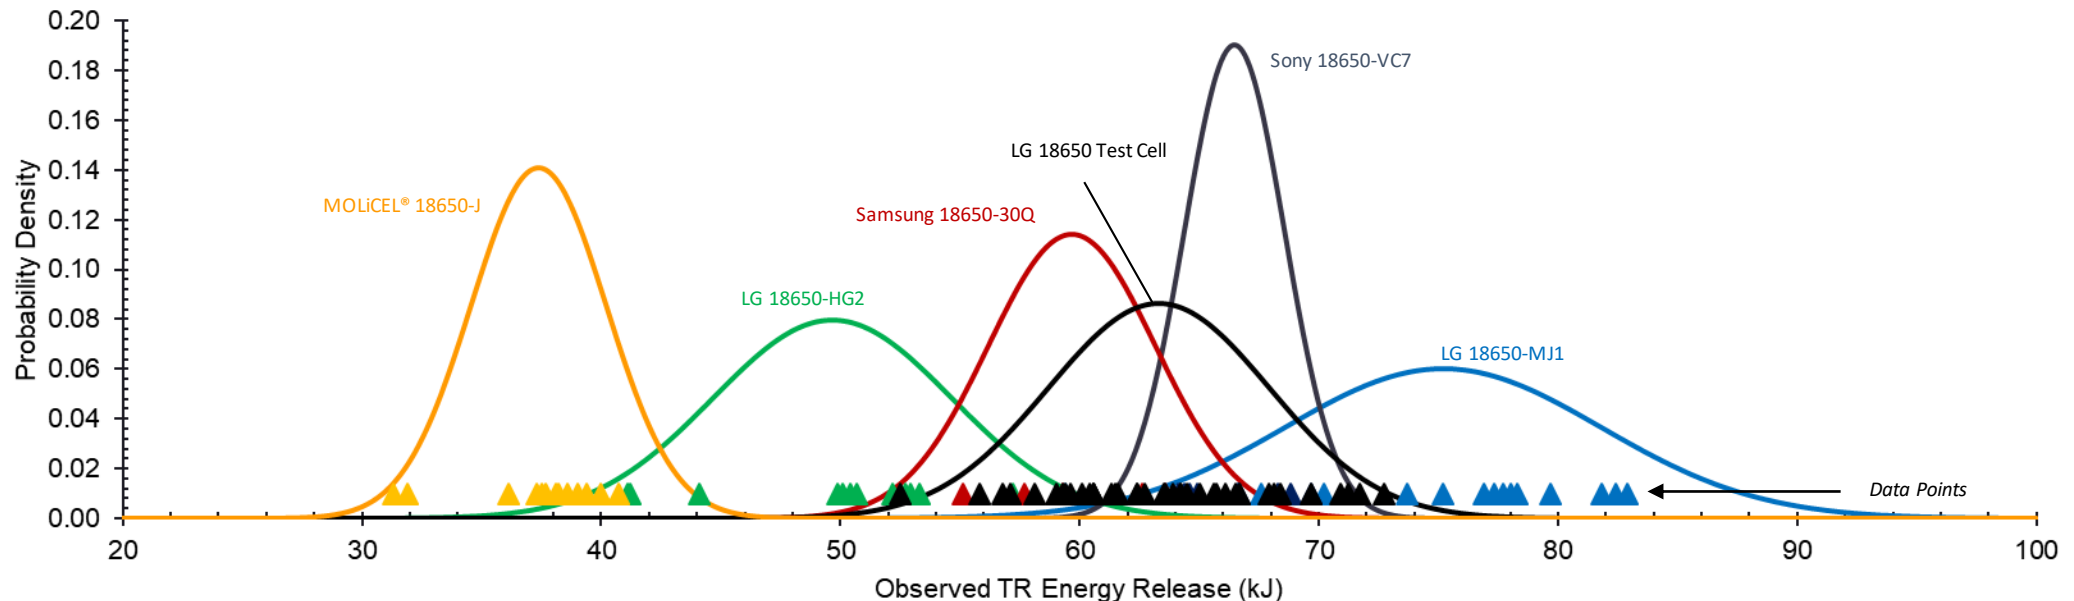




DIRECT COMPARISON OF TOTAL ENERGY RELEASE

➤ **There is not a linear relationship between stored electrochemical energy and the total energy released:**

- The two 10.8 Wh cells have significantly different thermal runaway responses with the Samsung 18650-30Q average total energy release at 59.7 kJ and the LG 18650-HG2 average total energy release at 49.7 kJ
- The three higher energy cells (12.4 to 12.7 Wh) also have differing thermal runaway responses with the LG 18650 Test Cell average total energy release of 63.3 kJ, the Sony 18650-VC7 average total energy release of 66.5 kJ, and the LG 18650-MJ1 average total energy release of 75.2 kJ
- Again, we recommend referring to the regression model results (next few slides) for final assessment of thermal runaway behavior

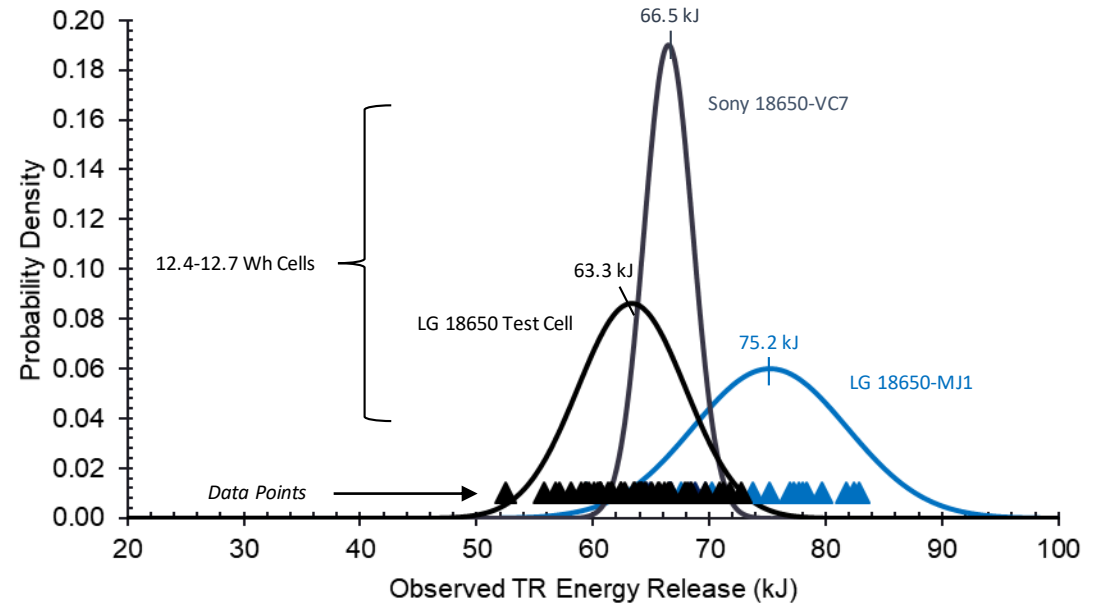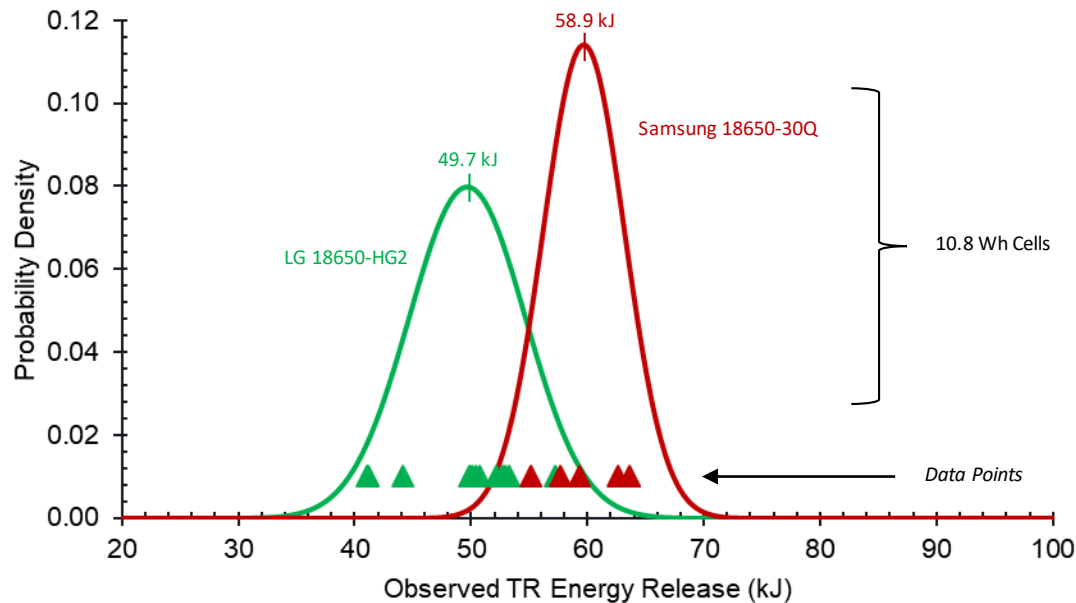



ENGINEERING STATISTICS METHODOLOGY

- **The TR results for each experiment are directly post-processed with primary consideration given to the following:**
 - Total TR energy yield
 - Fraction of energy released through the cell casing vs. through the ejecta materials and gases
 - Remaining cell mass following TR
 - The raw data derived versions of these values are referred to as the “observed” values and serve as inputs to a regression model



- **No two TR events are identical which results in variation of total TR energy release on a test-to-test basis:**
 - This variation is a function of various random and non-random factors associated with the experiments
 - A regression model was developed as a function of all of the FTRC results (e.g. cell type, failure mechanism, energy distribution, total energy release)
 - The completed regression model then uses the observed values for each experiment and outputs a corresponding predicted total energy release
 - The predicted energy release values are then used to recreate distributions to characterize the range of thermal runaway energy release

- **Note that the regression model can be used to predict energy fractions as well, but at this point we are only using it to predict total energy release:**
 - The predicted values and the associated distributions are shown on the next few slides



PREDICTED TOTAL ENERGY RELEASE


- **First it is important to examine how effective the regression model is at predicting total energy release:**
 - This effectiveness can be considered by looking at the residuals (differences between predicted and corresponding observed values)
- **A key assumption for the regression analysis was equal variability of the residuals across zero:**
 - Residual = difference between predicted value and corresponding observed value
 - Initial model, based on total energy release in kJ, did not satisfy this assumption (left image)
 - Performed inverse-square root translation of observed total energy release ($\text{kJ}^{-0.5}$) factor to achieve a better model (right image)

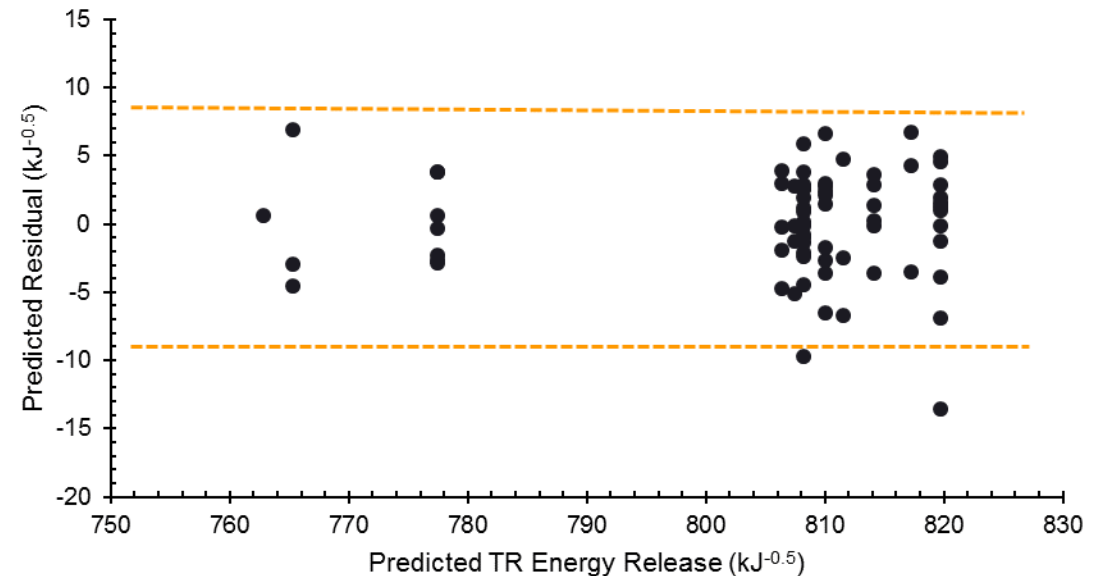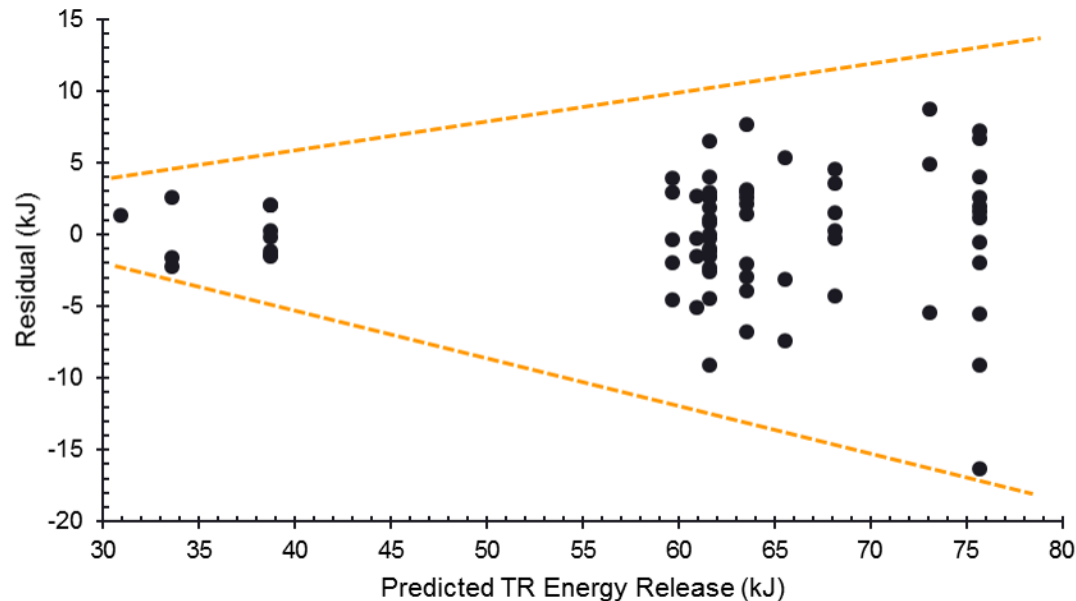




PREDICTED TOTAL ENERGY RELEASE


- **The transformed results for total energy release were in inverse square root units ($\text{kJ}^{-0.5}$) as seen on the previous slide:**
 - These predictions were then translated back into the original units (kJ) for final interpretation
- **Distributions based on the final predicted values (in kJ) were then created:**
 - Think of the distribution curves below, plus the previously shown fractional pie charts, as the end goal for every cell, cell configuration, and cell variable that we attempt to characterize
 - The power of the regression model becomes apparent as we are now able to analyze the impacts of the random and non-random variables on thermal runaway behavior

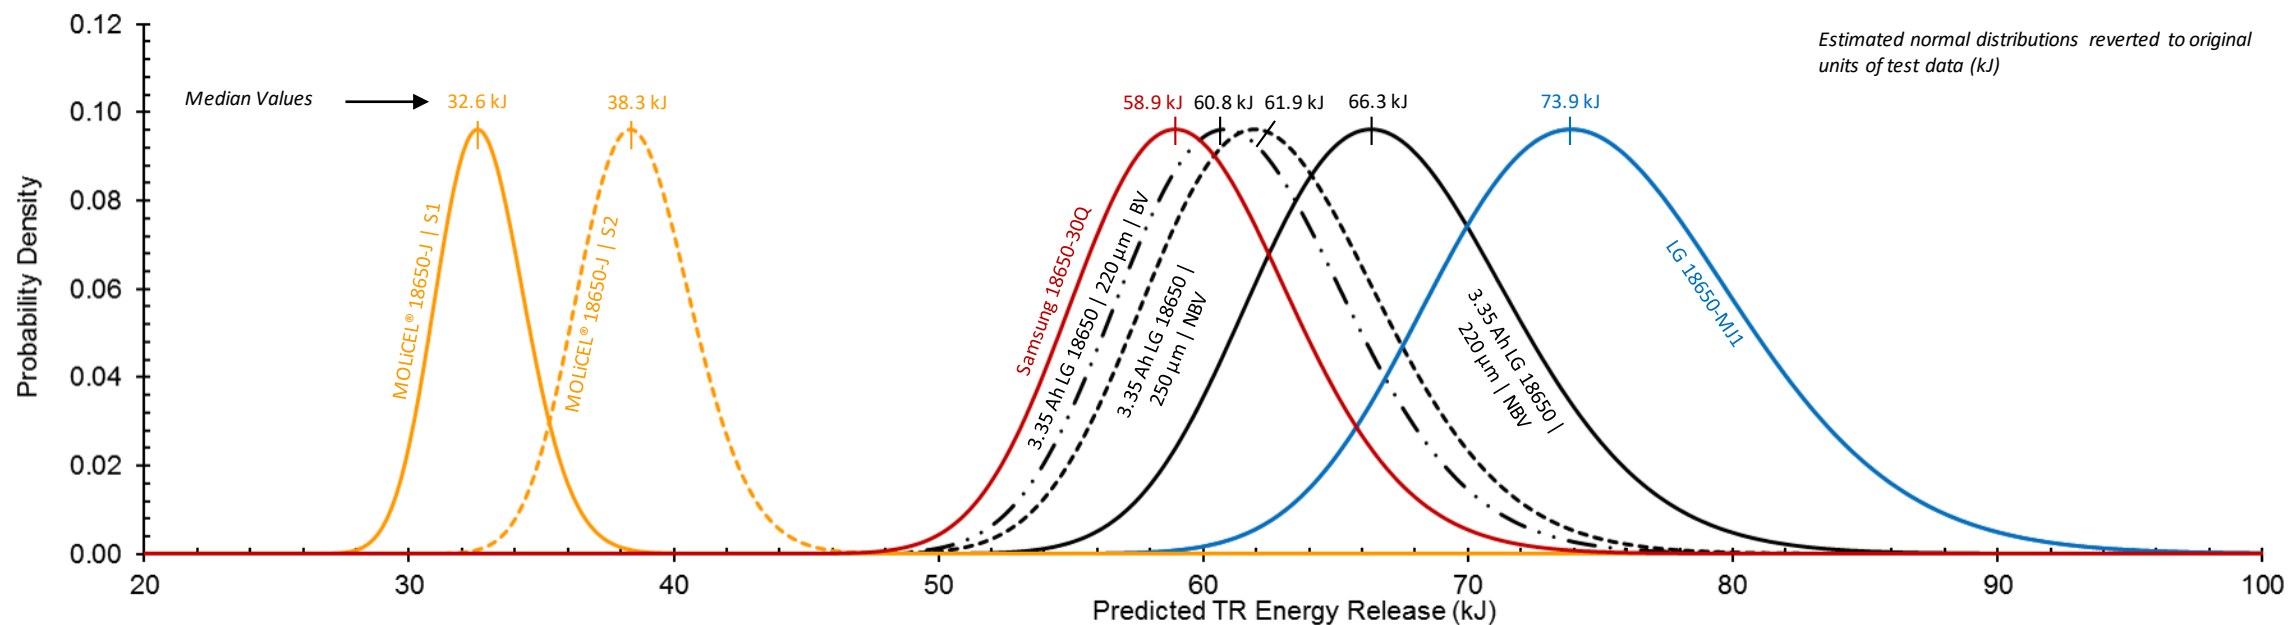




PREDICTED TOTAL ENERGY RELEASE

- **The regression model was recently updated after it was found that using the natural log of the total energy release (rather than inverse square root) resulted in a more accurate prediction:**
 - The predicted distributions translated from $\ln(\text{kJ})$ back into kJ are shown below
 - The overall results are similar to the previous, but in general it is revealed that higher energy cells have much higher standard deviations and that a long right tail better characterizes total thermal runaway energy release
 - This means that the variation in total thermal runaway energy release is non-normal (contrary to original assumption)

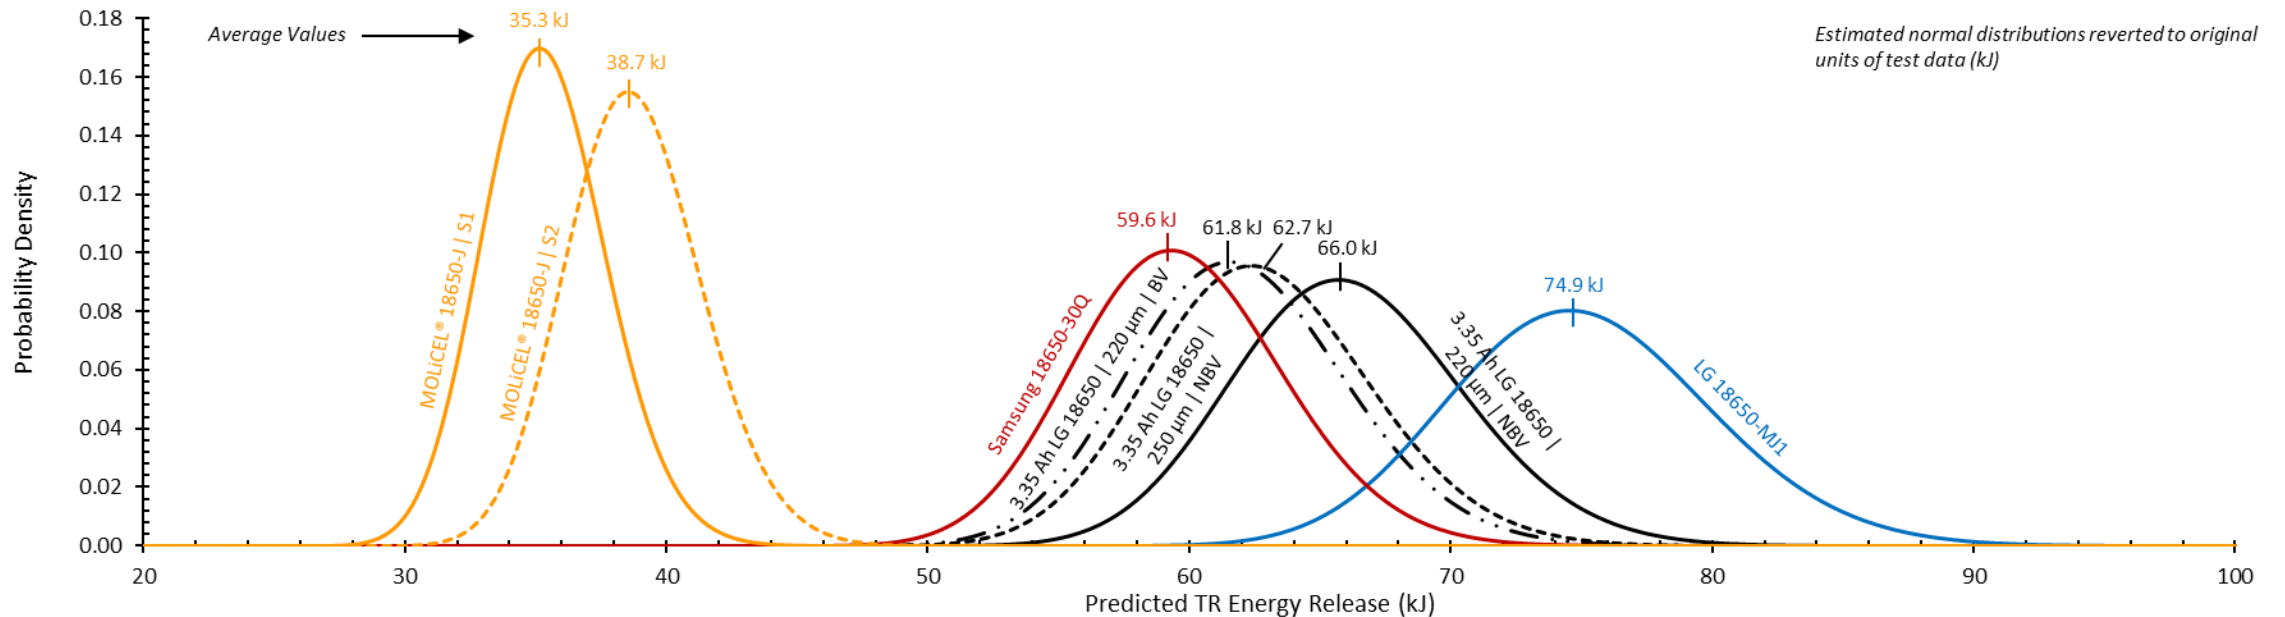





THERMAL RUNAWAY ENERGY FRACTIONS

- **The thermal runaway energy release fractions are determined for every cell configuration:**
 - Fractions can be determined from an average of all results for a given cell type or can be an average based on nominal vs. off nominal failure mechanism (e.g. difference between top vent vs. bottom rupture)
 - Fractional analysis is particularly helpful in comparing the distribution of standard vent cells to bottom vent cells
 - Standard cells typically release 20-30% through the cell casing and the remainder through the ejecta material
 - Bottom vent cells tend to release the energy in a three-way split between the casing and the top and bottom ejecta materials

- **The fractions provide test verification of how much energy is directly impinged on neighbor cells during runaway events**

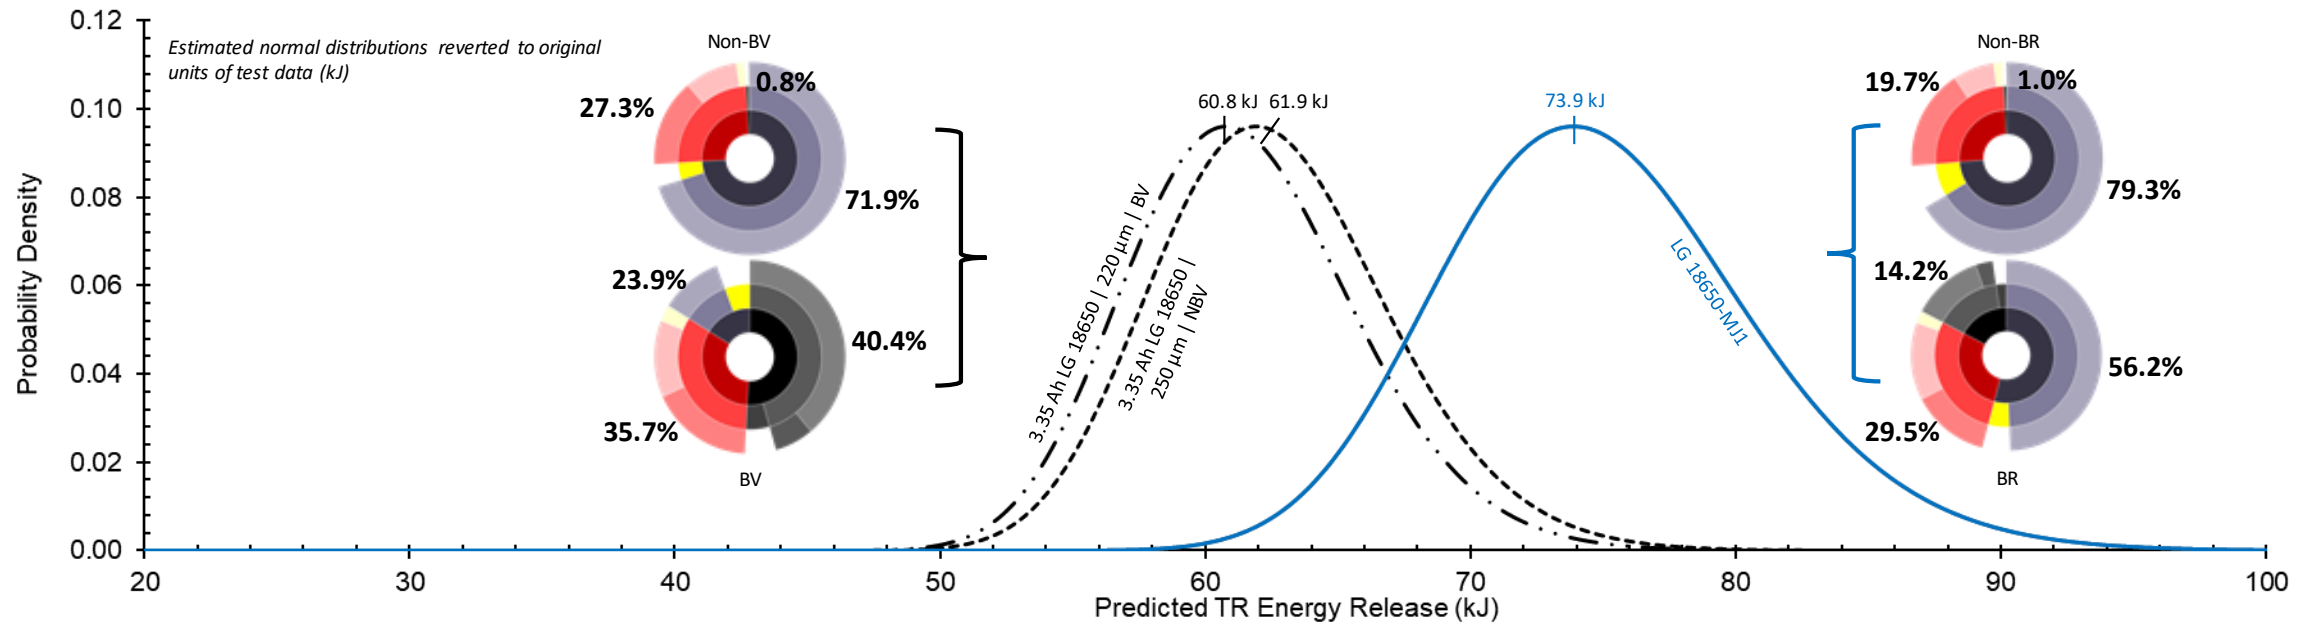




COMPARISON OF REMAINING CELL MASS AND TOTAL ENERGY RELEASE

➤ Relationships between ejected mass and total energy release appear to exist (in some cases):


- In general, higher energy cells tend to eject more mass and have lower remaining cell body mass (compare the LG-MJ1 to the Moli-J)
- Theorize that higher energy cells generate higher internal pressures which ultimately results in larger mass ejections
- This ultimately allows more ejected material to react with available oxygen, which then contributes to larger thermal runaway energy yields
- Note that the aforementioned trend is broken by the Samsung-30Q

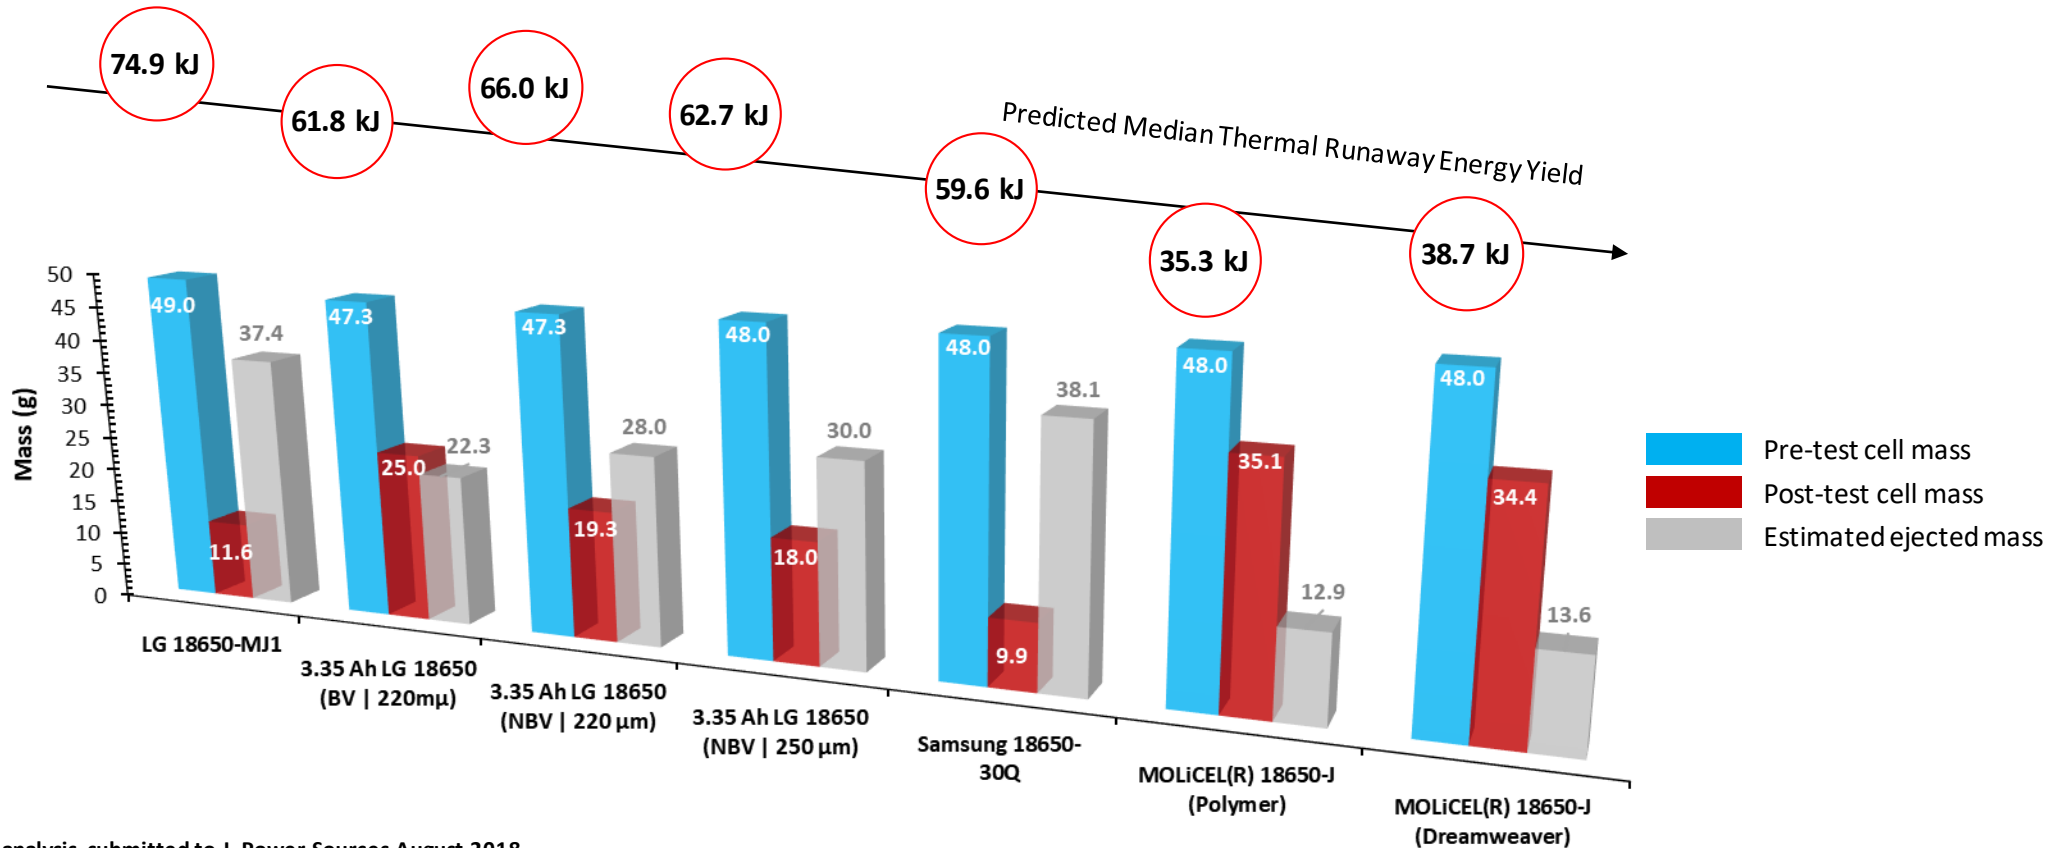



CONCLUSIONS

- **Results provide the means to develop optimized Li-ion batteries while also maintaining safety and margin**
- **FTRC, and the associated results, enables the discernment of the fractions of thermal runaway energy released through the cell casing and through the ejecta material:**
 - Due to the variability in thermal runaway responses, we recommend at least 10 runs to establish statistically defensible results
 - Can analyze the spread of heat sources when cells rupture and compare to when they remain intact
- **Higher energy cells produce more heat and eject more material during thermal runaway:**
 - Higher magnitudes of total energy released and more violent ejections
 - Less energy associated with the cell body and more energy associated with the ejecta
 - The correlation is not very linear because cell enclosure design impacts the results
 - Higher energy cells tend to have more variability in total energy release
- **BV cells released less energy (~4 kJ for 3.35 Ah LG cell) and have higher post runaway cell mass than non-BV cells:**
 - BV cells produce less and more localized heat, hence a less severe and more predictable thermal runaway event as an effect of the BV feature
 - Battery designers should be ready to accommodate and take advantage of cell designs with the BV feature in the future
- **There is not a linear relationship between stored electrochemical energy and total thermal runaway energy release**
 - Based on comparison of 30Q to HG2 (~10.8 Wh cells) and on comparison of the VC7 and MJ1 (~12.5 Wh cells)
- **The variation in thermal runaway energy release is non-normal and has a long right tail**



CONCLUSIONS

➤ Results provide the means to develop optimized Li-ion batteries while also maintaining safety and margin

➤ FTRC, and the cell casing and

- Due to the
- Can analyz

➤ Higher energy

- Higher ma
- Less energ
- The correl
- Higher ene

➤ BV cells releas


- BV cells pr
- Battery de

➤ There is not a

- Based on c

➤ The variation in thermal runaway energy release is non-normal and has a long right tail

Journal of Power Sources 410–411 (2019) xxx–xxx




ELSEVIER

Contents lists available at [ScienceDirect](#)

Journal of Power Sources


journal homepage: www.elsevier.com/locate/jpowsour



Decoupling of heat generated from ejected and non-ejected contents of 18650-format lithium-ion cells using statistical methods

William Q. Walker^{a,*}, John J. Darst^a, Donal P. Finegan^b, Gary A. Bayles^c, Kenneth L. Johnson^{d,e}, Eric C. Darcy^a, Steven L. Rickman^{a,d}

^a National Aeronautics and Space Administration (NASA) Johnson Space Center (JSC), 2101 NASA Parkway, Houston, TX 77058, USA
^b National Renewable Energy Laboratory (NREL), 15013 Denver West Parkway, Golden, CO 80501, USA
^c Science Applications International Corporation (SAIC), 12010 Sunset Hills Road, Reston, VA 20190, USA
^d NASA Engineering and Safety Center (NESC), 1 NASA Drive, Hampton, VA 23666, USA
^e Marshall Space Flight Center, USA



through the

ES

s:
f the BV feature

ase




CURRENT FOCUS OF FTRC EFFORTS

- **The current focus of the FTRC efforts is on characterizing thermal runaway behavior for like cells as a function of three trigger mechanisms; i.e. thermal, nail, and ISC (combined with thermal)**
- **Examining the effects of failure location on rupture behavior using the ISC device**
- **Development the 9th Generation FTRC which maintains accommodations for small format cells beyond 18650 cells including the following:**
 - 21700 cells
 - D-Cells
 - Pouch cells
 - These three (plus the 18650 calorimeter) are referred to as small format FTRC or S-FTRC
- **Characterizing the thermal runaway behavior of cells with combinations of Dreamweaver separators and Soteria current collectors (i.e. components which can impede thermal runaway and in some cases prevent altogether)**
- **Development of FTRC capability for >100 Ah Li-ion cells; this is referred to as large format FTRC or L-FTRC**
- **Improvement of regression modeling techniques**



ACKNOWLEDGEMENTS

- **NASA Engineering and Safety Center**
 - Steve Rickman and Christopher Iannello
- **NASA JSC Engineering Directorate (EA):**
 - Power and Propulsion Division (EP)
 - Structural Engineering Division (ES)
- **FTRC Team Members**
- **NASA JSC Energy Systems Test Area (ESTA)**

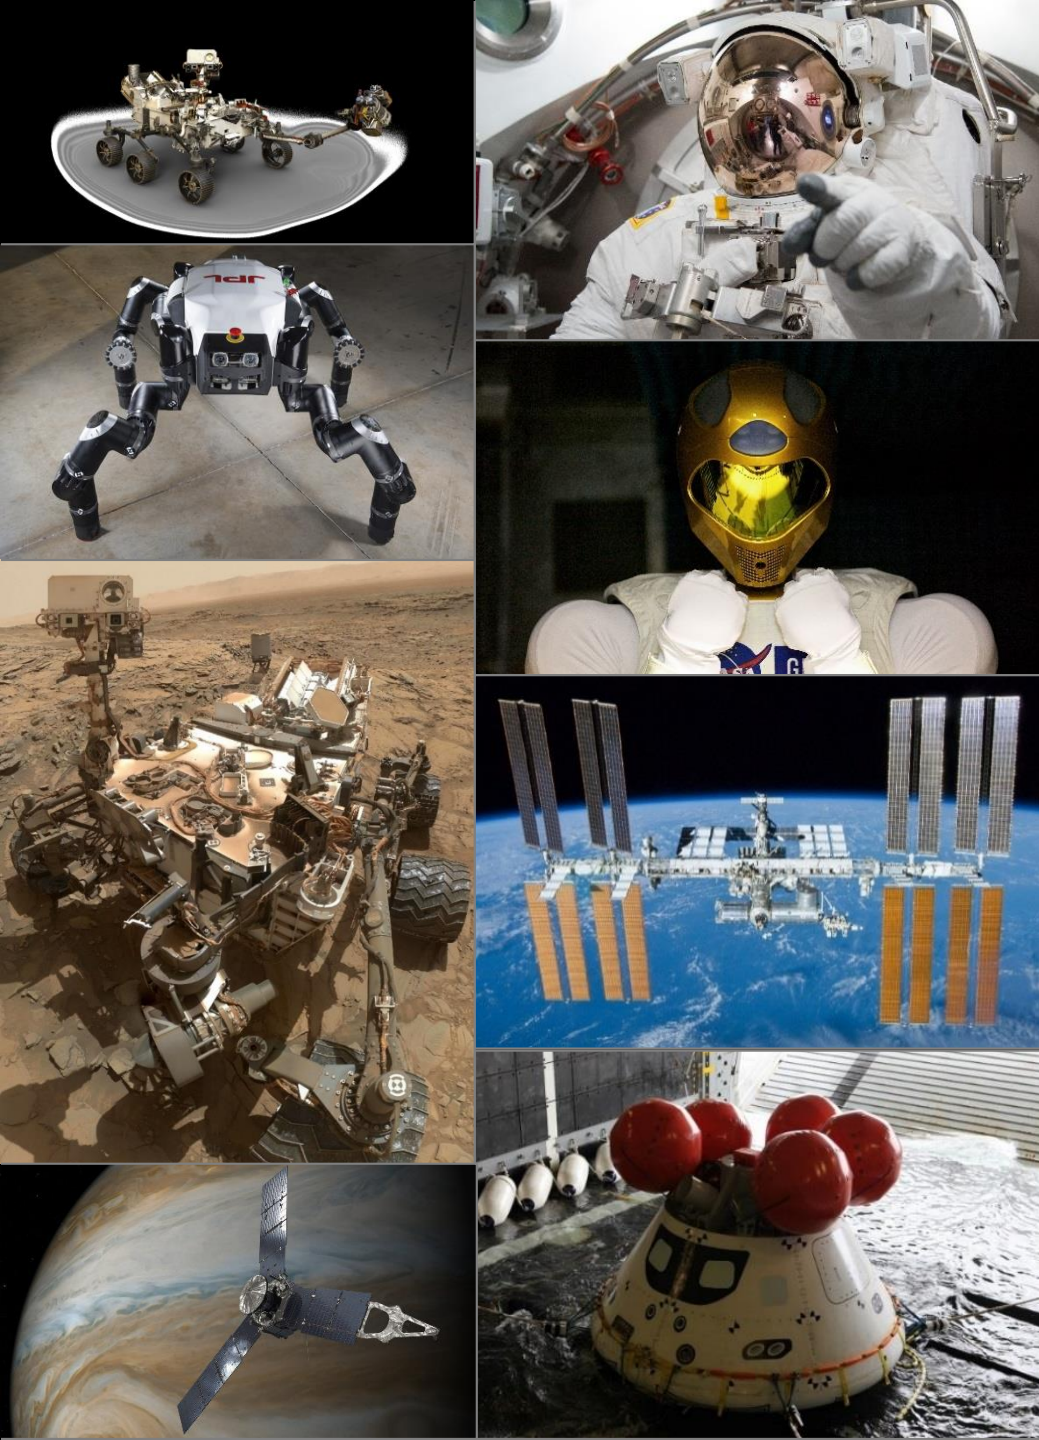

QUESTIONS?