

Superconducting Notch Filter for RFI Mitigation in Ground-Based Radio Telescope

Charles J Turner, Thomas Stevenson, Robin Cantor, Lawrence Hilliard, Thomas E Murphy, and Berhanu Bulcha

Abstract—This paper presents a high-rejection, thin-film HTS, microstrip bandstop filter to prevent a local and high-power RFI source from interfering with NASA GGAO’s VGOS cryogenic receiver. This filter has an excellent 2.7%, 50-dB-fractional-bandwidth and a center stop-band frequency of 9.41 GHz. It does not contain any narrow or interdigital features as found in some designs, which reduces the fringing electric fields and improves its power handling capability. The YBCO films were grown on 435- μm -thick R-plane sapphire substrate and the anisotropic behavior was modeled and simulated with a high degree of accuracy. The device was tested while cooled to 77 K and the measurements agree well with simulation.

Index Terms—high-temperature superconductors, radio astronomy, bandstop filters

I. INTRODUCTION

Radio Frequency Interference (RFI) mitigation can have a critical impact on the performance of receivers used for radio astronomy. Cryogenic receivers provide the necessary sensitivity to detect weak RF signals of galactic origin, but are especially susceptible to local RFI [1], [2]. Very Long Baseline Interferometry (VLBI) is a high angular resolution geodetic technique that uses cosmic radio sources as a reference to accurately measure global reference frames and monitor Earth’s orientation and variations. VLBI Global Observing System (VGOS) is the next-generation network of 12 m telescopes that provide broadband receiver systems with four frequency bands ranging from 2 to 14 GHz and high data rates to achieve a measurement accuracy of 1 mm in station position and 0.1 mm/year in station velocity on global scales [2], [3]. The Goddard Geophysical Astronomical Observatory (GGAO) is home to one of these VGOS helium-cooled receivers in Greenbelt, MD. Co-located approximately 110 m from this receiver, the Satellite Laser Ranging (SLR) system uses a 9.4 GHz radar to detect and prevent accidental illumination of overhead aircraft [4]. Under certain orientations, the VLBI receiver will measure one of the radar’s sidelobes. This scenario will saturate the front-end LNA and compromise receiver sensitivity, as well as potentially damage sensitive electronics. The presence of this interfering source imposes constraints on the dish orientation, sky coverage, and schedule; limiting both the scope and duration of observations.

C. Turner and T. Murphy are with the Department of Electrical and Computer Engineering, University of Maryland, College Park, MD 20742 USA (e-mail: cjturner@umd.edu; tem@umd.edu)

R. Cantor is President and Founder of STAR Cryoelectronics, Santa Fe, NM 87508 USA (e-mail: rcantor@starcryo.com)

B. Bulcha, T. Stevenson, and Lawrence Hilliard are with NASA Goddard Space Flight Center, 8800 Greenbelt Rd. Greenbelt, MD 20771 USA (e-mail: berhanu.t.bulcha@nasa.gov; lawrence.m.hilliard@nasa.gov; thomas.r.stevenson@nasa.gov)



Fig. 1. Photo of the 12 m GGAO VGOS antenna (courtesy of NASA SGP)

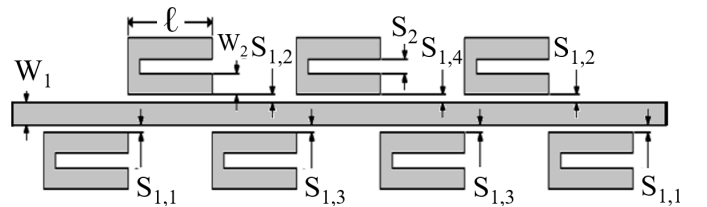


Fig. 2. Layout of microstrip self-coupled hairpin resonator notch filter design

Fortunately, the RFI falls between the various observation bands of this radio telescope and a suitable band rejection filter prior to the low-noise amplifier (LNA) would both protect sensitive electronics and enable uninterrupted full-sky observation. In our demonstrated filter, High Temperature Superconductor (HTS) planar circuits are used to minimize insertion loss in the pass-band and meet a strict form factor of 25 mm width, 32 mm length, and 6 mm height to fit in available space inside the existing receiver dewar. This notch filter must handle the higher-power radar sidelobe without a change in performance and requires at least 50 dB of signal rejection over 250 MHz of bandwidth with the stop-band centered on 9.4 GHz. To the best knowledge of the authors, no published HTS planar notch filter design has demonstrated a 50 dB fractional bandwidth of 2.7% in measurement.

We report here a notch filter realized in thin-film YBCO microstrip capable of rejecting a high-power local RFI source. The filter design consists of seven modified hairpin resonators where the arms are folded to increase parallel coupling. The

self-coupled hairpin resonator geometry provides the necessary shunt reactance to achieve higher stop-band rejection, demonstrates good quality factors to avoid significantly increasing insertion loss in the observation bands, and avoids the use of narrow-width microstrip or interdigital features. Current concentration at the resonator edges are the limiting factor in power handling capacity of HTS filters [5]. Using small features as in some other designs [6], [7] increases the amount of fringing electric fields along the microstrip edges and risks degrading the filter's performance while exposed to the local, high-power RFI source.

HTS filters have been employed in radio astronomy receivers in the past [8]. However, thin-film HTS notch filter designs are relatively neglected compared to their band-pass counterparts. Other resonator geometries have been measured at high external quality-factors, but impose an increased risk for this application due to their small features such as interdigital fingers or narrow meander lines [9]–[14]. HTS bulk disk and patch resonators have demonstrated higher power-handling capabilities [15]–[17], but in practice these bulkier resonators would not allow us to simultaneously achieve the quality factor, 50 dB fractional bandwidth, and volume requirements. Although not essential for this application, this filter layout is compatible with and could be modified by other filter design techniques such as Defected Ground Structure (DGS) [18] and cul-de-sac coupling configuration [19] to tailor its performance to other requirements.

II. BANDSTOP FILTER DESIGN

A. Materials

We selected 300 nm thin film YBCO on 435 μm thick R-plane sapphire substrate. This process achieved good epitaxial growth of YBCO and results in high-quality films to minimize surface resistivity. The selected substrate thickness and filter layout ensures a wide safety margin between the simulated current density and critical current density of the YBCO, such that the device could reliably handle a 1 Watt RFI signal with 50 Ω microstrip transmission lines when cooled to 20 K. R-plane sapphire provides low-dielectric losses and high thermal conductivity, but requires accurate electromagnetic (EM) simulation to address its anisotropic permittivity [20].

$$\epsilon_r = \begin{bmatrix} 10.0842 & -0.7842 & 0.7038 \\ -0.7842 & 10.0842 & -0.7038 \\ 0.7038 & -0.7038 & 9.9316 \end{bmatrix}$$

The 3D EM model incorporates this anisotropic permittivity matrix and is simulated through Ansys HFSS. In order to prevent a simulation error caused by the negative values in this permittivity matrix, it is necessary to insert a thin isotropic buffer ($\epsilon_r = 10$) on the ends of the anisotropic substrate and de-embed the waveports. The filter layout's orientation on the substrate could result in a frequency-shift of the stop-band and the EM model enabled us to accurately predict the impact of fabrication tolerances. At an ideal orientation, the simulation results agreed with an equivalent isotropic model with no noticeable impact to the field line behavior

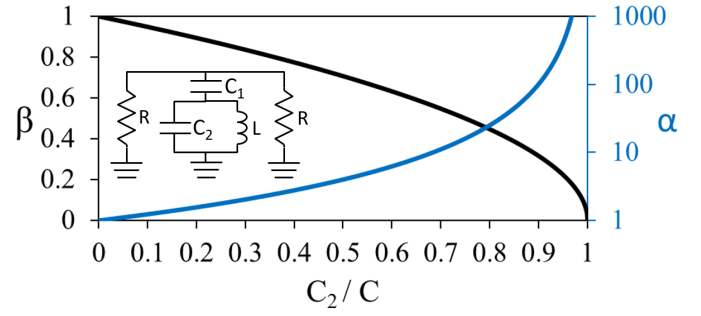


Fig. 3. Equivalent lumped circuit model for self-coupled hairpin resonator. When the sum $C_1 + C_2$ is held constant, the slope reactance and external quality factor will scale proportional to α .

or scattering parameters. However, rotating the filter layout near its optimal orientation results in approximately a 15 MHz shift per degree of rotation. Multiple design variations were produced on the wafer layout where the outer arm of the resonator was adjusted by increments of 25 μm to ensure a usable filter for the receiver in the first fabrication run.

B. Circuit

Fig. 2 illustrates the design layout and defines its physical dimensions. This filter design requires a 50-dB fractional bandwidth greater than 2.7%, and a 3-dB fractional bandwidth less than 5.3% to maximize stop-band RFI signal rejection and minimize pass-band insertion loss. Chebyshev values for a seven-element notch filter circuit set each element's required reactance slope values and external Q-factor (Q_e) values as large as 845 Ω and 35, respectively [21]. These relatively large values can be difficult to physically realize with planar microstrip. A typical planar microstrip notch filter design consists of a series of coupled half-wavelength resonators, each positioned a quarter-wavelength apart (with respect to the filter's center frequency ω_0) along the direction of propagation [21]. However, these designs limit coupling between the length (l) of the resonator and transmission line, making it difficult to achieve a larger coupling capacitance. Decreasing the gap (S_1) between the resonator and the transmission line will increase this capacitance, but only at the expense of decreasing (Q_e).

$$\omega_0^2 = \frac{1}{LC} = \frac{1}{L(C_1 + C_2)} = \frac{\beta^2}{LC_1} \quad (1)$$

$$X(\omega) = \frac{1 - \omega^2 L(C_1 + C_2)}{j\omega C_1(1 - \omega^2 LC_2)} \quad (2)$$

$$x = \frac{dX(\omega)}{d\omega} \frac{\omega_0}{2} = \alpha \omega_0 L \quad (3)$$

When $\Delta\omega = |\omega_0 - \omega| \ll \omega_0$:

$$|S_{21}| \approx [1 + (\frac{1}{4(x/Z_0)} \frac{\omega_0}{\Delta\omega})^2]^{-1/2} \quad (4)$$

$$Q_e = \alpha \frac{2}{R} \sqrt{\frac{L}{C}} \quad (5)$$

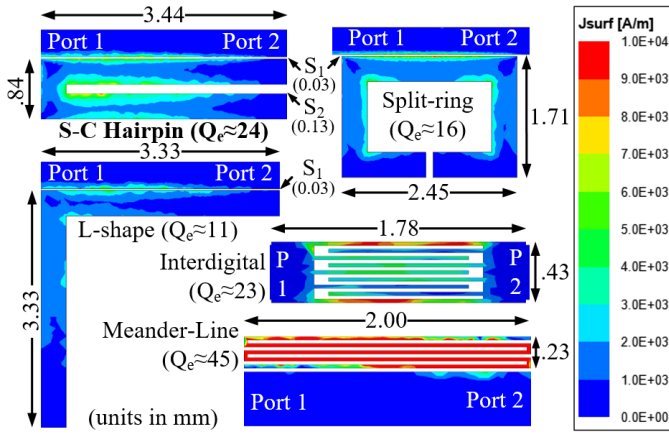


Fig. 4. Current density for various microstrip resonator geometries

Where:


$$\alpha = (1 - \frac{C_2}{C})^{-2}, \beta = \sqrt{1 - \frac{C_2}{C}} \quad (6)$$

The lumped element circuit in Fig. 3 approximates the response of the edge-coupled (transmission line to resonator), self-coupled (between resonator arms), hairpin resonator close to its resonant frequency. Folding the microstrip resonator introduces a parallel capacitance between its arms. The effect is equivalent to introducing a capacitance C_2 in parallel to the shunt inductance L in a lumped RLC circuit. If R , L and $C = C_1 + C_2$ are held constant, the resonant frequency ω_0 holds as C_2 increases and C_1 decreases. It also increases the reactance slope, insertion loss near the resonant frequency, and external quality factor as described by Eq.1 through 6. Eq. 1 equivalently describes both the resonant frequency for a common shunt RLC circuit and the depicted circuit with the given circuit parameter definitions. Eq. 2 and Eq. 3 define the circuit reactance and reactance slope respectively. Finally, Eq. 4 and Eq. 5 account for the insertion loss (or signal rejection) at frequencies near the resonant frequency and the external quality factor of the resonator.

Fig. 3 also illustrates the change in α and β as C_2/C is increased. The reactance slope and quality factor are proportional to α and increasing the reactance slope will increase the signal rejection at frequencies close to ω_0 . An additional advantage to this shunt circuit element is that as C_2/C increases, β decreases and reduces the effect a change in coupling capacitance to the resonator (ΔC_1) would have on a change in the resonator's center frequency ($\Delta\omega_0$). This artifact reduced the number of EM simulation model parameters and simplified the optimization process for the final filter design. Using this shunt circuit element enables us to choose inductance and capacitance values which meet the necessary reactance slopes of the Chebyshev filter model and can be realized with 50 Ω microstrip resonators.

C. Layout and EM Simulation

Fig. 4 shows the current density maps for a selection of various resonator geometries which were investigated for an

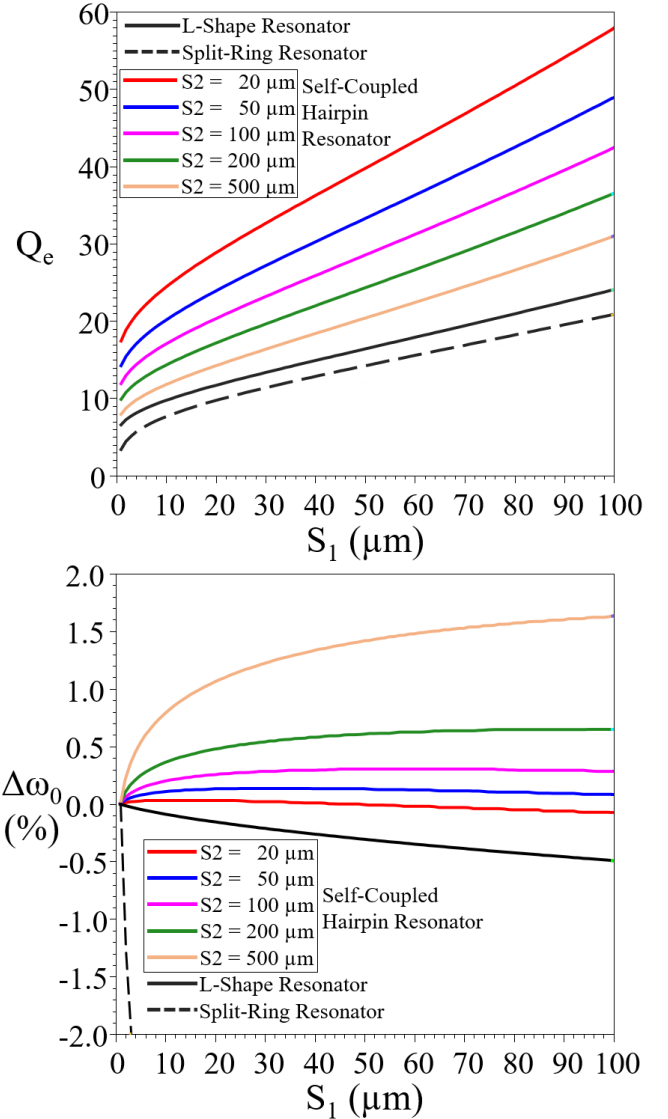
 Fig. 5. ADS microstrip circuit model simulations of external quality factor (Q_e) and shift in resonant frequency ($\Delta\omega_0$) for various resonators geometries

applied 1 Watt of power at 9.4 GHz. The smaller feature sizes of the interdigital or meander-line resonators result in more fringing electric fields and increased current density, increasing the current density beyond the targeted safety margin from the estimated critical current density. The L-shape and split-ring resonator examples had a lower Q_e (set to an equivalent coupling gap) and realized with 50 Ω transmission line. The split-ring resonator Q_e can be increased, but at the expense of expanding its width perpendicular to the transmission line. We chose the self-coupled hairpin resonator and set the gap at 127 μm as a trade-off between higher Q_e and lower current density.

Fig. 5 shows the ADS simulation results for a microstrip circuit model of the self-coupled hairpin resonator at different gaps between arms and compares it with microstrip circuit models of the L-shape and split-ring resonators. Observing the Q_e plot, S_2 is chosen for the range of achievable Q_e values

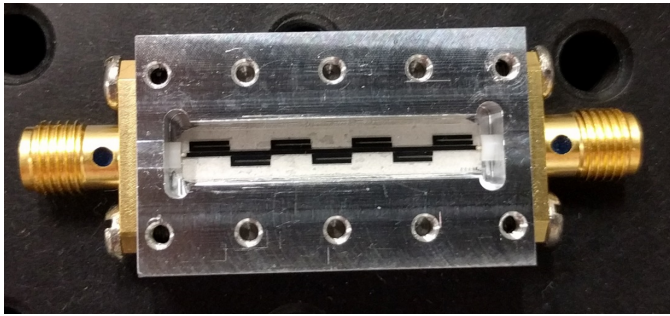


Fig. 6. Packaged notch filter with lid removed

while considering the current density from EM simulation. To physically realize the filter circuit, the appropriate values of S_1 are chosen from this plot. The $\Delta\omega_0$ plot highlights the additional advantage of decreasing the coupling gap between resonator arms. When S_2 is decreased, the change in resonant frequency also decreases with changing S_1 . This resulted in a closer agreement between circuit and EM simulation and reduced the simulation time and number of physical parameters that needed to be optimized.

Ansys HFSS provided 3D EM modeling and simulation of this filter design to account for the anisotropic substrate and minor parasitic impedances not captured in the simplified ADS circuit model. Optimizing the 3D EM model resulted in the following values as identified in Fig. 2: $w_1 = 381 \mu\text{m}$, $w_2 = 356 \mu\text{m}$, $l = 2.2 \text{ mm}$, $S_{1,1} = 76 \mu\text{m}$, $S_{1,2} = 38 \mu\text{m}$, $S_{1,3} = S_{1,4} = 25 \mu\text{m}$, and $S_2 = 127 \mu\text{m}$.

III. FABRICATION AND MEASUREMENTS

STAR Cryoelectronics performed the fabrication of the filter chips on a $435 \mu\text{m}$ thick R-plane sapphire wafer. The filter dimensions were patterned on thin-film YBCO with photo-lithography and the microstrip maintained a minimum $356 \times 0.3 \mu\text{m}$ cross-section. The selected R-plane crystal orientation allowed good quality epitaxial growth of YBCO films and the substrate thickness was important for achieving 50Ω transmission lines with physically realizable feature dimensions. For this application, the cryogenic receiver is cooled by compressed helium to 20 K and the T_c of YBCO is approximately 93 K, providing a buffer region of around 73 K. The film quality, cross-section, wafer thickness, operating temperature, and resonator geometry enhances its capability in rejecting higher-power RFI at 9.4 GHz without a degradation in performance while measuring the desired radio astronomy signals.

The final EM model incorporated multiple fabrication uncertainties which could impact filter performance. This included factors such as the circuit layout's orientation and position on the wafer. The sum effect of these various factors could shift the stop-band by an amount slightly less than half of the 50 dB fractional bandwidth. In order to ensure successful fabrication of an implementable filter in the first fabrication run, we created multiple design variations where the outer arm of each resonator was lengthened or shortened by $25 \mu\text{m}$. Small changes in temperature should not impact the

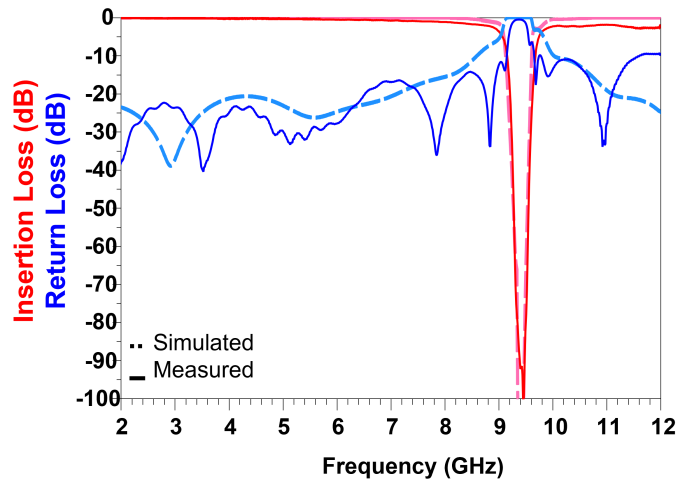


Fig. 7. Comparison of simulated and measured insertion loss and return loss for packaged filter cooled to 77K

TABLE I
COMPARISON WITH COMPARABLE BANDSTOP FILTERS

Ref	f_c (GHz)	$\Delta f_{20\text{dB}}$ (%)	$\Delta f_{50\text{dB}}$ (%)
[22]	1.8	0.9	—
[19]	2.0	1.9	—
[23]	14.8	2.9	—
[8]	1.6	7.9	—
[24]	1.4	0.7	0.5
[11]	2.3	1.3	0.8
[10]	2.2	1.8	1.1
[13]	2.0	4.2	1.5
[12]	0.9	7.8	1.5
This Work	9.4	4.3	2.7

filter's performance. The kinetic inductance in the YBCO film was approximated as less than 0.22 pH/square if operating at or below 20 K. This is a negligible contribution compared to an estimated 180 pH/square for the geometric inductance of the microstrip. As a result, initial testing of the filter was performed with liquid nitrogen (77 K) in a laboratory environment.

After dicing the wafer into chips, the nominal design was selected and epoxied into aluminum housing with a silver epoxy (EPO-TEK EJ2189-LV) suitable for cryogenic temperatures. SMA connectors were mounted to each side and the pins were similarly epoxied to $2 \mu\text{m}$ thick Au bond pads located on each end of the microstrip. Fig. 5 shows a picture of the final device without its lid. We used a Keysight VNA to measure the filter's insertion loss after reaching thermal equilibrium while submerged in liquid nitrogen. The VNA was calibrated for cable loss and stainless steel SMA cables were used to minimize thermal contraction in the cable length.

Fig. 6 provides a plot of the ADS simulation results and measurement. The measured filter achieved the target fractional bandwidth and is compared in Table 1 to other published notch filter designs. Another noteworthy achievement is that this filter design achieved a higher 50 dB fractional bandwidth, but in some cases a more narrow 20 dB fractional bandwidth than previously reported measurements. This is favorable for our application where we need strong stop-band rejection but

do not want a deliberately wideband design that overlaps with the observation bands of the radio telescope. The device was tested at approximately 57 K warmer than its intended operating temperature. Modeling the expected insertion loss based on use of the Mattis-Bardeen equation to estimate the quasi-particle dissipation at the actual operating temperature results in an approximate 2 dB insertion loss in the upper pass-band [25]. The maximum insertion loss in the lower and upper pass-bands are 0.614 dB and 2 dB, respectively. This loss is attributed to the test environment and impedance mismatch in the connector-to-chip interface as is apparent in the measured return loss as higher frequencies. We anticipate the insertion loss will be reduced in future testing at lower temperatures and in a revised packaging design. The measurement agrees well with simulation and confirms our estimation of kinetic inductance and insertion losses as a function of ambient temperature. In a future effort, we will assemble the filter chips in a new housing design and test these devices under the correct temperature of 20 K. The SMA connectors will also be replaced with 2.92 mm Ka-band connectors to provide improved higher-frequency performance and resilience to thermal cycling.

IV. CONCLUSION

Our team has successfully demonstrated a HTS microstrip notch filter with a significant 50-dB-fractional-bandwidth notch and low insertion loss in a wide pass-band to meet the described application's strict requirements. The selection of YBCO films, substrate parameters, and resonator geometry were tailored for a consistent filter response while exposed to a local and high-power RFI source. The self-coupled hairpin resonator design enabled us to physically realize the desired filter circuit model using planar microstrip and maintain a compact footprint. We anticipate improvements to the housing design will reduce losses at higher frequencies, making this device an immediately feasible solution for GGAO's VGOS RFI mitigation needs.

REFERENCES

- [1] P. V. Bout, "Interference and Radioastronomy," *Physics Today*, vol. 44, no. 11, pp. 41–49, 1991.
- [2] A. Nothnagel, T. Artz, D. Behrend, and Z. Malkin, "International VLBI Service for Geodesy and Astrometry: Delivering high-quality products and embarking on observations of the next generation," *Journal of Geodesy*, vol. 91, no. 7, pp. 711–721, jul 2017.
- [3] A. Niell, *et al.*, "Demonstration of a Broadband Very Long Baseline Interferometer System: A New Instrument for High-Precision Space Geodesy," *Radio Science*, vol. 53, no. 10, pp. 1269–1291, oct 2018.
- [4] J. F. McGarry, *et al.*, "NASA's satellite laser ranging systems for the twenty-first century," *Journal of Geodesy*, vol. 93, no. 11, pp. 2249–2262, nov 2019.
- [5] T. Zhang, J. Du, and Y. J. Guo, "High-Tc Superconducting Microwave and Millimeter Devices and Circuits—An Overview," *IEEE Journal of Microwaves*, vol. 2, no. 3, pp. 374–388, 2022.
- [6] L. Gao, *et al.*, "8-GHz narrowband high-temperature superconducting filter with high selectivity and flat group delay," *IEEE Transactions on Microwave Theory and Techniques*, vol. 57, no. 1, pp. 1767–1773, 2009.
- [7] T. Yu, *et al.*, "A wideband superconducting filter using strong coupling resonators for radio astronomy observatory," *IEEE Transactions on Microwave Theory and Techniques*, vol. 57, no. 1, pp. 1783–1789, 2009.
- [8] S. Wallage, J. L. Tauritz, G. H. Tan, P. Hadley, and J. E. Mooij, "High Tc superconducting CPW bandstop filters for radio astronomy front ends," *IEEE Transactions on Applied Superconductivity*, vol. 7, no. 2 PART 3, pp. 3489–3491, 1997.
- [9] H. Liu, *et al.*, "Design of High-Temperature Superconducting Wideband Bandpass Filter with Narrow-Band Notch Resonators for Radio Telescope Application," *IEEE Transactions on Applied Superconductivity*, vol. 27, no. 4, pp. 6–9, 2017.
- [10] Y. Heng, *et al.*, "Compact superconducting dual-band bandpass filter by combining bandpass and bandstop filters," *Electronics Letters*, vol. 49, no. 19, pp. 1230–1232, 2013.
- [11] S. Pal, M. J. Lancaster, and R. D. Norrod, "HTS bandstop filter for radio astronomy," *IEEE Microwave and Wireless Components Letters*, vol. 22, no. 5, pp. 236–238, 2012.
- [12] P. D. Laforge, R. R. Mansour, and M. Yu, "The use of low-pass filters as impedance inverters for highly miniaturized superconducting bandstop filter designs," *IEEE Transactions on Applied Superconductivity*, vol. 21, no. 3 PART 1, pp. 575–578, 2011.
- [13] A. Corona-Chavez, M. Nogues-Hoyos, L. Esteras-Otal, D. V. Murthy, and B. Sanchez-Rinza, "A high-temperature superconducting notch filter to suppress cellular-band interference in radiotelescopes," *IEEE Transactions on Applied Superconductivity*, vol. 21, no. 2, pp. 68–70, 2011.
- [14] Z. Aboush and A. Porch, "Compact, narrow bandwidth, lumped element bandstop resonators," *IEEE Microwave and Wireless Components Letters*, vol. 15, no. 8, pp. 524–526, 2005.
- [15] B. Aminov, *et al.*, "YBaCuO disk resonator filters operating at high power," *IEEE Transactions on Applied Superconductivity*, vol. 9, no. 2, pp. 4185–4188, jun 1999.
- [16] X. He, *et al.*, "An ultra-narrow band eight-pole dual-mode HTS patch filter," *Physica C: Superconductivity and its Applications*, vol. 469, no. 21, pp. 1925–1929, 2009.
- [17] T. Saito, S. Kodama, T. Saito, S. Ohshima, and A. Saito, "Design of High Power Handling Filter Using Cascaded Quadruplet Superconducting Bulk Resonators," *IEEE Transactions on Applied Superconductivity*, vol. 28, no. 4, pp. 4–7, 2018.
- [18] T. Zheng, *et al.*, "Design of a High-Power Superconducting Filter with Novel DGS Structures," *IEEE Transactions on Applied Superconductivity*, vol. 24, no. 6, 2014.
- [19] M. Ohira, M. Kanomata, Z. Ma, and X. Wang, "A New Microstrip Bandstop Filter for Fully Canonical Cul-de-Sac Coupling Configuration," in *IEEE MTT-S International Microwave Symposium Digest*, vol. 2018-June. Institute of Electrical and Electronics Engineers Inc., aug 2018, pp. 708–711.
- [20] F. Aiga, H. Fuke, Y. Terashima, M. Yamazaki, H. Kayano, and T. Hashimoto, "HTS hairpin microstrip filter on r-cut sapphire substrate," *IEEE Transactions on Applied Superconductivity*, vol. 13, no. 2 I, pp. 287–290, 2003.
- [21] J.-S. Hong and M. J. Lancaster, *Microstrip Filters for RF / Microwave*. Wiley, 2001, vol. 7.
- [22] Jia-Sheng Hong, *et al.*, "Thin film HTS passive microwave components for advanced communication systems," *IEEE Transactions on Applied Superconductivity*, vol. 9, no. 2, pp. 3893–3896, jun 1999.
- [23] M. Esmaili and J. Bornemann, "Microstrip bandstop filters using L- and T-shaped resonators," in *2015 Asia-Pacific Microwave Conference (APMC)*, vol. 0. IEEE, dec 2015, pp. 1–3.
- [24] G. Zhang, M. J. Lancaster, F. Huang, and N. Roddis, "A superconducting microstrip bandstop filter for an L-band radio telescope receiver," *35th European Microwave Conference 2005 - Conference Proceedings*, vol. 1, pp. 697–700, 2005.
- [25] D. C. Mattis and J. Bardeen, "Theory of the anomalous skin effect in normal and superconducting metals," *Phys. Rev.*, vol. 111, pp. 412–417, Jul 1958.