

NASA TECHNICAL NOTE



NASA TN D-3075

e.1

NASA TN D-3075

LOAN COPY: RETURN TO
AFWL (WLIL-2)
KIRTLAND AFB, N MEX.

0130067



FATIGUE OF RENÉ 41 UNDER CONSTANT-
AND RANDOM-AMPLITUDE LOADING AT
ROOM AND ELEVATED TEMPERATURES

by Edward P. Phillips
Langley Research Center
Langley Station, Hampton, Va.

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION • WASHINGTON, D. C.





FATIGUE OF RENÉ 41 UNDER CONSTANT- AND RANDOM-AMPLITUDE
LOADING AT ROOM AND ELEVATED TEMPERATURES

By Edward P. Phillips

Langley Research Center
Langley Station, Hampton, Va.

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION

For sale by the Clearinghouse for Federal Scientific and Technical Information
Springfield, Virginia 22151 - Price \$2.00

FATIGUE OF RENÉ 41 UNDER CONSTANT- AND RANDOM-AMPLITUDE

LOADING AT ROOM AND ELEVATED TEMPERATURES

By Edward P. Phillips
Langley Research Center

SUMMARY

Narrow-band random-amplitude and constant-amplitude bending fatigue tests were conducted on sharply notched René 41 specimens at room temperature, 700° F (644° K), and 1400° F (1033° K). When compared on the basis of the root mean square of the nominal peak stresses, the random loading generally gave shorter lives than the constant-amplitude loading. Theoretical life predictions were made for the random-loading tests by using the Palmgren-Miner cumulative-damage rule and two different peak stress distributions (the distribution determined from the tests and the classical Rayleigh distribution). The predictions underestimated the fatigue life in practically all cases. The predicted lives based on the Rayleigh peak distribution were always less than those predicted by using the experimentally determined peak distribution. For both types of loading in the long-life region, a loss of fatigue strength from that at room temperature occurred at 700° F (644° K) but no further loss occurred at 1400° F (1033° K).

INTRODUCTION

The prediction of the fatigue life of structures subjected to random loadings represents a challenging problem to present-day designers of aircraft and missiles. A particular vehicle may receive random loadings from several sources, each loading being characterized by a power spectrum of different magnitude and shape. At the present time no analytical methods are available to give accurate and consistent answers in this problem area even for materials for which the constant-amplitude fatigue properties are well-known. To make the problem even more difficult, the high-temperature environments in which many new vehicles must operate necessitate the use of new materials for which few fatigue data of any kind are available. A remedy to this situation is, of course, to conduct test programs employing representative random loadings and temperatures.

One material which is being considered for high-temperature structural applications is René 41, a nickel-base superalloy. Some constant-amplitude axial-load fatigue data are available and have been published in reference 1. The purpose of the present investigation was to compare the fatigue properties of René 41 under constant- and random-amplitude loading at room temperature ($\approx 78^\circ$ F or $\approx 299^\circ$ K), 700° F (644° K), and 1400° F (1033° K). All tests were

conducted on sharply notched cantilever-beam specimens with the loading applied at the free end. The stress response in the random-loading tests was narrow band in frequency and is representative of a structure for which a natural frequency occurs within the frequency range of the random-loading spectrum. Theoretical life predictions were made for the random-loading tests by using the Palmgren-Miner cumulative-damage theory. Two peak stress distributions were used in making the predictions, the distribution determined from the tests and, for comparison, the classical Rayleigh distribution which is often assumed for narrow-band stress response. (See refs. 2, 3, and 4.)

SYMBOLS

The units used for the physical quantities defined in this paper are given both in the U.S. Customary units and in the International System of Units (SI). (See ref. 5.) The Appendix presents factors relating these two systems of units.

| | |
|----------------------------|--|
| n | number of cycles applied at a given nominal peak stress |
| N | experimental life of fatigue specimen under constant-amplitude loading, cycles |
| N_F | theoretical life of fatigue specimen under random-amplitude loading, cycles |
| P_b | probability of stress peaks occurring in stress band |
| $(\overline{S^2})^{1/2}$ | root-mean-square nominal stress, ksi (MN/m ²) |
| S_p | nominal peak stress, ksi (MN/m ²) |
| $(\overline{S_p^2})^{1/2}$ | root mean square of nominal peak stresses, ksi (MN/m ²) |
| ρ | notch root radius, inches (cm) |

TESTS

Specimens

The specimen configuration used in this investigation is shown in figure 1. The dimensions shown in the figure are nominal; the actual dimensions used for computing section properties were determined by measuring to the nearest 0.0001 inch (3 μ m). This edge-notched configuration corresponds to a theoretical elastic-stress concentration factor of approximately 7 for an axially loaded specimen.

The René 41 material was obtained as nominal 3/16-inch (0.48-cm) thick sheet in the mill-annealed condition. The specimen blanks were sheared from the sheet with the longitudinal axis of the specimen parallel to the direction of rolling. The blanks were heat treated before machining according to the following procedures:

- (1) Heat to 1950° F (1339° K); maintain temperature for 30 minutes
- (2) Air cool to room temperature
- (3) Heat to 1400° F (1033° K); maintain temperature for 16 hours
- (4) Air cool to room temperature

This heat treatment was used to obtain maximum tensile strength. After heat treatment, the specimens were machined from the blanks, material being taken from all surfaces to remove the oxide film resulting from heat treatment. The finished specimens had a surface finish of approximately 0.0001 inch (3 μm) root mean square.

The tensile properties and nominal chemical composition of René 41 are given in tables I and II, respectively. The tensile properties were obtained from the present investigation and from reference 6.

Test Equipment and Procedure

All tests were conducted by using electromagnetic shakers as a means of loading. A 25-lbf (111-N) vector-force shaker was used for the random-loading tests and an 8-lbf (36-N) vector-force shaker for the constant-amplitude tests. The free end of the cantilevered specimen was attached to the shaker drive coil by means of a rod and flexible connector. The flexible connector minimized longitudinal and torsional loading of the specimen. A room-temperature test setup is shown in figure 2. A schematic of the testing machines is shown in figure 3.

Method of stress calibration.- The moving core of a linear variable differential transformer (LVDT) was rigidly attached to the drive coil of the shaker. Any displacement of the drive coil caused a change in the output of the LVDT. For each test, a specimen was alined in the grips and secured to the drive coil of the shaker. The load required to produce a desired nominal test-section stress was computed with the flexure formula and was applied statically by dead-weight loading. The change in output of the LVDT was recorded and used as the set point in the ensuing test. The stresses presented in this report are nominal stresses as calculated from the measured displacements by means of the flexure formula and thus do not take into account the effects of plasticity.

Random loading.- The input signals to the shaker for the random-loading tests were repetitions of a magnetic-tape recording of a 6.4-second sample of the noise produced by a 2-inch (5.1-cm) subsonic cold-air jet. The recording was frequency modulated so that wear of the tape would not affect the magnitude of the signal. This signal had been used previously in the fatigue

investigation in references 7 and 8. No significance is attached to using this particular signal in this investigation except that it is random and rather wide band in frequency.

Fifty-eight specimens were tested at zero mean stress, various root-mean-square stress (LVDT output) levels, and the three temperature levels. The root-mean-square stress was held constant at the calibration set point throughout each test. An automatic cutoff was provided to shut down the equipment when the specimen failed. Time to failure was recorded for each test.

Tests were monitored by using a root-mean-square (rms) voltmeter and an oscilloscope. An estimated maximum error of 5 percent on root-mean-square nominal stress was possible in the tests since the indicating needle of the root-mean-square voltmeter was continuously in motion and this motion had to be centered about the desired value by the person conducting the test.

Samples of the shaker input and stress-response signals were recorded simultaneously at the start of each test.

Constant-amplitude loading.- The input to the shaker for these tests was a sinusoidal signal from an oscillator which was adjusted to operate near the natural frequency of the specimen-shaker system. Sixty-seven specimens were tested at zero mean stress, various root-mean-square stress levels, and the three temperature conditions. The same techniques and equipment used in the random-loading tests were employed in conducting these tests.

Elevated-temperature testing.- For all tests the temperature was monitored and controlled with thermocouples which were spotwelded to the top of the fixed half of the grips. A calibration specimen with 9 thermocouples emplaced at the test section was used to determine the set point for the control thermocouple and to determine the length of time required to attain steady-state conditions.

Testing at 700° F (644° K) was accomplished by using commercially available tubular furnaces with a hole cut into the side to allow attachment of the forcing rod to the specimen. Power was supplied to the furnace through a power-stat which was regulated by a temperature controller-recorder unit. A test setup is shown in figure 4.

For testing at 1400° F (1033° K), the tubular furnaces proved to be too slow in heating; therefore, an apparatus employing quartz-tube radiant heaters and reflectors was built at the Langley Research Center. The temperature-control equipment was the same as that for the 700° F tests. A test setup is shown in figure 5.

RESULTS AND DISCUSSION

Stress Response for Random Loading

Typical power spectra of the shaker input (load) and the LVDT output (stress) are plotted in figures 6(a) and 6(b) with logarithmic vertical scales.

Samples of the time histories of these signals are also shown in figure 6(c). Although the shaker input was rather wide band in frequency, the specimen responded only to frequency components near its natural frequency. This type of response resulted in a stress history which was of essentially constant frequency but variable in amplitude.

Knowledge of the distribution of the peak stresses is important in characterizing the fatigue environment since the fatigue damage of a cycle of stress is generally considered to depend on stress amplitude rather than on the shape of the stress cycle. Therefore, distributions of peaks were obtained for several tests having different stress levels and temperatures. The distributions were obtained by recording the stress histories with a light-beam oscillograph and then manually measuring the distance of each peak from the mean over a 6.4-second sample. The root mean square of the peak stresses $\left(\overline{S_p^2}\right)^{1/2}$ was calculated from the measurements. For the first test, both positive and negative peaks were measured. The analysis, however, showed that the positive and negative peak distributions were practically the same; thus, for subsequent tests, only the positive peak distribution was obtained. The results of the measurements are shown in figure 7 in terms of $S_p/\left(\overline{S_p^2}\right)^{1/2}$ and in percent of peaks exceeding S_p . No trend due to stress level or temperature was noted from the distributions. An average distribution for all the tests is described by the dashed line drawn through the data. The solid line in the figure describes the Rayleigh distribution.

Test Results

The results of the random-loading tests are presented in table III and are plotted in figure 8 in terms of cycles to failure and root-mean-square nominal stress, the quantity measured in the test. The cycles to failure were not measured in the tests but were computed as the product of time to failure and the natural frequency of the specimen. Curves were faired through the data for each temperature condition.

The results of the constant-amplitude tests are presented in table IV and are plotted in figure 9 in terms of peak nominal stress and cycles to failure. The cycles to failure were computed by the same procedures as those for the random-loading tests. Curves were faired through the data for each temperature condition and extrapolated to higher stress levels since information was required at these levels for the theoretical predictions of random-loading results.

Theoretical Life Predictions

Theoretical life predictions were made for the random-loading tests based on the Palmgren-Miner linear cumulative-damage theory. To make the calculations, it was assumed that each positive peak stress was followed by a negative peak stress of the same magnitude. This assumption was justified since the

positive and negative peak distributions were practically identical and since the stress time history had the appearance of a modulated sine wave. The calculations were made for various values of the root mean square of the peak stresses.

Two life predictions were generated for each temperature condition; one using the measured peak distribution and, for comparison, one using the Rayleigh distribution. The method of calculation of predicted life for each distribution is as follows:

To calculate the theoretical cycles to failure by using the measured peak stress distribution, figure 7 was divided into small, equal bands of $\frac{S_p}{(\overline{S_p^2})^{1/2}}$ and the probability P_b of peaks occurring in each band was determined. The probability of peaks occurring in each band was divided by the constant-amplitude life N at the band midpoint stress, and the resulting quotients were summed. The reciprocal of this sum gives the predicted life, or expressed mathematically is:

$$N_F = \left(\sum \frac{P_b}{N} \right)^{-1}$$

To calculate the cycles to failure by using the Rayleigh distribution, the same procedure was used except that the probability of peaks in each stress band was calculated by using the Rayleigh probability density function. The upper cutoff level in stress magnitudes included in these calculations was taken as the level at which $\frac{P_b}{N}$ did not change the sum of quotients by more than 0.1 percent. This method of calculation of theoretical fatigue life is essentially the same as that explained in reference 2.

Comparison of Results

Comparison of constant and random loading.- In order to compare the constant- and random-amplitude tests on the basis of peak stresses, the ordinates of figures 8 and 9 were converted to the root mean square of peak stresses and the faired curves were replotted in figures 10, 11, and 12. For the constant-amplitude tests, the root mean square of peak stresses is the same as the stress amplitude or S_p . In the case of the random-loading tests, the root-mean-square stress was converted to the root mean square of peak stresses by the relation

$$\left(\overline{S_p^2} \right)^{1/2} = \left(2\overline{S^2} \right)^{1/2}$$

This relation was developed in reference 7 and is based on the theory of reference 9 for the narrow-band response of a lightly damped single-degree-of-freedom system.

When compared at equal values of the root mean square of peak stresses, the mean lives under random loading were generally shorter than those under constant-amplitude loading, the difference increasing from high to low stress levels. The only case where life under random loading was longer than that under constant-amplitude loading was at 1400° F (1033° K) at the highest random-loading stress levels. (See fig. 12.)

Comparison of experimental and predicted lives.- The fatigue-life predictions for the random-loading tests were made by using the Palmgren-Miner concept of fatigue damage in which $\sum \frac{n}{N} = 1$ means total damage or fatigue failure. Two life predictions were made for each temperature condition; one used the measured peak stress distribution, and the other used the Rayleigh peak stress distribution. The results of the life predictions for room temperature, 700° F (644° K), and 1400° F (1033° K) are plotted in figures 10, 11, and 12, respectively. The life predictions made by using the measured peak distribution were always greater than those made by using the Rayleigh peak distribution; however, the difference between the life predictions was generally small.

In practically all cases, experimental lives were greater than those predicted by using either the measured peak distribution or the Rayleigh peak distribution. Since the predicted lives represent $\sum \frac{n}{N} = 1$, this result means that for practically all the random-loading tests, $\sum \frac{n}{N} > 1$.

A clear trend for $\sum \frac{n}{N}$ for narrow-band random loading with a zero mean has not emerged from the literature. This point is illustrated in the following table:

| Source | Specimen material | Type of loading | Type of specimen | Trend for $\sum \frac{n}{N}$ |
|-----------------------|---------------------------|-----------------|-----------------------|------------------------------|
| Reference 3 | 2024 aluminum alloy | Bending | Central hole | <1 |
| Reference 8 | SAE 4130 normalized steel | Bending | Edge notched | <1 |
| Reference 10 | 24 ST aluminum alloy | Bending | Circumferential notch | <1 |
| Reference 11 | 2024 aluminum alloy | Bending | Circumferential notch | <1 |
| Reference 12 | 2024-T3 aluminum alloy | Bending | Unnotched | <1 |
| Reference 4 | L.73 aluminum alloy | Axial | Unnotched | >1 |
| Reference 7 | 7075-T6 aluminum alloy | Bending | Edge notched | >1 |
| Present investigation | René 41 | Bending | Edge notched | >1 |

A complete explanation cannot be given for the differences reported, but there is evidence that some of the differences in results could be due to the materials tested. For example, it has been reported in references 13 and 14 that for variable-amplitude tests with zero mean, 7075-T6 aluminum alloy gave consistently higher values of $\sum \frac{n}{N}$ than 2024-T3 aluminum alloy did. Of the investigations listed in the previous table, one used 7075 aluminum alloy and reported $\sum \frac{n}{N} > 1$, whereas four employed 2024 aluminum alloy and reported $\sum \frac{n}{N} < 1$. Adding to this evidence is the fact that the test programs of references 7 and 8 were practically identical except for specimen material and yet the tests resulted in different trends for $\sum \frac{n}{N}$.

Temperature effects.- For short lives, a progressive loss of fatigue strength occurred with increase in temperature, the greatest loss occurring between 700° F (644° K) and 1400° F (1033° K). (See figs. 8 and 9.) For longer lives, however, the curves for 700° F and 1400° F begin to converge and in the case of constant-amplitude loading, fatigue strength at 1400° F is higher than that at 700° F. The constant-amplitude S-N curve for 1400° F is marked by a very sharp break at the knee; this result, however, is based on a rather small number of data points.

The result that the fatigue strength did not progressively decrease with increase in temperature in the long-life region is not unique to René 41. Similar behavior has been reported for SAE 4340 steel in reference 15 and for PH15-7Mo stainless steel (Condition TH 1050) in reference 16.

CONCLUDING REMARKS

Narrow-band random-amplitude and constant-amplitude bending fatigue tests were conducted on sharply notched René 41 specimens. Tests were conducted at room temperature, 700° F (644° K), and 1400° F (1033° K). Theoretical life predictions were made for the random-loading tests by using the Palmgren-Miner cumulative-damage rule and two different peak stress distributions, the distribution determined from the tests and the classical Rayleigh distribution. From the data presented, the following observations are made:

1. When compared on the basis of the root mean square of peak nominal stresses, the random loading generally gave shorter fatigue lives than the constant-amplitude loading.
2. In practically all cases, the experimental lives were greater than those predicted by using either the measured peak stress distribution or the Rayleigh peak stress distribution.
3. The life predictions made by using the measured peak stress distribution were always greater than those made by using the Rayleigh distribution.

4. For short lives, a progressive loss of fatigue strength occurred with increase in temperature. For long lives, fatigue strength decreased from room temperature to 700° F (644° K) but did not decrease further at 1400° F (1033° K).

Langley Research Center,
National Aeronautics and Space Administration,
Langley Station, Hampton, Va., August 12, 1965.

APPENDIX

CONVERSION OF U.S. CUSTOMARY UNITS TO SI UNITS

The International System of Units (SI) was adopted by the Eleventh General Conference on Weights and Measures, Paris, October 1960, in Resolution No. 12 (ref. 5). Conversion factors for the units used herein are given in the following table:

| Physical quantity | U.S. Customary Unit | Conversion factor (*) | SI unit |
|-------------------|-----------------------------|-----------------------|--|
| Length | in. | 0.0254 | meters (m) |
| Temperature | $^{\circ}\text{F} + 459.67$ | 5/9 | degrees Kelvin ($^{\circ}\text{K}$) |
| Force | lbf | 4.448 | newtons (N) |
| Stress | psi = lbf/in. ² | 6.895×10^3 | newtons per sq meter (N/m ²) |

*Multiply value given in U.S. Customary Unit by conversion factor to obtain equivalent in SI unit.

Prefixes to indicate multiple of units are as follows:

| Prefix | Multiple |
|-----------------|-----------|
| kilo (k) | 10^3 |
| mega (M) | 10^6 |
| giga (G) | 10^9 |
| centi (c) | 10^{-2} |
| micro (μ) | 10^{-6} |

REFERENCES

1. Greene, A.; et al.: Research Investigation To Determine Mechanical Properties of Nickel and Cobalt-Base Alloys for Inclusion in Military Handbook 5. ML-TDR-64-116, vol. I, U.S. Air Force, Oct. 1964.
2. McClymonds, J. C.; and Ganoung, J. K.: Combined Analytical and Experimental Approach for Designing and Evaluating Structural Systems for Vibration Environments. Eng. Paper No. 3091, Missile and Space Systems Div., Douglas Aircraft Co., Oct. 1964.
3. Smith, P. W., Jr.; and Malme, C. I.: Fatigue Tests of a Resonant Structure With Random Excitation. J. Acoustical Soc. Am., vol. 35, no. 1, Jan. 1963, pp. 43-46.
4. Lowcock, M. T.; and Williams, T. R. G.: Effect of Random Loading On the Fatigue Life of Aluminum Alloy L.73. A.A.S.U. Rept. No. 225, Univ. of Southampton (Hampshire, England), July 1962.
5. Mechtly, E. A.: The International System of Units - Physical Constants and Conversion Factors. NASA SP-7012, 1964.
6. Weiss, V.; and Sessler, J. G., eds.: Aerospace Structural Metals Handbook. Volume II - Non-Ferrous Alloys. ASD-TDR-63-741, Vol. II, U.S. Air Force, Mar. 1963. (Revised Mar. 1964.)
7. Fralich, Robert W.: Experimental Investigation of Effects of Random Loading on the Fatigue Life of Notched Cantilever-Beam Specimens of 7075-T6 Aluminum Alloy. NASA MEMO 4-12-59L, 1959.
8. Fralich, Robert W.: Experimental Investigation of Effects of Random Loading on the Fatigue Life of Notched Cantilever-Beam Specimens of SAE 4130 Normalized Steel. NASA TN D-663, 1961.
9. Miles, John W.: An Approach to the Buffeting of Aircraft Structures by Jets. Rept. No. SM-14795, Douglas Aircraft Co., Inc., June 1953.
10. Head, A. K.; and Hooke, F. H.: Random Noise Fatigue Testing. Proc. Int. Conf. on Fatigue of Metals (London and New York), Inst. Mech. Eng. and A.S.M.E., 1956, pp. 301-303.
11. Kowalewski, J.: On the Relation Between Fatigue Lives Under Random Loading and Under Corresponding Program Loading. Full-Scale Fatigue Testing of Aircraft Structures, F. J. Plantema and J. Schijve, eds., Pergamon Press, 1961, pp. 60-75.
12. Fuller, J. R.: Research on Techniques of Establishing Random Type Fatigue Curves for Broad Band Sonic Loading. ASD-TDR-62-501 (Contract AF 33(616)-8087), U.S. Air Force, Oct. 1962.

13. Naumann, Eugene C.; Hardrath, Herbert F.; and Guthrie, David E.: Axial-Load Fatigue Tests of 2024-T3 and 7075-T6 Aluminum-Alloy Sheet Specimens Under Constant- and Variable-Amplitude Loads. NASA TN D-212, 1959.
14. Naumann, Eugene C.: Variable-Amplitude Fatigue Tests With Particular Attention to the Effects of High and Low Loads. NASA TN D-1522, 1962.
15. Trapp, W. J.: Elevated Temperature Fatigue Properties of SAE 4340 Steel. WADC Tech. Rept. 52-325, Pt. 1, U.S. Air Force, Dec. 1952.
16. Illg, Walter; and Castle, Claude B.: Axial-Load Fatigue Properties of PH 15-7 Mo Stainless Steel in Condition TH 1050 at Ambient Temperature and 500° F. NASA TN D-2358, 1964.

TABLE I.- TENSILE PROPERTIES OF RENÉ 41 AT ROOM AND ELEVATED TEMPERATURES

| Source | Temperature | Number of tests | Ultimate tensile strength | | Yield strength (0.2% offset) | | Elongation, percent | Modulus of elasticity | |
|-----------------------|-------------------|-----------------|---------------------------|-------------------|------------------------------|-------------------|-----------------------------|--------------------------------|-------------------|
| | | | ksi | MN/m ² | ksi | MN/m ² | | ksi | GN/m ² |
| Present investigation | Room | 7 | 178 minimum | 1228 minimum | 128 minimum | 883 minimum | 11.0 minimum ^{a,b} | 29.4 × 10 ³ minimum | 202.9 minimum |
| | | | 182 average | 1256 average | 131 average | 904 average | 12.9 average ^{a,b} | 30.4 × 10 ³ average | 210.0 average |
| | | | 187 maximum | 1290 maximum | 135 maximum | 932 maximum | 15.5 maximum ^{a,b} | 31.2 × 10 ³ maximum | 215.3 maximum |
| Reference 6 | Room | --- | 185 | 1276 | 140 | 966 | ^c 18.2 | 30.2 × 10 ³ | 208.4 |
| | 700° F (644° K) | --- | 180 | 1242 | 131 | 904 | ^c 16.5 | 27.3 × 10 ³ | 188.4 |
| | 1400° F (1033° K) | --- | 149 | 1028 | 117 | 807 | ^c 14.8 | 20.2 × 10 ³ | 139.4 |

^aBased on 6 tests.

^b2.00-inch (5.08-cm) gage length.

^cNo gage length given.

TABLE II.- NOMINAL CHEMICAL COMPOSITION OF RENÉ 41

| Element | Percent |
|------------|----------------|
| Carbon | 0.06 to 0.12 |
| Silicon | 0.50 maximum |
| Manganese | 0.50 maximum |
| Iron | 5.00 maximum |
| Chromium | 18.00 to 20.00 |
| Boron | 0.003 to 0.010 |
| Cobalt | 10.00 to 12.00 |
| Molybdenum | 9.00 to 10.50 |
| Titanium | 3.00 to 3.30 |
| Aluminum | 1.40 to 1.60 |
| Nickel | Balance |

TABLE III.- RESULTS OF RANDOM-LOADING FATIGUE TESTS OF RENE 41 SPECIMENS AT ROOM AND ELEVATED TEMPERATURES WITH ZERO MEAN STRESS

| | $(\bar{s}^2)^{1/2}$ | | Time to failure | Natural frequency | Fatigue life |
|-------------------|---------------------|-------------------|-----------------|-------------------|--------------|
| ksi | | MN/m ² | Minutes | cps or Hz | Cycles |
| Room temperature | | | | | |
| 52.8 | | 364 | 8 | 106 | 50 880 |
| 50.0 | | 345 | 10 | 107 | 64 200 |
| 50.0 | | 345 | 12 | 108 | 77 760 |
| 50.0 | | 345 | 14 | 101 | 84 840 |
| 40.0 | | 276 | 32 | 101 | 193 920 |
| 40.0 | | 276 | 36 | 101 | 218 160 |
| 40.0 | | 276 | 46 | 105 | 289 800 |
| 30.0 | | 207 | 112 | 110 | 739 200 |
| 30.0 | | 207 | 120 | 104 | 748 800 |
| 30.0 | | 207 | 125 | 102 | 765 000 |
| 30.0 | | 207 | 114 | 112 | 766 080 |
| 30.0 | | 207 | 152 | 103 | 939 360 |
| 30.0 | | 207 | 192 | 103 | 1 186 560 |
| 25.0 | | 172 | 281 | 105 | 1 770 300 |
| 25.0 | | 172 | 310 | 104 | 1 934 400 |
| 25.0 | | 172 | 507 | 106 | 3 224 520 |
| 20.0 | | 138 | 4 31 | 103 | 2 663 580 |
| 20.0 | | 138 | 860 | 105 | 5 418 000 |
| 20.0 | | 138 | 1 010 | 109 | 6 605 400 |
| 20.0 | | 138 | 2 397 | 106 | 15 244 920 |
| 20.0 | | 138 | 3 612 | 106 | 22 972 320 |
| 20.0 | | 138 | 12 902 | 108 | 83 604 960 |
| 17.0 | | 117 | 4 671 | 107 | 29 987 820 |
| 15.0 | | 104 | >11 365 | 101 | >68 871 900 |
| 700° F (644° K) | | | | | |
| 37.5 | | 259 | 30 | 104 | 187 200 |
| 36.7 | | 253 | 21 | 102 | 128 200 |
| 30.0 | | 207 | 96 | 98 | 564 480 |
| 30.0 | | 207 | 94 | 103 | 580 920 |
| 30.0 | | 207 | 81 | 100 | 486 000 |
| 30.0 | | 207 | 80 | 102 | 489 600 |
| 28.3 | | 195 | 52 | 108 | 336 960 |
| 20.0 | | 138 | 443 | 102 | 2 711 160 |
| 20.0 | | 138 | 578 | 103 | 3 572 040 |
| 20.0 | | 138 | 729 | 98 | 4 286 520 |
| 20.0 | | 138 | 811 | 103 | 5 011 980 |
| 17.0 | | 117 | 894 | 107 | 5 739 480 |
| 15.0 | | 104 | 1 749 | 102 | 10 703 880 |
| 15.0 | | 104 | 2 724 | 102 | 16 670 880 |
| 15.0 | | 104 | 3 840 | 103 | 23 731 200 |
| 13.0 | | 90 | 3 984 | 102 | 24 382 080 |
| 13.0 | | 90 | 5 076 | 98 | 29 846 880 |
| 10.0 | | 69 | >17 634 | 102 | >107 920 080 |
| 1400° F (1033° K) | | | | | |
| 26.3 | | 181 | 35 | 98 | 205 800 |
| 25.0 | | 172 | 43 | 97 | 250 260 |
| 25.0 | | 172 | 55 | 96 | 316 800 |
| 20.0 | | 138 | 96 | 98 | 564 480 |
| 20.0 | | 138 | 107 | 95 | 609 900 |
| 20.0 | | 138 | 130 | 94 | 733 200 |
| 15.0 | | 104 | 276 | 99 | 1 639 440 |
| 15.0 | | 104 | 463 | 94 | 2 611 320 |
| 15.0 | | 104 | 466 | 96 | 2 684 160 |
| 15.0 | | 104 | 539 | 100 | 3 234 000 |
| 13.0 | | 90 | 671 | 95 | 3 824 700 |
| 13.0 | | 90 | 702 | 97 | 4 085 640 |
| 13.0 | | 90 | 825 | 96 | 4 752 000 |
| 13.0 | | 90 | 1 833 | 97 | 10 668 060 |
| 11.0 | | 76 | 11 556 | 94 | 65 175 840 |
| 10.0 | | 69 | >17 187 | 99 | >102 090 780 |

TABLE IV. - RESULTS OF CONSTANT-AMPLITUDE FATIGUE TESTS OF RENÉ 41 SPECIMENS AT ROOM AND ELEVATED TEMPERATURES WITH ZERO MEAN STRESS

| ksi | $(\bar{s}^2)^{1/2}$ MN/m ² | Time to failure | Natural frequency | Fatigue life |
|-------------------|--|-----------------|-------------------|--------------|
| | | Minutes | cps or Hz | Cycles |
| Room temperature | | | | |
| 50.0 | 345 | 12 | 105 | 75 600 |
| 50.0 | 345 | 15 | 105 | 94 500 |
| 50.0 | 345 | 20 | 104 | 124 800 |
| 50.0 | 345 | 22 | 101 | 133 320 |
| 40.0 | 276 | 24 | 105 | 151 200 |
| 40.0 | 276 | 30 | 106 | 190 800 |
| 40.0 | 276 | 45 | 115 | 310 500 |
| 40.0 | 276 | 76 | 104 | 474 240 |
| 40.0 | 276 | 102 | 99 | 605 880 |
| 30.0 | 207 | 156 | 102 | 954 720 |
| 30.0 | 207 | 192 | 105 | 1 209 600 |
| 30.0 | 207 | 477 | 102 | 2 919 240 |
| 30.0 | 207 | 603 | 103 | 3 726 540 |
| 30.0 | 207 | 635 | 103 | 3 924 300 |
| 30.0 | 207 | 906 | 100 | 5 436 000 |
| 30.0 | 207 | 954 | 101 | 5 781 240 |
| 30.0 | 207 | 1 276 | 102 | 7 809 120 |
| 25.0 | 172 | 804 | 102 | 4 920 480 |
| 25.0 | 172 | 1 074 | 106 | 6 830 640 |
| 25.0 | 172 | 2 188 | 100 | 13 128 000 |
| 25.0 | 172 | 2 724 | 104 | 16 997 760 |
| 25.0 | 172 | 4 315 | 102 | 26 407 800 |
| 22.0 | 152 | 1 728 | 106 | 10 990 080 |
| 22.0 | 152 | 4 170 | 102 | 25 520 400 |
| 22.0 | 152 | 4 326 | 104 | 26 994 240 |
| 22.0 | 152 | >17 346 | 103 | >107 198 280 |
| 20.0 | 138 | >18 098 | 104 | >112 931 520 |
| 700° F (644° K) | | | | |
| 50.0 | 345 | 11 | 96 | 63 360 |
| 50.0 | 345 | 12 | 97 | 69 840 |
| 50.0 | 345 | 15 | 97 | 87 300 |
| 40.0 | 276 | 15 | 98 | 88 200 |
| 40.0 | 276 | 24 | 96 | 138 240 |
| 40.0 | 276 | 28 | 97 | 162 960 |
| 40.0 | 276 | 33 | 98 | 194 040 |
| 30.0 | 207 | 96 | 96 | 552 960 |
| 30.0 | 207 | 100 | 98 | 588 000 |
| 30.0 | 207 | 138 | 98 | 811 440 |
| 30.0 | 207 | 175 | 97 | 1 018 500 |
| 25.0 | 172 | 242 | 96 | 1 393 920 |
| 25.0 | 172 | 333 | 98 | 1 958 040 |
| 25.0 | 172 | 399 | 100 | 2 394 000 |
| 20.0 | 138 | 240 | 98 | 1 411 200 |
| 20.0 | 138 | 378 | 98 | 2 222 640 |
| 20.0 | 138 | 749 | 99 | 4 449 060 |
| 20.0 | 138 | 849 | 95 | 4 839 300 |
| 20.0 | 138 | 11 241 | 101 | 68 120 460 |
| 20.0 | 138 | 12 020 | 97 | 69 956 400 |
| 17.0 | 117 | 2 919 | 96 | 16 813 440 |
| 17.0 | 117 | 5 892 | 99 | 34 998 480 |
| 17.0 | 117 | >18 601 | 98 | >109 373 880 |
| 1400° F (1033° K) | | | | |
| 40.0 | 276 | 9 | 91 | 49 140 |
| 40.0 | 276 | 10 | 93 | 55 800 |
| 40.0 | 276 | 10 | 93 | 55 800 |
| 40.0 | 276 | 10 | 94 | 56 400 |
| 30.0 | 207 | 20 | 98 | 117 600 |
| 30.0 | 207 | 24 | 90 | 129 600 |
| 30.0 | 207 | 25 | 96 | 144 000 |
| 30.0 | 207 | 33 | 93 | 184 140 |
| 20.0 | 138 | 53 | 94 | 298 920 |
| 20.0 | 138 | 56 | 94 | 315 840 |
| 20.0 | 138 | 65 | 94 | 366 600 |
| 20.0 | 138 | 67 | 94 | 377 880 |
| 20.0 | 138 | 78 | 94 | 439 920 |
| 18.0 | 124 | 5 641 | 94 | 31 815 240 |
| 18.0 | 124 | 12 582 | 94 | 70 962 480 |
| 18.0 | 124 | >17 802 | 93 | >99 335 160 |
| 15.0 | 104 | >18 213 | 94 | >102 721 320 |

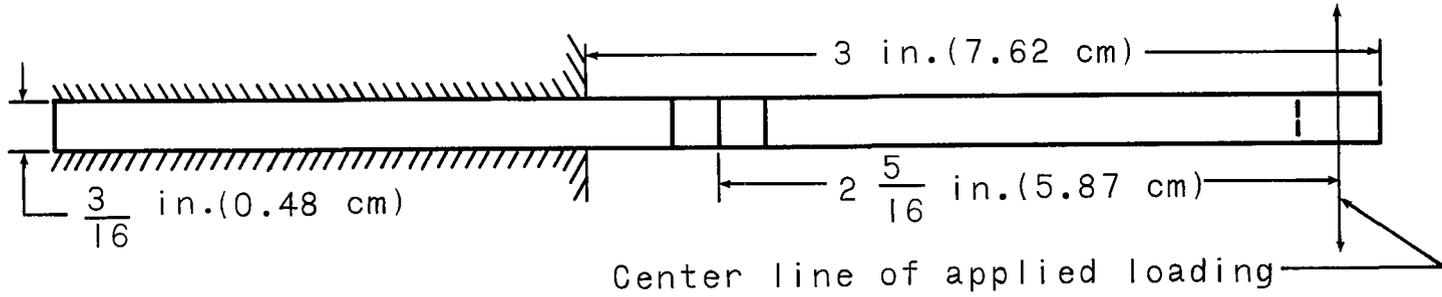
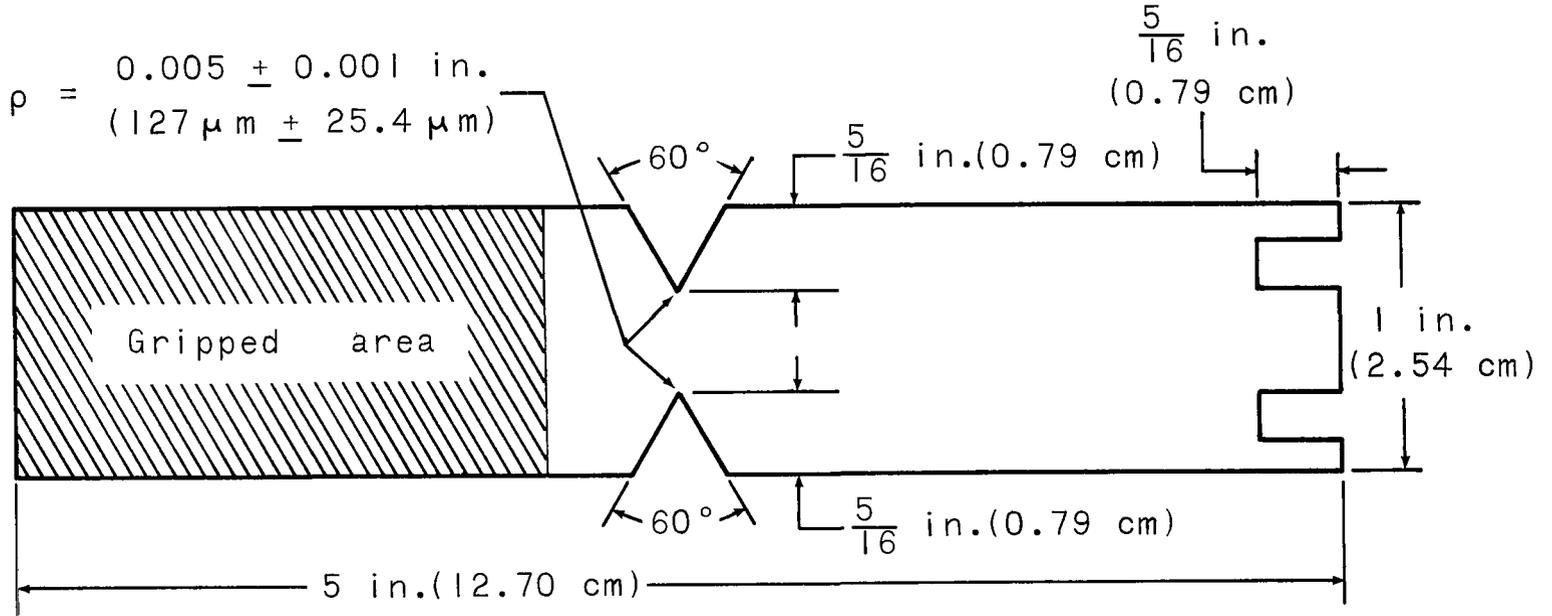


Figure 1.- Specimen configuration for fatigue tests on René 41.

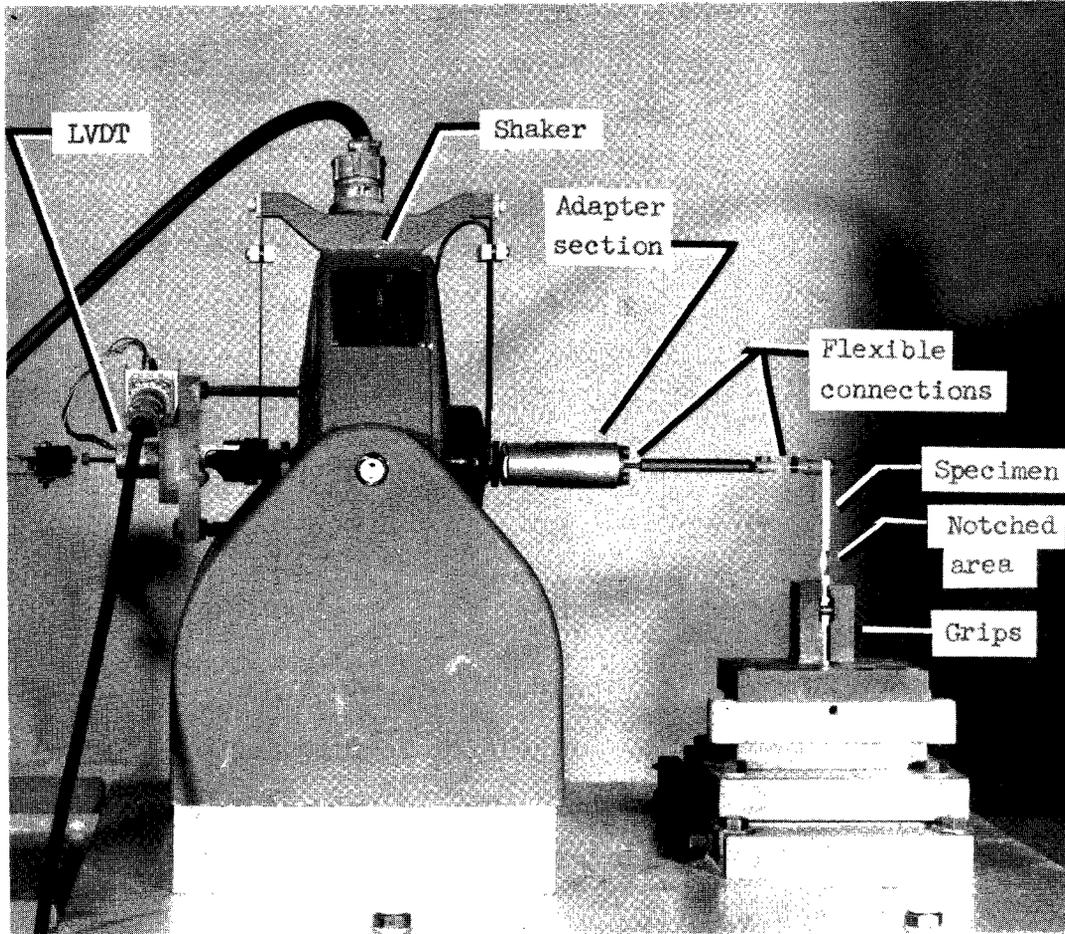


Figure 2.- Typical test setup for room-temperature fatigue test of René 41 specimen.

L-64-1007.1

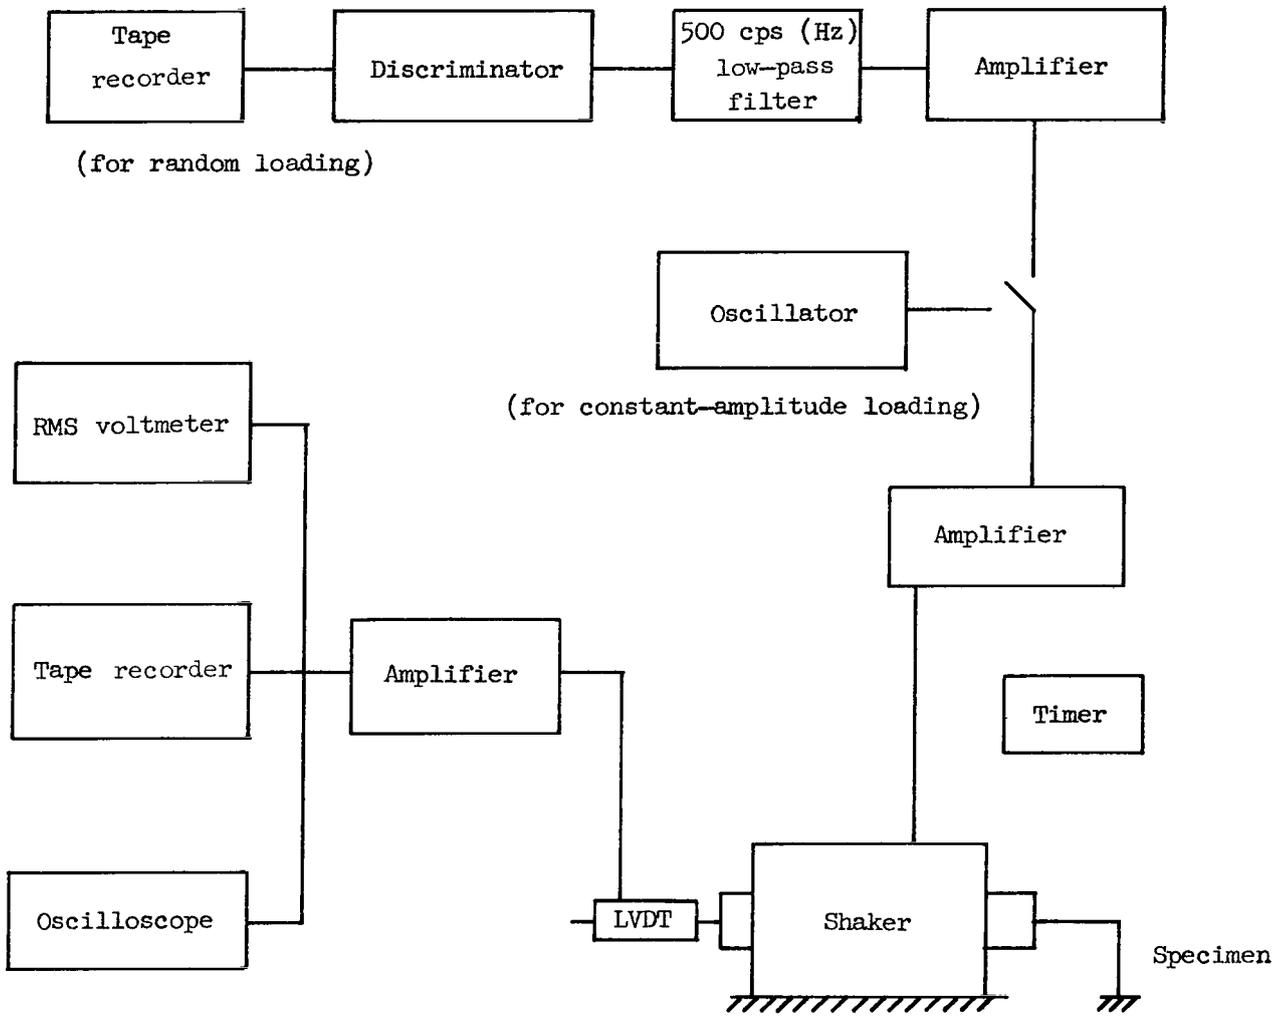


Figure 3.- Schematic of testing machines used in conducting fatigue tests.

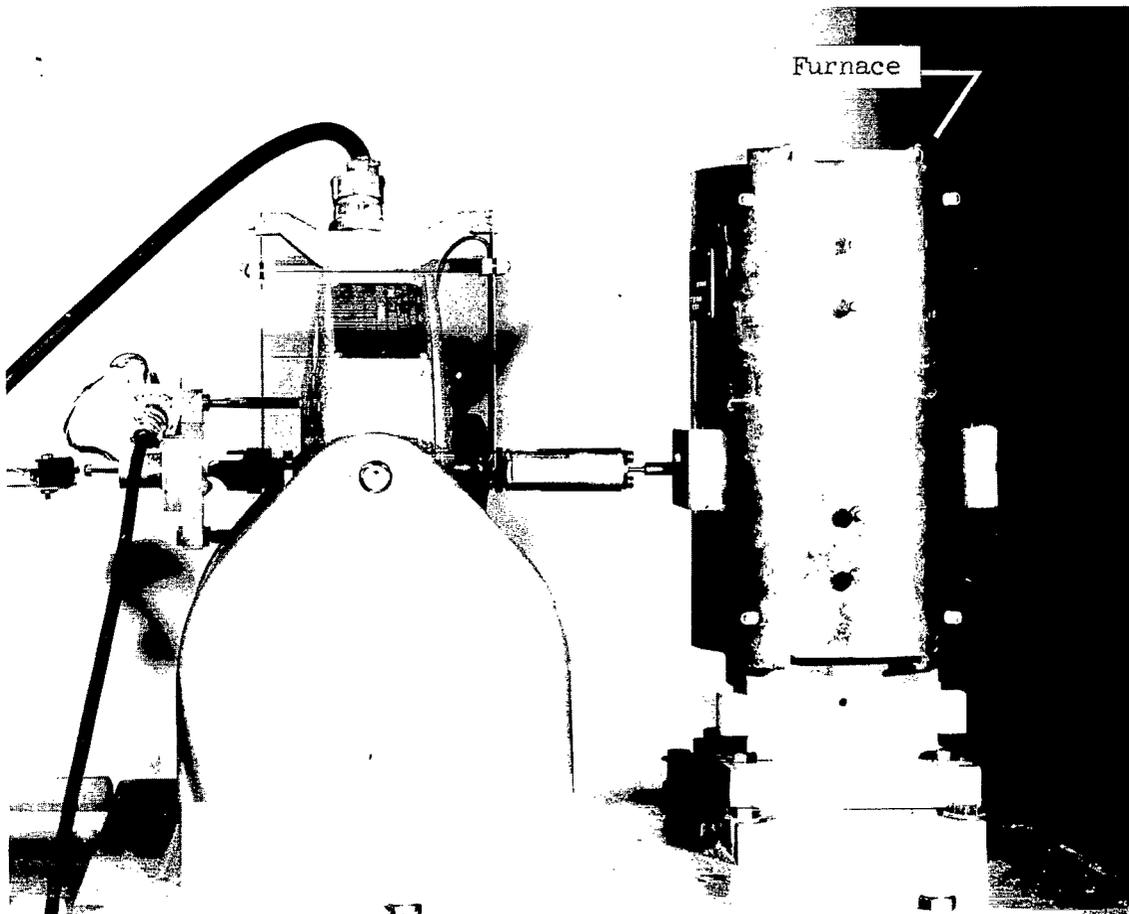


Figure 4.- Typical test setup for 700^o F (644^o K) fatigue test of René 41 specimen.

L-64-1003.1



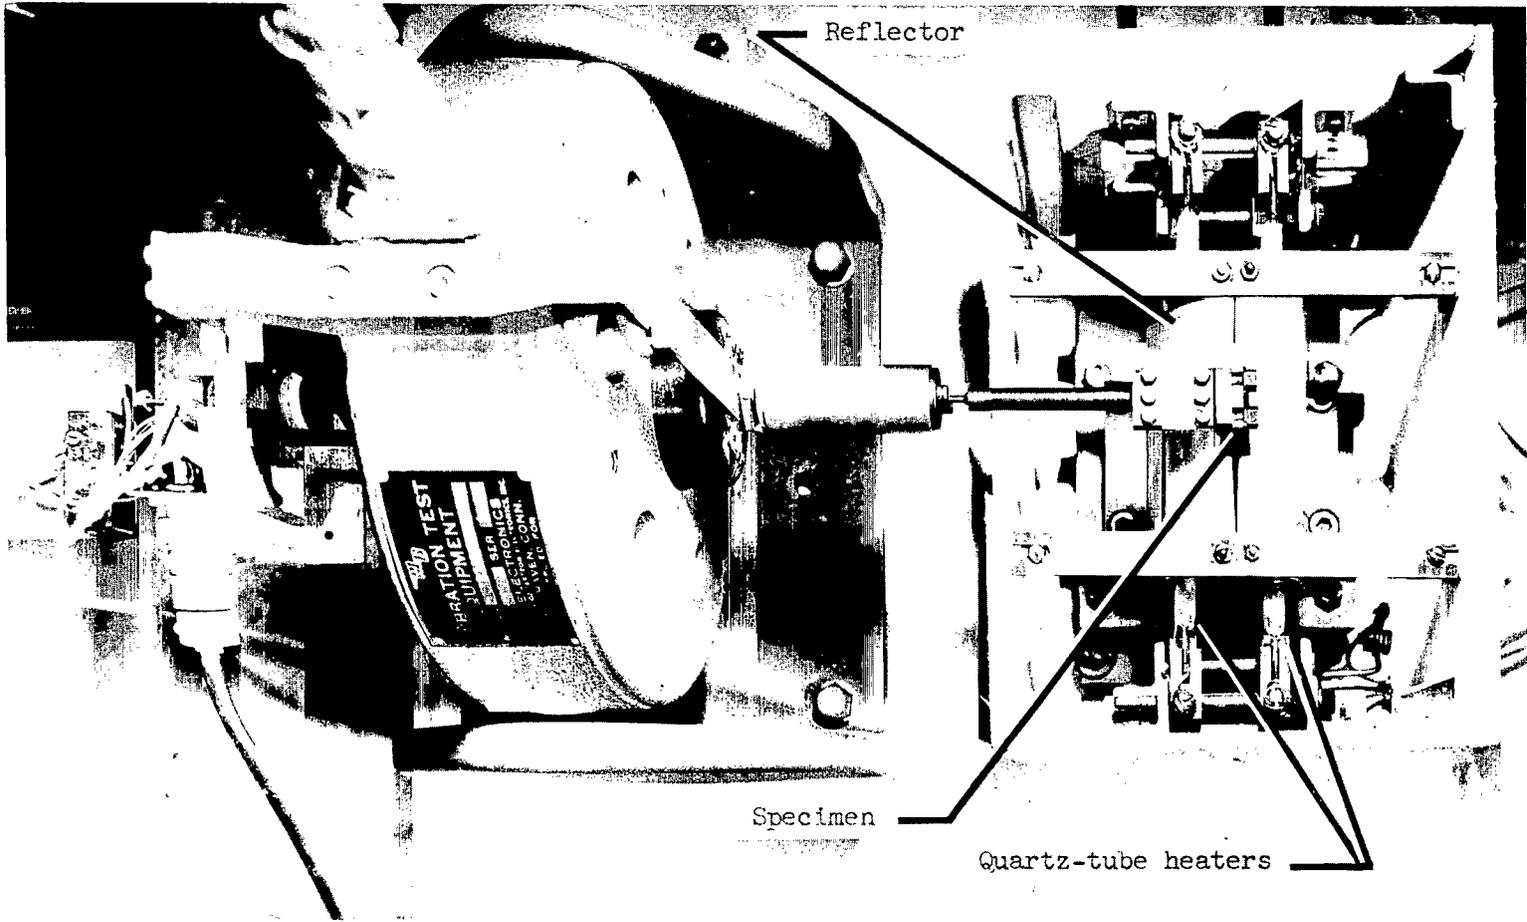


Figure 5.- Top view of typical test setup for 1400° F (1033° K) fatigue test of René 41 specimen.

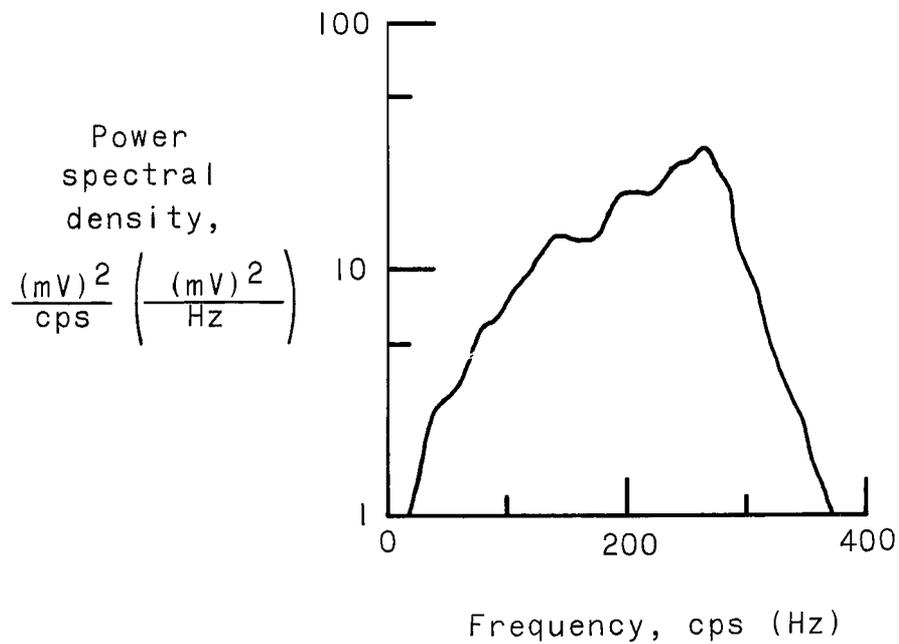


(a) Power spectrum of shaker input.

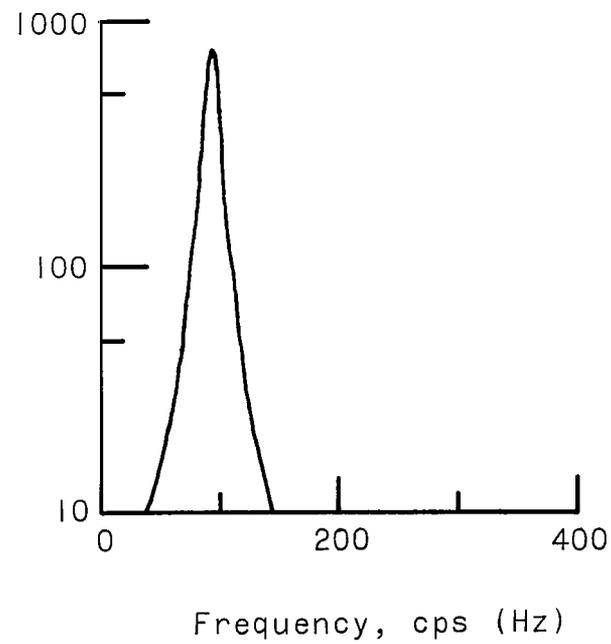

(b) Power spectrum of LVDT output.

Figure 6.- Characteristics of shaker input and LVDT output for typical random-loading test.

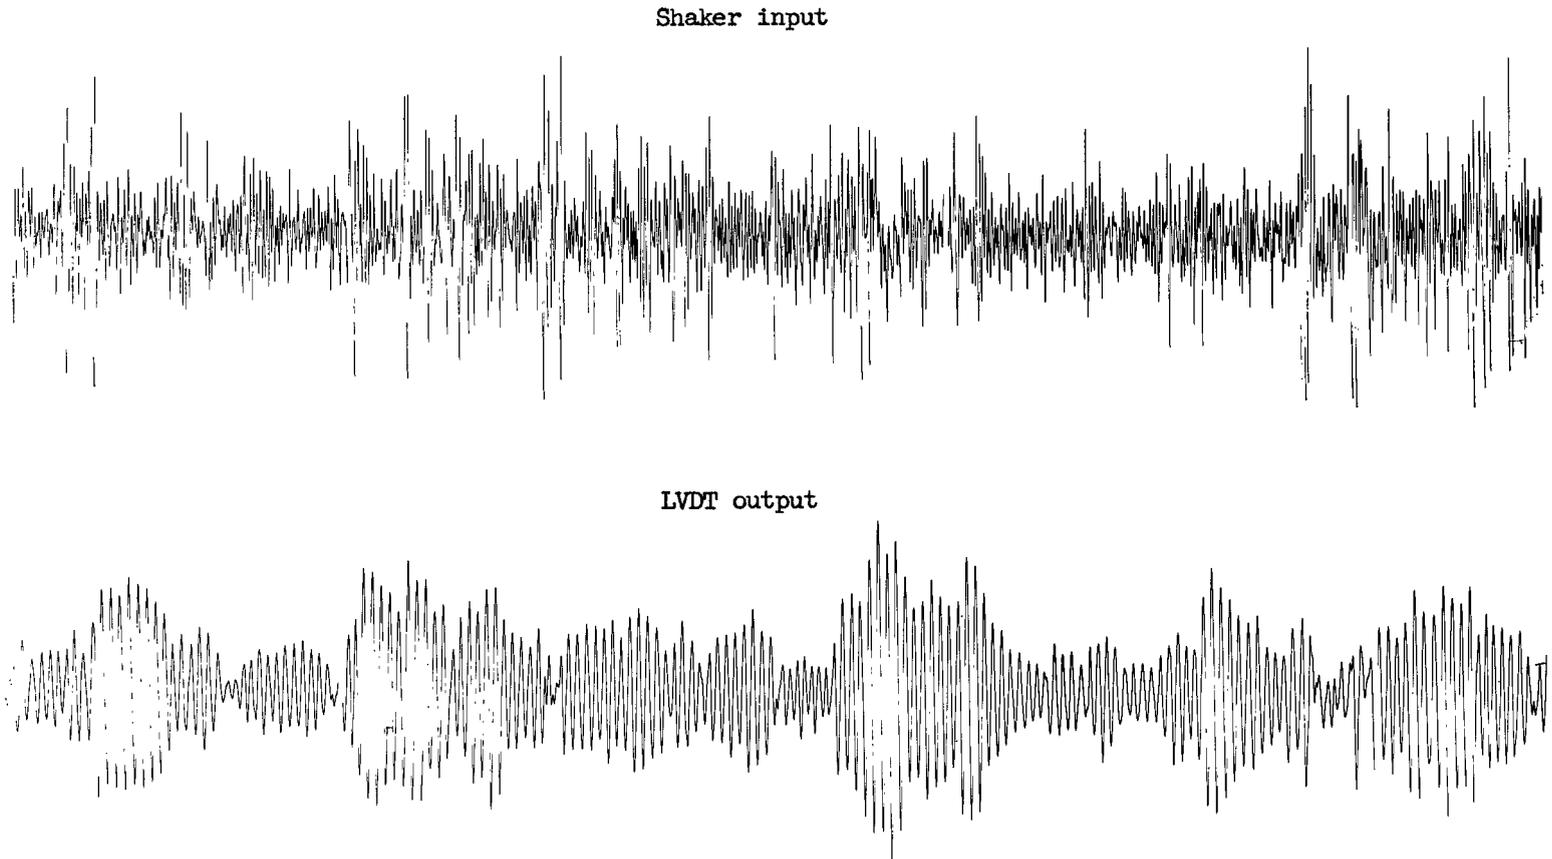

(c) Samples of time histories of shaker input and LVDT output.

Figure 6.- Concluded.

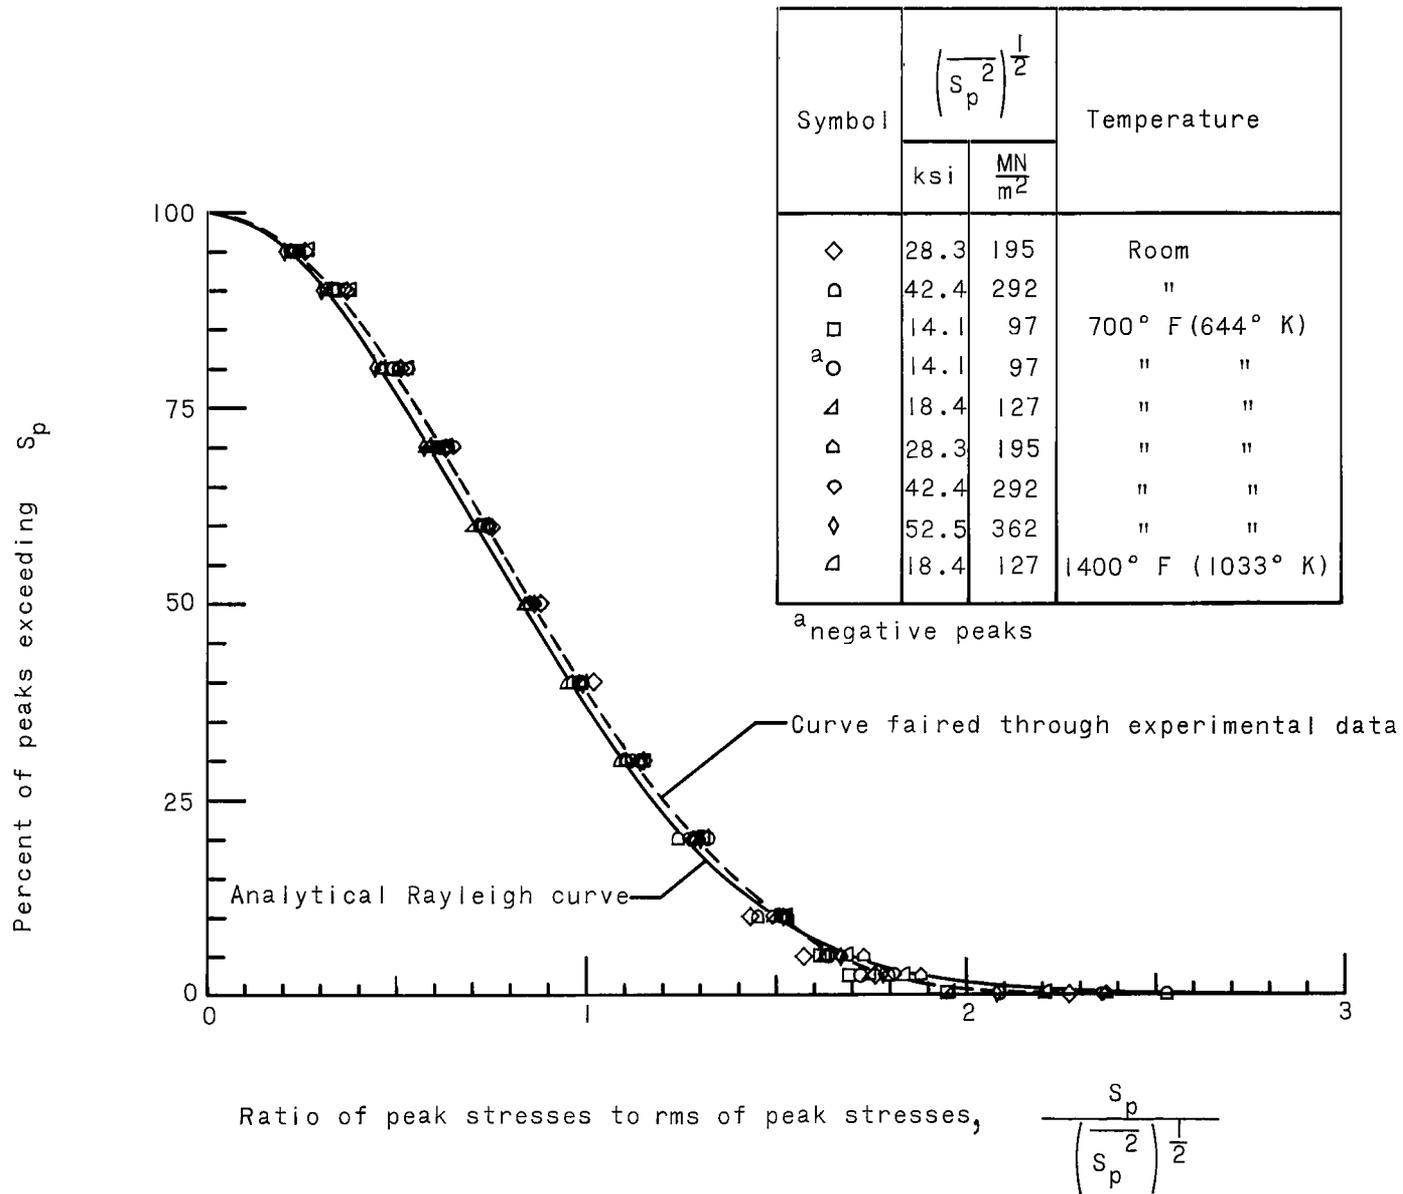


Figure 7.- Results of peak stress measurements for several random-loading tests on René 41 specimens at room and elevated temperatures.

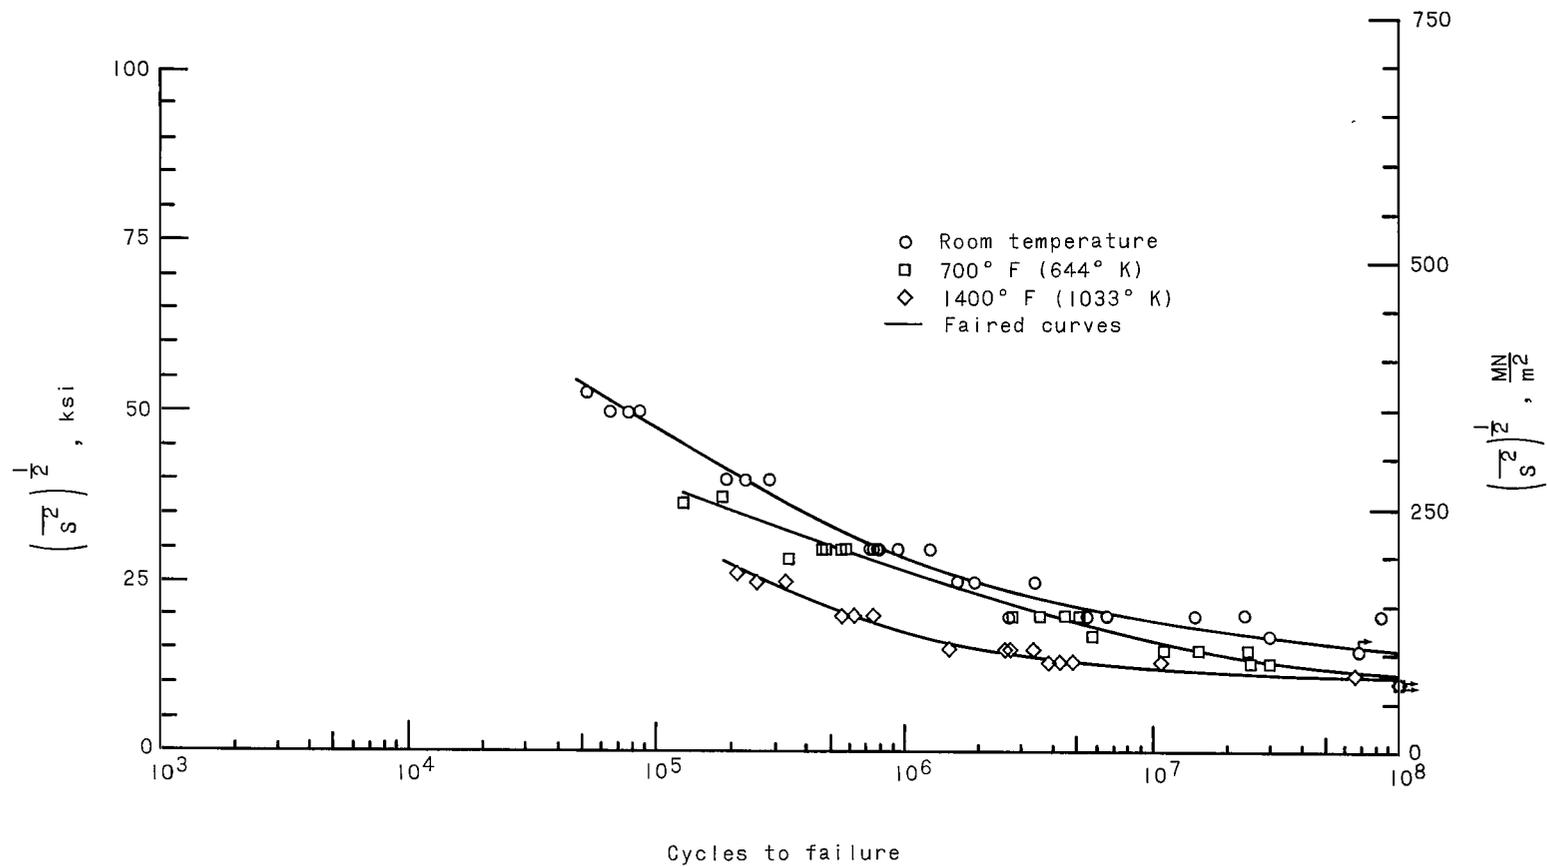


Figure 8.- Results of random-loading fatigue tests on René 41 specimens at room and elevated temperatures.

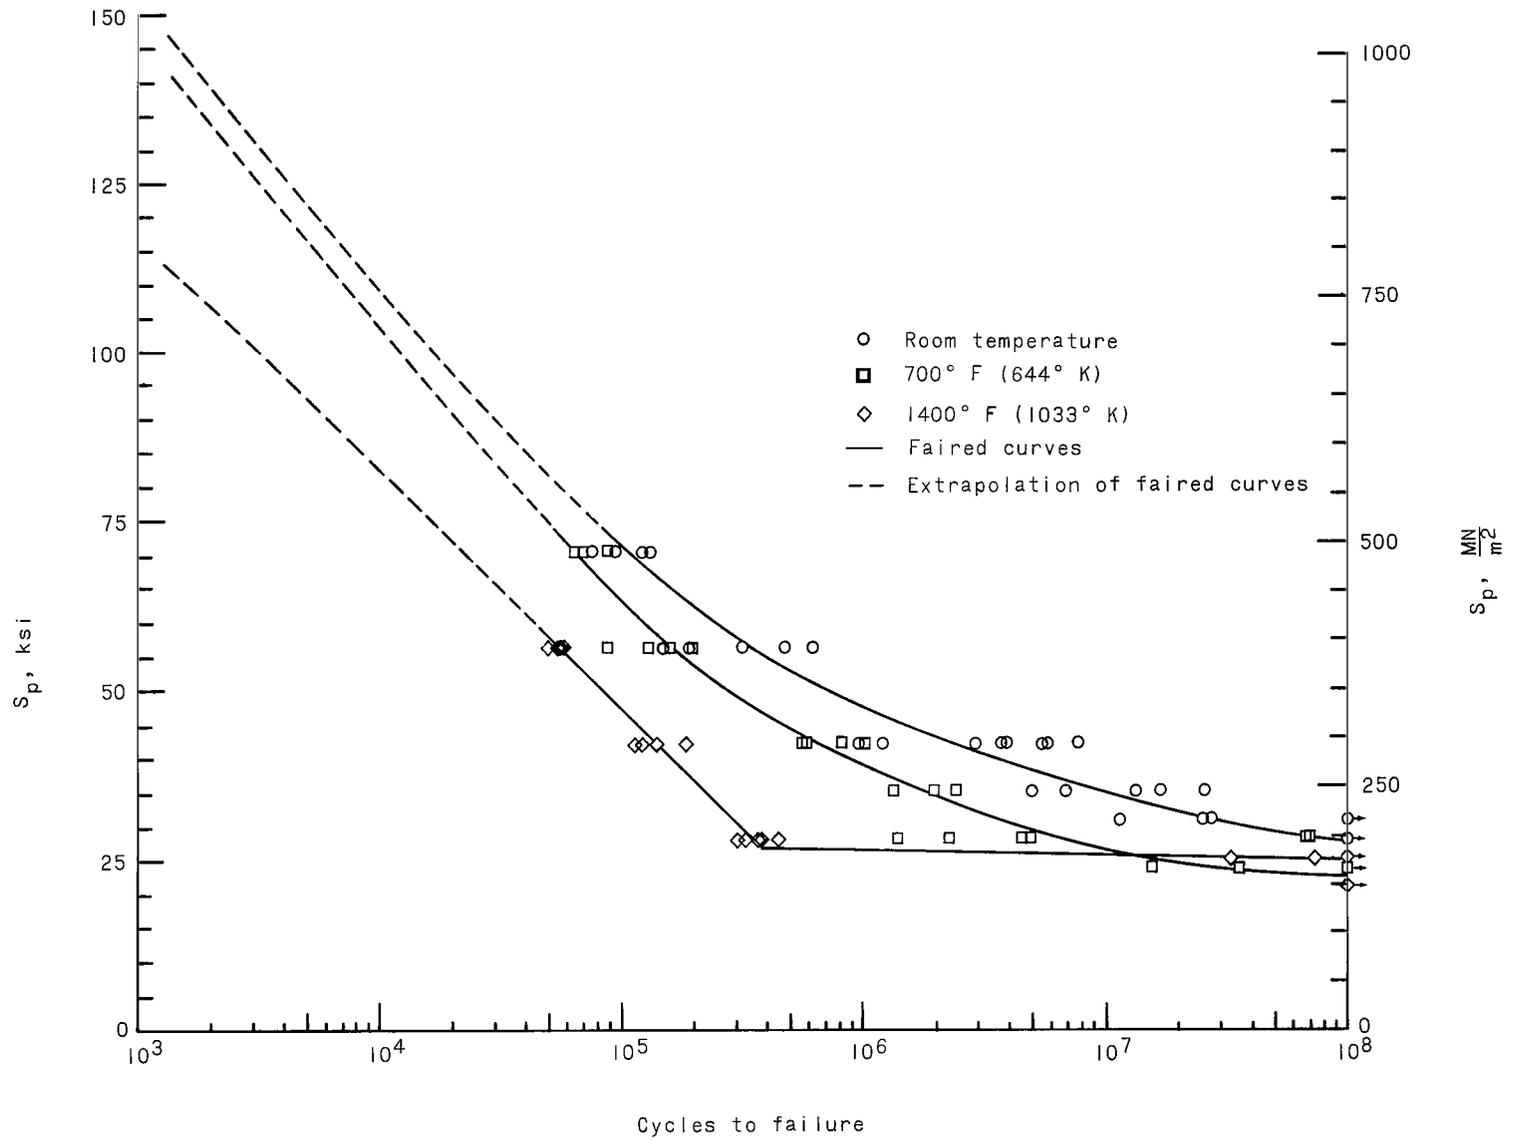


Figure 9.- Results of constant-amplitude fatigue tests on René 41 specimens at room and elevated temperatures.

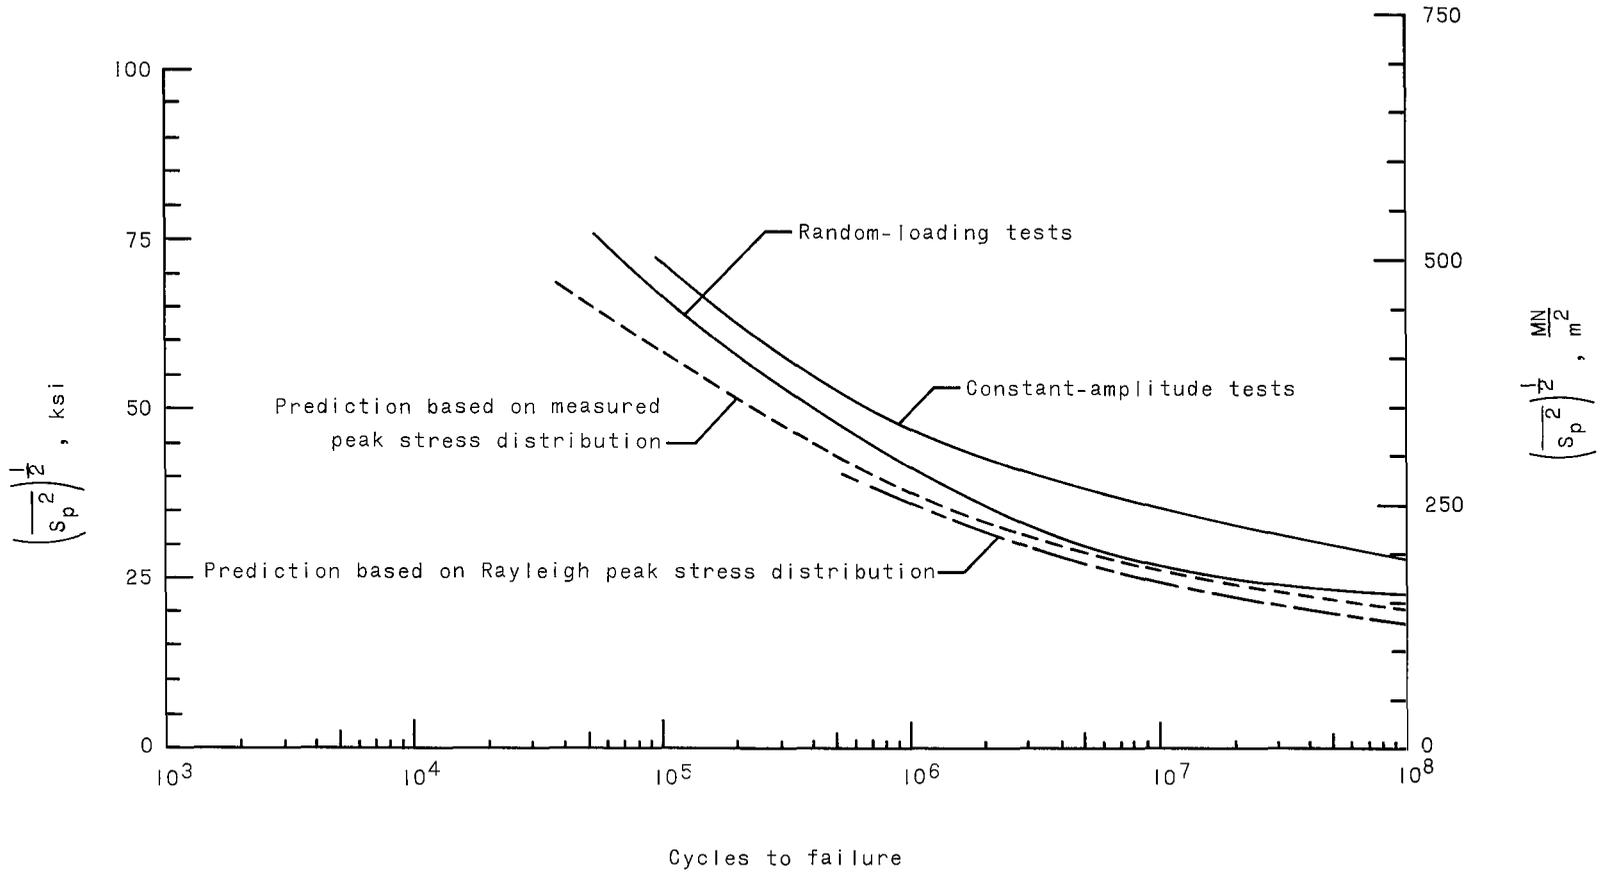


Figure 10.- Comparison of results of room-temperature random-loading tests, constant-amplitude tests, and theoretical predictions of random-loading tests.

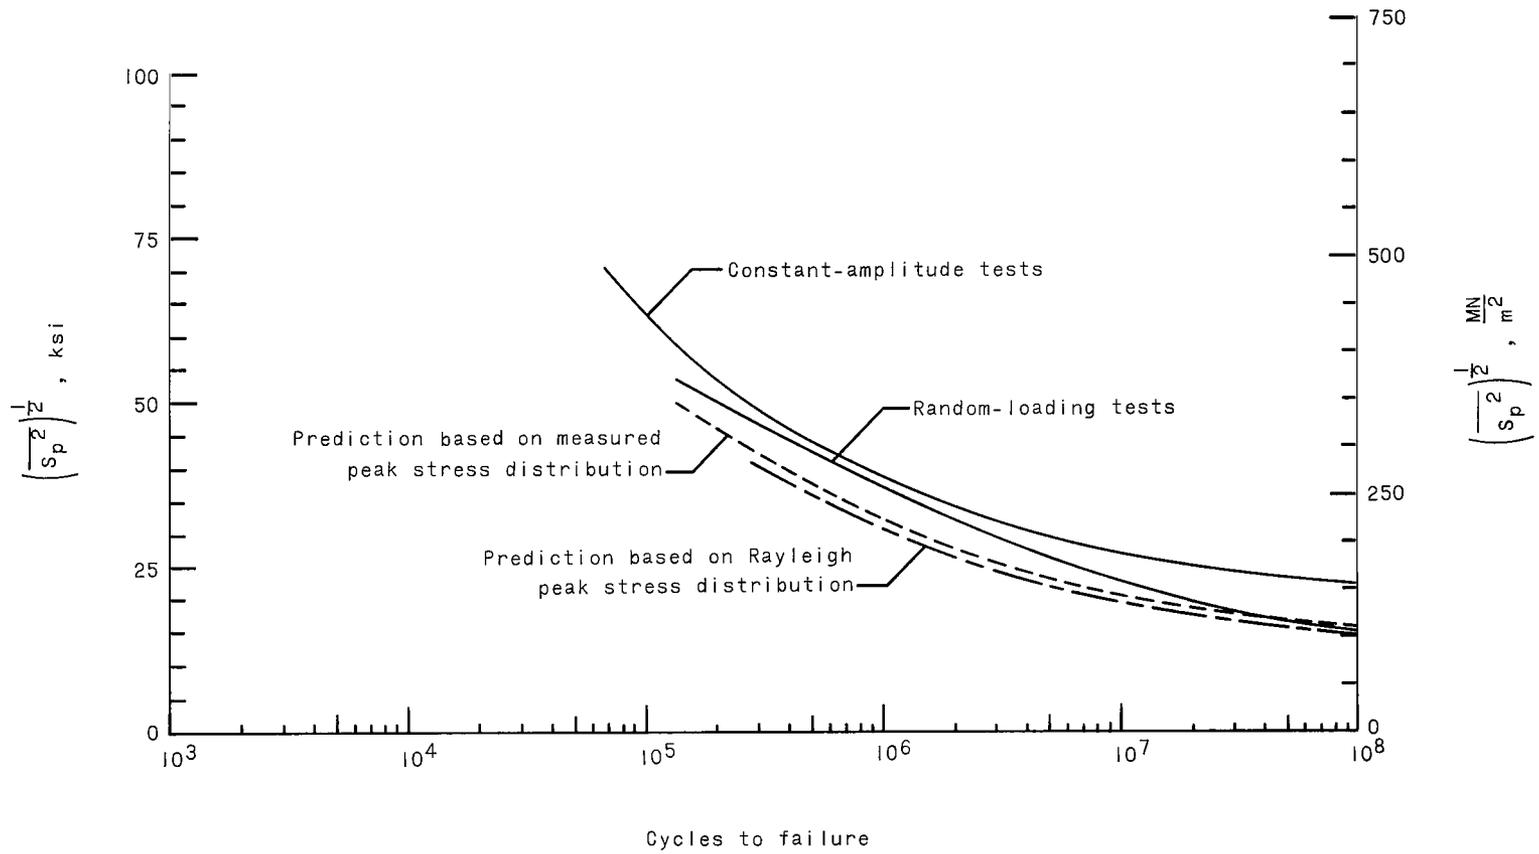


Figure 11.- Comparison of results of 700° F (644° K) random-loading tests, constant-amplitude tests, and theoretical predictions of random-loading tests.

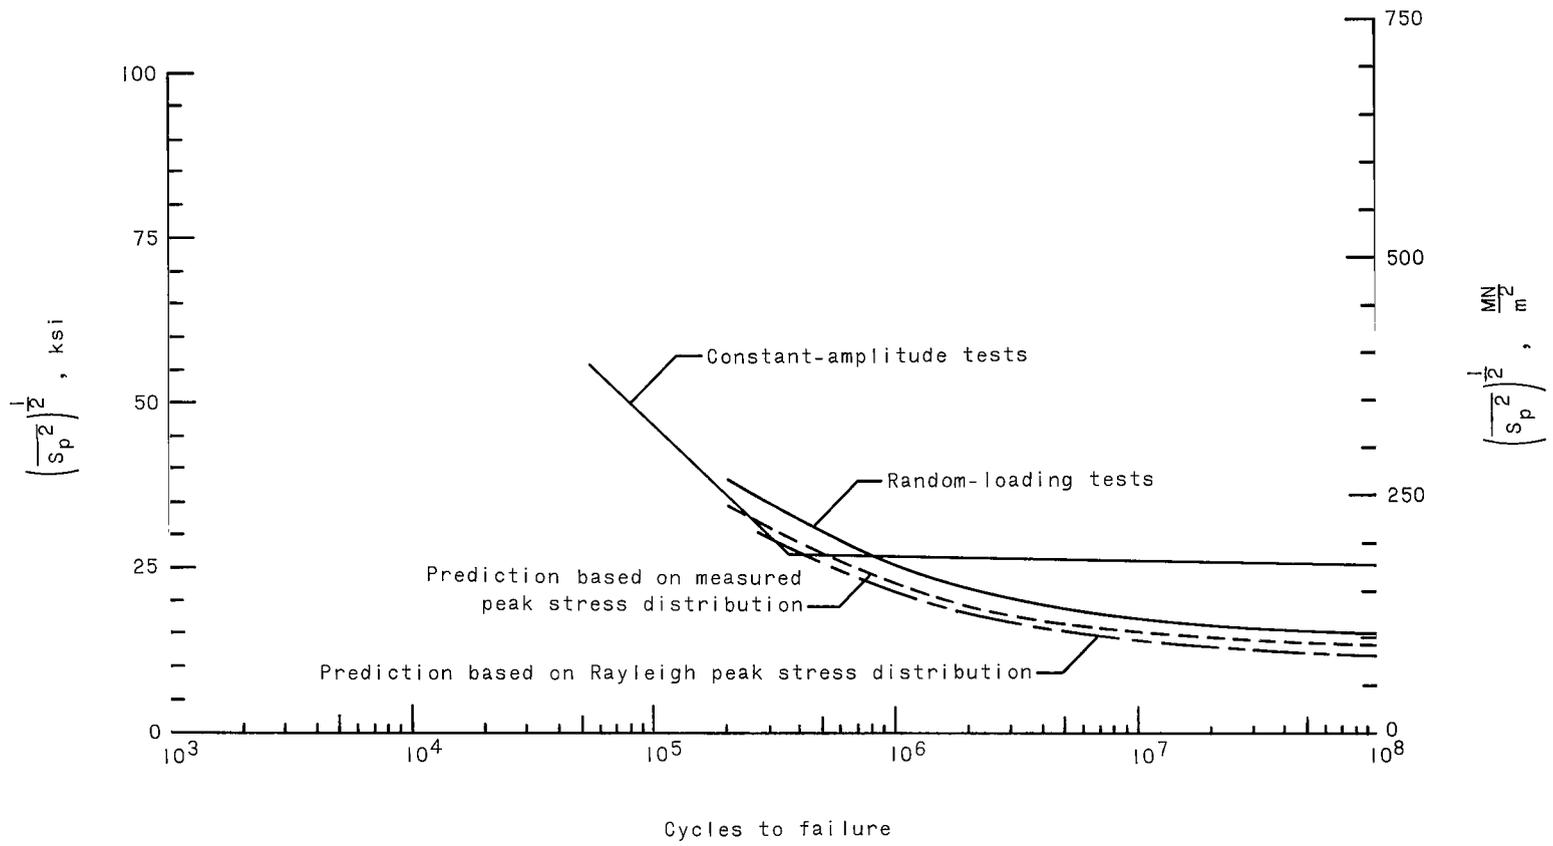


Figure 12.- Comparison of results of 1400° F (1033° K) random-loading tests, constant-amplitude tests, and theoretical predictions of random-loading tests.

3118/83
D

"The aeronautical and space activities of the United States shall be conducted so as to contribute . . . to the expansion of human knowledge of phenomena in the atmosphere and space. The Administration shall provide for the widest practicable and appropriate dissemination of information concerning its activities and the results thereof."

—NATIONAL AERONAUTICS AND SPACE ACT OF 1958

NASA SCIENTIFIC AND TECHNICAL PUBLICATIONS

TECHNICAL REPORTS: Scientific and technical information considered important, complete, and a lasting contribution to existing knowledge.

TECHNICAL NOTES: Information less broad in scope but nevertheless of importance as a contribution to existing knowledge.

TECHNICAL MEMORANDUMS: Information receiving limited distribution because of preliminary data, security classification, or other reasons.

CONTRACTOR REPORTS: Technical information generated in connection with a NASA contract or grant and released under NASA auspices.

TECHNICAL TRANSLATIONS: Information published in a foreign language considered to merit NASA distribution in English.

TECHNICAL REPRINTS: Information derived from NASA activities and initially published in the form of journal articles.

SPECIAL PUBLICATIONS: Information derived from or of value to NASA activities but not necessarily reporting the results of individual NASA-programmed scientific efforts. Publications include conference proceedings, monographs, data compilations, handbooks, sourcebooks, and special bibliographies.

Details on the availability of these publications may be obtained from:

SCIENTIFIC AND TECHNICAL INFORMATION DIVISION
NATIONAL AERONAUTICS AND SPACE ADMINISTRATION
Washington, D.C. 20546