


N71-36361

NASA TECHNICAL  
MEMORANDUM

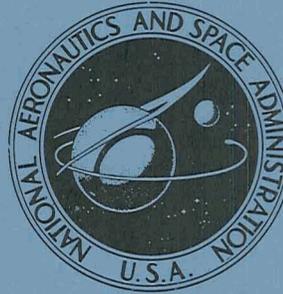

NASA TM X-2385

NASA TM X-2385

CASE FILE  
COPY

EFFECT OF PLASTIC SET  
ON THERMAL CONDUCTANCE  
AT LIGHT LOADING

*by Daniel J. McKinzie, Jr.*

*Lewis Research Center*

*Cleveland, Ohio 44135*

1. Report No. NASA TM X-2385	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle EFFECT OF PLASTIC SET ON THERMAL CONDUCTANCE AT LIGHT LOADING		5. Report Date September 1971	6. Performing Organization Code
		8. Performing Organization Report No. E-6402	10. Work Unit No. 124-09
7. Author(s) Daniel J. McKinzie, Jr.	9. Performing Organization Name and Address Lewis Research Center National Aeronautics and Space Administration Cleveland, Ohio 44135		11. Contract or Grant No.
12. Sponsoring Agency Name and Address National Aeronautics and Space Administration Washington, D. C. 20546			13. Type of Report and Period Covered Technical Memorandum
15. Supplementary Notes		14. Sponsoring Agency Code	
16. Abstract Smooth metal surfaces joined together (e. g. , by rivets, bolts, etc.) are commonly encountered in spacecraft. To predict the heat-transfer rates for high-vacuum conditions across such surfaces, the theories of A. M. Clausing and B. T. Chao and B. B. Mikic and W. M. Rohsenow are often used. Experimental data presented in this report indicate that the assumption of elastic deformation made in these theories is inadequate for accurate prediction of heat transfer with light loads.			
17. Key Words (Suggested by Author(s)) Heat transfer Thermodynamics		18. Distribution Statement Unclassified - unlimited	
19. Security Classif. (of this report) Unclassified	20. Security Classif. (of this page) Unclassified	21. No. of Pages 5	22. Price* \$3.00

\* For sale by the National Technical Information Service, Springfield, Virginia 22151

# EFFECT OF PLASTIC SET ON THERMAL CONDUCTANCE AT LIGHT LOADING

by Daniel J. McKinzie, Jr.

Lewis Research Center

## SUMMARY

Smooth metal surfaces joined together (e. g. , by rivets, bolts, etc.) are commonly encountered in spacecraft. To predict the heat-transfer rates for high-vacuum conditions across such surfaces, theories such as those of A. M. Clausing and B. T. Chao and B. B. Mikic and W. M. Rohsenow are often used. These theories assume that macroscopic elastic deformation occurs during the formation of such joints with an associated effect on the heat-transfer rates. Experimental data presented in this report indicate that this assumption is inadequate for accurate prediction of heat transfer with light loads.

## INTRODUCTION

The prediction of heat-transfer rates across smooth metal surfaces joined together by fasteners is required for spacecraft thermal design. The theories of references 1 and 2 are frequently used to predict the thermal balance across such surfaces under high-vacuum conditions and light loads. These theories assume that macroscopic elastic deformation occurs during the formation of such joints with an associated effect on the heat-transfer rates. Experimental data obtained from two Armco iron cylindrical specimens are presented in this report which provide new physical insight into the thermal contact conductance phenomenon at vacuum conditions of  $1.2 \times 10^{-7}$  torr and contact pressures which range from  $0.45 \times 10^6$  to  $3.44 \times 10^6$  newtons per square meter.

## EXPERIMENTAL PROCEDURE

The contact surfaces of the two specimens investigated had arithmetic average roughness heights ranging from 0.01 to 0.1 micrometer. Both were 2.54-centimeter-diameter Armco iron cylinders, the ends of which were placed in contact. The

contacting surfaces were analyzed with a stylus type of surface analyzer before the tests were conducted and were found to approximate convex spherical segments. The tests were conducted in the facility described in reference 3.

After the outgassed surfaces of a specimen were placed in contact at a loading pressure of  $4.48 \times 10^5$  newtons per square meter, the interface temperature was raised to approximately 367 K. The contact pressure was then varied through two monotonically increasing then decreasing loading cycles while a constant interface temperature was maintained. At each test point, a minimum of 50 hours of data were taken to assure that steady-state conditions were achieved. Both specimens were instrumented as described in reference 3.

## RESULTS AND DISCUSSION

Figure 1 shows the cyclic thermal contact conductance as a function of apparent contact pressure for specimen 1. The specimen was loaded through two cycles. The mean interface temperature of the specimen was kept at 369 K with one exception noted at the end of the first loading, where it was raised at constant pressure ( $350 \text{ N/m}^2$ ) to 477 K. It remained at this temperature for 50 hours. While still at this pressure, the interface temperature was then lowered to 369 K and the pressure cycling was continued. The data obtained for the first loading followed the generally recognized trend exhibited when macroscopic elastic deformation of contacting surfaces takes place. However, a comparison with the theoretical predictions from references 1 and 2 has shown the data obtained here to be low by several factors. All data following the first loading fell reproducibly very nearly on a curve having a slope of approximately 1, which is characteristic for a specimen as moderate loading pressures are reached (ref. 4). For the smallest apparent contact pressures these thermal conductance coefficients were consistently lower than those obtained initially. Therefore, it may be surmised that the specimen took a permanent set after the initial loading.

The results from the second specimen, under almost identical experimental conditions, are shown in figure 2. This specimen, however, was not exposed to a temperature excursion. In this case, all the data appear to follow the accepted trend for elastic deformation. However, closer examination of the data obtained at the lowest loading pressures shows a consistent and reproducible decrease in the conductance, perhaps indicating an increasing permanent set.

The contacting surfaces were reexamined with a surface analyzer after each test was completed. Table I presents the surface half-wave height  $d$  of each specimen obtained before and after the tests. The half-wave height of the top of specimen 1 increased by 3.35 micrometers and that of the bottom by 2.10 micrometers. The top of

specimen 2 increased by 1.49 micrometers and that of the bottom by 1.22 micrometers. Thus, both specimens deformed plastically with the attendant changes in the coefficient of thermal contact conductance noted in the experimental data. The interface temperature excursion apparently caused specimen 1 to deform more than did specimen 2.

Changes in the half-wave surface heights of specimens during tests may explain why the experimental data of references 1 and 5, to mention two, were not in good agreement with such macrostructural elastic deformation theories as those of references 1 and 2. If macrostructural plastic deformation occurs during a test, a basic assumption of these theories is violated, and disagreement between experiment and theory is to be expected.

Lewis Research Center,  
National Aeronautics and Space Administration,  
Cleveland, Ohio, July 8, 1971,  
124-09.

## REFERENCES

1. Clausing, A. M.; and Chao, B. T.: Thermal Contact Resistance in a Vacuum Environment. Rep. ME - TN 242-1, Univ. Ill. Eng. Experiment Station, 1963.
2. Mikic, B. B.; and Rohsenow, W. M.: Thermal Contact Resistance. Rep. 74542-4-1 Sept. 1966, Massachusetts Inst. Tech. (NASA CR-78319), Sept. 1966.
3. McKinzie, Daniel J., Jr.: Experimental Confirmation of Cyclic Thermal Joint Conductance. Paper 70-853, AIAA, June 1970.
4. Yovanovich, M. Michael: Thermal Contact Conductance of Nominally Flat, Rough Surfaces in a Vacuum Environment. Thermophysics and Temperature Control of Spacecraft and Entry Vehicles. Vol. 18 of Progress in Astronautics and Aeronautics. G. B. Heller, ed.; Academic Press, 1966, pp. 773-794.
5. Fletcher, L. S.; and Gyrogo, D. A.: Prediction of Thermal Contact Conductance Between Similar Metal Surfaces. Paper 70-852, AIAA, June 1970.

TABLE I. - HALF-WAVE SURFACE HEIGHT  
FOR ARMCO IRON SPECIMENS

Specimen	Specimen surface	Half-wave surface height, $d$ , $\mu\text{m}$	
		Before test	After test
1	Top	0.46	3.81
	Bottom	0.53	2.63
2	Top	1.33	2.82
	Bottom	0.51	1.73

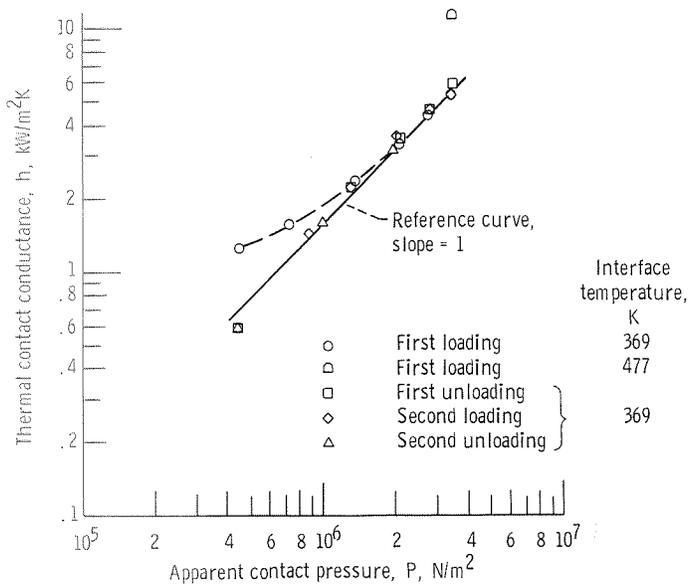


Figure 1. - Thermal contact conductance as function of pressure for Armco iron specimen 1. Arithmetic average roughness height of surface; top, 0.02 micrometer; bottom, 0.014 micrometer.

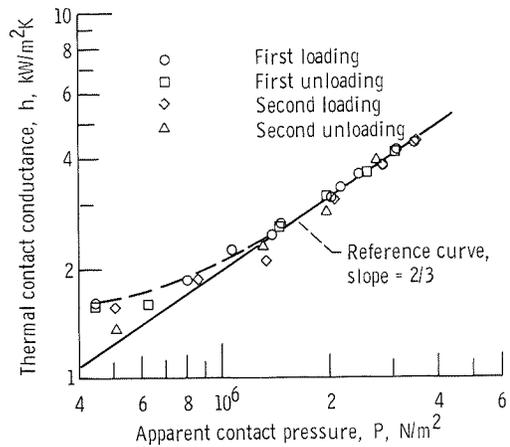


Figure 2. - Thermal contact conductance as function of pressure for Armco iron specimen 2. Interface temperature, 367 K; arithmetic average roughness height of surface; top, 0.038 micrometer; bottom, 0.102 micrometer.

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION  
WASHINGTON, D.C. 20546

OFFICIAL BUSINESS  
PENALTY FOR PRIVATE USE \$300

FIRST CLASS MAIL

POSTAGE AND FEES PAID  
NATIONAL AERONAUTICS AND  
SPACE ADMINISTRATION



POSTMASTER: If Undeliverable (Section 158  
Postal Manual) Do Not Return

*"The aeronautical and space activities of the United States shall be conducted so as to contribute . . . to the expansion of human knowledge of phenomena in the atmosphere and space. The Administration shall provide for the widest practicable and appropriate dissemination of information concerning its activities and the results thereof."*

— NATIONAL AERONAUTICS AND SPACE ACT OF 1958

## NASA SCIENTIFIC AND TECHNICAL PUBLICATIONS

**TECHNICAL REPORTS:** Scientific and technical information considered important, complete, and a lasting contribution to existing knowledge.

**TECHNICAL NOTES:** Information less broad in scope but nevertheless of importance as a contribution to existing knowledge.

**TECHNICAL MEMORANDUMS:** Information receiving limited distribution because of preliminary data, security classification, or other reasons.

**CONTRACTOR REPORTS:** Scientific and technical information generated under a NASA contract or grant and considered an important contribution to existing knowledge.

**TECHNICAL TRANSLATIONS:** Information published in a foreign language considered to merit NASA distribution in English.

**SPECIAL PUBLICATIONS:** Information derived from or of value to NASA activities. Publications include conference proceedings, monographs, data compilations, handbooks, sourcebooks, and special bibliographies.

**TECHNOLOGY UTILIZATION PUBLICATIONS:** Information on technology used by NASA that may be of particular interest in commercial and other non-aerospace applications. Publications include Tech Briefs, Technology Utilization Reports and Technology Surveys.

*Details on the availability of these publications may be obtained from:*

**SCIENTIFIC AND TECHNICAL INFORMATION OFFICE**

**NATIONAL AERONAUTICS AND SPACE ADMINISTRATION**

Washington, D.C. 20546