


NASA CR-134610  
SRD-74-034



STUDY, SELECTION, AND PREPARATION OF  
SOLID CATIONIC CONDUCTORS

by

W. L. Roth and O. Muller

GENERAL ELECTRIC COMPANY

prepared for

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION

NASA Lewis Research Center  
Contract NAS 3-17339

1. Report No. NASA CR-134610	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle STUDY, SELECTION, AND PREPARATION OF SOLID CATIONIC CONDUCTORS		5. Report Date April 1974	
		6. Performing Organization Code	
7. Author(s) W. L. Roth and O. Muller		8. Performing Organization Report No. SRD-74-034	
		10. Work Unit No.	
9. Performing Organization Name and Address General Electric Company P. O. Box 8 Schenectady, New York 12301		11. Contract or Grant No. NAS3-17339	
		13. Type of Report and Period Covered Final Report 11/13/72 - 11/12/73	
12. Sponsoring Agency Name and Address National Aeronautics and Space Administration Washington, D. C. 20546		14. Sponsoring Agency Code	
		15. Supplementary Notes Project Managers: J. B. Bush, General Electric Corporate Research and Development, P. O. Box 8, Schenectady, N. Y. 12301; Albert C. Antoine, Energy Conversion and Material Science Division, NASA Lewis Research Center, Cleveland, Ohio	
16. Abstract Crystal chemical principles and transport theory have been used to predict structures and specific compounds which might find application as solid electrolytes in rechargeable high energy and high power density batteries operating at temperatures less than 200°C. Structures with 1-, 2-, and 3-dimensional channels were synthesized and screened by nuclear magnetic resonance, dielectric loss, and conductivity. There is significant conductivity at room temperature in some of the materials but none attain a level that is comparable to beta-alumina. Microwave and fast pulse methods were developed to measure conductivity in powders and in small crystals.			
17. Key Words (Suggested by Author(s)) Ionic conductors Solid electrolytes Batteries Nuclear Magnetic Resonance Transport numbers		18. Distribution Statement  Unclassified, Unlimited	
19. Security Classif. (of this report) Unclassified	20. Security Classif. (of this page) Unclassified	21. No. of Pages 69	22. Price*

\* For sale by the National Technical Information Service, Springfield, Virginia 22151

## TABLE OF CONTENTS

	<u>Page</u>
I. SUMMARY - - - - -	1
II. INTRODUCTION - - - - -	2
A. Background - - - - -	2
B. Technical Approach and Experimental Methods - - - - -	3
1. Structure Selection - - - - -	3
2. Synthesis and Fabrication of Materials - - - - -	5
3. NMR Screening - - - - -	6
4. Conductivity and Transport Measurements - - - - -	6
a. Two-phase measurement of conductivity - - - - -	6
b. Microwave measurement of conductivity of powders - -	7
c. Conductivity, transport, and pulse measurements on micro-specimen - - - - -	9
III. VALIDATING EXPERIMENTS - - - - -	14
A. Bridge Measurements - - - - -	14
B. Applications of Pulse Technique to Beta-Alumina - - - - -	14
IV. RESULTS AND DISCUSSION OF RESULTS - - - - -	17
A. $\text{LiNb}_6\text{O}_{15}\text{F}$ -Type Compounds - - - - -	17
B. Hollandite-Type Compounds - - - - -	22
C. Cordierite-Type Compounds - - - - -	27
D. $\text{NaNbO}_2\text{F}_2$ -Type Compounds - - - - -	31
E. Phases with a Defect Perovskite Structure - - - - -	35
F. Sodium Tungsten Bronze-Type Compounds - - - - -	40
G. $\text{NaLiGe}_4\text{O}_9$ -Type Compounds - - - - -	41
H. $\text{Li}_2\text{Ge}_7\text{O}_{15}$ -Type Compounds - - - - -	46
I. Hexagonal $\text{NaLnF}_4$ -Type Compounds - - - - -	54
J. Dalyite-Type Compounds - - - - -	60
V. CONCLUSIONS AND RECOMMENDATIONS - - - - -	63
A. Conclusions - - - - -	65
B. Recommendations - - - - -	65
VI. REFERENCES - - - - -	67

# STUDY, SELECTION, AND PREPARATION OF SOLID CATIONIC CONDUCTORS

W. L. Roth and O. Muller

## I. SUMMARY

A proposal entitled "Study, Selection, and Preparation of Solid Cationic Conductors" was submitted to NASA in May 1971, in response to RFP No. 416187. It described a research program aimed at the identification and preparation of materials for use as nonporous solid ionic conductors in rechargeable high-energy and power density batteries operating at temperatures less than 200°C. The only materials capable of meeting the required objectives that are now identified are members of the beta-alumina family. A preliminary search for such solid electrolytes was carried out between July 1971 and June 1972 under NASA Contract NAS3-15692. The work was summarized in Report No. CR-120964, dated September 1972. More than twenty compounds were screened, and encouraging results were obtained for nine materials. None were proved to be good ionic conductors at low temperature, in large part because dense single-phase ceramics were not available for measurement of ion transport and conductivity.

This report summarizes a continuation of the search which was carried out between December 1972 and November 1973 under NASA Contract NAS3-17339. The structural criteria for predicting materials with high ion mobility at ambient temperature had been validated in the first phase of the study. These criteria were used to predict new candidates with particular emphasis on materials which could be fabricated in practical systems. The major modification in the technical approach was in the area of evaluation of materials. Two new techniques for measuring ionic conductivity and transport were developed and validated. By use of these methods it now is possible to evaluate candidate materials in the form of powders, small crystals, or fragments of ceramics or glasses. More than twenty-eight materials distributed among eight structure types were synthesized and evaluated. At least nine of these had conductivities of order  $10^{-6}$  ohm<sup>-1</sup> cm<sup>-1</sup> at room temperature, but additional work would be required to establish the level of ion transport.

The principal conclusions of the study are as follows:

1. Satisfactory crystal chemical and measurement tools for the prediction and the evaluation of solid ionic conductors have been developed and validated,

2. It is unlikely that the required high levels of ion transport can be sustained in one-dimensional tunnel structures, and

3. There are reasonable prospects for developing high ionic conductivity at moderate temperature in three- and two-dimensional interconnected channel structures. Specific recommendations are made for future work on a broad family of compounds which appear to satisfy the principal requirements for use in a low-temperature, high-energy and power density battery.

## II. INTRODUCTION

### A. Background

The objective of this research program is the identification and preparation of materials for use as nonporous solid ionic conductors in rechargeable high-energy and power density battery systems operating at temperatures less than 200°C. The primary requirements for the electrolyte are that:

1. The ionic conductivity at operating temperature must be sufficiently high to allow high power density. In practice this means the conductivity should be at least  $10^{-3} \text{ ohm}^{-1} \text{ cm}^{-1}$  at 200°C.
2. The cation transport number should be unity, i. e., the current carried by anions and electrons must be negligible.
3. The electrolyte must conduct ions of reactants with high oxidizing and reducing power to achieve high-power density. This requirement eliminates silver conductors and focuses attention on cations in the first and second columns of the periodic table.
4. It must be chemically stable with respect to the cell reactants and products.
5. It must be possible to fabricate the material into thin separators which are mechanically rigid and of low porosity to prevent mixing of the cell reactants.

The only solids known to satisfy these requirements are the beta-alumina sodium ion conductors.

The work to be described in this report is a continuation of a one-year program carried out under National Aeronautics and Space Administration Contract NAS3-15692<sup>(2)</sup> with the objective to conceive, synthesize, and characterize new solid ionic conductors. In that program a large number of materials were selected on the basis of thermodynamic and crystal-chemical criteria and were subjected to preliminary synthesis and evaluation of their potential as solid ionic conductors. A novel technique, nuclear magnetic resonance (NMR), was employed for the preliminary evaluation. This technique permits the rapid screening of loose powders, thus eliminating the need for the time-consuming preparation of dense, sintered compacts of a large number of materials. Among the materials subjected to NMR analysis, many showed encouraging evidence for ionic motion. These materials are  $\text{Li}_3\text{AlN}_2$ ,  $\text{Li}_3\text{BN}_2$ ,  $\text{Li}_x\text{Ta}_2\text{O}_5$ ,  $\text{Li}_x\text{V}_2\text{O}_5$ ,  $\text{NaPrF}_4$ ,  $\text{NaYbF}_4$ ,  $\text{LiNb}_6\text{O}_{15}\text{F}$ , and  $\text{LiNO}_3 \cdot \text{Z}$

which is  $\text{LiNO}_3$  occluded in the pores of zeolite 4A. Dense samples of the vanadates and tantalates were prepared and ionic conductivity measurements were carried out. The vanadates were shown to be partially ionic and partially electronic conductors with the level of electronic conductivity strongly dependent on the stoichiometry.

## B. Technical Approach and Experimental Methods

The search for new low-temperature cation conductors consists of several interrelated tasks. These are: the application of crystal chemical criteria to predict the structures of materials in which high cation mobility at low temperature is theoretically possible, the synthesis and fabrication of selected candidates, and the characterization of conductivity and transport in synthesized candidates. Several conclusions that were reached as a result of the work under Contract NAS3-15692 led to refinements and modifications in the technical approach followed for the work under this contract. One was a decision to reduce the time-consuming work which is required to fabricate dense ceramics until there is evidence the material is a good conductor of ions. A second was to prepare candidates as pure single-phase specimens in order to avoid the ambiguities inherent in the interpretation of conductivity and transport measurements on impure materials. A third was to find methods to measure conductivity and transport in powders or in small crystals.

### 1. Structure Selection

The basis of the structural approach<sup>(2a)</sup> is to concentrate the search on Type II and Type III ionic conductors since it is unlikely that Type I conductors can sustain the level of conductivity required for high energy density batteries. Type I conductors are solids in which the concentration of defects is small, generally less than  $10^{19} \text{ cm}^{-3}$ ; Type II are highly nonstoichiometric compounds which usually have a broad solid solution composition range; and Type III are compounds which have structures with many vacant sites of equal or nearly equal energy which mobile cations can occupy. This approach was well validated in the first year's program since many of the solids which satisfied these structural requirements gave evidence for some ion mobility at ambient temperature.

As a result of the first year's work it was possible this year to make the structural criteria more restrictive. Nonstoichiometric compounds frequently contain ions in more than one valence state. A typical example are the lithium vanadates which were studied in the first year's program. Multiple valence states resulted in considerable electronic conduction which made it difficult to assess the amount of charge transported by ions. In the materials prepared for this study the electronic conduction was reduced by incorporating charge compensating ions without destroying the desired structure. Last year, several open framework, low density compounds were studied which were relatively stoichiometric and contained only a small concentration of defects. Such solids were tested with the hope that they would exhibit some

motional narrowing of the NMR spectrum, thus indicating ionic motion, and that the level of mobility could later be enhanced by substituting foreign ions which would introduce the necessary defects. Examples for such compounds are  $\text{NaBO}_2$  and  $\text{Na}_2\text{BeF}_4$ . However, since none of these compounds gave evidence for potential ion motion, screening this time was limited to compounds which were known to contain defects.

In selecting structures for a more detailed study, use was made of three sources.

(1) The list of structures for which a preliminary study had already been made in the first year of the contract. Here the objective was to pick the most promising candidates of the previous year -- those which had successfully passed preliminary NMR screening -- and to synthesize them in a purer and/or nonstoichiometric form.

(2) A large list of promising structures that had been compiled some years ago. From this list a small number had been selected for study during the first year of the contract. Some structures from the larger original list were reconsidered during this contract period, even though they had been passed over during the first year.

(3) New promising structures obtained from a search of the recent literature.

In selecting a final group of candidates from these lists, the following crystal-chemical criteria have been applied:

(1) The candidate structures must have either (a) one-dimensional tunnels, (b) two-dimensional sheets of interconnected tunnels, or (c) a three-dimensional framework of interconnected channels. Such channels should be wide enough to allow for the motion of monovalent ions such as  $\text{Li}^{1+}$ ,  $\text{Na}^{1+}$ , or  $\text{K}^{1+}$ .

(2) If a one-, two- or three-dimensional path of ionic motion is available in a particular structure, a search was made for other clues which might indicate "looseness" of the monovalent ion, or empty sites in the structure toward which an ion could migrate. Such clues include:

(a) Abnormally large cation-anion distances for the migrating cation.

(b) Abnormally large x-ray temperature factors, meaning larger than normal thermal vibrations for the diffusing cations.

(c) Availability of vacant sites or structural holes toward which the cation could move.

(d) Potential of creating nonstoichiometric solid solutions or vacant sites in compounds where the path of easy ionic motion is "plugged up" with interfering cations.

(3) The physical and chemical properties of the candidate compounds should be of such a nature that practical applications are possible. This requirement eliminates from consideration large groups of compounds:

(a) The solid electrolyte should be chemically resistant toward attack by liquid alkali metals. Many transition metal ions would be reduced under such conditions and are therefore unsuitable.

(b) The candidate compounds should be electronic insulators. This requirement eliminates from consideration many transition metal ions with partly filled d-shells, e. g., tungsten or vanadium bronzes.

(c) Potential solid electrolytes should be chemically stable under ambient conditions; for example, they should not be too hygroscopic. This requirement makes poor candidates out of many lithium- or sodium-rich oxide phases which might otherwise be attractive candidates.

(d) Potential candidates should be capable of being fabricated into dense compacts.

The structures and compounds that were finally selected for experimental investigation were determined by the following procedure. A list of candidates with supporting documentation was generated from a survey of the literature and then submitted to NASA-Lewis Research Center for selection of specific compositions to synthesize and evaluate. Some candidates were unacceptable because there were reasons to believe difficulties would be encountered in their utilization in practical battery systems. One reason was ease of fabrication. Although  $\text{Li}_3\text{AlN}_2$ ,  $\text{Li}_3\text{BN}_2$ , and salt-impregnated zeolites had given strong evidence for large ionic motion at ambient temperature, they were rejected because they are hygroscopic and would be difficult to fabricate. Compounds which contained iron, cobalt, vanadium, and similar ions were excluded because they probably would be unstable toward oxidation-reduction reactions. The fluorite arrangements of  $\text{NaPrF}_4$  and  $\text{NaYbF}_4$  are probably good fluoride ion conductors but they were not investigated further because cation conductors are specifically desired. The encouraging result obtained for lithium tantalate was not followed up because a study of the tantalate system was to be undertaken at the National Bureau of Standards.

## 2. Synthesis and Fabrication of Materials

One of the objectives of the preliminary search was to screen a large number of compounds which were to be selected from as many different structure types as possible. For this reason it was not possible to devote much time to refining the synthesis, and many of the measurements were made on impure multiphase materials. The results showed that impure powders could be screened for ion motion by NMR but that pure single-phase material was essential for the evaluation of conductivity and transport.

Particular emphasis was placed on attempts to make nonstoichiometric defect solid solutions. Many structures have potentially conducting channels

or planes which are filled to capacity with alkali metal ions. If vacancies could be introduced into such tunnels or planes, it could provide a passage for the migration of alkali metal ions.

The synthesis of the various compounds was normally done by established methods suggested in the literature. Frequently these methods had to be modified to obtain higher phase purity or to make nonstoichiometric solid solutions.

The phase purity of the various compounds was checked primarily by x-ray diffraction, supplemented by microscopic observation, especially for the glassy phases. An effort was made to identify all phases, including the impurities.

### 3. NMR Screening

The screening of solids for ionic motion by observing motional narrowing of nuclear magnetic resonance spectra was accomplished with the same techniques described previously. (2) The measurements were made by I. Chung and H. S. Story in the Physics Laboratories of the State University of New York in Albany. Compounds in which the charge carrier was predicted to be a lithium or sodium ion were screened by measuring the NMR spectra at two or more temperatures. Line narrowing with increasing temperature was evidence for ionic motion and was a necessary but not sufficient criterion for ionic transport. The spectra were measured with a Varian Associates wide-line NMR spectrometer with signal averaging.

### 4. Conductivity and Transport Measurements

The significant properties for the evaluation of solid electrolytes are ionic conductivity and transport number. These measurements usually require either large single crystals or polycrystalline compacts which are dense and single phase. Since the growth of large crystals and the development of fabrication procedures for densifying new materials are difficult and time-consuming processes, the search for new electrolytes would be expedited by procedures which can be applied either to powders or to small crystals. A number of methods which were tested for achieving this objective are described below.

#### (a) Two-phase measurement of conductivity

Professor Charles W. Tobias suggested it might be possible to determine the conductivity of a powder by suspending it in a solution which contained the same conducting ion from measurements on the total conductivity of the two-phase system. Two experiments were performed by S. P. Mitoff and R. N. King to test the feasibility of this idea. The experiments showed that the two-phase method could not be used in its present form to obtain reliable conductivities of suspended powders.

The tests were carried out by measuring the conductivity of a solution of NaI in propylene carbonate containing a suspension of 60 mesh Monofrax beta-alumina powder. The measurements were compared with similar measurements on a suspension of Pyrex glass with the same particle size. The same results were obtained from two experiments. The second experiment was made with particular care to insure the solids were wet by the liquid by heating the suspension to 95°C under a vacuum of 30 inches of Hg. Both experiments showed the Pyrex glass and beta-alumina increased the resistance of the liquid electrolyte by the same amount (e.g., from 1320 ohms to 3350 ohms, four-probe AC measurements).

The measurements showed that both the Pyrex glass and beta-alumina behaved as insulators and the increase in resistance was due to the volume of the suspended solid. It was concluded that the conducting properties of the two-phase system are determined by the solid-liquid interface and cannot easily be used to obtain information about the suspended solid. No further work was done on this method as it seemed unlikely that it could be used in its present form to measure the conductivity of an unknown powder.

(b) Microwave measurement of conductivity of powders

The bulk conductivity of powders can be measured at microwave frequencies because at very high frequency the individual crystallites are capacitively coupled and the results are determined by the intrinsic properties of the solid. Microwave techniques are frequently used to measure semiconductor and dielectric materials, but to our knowledge they have not been used for the study of ionic conductivity in loose powders. The validity of the method was established by measuring the conductivity of beta-alumina. In addition a few preliminary measurements were made on two candidates synthesized in this study (W-doped  $\text{LiNb}_6\text{O}_{15}\text{F}$  and  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ ). At the request of NASA-Lewis Research Center, the microwave screening studies were discontinued and the candidate materials were sent to their laboratories for dielectric loss measurements. (2b) Since both were high-frequency measurements, this was done to avoid duplication of effort and allow the General Electric study to concentrate on the measurement of micro-specimens. A brief description of the microwave equipment and validation measurements is given below.

The conductivity and dielectric constant of powders was measured in the range of centimeter waves by the "hollow-pipe" method introduced by S. Roberts and A. von Hippel<sup>(2c)</sup> [J. Appl. Phys., 17, 610-616 (1946)] for dielectric measurements. The specimen is contained in a cavity attached to a coaxial line. A transmitter radiates waves of a given frequency which are reflected by a metallic short which terminates the cavity. Standing waves are set up and measured by a probe traveling along a slot in the pipe parallel to its axis. The conductivity and dielectric constant are calculated from the standing wave ratio (SWR) in air and the distance of the first node from the surface of the specimen. The conductivity and permittivity are related by

a transcendental equation which cannot be solved explicitly in terms of the measured parameters. The desired quantities were obtained by using a program written by G.H. Glover of our Laboratory in which a computer inverts the transcendental equations by successive interpolation. The specimen chambers were made of brass and the measurements were made over the frequency range 2 to 4 GHz.

The microwave method was tested by measurements on loosely packed powders (approximately < 100 mesh) of Monofrax H beta-alumina. The resistivity and dielectric constant of beta-alumina are given in Tables I and II. The results show powder conductivities were obtained which are close to accepted values measured on single crystals and dense ceramic specimens. The larger resistivity of the specimen that had not been dried agrees with the well known effects of water vapor absorbed in beta alumina. The frequency dependence indicates some dispersion but the method appears satisfactory for screening purposes.

More work would be required to establish the uniqueness of the parameters deduced by the inversion procedures. The hyperbolic functions are multivalued and measurements with a single thickness of specimen may give ambiguous results. The problem can be solved by measurements on specimens of different thickness. If the conductivity is calculated from two different thicknesses of material, only one pair of values will satisfy both sets of experimental results.

TABLE I

Microwave Conductivity and Dielectric Constant of Beta-Alumina Powder at Room Temperature

Frequency (GHz)	Not dried $\rho$ (ohm-cm)	$\epsilon_r$	Dried $\rho$ (ohm-cm)	$\epsilon_r$
4.00	756	12.1	810	3.00
3.75	1620	8.8	1388	2.59
3.50	1390	10.4	1732	2.94
3.25	2420	11.3	2052	3.31
3.00	2088	12.6	2027	3.83
2.75	7917	2.73	1942	4.03
2.50	5694	3.72	1605	5.31
2.25	5744	4.25	1424	6.43
2.00	--	--	1170	7.83

TABLE II

Temperature Dependence of Microwave Conductivity  
of Dry Beta-Alumina Powder

---

Temp (°C)	$\rho$ (ohm-cm)	$\epsilon_r$
24	810	3.007
52	614	3.012
60	560	2.960
70	497	2.976
80	473	2.828
90	438	2.810
100	413	2.830

(c) Conductivity, transport, and pulse measurements on micro-specimens

---

The following methods were developed to determine the ionic transport in small specimens. They can be used on glasses or polycrystalline ceramics, coarse grained powders, and single crystals. The techniques are still being improved but the methods have already given useful information that could not have been obtained with conventional methods. Key contributions to the success of these methods were made by Dr. G. C. Farrington for the techniques of measuring conductivity in nonaqueous solvents and with fast pulses, and by Mrs. Ethel Fontanella for developing methods for potting solid electrolytes and assembling conductivity cells. The first apparatus was a Teflon polymer cell in which specimens 2 to 4 mm in diameter and about 1 mm thick were measured successfully. The method next was applied to specimens with dimensions between 0.5 and 1 mm by potting the specimen in an epoxy cell (microcell). Some measurements were made with conventional four-probe DC and AC bridge methods, and particular success was obtained with fast pulse measurements.

i. Teflon polymer conductivity cell. The first conductivity cell is shown in Fig. 1. Above is an overall view of the assembled cell and below a disassembled cell. The cell is made of two Teflon polymer blocks,  $1\frac{1}{4} \times 1\frac{1}{4} \times 1$  inch and  $1\frac{1}{4} \times 1\frac{1}{4} \times \frac{7}{8}$  inch, which are drilled with cavities and clamped together to form compartments into which platinum or silver electrodes are inserted. The compartments are separated by an epoxy disk which contains the solid to be measured. The epoxy disk is sealed into the cell with a pair of Viton or silicone rubber "O"-rings. Each electrolyte compartment contains about 2 ml electrolyte solution and a variety of solvents and electrode systems were used to study different ions and for potentiometric measurements.

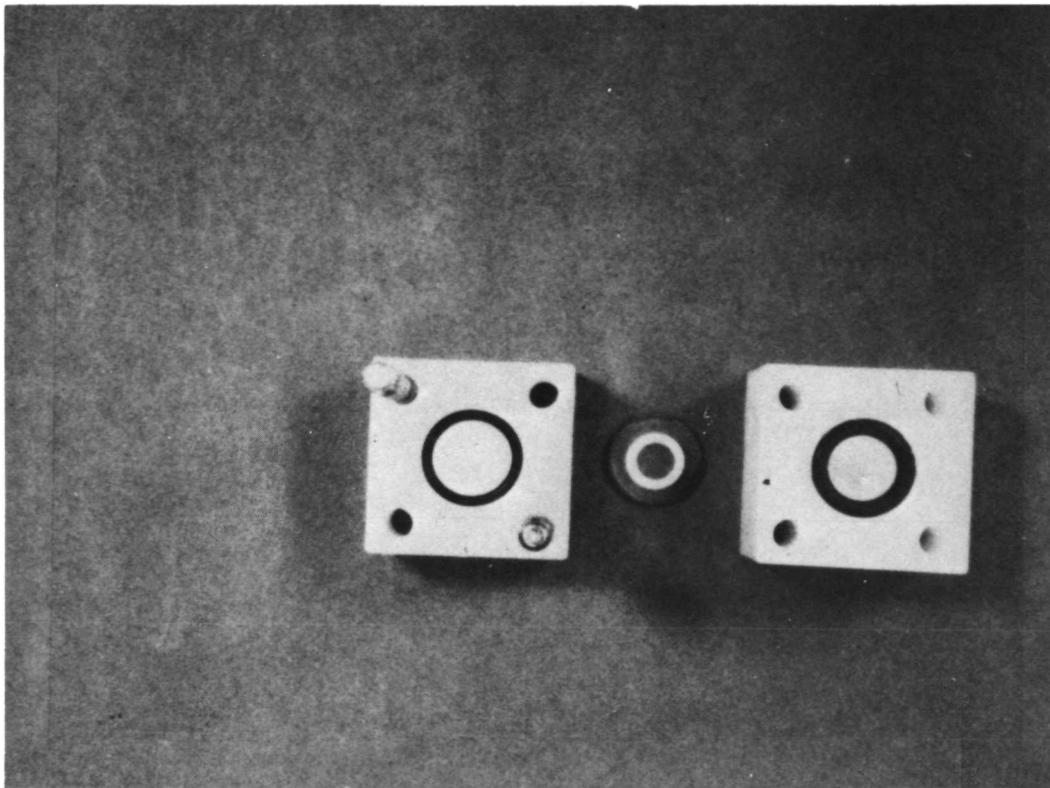
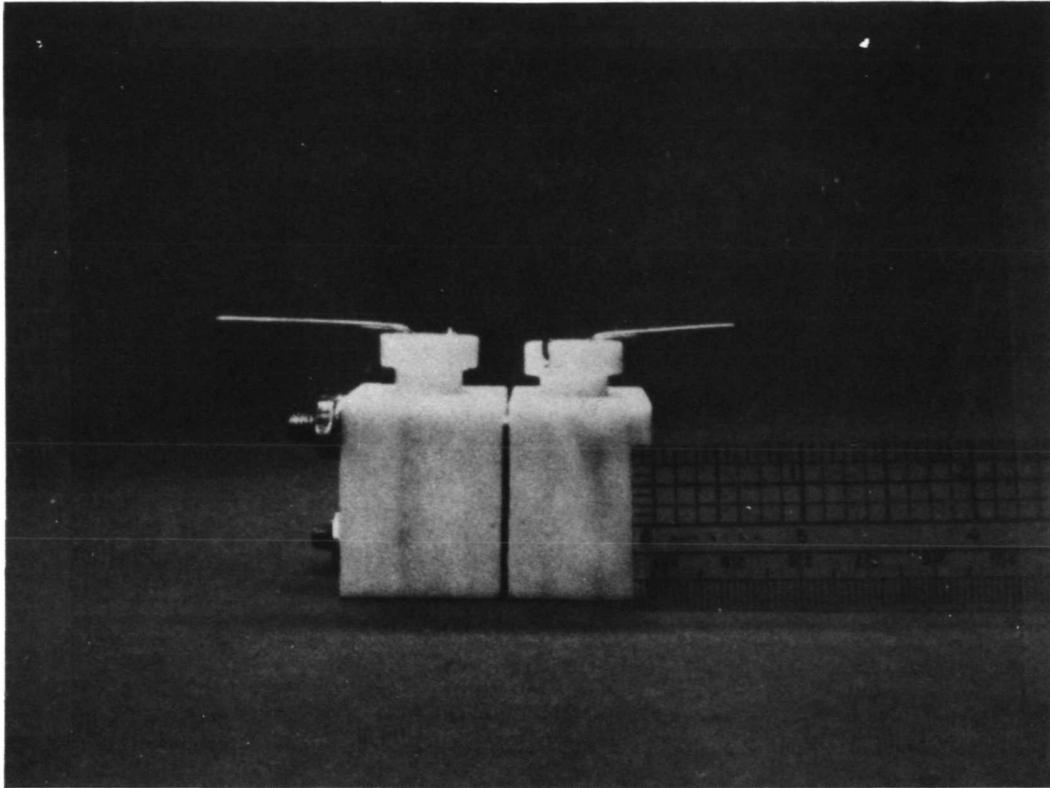


Fig. 1 Conductivity cell. Overall and disassembled views are shown. The specimen is a cross section of a beta-alumina tube tested to validate the pulse method for conductivity measurement.

The sample to be tested is potted in a specially formulated epoxy resin in the form of a disk, 16 mm diameter and usually about 0.5 mm thick. The disk is cast in a silicone rubber mold and curing techniques have been developed which produce disks without gas pockets. The final step in specimen preparation is to grind the disk until the solid electrolyte is exposed on both sides. The potted specimens are helium leak tested before assembling in the cell. Two methods are used to avoid leaks between the specimen and the epoxy potting matrix. Such leaks frequently develop during polishing to expose the surfaces of the solid electrolyte. The solid electrolyte surface may be protected by clamping the specimen between silicone rubber disks before submerging in epoxy. Alternatively, opposed small areas of the specimen are coated with RTV-112, a pourable silicone rubber sealant, cured for 24 hours, then imbedded in epoxy contained in a silicone mold. The cured RTV can be stripped off the surface after the epoxy resin has hardened. The latter procedure can be done under the microscope and is particularly useful for small samples.

The disk is clamped between the "O" -rings in the cell and the complete assembly tested for helium leaks. The cell then is placed in a dry box, the electrolyte solutions are added, and the electrodes are inserted. Electrolytes of lithium perchlorate or sodium trifluoromethane sulfonate dissolved in propylene carbonate and acetyl nitrite are stable and do not react with the components of the cell.

The cell was tested by preparing potted disks of ceramic beta-alumina and single-crystal beta-alumina. Disks were hand lapped to about 0.5 mm and to less than 0.2 mm with a jewelers lathe. This thickness sets the lower limit of crystal size that can be tested by this method.

ii. Microcell. The assembly shown in Fig. 1 was not satisfactory when specimens smaller than 0.5 mm were measured with the pulse technique that will be described later. This was due to the fact the epoxy matrix has a small but finite conductivity and capacitive and polarization effects at the liquid electrolyte-solid interface dominated the response of the samples with small dimensions. The problem was solved by constructing microcells of the type shown in Fig. 2 in which the liquid electrolyte-solid interface is reduced to the sample size. In essence, a cell is built around each sample by casting epoxy bubbles on both sides of the potted specimen, then tunnels are drilled to contain the liquid electrolyte and platinum leads. The liquid electrolyte is introduced into the cell with a hypodermic needle.

iii. Pulse technique for conductivity measurement. The procedure developed to measure ionic conductivity is to observe the structure of a square wave constant pulse in order to separate the IR drop in the solid electrolyte from interfacial polarization.

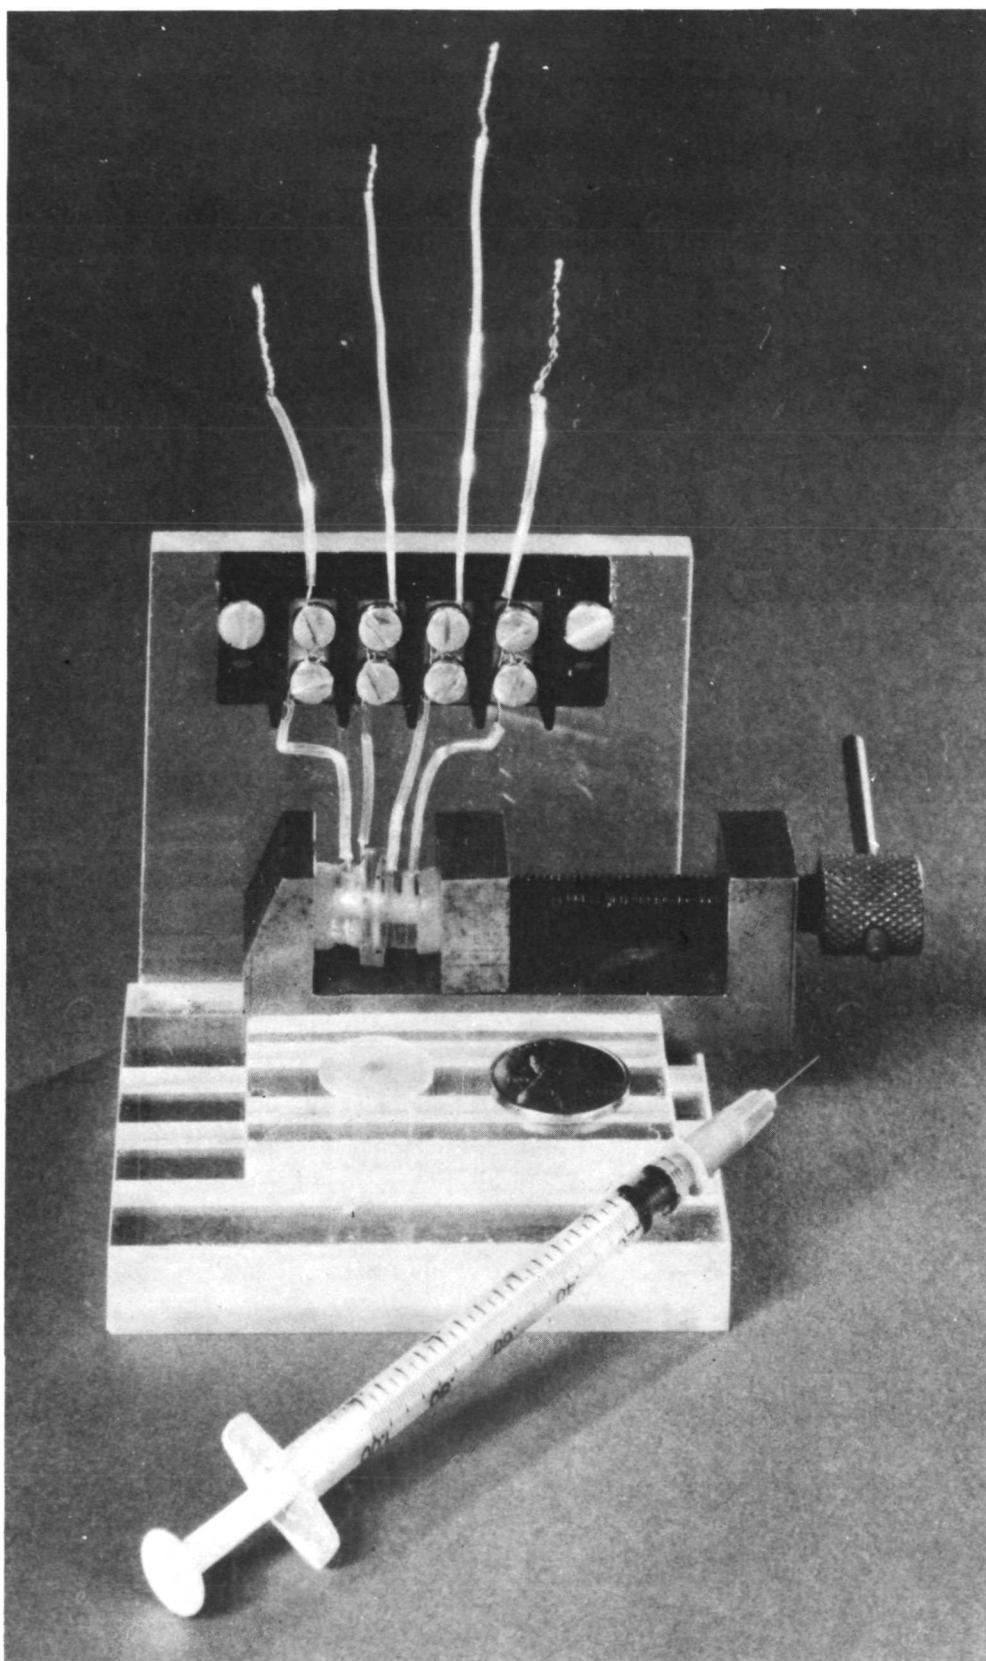


Fig. 2 Microcell for small specimens. Also shown is a potted sample before cell assembly. The liquid electrolyte is introduced with a hypodermic needle.

The experimental apparatus consists of a 2N3904 transistor acting as a fast response switch in series with a ca 20 Kohm resistance and a 22 1/2 volt battery. Switching is effected by driving the transistor base with a 0 to +4v square wave pulse train supplied by a PAR Model 175 universal programmer. The programmer also triggers a Model 7B52 delayed sweep time base in a Tektronic Model 7704A oscilloscope. Vertical oscilloscope input is provided by a dual trace Model 7A12 amplifier which permits simultaneous monitoring of the potentials of the two sensing electrodes in the Teflon polymer electrolysis cell.

The interface polarization was displayed by observing the rise and decay of a  $3 \times 10^{-4}$  amp current pulse introduced as a 0.05 sec square wave. The voltage drop due to polarization was manifested by approximately exponential slow components superimposed on the leading and trailing edges of the square wave. The resistivity of the beta-alumina calculated from the initial rapid decay was found to be 1550 ohm-cm.

With this apparatus it is possible to apply constant current pulses of varying amplitudes to the two working electrodes in the Teflon polymer electrolysis cells while simultaneously monitoring either the total pulse shape or magnified pulse structure at initiation or termination. Pulses of 200 msec to 1 msec duration have generally been used. These have had rise and fall times into a 2000 ohm dummy resistance of less than 0.4  $\mu$ sec.

In an actual measurement, a series of current pulses is applied to the electrolysis cell which is connected in series with a precise 2000 ohm General Radio resistor. Voltage drops across the sensing electrodes and the standard resistance are recorded. Typical currents are in the range of 15 to 50  $\mu$ amp. As has been described previously, the pulse measurement technique relies on the concept that the portion of the total applied cell voltage which arises from electrolyte iR drop decays almost instantaneously upon cessation of current flow while that portion of cell voltage which arises from interfacial polarization decays at a much slower rate, typically over a period of 10 to 50 msec. If a sharp enough current pulse can be applied to a cell and sensitive enough equipment is used to carefully examine the resulting shape of the total applied voltage, absolute magnitudes of iR drop and interfacial polarization can be determined. A four-electrode technique was used in these experiments to separate any electrochemical polarizations at the electrodes where current is applied from the polarizations at the solid electrolyte/liquid electrolyte interface.

### III. VALIDATING EXPERIMENTS

#### A. Bridge Measurements

The reliability of the conductivity techniques was tested by measurements on beta-alumina ceramic specimens of known conductivity. The room temperature resistivity of freshly prepared ceramic beta-alumina, measured by the four probe technique, was 2490 ohm-cm at 10 Hz and 66 ohm-cm at 300 kHz. Experience has shown these values may increase slightly (25%) due to absorption of water from the atmosphere. The beta-alumina was cut and ground to a regular parallelepiped with area equal to  $0.8 \times 0.6 = 0.48 \text{ cm}^2$  and thickness of 0.075 cm and potted in epoxy resin.

Measurements were made in a Teflon polymer cell with coiled Pt electrodes and 1M NaClO<sub>4</sub> in propylene carbonate. Initial values were obtained at 1000 Hz with an AC bridge. The resistance of the cell with no separator was 496 ohms and that of the blank epoxy disk without beta-alumina about  $10^6$  ohms. The apparent resistance of the beta-alumina membrane, after subtracting that of the liquid electrolyte, was then found to be  $2700 - 496 = 2204$  ohms, corresponding to a resistivity of

$$2204 \times \frac{0.48}{0.075} = 15,000 \text{ ohm-cm.}$$

The large resistivity calculated from the cell measurement, approximately seven-fold greater than the four-probe DC value, is evidence of significant polarization at the solid-liquid electrolyte interface.

#### B. Applications of Pulse Technique to Beta Alumina

The pulse technique was validated by measuring the ionic conductivity in a well-characterized sample of beta-alumina. The beta-alumina ceramic was cut and polished to expose a disk 2 mm in diameter and 0.474 mm thick.

Figure 3 shows the overall structure of the cell voltage response to a constant current pulse through beta-alumina separating two-cell compartments filled with 0.1M NaClO<sub>4</sub> in propylene carbonate. The numbers in the upper- and lower-left corners are the vertical scale factors in mV/cm for the upper and lower traces, respectively. Sweep time in  $\mu\text{sec/cm}$  is recorded in the upper or lower right-hand corners. Total cell voltage between the two sensing electrodes is the difference between both traces.

Note in Fig. 3 the sharp rise upon onset of pulse and sharp fall upon termination. The termination region is magnified in the lower photograph. A sharp drop occurring within a fraction of a microsecond occurs in the voltage of each electrode. Only the electrode response recorded in the upper trace includes the effects of the beta-alumina; the lower trace arises from the sensing electrode separated from ground solely by propylene carbonate

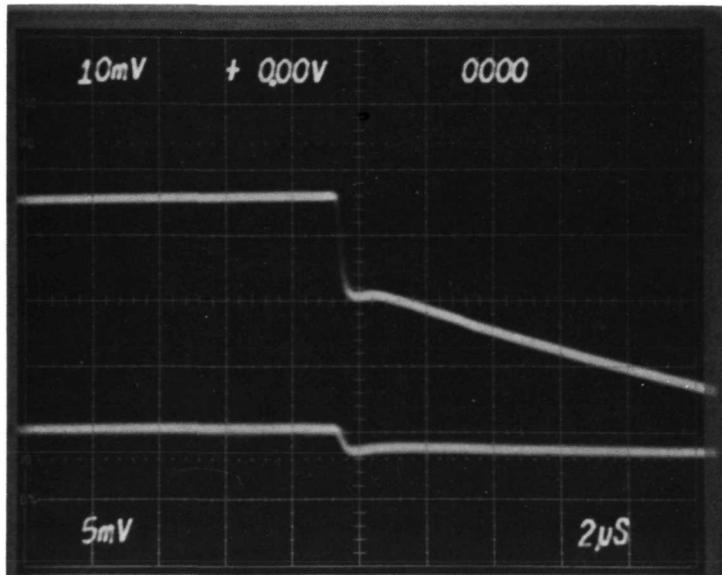
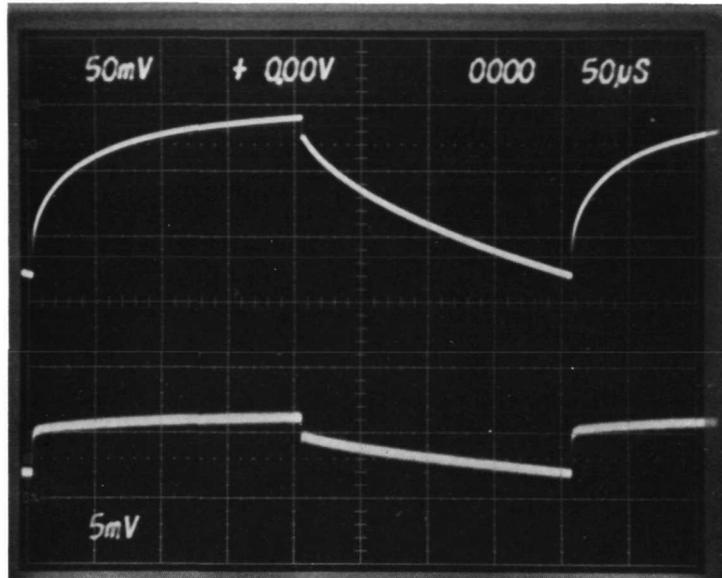


Fig. 3 Cell voltage response to constant current pulse through beta-alumina. Lower trace is expansion of termination region.

solution. The sharp voltage drops are interpreted as measurements of  $iR$  loss whereas the slower potential decay of the upper trace reflects decay of interfacial polarization at the beta-alumina surface. An ionic conductivity of 1100 ohm-cm is calculated from these data after correction for the resistance of the propylene carbonate solution. Since the conductivity and area of the candidate conductors frequently are much smaller than that measured above, experiments were undertaken to validate the method with a smaller specimen of beta-alumina.

An attempt was made to determine the resistance of a sample of polycrystalline beta-alumina having an area exposed of  $0.0020 \text{ cm}^2$ , or about 1% of that of any sample previously measured. The cell response was the same as that exhibited by a pure epoxy disk under similar conditions.

The sensitivity of the pulse technique for small specimens was increased by maximizing the ratio of sample area to disk area. With a minute sample of beta-alumina pulse measurements with the microcell described in the preceding section gave  $\rho \approx 1000 \text{ ohm cm}$ , in agreement with accepted values.

An additional complication stems from the fact that the epoxy disk between two conducting liquids acts as a capacitor. When the conductivity between the cells is high, this has little effect on these measurements. However, when the conductivity is low, the entire cell responds as a capacitor. The constant current source then ceases to function properly and the pulse technique becomes useless. The microcell, in which the nonconductive area is minimized, solved this problem as well.

The possibility was explored of using a potentiometric method to establish ionic conductivity in specimens which are extremely small or resistive. The liquid electrolyte was replaced by solutions which were  $0.2M \text{ AgClO}_4 + 0.1M \text{ NaClO}_4$  and  $0.002M \text{ AgClO}_4 + 0.1M \text{ NaClO}_4$  on opposite sides of the beta alumina sample. The potential developed between Ag electrodes was 0.131V, in reasonable agreement with the theoretical value

$$0.059 \log \frac{0.2}{0.002} = 0.118V.$$

Unfortunately, the same result was obtained when the blank epoxy disk was substituted for that containing beta-alumina, and we conclude the epoxy resin or Viton rubber are too conducting for this to be a practicable method.

## IV. RESULTS AND DISCUSSION OF RESULTS

### A. $\text{LiNb}_6\text{O}_{15}\text{F}$ -Type Compounds

#### 1. Structure and transport model

The tunnel structure found for  $\text{LiNb}_6\text{O}_{15}\text{F}^{(1)}$  is illustrated in Fig. 4. The building blocks are made up of pentagonal  $\text{NbX}_7$  bipyramids, sharing edges with five  $\text{NbX}_6$  octahedra. These building blocks are joined together at the corners in three dimensions, leaving hollow tunnels in which the  $\text{Li}^{1+}$  ions are presumed to occupy two possible sites.\* Either site would yield six to eight Li-O

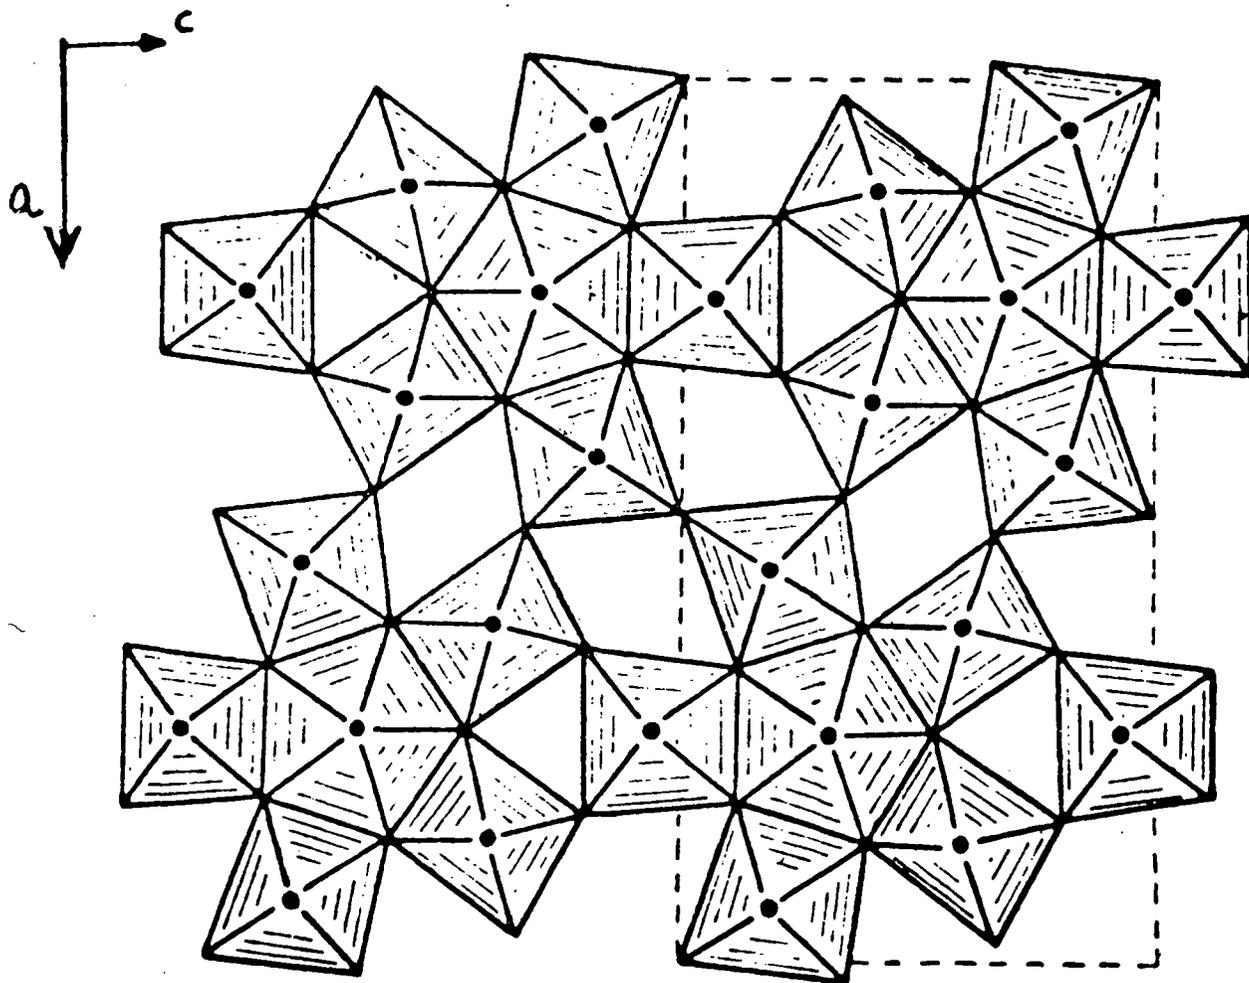


Fig. 4 The structure of  $\text{LiNb}_6\text{O}_{15}\text{F}$ . ( $\text{Li}^{1+}$  ions are not shown.) Taken from Ref. 1.

---

\*Due to their low scattering power, the Li atoms cannot be located easily by x-ray methods. The Li-sites have been inferred from the knowledge of the rest of the structure.

distances between 2.5Å and 3.0Å. These distances are considerably larger than conventional Li-O bonds which are of the order 1.95Å to 2.30Å. It would appear, therefore, that these tunnels are wide enough for migration of  $\text{Li}^{1+}$  ions along the tunnels or b-direction of Fig. 1. In preliminary NMR screening<sup>(2)</sup> motional narrowing at -26°C was observed for  $^7\text{Li}$  in  $\text{LiNb}_6\text{O}_{15}\text{F}$ , indicating at least local ionic motion of the  $\text{Li}^{1+}$  ions.

If the Li ions occupied fully one of the two Li sites, with the other type of channels completely empty, ionic conductivity would not be expected in stoichiometric  $\text{LiNb}_6\text{O}_{15}\text{F}$ . However, one could image nonstoichiometric variants (listed below) with either lower or higher Li content, made by substituting ions such as  $\text{Ti}^{4+}$ ,  $\text{Mo}^{6+}$ , or  $\text{W}^{6+}$  and adjusting the O/F ratio. It is quite possible that both Li sites are partly occupied by  $\text{Li}^{1+}$  ions. In this case high ionic mobility might be expected even for stoichiometric  $\text{LiNb}_6\text{O}_{15}\text{F}$ .

## 2. Synthesis

### (a) $\text{LiNb}_6\text{O}_{15}\text{F}$ and $\text{Li}_{0.8}\text{Nb}_{5.6}\text{W}_{0.4}\text{O}_{15.2}\text{F}_{0.8}$

$\text{LiNb}_6\text{O}_{15}\text{F}$  and  $\text{Li}_{0.8}\text{Nb}_{5.6}\text{W}_{0.4}\text{O}_{15.2}\text{F}_{0.8}$  can be prepared by heating the appropriate mixtures of LiF,  $\text{Nb}_2\text{O}_5$  and  $\text{WO}_3$  in sealed platinum tubing (as a loose powder) or a sealed platinum crucible (in the form of compressed pellets). For one set of samples the heat treatment was 2 days at 1200°C in a muffle furnace. A second set of samples was heated for 1 day at 950°C. The resulting products for both temperatures and compositions were single phase and of the  $\text{LiNb}_6\text{O}_{15}\text{F}$  type. No impurity peaks could be identified by x-ray diffraction. The crystals tend to be blade-like and up to 2 mm in length.

### (b) $\text{Li}_{0.9}\text{Nb}_{5.8}\text{Mo}_{0.2}\text{O}_{15.1}\text{F}_{0.9}$ and $\text{Li}_{0.86}\text{Nb}_{5.72}\text{Mo}_{0.28}\text{O}_{15.14}\text{F}_{0.86}$

Mo-substituted phases of the above compositions could be prepared in the same manner as described above for  $\text{LiNb}_6\text{O}_{15}\text{F}$ , except that here the samples are heat treated at lower temperatures: 1 day at 950°C. X-ray diffraction data showed that these phases were of the  $\text{LiNb}_6\text{O}_{15}\text{F}$  type. No impurity peaks could be detected.

### (c) Attempted Synthesis of $\text{Li}_{0.8}\text{Nb}_{5.6}\text{Mo}_{0.4}\text{O}_{15.2}\text{F}_{0.8}$ and $\text{Li}_{0.7}\text{Nb}_{5.4}\text{Mo}_{0.6}\text{O}_{15.3}\text{F}_{0.7}$

Attempts were also made to synthesize  $\text{LiNb}_6\text{O}_{15}\text{F}$ -type compounds of compositions  $\text{Li}_{0.8}\text{Nb}_{5.6}\text{Mo}_{0.4}\text{O}_{15.2}\text{F}_{0.8}$  and  $\text{Li}_{0.7}\text{Nb}_{5.4}\text{Mo}_{0.6}\text{O}_{15.3}\text{F}_{0.7}$ . However, these two compositions gave a two-phase mixture: (a) a coarsely crystalline  $\text{LiNb}_6\text{O}_{15}\text{F}$ -type phase with blade-like crystals up to 2 mm, (b) a fine needlelike phase of a darker color.

#### (d) Ti-Substituted Phases

Attempts were made to prepare a  $\text{LiNb}_6\text{O}_{15}\text{F}$ -type phase of composition  $\text{Li}_{1.2}\text{Nb}_{5.6}\text{Ti}_{0.4}\text{O}_{14.8}\text{F}_{1.2}$ . The synthesis proceeded as described for  $\text{LiNb}_6\text{O}_{15}\text{F}$ . A compound of the desired  $\text{LiNb}_6\text{O}_{15}\text{F}$  structure type could not be obtained, and it is tentatively concluded that  $\text{Ti}^{4+}$  cannot be substituted into the  $\text{LiNb}_6\text{O}_{15}\text{F}$  structure in significant amounts.

#### 3. Evaluation

Strong motional narrowing of  $^7\text{Li}$  in stoichiometric  $\text{LiNb}_6\text{O}_{15}\text{F}$  was previously reported. (2) The dependence of line width on temperature indicated the lithium motion was probably localized or short range. NMR spectra of  $\text{LiNb}_6\text{O}_{15}\text{F}$  doped with molybdenum and tungsten are shown in Figs. 5(a), (b), (c), and (d). The  $^7\text{Li}$  spectrum, measured at room temperature and  $186^\circ\text{C}$ , shows strong motional narrowing. The line widths of the doped compounds are more narrow than in stoichiometric  $\text{LiNb}_6\text{O}_{15}\text{F}$  (Table III), showing that substitution of Nb by Mo and W increases the lithium mobility, probably because more vacancies and disorder were introduced in the tunnels. No motional narrowing of the fluorine NMR spectrum was detected over the same temperature range. The absence of a Knight shift in the stoichiometric compound was previously reported to show the absence of electronic conductivity. It is believed the same is true for the doped compounds because the composition of the phases was adjusted to maintain the niobium in the pentavalent state.

TABLE III

NMR Spectra of  $\text{LiNb}_6\text{O}_{15}\text{F}$  Compounds

<u>Sample</u>	<u>Compound</u>	<u>Nucleus</u>	<u>Temp (<math>^\circ\text{C}</math>)</u>	<u>Width, Gauss</u>
C-5a	$\text{Li}_{0.9}\text{Nb}_{5.8}\text{Mo}_{0.2}\text{O}_{15.1}\text{F}_{0.9}$	$^7\text{Li}$	22	$1.8 \pm 0.5$
			186	$0.17 \pm 1.0$
		$^{19}\text{F}$	22	$4.0 \pm 1.0$
			186	$4.0 \pm 1.0$
C-9a	$\text{Li}_{0.9}\text{Nb}_{5.8}\text{W}_{0.2}\text{O}_{15.1}\text{F}_{0.9}$	$^7\text{Li}$	22	$2.0 \pm 0.4$
			186	$0.18 \pm 0.04$
		$^{19}\text{F}$	22	$4.0 \pm 1.0$
			186	Not measured
		$\text{LiNb}_6\text{O}_{15}\text{F}$	$^7\text{Li}$	22
		183		$0.6 \pm 0.1$

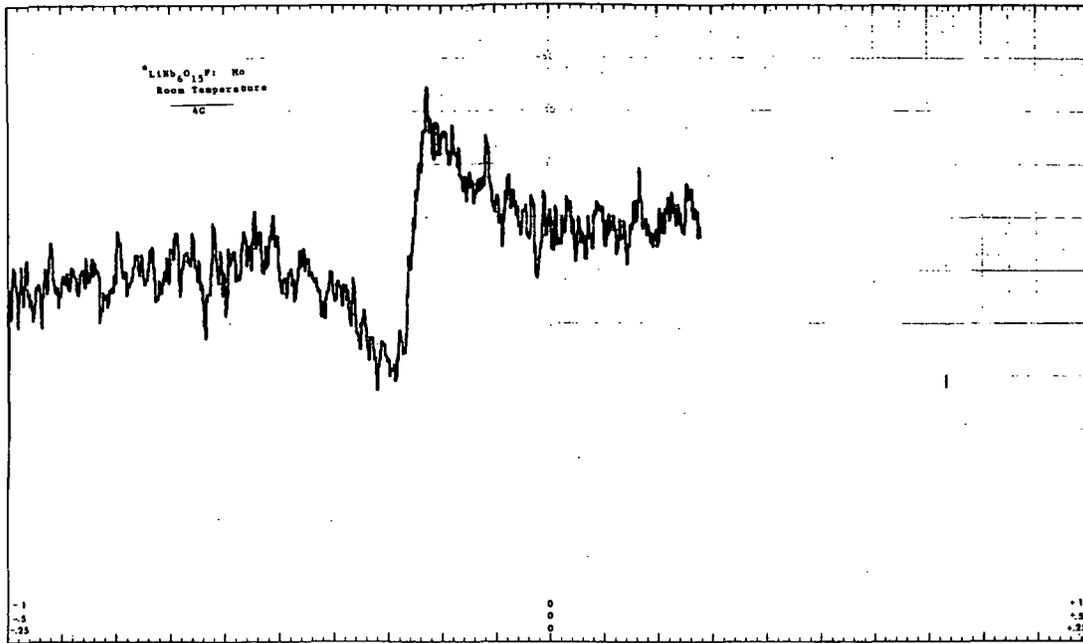


Fig. 5(a) NMR spectrum of  ${}^7\text{Li}$  in  $\text{Li}_{0.9}\text{Nb}_{5.8}\text{Mo}_{0.2}\text{O}_{15.1}\text{F}_{0.9}$  at room temperature. The peak width is 1.8 gauss.

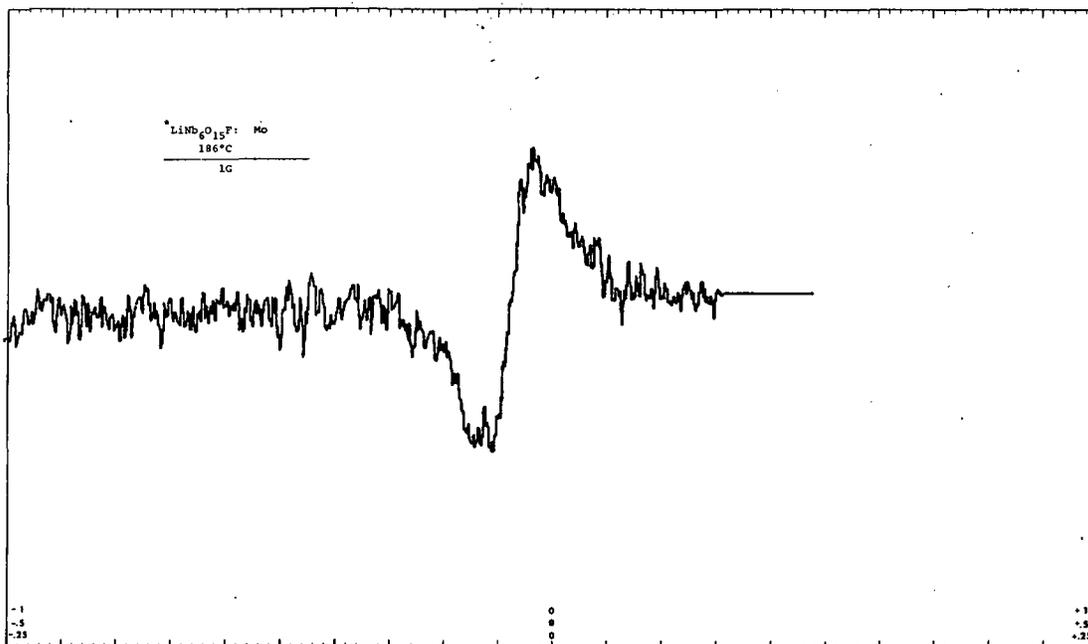


Fig. 5(b) Above at 186°C. The peak width is motionally narrowed to 0.17 gauss.

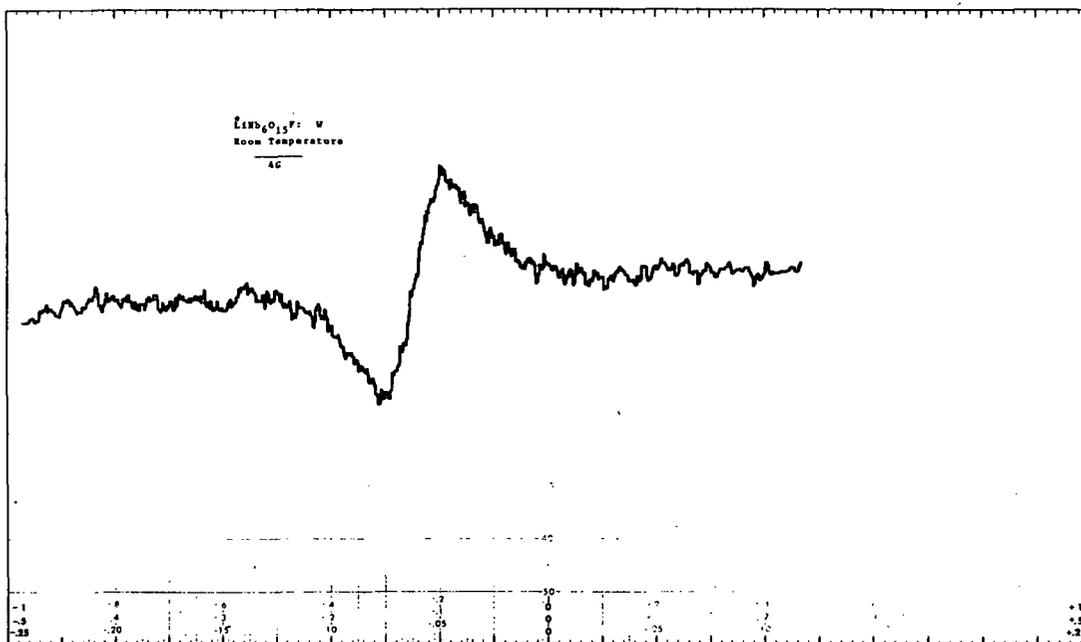


Fig. 5(c) NMR spectrum of  ${}^7\text{Li}$  in  $\text{Li}_{0.8}\text{Nb}_{5.6}\text{W}_{0.4}\text{O}_{15.2}\text{F}_{0.8}$  at room temperature. The peak width is 2.0 gauss.

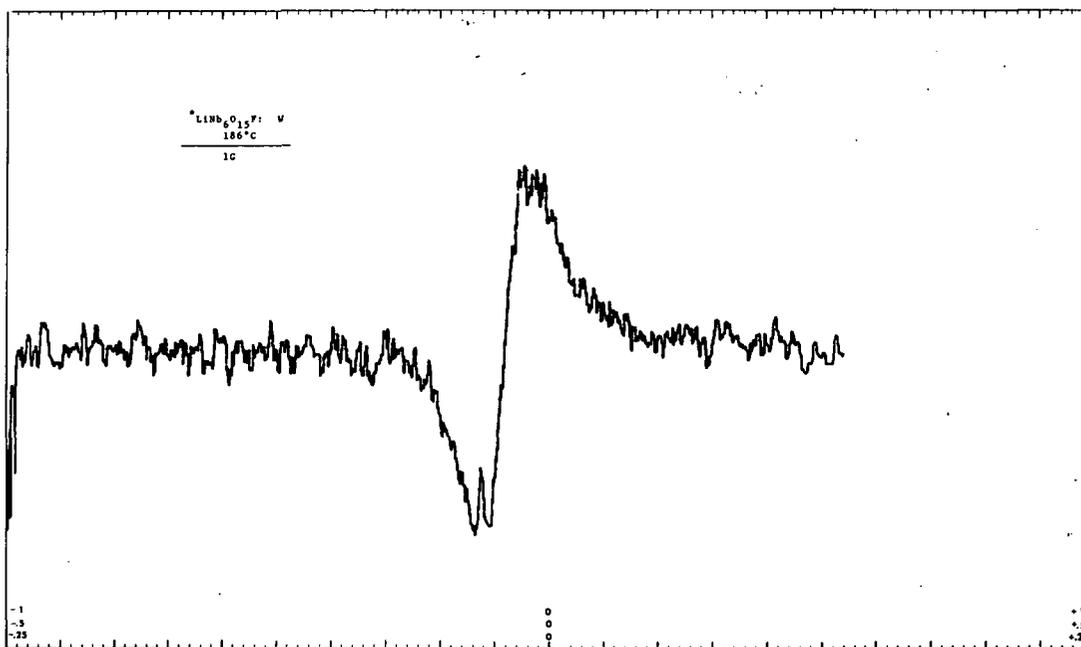


Fig. 5(d) Above at  $186^\circ\text{C}$ . The peak width is reduced to 0.18 gauss.

The crystals that were available were too small for reliable transport measurements at the present stage of development of our microcell method. Attempts were made to measure the conductivity in molybdenum-doped single crystals ( $\text{Li}_{1-x}\text{Nb}_6\text{Mo}_{2x}\text{O}_{15+x}\text{F}_{1-x}$  with  $x < 0.2$ ). In order to prevent leaks about the edges, it was necessary to pot the crystal completely and expose a circular area only 0.25 mm in diameter for measurement. The growth habit is not known so individual crystals were potted with their major face parallel and perpendicular to the applied potential. The first set of measurements, which were made in the Teflon polymer cell, gave responses that were the same as expected for the epoxy disk. The measurements were repeated with similar results in a microcell to reduce interface effects (Fig. 6). It is estimated that the conductivity is probably less than  $10^{-5}$  ohm $^{-1}$  cm $^{-1}$  at room temperature.

Dielectric loss measurements were made at NASA-Lewis Research Center on three of the lithium niobate compositions (Table IV). Neither the stoichiometric compound (C-1) nor the tungsten-doped material (C-3) gave indication of resonance peaks over the temperature range of 100° to 500°K. Titanium-doped lithium niobate (C-4) exhibited resonance peaks which were taken as strong evidence that the relaxation responsible for the resonances is that of mobile ions. The AC conductivity measured at  $10^6$  Hz was as follows:

TABLE IV

Sample	Composition	AC Conductivity (ohm $^{-1}$ cm $^{-1}$ )	
		Room Temp	500°K
C-1	$\text{LiNb}_6\text{O}_{15}\text{F}$	$2 \times 10^{-7}$	$2 \times 10^{-6}$
C-3	$\text{Li}_{0.8}\text{Nb}_{5.6}\text{W}_{0.4}\text{O}_{15.2}\text{F}_{0.8}$	$5 \times 10^{-7}$	$6 \times 10^{-6}$
C-4	$\text{Li}_{1.2}\text{Nb}_{5.6}\text{Ti}_{0.4}\text{O}_{14.8}\text{F}_{1.2}$	$8 \times 10^{-6}$	$6 \times 10^{-4}$

In summary, lithium niobium oxyfluoride appears to be a moderate to poor conductor of lithium ions at low temperature, and the conductivity is improved by doping.

## B. Hollandite-Type Compounds

### 1. Structure and Transport Model

Hollandite is a tunnel structure which takes its name from the mineral hollandite, approximately  $\text{BaFeMn}_7\text{O}_{16}$ .  $\text{K}^{1+}$ ,  $\text{Na}^{1+}$  and  $\text{Pb}^{2+}$  can substitute for  $\text{Ba}^{2+}$  and  $\text{Al}^{3+}$  for manganese or iron. The structure was first described by Byström and Byström<sup>(3)</sup> and is illustrated in Fig. 7. In the structure,  $\text{MnO}_6$  octahedra and  $\text{FeO}_6$  octahedra randomly form an open framework which leaves empty channels. Approximately half of the available sites in the channels are occupied by  $\text{Ba}^{2+}$  ions. It has been postulated<sup>(3)</sup> that these  $\text{Ba}^{2+}$  ions are strung out along these tunnels in a regular manner, such that each

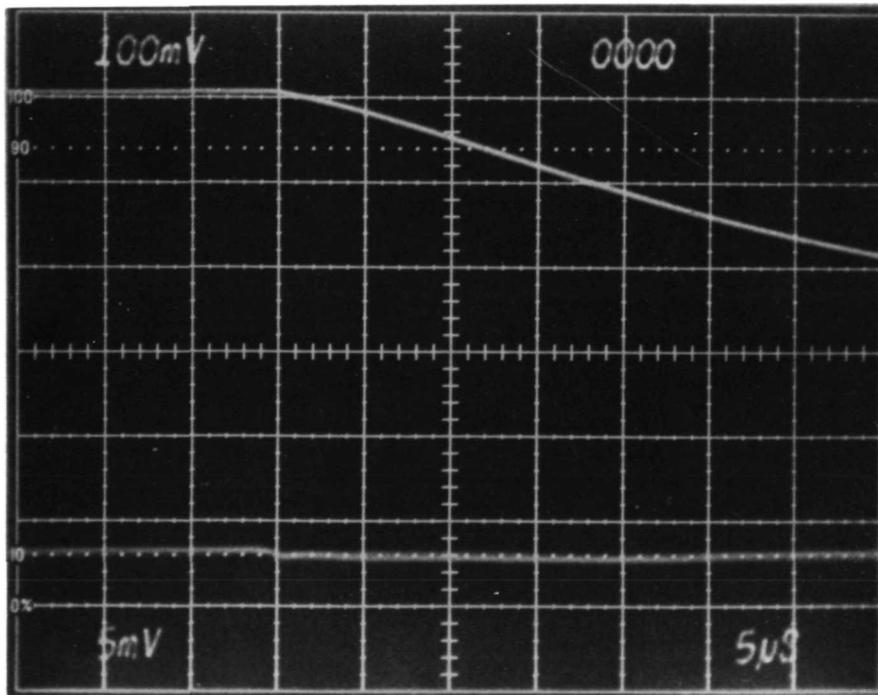
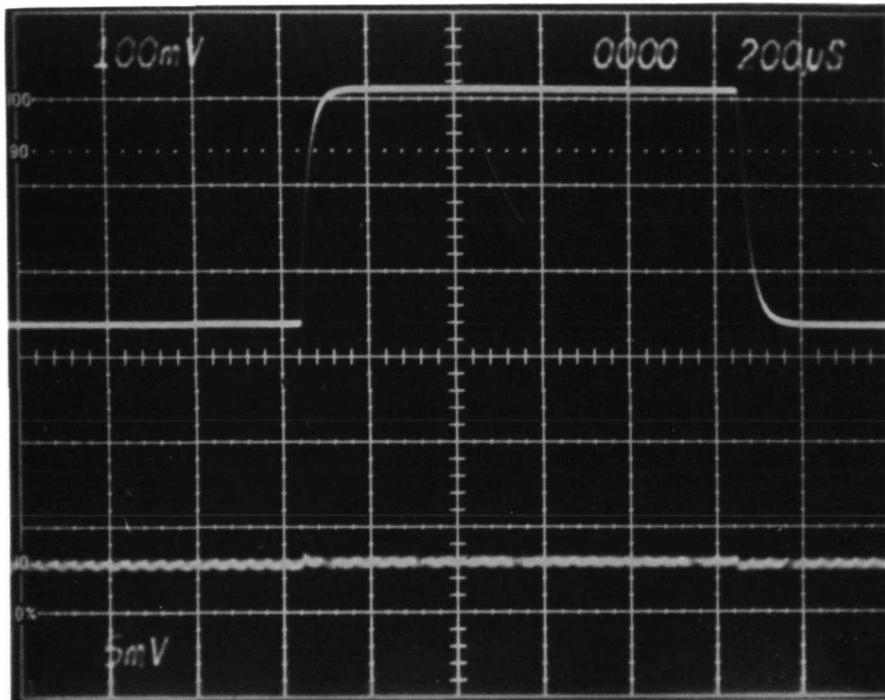


Fig. 6 Response of Mo-substituted  $\text{LiNb}_6\text{O}_{15}\text{F}$  crystal in microcell. The lower trace is an expansion of the termination region.

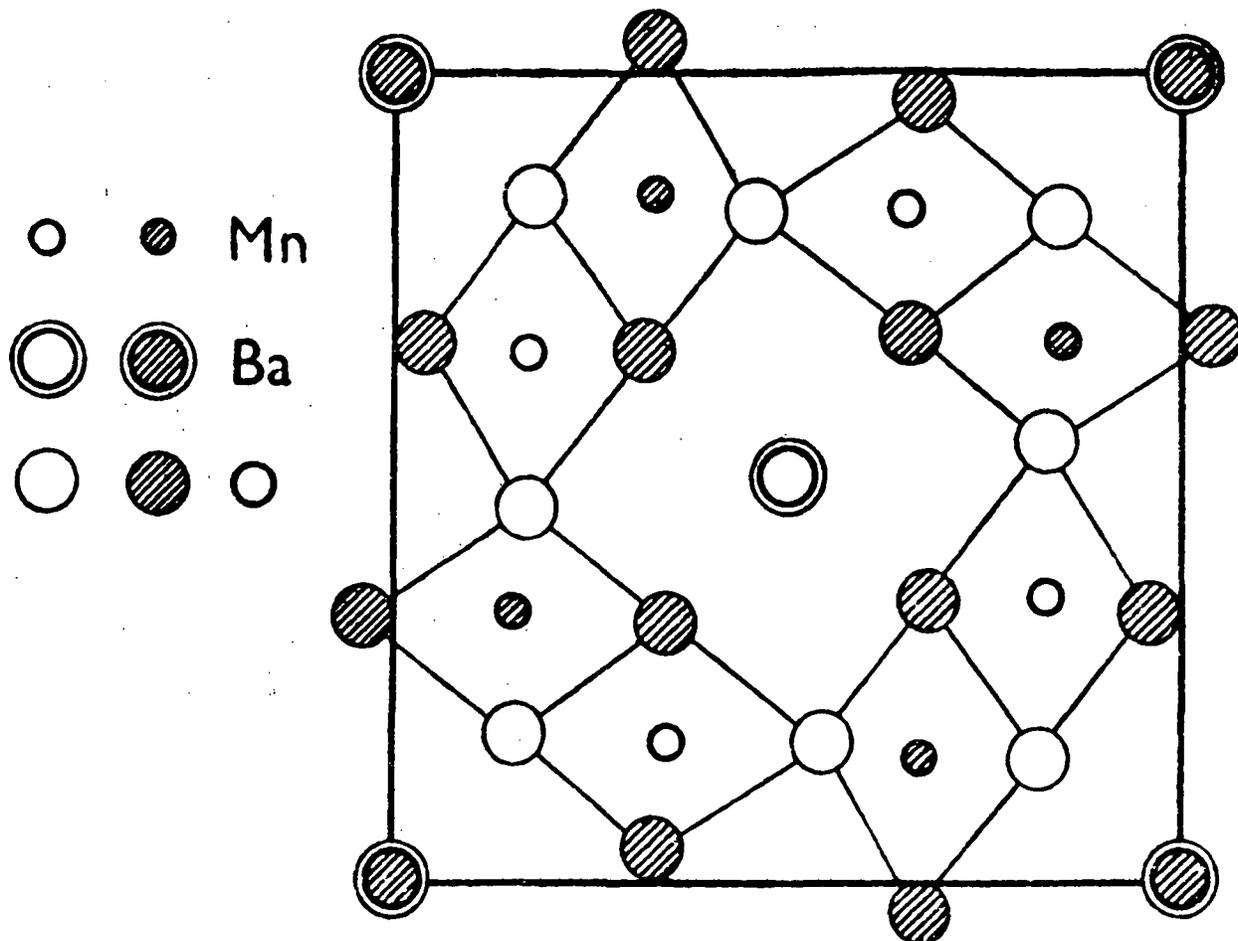


Fig. 7 The structure of hollandite projected on the (001) plane. After Ref. 3.

$\text{Ba}^{2+}$  ion is followed by a vacant site and each vacant site by a  $\text{Ba}^{2+}$  ion. These  $\text{Ba}^{2+}$ -□- $\text{Ba}^{2+}$ - . . . . chains are randomly arranged in the structure, so that there is only a one-dimensional order in the tunnels. It has also been postulated that the vacant sites between  $\text{Ba}^{2+}$  ions can be partly occupied by water molecules which are always present in the mineral. (3)

In recent years a large number of new hollandite-type compounds have been reported (4, 5) in which alkali metal ions (especially  $\text{K}^{1+}$  and  $\text{Rb}^{1+}$ ) completely replace the  $\text{Ba}^{2+}$  ions inside the tunnels. Such  $\text{K}^{1+}$  or  $\text{Rb}^{1+}$ -hollandites can be completely stoichiometric so that all sites within the channels are occupied, and no vacancies exist, e. g.,  $\text{K}_2\text{ZnTi}_7\text{O}_{16}$ ,  $\text{K}_2\text{Ga}_2\text{Ti}_6\text{O}_{16}$ ,  $\text{Rb}_2\text{MgTi}_7\text{O}_{16}$ ,  $\text{Rb}_2\text{Al}_2\text{Ge}_6\text{O}_{16}$ , etc. For some systems, both stoichiometric and non-stoichiometric phases can be prepared. For example, in the  $\text{K}_2\text{O}-\text{TiO}_2-\text{Al}_2\text{O}_3$  system, stoichiometric  $\text{K}_2\text{Al}_2\text{Ti}_6\text{O}_{16}$  and nonstoichiometric  $\text{K}_{1.6}\square_{0.4}(\text{Al}_{1.6}\text{Ti}_{6.4})\text{O}_{16}$  can be prepared, both with the hollandite structure. (4)

Stoichiometric hollandites have also been made with  $\text{Ag}^{1+}$ ,  $\text{Tl}^{1+}$  or  $\text{Na}^{1+}$  in the tunnels; (5) however,  $\text{Cs}^{1+}$ -hollandites can only be made non-stoichiometric. (4) Apparently the large size of the  $\text{Cs}^{1+}$  and  $\text{Ba}^{2+}$  ions does

not permit complete filling of the hollandite channels. For  $\text{Ba}^{2+}$ -hollandites, the repulsion between two adjacent  $\text{Ba}^{2+}$  ions is probably another reason why attempts to synthesize stoichiometric Ba-hollandites (such as  $\text{Ba}_2\text{Mg}_2\text{Ti}_6\text{O}_{16}$ ) have so far been unsuccessful.

## 2. Synthesis

The hollandite samples were of composition  $\text{K}_{1.6}\text{Mg}_{0.8}\text{Ti}_{7.2}\text{O}_{16}$  and were obtained from the NASA-Lewis Research Center.

## 3. Evaluation

The hollandite boule was described as polycrystalline with preferred orientation of crystallites with tetragonal c-axes parallel to the boule axis. The resistivity at room temperature measured by dielectric loss on similar material was 80 ohm-cm. On the other hand, the room-temperature resistivity measured with four-probe DC was  $10^4$  to  $10^5$  ohm-cm.

No attempt was made to determine motional narrowing of the potassium NMR spectrum because the nuclear moment is very small and the potassium peak probably would not have been seen above background.

Four hollandite specimens were cut from the boule for conductivity and transport measurements. Each had a cross-sectional area of about  $0.12 \text{ cm}^2$  and was 0.10 cm thick. Two were cut parallel and two were cut perpendicular to the boule axis. Identical results were obtained with the two pairs of duplicate specimens.

The conductivity of hollandite was measured in the Teflon polymer cell. The top trace of Fig. 8 shows the voltage response to an  $18 \mu\text{amp}$ , 200 msec pulse through a solution of 0.05M tetrabutyl ammonium tetrafluoroborate, 0.02M  $\text{KClO}_4$  in propylene carbonate, without an epoxy disk or sample present. The center trace shows the response to the same current pulse with the cell containing the sample of hollandite cut with the conducting tunnels (c-axis) parallel to the pulse direction. Note the well-defined  $iR$  drop upon pulse termination. We have calculated a hollandite ionic conductivity of 200 ohm-cm from these plots after correction was made for the resistance of the propylene carbonate solution.

In contrast, the bottom trace of Fig. 8 shows the cell response when the same current pulse was applied to a hollandite sample in a direction perpendicular to the conducting tunnels. The cell impedance is so high that less than  $1 \mu\text{amp}$  current flows. No sharp  $iR$  drop is seen in the magnified trace because the total cell impedance is so high that the cell responds like a capacitor shunted by a large resistance. Sample resistance perpendicular to the tunnels is estimated to be greater than  $10^5$  ohm-cm from these traces.



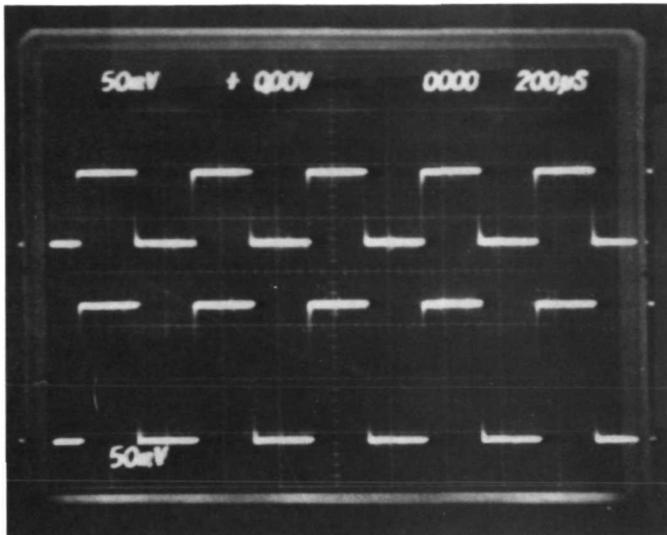


Fig. 8 Hollandite. The upper trace is voltage response with no specimen present:  $18 \mu\text{amp} - 200 \mu\text{sec}$  pulse through  $0.02 \text{ M KClO}_4$ . Middle trace is response to hollandite oriented with tunnels parallel to field. Lower trace is response when tunnels are perpendicular to the field.

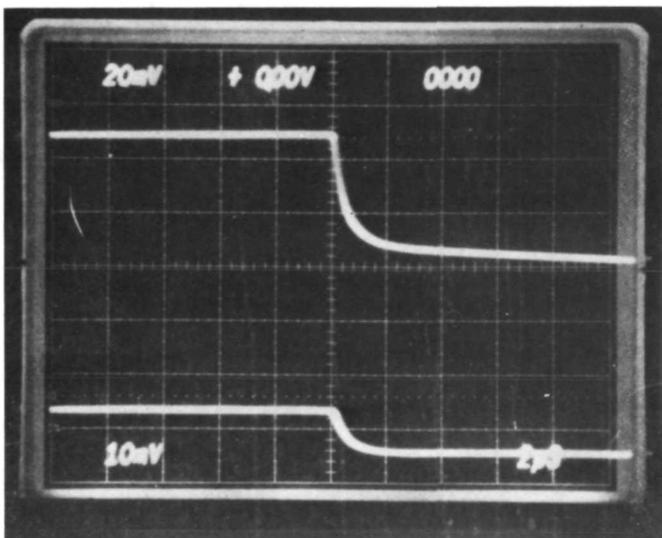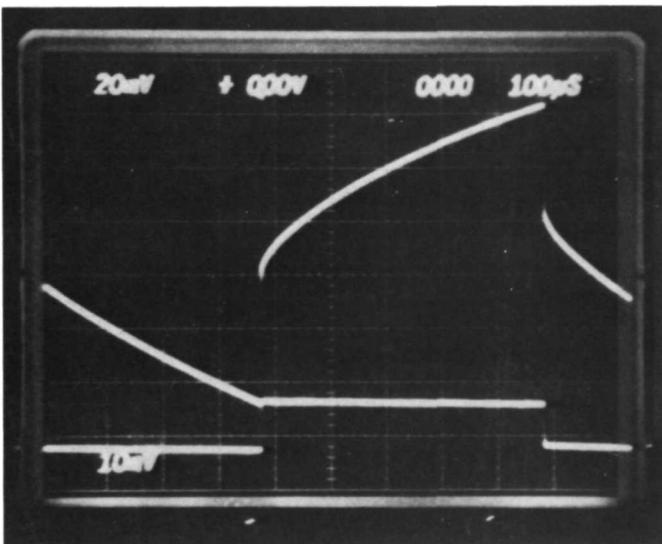

The pulse measurements having shown that there is large ionic conductivity in a direction parallel to the tunnels in hollandite, an attempt next was made to determine the potassium transport down the tunnels.

The hollandite slab was placed between two propylene carbonate solutions, both 0.1 M in tetrabutyl ammonium tetrafluoroborate one saturated with  $\text{KClO}_4$ . The propylene carbonate was dried over activated alumina. The cell was filled in a dry box, then closed tightly to prevent contamination by water before removing for measurement.

The hollandite specimen was polarized between two platinum electrodes maintained at 5V potential difference. The cell developed an initial current greater than  $1 \mu\text{amp}$  which decayed to  $0.09 \mu\text{amp}$  in 5 minutes after transporting a total of  $2.7 \times 10^{-5}$  coulombs. After 20 minutes the current was  $0.05 \mu\text{amp}$  and  $7.4 \times 10^{-5}$  coulombs had been passed. The current continued to decay with time and the experiment was discontinued after one hour 52 minutes when  $i = 0.03 \mu\text{amp}$  and  $Q = 2.3 \times 10^{-4}$  coulombs. Pulse measurements were made in both directions throughout the experiment and we continued to observe the same responses as previously reported. No attempt was made to measure the transport number by analyzing for potassium since the maximum potassium that could have been transferred was only  $2 \times 10^{-9}$  eq.

There are about  $10^{15}$  tunnels per  $\text{cm}^2$  of the c-face of hollandite. The large current that was observed at the beginning of the experiment corresponded to a transport of about  $2 \times 10^{-14}$  coulombs/ $\text{cm}^2$ , approximately equal to that calculated if a few potassium ions entered or left each tunnel. The current then decayed to the relatively small value of  $0.2 \mu\text{amp}/\text{cm}^2$  which may represent migration down the tunnel.

We conclude there is high short-range conductivity in potassium hollandite and this property is measured by both the DC pulse method and by dielectric loss. However, the transport and DC measurements show that long-range conductivity at room temperature is small and probably is determined by the slow migration of potassium ions down the tunnels.

## C. Cordierite-Type Compounds

### 1. Structure and Transport Model

The structure of the mineral cordierite (essentially  $\text{Mg}_2\text{Al}_4\text{Si}_5\text{O}_{18} \cdot x\text{H}_2\text{O}$ ) is another tunnel structure which is of interest as a potential solid electrolyte. The structure was first studied by Byström<sup>(6)</sup> and later by Gibbs,<sup>(7)</sup> Smith and Schreyer.<sup>(8)</sup> It is made up of a three-dimensional tetrahedral network of the composition  $\text{Al}_4\text{Si}_5\text{O}_{18}$ . The  $\text{Mg}^{2+}$  ions occupy octahedral sites, and varying amounts of water are located in the wide channels running parallel to the c-axis. The structure is illustrated in Figs. 9 and 10 giving a good view of the channels which are lined with oxygen ions and have a radius of

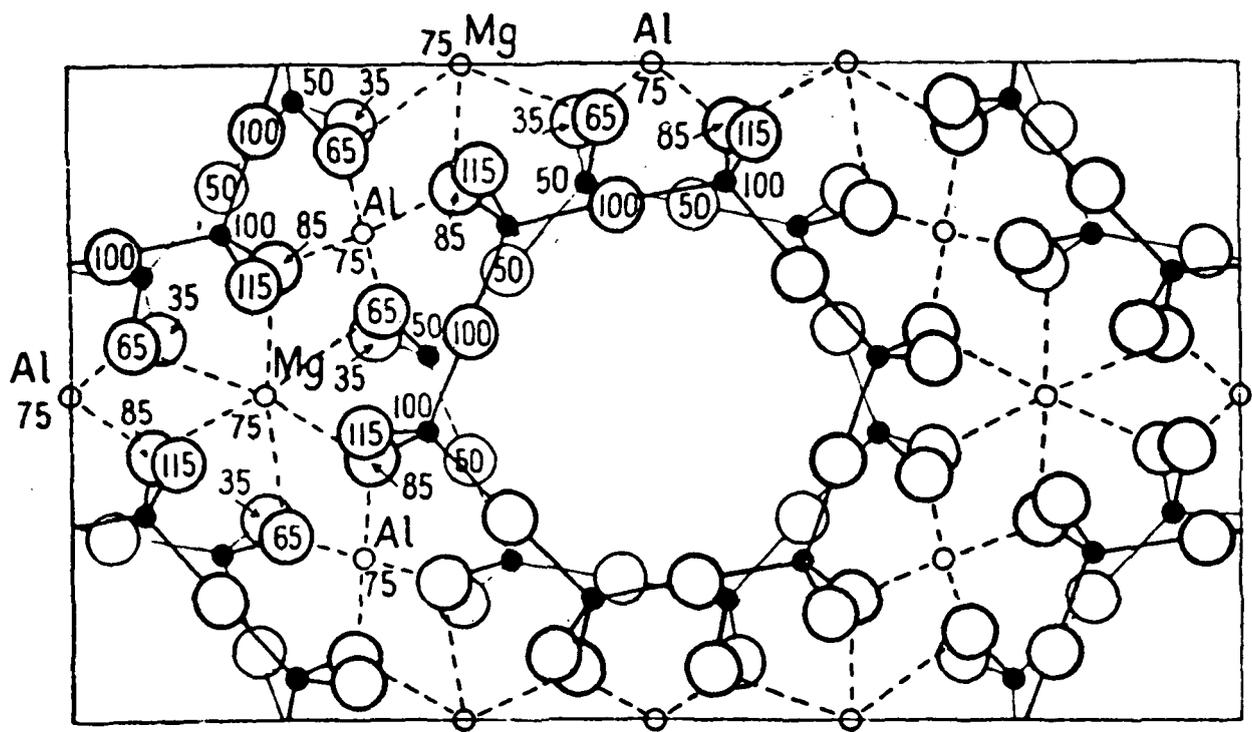


Fig. 9 The structure of cordierite, viewed down the c-axis. After Ref. 6.

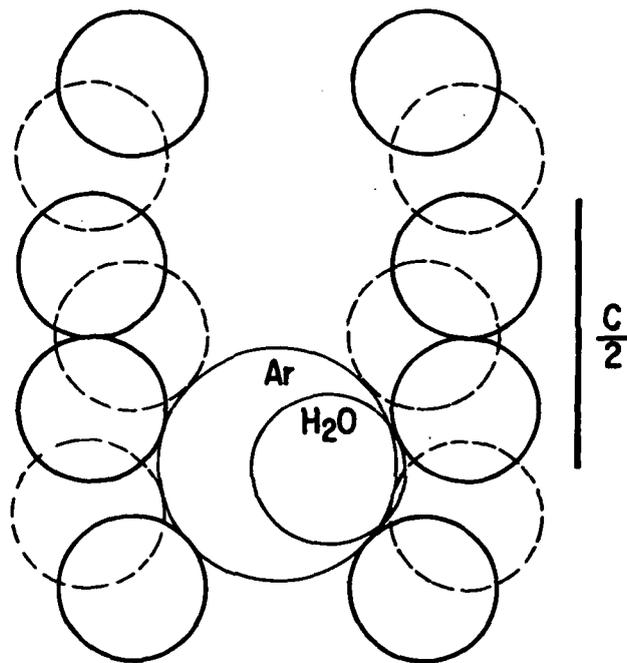


Fig. 10 Cross-sectional view of a tunnel in the cordierite structure. After Ref. 8. Note that the tunnels are large enough to accommodate not only water molecules but even the larger argon atoms with a radius of  $1.92\text{\AA}$ .

1. 4Å at the narrowest neck and 2.2Å at the widest. The channels can be completely free from any water, and in fact, the compound  $Mg_2Al_4Si_5O_{18}$  exists as a stable phase in the ternary system  $MgO-Al_2O_3-SiO_2$ . See W. Schreyer and J. F. Schairer. (9) It is known from the analyses of cordierite minerals and from recent crystal chemical studies that alkali ions such as  $Na^{1+}$  can occupy to some extent the wide channels.  $Na^{1+}$  ions are expected to be too small to occupy the center of the tunnels and would probably be located at the edge of the channels. Larger ions would probably occupy a more central position in the tunnels. It is possible ionic conductivity may result if alkali ions are introduced into these channels. The situation is expected to be especially favorable for  $K^{1+}$  and  $Rb^{1+}$  ions.

Recently cordierites of the compositions  $Na_xMg_2(Al_{4-x}Be_xSi_5O_{18})$  have been synthesized where x can be up to 0.55. Here the substitution  $Al^{3+} = Be^{2+} + Na^{1+}$  was used to introduce substantial amounts of  $Na^{1+}$  into the empty channels. See Provondra and Langer. (10)

## 2. Synthesis

To synthesize alkali-rich cordierites, it was felt best to avoid systems involving the toxic element beryllium, such as the  $Na_xMg_2(Al_{4-x}Be_xSi_5O_{18})$  solid solution series. (10)

We have therefore tried to modify cordierite ( $Mg_2Al_4Si_5O_{18}$ ) by making other substitutions, namely:  $Si^{4+} = Al^{3+} + K^{1+}$ ,  $Si^{4+} = Al^{3+} + Na^{1+}$ ,  $Mg^{2+} = Li^{1+} + K^{1+}$  and  $Mg^{2+} = Li^{1+} + Na^{1+}$ . In the last two cases, the  $Li^{1+}$  ion substitutes for  $Mg^{2+}$  and the larger alkali ions go into the channels. The following cordierite-type compositions were chosen for synthesis:  $Na_{0.2}Mg_2Al_{4.2}Si_{4.8}O_{18}$ ,  $K_{0.2}Mg_2Al_{4.2}Si_{4.8}O_{18}$ ,  $Na_{0.4}Mg_2Al_{4.4}Si_{4.6}O_{18}$ ,  $K_{0.4}Mg_2Al_{4.4}Si_{4.6}O_{18}$ ,  $Rb_{0.4}Mg_2Al_{4.4}Si_{4.6}O_{18}$ ,  $Na_{0.2}Mg_{1.8}Li_{0.2}Al_4Si_5O_{18}$  and  $K_{0.2}Mg_{1.8}Li_{0.2}Al_4Si_5O_{18}$ . The starting materials were  $NH_4Al(SO_4)_2 \cdot 12H_2O$ ,  $MgSO_4$  and the appropriate alkali sulfates. Ammonium stabilized Ludox colloidal silica suspension was used as a source of silica. The sulfates were first dissolved in hot water; then the appropriate amount of Ludox colloidal silica was added. The suspension was heated to dryness (at  $\sim 200^\circ C$ ) in a drying oven and then transferred to a platinum crucible and heated gradually from  $300^\circ$  to  $1200^\circ C$  in a furnace in air. The samples were kept at  $1200^\circ C$  for about 20 minutes and then withdrawn from the furnace. At this stage the samples are fine, white powders which x-ray diffraction indicated is made up of three phases: mullite ( $3Al_2O_3 \cdot SiO_2$ ), sapphirine ( $Mg_7Al_{18}Si_3O_{40}$ ) and cristobalite-related (or carnegieite-like) alkali silicate phases. At this stage no trace of a cordierite phase was detected.

The powders were now heated at  $1560^\circ C$  for 20 minutes in air and cooled. In this way glasses were formed which were devitrified for two days at  $1000^\circ C$ .

The products were then x-rayed with the following results:

<u>Nominal Composition</u>	<u>X-ray Results</u>
$\text{Na}_{0.2}\text{Mg}_2\text{Al}_{4.2}\text{Si}_{4.8}\text{O}_{18}$	100% cordierite. No detectable impurities.
$\text{K}_{0.2}\text{Mg}_2\text{Al}_{4.2}\text{Si}_{4.8}\text{O}_{18}$	98% cordierite. Possible trace (2%) of spinel.
$\text{Na}_{0.2}\text{Mg}_{1.8}\text{Li}_{0.2}\text{Al}_4\text{Si}_5\text{O}_{18}$	~90% cordierite. Some spinel and possibly $\beta$ -spodumene.
$\text{K}_{0.2}\text{Mg}_{1.8}\text{Li}_{0.2}\text{Al}_4\text{Si}_5\text{O}_{18}$	~90% cordierite. Some spinel and possibly $\beta$ -spodumene.
$\text{Na}_{0.4}\text{Mg}_2\text{Al}_{4.4}\text{Si}_{4.6}\text{O}_{18}$	~97% cordierite. Possible trace of $\alpha$ - $\text{Al}_2\text{O}_3$ .
$\text{K}_{0.4}\text{Mg}_2\text{Al}_{4.4}\text{Si}_{4.6}\text{O}_{18}$	~95% cordierite. ~5% $\alpha$ - $\text{Al}_2\text{O}_3$ .

The excess  $\alpha$ - $\text{Al}_2\text{O}_3$  may indicate that the real composition of the solid solution is somewhat below the nominal composition in sodium or potassium. Some sodium or potassium may be lost through volatilization during the firing of the samples, and a chemical analysis will be necessary to determine the real alkali content. Refractive index measurements of both the crystalline and glassy cordierite samples indicate that the alkali substituted cordierites have significantly lower indices than pure crystalline or glassy  $\text{Mg}_2\text{Al}_4\text{Si}_5\text{O}_{18}$ .

For the Rb analogue, significant amounts of a pure, homogeneous glass could not be obtained. In attempting to make such glasses, the reaction was so vigorous that a foamy, porous material was obtained instead of pure glass. The major components of the porous material were glass and crystalline spinel-type  $\text{MgAl}_2\text{O}_4$ . The same type of foaming also occurred in several runs with the Na and K-cordierites, but here such foaming could be avoided by the use of smaller samples.

Our results for the  $\text{Na}^{1+}$  and  $\text{K}^{1+}$  substituted cordierites are encouraging, and indicate that limited substitution of the types:  $\text{Si}^{4+}=\text{Al}^{3+}+\text{K}^{1+}$  or  $\text{Si}^{4+}=\text{Al}^{3+}+\text{Na}^{1+}$  can take place. The possible presence of  $\beta$ -spodumene ( $\text{LiAlSi}_2\text{O}_6$ ) in the  $\text{Li}^{1+}$ -substituted samples, raises some doubt as to whether the substitution  $\text{Mg}^{2+}=\text{Li}^{1+}+\text{Na}^{1+}$  really occurs. The identification of small amounts  $\beta$ -spodumene in these samples must be considered as tentative, since only the most intense  $\beta$ -spodumene-type x-ray peak could be detected.

### 3. Evaluation

Several attempts were made to observe the sodium NMR spectrum in sodium cordierite. The spectra were averaged for 30 to 40 hours and measured at high r-f to increase the sensitivity. In no case was the sodium peak detected above the background. A typical NMR spectrum of Na-cordierite obtained by sweeping through the region expected for the sodium peak is shown in Fig. 11. The failure to detect any sodium could be due to many

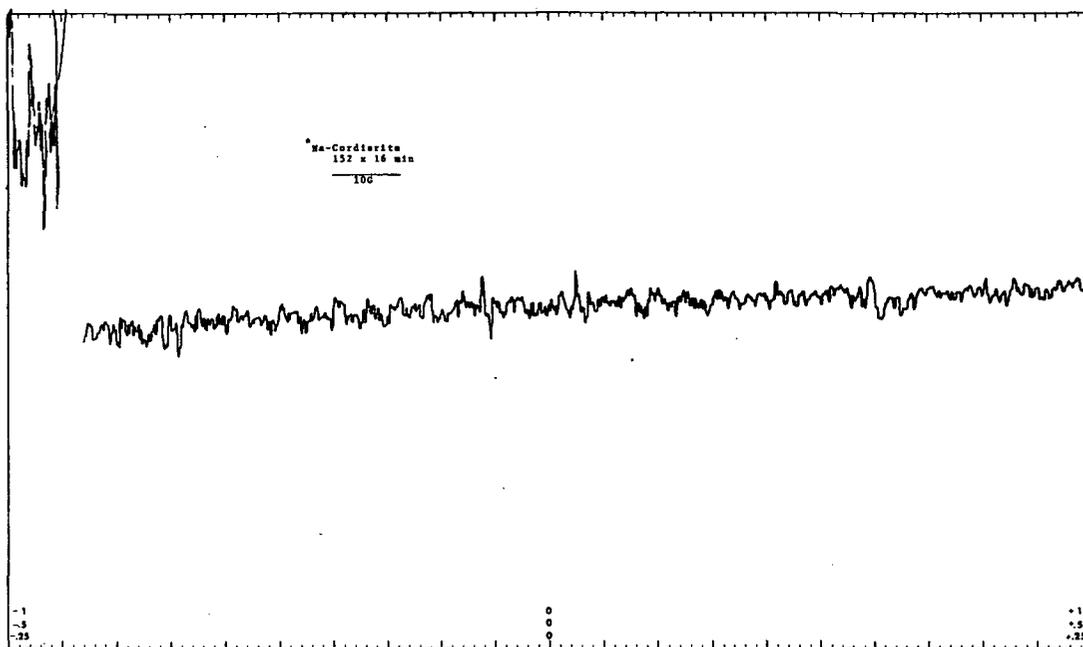


Fig. 11 NMR spectrum of sodium cordierite ( $\text{Na}_{0.4}\text{Mg}_2\text{Al}_{4.4}\text{Si}_{4.6}\text{O}_{18}$ ) at room temperature. The  $^{23}\text{Na}$  spectrum was accumulated for 40 hours.

reasons: low sodium concentration, large quadrupole interactions, and/or the distribution of sodium ions in two or more crystallographic sites.

The response of potassium cordierite ( $\text{K}_{0.2}\text{Mg}_2\text{Al}_{4.2}\text{Si}_{4.8}\text{O}_{18}$ ) was tested in a microcell. The exposed specimen area was a disk with diameter 1.5 mm thickness about 1.5 mm. The shape of the complete pulse and the trailing edge at high resolution is shown in Fig. 12. The small rapid iR drop and the current flow indicates that potassium cordierite is probably a potassium ion conductor. The room-temperature conductivity is small, probably less than potassium hollandite.

The results of the dielectric loss measurements on the cordierite samples are in Table V. None of the materials gave indication of resonance peaks over the temperature range of  $100^\circ$  to  $500^\circ\text{K}$ .

#### D. $\text{NaNbO}_2\text{F}_2$ -Type Compounds

##### 1. Structure and Transport Model

The structure of monoclinic  $\text{NaNbO}_2\text{F}_2$  can be described as a layer structure made up of  $(\text{NbO}_2\text{F}_2)_n^{n-}$  sheets which are held together by  $\text{Na}^{1+}$  ions only. (There are no anion bridges connecting these sheets.)<sup>(11)</sup> The sheets are apparently made up of  $\text{NbO}_4\text{F}_2$  octahedra, linked to each other at the four oxygen corners. The structure is illustrated in Fig. 13. The eight nearest Na-X distances in the irregular  $\text{NaF}_6\text{O}_2$  polyhedron range from

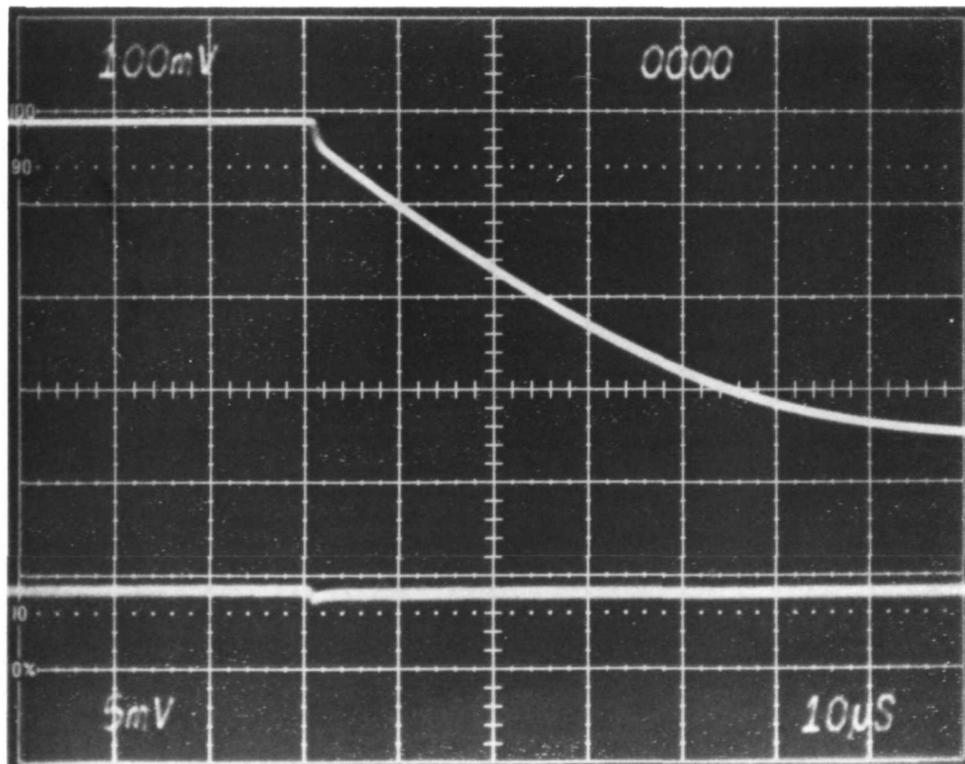
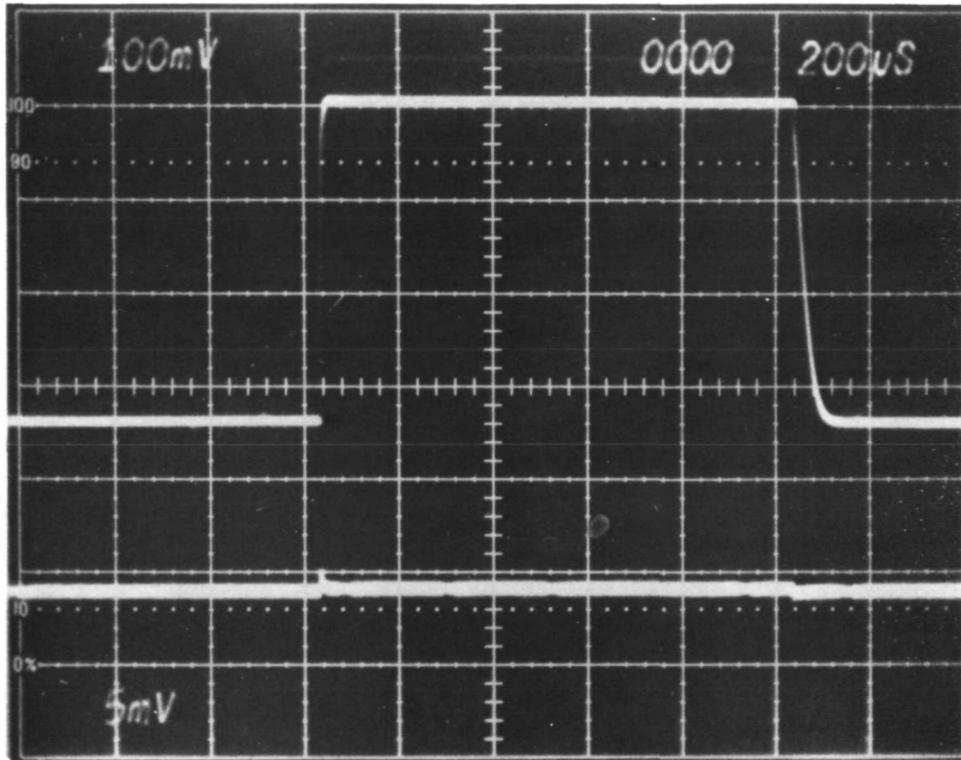


Fig. 12 Voltage response of potassium cordierite in microcell. The trailing edge of the pulse is shown below.

TABLE V

Sample and Composition			Room Temperature Conductivity	
			Frequency (Hz)	ohm <sup>-1</sup> cm <sup>-1</sup>
B42as	K <sub>0.2</sub> Mg <sub>2</sub> Al <sub>4.2</sub> Si <sub>4.8</sub> O <sub>18</sub>	100% cordierite	10 <sup>3</sup>	4.9 × 10 <sup>-10</sup>
			10 <sup>4</sup>	3 × 10 <sup>-9</sup>
			10 <sup>5</sup>	1.8 × 10 <sup>-8</sup>
			10 <sup>6</sup>	1.1 × 10 <sup>-7</sup>
B49as	K <sub>0.4</sub> Mg <sub>2</sub> Al <sub>4.4</sub> Si <sub>4.6</sub> O <sub>18</sub>	95% cordierite; 5% Al <sub>2</sub> O <sub>3</sub>	10 <sup>3</sup>	1.3 × 10 <sup>-9</sup>
			10 <sup>4</sup>	9 × 10 <sup>-9</sup>
			10 <sup>5</sup>	7 × 10 <sup>-8</sup>
			10 <sup>6</sup>	4 × 10 <sup>-7</sup>
B41as	Na <sub>0.2</sub> Mg <sub>2</sub> Al <sub>4.2</sub> Si <sub>4.8</sub> O <sub>18</sub>	100% cordierite	10 <sup>3</sup>	3 × 10 <sup>-10</sup>
			10 <sup>4</sup>	2 × 10 <sup>-9</sup>
			10 <sup>5</sup>	9 × 10 <sup>-9</sup>
			10 <sup>6</sup>	1.2 × 10 <sup>-9</sup>
B48as	Na <sub>0.4</sub> Mg <sub>2</sub> Al <sub>4.4</sub> Si <sub>4.6</sub> O <sub>18</sub>	97% cordierite; 3% Al <sub>2</sub> O <sub>3</sub>	10 <sup>3</sup>	6 × 10 <sup>-10</sup>
			10 <sup>4</sup>	4 × 10 <sup>-9</sup>
			10 <sup>5</sup>	1.5 × 10 <sup>-8</sup>

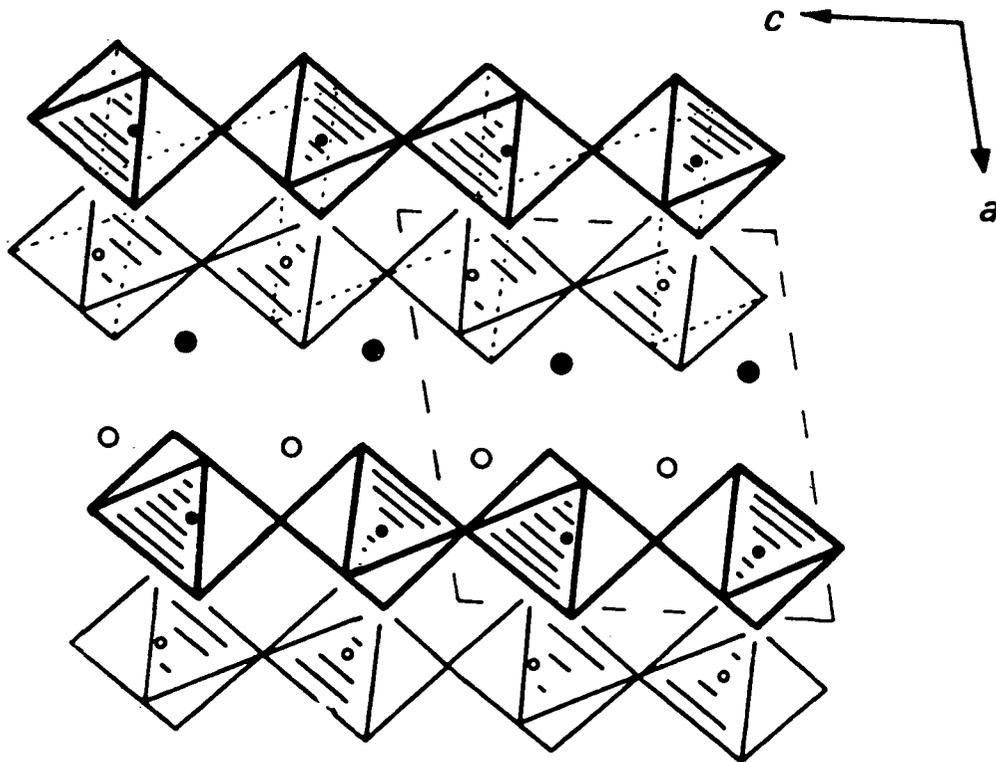



Fig. 13 The structure of NaNbO<sub>2</sub>F<sub>2</sub> projected on the (010) plane. After Ref. 11.

2.22Å to 3.13Å). The isotropic temperature coefficient for  $\text{Na}^{1+}$  ( $B = 2.42$ ) indicates larger than normal thermal vibrations. (11)

We believe that there is a chance of high  $\text{Na}^{1+}$  ion mobility in this structure if vacancies can be introduced into the  $\text{Na}^{1+}$  sites. For this purpose, the composition of  $\text{NaNbO}_2\text{F}_2$  could be modified by changing the O/F ratio or introducing hexavalent ions into the octahedral site, e.g.,  $\text{Mo}^{6+}$  or  $\text{W}^{6+}$ . One could similarly try to modify the composition of  $\text{NaNbO}_2\text{F}_2$  by substituting  $\text{Ca}^{2+}$ ,  $\text{Sr}^{2+}$ ,  $\text{Pb}^{2+}$ ,  $\text{Y}^{3+}$  or  $\text{Nd}^{3+}$  ions for  $\text{Na}^{1+}$ .

## 2. Synthesis

There is probably little chance of  $\text{Na}^{1+}$  ion conduction in stoichiometric  $\text{NaNbO}_2\text{F}_2$ . With a view of making sodium-deficient  $\text{NaNbO}_2\text{F}_2$  phases, the following reactions were tried:



For most chemicals, reagent grade starting materials were used, but  $\text{NbO}_2\text{F}$  had to be prepared according to the following procedure:

Optical grade  $\text{Nb}_2\text{O}_5$  (99.95%) was dissolved in concentrated hydrofluoric acid in a platinum crucible. The resulting solution was filtered and the clear solution was evaporated to dryness. The powder was heated for one day under vacuum at 220°C. The resulting dry powder was pure  $\text{NbO}_2\text{F}$ , with no impurity peaks detectable in the x-ray pattern.

The starting materials were dried under vacuum at 220°C, weighed out in the appropriate ratio, mixed, and pressed into pellets. The pellets were loaded into platinum crucibles, heated at 400°C under vacuum for 1 hour and then sealed. The crucibles were then heated at 600°C for 2 hours to 1 day. Some mixtures were also heat-treated at 700°C for 1/2 day.

Although stoichiometric  $\text{NaNbO}_2\text{F}_2$  could be made in reasonably pure form, there was no evidence for the existence of the defect solid solutions, no matter what heat treatment was used. It appears that the hoped-for solid solutions do not form, and instead new phases appear. Efforts were made to

identify these new phases and for some compositions a tentative interpretation is given below.

X-ray patterns for the Mo and W-substituted phases give a two-phase mixture of  $\text{NaNbO}_2\text{F}_2$  and substantial amounts of an unknown phase. The x-ray patterns for  $\text{Na}_{0.7}\text{Y}_{0.1}\text{NbO}_2\text{F}_2$ ,  $\text{Na}_{0.7}\text{Nd}_{0.1}\text{NbO}_2\text{F}_2$  and  $\text{Na}_{0.8}\text{Ca}_{0.1}\text{NbO}_2\text{F}_2$  bear a strong resemblance to each other and may belong to the same structure type. These patterns could not be identified with any known Na-Nb compounds. However, a study of various sodium tantalum oxyfluorides has been published recently<sup>(12)</sup> and from the given cell constants for these tantalum oxyfluorides we calculated x-ray powder patterns. We found that the major x-ray peaks of  $\text{Na}_{0.7}\text{Y}_{0.1}\text{NbO}_2\text{F}_2$ ,  $\text{Na}_{0.7}\text{Nd}_{0.1}\text{NbO}_2\text{F}_2$  and  $\text{Na}_{0.8}\text{Ca}_{0.1}\text{NbO}_2\text{F}_2$  can be indexed on the basis of the  $\text{Na}_2\text{Ta}_3\text{O}_6\text{F}_5$ -type unit cell. Similarly, the patterns of  $\text{Na}_{0.8}\text{Sr}_{0.1}\text{NbO}_2\text{F}_2$  and  $\text{Na}_{0.9}\text{NbO}_2\text{F}_{1.9}$  can be indexed for the most part on the basis of the  $\text{Na}_4\text{Ta}_5\text{O}_{10}\text{F}_9$ -type unit cell. These two structure types are unknown and their x-ray patterns have not been published; therefore, the tentative identifications made above are speculative. The x-ray pattern for  $\text{Na}_{0.8}\text{Pb}_{0.1}\text{NbO}_2\text{F}_2$  is different from the others but bears some resemblance to that of  $\text{Na}_{0.8}\text{Sr}_{0.1}\text{NbO}_2\text{F}_2$ . It seems that the  $\text{NaNbO}_2\text{F}_2$  structure does not tolerate defect solid solutions and that new structure types appear if the Na/Nb ratio is lowered.

### 3. Evaluation

The sodium and fluorine NMR spectrum in  $\text{Na}_{0.8}\text{Sr}_{0.1}\text{NbO}_2\text{F}_2$  were measured at room temperature and  $186^\circ\text{C}$  (Figs. 14a, b). The peak-to-peak line widths were broad (about 8 gauss) and no motional narrowing was observed over this temperature range.


The ionic conductivity of the pure and doped  $\text{NaNbO}_2\text{F}_2$  specimens could not be measured because they were too porous. The dielectric loss and AC conductivity results are given in Table VI.

## E. Phases with a Defect Perovskite Structure


### 1. Structure and Transport Model

The well-known perovskite structure is illustrated in Fig. 15 for the idealized cubic form.

Normally the perovskite structure would not be considered as a good candidate for high cationic conductivity. In this  $\text{ABX}_3$  structure, the large A-cations are 12-coordinated and form together with the X-anions cubic close-packed layers perpendicular to the cubic [111] directions. In this close-packed array, the B-cations occupy octahedral interstices. In stoichiometric  $\text{ABX}_3$  perovskites, such as  $\text{SrTiO}_3$  or  $\text{KNbO}_3$ , the high packing efficiency and lack of open channels would rule out any high cationic

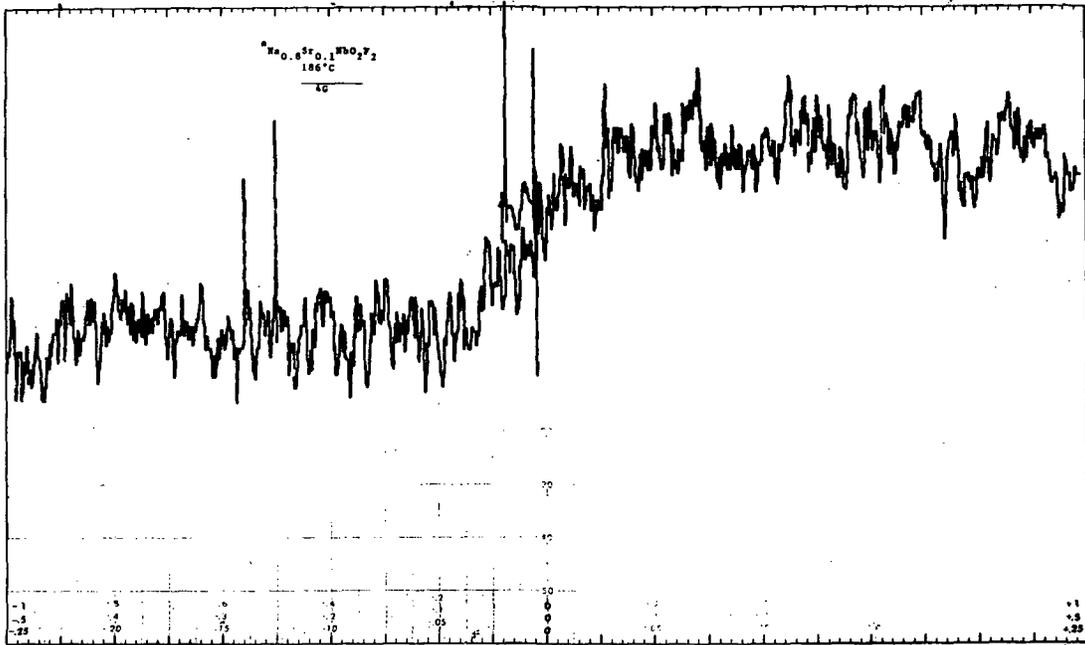

(a)

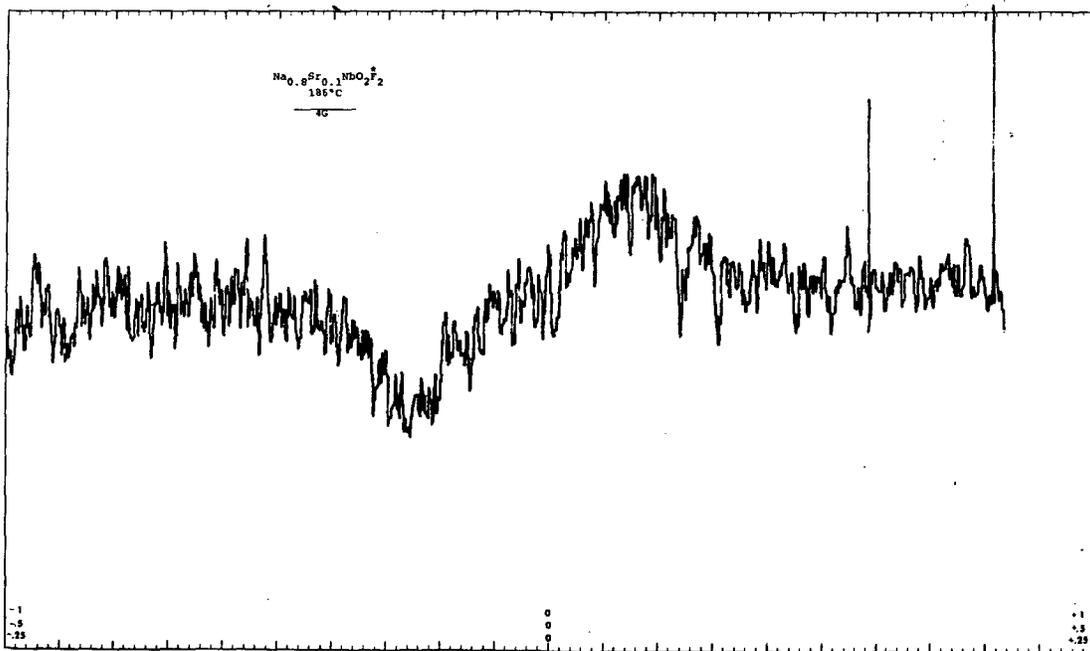

(b)

Fig. 14 (a) NMR spectrum of  $^{23}\text{Na}$  in  $\text{Na}_{0.8}\text{Sr}_{0.1}\text{NbO}_2\text{F}_2$  at  $186^\circ\text{C}$ .  
 (b) Spectrum of  $^{19}\text{F}$ .

TABLE VI

Sample	Additive	Resonance Peak	AC Conductivity at Room Temp. ( $\text{ohm}^{-1} \text{cm}^{-1}$ )	
C-12 b		Yes $\Delta E < 1$ kcal (must be electron blocking with $\rho_{\text{elect}} \geq 10^8$ )	$10^3 \text{Hz}$	$2 \times 10^{-9}$
			$10^4$	$1 \times 10^{-8}$
			$10^5$	$4 \times 10^{-8}$
			$10^6$	$1 \times 10^{-7}$
C-18	Y	No	$10^3$	$1.9 \times 10^{-10}$
			$10^4$	$1.5 \times 10^{-9}$
			$10^5$	$2 \times 10^{-8}$
			$10^6$	$3 \times 10^{-7}$
C-19	Nd	No	$10^3$	$2 \times 10^{-9}$
			$10^4$	$1.4 \times 10^{-8}$
			$10^5$	$9 \times 10^{-8}$
			$10^6$	$4 \times 10^{-7}$
C-20	Ca	No	$10^3$	$8 \times 10^{-10}$
			$10^4$	$3 \times 10^{-9}$
			$10^5$	$3 \times 10^{-8}$
			$10^6$	$3 \times 10^{-7}$
C-21	Sr	Yes $\Delta E \sim 8.1$ kcal mol $^{-1}$ $\rho_{25^\circ} \sim 6 \times 10^6$ ohm-cm	$10^3$	$1.3 \times 10^{-8}$
			$10^4$	$9 \times 10^{-8}$
			$10^5$	$3 \times 10^{-7}$
			$10^6$	$8 \times 10^{-7}$
C-22	Pb	No	$10^3$	$5.7 \times 10^{-10}$
			$10^4$	$2.5 \times 10^{-9}$
			$10^5$	$1.5 \times 10^{-8}$
			$10^6$	$4 \times 10^{-8}$

mobility. Even if the structure is made nonstoichiometric by creating vacancies in the A-site, one would not normally expect these large A-cations to move easily to the vacant sites because the constrictions which separate the A-sites are too narrow.

However, these objections can be partly overcome when we consider non-stoichiometric variants of the known cubic perovskite  $\text{La}_{0.5}\text{Li}_{0.5}\text{TiO}_3$  ( $a_0 = 3.861\text{\AA}$ )(13). Here  $\text{Li}^{1+}$  apparently occupies (randomly with  $\text{La}^{3+}$ ) the 12-coordinated A-site with twelve very large Li-O distances of  $2.73\text{\AA}$ . It is very unusual for an intermediate size cation such  $\text{Li}^{1+}$  to occupy a 12-coordinated site with such very large Li-O separations. More typical Li-O distances are of the order  $1.95\text{\AA}$  to  $2.30\text{\AA}$ .

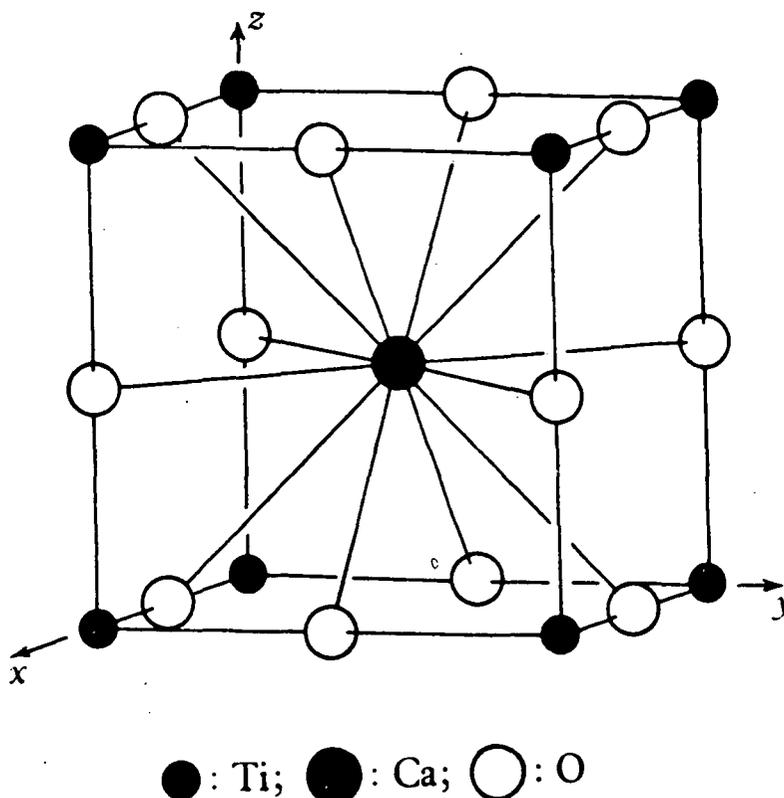


Fig. 15 The ideal or cubic perovskite structure.

It was hoped that vacancies can be induced in this perovskite to provide for cation motion. This could be done by substituting a stable pentavalent ion such as  $\text{Nb}^{5+}$  or  $\text{Ta}^{5+}$  for tetravalent Ti. We could thus envision a cubic perovskite of composition  $(\text{La}_{0.5}\text{Li}_{0.3}\square_{0.2})^{\text{XII}}(\text{Ti}_{0.8}\text{Ta}_{0.2})^{\text{VI}}\text{O}_3$ , where the introduction of 20% vacancies into the A-site could result in high lithium ion mobility. For this study it is especially significant that a cubic perovskite of composition  $(\text{La}_{2/3}\square_{1/3})\text{TiO}_3$  can be very closely approached, (13-17) and that here density measurements definitely indicate vacancies in the A-site. (16)


The greatest stumbling block toward high  $\text{Li}^{1+}$  mobility in a perovskite such as  $(\text{La}_{0.5}\text{Li}_{0.3}\square_{0.2})^{\text{XII}}(\text{Ti}_{0.8}\text{Ta}_{0.2})^{\text{VI}}\text{O}_3$  is perhaps the narrow constriction through which the  $\text{Li}^{1+}$  ion must move to go from one A-site to one of the six neighboring A-sites. (On the average, about one of these six A-sites would be vacant.) At its closest approach to the other ions,  $\text{Li}^{1+}$  will be surrounded by four square planar oxygens at a distance of  $1.93\text{\AA}$  and four square planar  $\text{Ti}^{4+}$  (or  $\text{Ta}^{5+}$ ) ions at a distance of  $2.73\text{\AA}$ . However, this short Li-O bond is still within the range of typical 4-coordinated Li-O distances:  $1.86\text{\AA}$  to  $2.05\text{\AA}$  according to the International Tables for X-ray Crystallography. The motion of  $\text{Li}^{1+}$  ions through this constriction would therefore be possible, but not easy.

The phase diagram for the ternary system  $\text{Li}_2\text{O}-\text{La}_2\text{O}_3-\text{TiO}_2$  has not been established and of the binaries, only the system  $\text{La}_2\text{O}_3-\text{TiO}_2$  has been studied over the entire range. (18) However, fragmentary data are available on the other two binary systems.

Recently cubic perovskites were found in the system  $\text{Y}_x(\text{Ta}_{3x}\text{W}_{1-3x})\text{O}_3$  (19) over a narrow composition range  $0.20 < x < 0.24$ . We have investigated the possibility of using such a cubic perovskite--e. g.,  $\text{Ca}_{0.78}\text{Y}_{0.22}(\text{Ta}_{0.66}\text{W}_{0.34})\text{O}_3$ -- as a base for introducing small amounts of Li and Na in the 12-coordinated site.

## 2. Synthesis

For the titanium-perovskites, the following compositions were attempted:



$\text{Li}_2\text{CO}_3$ ,  $\text{Na}_2\text{CO}_3$ ,  $\text{Ta}_2\text{O}_5$ ,  $\text{TiO}_2$ ,  $\text{La}_2\text{O}_3$ , and  $\text{Nd}_2\text{O}_3$  were intimately mixed in the appropriate ratios. In the attempted synthesis, two approaches were used:


1. The mixes were loaded into platinum boats and heated at  $1200^\circ\text{C}$  for 2 hours. Then the samples were withdrawn from the furnace and cooled in air.

2. The mixtures were dissolved in concentrated nitric acid. The resulting solution was heated to dryness in platinum crucibles. The crucibles were then transferred to a muffle furnace and heated very gradually from  $300^\circ$  to  $1200^\circ\text{C}$ . The temperature was maintained at  $1200^\circ\text{C}$  for 2 hours and the crucibles were subsequently quenched by quickly immersing them in cold water.

Neither of the two methods of synthesis resulted in the hoped for cubic defect perovskite. Instead, a birefringent product was obtained in all cases.

The complex x-ray patterns of the products have not yet been interpreted completely, but the more intense x-ray peaks are near the peak positions expected for a cubic perovskite. It appears that the products may be ordered, distorted perovskites.

For the tantalum-tungsten perovskites, the oxides were mixed as shown in the equation below:



To make the Na-analogue,  $\text{Na}_2\text{WO}_4 \cdot 2\text{H}_2\text{O}$  was substituted for  $\text{Li}_2\text{WO}_4$ . These two mixtures were pressed into pellets and reacted for one-half hour at  $1200^\circ\text{C}$ . In a modification of the above procedure, the samples were sealed into platinum tubing, heated at  $1400^\circ\text{C}$  for about one hour, and then quickly withdrawn and quenched in cold water.

None of the resulting products appeared to be of the cubic perovskite type. All samples were birefringent with a more complex perovskite-related x-ray pattern.

It appears that for all the attempted perovskites, the undistorted cubic structure could not be obtained. The distorted (and ordered) perovskites which were apparently formed would not be considered good candidates for cationic conductivity since the structural perovskite-like framework has probably collapsed around the small  $\text{Li}^{1+}$  or  $\text{Na}^{1+}$  sites, making ionic mobility of these ions less likely.

### 3. Evaluation

The two Ta-W perovskite-type samples were evaluated by dielectric loss. No loss peaks were observed and it is unlikely that these materials are good ionic conductors at low temperature. As pointed out in Section 2, we attribute the absence of conductivity to the collapse of the perovskite-like framework around the small monovalent cations.

## F. Sodium Tungsten Bronze-type Compounds

### 1. Structure and Transport Model

A considerable effort was made last year in attempts to determine the ionic transport in nonstoichiometric lithium vanadates which are mixed electronic-ionic conductors. Since the differentiation of electron and ion charge carriers is a problem requiring investigation in all solid conductors, it was desirable to observe the nature of the response of our newly developed fast-pulse technique to materials of that kind. Sodium tungsten bronze was chosen for the test instead of lithium vanadate because large single crystals were available.

The  $\text{Na}_{0.9}\text{WO}_3$  structure is essentially a slightly distorted version of the ideal (cubic) perovskite structure shown in Fig. 15. 10% of the Na sites are vacant, and some degree of ionic motion might therefore be possible. Such ionic motion would be difficult to detect by conventional conductivity measurements, due to the very high electronic conduction.

### 2. Sample Preparation

An electrolytically grown single crystal of  $\text{Na}_{0.9}\text{WO}_3$  was obtained from Dr. R. C. DeVries of the General Electric Company. From a larger single

crystal, a smaller piece was cut for the cell measurements described below.

### 3. Evaluation

The sodium tungsten bronze crystal was cut parallel to one of the pseudo-cubic crystal axes and mounted in a microcell. The conducting surface was a circular area 1.0 mm in diameter and the crystal was 1.2 mm thick. The response of the cell to pulses of long and short duration is shown in Fig. 16. A large current flow is observed, and in addition, a slow, capacitive-like charge and decay extending for approximately 20  $\mu$ sec. The capacitive-like behavior was not observed when platinum was substituted for the sodium tungsten bronze and, therefore, it is unlikely the slow processes are due to polarization at the interface. The observations suggest there may be a threshold for current flow, possibly related to the displacement of sodium ions in the tunnels.

## G. NaLiGe<sub>4</sub>O<sub>9</sub>-Type Compounds

### 1. Structure and Transport Model

The structure of the orthorhombic NaLiGe<sub>4</sub>O<sub>9</sub><sup>(20)</sup> is illustrated in Fig. 17 and consists of (GeO<sub>3</sub>)<sub>n</sub><sup>2n-</sup> chains made up of GeO<sub>4</sub> tetrahedra sharing corners. These chains are connected by GeO<sub>6</sub> octahedra to form a three-dimensional framework. This framework gives rise to interwoven tunnels which are occupied by Na<sup>+</sup> and Li<sup>+</sup> ions. The tunnels might be sufficiently wide to permit some alkali ion motion in three dimensions. The most promising ionic conductors are perhaps the nonstoichiometric variants where vacancies in the alkali ion positions are created by substituting pentavalent ions for Ge<sup>4+</sup>, either in the octahedral site (Nb<sup>5+</sup>, Ta<sup>5+</sup>, Sb<sup>5+</sup>) or tetrahedral site (V<sup>5+</sup>). However, some ionic motion may take place even in the stoichiometric Li<sub>2</sub>Ge<sub>4</sub>O<sub>9</sub> along interstitial sites.

In their regular sites, Li<sup>1+</sup> ions are 5-coordinated with Li-O bonds at 1.827Å to 2.397Å at the corners of a square pyramid. Actually this Li<sup>1+</sup> ion is distributed randomly over two equivalent sites 0.6Å apart, and there is a good chance that dynamic exchange between these two places may occur, which would enhance the likelihood of Li<sup>1+</sup> ion mobility along the channels.

Na<sup>1+</sup> ions occupy six-coordinated sites in different channels than the Li<sup>1+</sup> ions, with Na-O distances ranging from 2.326Å to 2.900Å. This Na<sup>1+</sup> ion can be completely replaced with Li<sup>1+</sup> to form the end member Li<sub>2</sub>Ge<sub>4</sub>O<sub>9</sub>. If the Li<sup>+</sup> ions were to occupy exactly the same site as Na<sup>1+</sup> ions, there would be six very large Li-O distances (2.55Å on the average). It has been postulated<sup>(20)</sup> (but not proved) that Li<sup>1+</sup> would prefer a different site (removed by 1/2 b<sub>0</sub> = 2.31Å) along the same channel which would yield six shorter Li-O distances (2.26Å), on the average. Since Li<sup>1+</sup> ions have a low scattering

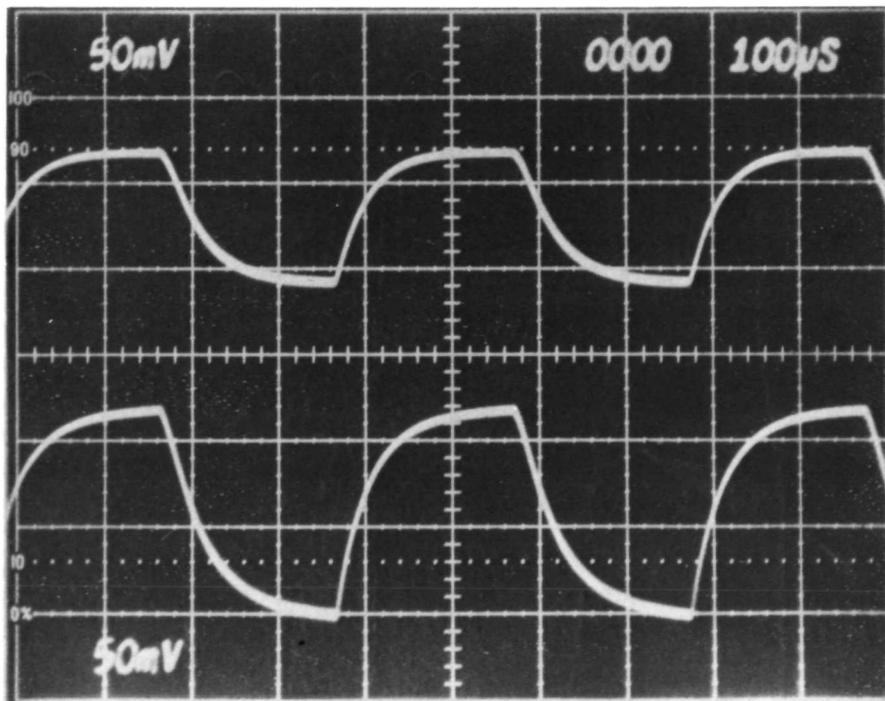
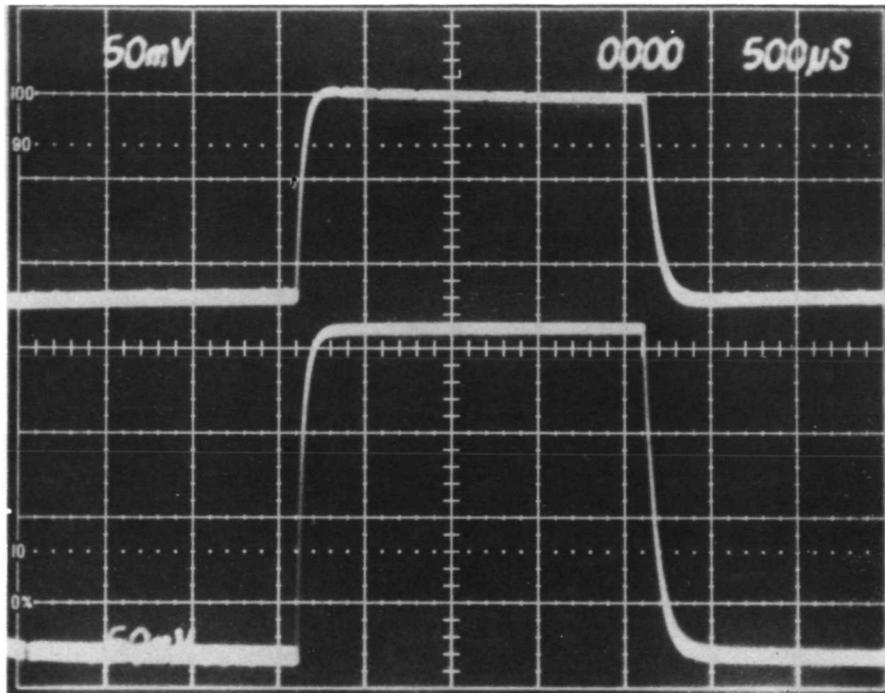


Fig. 16 Voltage response of sodium tungsten bronze crystal to constant current pulse. Above, 250  $\mu$ sec pulse; below, 20  $\mu$ sec pulse.

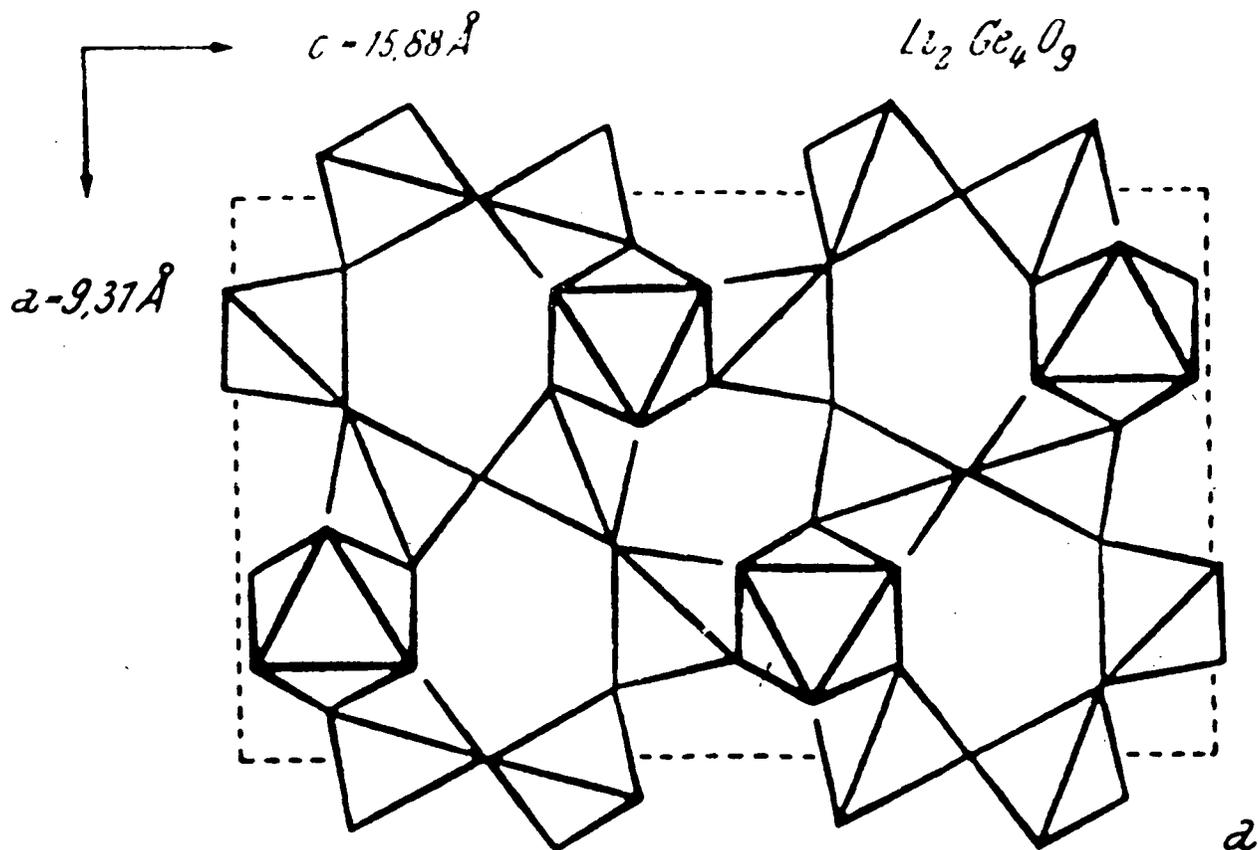


Fig. 17 The framework of interlinked  $\text{GeO}_4$  tetrahedra and  $\text{GeO}_6$  octahedra in the  $\text{NaLiGe}_4\text{O}_9$  structure. After Ref. 23.

factor and cannot be easily placed by x-ray diffraction study, there is some uncertainty regarding the sites occupied by  $\text{Li}^{1+}$  ions in  $\text{Li}_2\text{Ge}_4\text{O}_9$ . However, the intensity agreement is a little better if  $\text{Li}^{1+}$  ions are placed in the site giving shorter Li-O bonds. It seems possible, however, that both sites could be partially occupied, a factor that might enhance ionic mobility.

## 2. Synthesis

A phase equilibrium diagram is available for the system  $\text{Li}_2\text{O}-\text{GeO}_2$ , (21) however, it is partly incorrect in the region of interest. (22) Since glasses can be quenched from the  $\text{Li}_2\text{O}-\text{GeO}_2$  melt, it was decided to synthesize and examine both glassy and crystalline samples.

Several glasses near the  $\text{Li}_2\text{Ge}_4\text{O}_9$  composition have been prepared:  $\text{Li}_2\text{Ge}_4\text{O}_9$ ,  $\text{NaLiGe}_4\text{O}_9$ ,  $\text{Li}_{1.7}\text{Ge}_{3.7}\text{Nb}_{0.3}\text{O}_9$ ,  $\text{Li}_{1.7}\text{Ge}_{3.7}\text{Ta}_{0.3}\text{O}_9$ ,  $\text{Li}_{1.7}\text{Ge}_{3.7}\text{Sb}_{0.3}\text{O}_9$  and  $\text{Li}_{1.7}\text{Ge}_{3.7}\text{V}_{0.3}\text{O}_9$ . To synthesize these glasses, the appropriate amounts of  $\text{GeO}_2$  and  $\text{Li}_2\text{CO}_3$  (or  $\text{Na}_2\text{CO}_3$ ) were intimately mixed and heated in air at  $900^\circ\text{C}$  in a platinum crucible. The resulting powder was then mixed with appropriate amounts of the other oxides ( $\text{Nb}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5$ ,  $\text{Sb}_2\text{O}_5$  and  $\text{V}_2\text{O}_5$ ).

The powders were loaded into platinum capsules and sealed. The sample capsules were heated at 1200°C for 1/2 hour and then quenched by quickly immersing them into cold water. The quench rate must be quite rapid or partial crystallization occurs. If larger mixtures of powder are heated in a platinum crucible, a clear glass cannot be quenched from 1200°C due to partial crystallization on cooling. In such cases clear glasses could be recovered only as a skin near the platinum wall. The glasses were homogeneous, clear, and colorless, except for the V<sup>5+</sup>-substituted glass which was amber-colored. The glasses were checked microscopically for homogeneity by observing the refractive index.

Initially some problems were encountered in the attempted synthesis of crystalline Li<sub>2</sub>Ge<sub>4</sub>O<sub>9</sub> and substituted variants. When the starting materials were heated at various temperatures below 1200°C, the resulting Li<sub>2</sub>Ge<sub>4</sub>O<sub>9</sub> phase was impure and x-ray analysis indicated the presence of significant amounts of Li<sub>2</sub>GeO<sub>3</sub>, Li<sub>2</sub>Ge<sub>7</sub>O<sub>15</sub> and GeO<sub>2</sub>. Purer crystalline products could be obtained by heating the glasses, described above, in sealed platinum tubes, at 650° to 700°C for several days. The crystalline products thus obtained gave the expected x-ray pattern for stoichiometric Li<sub>2</sub>Ge<sub>4</sub>O<sub>9</sub> free from impurity peaks. For compositions Li<sub>1.7</sub>Ge<sub>3.7</sub>Ta<sub>0.3</sub>O<sub>9</sub> and Li<sub>1.7</sub>Ge<sub>3.7</sub>Nb<sub>0.3</sub>O<sub>9</sub> impurities of the Li<sub>2</sub>Ge<sub>7</sub>O<sub>15</sub> phase (5% to 15%) were detected.

For the composition NaLiGe<sub>4</sub>O<sub>9</sub> a pure crystalline material could be prepared by either of two methods:

(a) Heating NaLiGe<sub>4</sub>O<sub>9</sub> glass at 700°C for several days. This results in a very finely crystallized sample.

(b) Heating the appropriate amounts of Na<sub>2</sub>CO<sub>3</sub> and GeO<sub>2</sub> slowly in a platinum crucible to 1200°C, and then withdrawing the crucible and letting it cool in air. This gives a coarsely crystallized material.

### 3. Evaluation

The compositions Li<sub>2</sub>Ge<sub>4</sub>O<sub>9</sub> and NaLiGe<sub>4</sub>O<sub>9</sub> were prepared as glasses and screened by NMR for cation mobility at room temperature. The glasses were then devitrified and NMR screening repeated on the crystalline phases. The NMR results are summarized in Table VII.

There is strong motional narrowing of the lithium resonance in the glass form of Li<sub>2</sub>Ge<sub>4</sub>O<sub>9</sub>. The peak width at room temperature (Fig. 18) is only 1.4 gauss and it narrows further to 0.4 gauss at 153°C. The lithium spectrum in the crystallized compound is nearly the same at room temperature (Fig. 19), but at 115°C the spectrum is resolved into two peaks: one with width 1.5 gauss, the second 0.35 gauss. This agrees with the prediction made on the basis of structural considerations that lithium atoms might occupy two different crystallographic sites. The latter motionally narrowed peak is probably due to lithium ions with large Li-O distances which have replaced the sodium in the 6-fold sites occupied by Na in NaLiGe<sub>4</sub>O<sub>9</sub>.

TABLE VII

NMR Spectra of  ${}^7\text{Li}$  in  $\text{Li}_2\text{Ge}_4\text{O}_9$  Compounds

<u>Material</u>	<u>Phase</u>	<u>Temp (°C)</u>	<u>Line Width (Gauss)</u>
$\text{Li}_2\text{Ge}_4\text{O}_9$	Glass	-100	1.9
		22	1.4
		120	0.8
		163	0.4
$\text{Li}_2\text{Ge}_4\text{O}_9$	Polycrystal	22	1.5
		115	{ 0.35 and 1.5
$\text{NaLiGe}_4\text{O}_9$	Glass	-34	1.6
		22	1.6
		95	1.6
	Polycrystal	22	1.3
		115	1.3

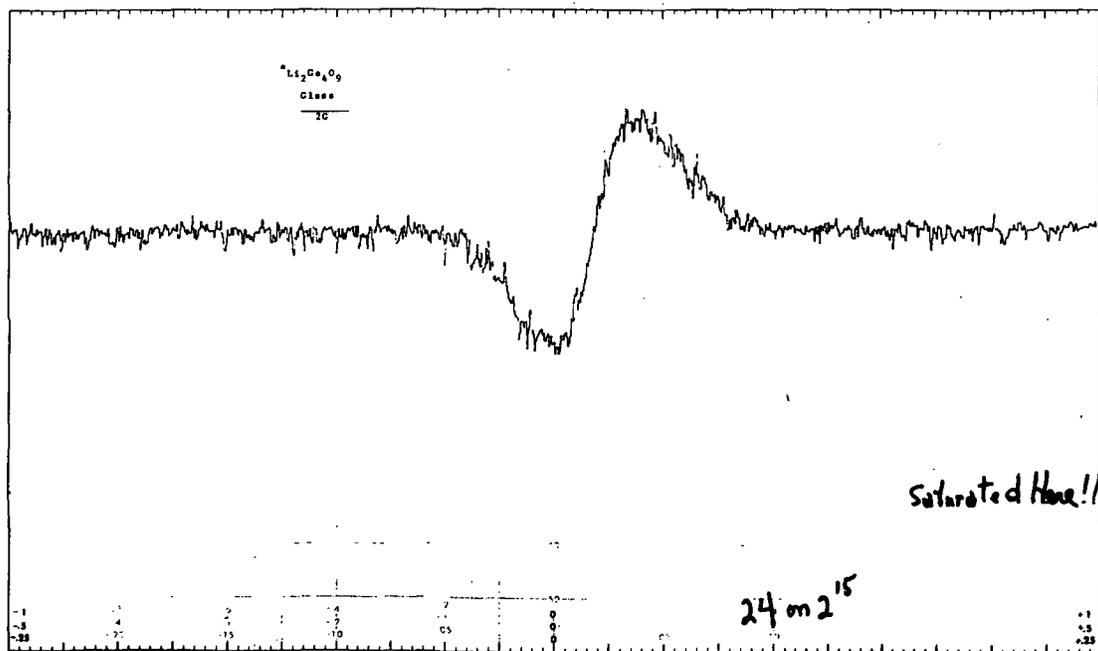


Fig. 18 NMR spectrum of  ${}^7\text{Li}$  in glass with composition  $\text{Li}_2\text{Ge}_4\text{O}_9$  at room temperature. The peak width is 1.4 gauss.

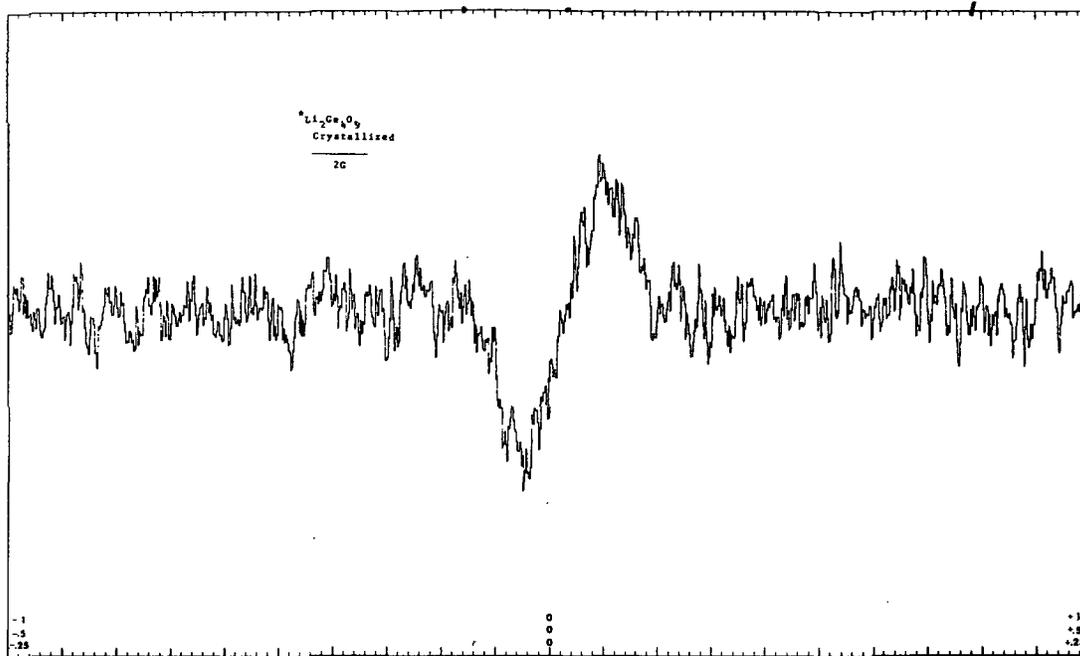


Fig. 19 NMR spectrum of  ${}^7\text{Li}$  in crystalline  $\text{Li}_2\text{Ge}_4\text{O}_9$  at room temperature. The peak width is 1.5 gauss.

Motional narrowing of the lithium NMR spectrum was not observed either in the glass or in the crystalline phases of  $\text{NaLiGe}_4\text{O}_9$  (Figs. 20 and 21). This is consistent with the structural interpretation suggested to explain the  $\text{Li}_2\text{Ge}_4\text{O}_9$  spectra because sodium ions are significantly larger than lithium ions. The sodium spectrum could not be detected despite prolonged signal averaging (25 hours). This indicates the spectrum is broadened by the crystalline fields, and the sodium ions are relatively immobile.

The pulse shape in one specimen of  $\text{Li}_2\text{Ge}_4\text{O}_9$  glass was successfully observed in a microcell. Attempts to measure the other compositions failed because the materials cracked and developed leaks when they were helium tested. The glass was 0.24 mm thick with an effective cross section of  $2.5 \times 3.5$  mm. The cell response indicated the conductivity is small, in agreement with dielectric loss measurements made at NASA-Lewis Research Center. No resonance peaks were observed and the room-temperature AC conductivity was  $4 \times 10^{-10}$  at  $10^3$  Hz and  $2 \times 10^{-7}$   $\text{ohm}^{-1} \text{cm}^{-1}$  at  $10^6$  Hz.

## H. $\text{Li}_2\text{Ge}_7\text{O}_{15}$ -Type Compounds

### 1. Structure and Transport Model

The structure of  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ <sup>(23)</sup> is related to the  $\text{NaLiGe}_4\text{O}_9$  type discussed above. In  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ ,  $\text{GeO}_4$  tetrahedra are linked together at the corners to form corrugated layers which are connected by  $\text{GeO}_6$  octahedra to form a

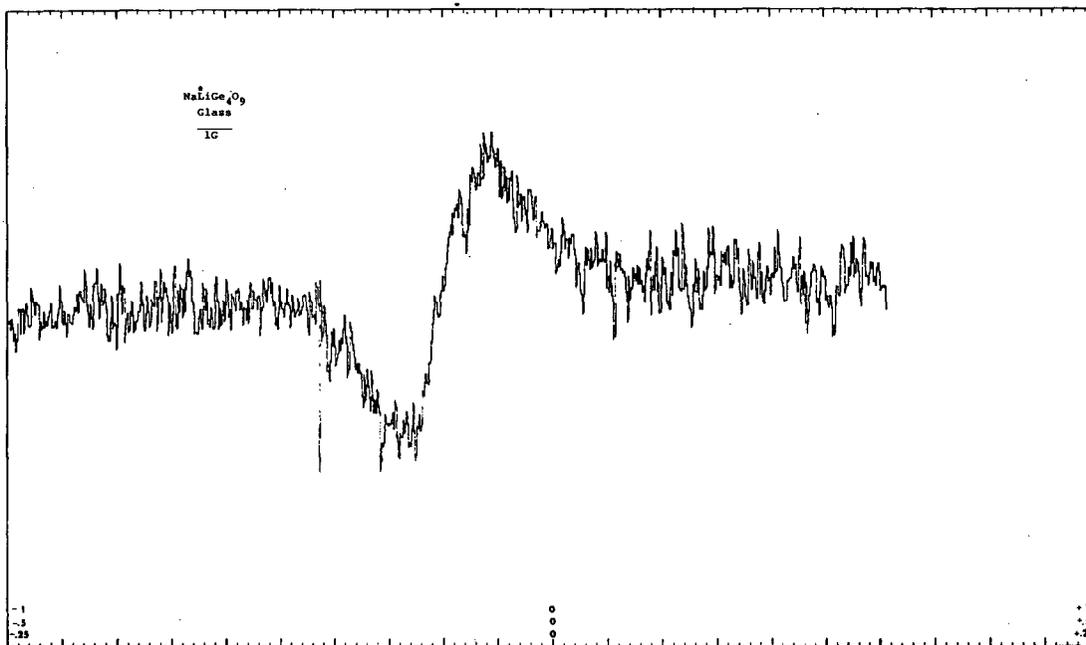


Fig. 20 NMR spectrum of  ${}^7\text{Li}$  in glass with composition  $\text{NaLiGe}_4\text{O}_9$  at room temperature. The peak width is 1.6 gauss.

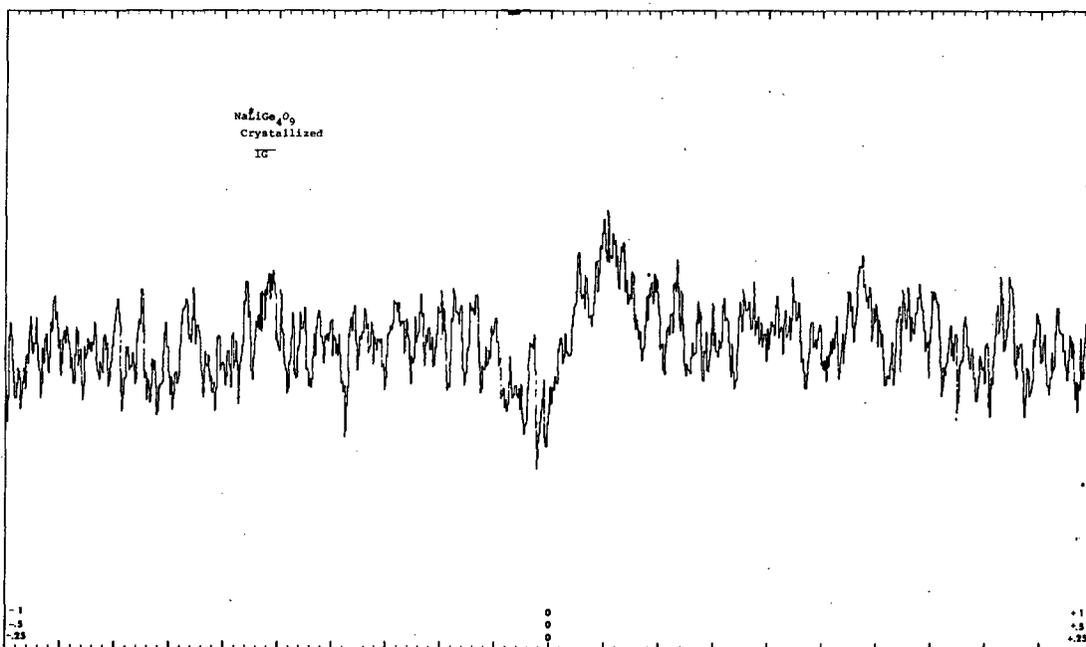


Fig. 21 NMR spectrum of  ${}^7\text{Li}$  in crystalline  $\text{NaLiGe}_4\text{O}_9$  at room temperature. The peak width is 1.3 gauss.

loose three-dimensional framework. This can be seen from Fig. 22. Within this framework there are interwoven channels which can accommodate  $\text{Li}^{1+}$  ions. (23) The two  $\text{Li}^{1+}$  sites both have 6-coordinated  $\text{Li}^{1+}$  ions with Li-O distances varying from 1.933Å to 2.367Å. The structure is so loose that it might accommodate larger ions (such as  $\text{Na}^{1+}$ ) in interstitial sites. One such 6-coordinated interstitial site has an average X-O distance of 2.563Å. (23)

Three-dimensional motion of alkali ions is conceivable both for stoichiometric  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  and nonstoichiometric variants (described below), since there are interstitial sites and wide enough tunnels in this loose framework structure.

The low density and "looseness" of the  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  structure is apparent from the large molecular volume ( $298.8\text{Å}^3$ ) when compared to the molecular volume of  $218.2\text{Å}^3$  derived from the component oxides  $\text{Li}_2\text{O}$  and tetragonal  $\text{GeO}_2$ .

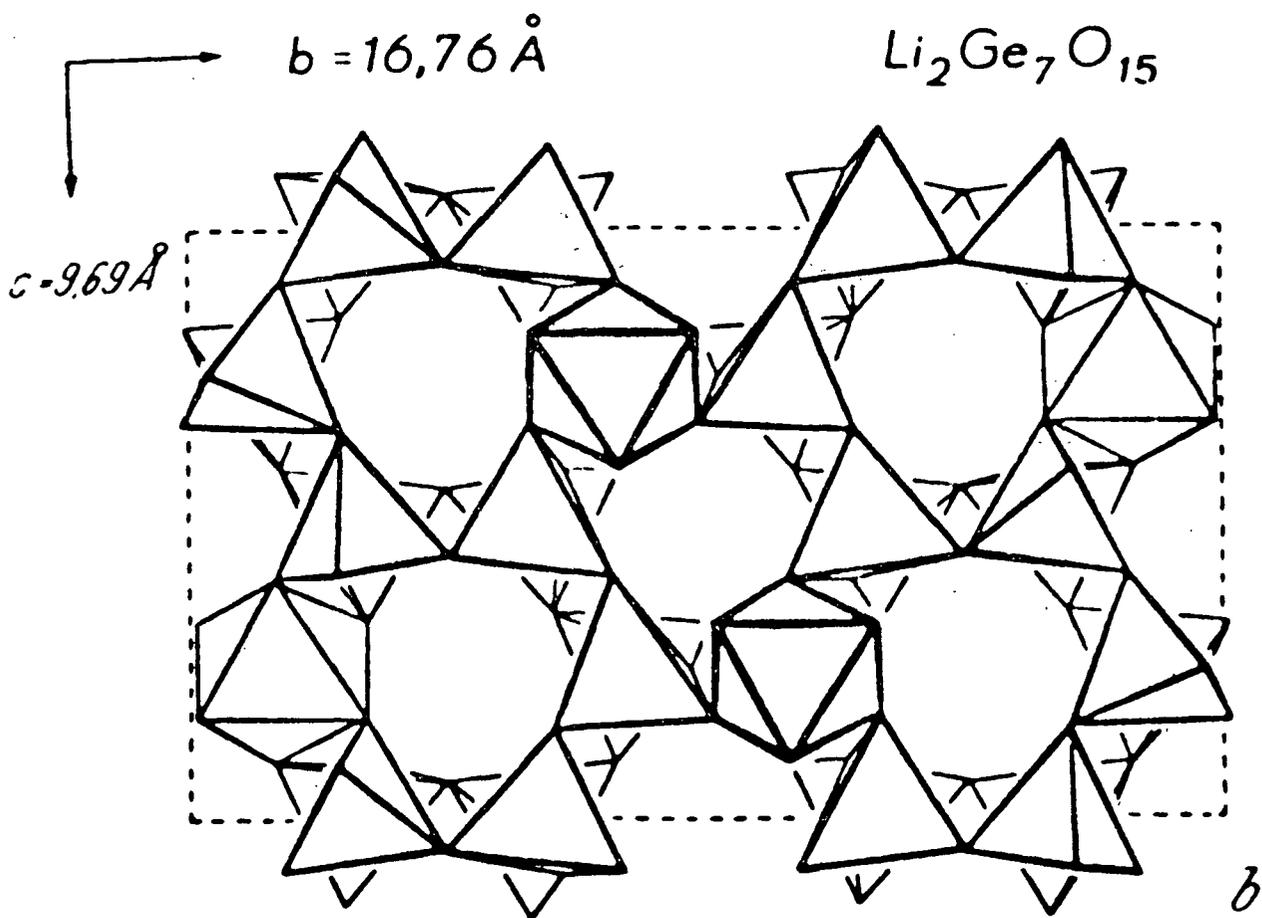


Fig. 22 The structure of  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  projected on the (100) plane.

Nonstoichiometric  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  type phases can be envisioned by substituting pentavalent ions for  $\text{Ge}^{4+}$  and creating vacancies in the  $\text{Li}^{1+}$  sites, e. g.,  $\text{Li}_{2-x}\text{Ge}_7-x\text{Nb}_x\text{O}_{15}$ . Alternately one could try to force additional alkali ions (like  $\text{Na}^{1+}$ ) into the large interstitial holes by making solid solutions of the type  $\text{Li}_2\text{Na}_x\text{Ge}_{7-x}\text{Al}_x\text{O}_{15}$ .

## 2. Synthesis

Both glassy and crystalline phases have been prepared for  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  and substituted derivatives.

### (a) $\text{Li}_2\text{Ge}_7\text{O}_{15}$

Larger amounts of  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  (20 to 50 grams) have been prepared by slowly heating an intimate mixture of the appropriate amounts of  $\text{Li}_2\text{CO}_3$  and  $\text{GeO}_2$  from  $450^\circ$  to  $1000^\circ\text{C}$  in a platinum crucible, holding the temperature at  $1000^\circ\text{C}$  for one hour, and then withdrawing the crucible from the furnace. The  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  product so obtained is a very fine crystalline powder of high purity. X-ray patterns show either no detectable impurity peaks or only traces of  $\text{GeO}_2$ .

When the above-described synthesis is carried out at significantly higher or lower final heating temperatures, pure  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  is not obtained. A synthesis at  $1120^\circ\text{C}$  resulted in large amounts of excess  $\text{GeO}_2$ . A low-temperature preparation ( $850^\circ\text{C}$ ) contained in addition to  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  significant amounts of four other phases:  $\text{GeO}_2$  (quartz structure),  $\text{GeO}_2$  (rutile structure),  $\text{Li}_2\text{Ge}_4\text{O}_9$ , and  $\text{Li}_2\text{GeO}_3$ .

Glassy  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  can be made by heating the appropriate  $\text{Li}_2\text{CO}_3$ - $\text{GeO}_2$  mixture (or crystalline  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ ) slowly up to  $1200^\circ\text{C}$  in a platinum tube or crucible. The platinum containers are then quickly withdrawn from the furnace and immersed in cold water. If a slower cooling rate is used, partial crystallization takes place. The  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  glass has a refractive index of 1.690.

### (b) Substituted glasses near the $\text{Li}_2\text{Ge}_7\text{O}_{15}$ stoichiometry

Homogeneous glasses of the following compositions were made and are listed below with their refractive indices:

<u>Composition of Glass</u>	<u>Refractive Index</u>
$\text{Li}_{1.7}\text{Ge}_{6.7}\text{Sb}_{0.3}\text{O}_{15}$	1.692
$\text{Li}_{1.7}\text{Ge}_{6.7}\text{Ta}_{0.3}\text{O}_{15}$	1.698
$\text{Li}_{1.7}\text{Ge}_{6.7}\text{Nb}_{0.3}\text{O}_{15}$	1.698
$\text{Li}_{1.7}\text{Ge}_{6.7}\text{V}_{0.3}\text{O}_{15}$	1.688
$\text{Li}_2\text{Na}_{0.3}\text{Ge}_{6.7}\text{Al}_{0.3}\text{O}_{15}$	1.676

The glasses can be made by heating the appropriate mixtures of crystalline  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ ,  $\text{GeO}_2$ ,  $\text{Sb}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5$ ,  $\text{Nb}_2\text{O}_5$ , and  $\text{V}_2\text{O}_5$  in sealed platinum tubes for 1/2 hour at  $1200^\circ\text{C}$ , and then rapidly quenching the tubes in cold water.

The  $\text{Li}_{1.7}\text{Ge}_{6.7}\text{Ta}_{0.3}\text{O}_{15}$  glass has the lowest tendency to crystallize, and this composition can therefore be prepared in larger batches by slowly heating the appropriate mixture of oxides in an open platinum crucible to  $1200^\circ\text{C}$ , and then removing the crucible from the furnace.

The  $\text{Li}_2\text{Na}_{0.3}\text{Ge}_{6.7}\text{Al}_{0.3}\text{O}_{15}$  glass can be made by heating the appropriate mixture of  $\text{Li}_2\text{CO}_3$ ,  $\text{Na}_2\text{CO}_3$ ,  $\text{GeO}_2$ , and  $\text{Al}_2\text{O}_3$  at  $850^\circ\text{C}$  for two hours. The resulting mixture was then sealed into platinum tubes and heated for 1/2 hour at  $1200^\circ\text{C}$ . The tubes were then quenched in cold water.

### (c) Crystalline, Nonstoichiometric $\text{Li}_2\text{Ge}_7\text{O}_{15}$ -Type Phases

Efforts were made to prepare nonstoichiometric  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ -type phases by heating the appropriate mixtures of oxides and  $\text{Li}_2\text{CO}_3$  from  $450^\circ$  to  $1000^\circ\text{C}$ . This method, however, yielded pure samples only for stoichiometric  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ . Even when the heat treatment was modified, nonstoichiometric  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  type phases could not be prepared in the pure state.

A successful synthesis of pure crystalline  $\text{Li}_{1.7}\text{Ge}_{6.7}\text{Ta}_{0.3}\text{O}_{15}$  and  $\text{Li}_{1.7}\text{Ge}_{6.7}\text{Sb}_{0.3}\text{O}_{15}$  was finally achieved when glasses of the same compositions were used as starting materials. The glasses were annealed at  $600^\circ\text{C}$  for about three days. The x-ray patterns of the products showed only peaks belonging to the  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  structure, indicating a high phase purity.

Attempts to anneal the  $\text{Li}_2\text{Na}_{0.3}\text{Ge}_{6.7}\text{Al}_{0.3}\text{O}_{15}$  glass at  $600^\circ\text{C}$  did not result in a pure crystalline phase. While the major phase was of the  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  type, smaller (but significant) amounts of  $\text{NaLiGe}_4\text{O}_9$  and a quartz type phase were also present.

### 3. Evaluation

Strong motional narrowing of the  $^7\text{Li}$  NMR spectrum is seen in both  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  and  $\text{Li}_{1.7}\text{Ge}_{6.7}\text{Ta}_{0.3}\text{O}_{15}$  glasses (Figs. 23, 24, and Table VIII). Devitrifying the glasses resulted in slight line broadening indicating that crystallization tends to immobilize the lithium atoms. The lithium spectrum in the crystalline compounds is still narrow (1.0 gauss) and the critical temperature for motional narrowing may have been displaced to a higher value.

The conductivity in  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  glass and in the tantalum doped glass was measured in a microcell. The response is nearly capacitive (Fig. 25), but there was a slight current flow indicating small conductivity.

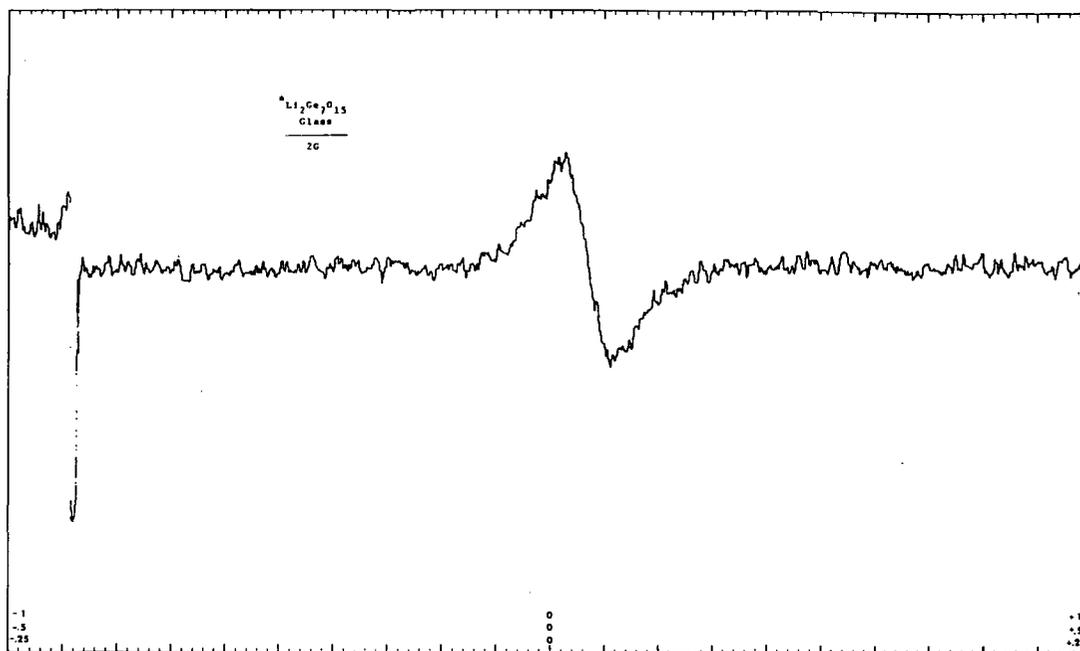


Fig. 23 NMR spectrum of  ${}^7\text{Li}$  in glass with composition  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  at room temperature. The peak width is 0.9 gauss.

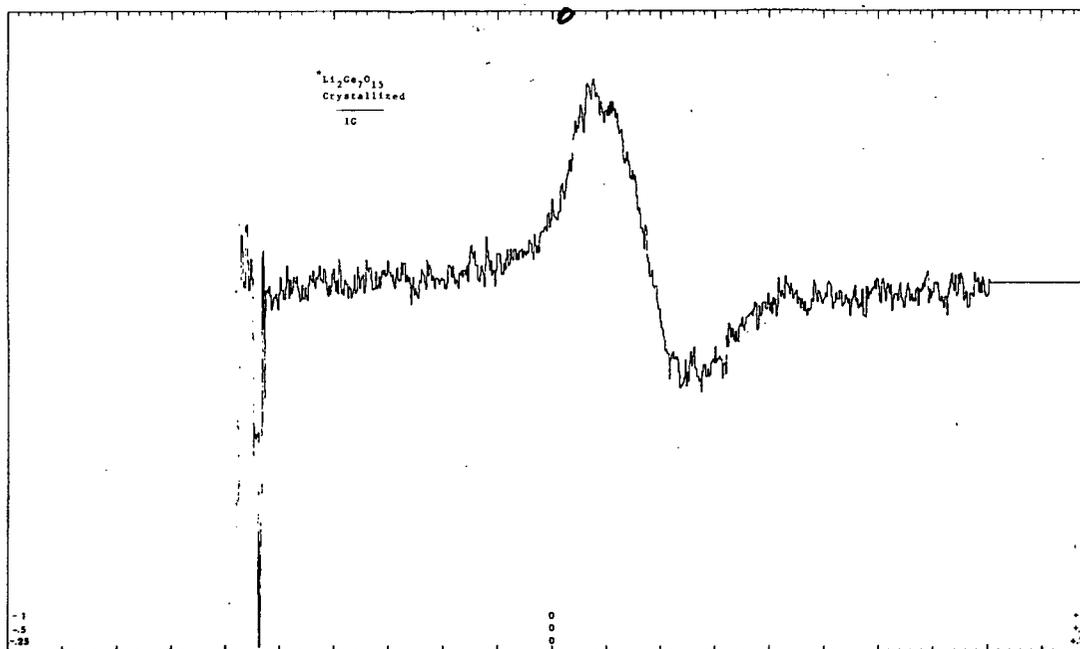


Fig. 24 NMR spectrum of  ${}^7\text{Li}$  in crystalline  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ . The peak width is 1.0 gauss.

TABLE VIII

NMR Spectra of  ${}^7\text{Li}$  in  $\text{Li}_2\text{Ge}_7\text{O}_{15}$ -Type Compounds

<u>Material</u>	<u>Phase</u>	<u>Temp (°C)</u>	<u>Line Width (Gauss)</u>
$\text{Li}_2\text{Ge}_7\text{O}_{15}$	Glass	22	0.9
		165	0.45
	Crystal	22	1.0
		170	1.0
$\text{Li}_{1.7}\text{Ge}_{6.7}\text{Ta}_{0.3}\text{O}_{15}$	Glass	-34	1.2
		22	1.0
		96	0.65
	Crystal	22	1.0
		95	1.0

The dielectric loss and room temperature AC conductivity measurements on glassy and crystalline  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  compositions are summarized in Table IX.

TABLE IX

<u>Sample</u>	<u>Phase</u>	<u>AC Conductivity at Room Temp (ohm<sup>-1</sup> cm<sup>-1</sup>)</u>	
$\text{Li}_2\text{Ge}_7\text{O}_{15}$	Glass	$10^3$ Hz	$\sim 10^{-6}$
		$10^5$	$\sim 10^{-6}$
	Polycrystal	$10^3$	$< 5 \times 10^{-12}$
		$10^5$	$\sim 1.5 \times 10^{-9}$
$\text{Li}_{1.7}\text{Ge}_{6.7}\text{Ta}_{0.3}\text{O}_{15}$	Glass	$10^3$	$\sim 5 \times 10^{-10}$
		$10^5$	$3 \times 10^{-8}$
	Polycrystal	$10^3$	$1.5 \times 10^{-10}$
		$10^4$	$1.4 \times 10^{-9}$
		$10^5$	$1.2 \times 10^{-8}$
		$10^6$	$< 5 \times 10^{-8}$

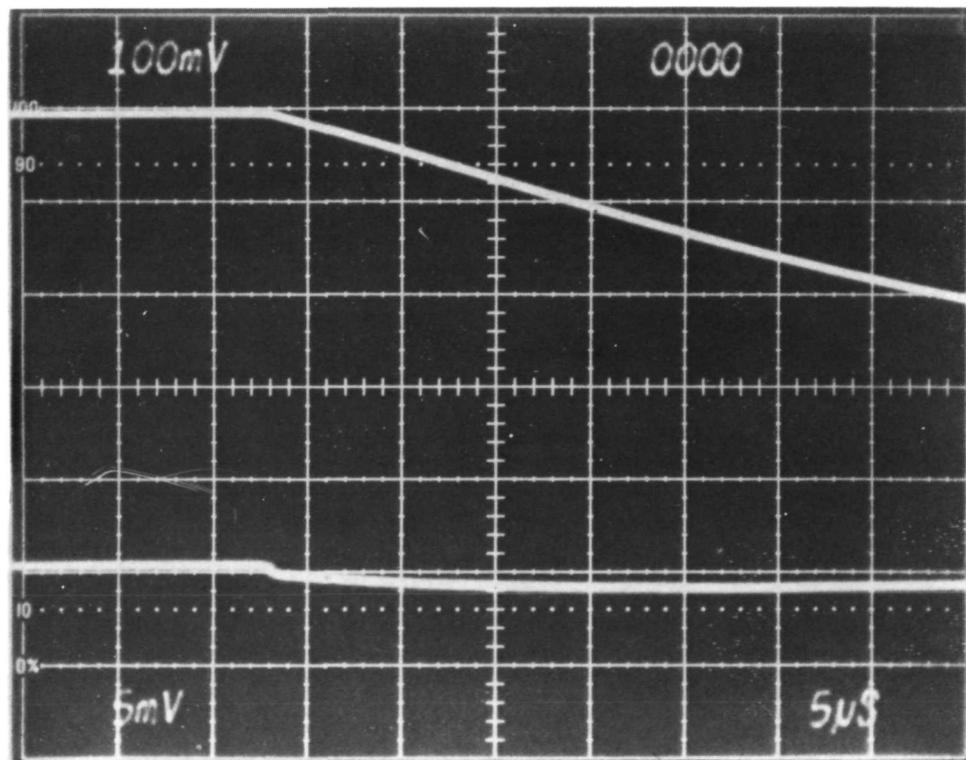
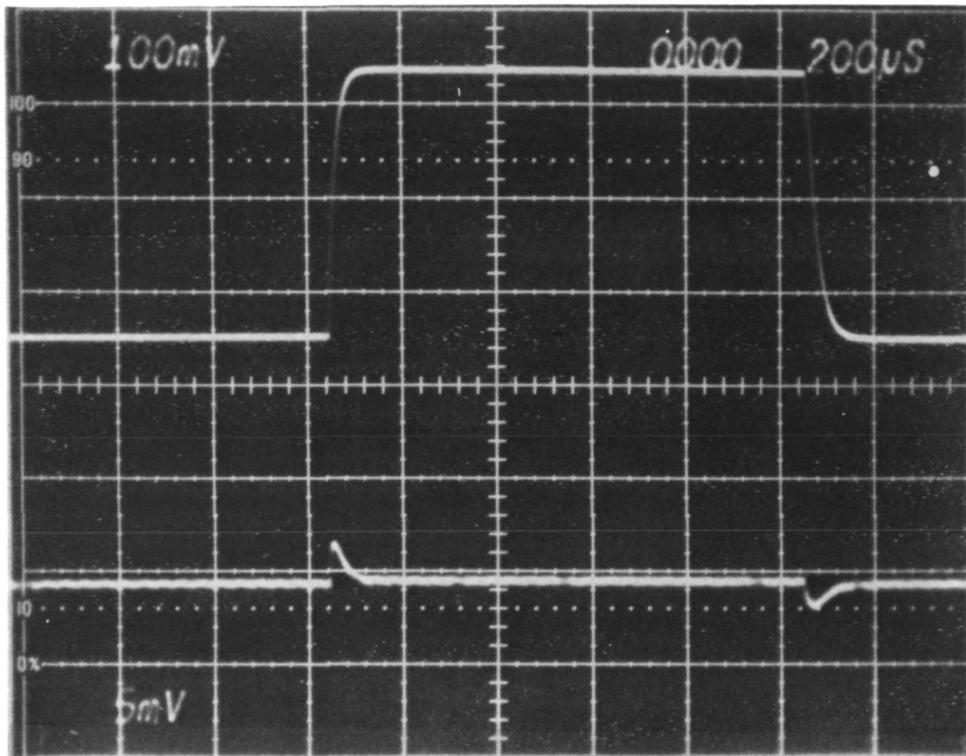


Fig. 25 Voltage response of  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  glass to constant current pulse in microcell. A small current flow can be seen in the expanded region of the trailing edge of the pulse.

The dielectric loss showed no peaks, but a small AC conductivity was measured at room temperature in lithium germanate glass. The reason for the smaller AC conductivity in the doped glass is not understood.

In summary, there is strong short-range motion of lithium atoms in pure and doped  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  glass, and this motion is decreased when the phase is crystallized. The ionic conductivity due to long-range movement of lithium ions is small but possibly was detected in  $\text{Li}_2\text{Ge}_7\text{O}_{15}$  glass.

## I. Hexagonal $\text{NaLnF}_4$ -Type Compounds

### 1. Structure and Transport Model

The hexagonal  $\text{NaNdF}_4$  structure is the stable low-temperature form for all  $\text{NaLnF}_4$  phases (Ln = lanthanon or yttrium). For many  $\text{NaLnF}_4$  compounds a phase transition takes place at higher temperatures to the well-known cubic fluorite structure. (24-26)

The structure of the hexagonal  $\text{NaNdF}_4$ <sup>(24)</sup> is shown in Fig. 26. There are three crystallographically independent sites for the cations. One is a 9-coordinated site and occupied only by  $\text{Nd}^{3+}$  ions. Another 9-coordinated

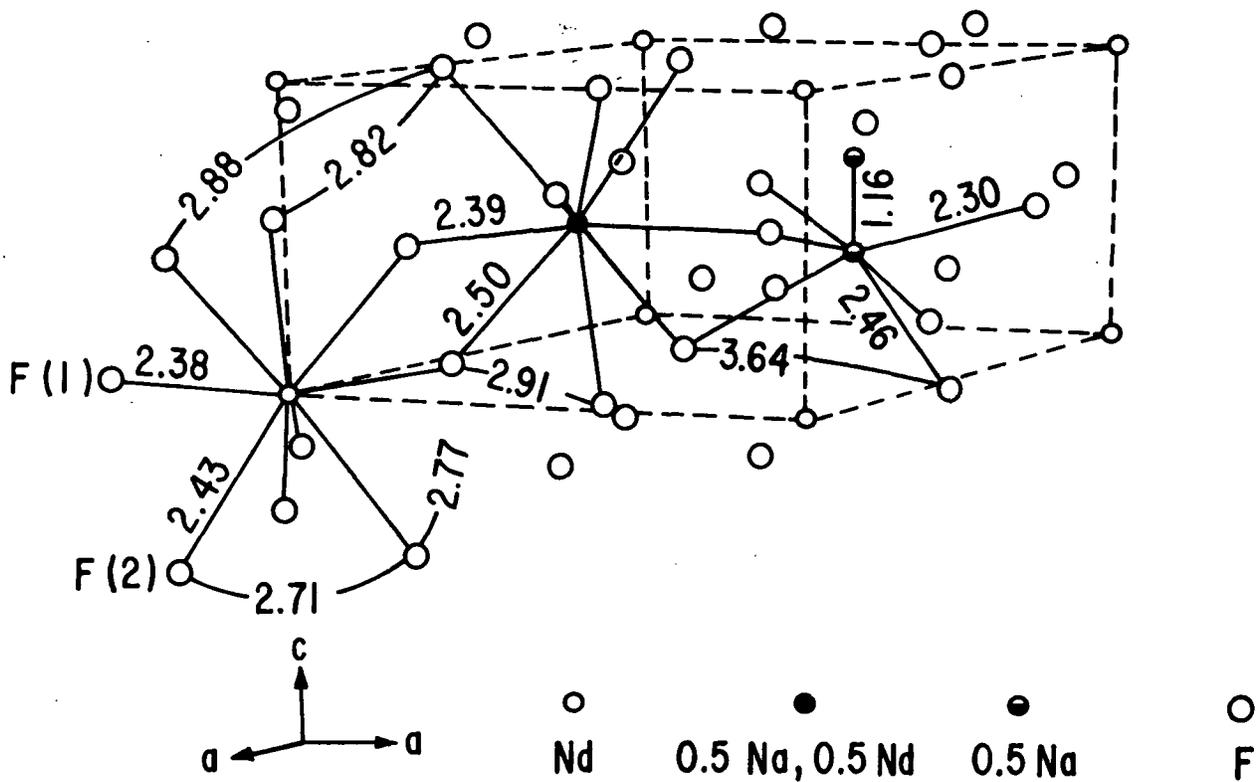


Fig. 26 The structure of hexagonal  $\text{NaNdF}_4$ .

site has 50%  $\text{Nd}^{3+}$  and 50%  $\text{Na}^{1+}$  ions distributed at random. A third octahedral site is half empty and half occupied by  $\text{Na}^{1+}$  ions. The structure study<sup>(24)</sup> shows that the  $\text{Na}^{1+}$  ions in these half-empty  $\text{Na}^{1+}$ -sites have strong anisotropic thermal motion, as do some of the fluoride ions. The thermal parameters of the  $\text{Na}^{1+}$  ion may reflect the uncertainty of site occupancy rather than true thermal motion.

Our interest in the  $\text{NaNdF}_4$ -compounds was primarily in the high-temperature cubic fluorite type solid solution phases<sup>(25, 26)</sup> rather than in the low-temperature hexagonal structure.<sup>(24)</sup> It was recognized, however, that the high-temperature fluorite form was more likely to be a  $\text{F}^-$  ion conductor than a  $\text{Na}^{1+}$  ion conductor. Since there was no interest in potential  $\text{F}^-$  ion conductors (for practical reasons) the earlier preliminary studies on the cubic  $\text{NaLnF}_4$  phases<sup>(2)</sup> were dropped. The studies on the hexagonal phases were continued since high ion mobility had been established in the cubic form, and it was possible the  $\text{Na}^{1+}$  ion in the half-empty site might be mobile.

## 2. Synthesis of $\text{NaNdF}_4$ -Type Phases

Hexagonal  $\text{NaPrF}_4$ ,  $\text{NaNdF}_4$ , and  $\text{NaYF}_4$  were prepared as follows: commercially obtained  $\text{NaF}$ ,  $\text{PrF}_3$ ,  $\text{NdF}_3$ , and  $\text{YF}_3$  were dried at  $220^\circ\text{C}$  under vacuum for about a day. The starting materials were then mixed in a 1:1 molar ratio and compressed into pellets. The pellets were placed in a platinum crucible and heated at  $400^\circ\text{C}$  under high vacuum to eliminate any traces of moisture. The crucible was then sealed and heated at  $750^\circ\text{C}$  for 7 hours and subsequently at  $600^\circ\text{C}$  for 12 hours. The pellets were analyzed by x-ray diffraction, which showed that the hexagonal  $\text{NaYF}_4$  and  $\text{NaNdF}_4$  phases were free from detectable impurities. In the  $\text{NaPrF}_4$  sample small amounts ( $\sim 5\%$ ) of  $\text{NaF}$  were detectable.

No attempt was made to prepare nonstoichiometric phases of the hexagonal  $\text{NaNdF}_4$  type. It is well known from a study of the phase equilibria of the  $\text{NaF-LnF}_3$  systems<sup>(25, 26)</sup> that these hexagonal phases do not form extensive solid solutions, unlike the high-temperature cubic forms.

A sample of  $\text{NaYF}_4$  was hot pressed for 20 minutes at 7700 psi and  $620^\circ$  to  $630^\circ\text{C}$ . The specimen was contained in a graphite die and shown by x-ray diffraction to still be of the hexagonal modification, with no impurity peaks detectable.

## 3. Evaluation

Three samples of hexagonal  $\text{NaLnF}_4$  compounds were examined for evidence of motional narrowing using wide-line NMR (Table X). Both the  $^{23}\text{Na}$  and  $^{19}\text{F}$  spectra were run at different temperatures. The room-temperature spectra of  $\text{NaYF}_4$ ,  $\text{NaPrF}_4$ , and  $\text{NaNdF}_4$  are shown in Figs. 27 through 32. The peak-to-peak line widths measured at various temperatures

TABLE X  
NMR Spectra in Hexagonal NaLnF<sub>4</sub> Compounds

<u>Material</u>	<u>Nucleus</u>	<u>Temp (°C)</u>	<u>Width (Gauss)</u>	
NaYF <sub>4</sub>	Na	22	6.0	
		90	6.0	
		186	6.0	
	F	22	9.0	
		186	10.0	
NaPrF <sub>4</sub>	Na	22	8.0	
		90	8.0	
		186	8.0	
	F	22	7,	30
		186	5,	19
NaNF <sub>4</sub>	Na	22	8.0	
		90	8.0	
		186	8.0	
	F	22	7,	34
		186	5,	20

are given in Table X. There is no evidence for motional narrowing of the sodium nuclei in any of the samples. On the other hand, some of the fluorine spectra did show some decline in line width with increasing temperature. The fluorine spectra are complex, apparently having a narrow line superposed on a broad line. The mechanism of the broadening is not understood. <sup>19</sup>F has no quadrupole moment and any broadening effects would arise from its dipole moment. The line width of the broad lines is believed too great to be accounted for on the basis of coupling between fluorine neighbors and may arise from coupling between the fluorine and the rare earth ions. This is consistent with the less broad line observed for the yttrium compound.

The absence of motional narrowing of the sodium nuclei is in contrast to what was observed in the cubic NaLnF<sub>4</sub> compounds last year. Motional narrowing of both the sodium and fluorine spectra was observed and the results could be interpreted by motion of either or both kinds of nuclei.

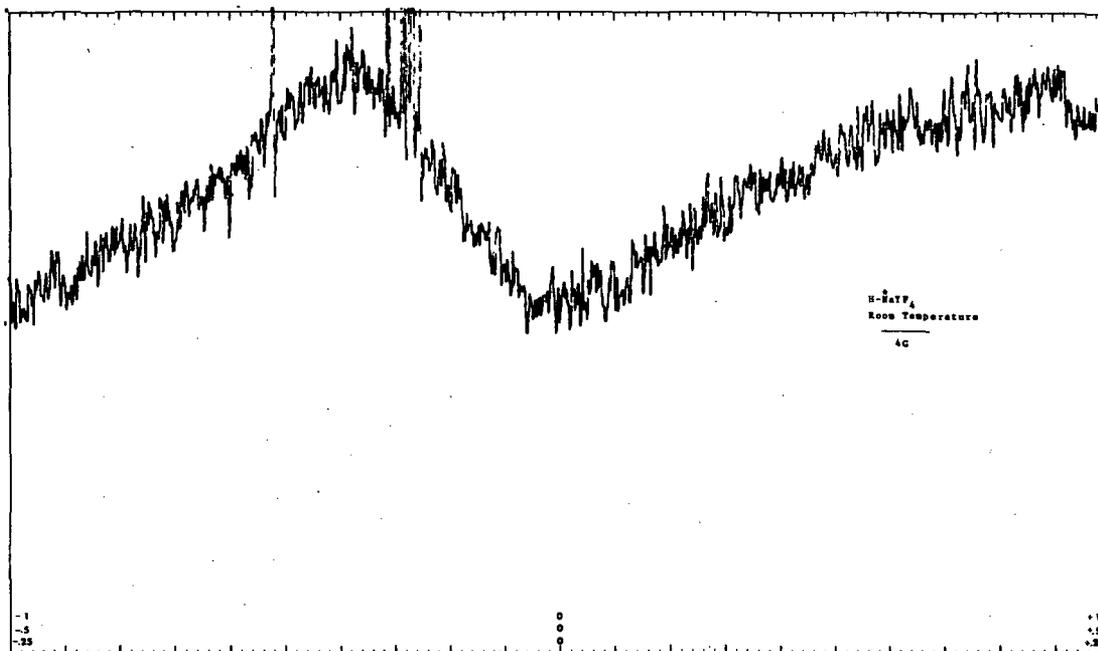


Fig. 27 NMR spectrum of  $^{23}\text{Na}$  in hexagonal  $\text{NaYF}_4$  at room temperature. The peak-to-peak width is 6.0 gauss.

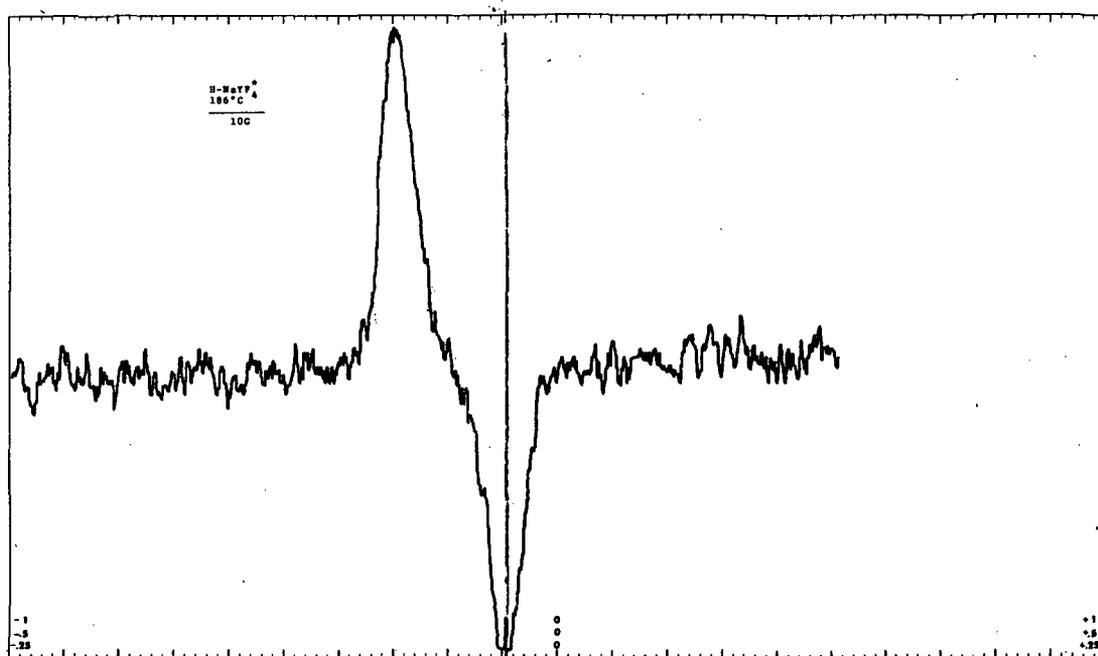


Fig. 28 NMR spectrum of  $^{19}\text{F}$  in hexagonal  $\text{NaYF}_4$  at  $186^\circ\text{C}$ . The peak width is 10 gauss, approximately the same as room temperature.

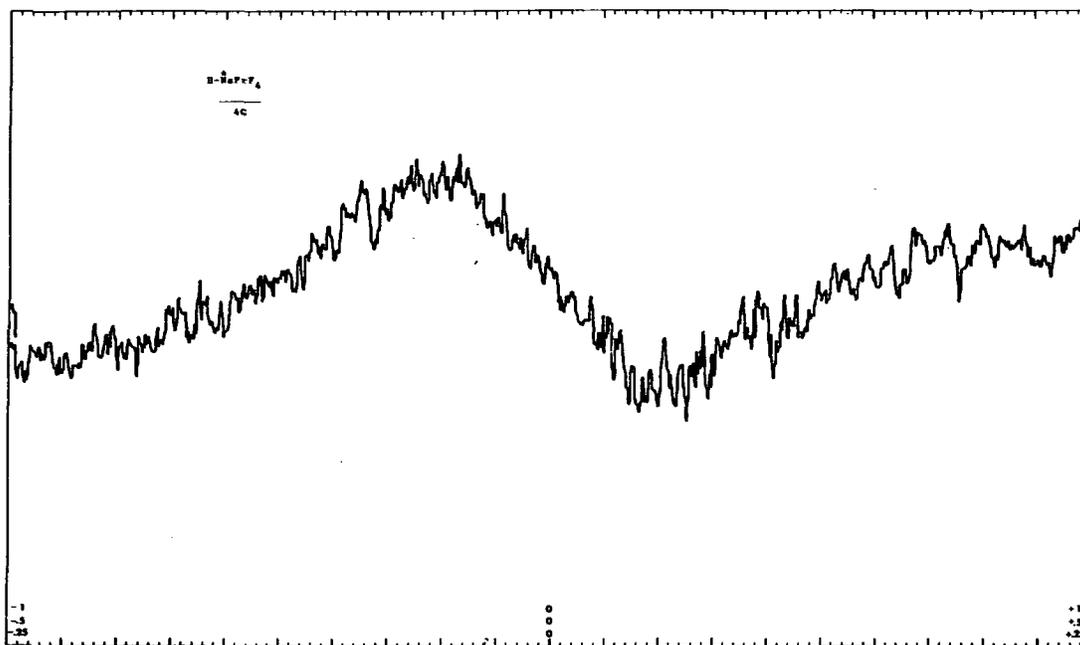


Fig. 29 NMR spectrum of  $^{23}\text{Na}$  in hexagonal  $\text{NaPrF}_4$  at room temperature. The peak width is 8.0 gauss.

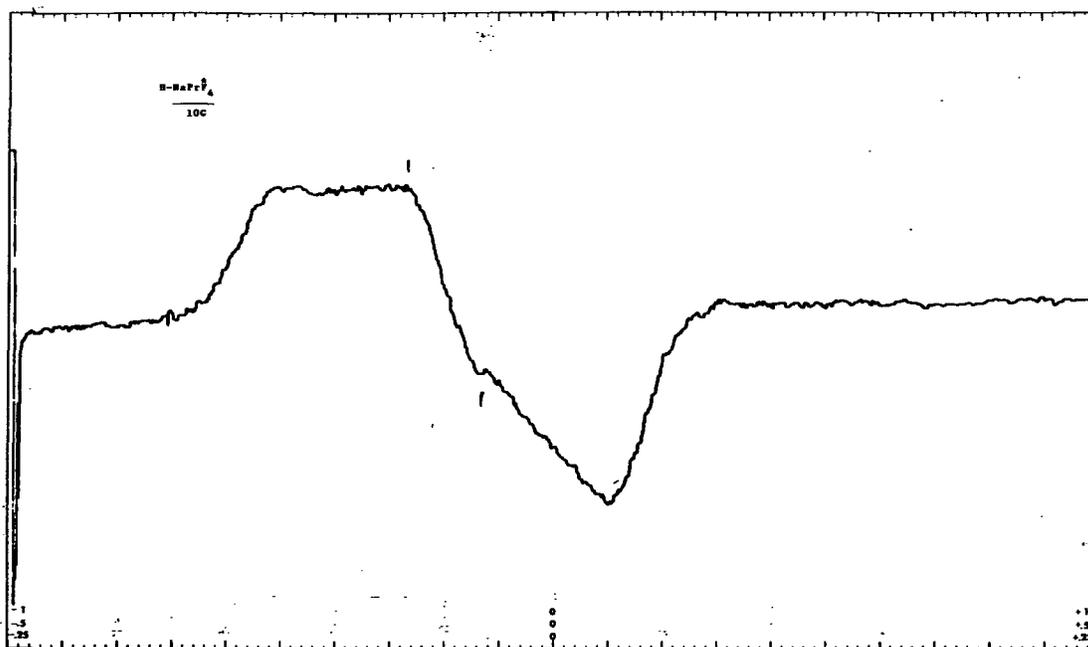


Fig. 30 NMR spectrum of  $^{19}\text{F}$  in hexagonal  $\text{NaPrF}_4$  at room temperature. The spectrum is complex and apparently consists of a narrow peak superposed on a broad peak.

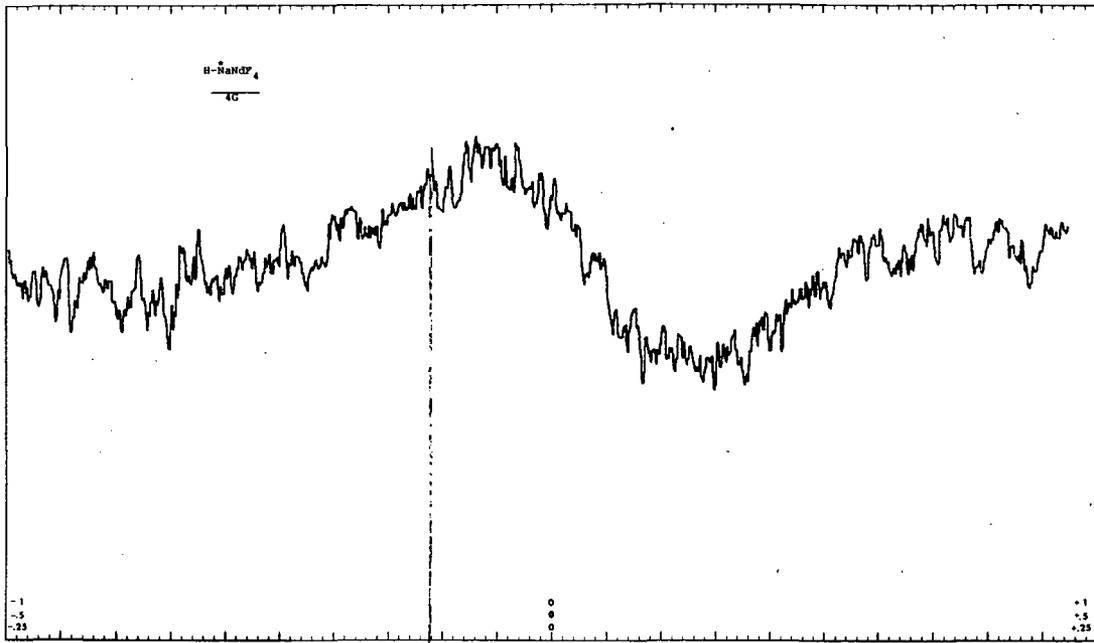


Fig. 31 NMR spectrum of  $^{23}\text{Na}$  in hexagonal  $\text{NaNdF}_4$  at room temperature. The peak width is 8.0 gauss.

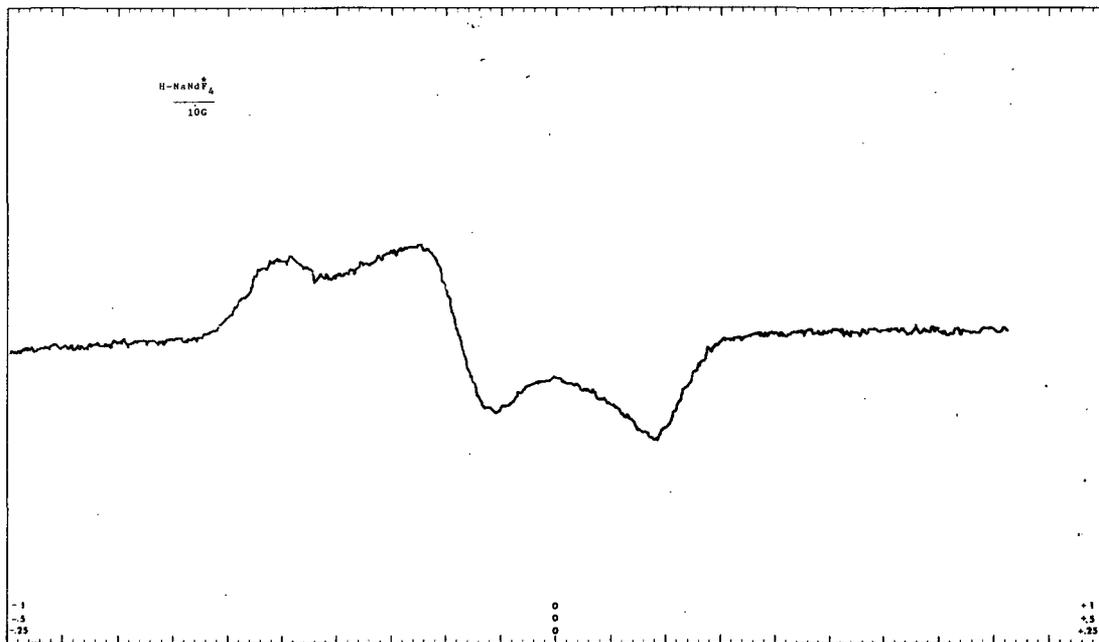


Fig. 32 NMR spectrum of  $^{19}\text{F}$  in hexagonal  $\text{NaNdF}_4$  at room temperature. The two fluorine peaks are resolved.

Since narrowing of the fluorine spectrum alone is seen in the hexagonal compounds, the sharpening of the sodium spectrum in the cubic compounds was probably caused by sodium motion and was not due to motion of the neighboring fluorine nuclei.

Dielectric loss and room temperature AC conductivity measurements made at NASA-Lewis Research Center indicated possible ionic conductivity in hexagonal  $\text{NaNdF}_4$  and  $\text{NaYF}_4$ . Their results are given in Table XI.

TABLE XI

Sample	Resonance Peak	AC Conductivity at Room Temp ( $\text{ohm}^{-1} \text{cm}^{-1}$ )	
C-15a $\text{NaPrF}_4$	Yes	$10^3$ Hz	$5 \times 10^{-9}$
	(two peaks observed: $\Delta E = 5.4-6.9$ kcal from low-temp peak may be Na motion; $\rho$ $25^\circ\text{C} \sim 1$ $\text{ohm-cm}$	$10^4$	$6 \times 10^{-8}$
	$\Delta E = 15.9$ kcal from high-temp peak may be F motion); $\rho$ $25^\circ\text{C} = 5 \times 10^5$	$10^5$	$5 \times 10^{-7}$
		$10^6$	$2 \times 10^{-6}$
C-16 $\text{NaNdF}_4$	Yes	$10^3$	$1.6 \times 10^{-8}$
	( $10^6$ Hz, $125^\circ\text{C}$ , Cole-Cole conductivity $\sim 2 \times 10^{-6}$ $\text{ohm}^{-1} \text{cm}^{-1}$ at $125^\circ\text{K}$ )	$10^4$	$4. \times 10^{-8}$
		$10^5$	$1.6 \times 10^{-7}$
		$10^6$	$6.4 \times 10^{-7}$
C-17 $\text{NaYF}_4$	Yes	$10^3$	$2.6 \times 10^{-8}$
	( $10^6$ Hz, $125^\circ\text{K}$ , Cole-Cole conductivity $\sim 5 \times 10^{-6}$ $\text{ohm}^{-1} \text{cm}^{-1}$ at $125^\circ\text{K}$ )	$10^4$	$6.9 \times 10^{-8}$
		$10^5$	$2.4 \times 10^{-7}$
		$10^6$	$1.1 \times 10^{-6}$
C-17as $\text{NaYF}_4$ hot-pressed	Yes	$10^3$	$4.8 \times 10^{-9}$
	$\Delta E = 4.3$ kcal	$10^4$	$2.6 \times 10^{-8}$
	$\rho$ $25^\circ\text{C} \sim 10$ $\text{ohm-cm}$	$10^5$	$1.4 \times 10^{-7}$
		$10^6$	$1.9 \times 10^{-6}$

We conclude from the dielectric loss and AC conductivity measurements that the hexagonal  $\text{NaLnF}_4$  compounds are moderate conductors at low temperature. The conductivity probably could be increased by doping, but the NMR spectra show the phase is an anion conductor and consequently of little interest in the present context.

## J. Dalyite-Type Compounds

### 1. Structure and Transport Model

The structure of the rare mineral dalyite (ideally  $\text{K}_2\text{ZrSi}_6\text{O}_{15}$ ) has recently been determined by Fleet. (27) The structure is illustrated in Figs. 33 and 34, and can be considered as a layer structure of a new type. The layers are


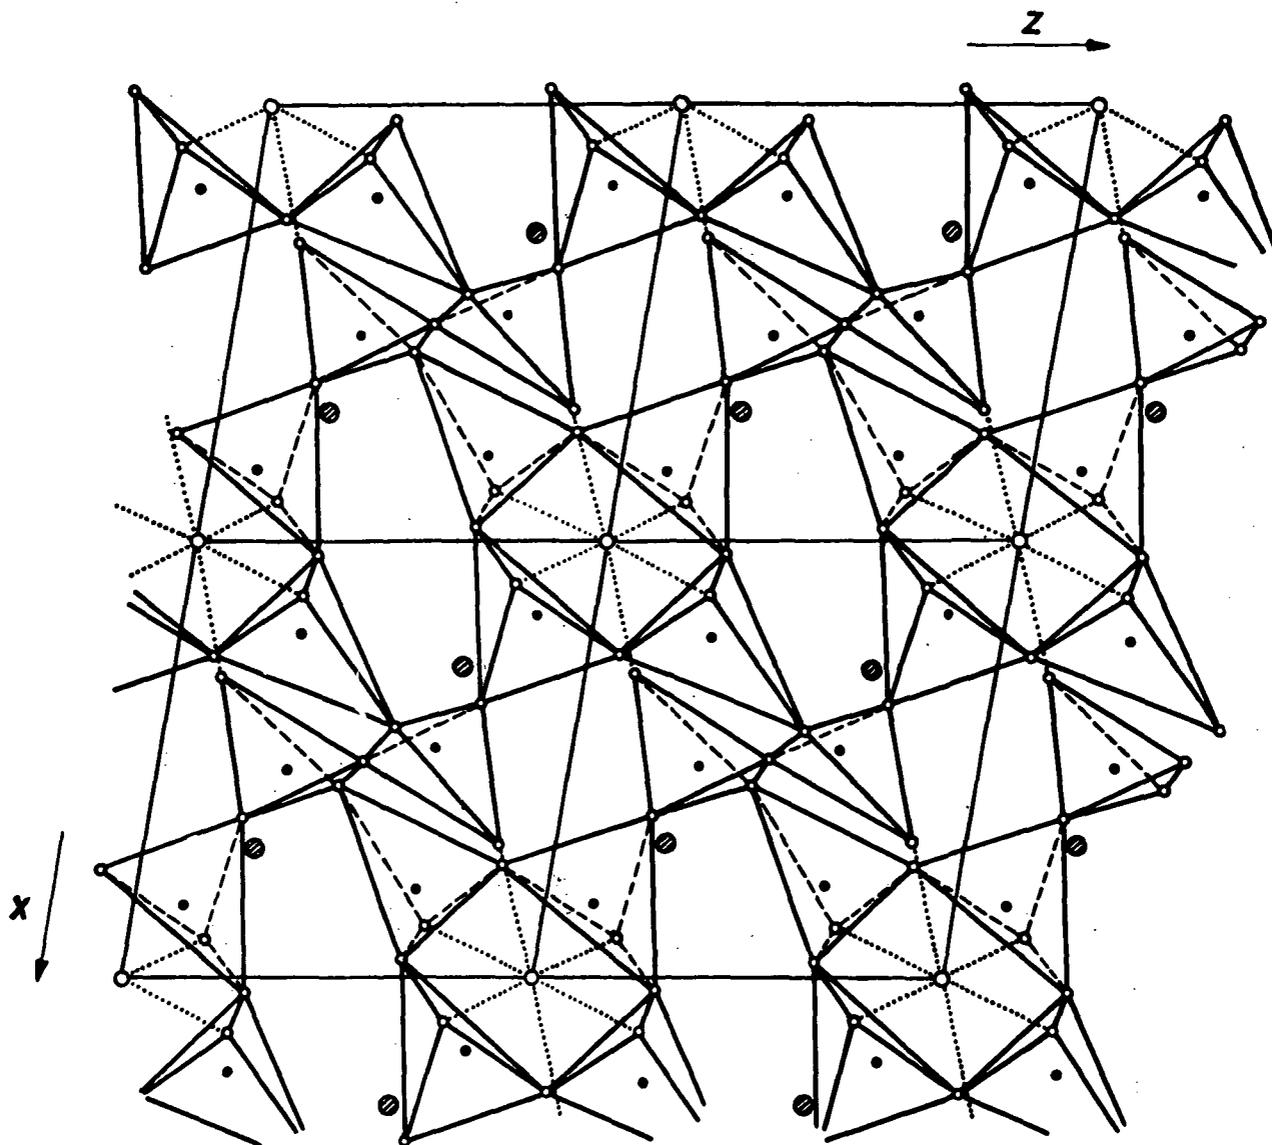


Fig. 33 The dalyite structure (ideally  $K_2ZrSi_6O_{15}$ ):  $\bullet$  = Si;  $\circ$  = O;  $\bigcirc$  = Zr;  $\bigcirc$  = K. After Ref. 27.

made up of  $SiO_4$  tetrahedra sharing corners to give four, six and 8-membered rings, as illustrated in Fig. 33. These silica sheets are held together in the third dimension by  $ZrO_6$  octahedra, giving rise to a three-dimensional framework with interconnected channels, occupied by  $K^+$  ions. Motion of the  $K^+$  ions seems possible in this structure, particularly if we consider the large temperature factor for  $K^+$  ( $B = 3.8 \text{ \AA}^3$  in the a-direction). The K-O distances are also larger than average ( $2.83 \text{ \AA}$  to  $3.49 \text{ \AA}$ ) which may indicate a fairly loose  $K^+$  ion.

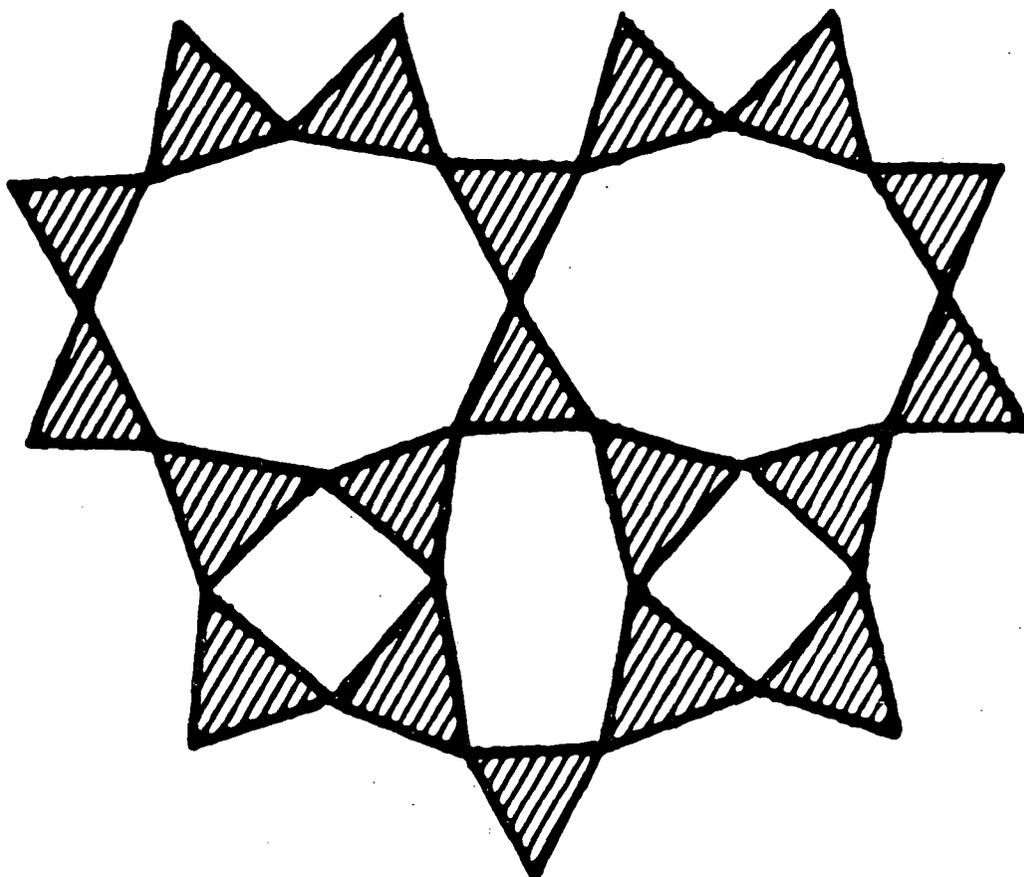

(III)

Fig. 34 Idealized dalyite sheets made up of  $\text{SiO}_4$  tetrahedra sharing corners.  
After Ref. 27.

The structure would be even a more attractive candidate if nonstoichiometric variants could be made and if the  $\text{K}^+$  ion could be exchanged with  $\text{Na}^+$  or  $\text{Ag}^+$ . To make the structure nonstoichiometric, one could substitute  $\text{Zr}^{4+}$  with  $\text{Ta}^{5+}$ , i. e.,  $\text{K}^+ + \text{Zr}^{4+} = \square + \text{Ta}^{5+}$ . It might also be possible to exchange  $\text{K}^+$  with  $\text{Na}^+$  or  $\text{Ag}^+$  in a nitrate melt. It is well known that, in the mineral dalyite, significant amounts of  $\text{Na}^+$  (~15%) can replace the  $\text{K}^+$  ions, (27, 28) and the smaller  $\text{Na}^+$  or  $\text{Ag}^+$  ions might be very loose and mobile in the structure.

## 2. Synthesis of Dalyite-Type Phases

So far, synthetic dalyite has been prepared only under hydrothermal conditions at low temperatures and efforts to make the phase by more conventional sintering techniques have been unsuccessful. (29, 30) It was felt that an effort should be made to synthesize  $\text{K}_2\text{ZrSi}_6\text{O}_{15}$  by a more easily accessible method.

Reagent grade  $K_2CO_3$ ,  $ZrOSO_4 \cdot H_2SO_4 \cdot 3H_2O$ , and silicic acid ( $SiO_2 \cdot xH_2O$ ) were intimately mixed, pelletized, and heated gradually up to  $1200^\circ C$  in a platinum container. At this stage the resulting product did not contain any dalyite-like phase but was a mixture of at least four different products, as observed by optical and x-ray methods: a glassy phase, a cristobalite-like crystalline material,  $ZrO_2$ , and an unidentified crystalline product.

This mixture was now heated for 20 minutes at  $1700^\circ C$  in a platinum boat, and cooled in air. The resulting product was a homogeneous glass. (Attempts to prepare such glasses at lower temperatures were unsuccessful.) When this glass was heated for one day at  $1200^\circ C$ , the resulting product had completely crystallized. The x-ray pattern of this crystallized product is not identical to the published dalyite patterns, (28, 29) but it nevertheless bears a resemblance to these published patterns. It is possible to interpret these data as indicating the presence of a dalyite-related phase, not identical to the mineral dalyite, but similar to it.

Since the dalyite work was initiated two weeks before the termination of the contract, no further synthesis could be carried out.

### 3. Evaluation

The "dalyite" samples could not be synthesized in time for evaluation before the expiration of the contract.

## V. CONCLUSIONS AND RECOMMENDATIONS

A large number of structure types and many compounds have now been evaluated as possible solid electrolytes for high-energy and power-density batteries to operate at ambient temperature. A compilation of the results obtained this year is given in Table XII. The crystal-chemical basis for predicting potential conductors has been validated in many cases. We have obtained evidence for ionic conductivity in one-dimensional and three-dimensional channel structures. No new solid electrolyte has yet been discovered with the requisite properties of high cation conductivity and chemical stability for application in a practical low-temperature battery, but we believe further work as outlined below is warranted and has a high probability for success. We have obtained new information which allows us to make the crystal-chemical criteria for high ionic conductivity more restrictive. In addition, we have developed significant new methods for evaluation of ion transport. In this section we have summarized the conclusions which result from the present study and make recommendations for future work.

TABLE XII

Summary of Materials and Screening Results

<u>Structure</u>	<u>Substitutions and Phase</u>	<u>Screened by</u>			<u>Estimated Conductivity at Room Temp (ohm<sup>-1</sup> cm<sup>-1</sup> at 10<sup>6</sup> Hz)</u>			
		<u>NMR</u>	<u>Dielectric Loss</u>	<u>AC</u>	<u>Pulse</u>	10 <sup>-8</sup>	10 <sup>-6</sup>	10 <sup>-4</sup>
<u>1-Dimensional</u>								
LiNb <sub>6</sub> O <sub>15</sub> F	Mo, W, Ti	●	●	●	●			
Hollandite	K <sub>2</sub> [MgTi] <sub>8</sub> O <sub>16</sub>		●	●	●			
Cordierite	Na, K	●	●	●				
<u>2-Dimensional</u>								
NaNb <sub>2</sub> O <sub>7</sub> F <sub>2</sub>	Ca, Sr, Pb Y, Nd, Mo, W	●	●	●				
<u>3-Dimensional</u>								
Perovskite	Li, Na-La, Nd, Y							
Tungsten Bronze	Na				●			
NaLiGe <sub>4</sub> O <sub>9</sub>	glass, crystal Ta, Nb, Sb, V	●	●	●	●			
Li <sub>2</sub> Ge <sub>7</sub> O <sub>15</sub>	glass, crystal Ta, Nb, Sb, V	●	●	●	●			
H-NaLnF <sub>4</sub>	Pr, Nd, Y	●	●	●				

## A. Conclusions

The principal conclusions resulting from this study are as follows:

1. Crystal chemistry has been used successfully to predict and identify many structures in which cations are loosely bound and capable of at least short-range motion at low temperature.

2. Compounds with this degree of ionic mobility can be screened by NMR and dielectric loss.

3. Short-range motion is a necessary although not sufficient condition for ion transport. In the compounds that have been evaluated thus far the long-range ionic motion or transport has been small at room temperature.

4. Our investigation of channel structures has led to an important refinement of the crystal chemical criteria for the selection of candidate cation conductors:

(a) The channels through which ion migration is expected to occur should be interconnected in at least two dimensions, and preferably in three dimensions.

(b) Each potentially mobile ion should have available a minimum of three vacant sites into which it can move in a single elementary jump.

5. We have developed and validated a new fast pulse technique for the measurement of ion transport in very small solid specimens. This method is extremely promising and we believe it probably will prove to be a major breakthrough in evaluating ion transport in solids. The method will be particularly useful for measuring materials that are difficult to prepare as large single crystals or as pure dense polycrystalline solids.

6. Microwave measurements can be used to measure the conductivity of powders.

## B. Recommendations

We believe that work in the future should be restricted to three- and two-dimensional interconnected channel structures, and that evaluation should be made principally by the fast pulse technique. Dielectric loss and/or microwave conductivity on powders are useful adjunct measurements.

A broad family of anhydrous zeolitic\*-like structures related to analcite ( $\text{NaAlSi}_2\text{O}_6$ ) has been selected for a focused search. The following considerations were used to arrive at this class of compounds:

- (1) The channels should be interconnected in three-dimensions to avoid blocking;
- (2) The channel diameter should be slightly larger than the dimensions of nonhydrated ions;
- (3) It should be possible to modify the materials in a relatively continuous manner over a broad range of composition and structure;
- (4) It should be possible to fabricate the materials into dense nonporous membranes for battery applications; and
- (5) There should be x-ray or other evidence of ion mobility in at least some of the compositions.

The starting points chosen for our zeolite system are the anhydrous compositions  $\text{NaAlSi}_2\text{O}_6$  (analcite),  $\text{KAlSi}_2\text{O}_6$  (high leucite), and  $\text{CsAlSi}_2\text{O}_6$  (pollucite). These are well-known minerals and their structures have been described. (34-39)

All three of these minerals are cubic with space group  $\text{O}_h^1\text{-Ia}3\text{d}$  and with cell constants around  $13.7\text{\AA}$ . The zeolitic, three-dimensional alumino-silicate network is the same for all three minerals, but only high-leucite and pollucite are truly isotypic. The  $\text{AlO}_4$  and  $\text{SiO}_4$  tetrahedra are randomly interlinked at all four corners to form an open three-dimensional framework.

---

\*It is appropriate to comment on two objections usually encountered when zeolites are considered as potential solid electrolytes. The first of these involves the fact that it is well known that removal of water from the zeolite structure results in disappointingly low conductivities and diffusion rates. (31) This is a valid concern, but there have not been intensive studies of ion transport in nonstoichiometric, anhydrous, small channel zeolites of the type considered for this study. In fact, the channels in the proposed compounds are so small it may be somewhat inaccurate to refer to them as zeolites. A second objection is that since most zeolites are porous and composed of extremely small crystallites, it may be difficult to fabricate into dense non-porous membranes for practical applications. We believe this is not necessarily a valid objection since some anhydrous zeolites can be made by devitrifying glasses of the same composition. For example,  $\text{KAlSi}_2\text{O}_6$  (leucite), and  $\text{CsBSi}_2\text{O}_6$  (pollucite structure) can be made by devitrifying the appropriate glasses. (32, 33) We feel that if glasses can be used as precursors to the crystalline materials, it may be possible to fabricate dense membranes.

This leaves large channels, which in high leucite and pollucite, are occupied by potassium and cesium ions, respectively. The potassium and cesium ions are surrounded loosely by 12 oxygens at K-O distances of 3.35Å to 3.54Å and Cs-O distances of 3.40Å to 3.57Å. In hydrated specimens, water can partly occupy these 12-coordinated sites (or adjacent sites in pollucite).

The analcite structure differs from that of pollucite and high-leucite in that sodium ions occupy the "windows" that connect the large cavities. The Na-O distances are approximately 2.4Å. These smaller window sites are more suited for the smaller sodium ions than are the larger cavities.

We believe high ionic conductivity might be obtained in nonstoichiometric zeolites by the creation of additional vacancies (by adjustment of the Si/Al ratio) and by the simultaneous substitution of potassium ions for sodium or cesium ions. These intermediate-size ions may be small enough to move through the "windows," yet small enough to be only loosely bonded inside the large cavity.

Such loose bonding has been observed in high temperature leucite,  $\text{KAlSi}_2\text{O}_6$ .<sup>(36)</sup> Here, the ion inside the large cavity is bonded to six oxygens at 3.37Å and to six oxygens at 3.57Å, with the potassium ions having the large isotropic temperature factor of  $15.4\text{Å}^{-2}$ . In such an environment, potassium ion mobility appears possible, since K-O distances normally average about 2.7Å to 2.9Å. Unfortunately, the high form of  $\text{KAlSi}_2\text{O}_6$  cannot be quenched and reverts to a distorted low temperature form at about 605°C. By crystal-chemical substitutions, it may be possible to lower this transition temperature.

## VI. REFERENCES

1. Lundberg, M., Acta Chem. Scand. 19, 2274 (1965).
2. Roth, W. L., Mitoff, S. P., and King, R. N., Final Report, "Study, Selection and Preparation of Solid, Cationic Conductors," Sept. 1972, Contract NAS3-15692, NASA-Lewis Research Center, Cleveland, Ohio.
- 2a. Rice, M. J. and Roth, W. L., J. Solid State Chem. 4, 294 (1972).
- 2b. Kautz, H. E., Singer, J., Fielder, W. L., and Fordyce, J. S., NASA TN D-7146, "Electrical Screening Procedure for Solid Ionic Conductors," March (1973).
- 2c. Roberts, S. and von Hippel, A., J. Appl. Phys. 17, 610 (1946).
3. Byström, A. and Byström, A. M., Acta Cryst. 3, 146 (1950) and Acta Cryst. 4, 469 (1951).

4. Bayer, G. and Hoffman, W., *Am. Mineralogist* 51, 511 (1966).
5. Kinomura, N., *J. Am. Ceram. Soc.* 56, 344 (1973).
6. Byström, A., *Arkiv Kemi Min. Geol.* 15B [12], 1 (1942).
7. Gibbs, G. V., *Am. Mineralogist* 51, 1068 (1966).
8. Smith, J. V. and Schreyer, W., *Min. Mag.* 33, 226 (1962).
9. Schreyer, W. and Schairer, J. F., *J. Petrology* 2, 324 (1961).
10. Provondra, P. and Langer, K., *Neues Jahrbuch für Mineralogie, Abhandlungen* 116, 1 (1971).
11. Anderson, S. and Galy, J., *Acta Cryst.* B25, 847 (1969).
12. Chaminade, J. -P., Pouchard, M., and Hagenmuller, P., *Compt. Rend.* 273C, 984 (1971).
13. Brous, J., Fankuchen, I., and Banks, E., *Acta Cryst.* 6, 67 (1953).
14. Kestigian, M. and Ward, R., *J. Am. Chem. Soc.* 77, 6199 (1955).
15. Johnston, W. D. and Sestrich, D., *J. Inorg. Nucl. Chem.* 20, 32 (1961).
16. Tien, T. Y. and Hummel, F. A., *Trans. Brit. Ceram. Soc.* 66, 233 (1967).
17. Lejus, A. M. and Queyroux, F., *Compt. Rend.* 271C, 56 (1970).
18. MacChesney, J. B. and Sauer, H. A., *J. Am. Ceram. Soc.* 45, 419 (1962).
19. Studer, F., Montfort, Y., and Raveau, B., *J. Solid State Chem.* 7, 269 (1973).
20. Völlenkne, H., Wittmann, A., and Nowotny, H., *Mh. Chem.* 100, 79 (1969).
21. Krishna Murthy, M. and Ip, J., *J. Am. Ceram. Soc.* 47, 328 (1964).
22. Wittmann, A. and Modern, E., *Mh. Chem.* 96, 581 (1965).
23. Völlenkne, H., Wittmann, A., and Nowotny, H., *Mh. Chem.* 101, 46 (1970).

24. Burns, J.H., *Inorg. Chem.* 4, 881 (1965).
25. Thoma, R.E., Hebert, G.M., Insley, H., and Weaver, C.F., *Inorg. Chem.* 2, 1005 (1963).
26. Thoma, R.E., Insley, H., and Hebert, G.M., *Inorg. Chem.* 5, 1222 (1966).
27. Fleet, S.G., *Zeit. Krist.* 121, 349 (1965).
28. Van Tassel, R., *Min. Mag.* 29, 850 (1954).
29. Caruba, R., Baumer, A., and Turco, G., *Compt. Rend.* 270D, 2741 (1970).
30. Thibaut, G., Caruba, R., and Turco, G., *Compt. Rend* 274D, 792 (1972).
31. Beattie, I.R., *Trans. Faraday Soc.* 50, 581 (1954).
32. Schairer, J.F. and Bowen, N.L., *Am. J. Sci.* 253, 681 (1955).
33. Richerson, D.R., and Hummel, F.A., *J. Am. Ceram. Soc.* 55, 269 (1972).
34. Taylor, W.H., *Z. Krist.* 74, 1 (1930).
35. Knowles, C.R., Rinaldi, F.F., and Smith, J.V., *Indian Mineralogist* 6, 127 (1965).
36. Peacor, D.R., *Zeit. Krist.* 127, 213 (1968).
37. St. v. Náráy-Szabó, *Zeit. Krist.* 99, 277 (1938).
38. Newnham, R.E., *Am. Mineralogist* 52, 1515 (1967).
39. Beger, R.M. and Buerger, M.J., *Proc. Nat. Acad. Sci. U.S.* 58, 853 (1967).

OFFICIAL DISTRIBUTION LIST

NASA

NASA-Lewis Research Center (40)  
Attn: Mr. A. C. Antoine (M. S. 309-1)  
21000 Brookpark Road  
Cleveland, OH 44135

NASA-Lewis Research Center  
Attn: L. W. Schopen (M. S. 500-206)  
21000 Brookpark Road  
Cleveland, OH 44135

NASA-Lewis Research Center  
Attn: N. T. Musial (M. S. 500-113)  
21000 Brookpark Road  
Cleveland, OH 44135

NASA-Lewis Research Center (2)  
Attn: Library (M. S. 60-3)  
21000 Brookpark Road  
Cleveland, OH 44135

National Aeronautics and Space Administration  
Scientific and Technical Information Facility  
Attn: Acquisitions Branch  
P. O. Box 33  
College Park, MD 20740  
(12 copies and 1 reproducible)

Mr. Simon Manson, Code ES  
National Aeronautics and Space Administration  
Washington, DC 20546

Mr. Floyd Ford, Code 761. Z  
Goddard Space Flight Center  
National Aeronautics and Space Administration  
Greenbelt, MD 20771

Mr. Gerald Halpert, Code 761. Z  
Goddard Space Flight Center  
National Aeronautics and Space Administration  
Greenbelt, MD 20771

Mr. Thomas Hennigan, Code 761  
Goddard Space Flight Center  
National Aeronautics and Space Administration  
Greenbelt, MD 20771

Dr. Louis Rosenblum, MS 302-1  
Lewis Research Center  
National Aeronautics and Space Administration  
21000 Brookpark Road  
Cleveland, OH 44135

Mr. Harvey Schwartz, MS 309-1  
Lewis Research Center  
National Aeronautics and Space Administration  
21000 Brookpark Road  
Cleveland, OH 44135

Dr. J. Stuart Fordyce, MS 309-1  
Lewis Research Center  
National Aeronautics and Space Administration  
21000 Brookpark Road  
Cleveland, OH 44135

Mr. Charles B. Graff, S&E-ASTR-EP  
George C. Marshall Space Flight Center  
National Aeronautics and Space Administration  
Huntsville, AL 35812

Mr. Hoyt McBryar, EP5  
Johnson Space Center  
National Aeronautics and Space Administration  
Houston, TX 77058

JPL

Mr. Daniel Runkle, MS 198-220  
Jet Propulsion Laboratory  
4800 Oak Grove Drive  
Pasadena, CA 91103

Dr. R. Lutwack, MS 198-220  
Jet Propulsion Laboratory  
4800 Oak Grove Drive  
Pasadena, CA 91103

Mr. Aiji A. Uchiyama  
MS 198-220  
Jet Propulsion Laboratory  
4800 Oak Grove Drive  
Pasadena, CA 91103

ARMY

Harry Diamond Laboratories  
Room 300, Building 92  
Connecticut Ave. & Van Ness St., N. W.  
Washington, DC 20438

U. S. Army Electronics Command  
Attn: AMSEL-TL-P  
Port Monmouth, NJ 07703

Commanding Officer  
U. S. Army Mobility Equip. Research &  
Development Center  
Electrotechnology Department  
Electrochemical Division  
Attn: SMEFB-EE  
Fort Belvoir, VA 22061

NAVY

Director, Power Program, Code 473  
Office of Naval Research  
Arlington, VA 22217

D2

Dr. George A. Neece  
Code 472  
800 N. Quincy St.  
Office of Naval Research  
Arlington, VA 22217

Mr. S. Schuldiner, Code 6160  
Naval Research Laboratory  
4555 Overlook Avenue, S. W.  
Washington, DC 20375

Mr. J.H. Harrison, Code 2724  
Naval Ship R&D Center  
Annapolis, MD 21402

Commanding Officer  
Naval Ammunition Depot  
(305, Mr. D. G. Miley)  
Crane, Indiana 47522

Mr. Phillip B. Cole, Code 232  
Naval Ordnance Laboratory  
Silver Spring, MD 20910

Mr. Albert Himy, 6157D  
Naval Ship Engineering Center  
Center Bldg., Prince Georges Center  
Hyattsville, MD 20782

Dr. H. E. Ruskie, NISC-4321  
4301 Suitland Road  
Suitland, MD 20390

#### AIR FORCE

AFAPL/POE-1/D. R. Warnock  
Wright-Patterson AFB, OH 45433

Air Force Aero Propulsion Laboratory  
POE-1/W. S. Bishop  
WPAFB, OH 45433

Mr. Edward Raskind, LCC, Wing F  
U. S. AF Cambridge Research Laboratory  
L. G. Hanscom Field  
Bedford, MA 01731

Rome Air Development Center  
Attn: TUGG/F. J. Mollura  
Griffiss AFB, NY 13441

SAMSO/DYAE  
P. O. Box 92960  
Worldway Postal Center  
Los Angeles, CA 90009

#### OTHER GOVERNMENT ORGANIZATIONS

Dr. Leonard Topper  
NSF, RANN  
Washington, DC 20550

#### PRIVATE ORGANIZATIONS

Dr. E. A. Heintz  
Technical Department  
Airco Speer Carbon-Graphite  
P. O. Box 828  
Niagara Falls, NY 14302

Dr. R. T. Foley  
Chemistry Department  
American University  
Massachusetts & Nebraska Aves., N. W.  
Washington, DC 20016

Mr. R. A. Knight  
Research Division  
AMF Inc.  
689 Hope Street  
Stamford, CT 06907

Dr. H. Shalit  
ARCO Chemical Co.  
Division of Atlantic Richfield Co.  
500 South Ridgeway Avenue  
Glenolden, PA 19036

Dr. James D. Birkett  
Arthur D. Little, Inc.  
Acorn Park  
Cambridge, MA 02140

Dr. H. L. Recht  
Atomics International Division  
International Corp.  
P. O. Box 309  
Canoga Park, CA 91304

Mr. R. F. Fogle, GA 28  
North American Rockwell  
Autonetics Division, NAR  
P. O. Box 4192  
Anaheim, CA 92803

Mr. J. E. Clifford, Technical Representative  
Electrochemical Eng. Technical Division  
Battelle  
Columbus Laboratories  
505 King Avenue  
Columbus, OH 43201

Mr. D. O. Feder  
Bell Telephone Laboratories, Inc.  
Murray Hill, NJ 07974

Dr. Carl Berger  
13401 Kootenay Drive  
Santa Ana, CA 92705

Mr. Sidney Gross  
MS 8+-37  
The Boeing Company  
P. O. Box 3999  
Seattle, WA 98124

Professor T. P. Dirkse  
Calvin College  
3175 Burton Street, S. E.  
Grand Rapids, MI 49506

Professor Ernest Yeager  
Department of Chemistry  
Case Western Reserve Univ.  
Cleveland, OH 44106

Mr. C. E. Thomas  
Chrysler Corporation  
Space Division  
Dept. 2730  
P. O. Box 29200  
New Orleans, LA 70189

Mr. E. P. Broglio  
Eagle-Picher Industries, Inc.  
P. O. Box 47, Couples Dept.  
Joplin, MO 64801

Dr. J. M. Williams  
Experimental Station, Bldg. 304  
Engineering Technology Lab.  
E. I. du Pont de Nemours & Co.  
Wilmington, Delaware 19898

Mr. R. P. Mikkelson  
Electrical Systems Dept. 623-2  
General Dynamics/Convair Aerospace Division  
P. O. Box 80847  
San Diego, CA 92138

Xerox Corporation  
Electro-Optical Systems  
300 North Halstead Street  
Pasadena, CA 91107

Mr. Martin Klein  
Energy Research Corporation  
15 Durant Avenue  
Bethel, CT 06801

Dr. J. G. Cohn  
Engelhard Industries  
Menlo Park  
Edison, NJ 08817

Mr. L. Berkowitz  
Government Research Lab.  
Esso Research and Engineering Co.  
P. O. Box 8  
Linden, NJ 07036

Dr. Arthur Fleischer  
466 South Center Street  
Orange, NJ 07050

The Garrett Corporation  
Suite 515, Cafritz Building  
1625 Eye Street, N. W.  
Washington, DC 20006

Dr. J. B. Bush, Jr.  
Research and Development Center  
General Electric Company  
Bldg. K-1, Room 4A28  
P. O. Box 8  
Schenectady, NY 12301

Mr. Kenneth Hanson  
General Electric Company  
Valley Forge Space Technology Center  
P. O. Box 8555  
Philadelphia, PA 19101

Mr. J. A. Keralla  
Delco Remy Division  
General Motors Corporation  
2401 Columbus Avenue  
Anderson, IN 46011

Dr. John McCallum  
President  
Invention Talents, Incorporated  
1149 Cheseapeake Avenue  
Columbus, OH 43212

Mr. L. G. Nuttall  
General Electric Company  
930 Western Avenue, 274A4  
Lynn, MA 01910

Mr. F. T. O'Brien  
Direct Energy Conversion Programs  
General Electric Company  
930 Western Avenue  
Lynn, MA 01910

Dr. E. L. Simons  
Environmental Protection Operation - Building 36  
General Electric Company  
Schenectady, NY 12345

Dr. G. Goodman  
Globe-Union, Inc.  
P. O. Box 591  
Milwaukee, WI 53201

Dr. J. E. Oxley  
Dr. B. B. Owens  
Gould Inc., Gould Lab.  
P. O. Box 3140  
St. Paul, Minnesota 55165

Grumman Aerospace Corp.  
S. J. Gaston, Plant 35,  
Dept. 553  
Bethpage, Long Island  
New York 11714

Gulton Battery Corporation  
212 Durham Ave., Middlesex County  
Metuchen, NJ 08840

Dr. P. L. Howard  
Millington, MD 21651

D4

Dr. M. E. Ellion, Manager  
Propulsion & Power Systems Lab.  
Building 366, MS 524  
Hughes Aircraft Company  
El Segundo, CA 90245

Mr. R. Hamilton  
Institute for Defense Analyses  
400 Army-Navy Drive  
Arlington, VA 22202

Mr. James R. Hunt  
International Nickel Company  
1000-16th Street, N.W.  
Washington, DC 20036

Dr. A. Moos  
Leesona Corporation  
Warwick, RI 02887

Dr. R. A. Wynveen, President  
Life Systems, Inc.  
23715 Mercantile Road  
Cleveland, OH 44122

Mr. Robert E. Corbett  
Department 62-25, Building 151/1  
Lockheed Aircraft Corporation  
P. O. Box 504

Sunnyvale, CA 94088  
Mr. S. J. Angelovich  
Chief Engineer  
Mallory Battery Company  
South Broadway  
Tarrytown, NY 10591

Mr. A. D. Tonelli  
Dept. A3-833, MS 22-2  
McDonnell Douglas Astronautics Co.  
5301 Bolsa Avenue  
Huntington Beach, CA 92647

Dr. Robert C. Shair  
4921 Sanayer Dr.  
Hollywood, FL 33021

Rocketdyne Division  
North American Rockwell Corp.  
Attn: Library  
6633 Canoga Avenue  
Canoga Park, CA 91304

National Center for Energy Management & Power  
113 Towne Building  
University of Pennsylvania  
Phil., PA 19104

Dr. C. Bocciarelli  
112 E. 2nd Street  
Moorestown, NJ 08057

Mr. D. C. Briggs  
WDL Division  
Philco-Ford Corporation  
3939 Fabian Way  
Palo Alto, CA 94303

Dr. Per Bro  
P. R. Mallory & Company, Inc.  
Northwest Industrial Park  
Third Avenue  
Burlington, MA 01801

P. R. Mallory & Company, Inc.  
Library  
P. O. Box 706  
Indianapolis, IN 46206

Mr. V. D'Agostino  
RAI Research Corporation  
225 Marcus Blvd.  
Hauppauge, L. I., NY 11787

Southwest Research Institute  
Attn: Library  
P. O. Drawer 28510  
San Antonio, TX 78284

Library  
Standord Research Institute  
333 Ravenswood Avenue  
Menlo Park, CA 94025

Dr. W. R. Scott (M1-1208)  
TRW Systems, Inc.  
One Space Park  
Redondo Beach, CA 90278

Dr. Herbert P. Silverman  
(R-1/2094)  
TRW Systems, Inc.  
One Space Park  
Redondo Beach, CA 90278

Union Carbide Corporation  
Battery Products Division  
Development Laboratory Library  
P. O. Box 6056  
Cleveland, OH 44101

Dr. Robert Powers  
Consumer Products Division  
Union Carbide Corporation  
P. O. Box 6116  
Cleveland, OH 44010

United Aircraft Corporation  
Attn: Library  
400 Main Street  
East Hartford, CT 06108

Power Information Center  
University City Science Institute  
3401 Market Street, Room 2210  
Philadelphia, PA 19104

Dr. Frederick Morse  
Department of Mechanical Engineering  
University of Maryland  
College Park, MD 20742

Yardney Electric Corporation  
Power Sources Division  
3850 Olive Street  
Denver, CO 80207

Yardney Electric Division  
82 Mechanic Street  
Pawcatuck, CT 02891

Dr. Eugene Y. Weissman, Director  
Inorganic-Electrolytic R&D  
BASF Wyandotte Corporation  
Wyandotte, MI 48192

Dr. Charles Levine  
Dow Chemical U. S. A.  
Walnut Creek Research Center  
2800 Mitchell Drive  
Walnut Creek, CA 94598

Prof. Donald M. Smyth  
Materials Research Center  
Lehigh University  
Bethlehem, PA 18015

Prof. John W. Patterson  
Dept. of Metallurgy  
Iowa State University  
Ames, IA 50010

Prof. Rustum Roy  
Materials Science Dept.  
Pennsylvania State University  
University Park, PA 16802

Prof. John H. Kennedy  
Univ. of Calif. at Santa Barbara  
Santa Barbara, CA 93106

Dr. Paul Jorgensen  
Stanford Research Institute  
Menlo Park, CA 94025

Dr. L. Topper  
Div. of Advanced Technology Applications  
National Science Foundation  
Washington, DC 20550

Mr. L. R. Rothrock  
Union Carbide Corp.  
8888 Balboa Ave.  
San Diego, CA 92123

Prof. K. E. Cox  
Dept. of Chem. & Nucl. Eng.  
Tech. Appl. Center  
University of New Mexico  
Albuquerque, N. M. 87131

Dr. Robert A. Huggins  
Dept. of Materials Science and Engineering  
Stanford University  
Stanford, CA 94305

Dr. M. Stanley Whittingham  
Esso Research and Engineering Co.  
Linden, NJ 07036

Dr. Neill T. Weber  
Ford Motor Co. Research Lab.  
Dearborn, MI 48121

Prof. James I. Mueller  
Ceramic Engineering Div.  
University of Washington  
Seattle, WA 98195

Dr. Douglas O. Raleigh  
North American Rockwell Science Center  
Thousand Oaks, CA 91360

Dr. R.H. Doremus  
Rensselaer Polytechnic Institute  
Materials Division  
Troy, NY 12181

Dr. Robert S. Roth  
National Bureau of Standards  
U. S. Department of Commerce  
Washington, DC 20234

Prof. Alexander F. Wells  
Dept. of Chemistry  
University of Connecticut  
Storrs, CT 06268

Dr. Elton J. Cairns  
Electrochemistry Dept.  
General Motors Research Lab.  
12 Mile and Mound Roads  
Warren, Michigan 48090

Dr. John B. Goodenough  
Massachusetts Institute of Technology  
Lincoln Laboratory  
Lexington, Mass. 02173