



Burp Charging Nickel Metal Hydride Cells

by

Eric Darcy
NASA-Johnson Space Center
Houston, Texas

and

Richard Pollard
University of Houston
Houston, Texas


Presented by Bob Bragg
to the
1996 NASA Aerospace Battery Workshop
Dec 4, 1996

1996 NASA Aerospace Battery Workshop


-577-

Other Secondary Technologies Session

Handwritten signature

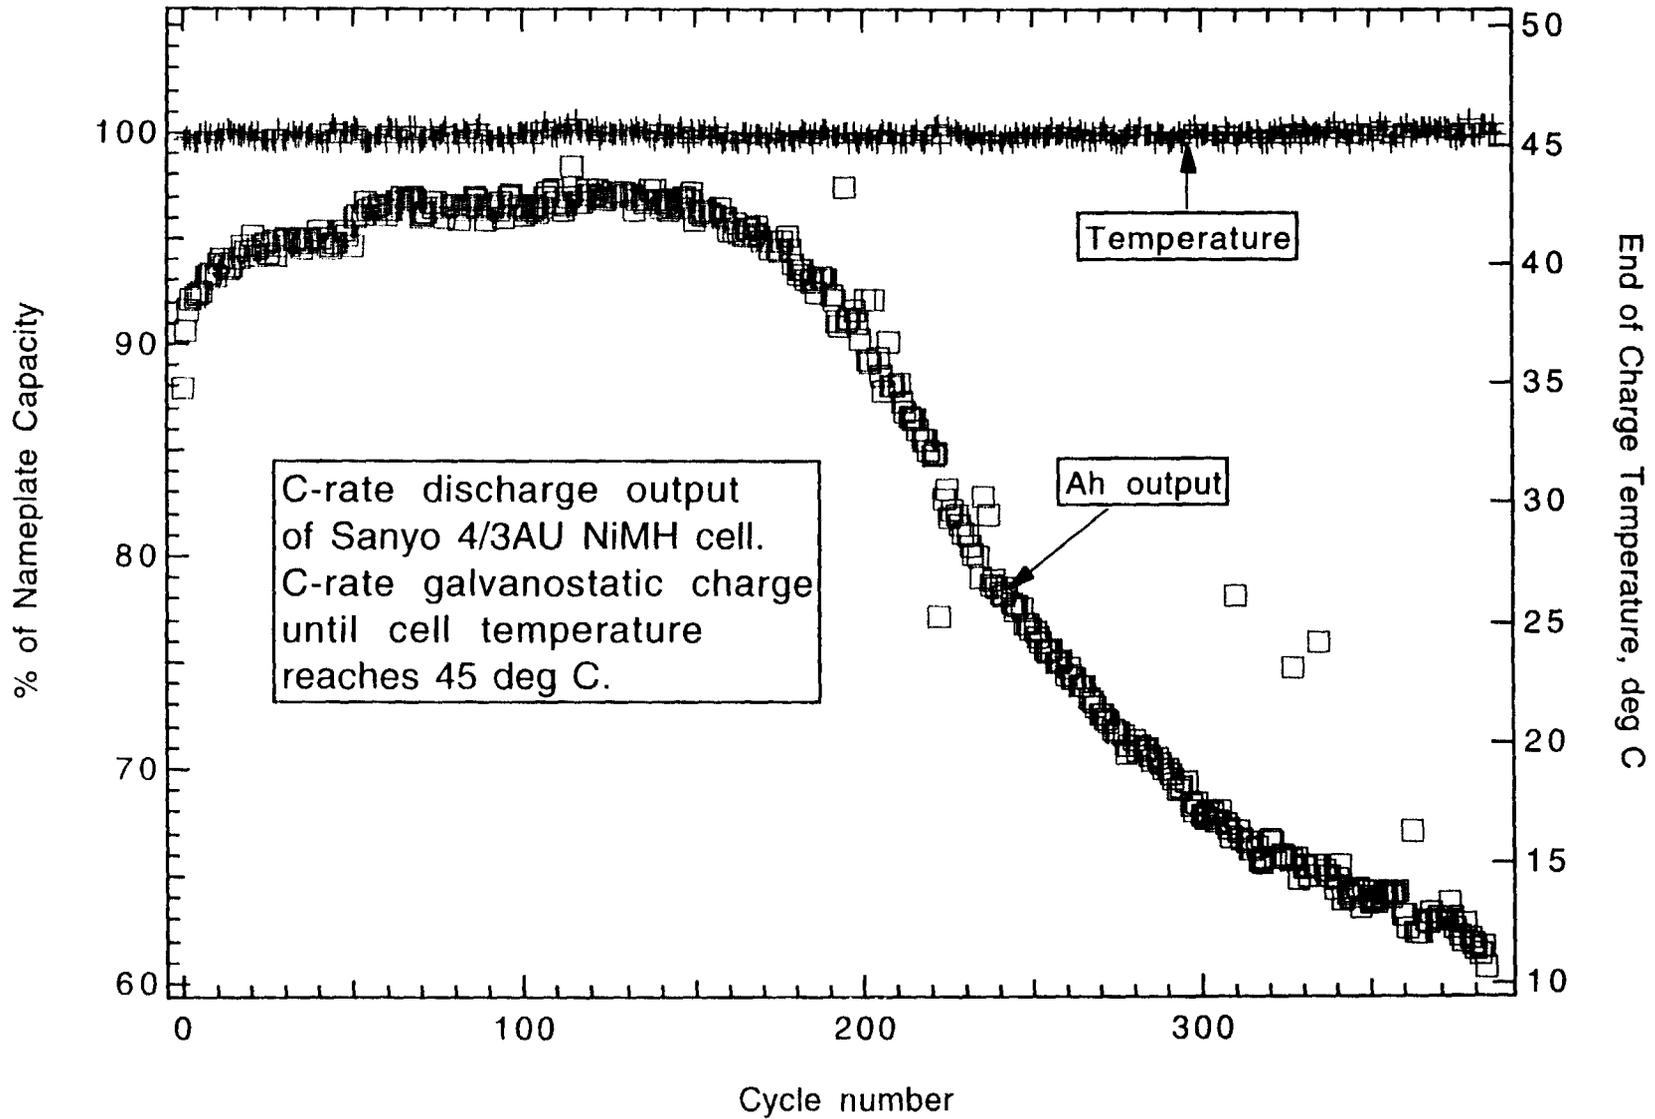

$$\partial V/\partial t = -X \text{ or } \partial T/\partial t = Y$$

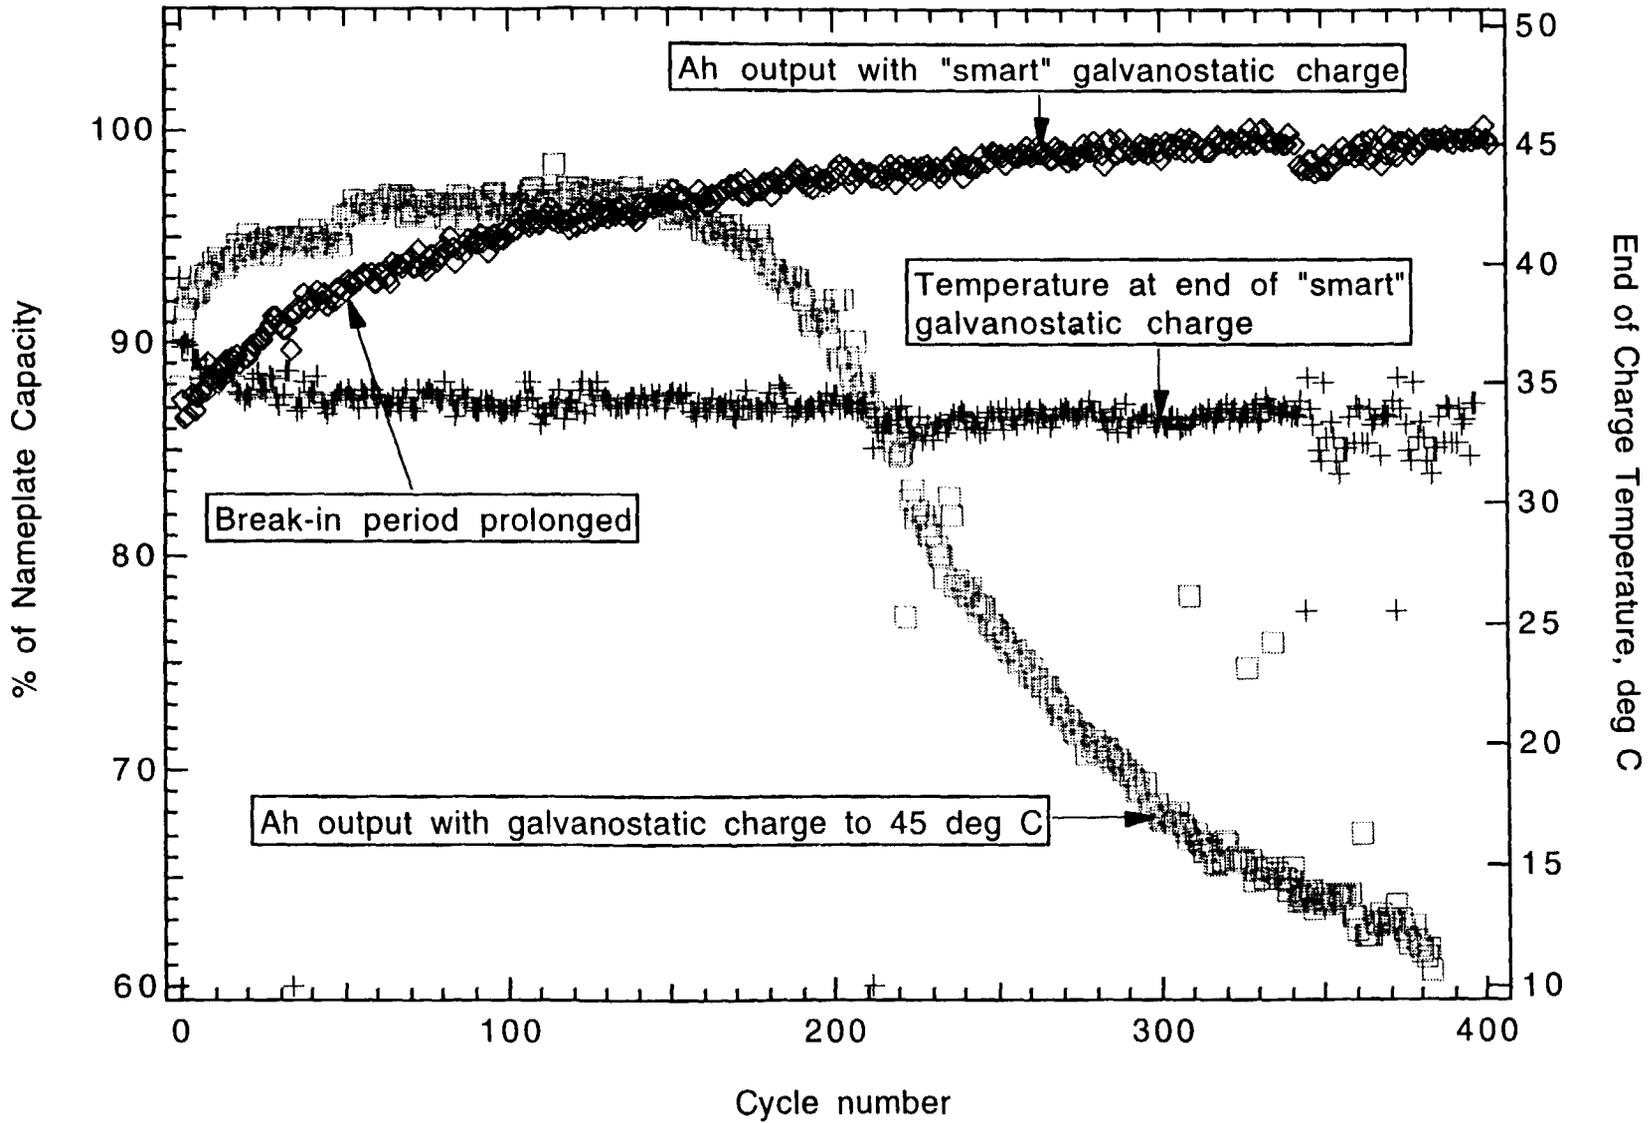


Some methods for improving cell performance

- **Smart termination**
 - negative voltage slope, $\partial V/\partial t < 0$
 - rise in temperature, $\partial T/\partial t = Y$
- **Charge current waveform changes**
 - relaxation, $I = 0$
 - discharge burp, $I < 0$


Areas of improvement remaining

- can break-in period to maximum capacity be accelerated?
- can discharge capacity be increased without compromising cycle life?
- can charge heat be reduced further?

Modifying the current waveform shown effective with NiCd cells

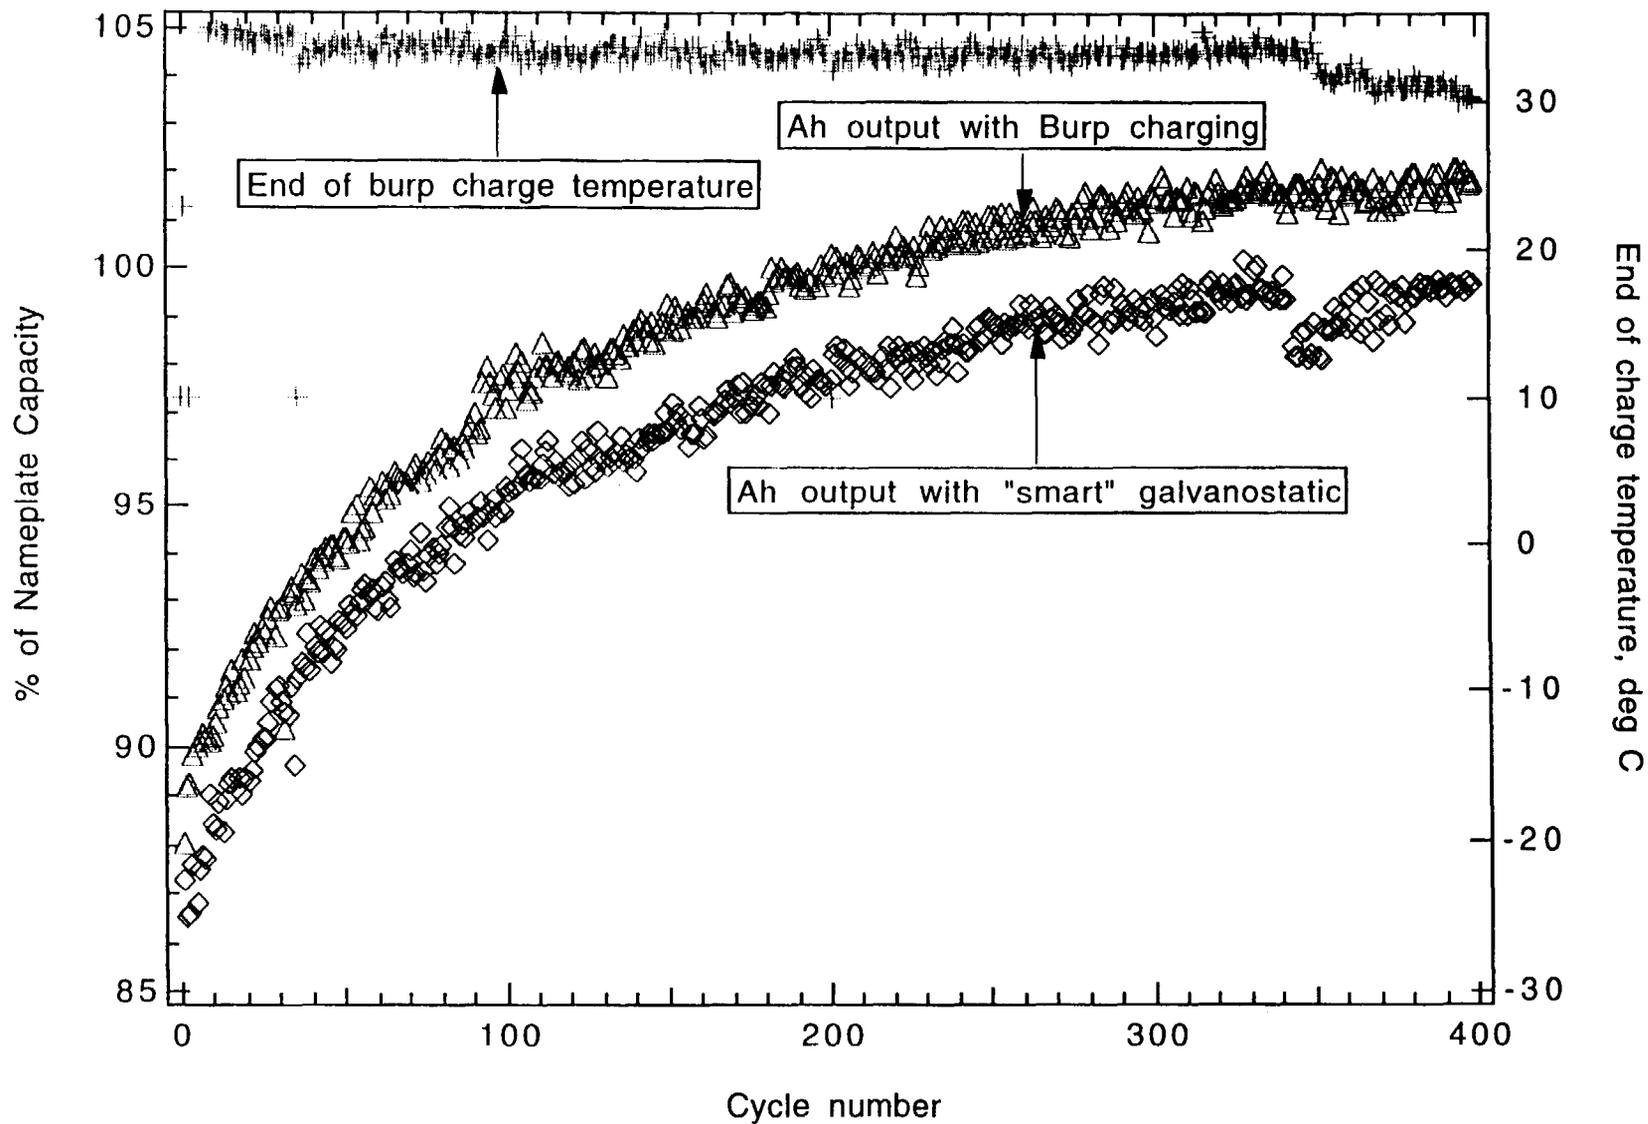


What is Burp Charging?

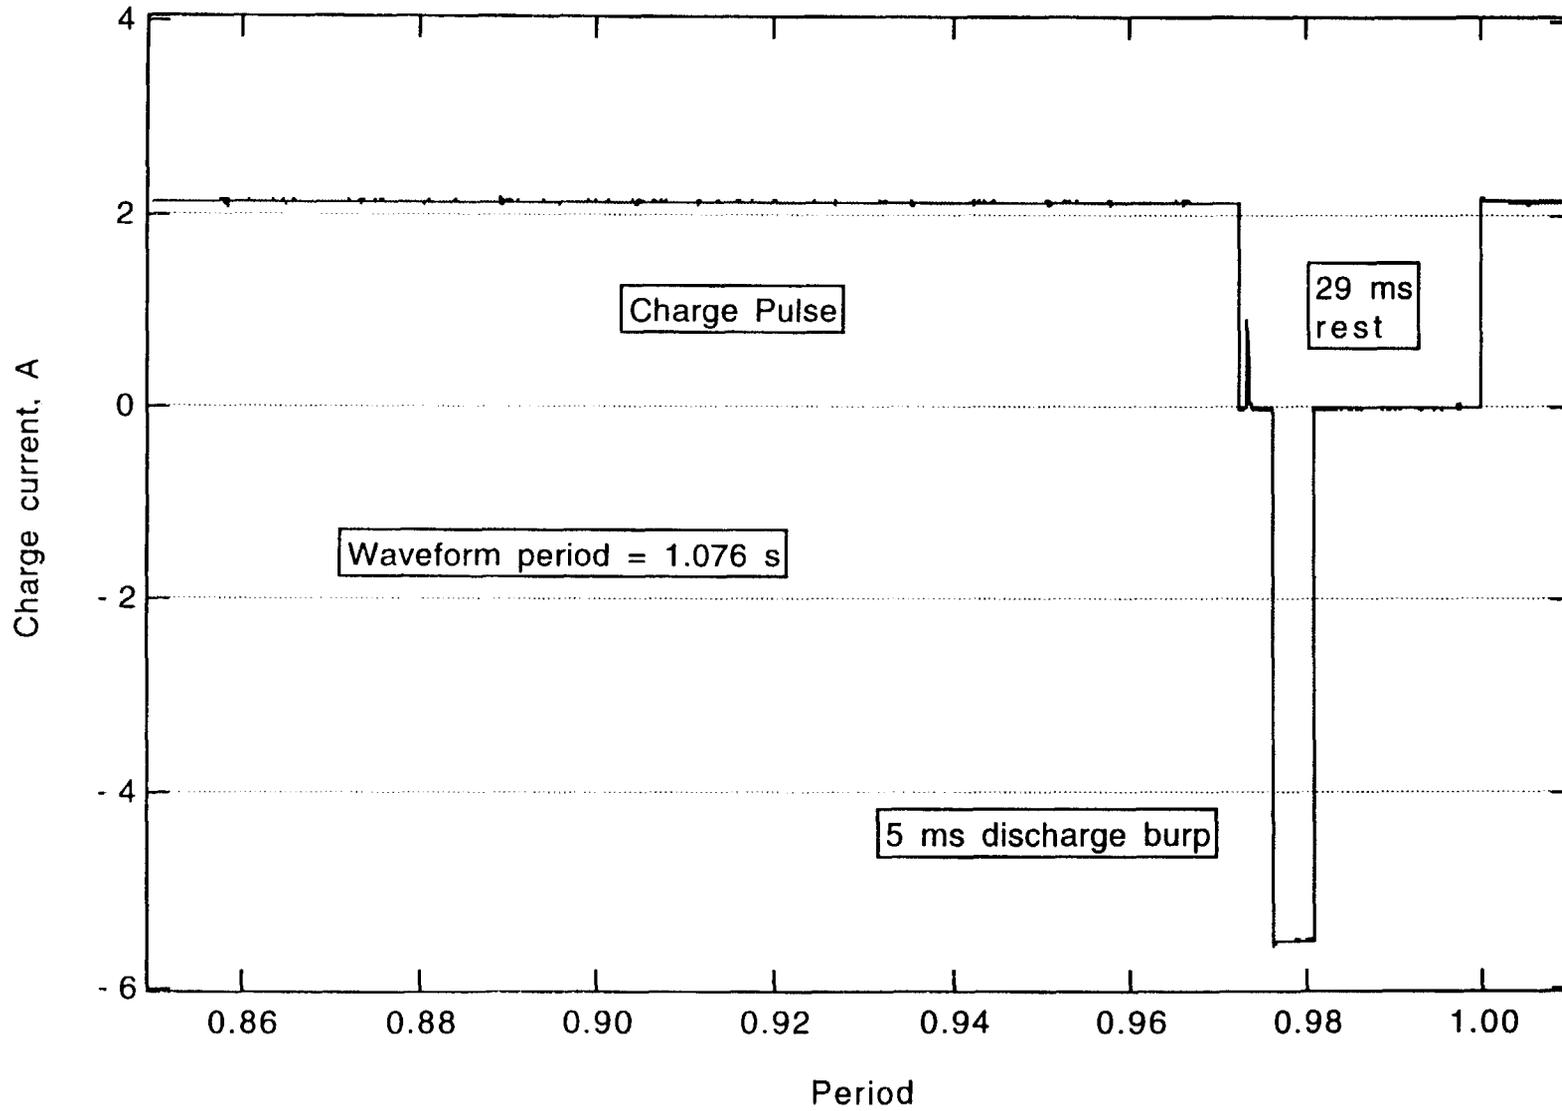

Methods to study effects of relaxation and burp discharge

	Charge Waveform	Termination Method		
		$\partial T/\partial t = X$	$\partial V/\partial t = -Y$	$\partial^2 V/\partial t^2 = 0$
Galvanostatic	Constant current	X	X	
Pause	Constant current with short relaxation periods	X	X	X
Burp	Constant current with relaxation periods and discharge burps	X	X	X

Calorimetric Results

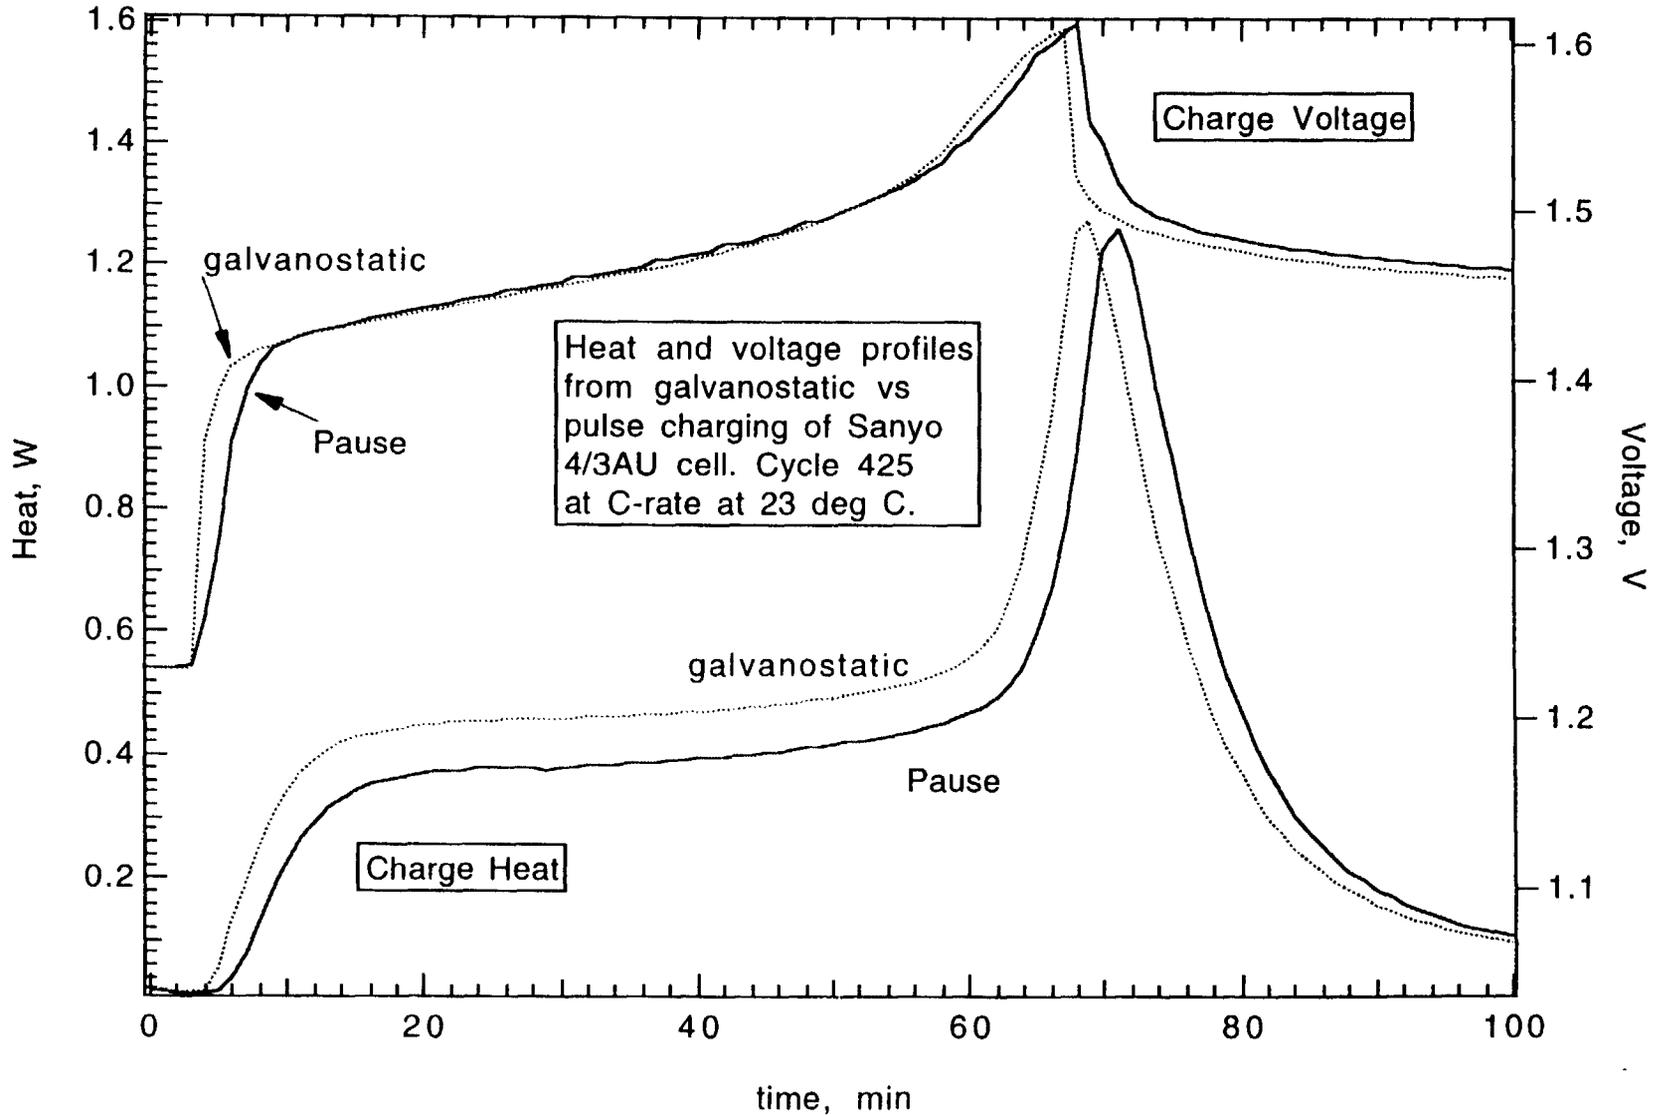

1996 NASA Aerospace Battery Workshop


-584-

Other Secondary Technologies Session


Effects of interrupting the galvanostatic charge

- Lowers Ah input rate by 2.7%
- Total Ah input lowered by 4%, while Ah output unchanged
- Overvoltages essentially the same
- Charge heat rate, W, reduced throughout the charge *
- Total charge heat, J, lowered by 8% *
- Rise in cell temperature ($T_{\text{final}} - T_{\text{init}}$) not affected *

* evaluated at 425th cycle

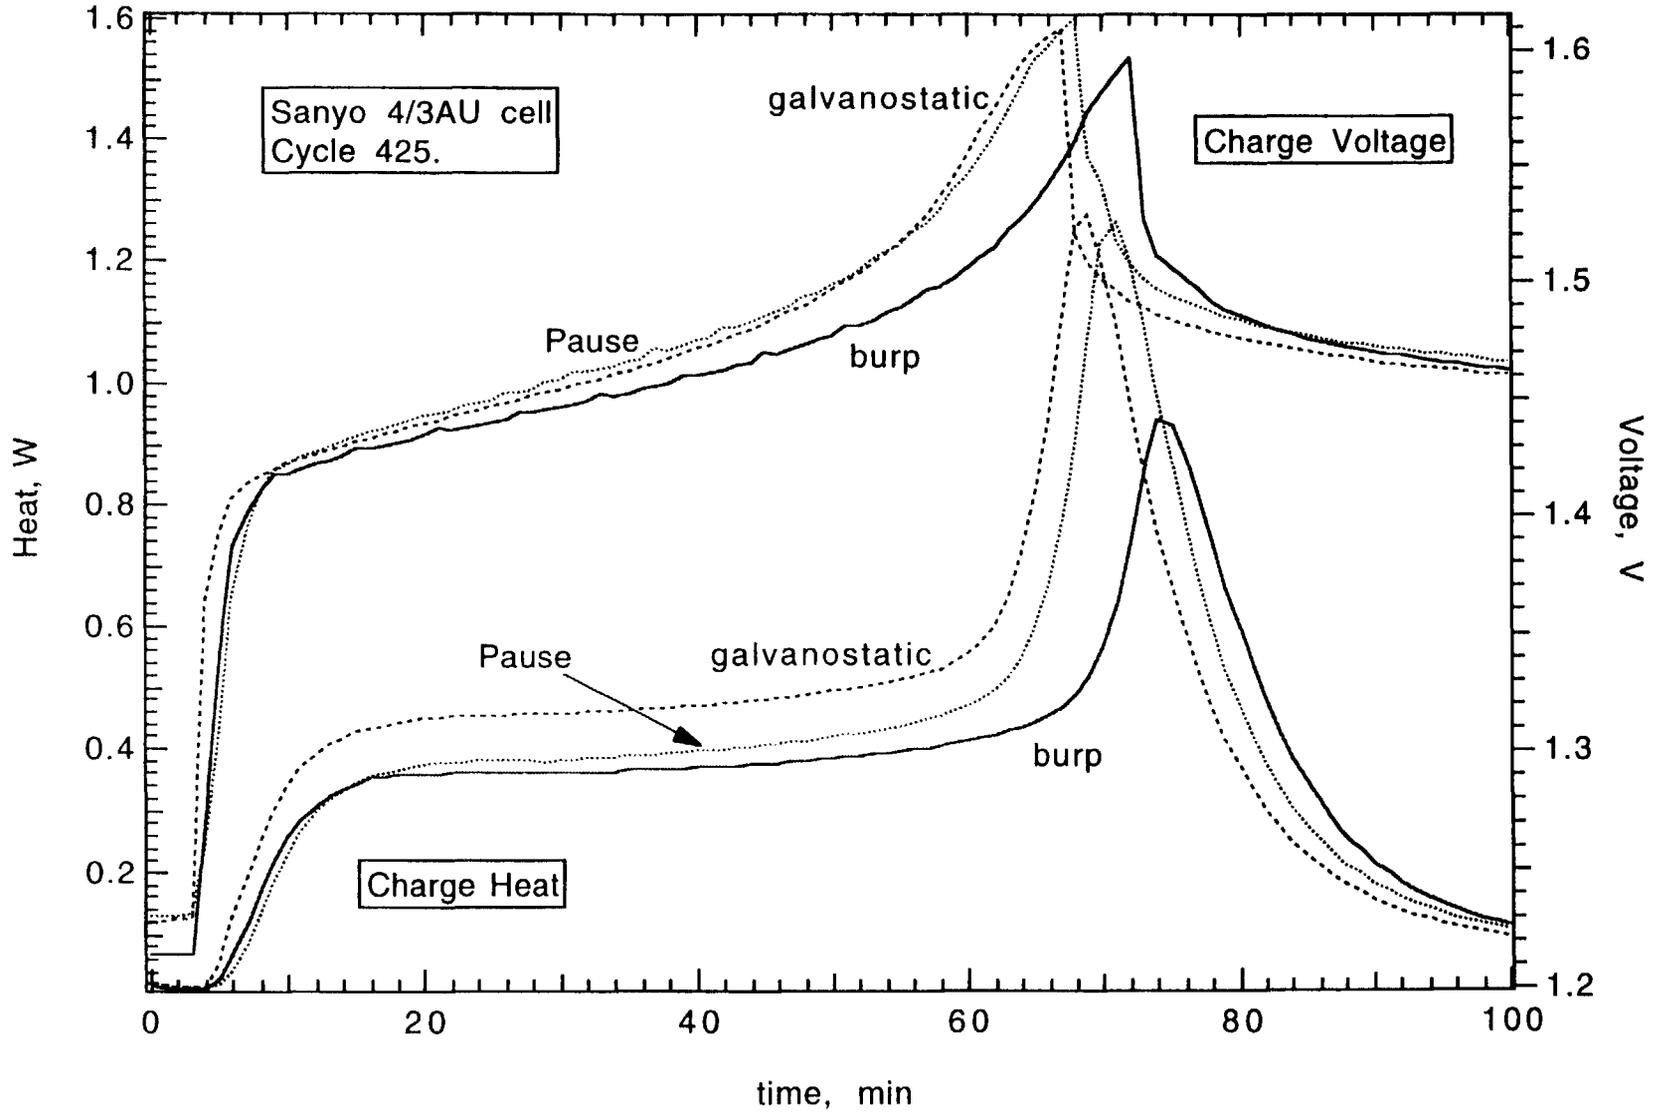

Results

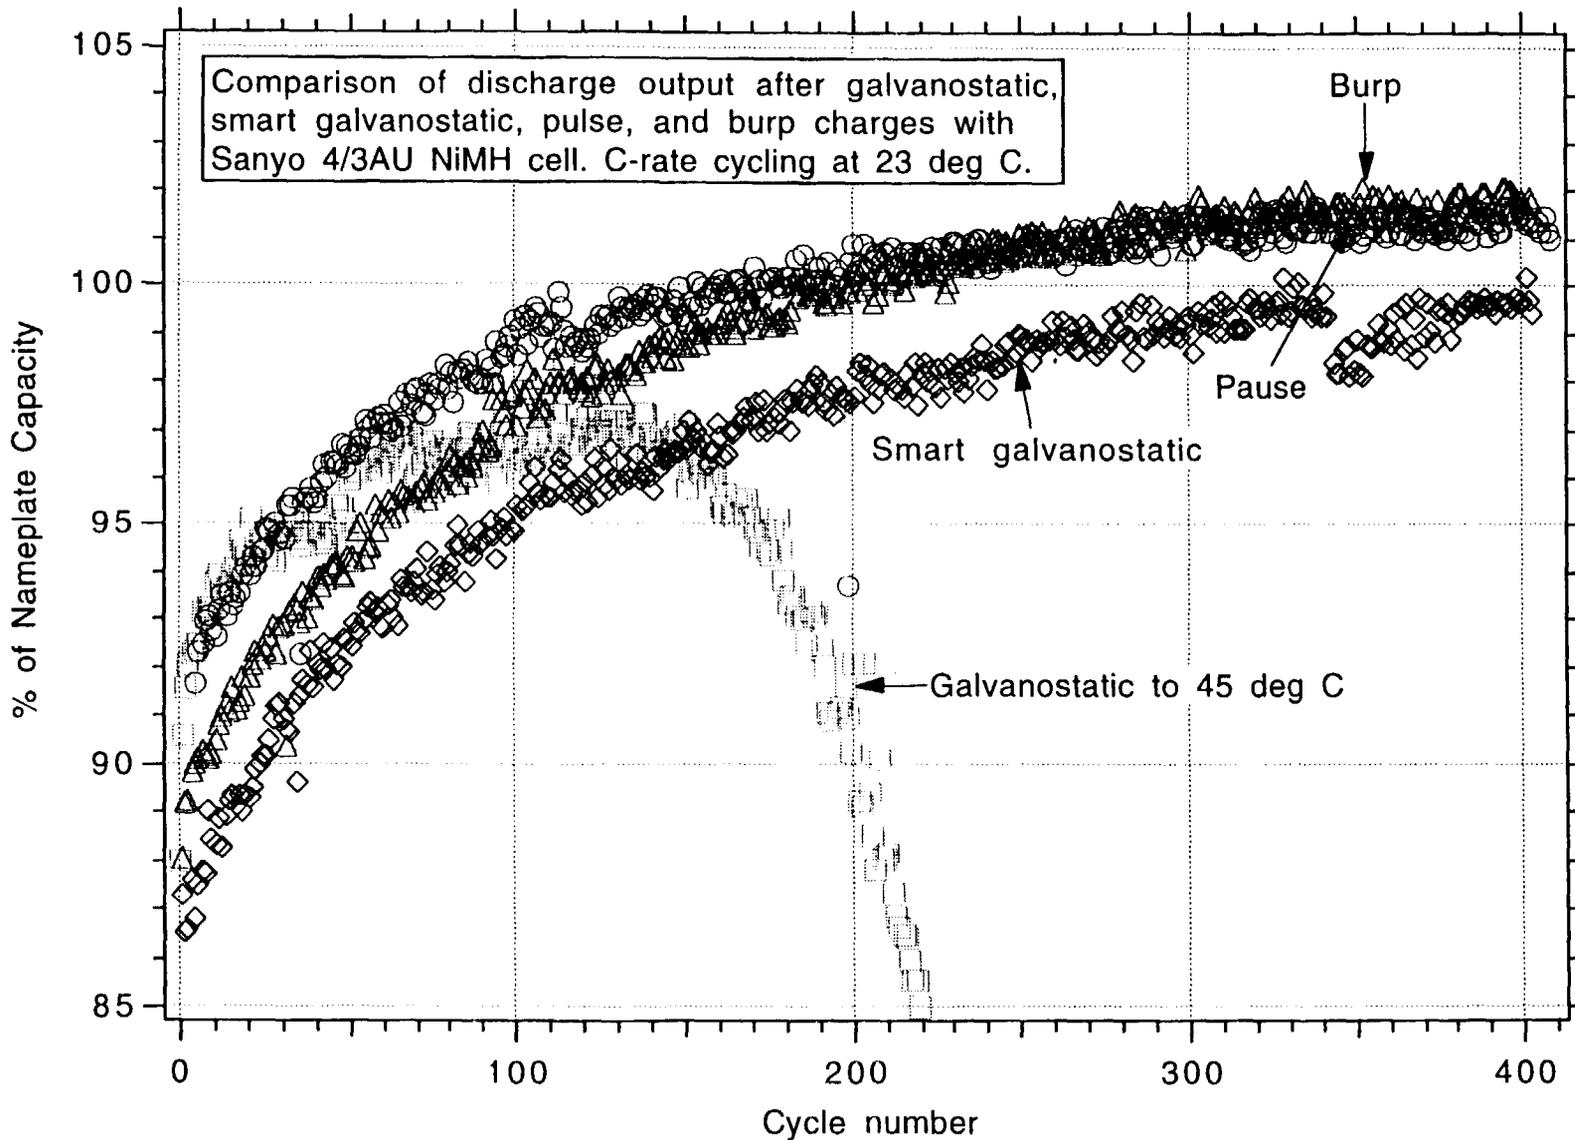

1996 NASA Aerospace Battery Workshop

-587-

Other Secondary Technologies Session

Effects of adding 5 ms discharge burps


- Reduces Ah input rate by 1.1%
- Increases total Ah input and output by 5%
- Lowers charge heat rate (e.g., by an additional 6% at midcharge point) *
- Lowers rise in cell temperature by ~ 1 °C, despite larger Ah input *
- Reduces overvoltage throughout charge (e.g., by ~ 50 mV near end of charge) *

Do differences between burp vs pause charging depend on cycle number?

- break-in period shorter with pause

Is overvoltage reduction developed with cycle number?


* evaluated at 425th cycle

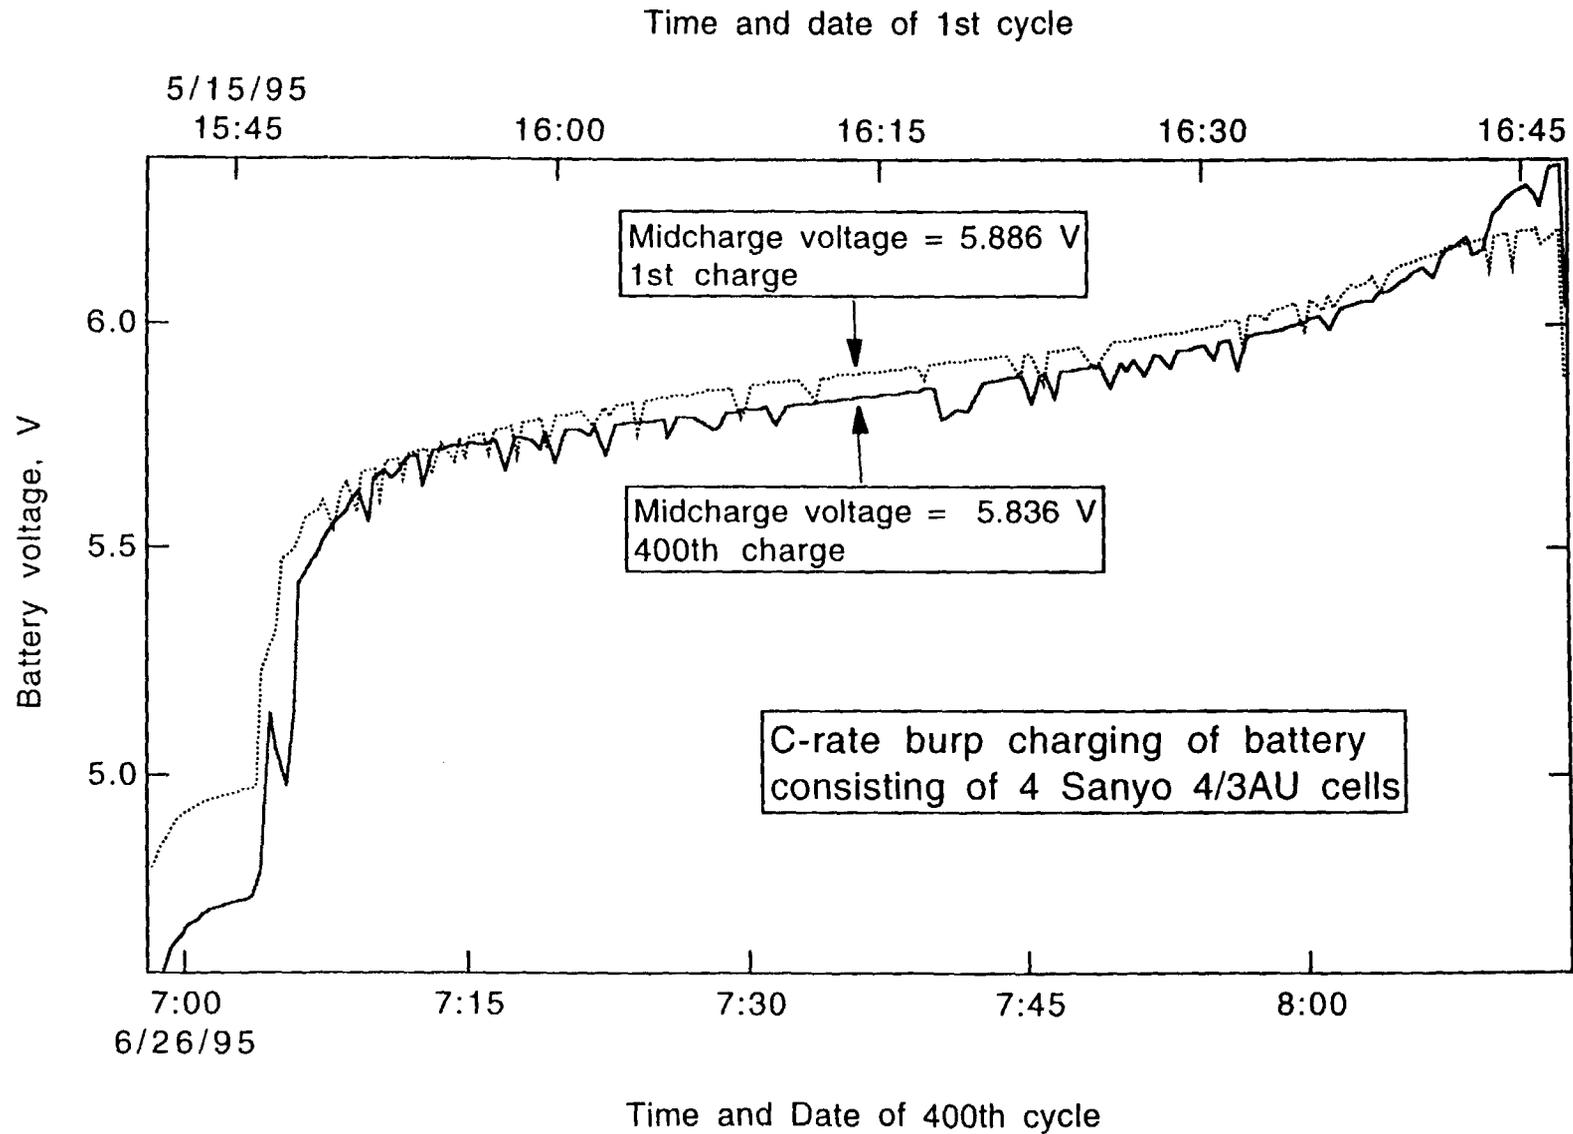



Do other NiMH cell designs exhibit similar behavior?

Performance dependent on charge method

- cycle life
- rise in cell temperature
- overvoltage
- break-in period
- etc.

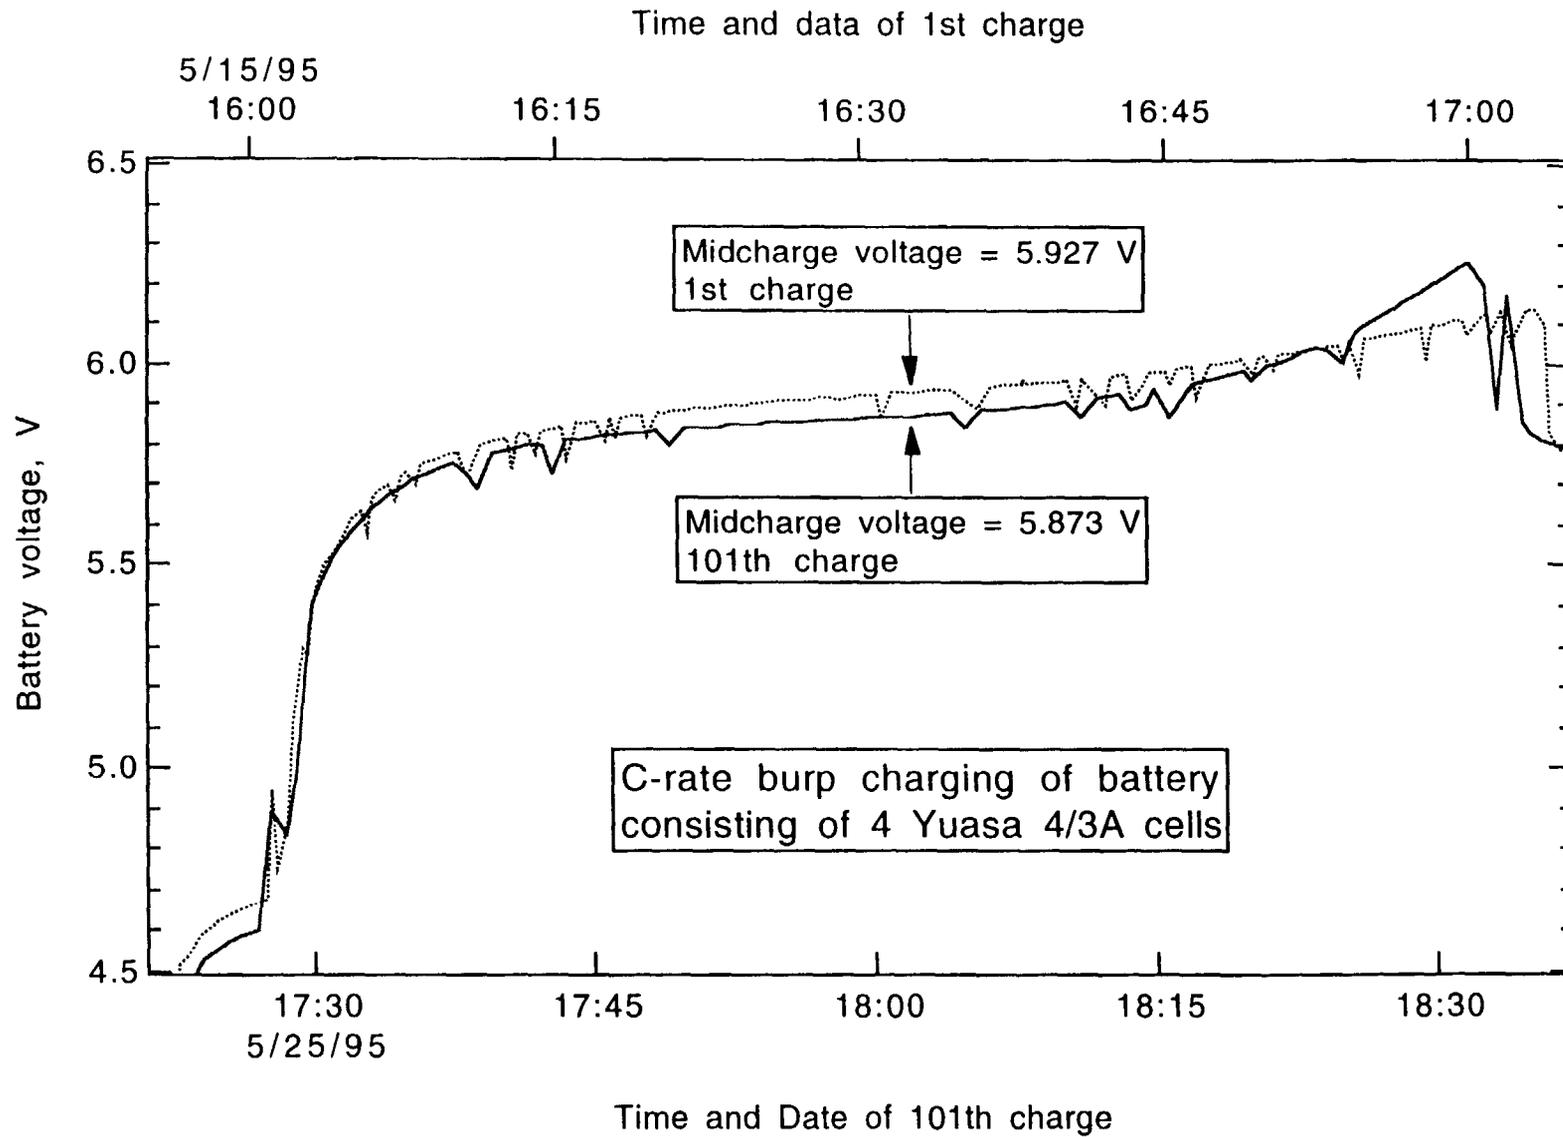

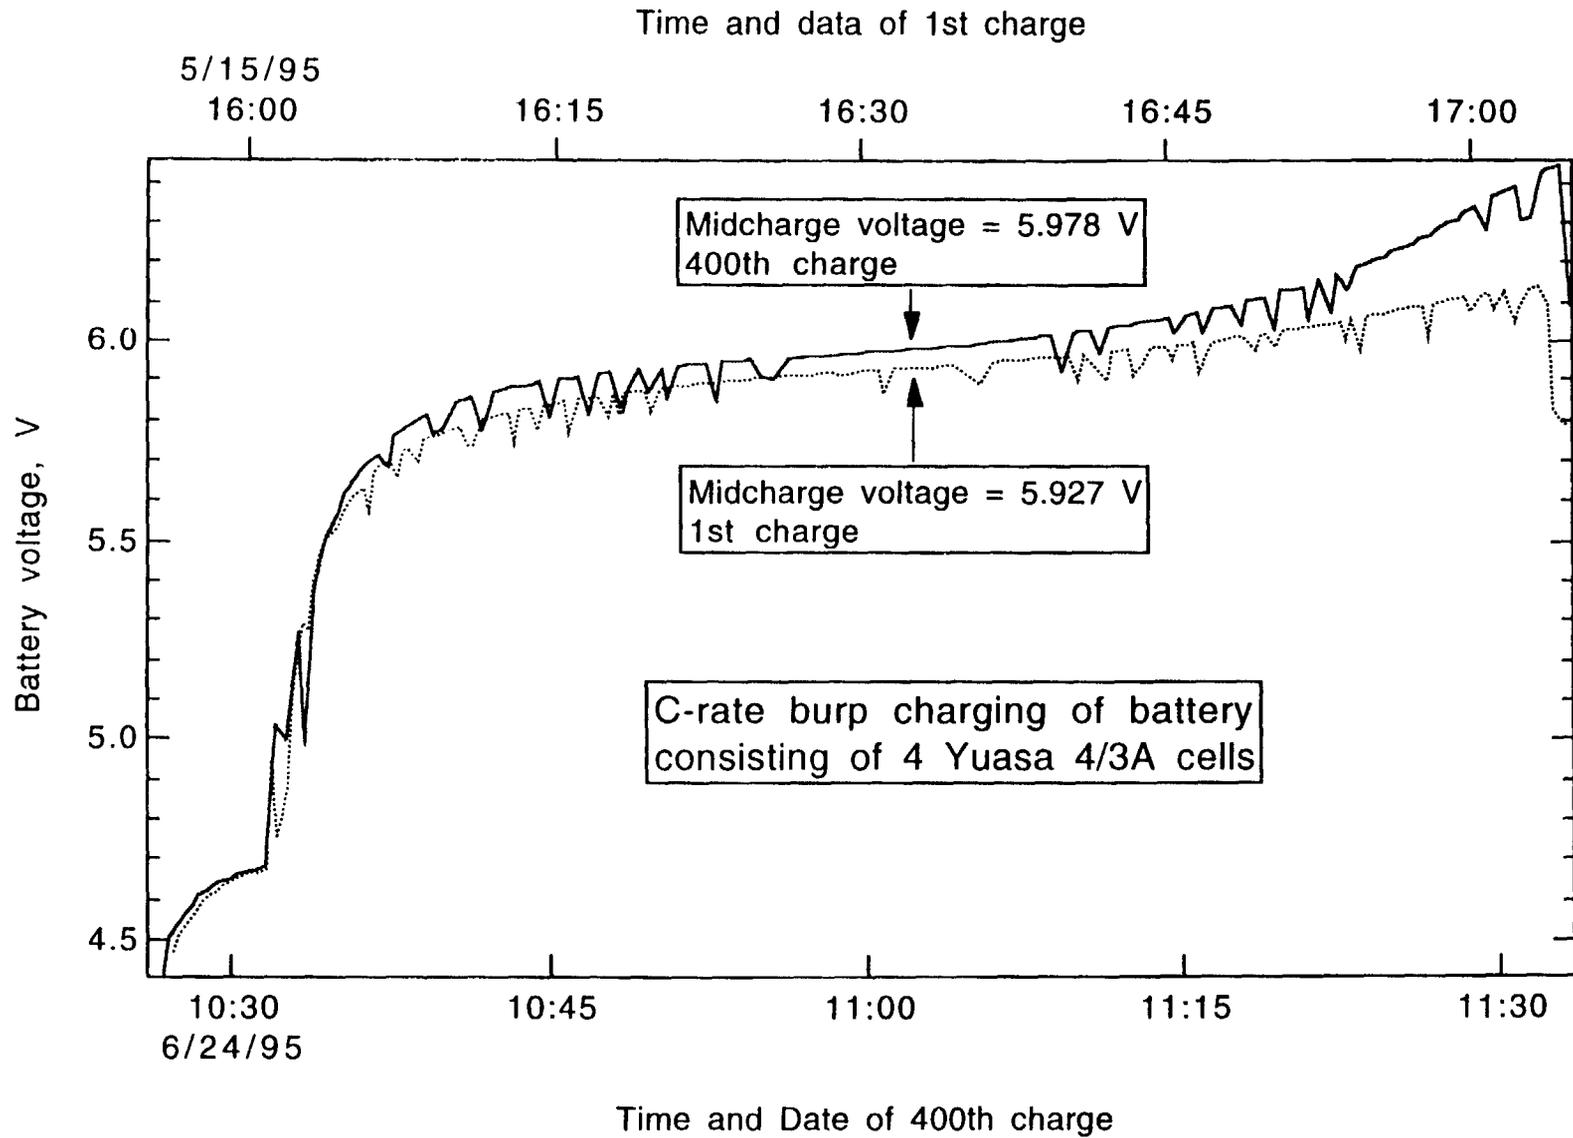

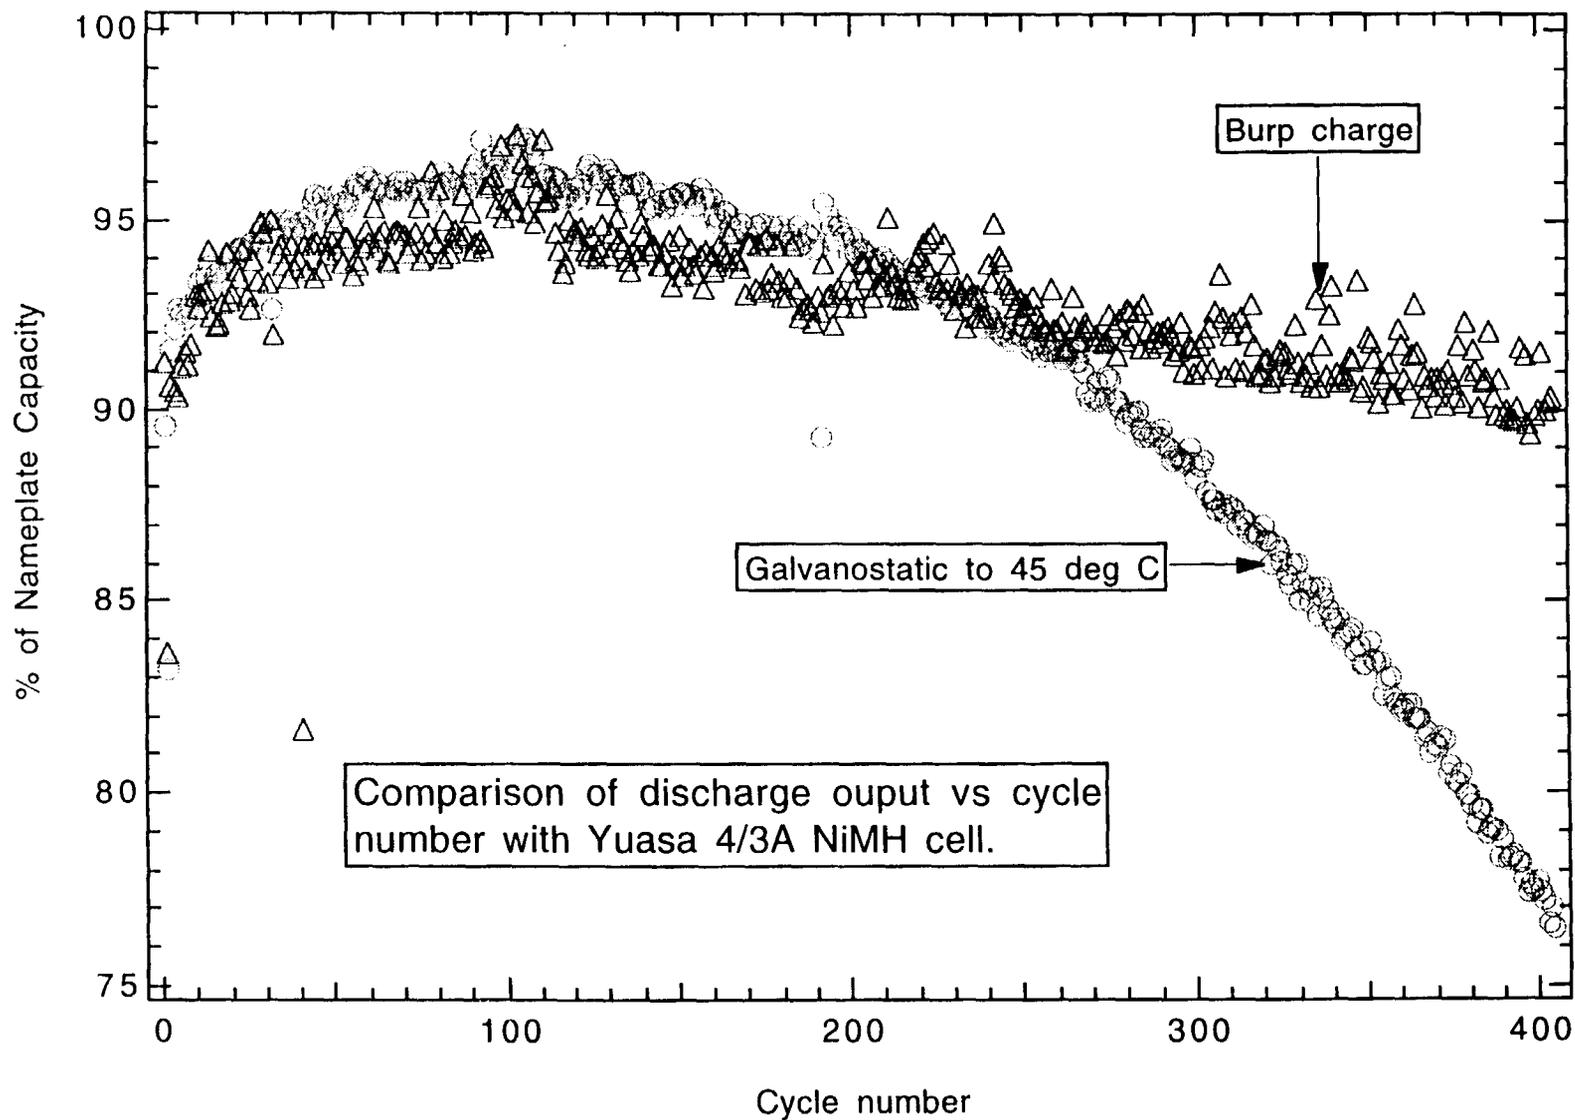

Conclusions

Addition of “smart” termination to simple galvanostatic charge *

- **prolongs cycle life**
- **lengthens break-in period**

Addition short relaxation periods to “smart” galvanostatic charge *

- **lowers total Ah input without compromising discharge capacity**
- **shortens break-in period**
- **no effect on cycle life (to 400 cycles)**

Adding very short discharge burps to the relaxation periods *

- **increases total Ah input and output by same amount**
- **lengthens break-in period**
- **no effect on cycle life (to 400 cycles)**

Burp charging improves cycle life with different NiMH cell designs

*** Based on studies with 1 cell design**

On-going Work

- Continue cycling comparison of galvanostatic, pause, and burp charging
- Compare morphology changes of electrodes
 - particle size distribution
 - porosity
- Compare burp heat effects with other cell designs
- Develop thermal model of NiMH cell based on obtained properties
 - heat capacity
 - thermoneutral potential
 - $\partial E/\partial T$

Why does burping lower overvoltage?

Possible reasons;

- **dislodges O₂ from cathode pores, preventing local current density rise**
- **increases or maintains electrode porosity, aiding ion transport**
- **results in less O₂ evolution, due to lower charge heat**

SEM analysis to date of electrodes after 400 cycles is unsupportive

- **particle size differences are small in negative electrode**
- **porosity differences not yet discernable in positive electrode**

In-situ analysis of positive electrode with 7x magnification fibroscope reveals

- **bubbling activity increases with SOC during charging**
- **differences between charge techniques are not discernable**

On-going Work

- **Compare galvanostatic, pulse, and burp charging with 50x magnification**
 - **place electrode coil from NiMH cell into a transparent KOH beaker**
 - **place a reference electrode (Hg/HgO) between the electrodes**
 - **expose a portion of positive electrode for viewing**
 - **control waveform with an automated waveform generator**
 - **mark occurrence of pulses and burps with audio signal**
 - **record video and audio of bubbling activity on positive during charge**

First Application - EMU Helmet Interchangeable Portable (EHIP) Lights

- **Battery (P/N SED39130223)**
 - 15 Sanyo NiMH cells arranged 3P-5S
 - strings connected in parallel to power 6W lights for 7 hours
 - bottom glide latches allow EVA replaceability from helmet
 - Raychem polyswitches limit current to 1.5 A/cell
 - weighs 1.04 kg
- **Charger (P/N QC-1001)**
 - charges 4 batteries in <4 hours independently and simultaneously
 - “burp” charge control achieved by 4 ICS-1702 chips
 - uses shuttle 28 \pm 4 Vdc input
 - strings connected in series (18V) during charging
 - thermistors in battery provide temperature input to charger
 - velcro mounted to mid-deck area
 - weighs 1.39 kg
- **Charger has passed all certification tests**
- **New lights, battery, and charger first flight is STS-82 in Feb 97**