

NASA/CR–2013-218022



Floating Node Method and Virtual Crack Closure Technique for Modeling Matrix Cracking-Delamination Interaction

N. V. De Carvalho
National Institute of Aerospace, Hampton, Virginia

B. Y. Chen, S. T. Pinho, and P. M. Baiz
Imperial College London, London, United Kingdom

J. G. Ratcliffe
National Institute of Aerospace, Hampton, Virginia

T. E. Tay
National University of Singapore, Singapore

NASA STI Program . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA scientific and technical information (STI) program plays a key part in helping NASA maintain this important role.

The NASA STI program operates under the auspices of the Agency Chief Information Officer. It collects, organizes, provides for archiving, and disseminates NASA's STI. The NASA STI program provides access to the NASA Aeronautics and Space Database and its public interface, the NASA Technical Report Server, thus providing one of the largest collections of aeronautical and space science STI in the world. Results are published in both non-NASA channels and by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA Programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers, but having less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or co-sponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services also include organizing and publishing research results, distributing specialized research announcements and feeds, providing information desk and personal search support, and enabling data exchange services.

For more information about the NASA STI program, see the following:

- Access the NASA STI program home page at <http://www.sti.nasa.gov>
- E-mail your question to help@sti.nasa.gov
- Fax your question to the NASA STI Information Desk at 443-757-5803
- Phone the NASA STI Information Desk at 443-757-5802
- Write to:
STI Information Desk
NASA Center for AeroSpace Information
7115 Standard Drive
Hanover, MD 21076-1320

NASA/CR–2013-218022



Floating Node Method and Virtual Crack Closure Technique for Modeling Matrix Cracking-Delamination Interaction

N. V. De Carvalho
National Institute of Aerospace, Hampton, Virginia

B. Y. Chen, S. T. Pinho, and P. M. Baiz
Imperial College London, London, United Kingdom

J. G. Ratcliffe
National Institute of Aerospace, Hampton, Virginia

T. E. Tay
National University of Singapore, Singapore

National Aeronautics and
Space Administration

Langley Research Center
Hampton, Virginia 23681-2199

Prepared for Langley Research Center
under Cooperative Agreement NNL09AA00A

July 2013

Trade names and trademarks are used in this report for identification only. Their usage does not constitute an official endorsement, either expressed or implied, by the National Aeronautics and Space Administration.

Available from:

NASA Center for AeroSpace Information
7115 Standard Drive
Hanover, MD 21076-1320
443-757-5802

Abstract

A novel approach is proposed for high-fidelity modeling of progressive damage and failure in composite materials that combines the Floating Node Method (FNM) and the Virtual Crack Closure Technique (VCCT) to represent multiple interacting failure mechanisms in a mesh-independent fashion. In this study, the approach is applied to the modeling of delamination migration in cross-ply tape laminates. Delamination, matrix cracking, and migration are all modeled using fracture mechanics based failure and migration criteria. The methodology proposed shows very good qualitative and quantitative agreement with experiments.

1 Introduction

Damage in composite materials generally occurs as a combination of different and interacting failure mechanisms, e.g. delamination and matrix cracking. Capturing these interactions accurately is essential to confidently model and predict progressive damage and failure. Many approaches have recently been proposed that explicitly model different failure mechanisms and attempt to capture their interaction [1-3]. However, no single strategy has yet surfaced as totally satisfactory. The present approach combines the Floating Node Method (FNM) [4] with the Virtual Crack Closure Technique (VCCT) [5,6] to explicitly account for different failure mechanisms and their interaction. Delamination, matrix cracking, and migration events are all modeled with the same FNM element using fracture-mechanics-based failure and migration criteria. The approach is validated using recent experimental results in which a setup capable of isolating a single complete migration event was developed [7]. Migration is defined as the transition of a delamination from its current ply interface to a new interface via transverse ply cracking. The results obtained offer a simple, yet very challenging, benchmark for the validation of numerical and analytical approaches aimed at high-fidelity modeling of composite materials, such as the one proposed in the present paper.

2 Floating Node Method (FNM)

2.1 Introduction

The FNM is a recently proposed numerical method, capable of representing multiple evolving discontinuities in solids [4]. Compared to other methods used for the same purpose, such as eXtended Finite Element Method (XFEM) or the Phantom Node Method (PNM), it provides the following key advantages. First, FNM does not introduce an error on the crack geometry when mapping to natural coordinates. Second, it does not require numerical integration over only part of a domain. Third, it is ideally suited for the representation and incorporation of multiple and complex networks of weak, strong and cohesive, discontinuities. Fourth, FNM yields the same solution as a finite element mesh where the discontinuity is represented explicitly, and finally it is conceptually simpler than the PNM or XFEM.

2.2 Element formulation

The static equilibrium of a body with volume Ω under body forces with density \mathbf{f} (acting on Ω) and traction \mathbf{t} acting on the boundary Γ_Ω can be expressed in the weak form as:

$$\int_{\Omega} \boldsymbol{\epsilon}^T(\mathbf{v})\boldsymbol{\sigma}(\mathbf{u})d\Omega = \int_{\Omega} \mathbf{v}^T\mathbf{f}d\Omega + \int_{\Gamma_\Omega} \mathbf{v}^T\mathbf{t}d\Gamma_\Omega \quad (1)$$

where \mathbf{u} is the displacement vector; \mathbf{v} is the test function; $\boldsymbol{\epsilon}$ is the strain tensor related to \mathbf{u} through the differential operator relative to Cartesian coordinates \mathcal{L}_x as $\boldsymbol{\epsilon} = \mathcal{L}_x(\mathbf{u})$; and $\boldsymbol{\sigma}$ is the stress tensor related to the strains through Hooke's law as $\boldsymbol{\sigma} = \mathbf{D}\boldsymbol{\epsilon}$, with \mathbf{D} being the constitutive tensor. In the Floating Node Method, each real node “ i ” is characterized by its nodal coordinates \mathbf{x}_i and associated Degrees of Freedom (DoF) \mathbf{q}_i . In addition, an FNM element contains a suitable number of floating DoF without pre-defined associated nodal position vectors. These additional floating nodes are used to represent discontinuities. Their number varies with the number and type of discontinuities, weak or strong, modeled within each element. A strong discontinuity is defined as a jump in a field quantity (e.g. displacements), while a weak discontinuity is defined as a jump in the gradient of a field quantity (e.g. strains). Figure 1 shows an example of such an element with four nodes and four additional sets of floating DoF required to represent a strong discontinuity.

2.2.1 Element formulation without weak/strong discontinuity

If there is no discontinuity to be modeled by the element (e.g. before failure), the formulation is the same as in the standard Finite Element Method (FEM). The vector of nodal coordinates is given as \mathbf{x}_Ω . In the case of Figure 1, \mathbf{x} is given by:

$$\mathbf{x}_\Omega^T = [\mathbf{x}_1, \mathbf{x}_2, \mathbf{x}_3, \mathbf{x}_4] \quad (2)$$

The Jacobian of the transformation from physical coordinates \mathbf{x} to natural coordinates $\boldsymbol{\xi}$ is:

$$\mathbf{J} = \frac{d\mathbf{x}}{d\boldsymbol{\xi}} = \frac{d\mathbf{N}}{d\boldsymbol{\xi}} \mathbf{x}_\Omega \quad (3)$$

where \mathbf{N} is a matrix of shape functions. Assuming an isoparametric formulation, the displacement field \mathbf{u} is related to the real DoF \mathbf{q} through:

$$\mathbf{u} = \mathbf{N}\mathbf{q} \quad (4)$$

In the case of Figure 1, $\mathbf{q}^T = [\mathbf{q}_1, \mathbf{q}_2, \mathbf{q}_3, \mathbf{q}_4]$. The strains can also be expressed in terms of the real DoF \mathbf{q} as:

$$\boldsymbol{\epsilon} = \mathcal{L}_{\mathbf{x}}(\mathbf{u}) = \mathcal{L}_{\xi}(\mathbf{N})\mathbf{J}^{-1}\mathbf{q} = \mathbf{B}\mathbf{q} \quad (5)$$

where $\mathbf{B} = \mathcal{L}_{\xi}(\mathbf{N})\mathbf{J}^{-1}$, leading to the stiffness matrix:

$$\mathbf{K} = \int_{\Xi} \mathbf{B}^T \mathbf{D} \mathbf{B} \det(\mathbf{J}) d\Xi \quad (6)$$

where Ξ is the integration domain (in natural coordinates) corresponding to Ω (in physical coordinates), and to the vector of nodal forces:

$$\mathbf{Q} = \int_{\Xi} \mathbf{N}^T \mathbf{f} \det(\mathbf{J}) d\Xi + \int_{\Gamma_{\Xi}} \mathbf{N}^T \mathbf{f} \det(\mathbf{J}) d\Xi \quad (7)$$

where Γ_{Ξ} is similarly the boundary corresponding to Γ_{Ω} . The weak form of equilibrium, Equation 1, becomes:

$$\mathbf{K}\mathbf{q} = \mathbf{Q} \quad (8)$$

2.2.2 Element formulation with weak/strong discontinuity

Once a discontinuity in the element is defined, the element is split in two or more partitions (depending on the discontinuity). Without loss of generality, a case in which the element is split in two partitions, Ω_A and Ω_B , is illustrated in Figure 1. For each partition, Ω_A and Ω_B , a vector of nodal coordinates, \mathbf{x}_{Ω_A} and \mathbf{x}_{Ω_B} , is defined. For the case in Figure 1:

$$\mathbf{x}_{\Omega_A}^T = [\mathbf{x}_5, \mathbf{x}_6, \mathbf{x}_3, \mathbf{x}_4] \quad (9)$$

$$\mathbf{x}_{\Omega_B}^T = [\mathbf{x}_1, \mathbf{x}_2, \mathbf{x}_6, \mathbf{x}_5] \quad (10)$$

Each partition has a separate Jacobian:

$$\mathbf{J}_A = \frac{d\mathbf{x}}{d\xi} = \frac{d\mathbf{N}}{d\xi} \mathbf{x}_{\Omega_A} \quad (11)$$

$$\mathbf{J}_B = \frac{d\mathbf{x}}{d\xi} = \frac{d\mathbf{N}}{d\xi} \mathbf{x}_{\Omega_B} \quad (12)$$

The displacements \mathbf{u}_A and \mathbf{u}_B , in partitions Ω_A and Ω_B , respectively, are interpolated separately from the DoFs \mathbf{q}_A and \mathbf{q}_B associated with each partition:

$$\mathbf{u}_A = \mathbf{N}\mathbf{q}_A \quad \text{and} \quad \mathbf{u}_B = \mathbf{N}\mathbf{q}_B \quad (13)$$

These DoFs, \mathbf{q}_A and \mathbf{q}_B , did not have an associated position beforehand, and therefore were considered to be “floating”. As the discontinuity is defined, they are linked to the respective

position vector. In the case of Figure 1, which represents a strong discontinuity, $\mathbf{q}_A^T = [\mathbf{q}_5, \mathbf{q}_6, \mathbf{q}_3, \mathbf{q}_4]$ and $\mathbf{q}_B^T = [\mathbf{q}_1, \mathbf{q}_2, \mathbf{q}_6', \mathbf{q}_5']$. Note that there are four different sets of floating DoF: \mathbf{q}_5 is different from \mathbf{q}_5' , and \mathbf{q}_6 is different from \mathbf{q}_6' . If a weak discontinuity were to be modeled, only two sets of floating DoF would be included in the element, and the DoF with a prime would coincide with those without a prime.

The strains then become:

$$\boldsymbol{\epsilon}_A = \mathcal{L}_x(\mathbf{u}_A) = \mathcal{L}_\xi(\mathbf{N})\mathbf{J}_A^{-1}\mathbf{q}_A = \mathbf{B}_A\mathbf{q}_A \quad (14)$$

$$\boldsymbol{\epsilon}_B = \mathcal{L}_x(\mathbf{u}_B) = \mathcal{L}_\xi(\mathbf{N})\mathbf{J}_B^{-1}\mathbf{q}_B = \mathbf{B}_B\mathbf{q}_B \quad (15)$$

The stiffness matrices for partitions Ω_A and Ω_B are:

$$\mathbf{K}_A = \int_{\Xi} \mathbf{B}_A^T \mathbf{D} \mathbf{B}_A \det(\mathbf{J}_A) d\Xi \quad (16)$$

$$\mathbf{K}_B = \int_{\Xi} \mathbf{B}_B^T \mathbf{D} \mathbf{B}_B \det(\mathbf{J}_B) d\Xi \quad (17)$$

and the force vectors:

$$\mathbf{Q}_A = \int_{\Xi} \mathbf{N}^T \mathbf{f} \det(\mathbf{J}_A) d\Xi + \int_{\Gamma_E} \mathbf{N}^T \mathbf{f} \det(\mathbf{J}_A) d\Xi \quad (18)$$

$$\mathbf{Q}_B = \int_{\Xi} \mathbf{N}^T \mathbf{f} \det(\mathbf{J}_B) d\Xi + \int_{\Gamma_E} \mathbf{N}^T \mathbf{f} \det(\mathbf{J}_B) d\Xi \quad (19)$$

Finally, the equations of equilibrium can be written as:

$$\mathbf{K}_A \mathbf{q}_A = \mathbf{Q}_A \text{ and } \mathbf{K}_B \mathbf{q}_B = \mathbf{Q}_B \quad (20)$$

2.2.3 Element topology and assembly

To illustrate this approach, a floating node element capable of modeling two weak interfaces with an arbitrary crack between them was implemented, as shown in Figure 2(a). The nodal position of the initial integration domain, and the real and floating DoF are indicated in the figure. Each floating DoF is associated with either an edge or the inner domain of the element. Once weak/strong discontinuities are detected, the floating DoF at the edges are used to determine the solution for the nodal positions given by the intersection of these discontinuities with the element edges (Figs. 2(b) to 2(e)). The additional inner floating DoF are used to determine the solution for the nodal positions originated by the intersection of multiple cracks within the element (Fig. 2(f)). In Figures 2(b) to (f) only the floating DoF used are represented. In each case, the floating DoF that are not used have no assigned position, only a topological relation to an edge or to the inner domain. During assembly, inner floating DoF can be removed from the analysis through static condensation. The floating DoF associated with the edges are assembled with the corresponding DoF of neighboring elements, and will therefore have a

unique position in the global DoF vector. All floating DoF are then used as required to model weak/strong discontinuities as they evolve throughout the simulation.

The approach can be extended to model an arbitrary number of weak and strong discontinuities within an element, and therefore an arbitrary number of plies and interacting cracks, provided the topology is adequately defined, and a sufficient number of floating DoF are used.

3 Virtual Crack Closure Technique (VCCT)

In the present work, the FNM method has been coupled to the Virtual Crack Closure Technique (VCCT) [5]. An extensive review of VCCT is provided in [6]. Traditionally, VCCT is used to obtain energy release rates in cases where the crack path is known beforehand and can be aligned with the elements' edges, such as the case for delamination.

In VCCT, the Mode I and II energy release rates are obtained from [6]:

$$G_I = \frac{1}{2a_1} F_n \llbracket q_n \rrbracket \left(\frac{a_1}{a_2} \right)^{1/2} \quad (21)$$

$$G_{II} = \frac{1}{2a_1} F_t \llbracket q_t \rrbracket \left(\frac{a_1}{a_2} \right)^{1/2} \quad (22)$$

where F_n and F_t are the normal and tangential components of internal force vector \mathbf{F} at the crack tip; $\llbracket q_n \rrbracket$ and $\llbracket q_t \rrbracket$ are the normal and tangential components of the displacement jump $\llbracket \mathbf{q} \rrbracket$ between the nodes immediately behind the crack tip; and a_1 and a_2 are the lengths of the crack in the elements behind and ahead of the crack tip, respectively (Fig. 3). When combining VCCT with FNM, the forces and displacements needed to obtain the energy release rates, Eqs (21) and (22), are computed at the floating DoF as the crack develops (Fig. 3). Additionally, floating DoF are also added along a virtual crack plane up to a distance r , named the 'enrichment radius', r_{enr} . The associated floating nodes provide additional degrees of freedom along this path, which enable the accurate modeling of the deformations near the crack tip [4]. At the end of the enrichment radius, the displacements of the floating DoF are interpolated from the displacements of the real DoF. In the present work, the enrichment radius was chosen to be equal to the largest in-plane dimensions of the numerical model.

4. Delamination propagation

In this paper, delamination is modeled using VCCT to compute the energy release rates G_I and G_{II} at each delamination front position. These are then used in a failure criterion:

$$f(G_I, G_{II}) = \frac{G_T}{G_c} - 1 = 0 \quad (23)$$

where $G_T = G_I + G_{II}$, and G_c is the critical energy release rate given by [8]:

$$G_c = G_{Ic} + (G_{IIc} - G_{Ic}) \left(\frac{G_{II}}{G_T} \right)^\eta \quad (24)$$

For delamination growth according to this criterion, G_c is assumed to equal the critical energy release rate of the interface, G_c^{Int} . The delamination front is advanced by one element along the projected crack path when $G_T = G_c^{Int}$.

5 Matrix crack propagation

In the present study, matrix crack propagation is also modeled with VCCT. However, unlike delamination, the matrix crack is assumed to propagate following a Mode I path in the through-thickness direction, as supported by experimental evidence [7]. Therefore, the failure criterion is assumed to be given by:

$$f(G_I) = \frac{G_I}{G_c} - 1 = 0 \quad (25)$$

where the critical energy release rate is given by $G_c = G_{Ic}$.

At each crack growth increment, the Mode I crack path orientation is approximately determined using a maximum tangential stress criterion. This criterion, typically written in terms of the Mode I and II stress intensity factors [9], can also be written in terms of energy release rates G_I and G_{II} , where the angle θ that maximizes the tangential stress $\sigma_{\theta\theta}$ is obtained by evaluating:

$$\theta = 2 \tan^{-1} \left(\frac{1}{4} \left[\left(\frac{G_I}{G_{II}} \right) \pm \sqrt{\left(\frac{G_I}{G_{II}} \right)^2 + 8} \right] \right) \quad (26)$$

and for the two solutions obtained choosing the one that maximizes $\widetilde{\sigma}_{\theta\theta}$ given by:

$$\widetilde{\sigma}_{\theta\theta} = \sqrt{G_I} \left\{ 3 \cos \left(\frac{\theta}{2} \right) + \cos \left(\frac{3\theta}{2} \right) \right\} + \sqrt{G_{II}} \text{Sgn}(F_t) \left\{ -3 \sin \left(\frac{\theta}{2} \right) - 3 \sin \left(\frac{3\theta}{2} \right) \right\} \quad (27)$$

where F_t is the tangential component of the internal force vector \mathbf{F} at the crack tip. The tangential stress $\sigma_{\theta\theta}$ relates to $\widetilde{\sigma}_{\theta\theta}$ by:

$$\sigma_{\theta\theta} = \frac{1}{4} \sqrt{\frac{E^*}{2\pi r}} \widetilde{\sigma}_{\theta\theta} \quad (29)$$

where,

$$E^* = \begin{cases} E & \text{plane stress} \\ \frac{E}{1-\nu^2} & \text{plane strain} \end{cases} \quad (30)$$

E is the Young's modulus; and ν the Poisson's ratio. Once the angle is determined, the criterion given by Eq. (25) is assessed. If the criterion is met, the crack advances by one element along the projected crack path.

6 Migration

6.1 Delamination to matrix crack – migration criterion

Extensive research has been done on migration of cracks from a bi-material interface. He and Hutchinson [10] have proposed a necessary condition for migration to occur:

$$\frac{G_{max}^B}{G_c^B} > \frac{G_T^{Int}}{G_c^{Int}} \quad (31)$$

This condition states that for a crack to migrate from an interface into a given Material B, as shown in Figure 4, the ratio between the energy release rate associated with its growth into that material G_{max}^B , (at an angle ω_{max} that maximizes its value) and the critical energy release rate of that material G_c^B , has to be higher than the ratio between the energy release rate associated with the growth of the crack along the interface G_T^{Int} , and the critical energy release rate G_c^{Int} of that interface.

With the approach proposed, evaluating Eq. (31) would require more than one FE analysis at each interface crack position. In each of these analyses, a branched crack would need to be initiated at different tentative angles ω in order to determine the angle, ω_{max} , that would maximize G^B .

In the present work, an alternative criterion is proposed. With this criterion, all variables needed to determine whether migration occurs, can be directly obtained from the FNM results at the each interface crack position. The criterion states that: (i) the sign of the tangential component of the internal force vector F_t , associated with Mode II shear displacement, dictates the direction and therefore the material into which the interface crack migrates and (ii) migration can only be completed if it is energetically favorable. The criterion is given by $M_B^A: \{G_T^{Int}, F_t\} \rightarrow \{-1, 0, 1\}$ as:

$$M_B^A = \begin{cases} \left(\frac{\text{Sgn} \left(\frac{G_T^{Int}}{G_c^A} - \frac{G_T^{Int}}{G_c^{Int}} \right) + 1}{2} \right) \text{Sgn}(F_t), & \text{Sgn}(F_t) < 0 \\ \left(\frac{\text{Sgn} \left(\frac{G_T^{Int}}{G_c^B} - \frac{G_T^{Int}}{G_c^{Int}} \right) + 1}{2} \right) \text{Sgn}(F_t), & \text{Sgn}(F_t) > 0 \end{cases} \quad (32)$$

If $M_B^A = 0$ the interface crack does not migrate, and if $M_B^A = -1$ or $M_B^A = 1$ the crack migrates into material A or B, respectively. In the present form, Eq. (32) assumes that internal force vector is computed at the lower surface (Material B). If the internal force vector is computed at the upper surface the signs of the inequalities in Eq. (32) need to be reversed. Depending on the sign of F_t , the ratio between the energy release rate determined at the interface, and the critical energy release rate of Material A or B, $\frac{G_T^{Int}}{G_c^A}$ or $\frac{G_T^{Int}}{G_c^B}$, is compared to the ratio between the energy release rate determined at the interface and the critical energy release rate of the interface, $\frac{G_T^{Int}}{G_c^{Int}}$. If the

ratio $\frac{G_T^{Int}}{G_c^A}$ or $\frac{G_T^{Int}}{G_c^B}$ is greater than $\frac{G_T^{Int}}{G_c^{Int}}$, the necessary condition for migration is met, and $M_B^A = -1$ or $M_B^A = 1$. With this criterion, all variables needed to determine whether migration occurs, F_t and G_T^{Int} , can be directly obtained from the FNM results. Note that although this criterion is necessary, it is not sufficient for migration to occur unless the ratio being assessed is greater than one.

In the present work, the interfacial crack, or delamination, propagates between a 0° and a 90° ply. Assuming Material A is the 0° ply, and Material B is the 90° ply, the critical energy release rate to propagate a crack into a 0° ply is much greater than the critical energy release rate of the interface, since fiber fracture is required for that process to occur, i.e. $G_c^{0^\circ} = G_c^A \gg G_c^{Int}$ [11]. Thus, $\frac{G_T^{Int}}{G_c^A}$ is always smaller than $\frac{G_T^{Int}}{G_c^{Int}}$. Therefore, even if the sign of F_t favors migration into Material A, migration will not occur, since it is not energetically favorable. Typically for composite laminates, the critical energy release rate of an interface crack (delamination) and of a matrix crack are of the same order of magnitude, i.e. $G_c^{90^\circ} \approx G_c^{Int}$ [12]. Hence, G_c^{Int} is assumed to be given by Eq. (24) and $G_c^{90^\circ}$ to be equal to G_{Ic} . Therefore, assuming Material B is the 90° ply, provided the sign of F_t favors migration into Material B and it is energetically favorable, migration can occur.

6.2 Matrix crack to delamination – migration criterion

When a matrix crack reaches a weak interface, it is assumed to trigger delamination. This delamination is at first contained within the FNM element, as illustrated in Figure 2(f). In the following steps, the delamination will propagate, or migrate, as detailed in Sections 4 and 6.1, respectively.

7 Simulation of delamination migration specimens

7.1 Delamination migration test configuration

In reference [7] a test aimed at investigating delamination migration was proposed. Its configuration is illustrated in Figure 5. The specimen possesses three main features that permit the controlled observation of delamination growth followed by migration to another ply interface. First, the specimen geometry is in the form of a beam with the intent of promoting uniform delamination growth and migration across the specimen width. Second, the specimen contains a PTFE insert (acting as an artificial delamination) at an interface between a 0° ply (specimen span direction) and a stack of four 90° plies (specimen width direction) (Fig. 5). This provides an opportunity for the delamination to migrate to another ply interface by kinking through the 90° ply stack. Third, the specimen can be loaded in a manner to cause delamination growth from the PTFE insert that eventually migrates to another ply interface. This sequence of fracture events is made possible by the way in which specimen loading affects shear stresses acting across the delamination front.

7.2 Finite Element Model

The experiments presented in [7] were simulated using the finite element solver ABAQUS/Standard® (Implicit). Plane-stress and a small-displacement formulation were used. The floating node element (Fig. 2) was developed and implemented as a user defined element (UEL) in ABAQUS, and applied in the center region of the model, as shown in Figure 6. The specimen layout used in the experiments and in the model, is also given in Figure 6. In the layout description T represents the PTFE insert. Each block of plies of the same orientation was modeled with a separate element CPS4 (through-thickness), except for the highlighted plies at the center of the model (Fig. 6). These were modeled within a single FNM element, as illustrated in Figure 2. The material properties used are given in Tables 1 and 2. A prescribed displacement was applied at different positions, L , at a single node, to simulate the displacement-controlled test. Four load positions were simulated corresponding to $L = \{a_0, 1.1a_0, 1.2a_0, 1.3a_0\}$ (Fig. 6). In the experiments, the specimens were subject to moisture intake from the ambient air leading to relaxation of residual thermal stress. Therefore, residual thermal stresses were not considered.

7.3 Load-displacement response and sequence of events

The computed load-displacement curves obtained for different values of L are given in Figure 7. Even accounting for the compliance of the test fixture, measured in [7], all load-displacement curves obtained from the simulations show a slightly stiffer response than what was observed experimentally. The maximum load is in general very well predicted for the cases $L = a_0$ to $L = 1.2a_0$, and slightly over-predicted for the case $L = 1.3a_0$ (Figs. 7(a) to 7(d)). For $L = a_0$, the simulations predict unstable delamination after the peak load (Fig. 7(a)). This unstable delamination stops just before migration. After the migration event, delamination continues stably along the next $0^\circ/90^\circ$ interface. A similar sequence of events was observed experimentally [7]. However, in the experiments, after the first unstable event, further loading was necessary before migration occurred. For the cases $L = 1.1a_0$ to $L = 1.3a_0$, the simulations predict that (i) the first peak in load is followed by a region of stable delamination growth (Figs 7(b) to 7(d)) that increases with the load offset, and that (ii) stable delamination is followed by a region of unstable delamination, which corresponds to the load-drop in Figures 7(b) to 7(d). The migration event occurs within this load-drop. After the migration, unstable delamination continues propagating along the next $0^\circ/90^\circ$ interface. Loading the specimen further eventually leads to a transition from unstable to stable delamination propagation. This sequence of events is very similar to what was reported experimentally [7]. The main difference is that in the experiments, for the cases $L = 1.2a_0$ and $L = 1.3a_0$, after the peak load, delamination propagates through a series of unstable events, rather than stably, as predicted by the simulations.

7.4 Migration location

Figure 8(a) provides an illustration of the typical crack paths predicted by the simulations and obtained experimentally. Figure 8(b) compares numerical and experimental results for the distance from the load-application point at which migration onset occurs, Δ_K , as a function of the normalized load offset, L/a_0 . Overall, except for $L = a_0$, migration is predicted to occur closer to the load application point than what was observed experimentally. The simulations also

predict a decreasing trend in Δ_K with L/a_0 , which is similar to what was observed experimentally for the cases $L = 1.1a_0$ to $L = 1.3a_0$.

7.5 Matrix crack path

In Figure 9, the simulated matrix crack paths obtained for the different load positions was superimposed on an image of a typical crack path observed experimentally, where $L = a_0$. The predicted matrix crack path agrees well the crack path observed experimentally [7]. The simulations do not predict variation in the matrix crack path with a change in load offset.

7.6. Discussion

All load-displacement curves obtained numerically show a slightly stiffer response than the experimental results. In the simulations, the engineering properties used were obtained from uniaxial test data. These are known to be higher than their flexural counterparts [13]. Since the specimen is predominantly loaded in flexure, the difference between uniaxial and flexural properties is therefore likely to be the cause for the overall stiffer response obtained in the simulations. Overall, the simulated load-displacement curves, sequence of events, and failure morphology are in very good agreement with the experimental results. For the case $L = a_0$, experimental results show an increase in load at the end of the first unstable event, before migration. This increase in load is likely to be caused by the development of fiber bridging during the unstable part of the delamination, which was not accounted for in the model. For the load cases $L = 1.2a_0$ to $L = 1.3a_0$, the only significant difference between simulations and experiments is that delamination growth onset and propagation, prior to the final load-drop see (Figs. 7(c) and 7(d)), does not occur stably as predicted in the simulations, but rather through a series of unstable events. In these experiments the unstable delamination growth onset was likely due to the presence of resin rich pockets at the tip of the PTFE insert, while the subsequent unstable events, prior to the final load-drop, may be due to features accompanying delamination growth, such as fiber bridging. Both of these were not accounted for in the simulations.

The migration location was slightly under-predicted for all cases except $L = a_0$. Nevertheless, the migration location trend observed experimentally, for the cases $L = 1.1a_0$ to $L = 1.3a_0$, was well captured. This further supports the validity of the approach, and in particular, of the migration criterion proposed. The latter is additionally confirmed by the good agreement between the predicted matrix crack path and that observed experimentally. This also suggests that the criterion used to determine the matrix crack orientation (as it propagates in the through-thickness direction) is adequate.

8. Conclusions

A novel approach that combines the FNM (Floating Node Method) with VCCT (Virtual Crack Closure Technique) has been demonstrated to adequately capture delamination migration in cross-ply laminates. Delamination, matrix cracking, and migration, are all modeled with the same FNM element using fracture mechanics based failure and migration criteria. Results show very good agreement with the maximum load, and migration location obtained experimentally. In addition, simulations capture the overall failure morphology and typical crack path, observed in the experiments.

References

- [1] D. Ling, Q. Yang, B. Cox, “An augmented finite element method for modeling arbitrary discontinuities in composite materials,” *International journal of fracture*, Vol. 156, No. 1, pp. 53-73, 2009.
- [2] E. V. Iarve, M. R. Gurvich, D. H. Mollenhauer, C. A. Rose and C. G. Dávila, “Mesh-independent matrix cracking and delamination modeling in laminated composites,” *International Journal for Numerical Methods in Engineering*, Vol. 88, No. 8, pp. 749-773, 2011.
- [3] F. P. van der Meer, L. J. Sluys, S. R. Hallet and M. R. Wisnom, “Computational modeling of complex failure mechanisms in laminates,” *Journal of Composite Materials*, Vol. 46, No. 5, pp. 603-623, 2012.
- [4] B.Y. Chen, S. T. Pinho, P. M. Baiz, N. V. De Carvalho and T. E. Tay, “Floating node method for the modeling of multiple discontinuities within an element,” *19th International conference on Composite Materials*, Montreal, 2013.
- [5] E. F. Rybicki and M. F. Kanninen, “A finite element calculation of stress intensity factors by a modified crack closure integral,” *Eng. Fract. Mech.* Vol. 9, pp. 931-938, 1977.
- [6] R. Krueger, “Virtual crack closure technique: history, approach and applications,” *Applied Mechanics Reviews*, Vol. 57, pp. 109-143, 2004.
- [7] J. G. Ratcliffe, M. W. Czabaj, T. K. O’Brien, “Characterizing delamination migration in carbon/epoxy tape laminates,” *Proceedings of the American Society for Composites – Twenty-Seventh Technical Conference*, Arlington, TX, USA, paper 313, 2012.
- [8] M.L. Benzeggagh and M. Kenane, “Measuring of mixed-mode delamination fracture toughness of unidirectional glass/epoxy composites with mixed-mode bending apparatus,” *Composites Science and Technology*, Vol. 56, pp. 439-449, 1996.
- [9] N. Moës, J. Dolbow and T. Belytschko, “A finite element method for crack growth without remeshing,” *Int. J. Numer. Meth. Engng.* Vol. 46, pp. 131-150, 1999.
- [10] He, M-Y., and J. W. Hutchinson, “Kinking of a crack out of an interface,” *Journal of Applied Mechanics*, Vol 56, pp. 270-278, 1989.
- [11] M.J. Laffan, S.T. Pinho, P. Robinson and A.J. McMillan, “Translaminar fracture toughness: The critical notch tip radius of 0° plies in CFRP,” *Composites Science and Technology*, Vol. 72, No 1, pp. 97-102, 2011.
- [12] M. W. Czabaj and J. G. Ratcliffe, “Comparison of intralaminar and interlaminar mode-I fracture toughness of unidirectional IM7/8552 graphite/epoxy composite,” *Proceedings of the American Society for Composites – Twenty-Seventh Technical Conference*, Arlington, TX, USA, paper 114, 2012
- [13] T. K. O'Brien, G. B. Murri and S. A. Salpekar, “Interlaminar shear fracture toughness and fatigue thresholds for composite materials,” *Composite Materials: Fatigue and Fracture*, Vol. 2, ASTM STP 1012, Paul A. Lagace, Ed., American Society for Testing and Materials, Philadelphia, pp. 222-250, 1989.
- [14] T. K. O'Brien and R. Krueger, “Analysis of flexure tests for transverse tensile strength characterization of unidirectional composites,” *Journal of Composites Technology and Research*, Vol 25, pp. 50-68, 2003.
- [15] R. Krueger, “Development of and application of benchmark examples for mixed-mode I/II quasi-static delamination propagation predictions,” NASA/CR-2012-217562, 2012.

Table 1. Elastic properties, IM7-8552 [14].

| E_{11} (GPa) | $E_{22} = E_{33}$ (GPa) | $\nu_{12} = \nu_{13}$ | ν_{23} | $G_{12} = G_{13}$ (GPa) | G_{23} (GPa) | α_1 (K ⁻¹) | $\alpha_2 = \alpha_3$ (K ⁻¹) |
|-------------------|----------------------------|-----------------------|------------|----------------------------|-------------------|----------------------------------|---|
| 161.0 | 11.38 | 0.32 | 0.44 | 5.17 | 3.98 | 1×10^{-5} | 31×10^{-6} |

Table 2. Critical energy release rates for delamination of IM7-8552 [15].

| G_{Ic} (kJ/m ²) | G_{IIc} (kJ/m ²) | η |
|----------------------------------|-----------------------------------|--------|
| 0.21 | 0.77 | 2.1 |

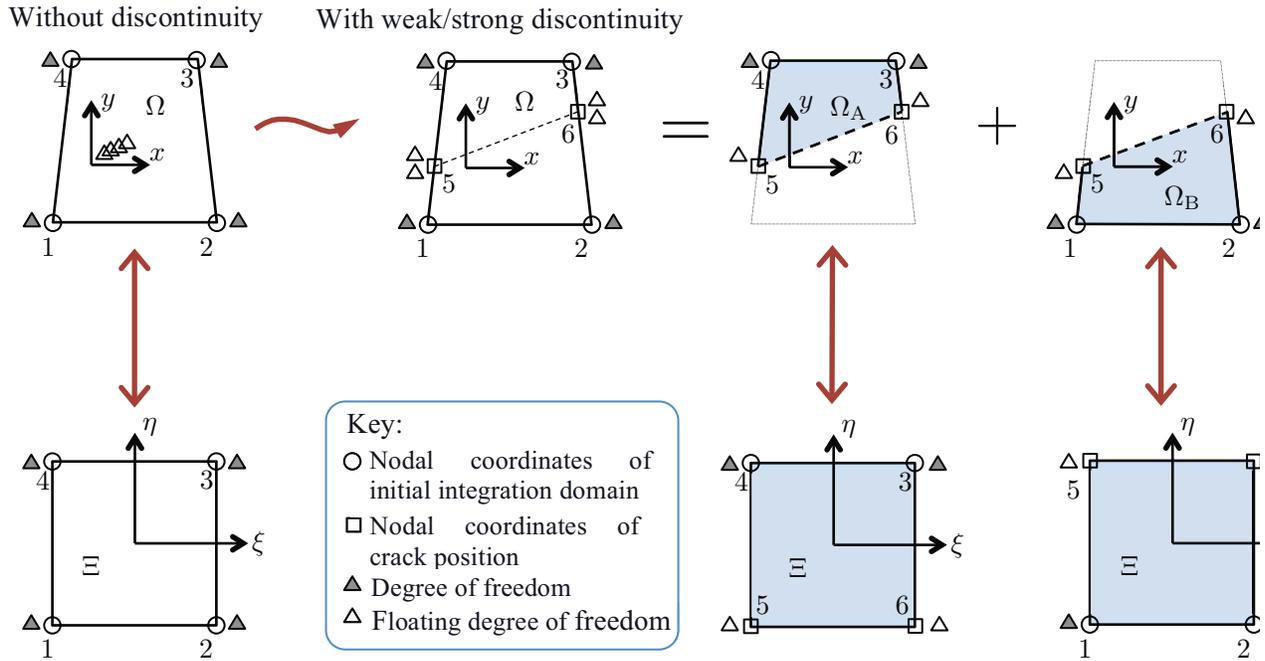


Figure 1. Overview of the Floating Node Method (FNM).

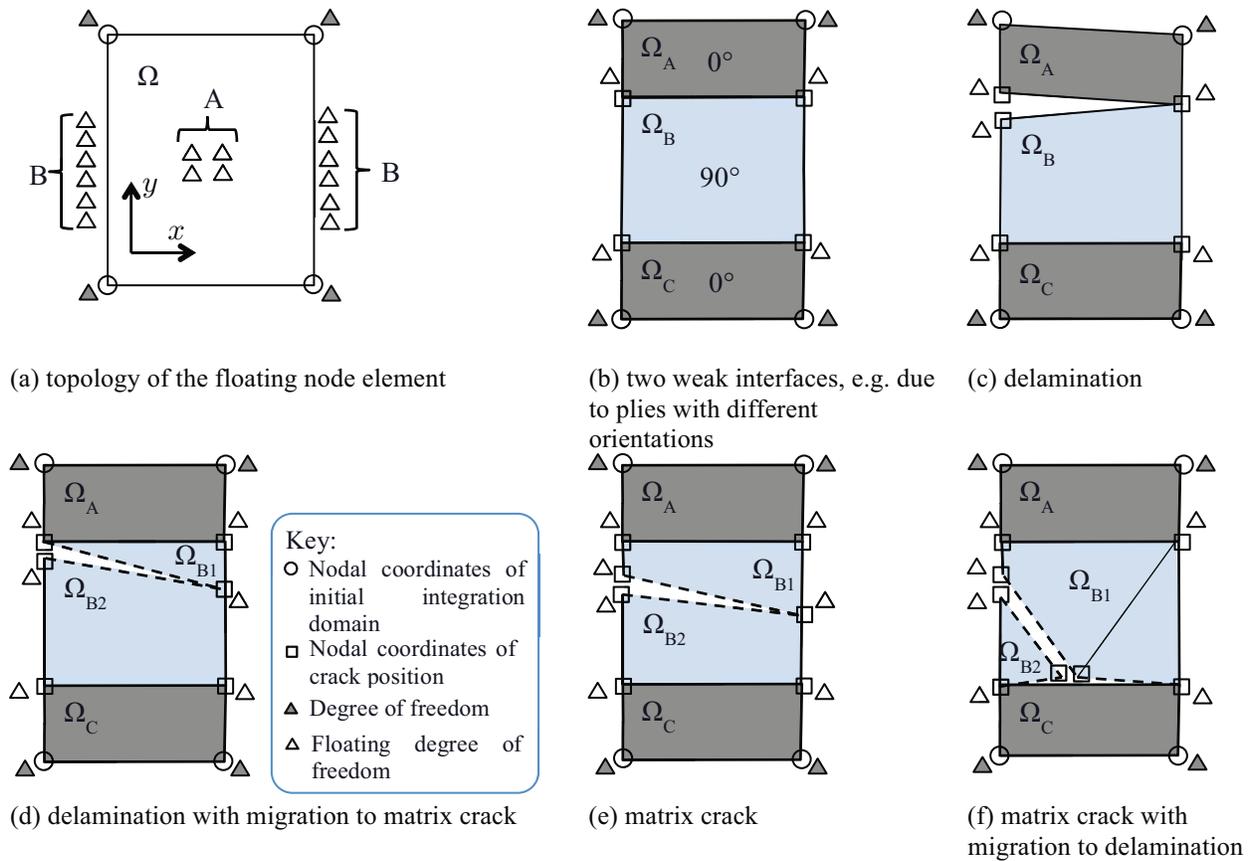


Figure 2. Floating node element used showing different weak/strong discontinuities scenarios

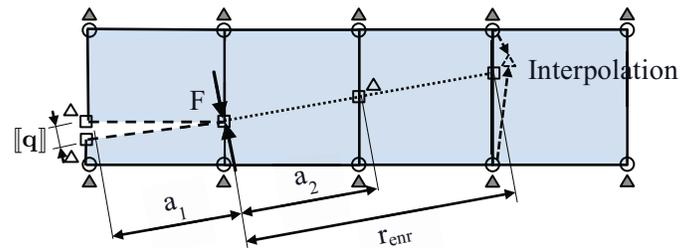


Figure 3. Virtual Crack Closure Technique and Floating Node Method for arbitrary crack propagation.

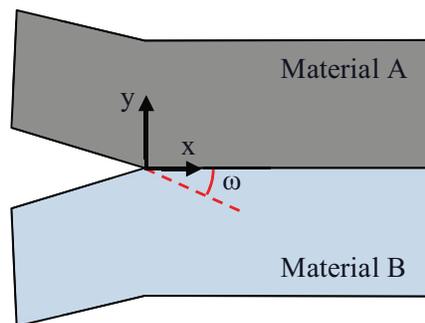


Figure 4. Bi-material interface.

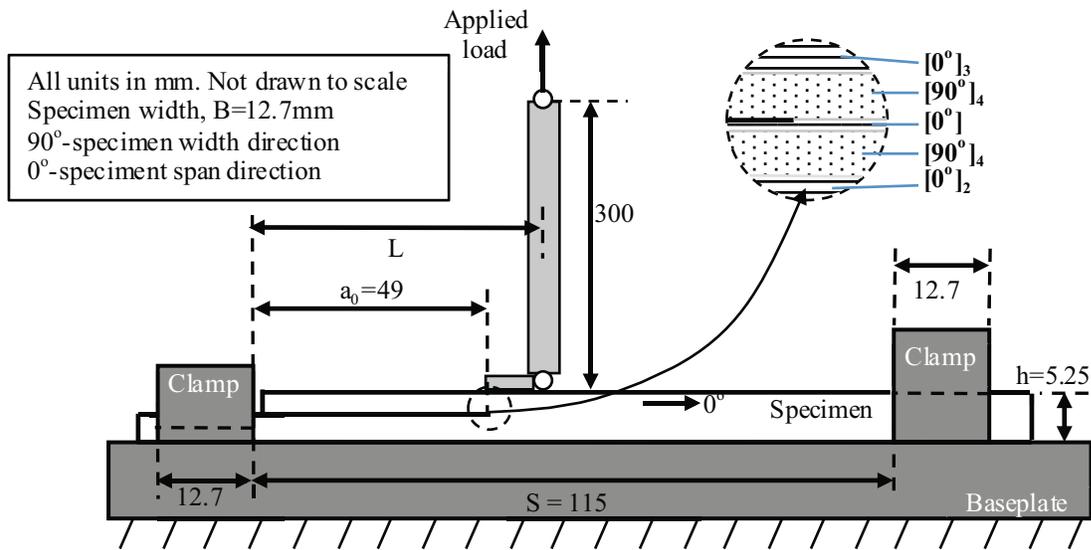


Figure 5. Schematic of delamination migration test configuration [7].



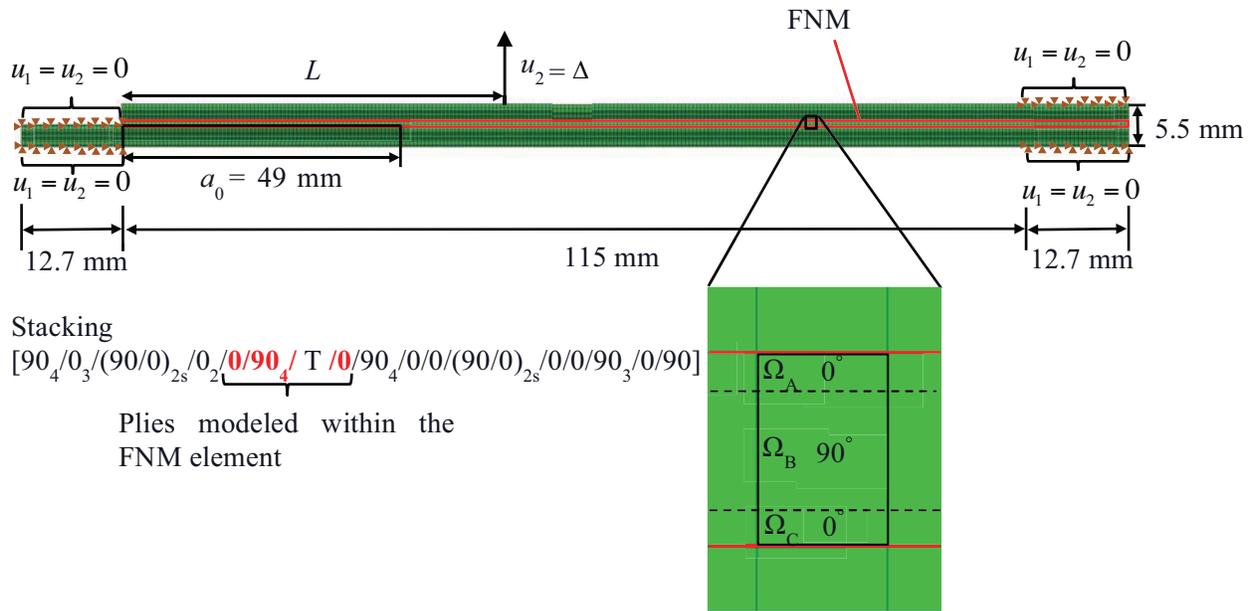



Figure 6. Finite element model, and boundary conditions of migration test specimen [7].

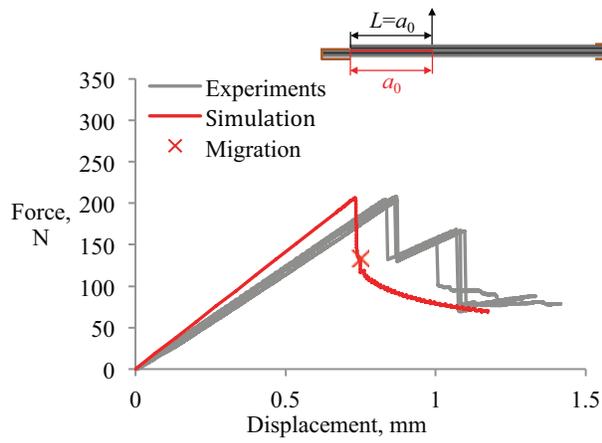


(a) load offset: $L = a_0$,

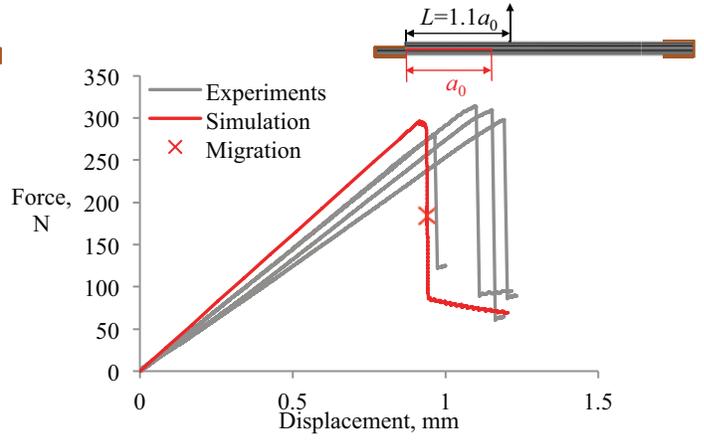

(b) load offset: $L = 1.1a_0$,

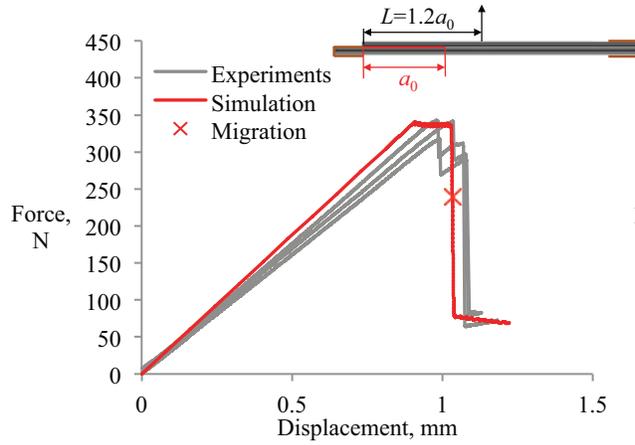


(c) load offset: $L = 1.2a_0$,

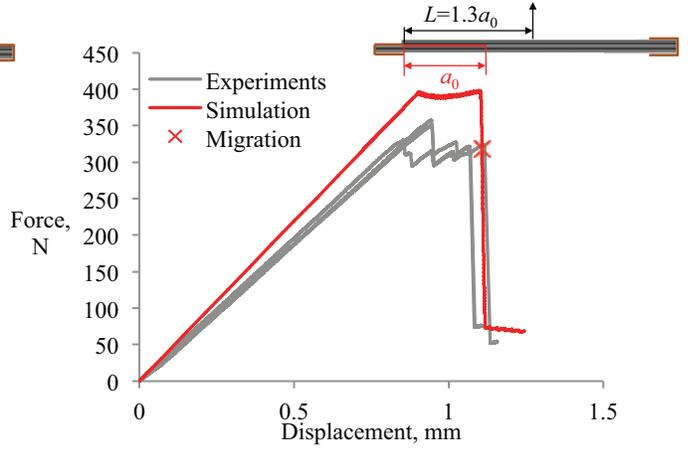

(d) load offset: $L = 1.3a_0$,

Figure 7. Experimental and predicted load-displacement plots.

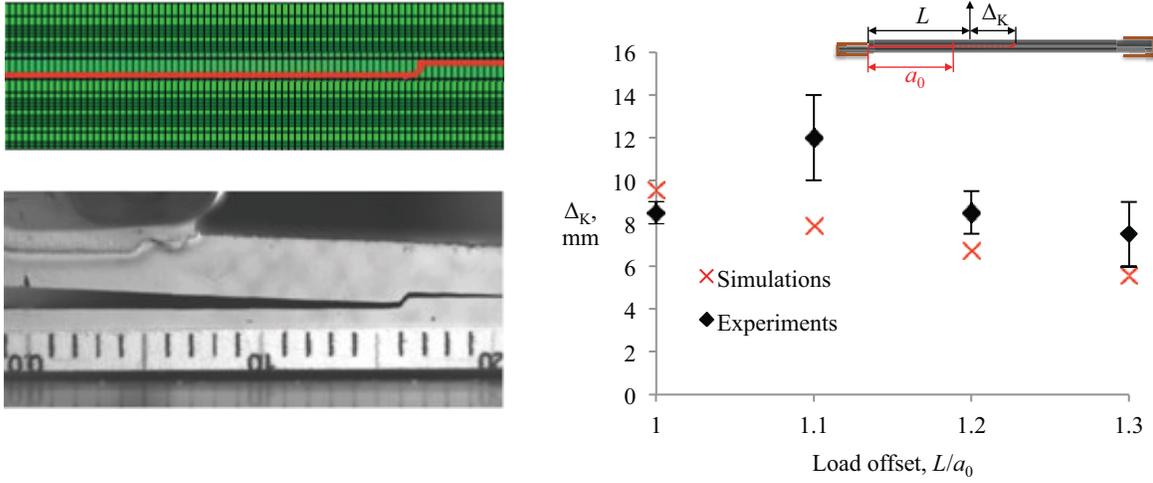

(a) qualitative comparison between simulated and experimental crack paths (b) variation of Δ_K with normalized load offset L/a_0

Figure 8. Crack path and migration location.

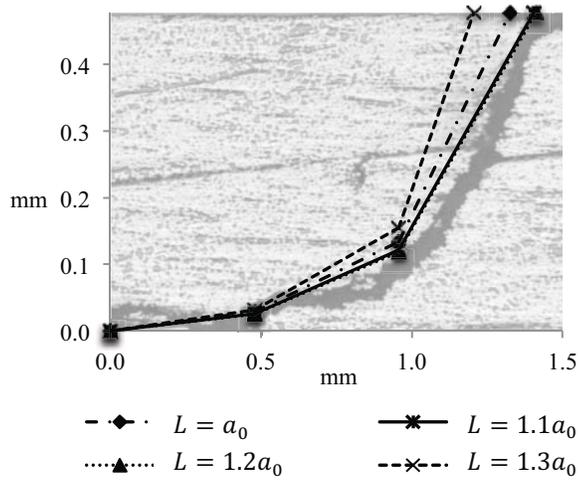


Figure 9. Comparison of experimentally observed crack path for $L = a_0$, and simulated crack paths for different load-offsets, L .

REPORT DOCUMENTATION PAGE

*Form Approved
OMB No. 0704-0188*

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.
PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.

| | | | | | |
|---|--------------------|--|-----------------------------------|--|--|
| 1. REPORT DATE (DD-MM-YYYY) 01-07-2013 | | 2. REPORT TYPE Contractor Report | | 3. DATES COVERED (From - To) | |
| 4. TITLE AND SUBTITLE Floating Node Method and Virtual Crack Closure Technique for Modeling Matrix Cracking-Delamination Interaction | | | | 5a. CONTRACT NUMBER | |
| | | | | 5b. GRANT NUMBER NNL09AA00A | |
| | | | | 5c. PROGRAM ELEMENT NUMBER | |
| 6. AUTHOR(S) De Carvalho, N. V.; Chen, B. Y.; Pinho, S. T.; Baiz, P. M.; Ratcliffe, J. G.; Tay, T. E. | | | | 5d. PROJECT NUMBER | |
| | | | | 5e. TASK NUMBER | |
| | | | | 5f. WORK UNIT NUMBER 031102.02.07.05.9D46.12 | |
| 7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) NASA Langley Research Center Hampton, Virginia 23681 | | | | 8. PERFORMING ORGANIZATION REPORT NUMBER | |
| 9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001 | | | | 10. SPONSOR/MONITOR'S ACRONYM(S) NASA | |
| | | | | 11. SPONSOR/MONITOR'S REPORT NUMBER(S) NASA/CR-2013-218022 | |
| 12. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category 24 Availability: NASA CASI (443) 757-5802 | | | | | |
| 13. SUPPLEMENTARY NOTES Langley Technical Monitor: Thomas K. O'Brien | | | | | |
| 14. ABSTRACT A novel approach is proposed for high-fidelity modeling of progressive damage and failure in composite materials that combines the Floating Node Method (FNM) and the Virtual Crack Closure Technique (VCCT) to represent multiple interacting failure mechanisms in a mesh-independent fashion. In this study, the approach is applied to the modeling of delamination migration in cross-ply tape laminates. Delamination, matrix cracking, and migration are all modeled using fracture mechanics based failure and migration criteria. The methodology proposed shows very good qualitative and quantitative agreement with experiments. | | | | | |
| 15. SUBJECT TERMS Composite materials; Crack closure; Delamination; Failure; Matrix cracking; Migration | | | | | |
| 16. SECURITY CLASSIFICATION OF: | | | 17. LIMITATION OF ABSTRACT | 18. NUMBER OF PAGES | 19a. NAME OF RESPONSIBLE PERSON |
| a. REPORT | b. ABSTRACT | c. THIS PAGE | | | STI Help Desk (email: help@sti.nasa.gov) |
| U | U | U | UU | 22 | 19b. TELEPHONE NUMBER (Include area code) (443) 757-5802 |