Polymer and Nano-Material Research in the Polymers Branch at NASA Glenn Research Center

SERMACS 2011

October 26th – 28th

Richmond, VA

Sandi Miller, Marisabel Lebrón-Colón, Tiffany Williams, and Michael Meador

Polymers Branch

Structures and Materials Division

NASA Glenn Research Center

Cleveland, OH. 44135

Future Exploration Mission Requirements Cannot Be Met with Conventional Materials

Satellites and rovers

- Reduced mass and volume
- Reduced power requirements
- Increased capability, multifunctionality

Vehicles and habitats

- Reduced mass
- High strength
- Thermal and radiation protection
- Self-healing, self-diagnostic
- Multifunctionality
- Improved durability
- Environmental resistance (dust, atmosphere, radiation)

EVA Suits

- Reduced mass
- Increased functionality and mobility
- Thermal and radiation protection
- Environmental resistance

RXP Nanomaterials Research

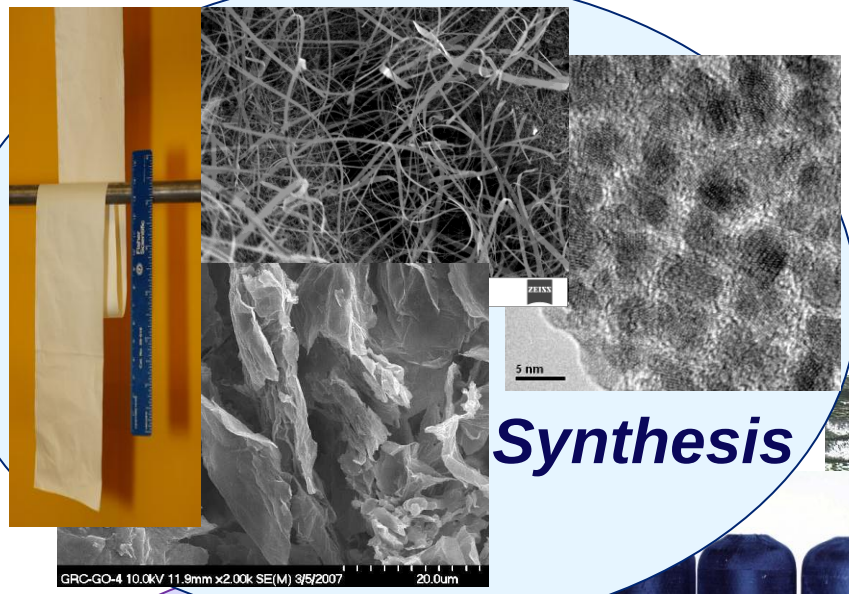

Synthesis

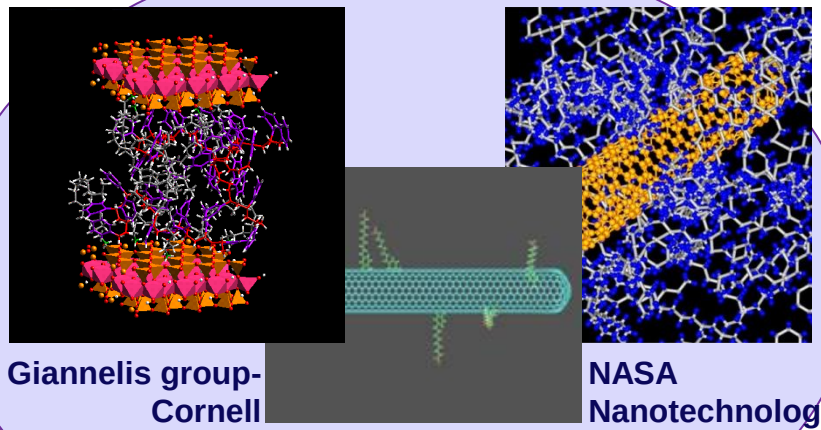

Giannelis group-Cornell

NASA Nanotechnology Gallery

Functionalization

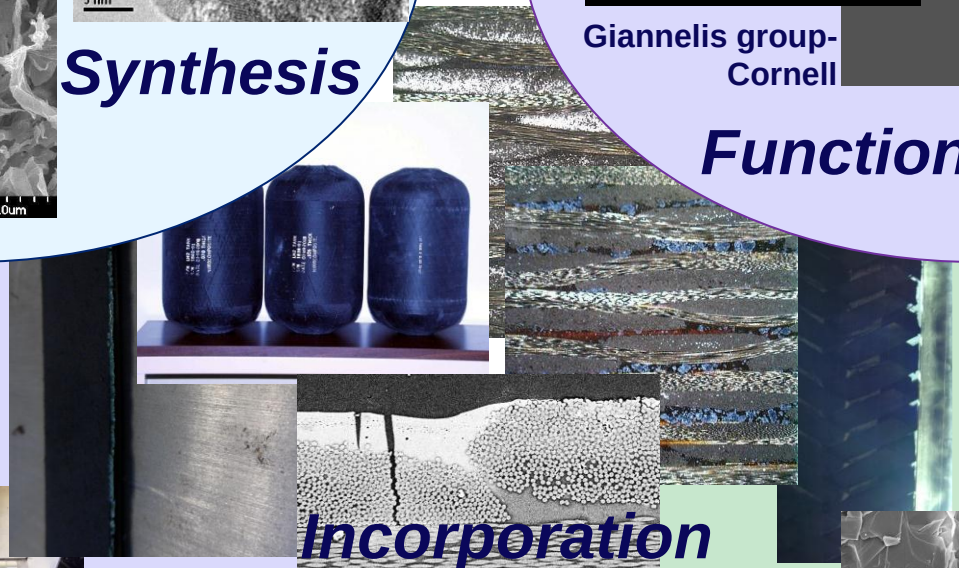

Incorporation into Composite Structures

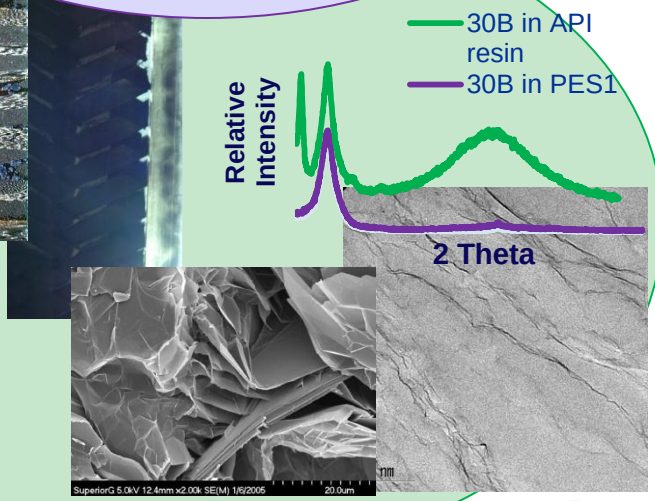

Dispersion/Processing

Characterization

Outline

- Nanocomposites for Highly Loaded Structures
- Nanocomposites for Cold Temperature Applications (cryogen storage)
- Nanocomposites for High Temperature Applications (300°C)

Composite Fan Blade

Goal: Enable Reduced Blade Thickness through Improved Composite Fracture Toughness and Interlaminar Strain

Approach:

1. Investigate the influence of a wide range of nanoparticles on epoxy toughness.
2. Design materials to best utilize the various nanoparticles.

Composite Fan Blades
Background

Materials:

Epon 826



Araldite DY3601



Jeffamine D230

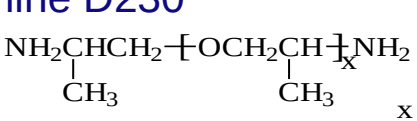

- Tensile strength and ductility are improved when nano-particles can align in the direction of applied load.
- Pre-dispersion forces clay into the more mobile components of the resin.

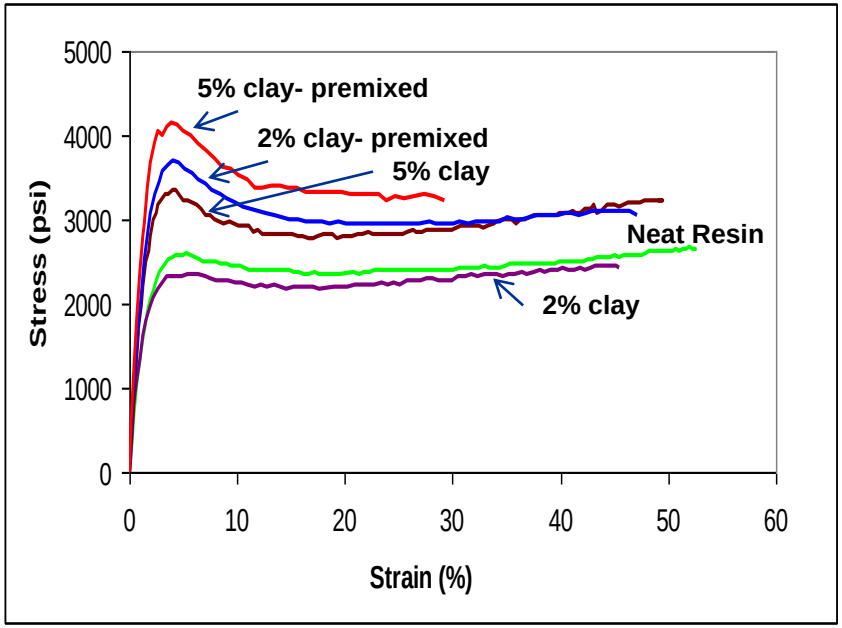

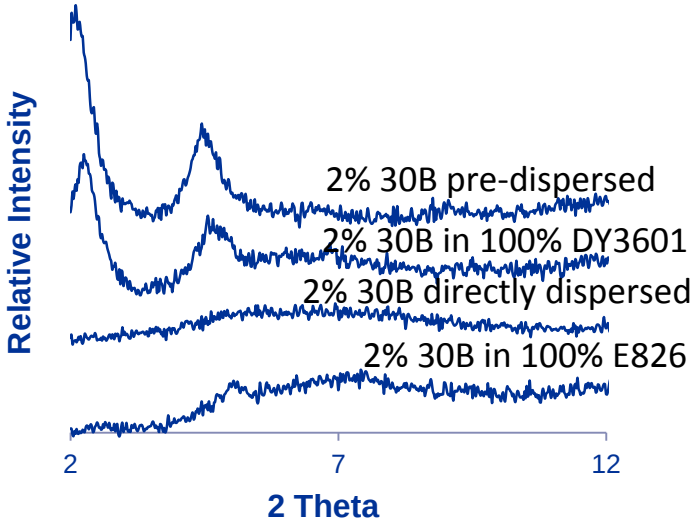

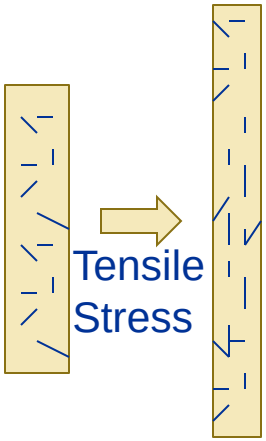

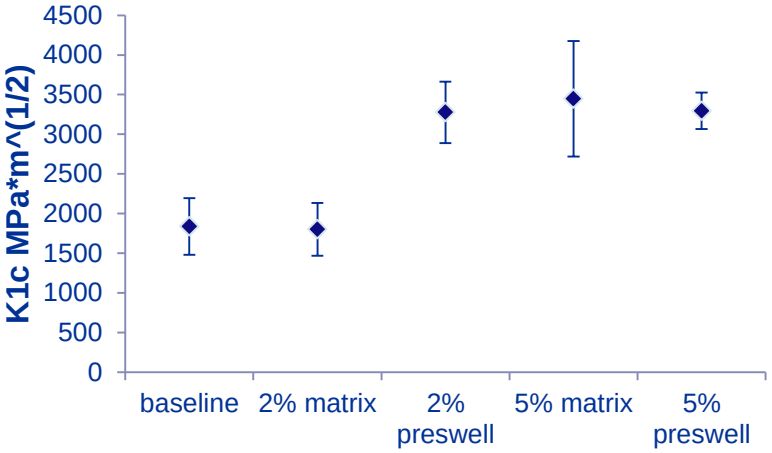

Strain in Un-Toughened Epoxy-Clay Nanocomposites

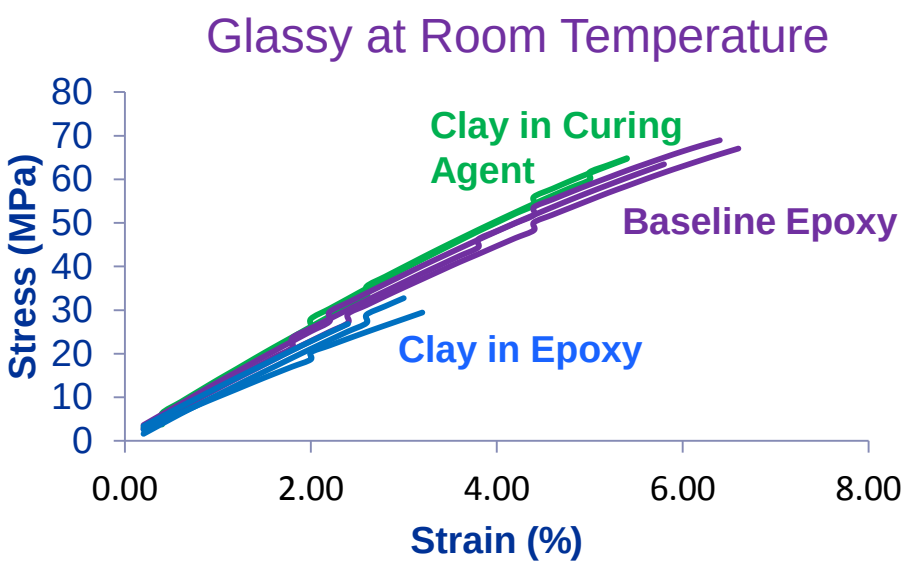

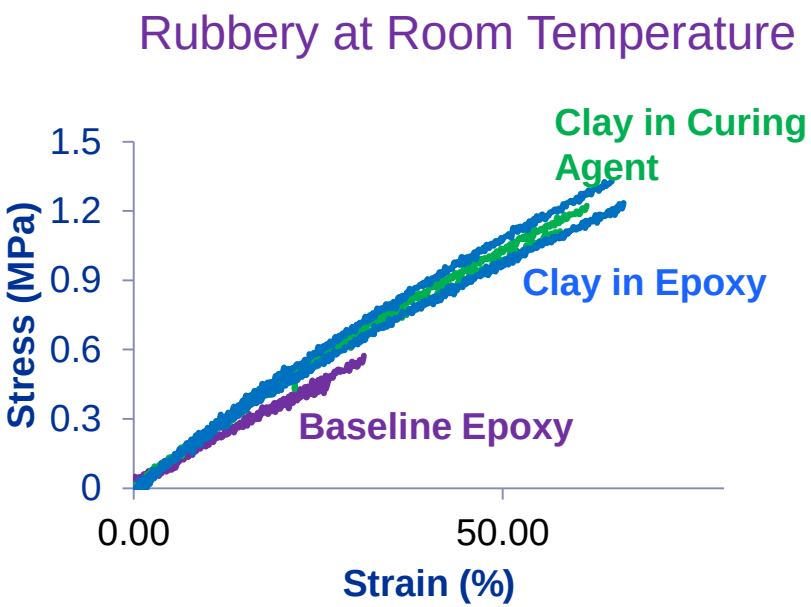

Nanocomposites Based on Aerospace Grade Epoxies

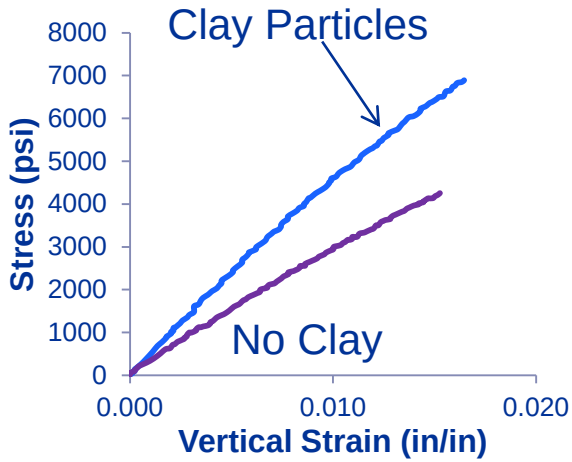

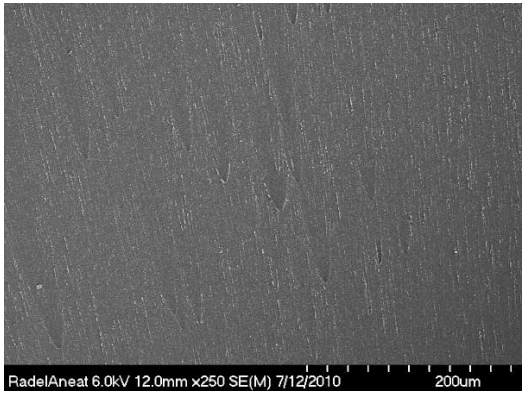

Fracture surface of nano-reinforced samples indicate increased material toughness

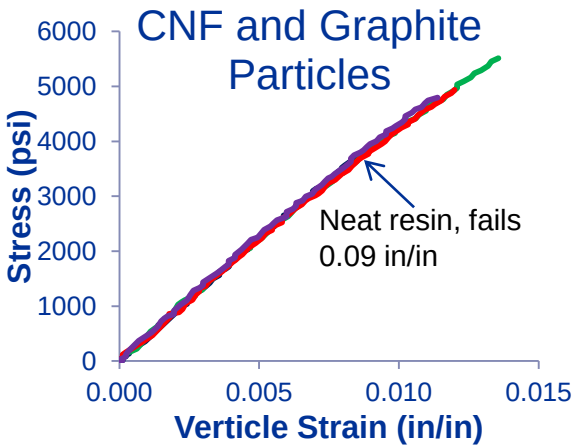

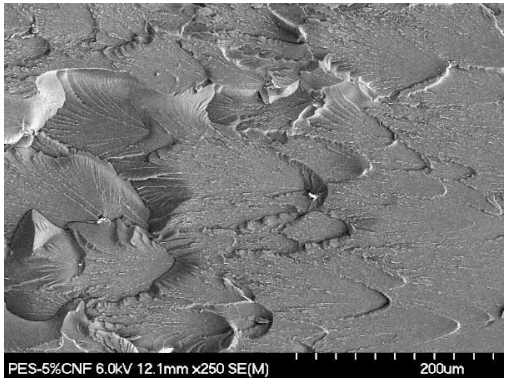

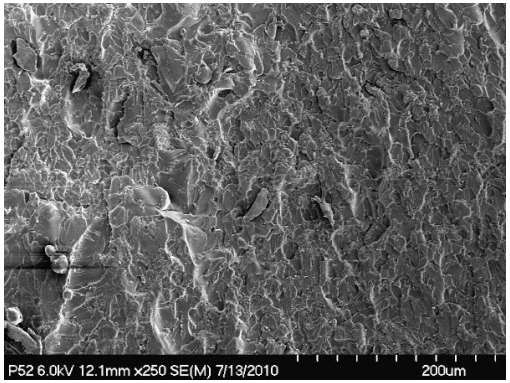

Graphite particles were epoxy functionalized via solvent-based wash. CNF particles were not functionalized.

Composite Structures

1. Epoxy Nanocomposite film laid up with between plies of base laminate.
2. Autoclave cured using vendor recommended cure cycle
3. Characterized for panel quality
   1. C-scan
   2. Acid Digestion
   3. Optical Microscopy
4. Mechanical Testing

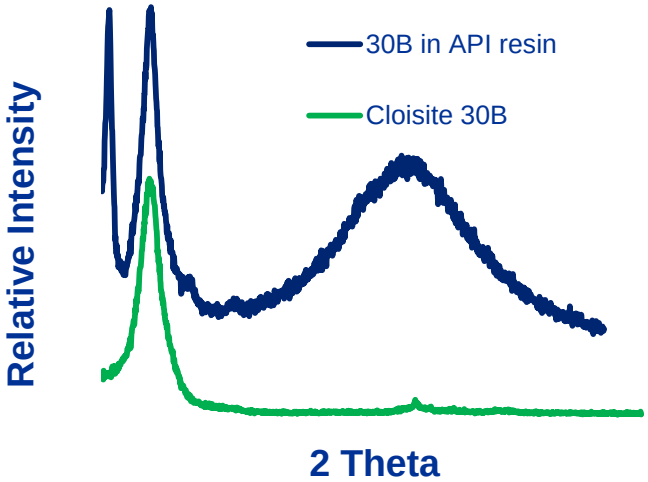

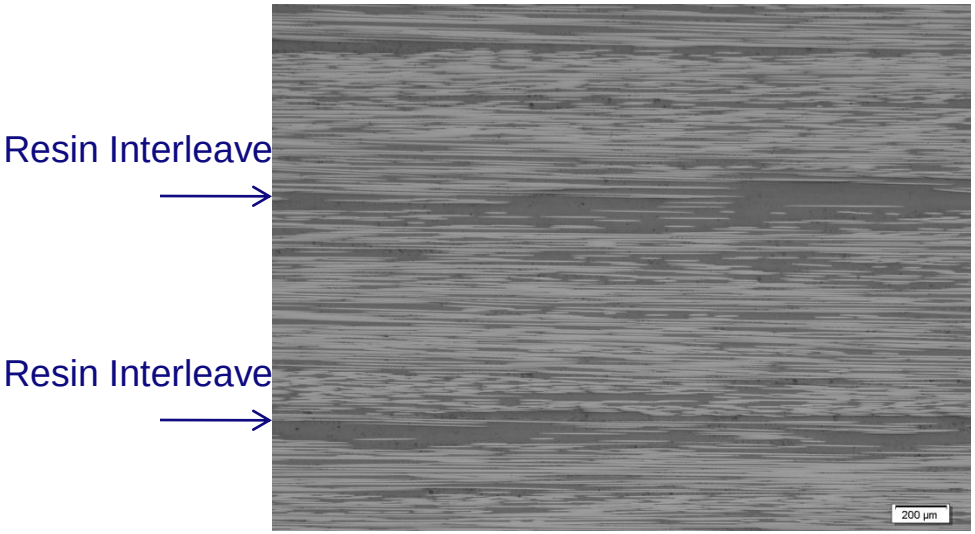

Photomicrograph of SBS test coupon, $[0]_{16}$ lay-up, along fiber direction

Composite Testing: Thermal and Mechanical

Testing Results

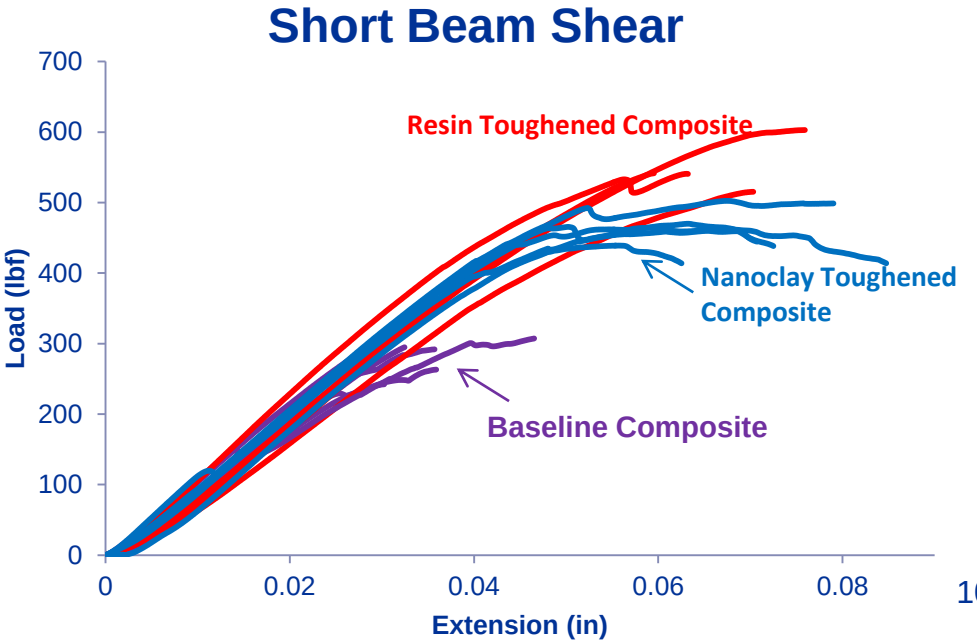

Nanoclay interleave shows drop in short beam shear strength, but comparable or improved ductility

Little difference in dynamic mechanical data.

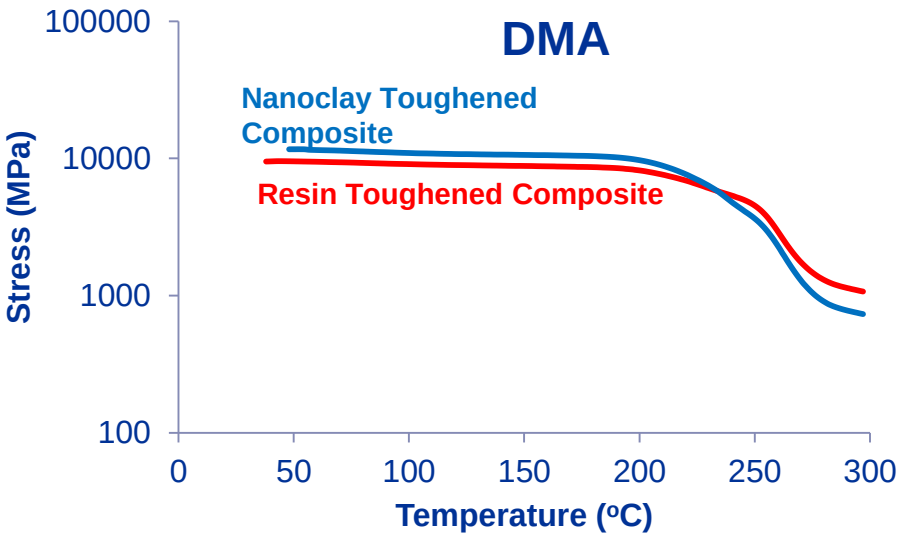

Next Steps - Improved Nano-Incorporation

- Need Better Dispersion
  - Do not have the facilities to handle this scale of dispersion.
  - Contract in place with Nanosperse to aid in dispersion

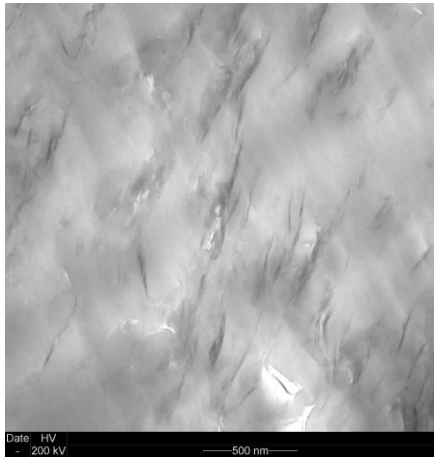

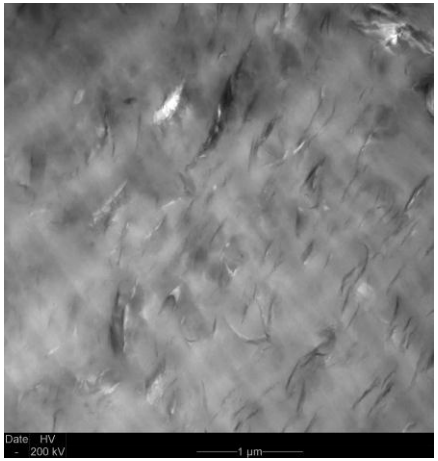

- Exploring Alternative Mechanisms to Include Nanoparticles
  - Purchases in place with Nanocomp to incorporate CNT sheets
  - Working with North Carolina A&T University to electro-spin PES for interleave material.

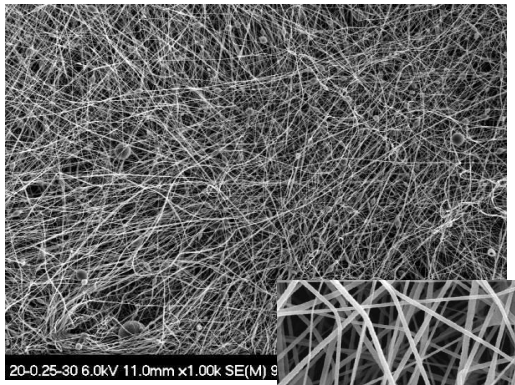

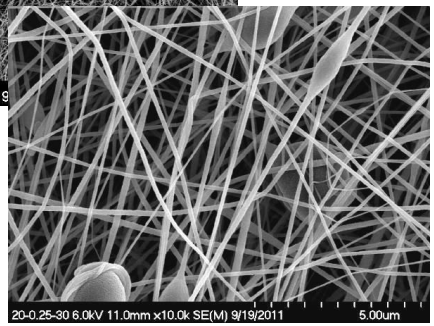

Composite Tanks

Goal: Reduce Permeation through Composite

- The majority of this effort has focused on clay nanoparticles.
- Reduced material permeability following nanoclay dispersion is well documented.
- Expected that the platelet structure of clay contributes to the improved barrier performance.

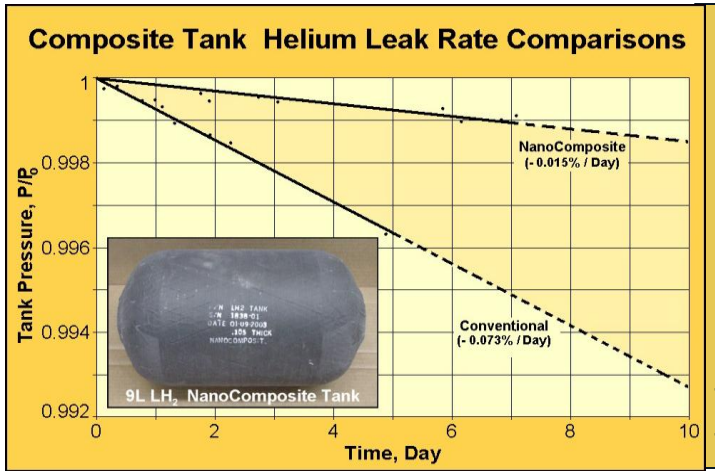

5% clay in epoxy matrix lead to a 70% reduction in helium leak rate compared to the baseline tank.

Clay layer dispersion and alignment, with respect to the permeation direction, greatly influence the barrier performance of the matrix

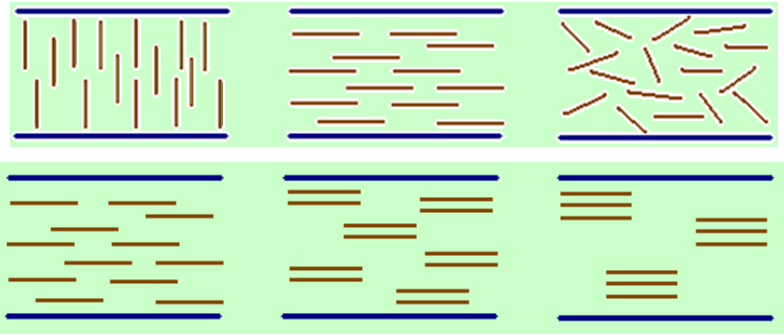

Bharadwaj, R.K. *Macromolecules* 2001, *34*, 9189

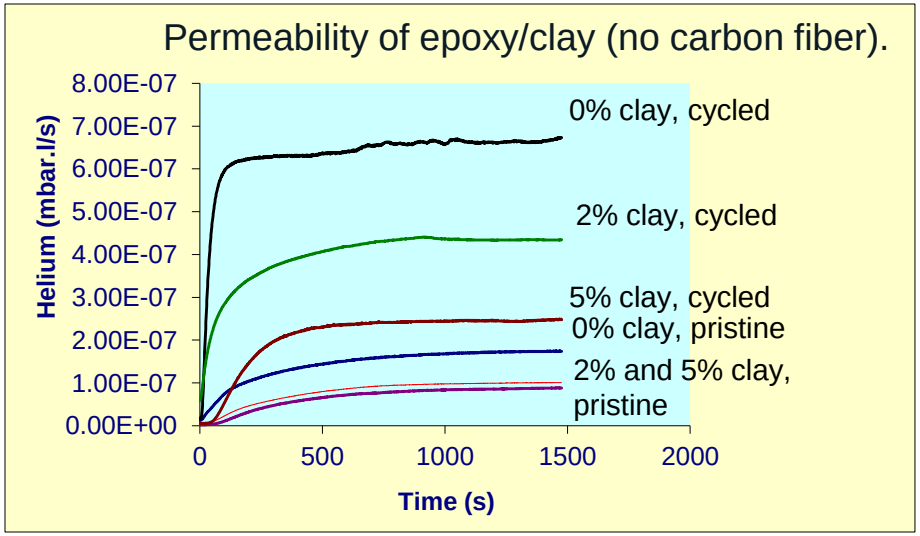

High Temperature Polymer Nanocomposites

Goal: Improve High Temperature Durability of Matrix Resin

Elevated PMR-15 processing temperatures led to development of unique nanoclay modifier.

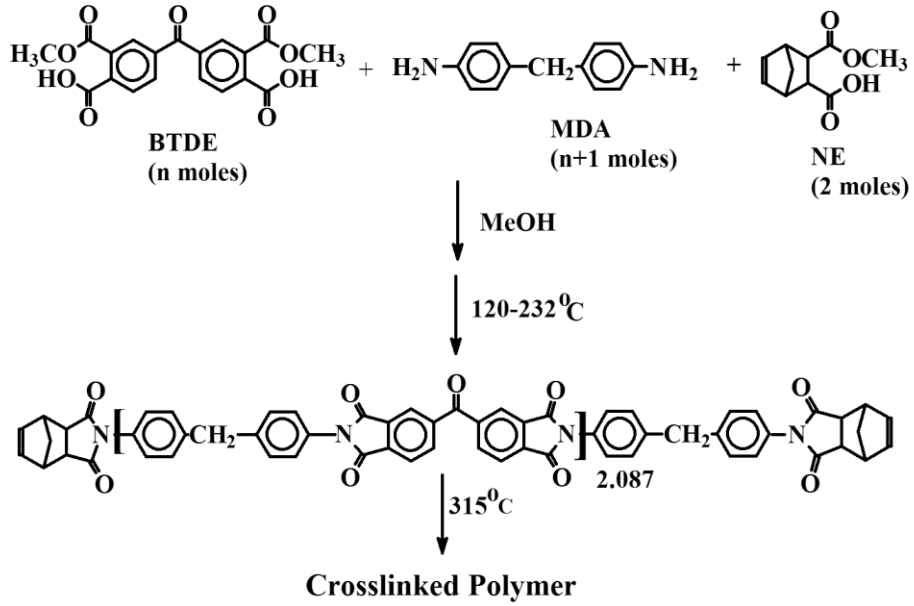

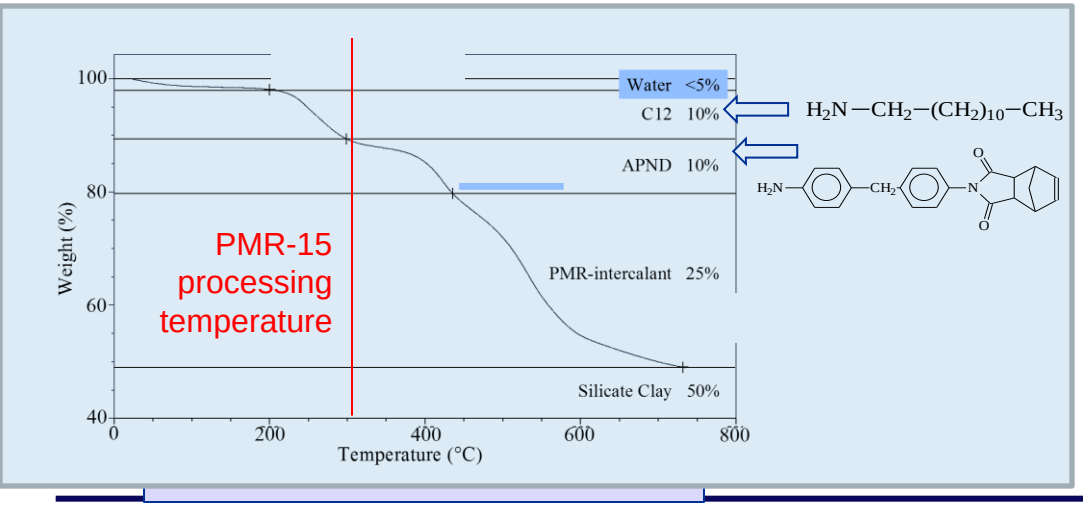

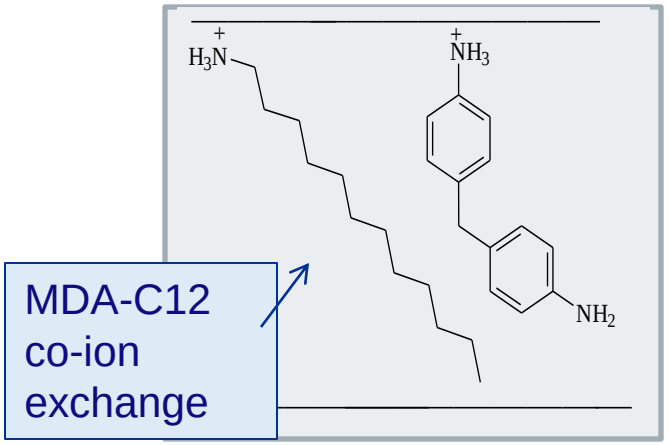

Thermal and Physical Properties of PMR-15/Clay Nanocomposites

Silicate	PGV-(MDA-C12)	PGV-C12
0%	**335**	**335**
1%	336	337
3%	340	326
5%	337	321
7%	338	311

- Glass transition temperature was maintained with increased clay loading.
- Weight loss with thermal aging reduced with increased clay loading.
- Oxygen permeation through nanocomposite reduced compared to baseline material.

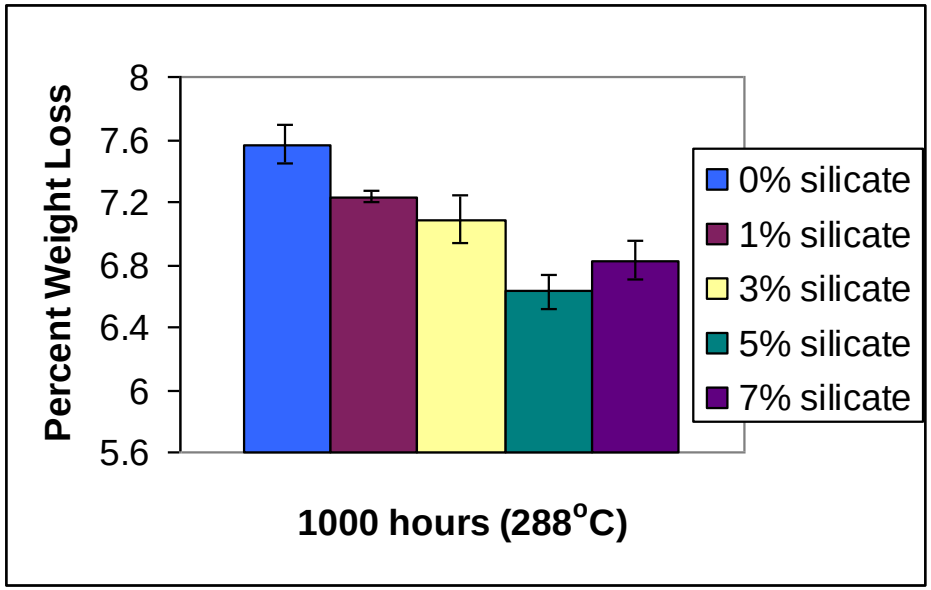

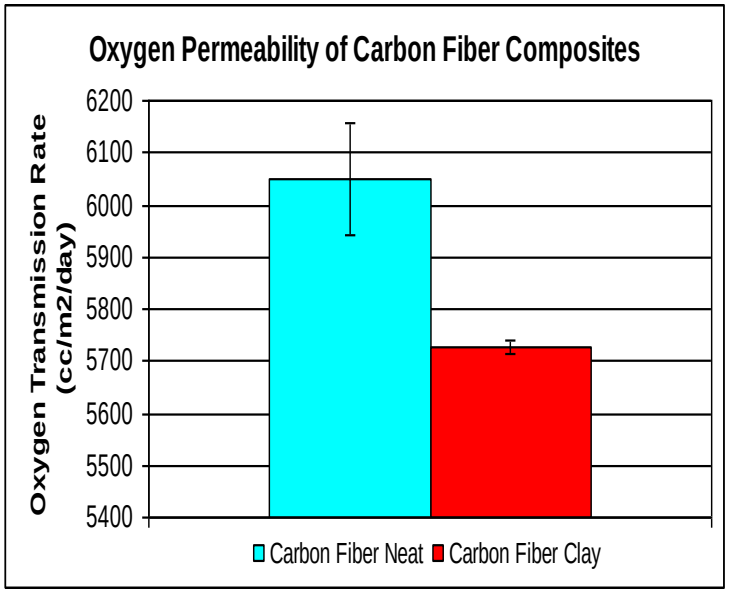

High Temperature Polymer Nanocomposites

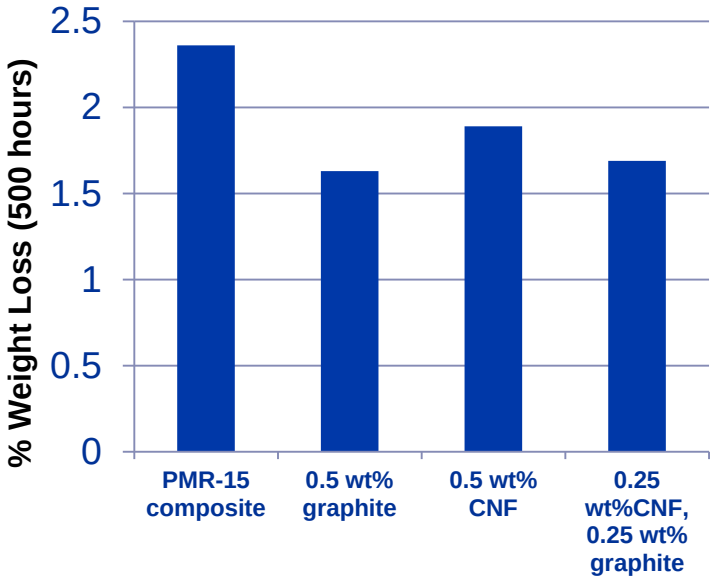

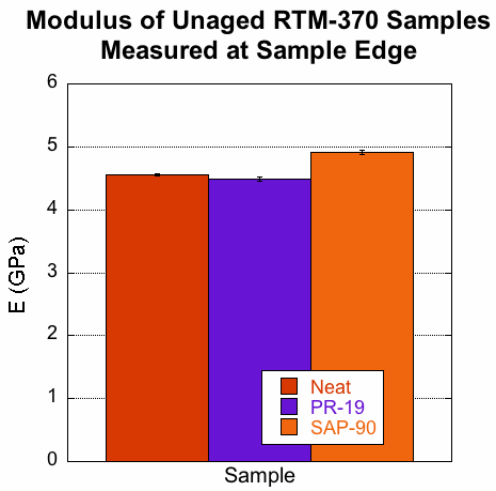

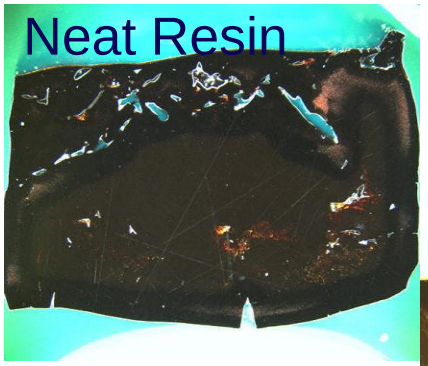

CNF dispersion results in weight loss comparable to clay

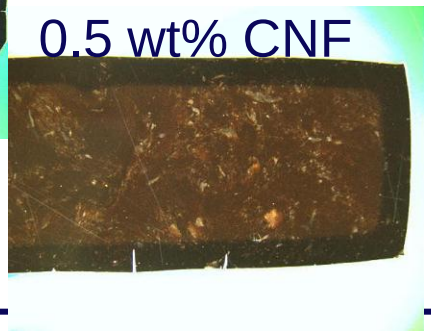

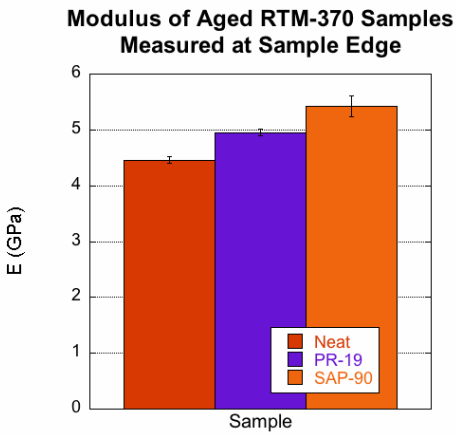

Carbon Nanotube Efforts- Focus on Functionalization

SWCNTs Non-Covalent Functionalization

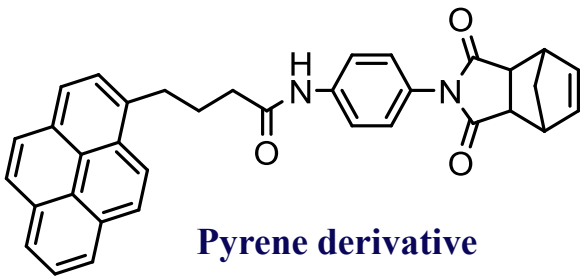

Pyrene derivative

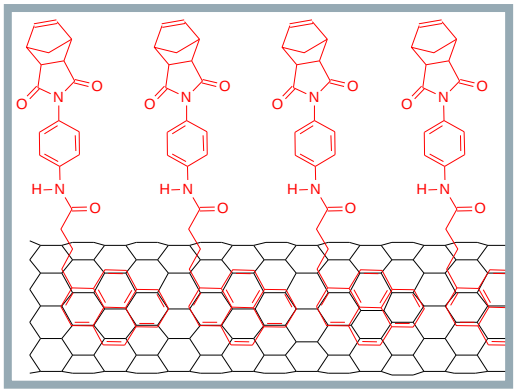

Schematic illustration of the SWCNTs/Pyrene complex

FT-IR

TGA

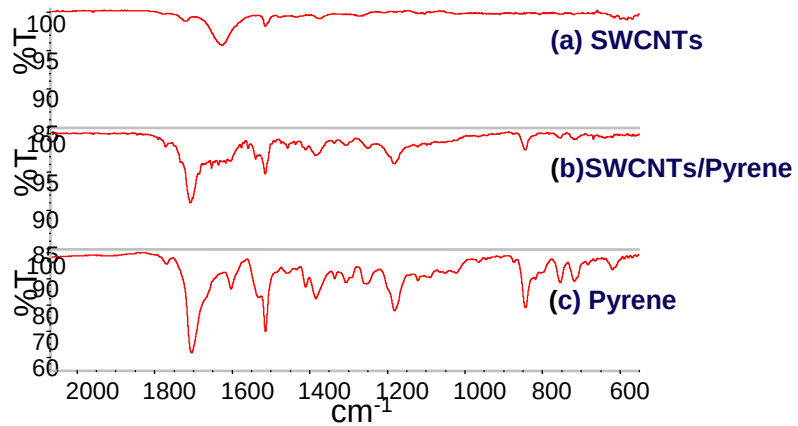

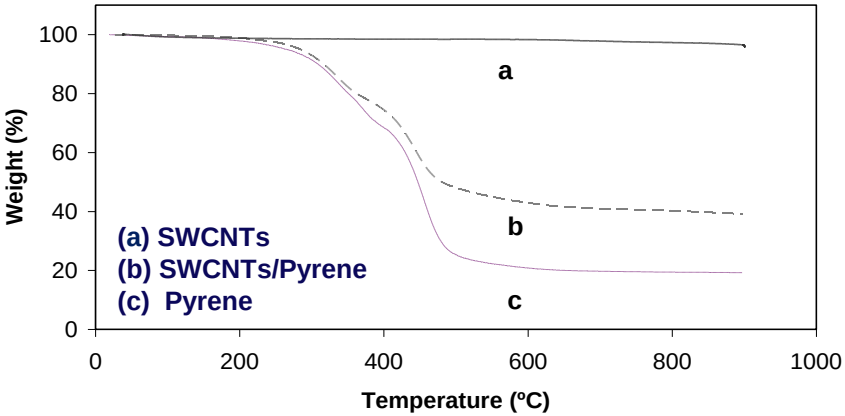

SWCNTs Non-Covalent Functionalization



SWCNTs

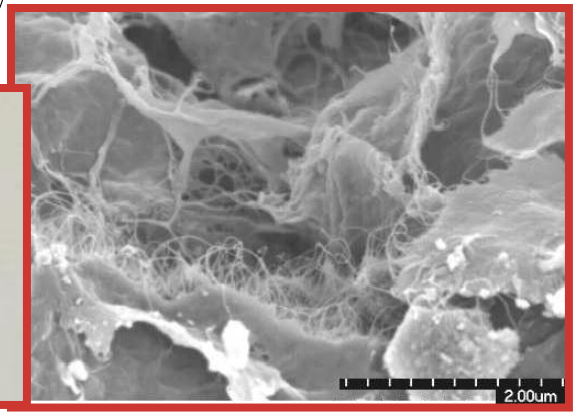

Agglomeration of SWCNTs is clearly visible in the SEM image of the SWCNT nanocomposite film.

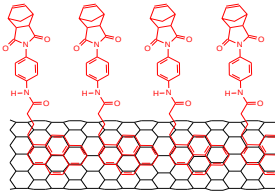

SWCNTs complex

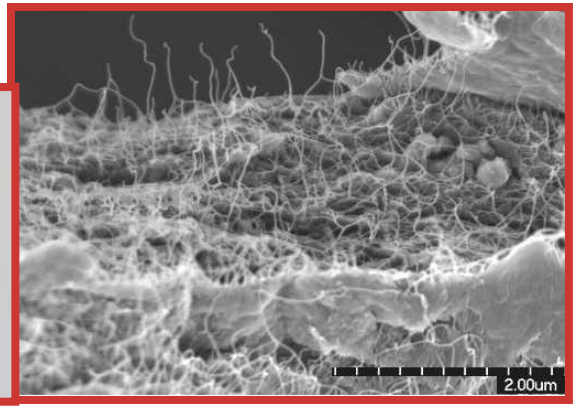

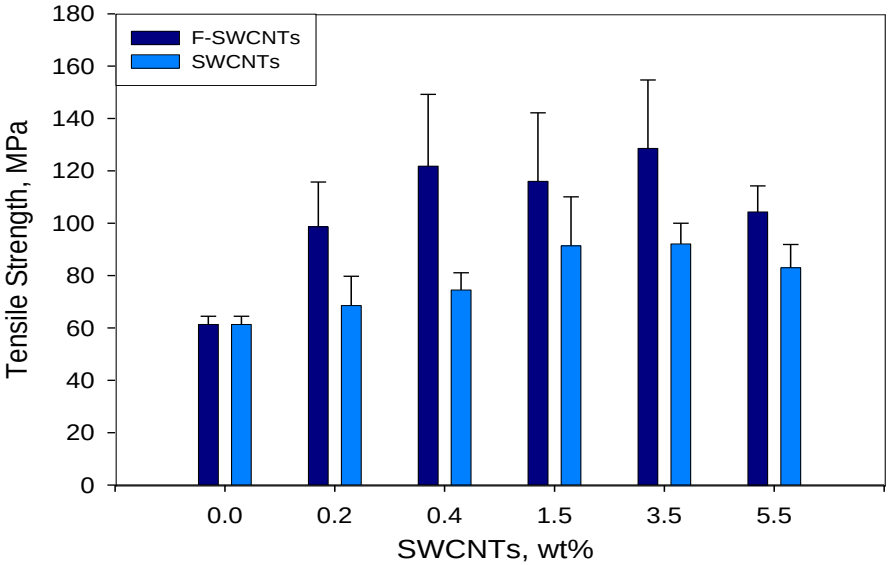

The addition of 3.5 wt% SWCNT/complexes increased the tensile strength of the polyimide from 61.4 to 129 MPa; higher loading levels led to embrittlement and lower tensile strengths

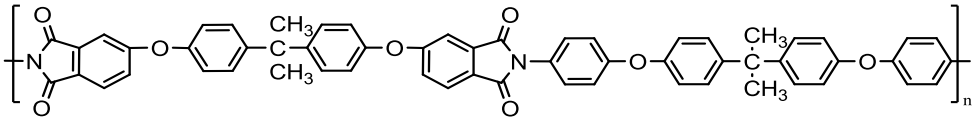

BPADA/BAPP

Complexes form stable colloidal dispersion in polar solvents –enables production of homogeneous polymer films.

Results: Photo-Oxidation of SWCNTs

- The oxygen content of the SWCNTs (i.e., photo-oxidation, acid treatment) has been studied by X-ray photoelectron spectroscopy (XPS).
- **Photo-oxidation adds nearly 2X the oxygen to the SWNTs than acid treatment alone.**

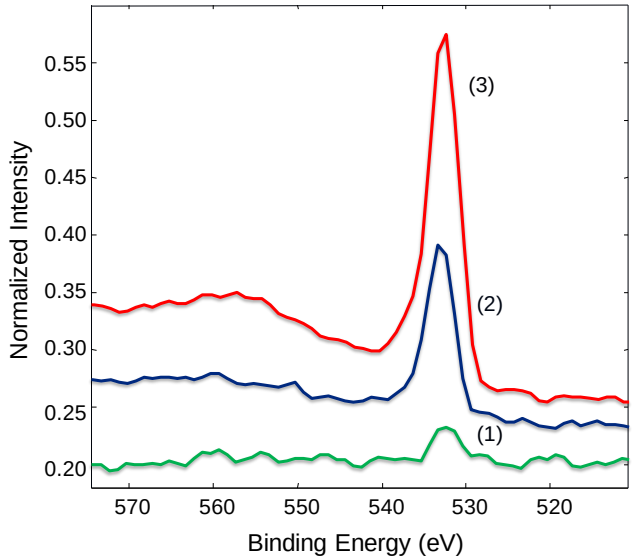

(a)

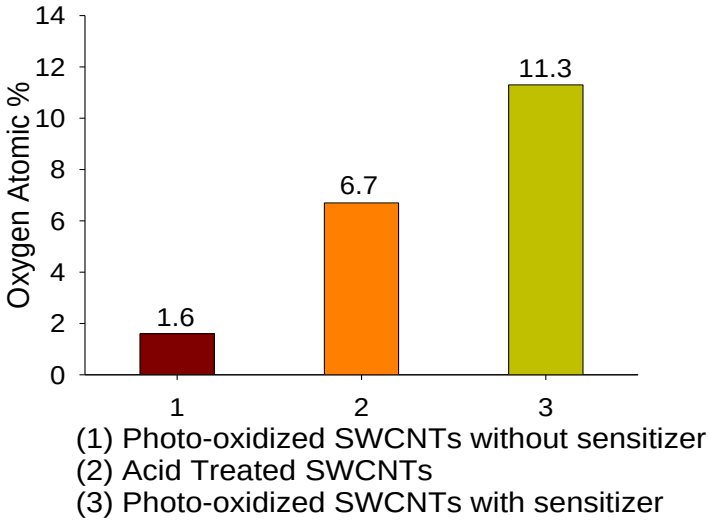

(b)

(a) Overlay of oxygen peaks from the survey scan after normalizing the carbon peaks.
(b) Oxygen concentration of SWCNTs oxidized by photo-oxidation (with and without sensitizer) and by acid treatment.

Results: Photo-Oxidation of SWCNTs

- XPS is sensitive to matrix effects and is able to provide both oxidation and chemical state information about the elements detected.
- An overlay of all of the carbon regions after normalization revealed the presence of a shoulder on the main carbon peak (284.8 eV) of the photo-oxidized
- Peaks at 286.3 eV, 287.9 eV, and 289.3 eV are indicative of C-O, C=O, and O-C=O, respectively.
- Analytical characterizations by FT-IR also confirmed the presence of oxygen groups.

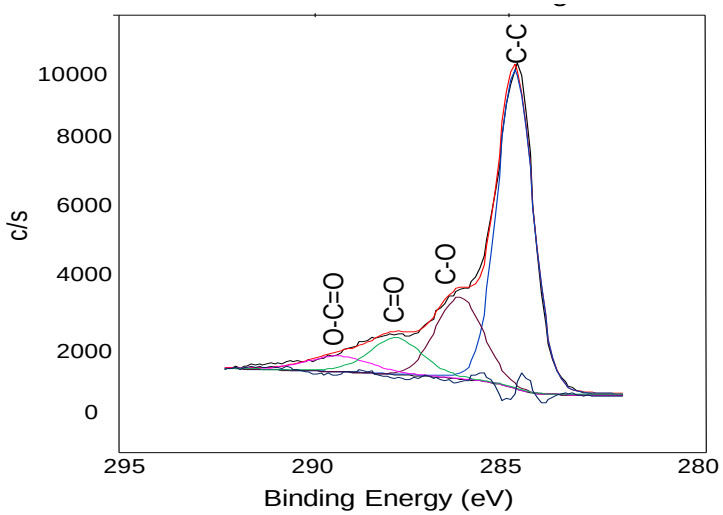

XPS: Curve-fitting of the carbon region of the photo-oxidized SWCNTs with RB.

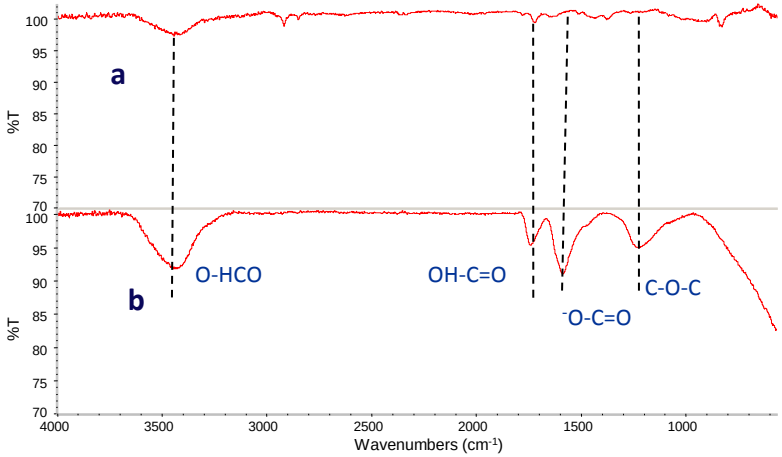

FT-IR: (**a**) SWCNTs and (**b**) photo-oxidized SWCNTs.

.

Additional Nanomaterials Efforts

- Magnetic nanoparticle synthesis and dispersion
- Nanoparticle influence on shape memory polymer
- Nanoparticle modified carbon fibers
- Boron Carbide Nanotube materials (radiation shielding)
- Graphene nanocomposites for improved electrical conductivity.